

Student Scholarship

---

Summer 2021

## Surface Energy and Microstructure: The Effect of the Underlying Substrate on Perovskite Film Formation for Solar Cell Absorbers

Mirra M. Rasmussen

*Case Western Reserve University, mmr125@case.edu*

Kyle M. Crowley

*Case Western Reserve University*


Ina T. Martin

*Case Western Reserve University, ixm98@case.edu*

Author(s) ORCID Identifier:

 Mirra M. Rasmussen

Follow this and additional works at: <https://commons.case.edu/studentworks>

 Part of the [Semiconductor and Optical Materials Commons](#)

---

### Recommended Citation

Rasmussen, Mirra M.; Crowley, Kyle M.; and Martin, Ina T., "Surface Energy and Microstructure: The Effect of the Underlying Substrate on Perovskite Film Formation for Solar Cell Absorbers" (2021). *Student Scholarship*. 12.

<https://commons.case.edu/studentworks/12>

This Poster is brought to you for free and open access by Scholarly Commons @ Case Western Reserve University. It has been accepted for inclusion in Student Scholarship by an authorized administrator of Scholarly Commons @ Case Western Reserve University. For more information, please contact [digitalcommons@case.edu](mailto:digitalcommons@case.edu).

CWRU authors have made this work freely available. [Please tell us](#) how this access has benefited or impacted you!



## Introduction & Background

### Pb-Based Perovskite Films as an Emerging PV Absorber


Record devices are over 20% efficient but there are materials problems that need to be solved [1].

Interfacial modification affects:


- Film uniformity
- Crystallinity
- Grain size
- Defect density

Small molecule modifiers and their positive effects on device performance. Data from references [2] and [4].

Modifier	Stack Structure	V <sub>oc</sub> [V]	J <sub>sc</sub> [mA cm <sup>-2</sup> ]	PCE [%]
Bromobenzoic Acid (Br-BA) [2]	ITO/NiO <sub>x</sub> /MAPbI <sub>3</sub> /PCBM/bis-C <sub>60</sub> /Ag	1.07	19.1	15.3
	ITO/NiO <sub>x</sub> /Br-BA/MAPbI <sub>3</sub> /PCBM/bis-C <sub>60</sub> /Ag	1.11	21.7	18.4
(3-Aminopropyl) triethoxysilane (APTES) [4]	FTO/SnO <sub>2</sub> /MAPbI <sub>3</sub> /Spiro-OMeTAD/Au	1.065	20.84	14.69
	FTO/SnO <sub>2</sub> /APTES/MAPbI <sub>3</sub> /Spiro-OMeTAD/Au	1.16	21.23	17.03

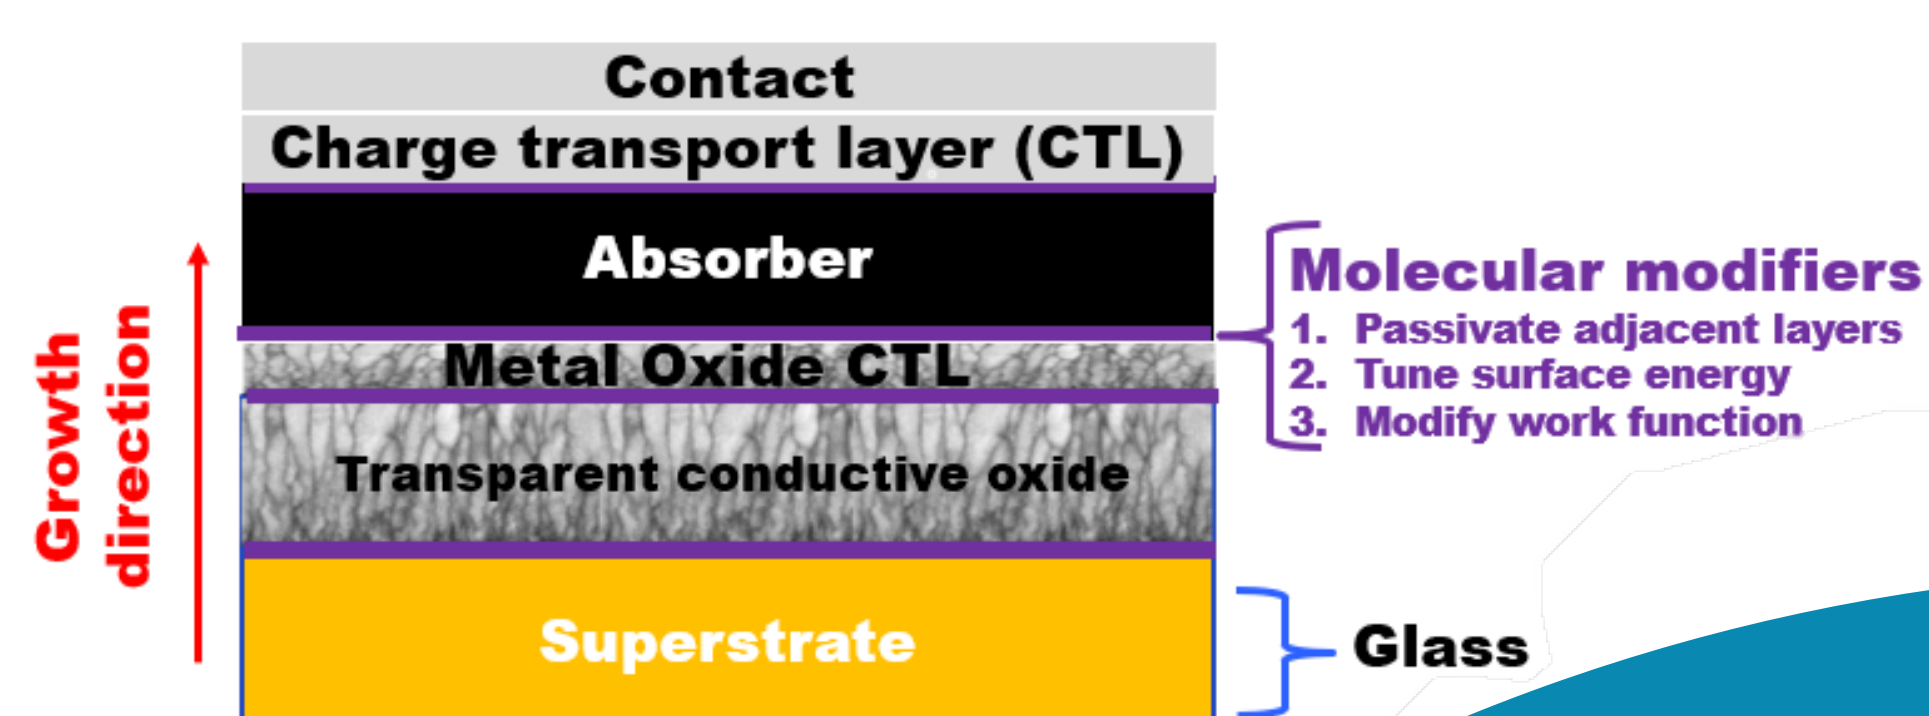

**Goal:** Improve stability of perovskite absorbers through small molecule modification of perovskite-TCO interface.

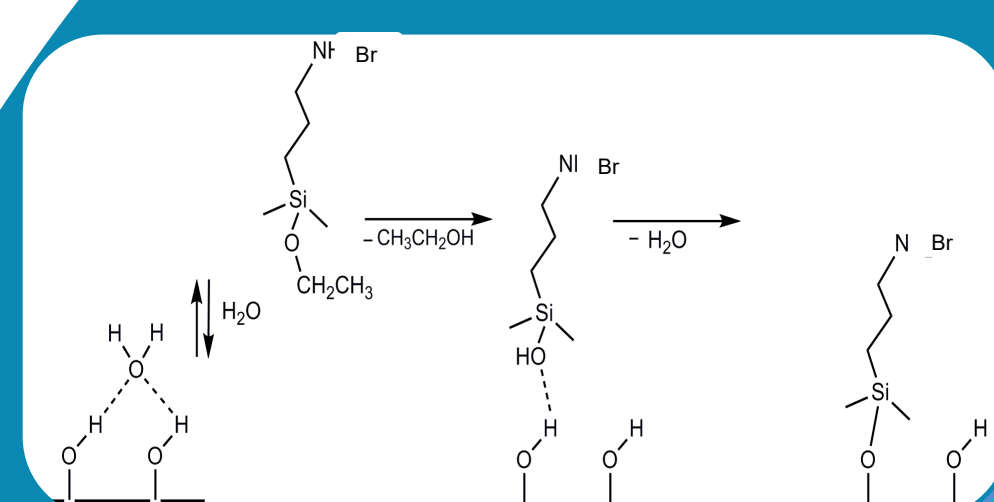


Device properties and performance are directly tied to perovskite film properties [3].


## Interfacial Modification and Stability

### BPTMS and MAPbI<sub>3</sub> Grain Growth

- BPTMS leads to growth of smaller grains on ITO
- MAPbI<sub>3</sub> grains on s-ITO comparable in size to those grown on glass

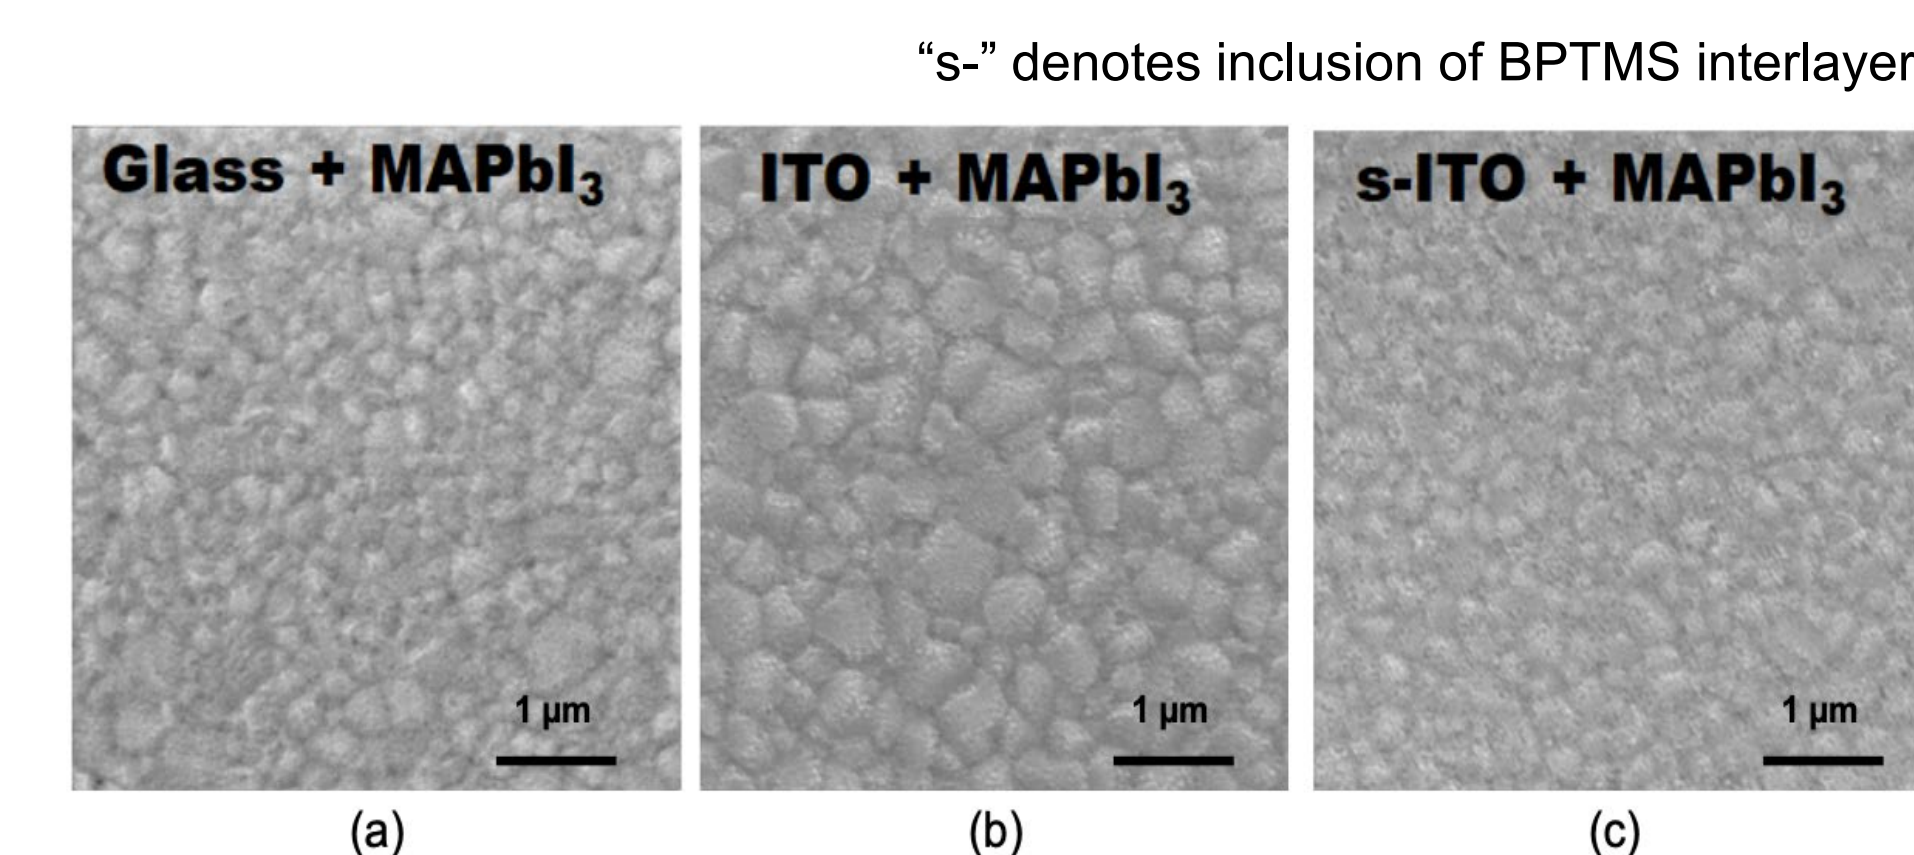


**Results:** BPTMS passivates the perovskite-TCO interface, affecting both the film morphology and degradation profile of the perovskite.

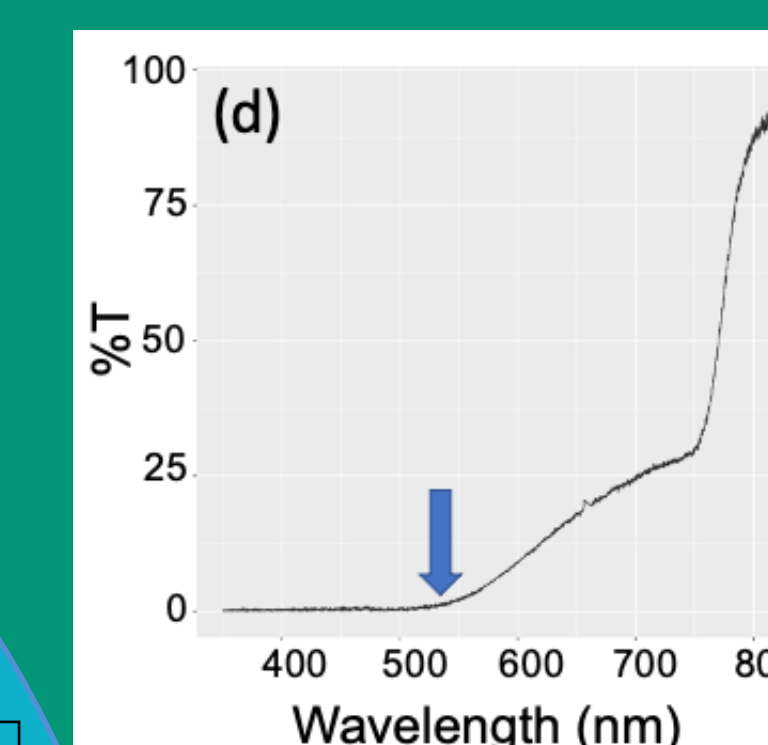

UV-Vis spectrum of MAPbI<sub>3</sub> on s-ITO.

### BPTMS and MAPbI<sub>3</sub> Degradation




- BPTMS mitigates MAPbI<sub>3</sub> degradation on ITO (in green) compared to the unmodified control (in red)
- Decouples effects of grain size from interfacial chemistry in terms of stability

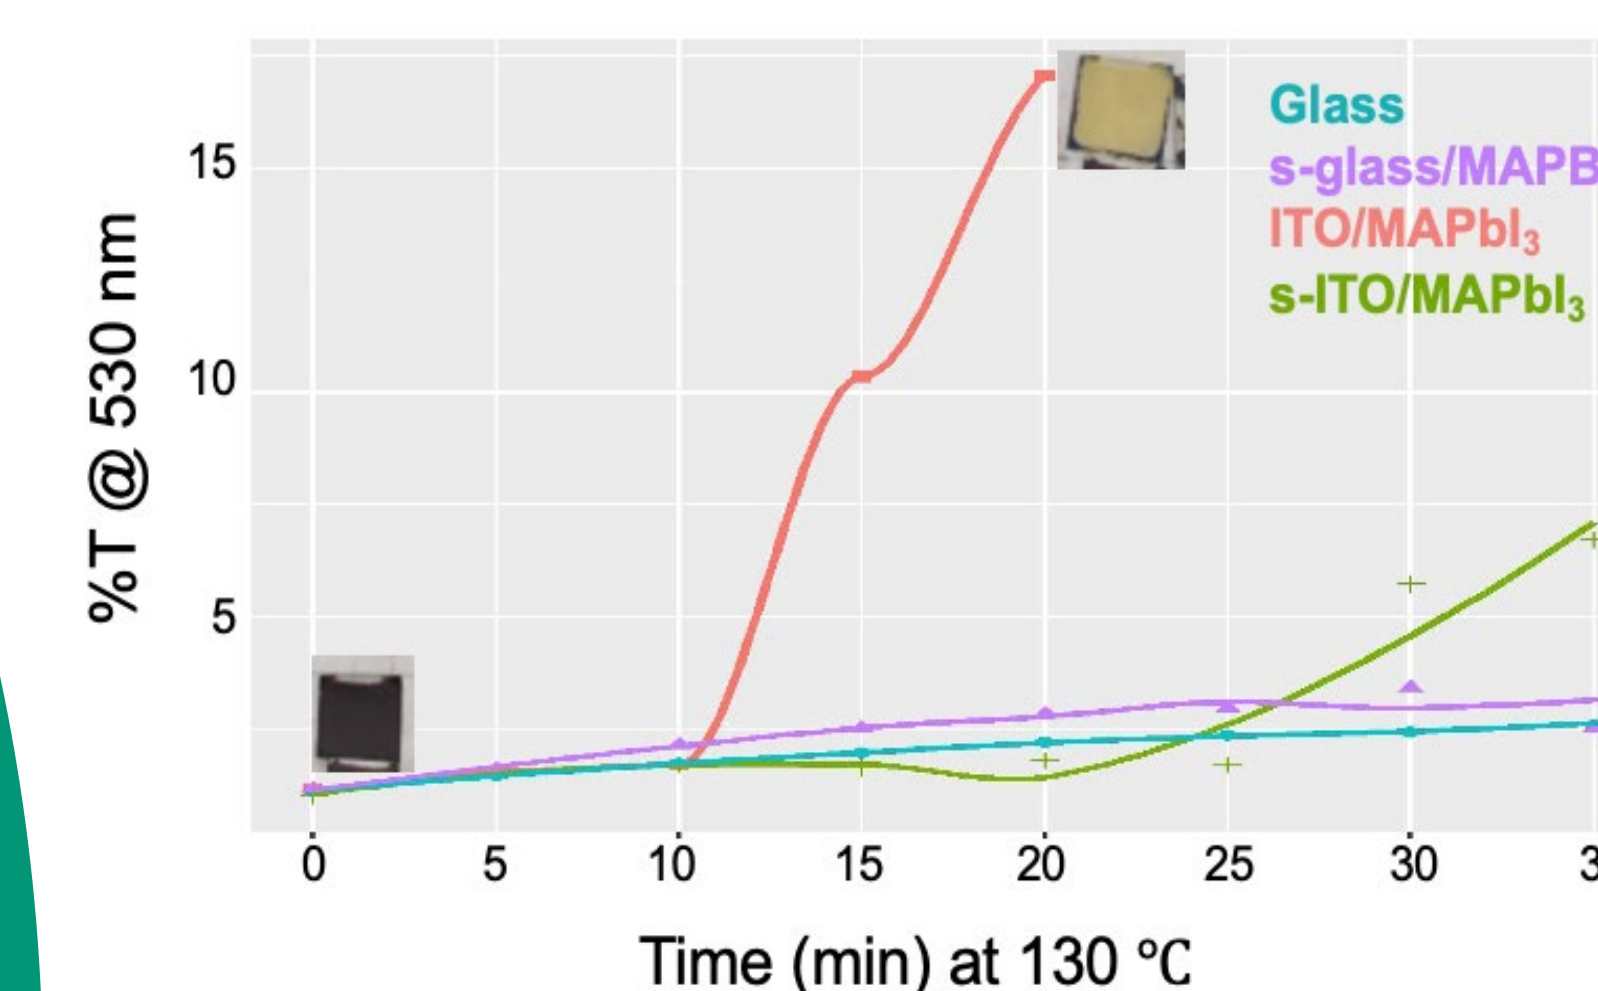


## Materials Design for Reliability

### Materials Synthesis & Characterization

### Device Fabrication & Optimization

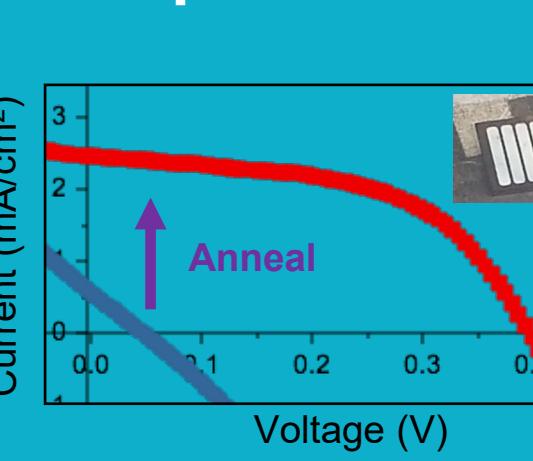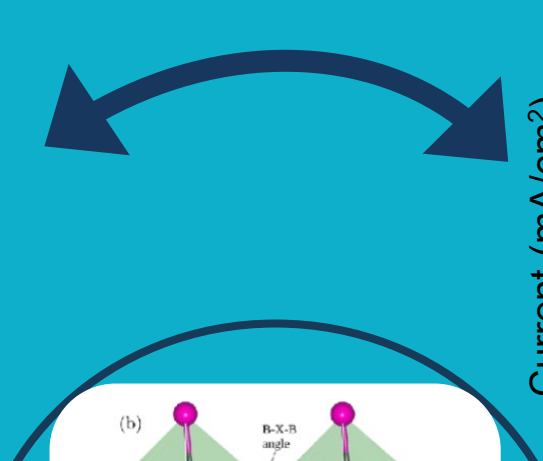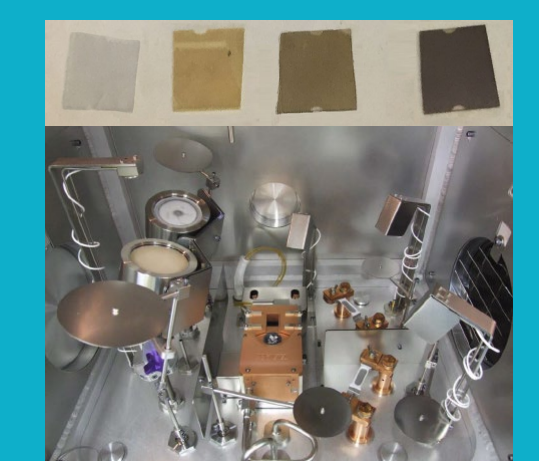

### Lifetime Enhancement

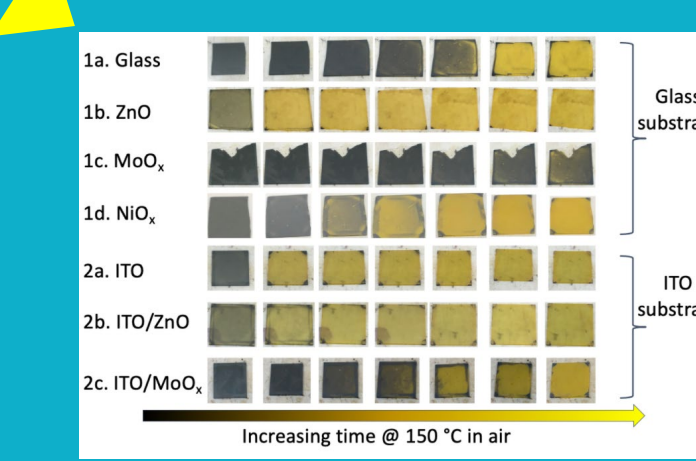

### Future Directions:

- Apply silanes to MOs (Metal Oxides), commonly used as PV charge transport layers
- Investigate systematically varied TCO/MO/silane combinations in half-stack degradation studies

- Further investigate silane-MO interface and its effects on the perovskite film with SE and XPS

## Conclusions

- ❖ Results highlight importance of film studies under device-relevant conditions
- ❖ Organofunctional silanes used as molecular modifiers can passivate a TCO/perovskite interface
- ❖ Interfacial modifiers have multifaceted effects on perovskite film morphology and lifetime

## Acknowledgements

We acknowledge the Case Western Reserve University School of Engineering Faculty Investment Fund for funding the bulk of this work ("Fundamental Materials Studies of a Novel Lead-Free Perovskite"). We also acknowledge the CWRU Flora Stone Mather Center for Women for funding Mirra Rasmussen via a 2021 Women in STEM SOURCE grant. Experimental work was performed in the CWRU Materials for Opto/electronics Research and Education (MORE) Center, a core facility est. 2011 by Ohio Third Frontier grant TECH 09-021.


## References

- <sup>1</sup> *Nature Energy*, vol. 4, pp. 1, Jan. 2019.
- <sup>2</sup> *ChemSusChem*, 10 (2017), 3794-3803. DOI: 10.1002/cssc.201701262.
- <sup>3</sup> *J. Photon. Energy* 6(2), 022001 (2016), DOI: 10.1117/1.JPE.6.022001.
- <sup>4</sup> *Journal of Materials Chemistry A*, vol. 5, no. 4, pp. 1658-1666, 2017.
- <sup>5</sup> *ACS Appl. Energy Mater.* 2020, 3, 2386-2393 DOI:10.1021/acsaem.9b02052
- <sup>6</sup> *Langmuir* 29 (2013), 4057-67. DOI:10.1021/la304719y
- <sup>7</sup> *ACS Appl. Mater. Interfaces* 9 (2017), 17620-17628. DOI: 10.1021/acsaami.7b02638
- <sup>8</sup> *AIP Advances*, vol. 9, no. 8, p. 085123, 2019.

## Experimental Flow

1. Clean substrates
2. Deposit organofunctional silane [6,7]
3. Spin coat MAPbI<sub>3</sub> and anneal [5]
4. Characterization and degradation

### Schematic overview of film stacks

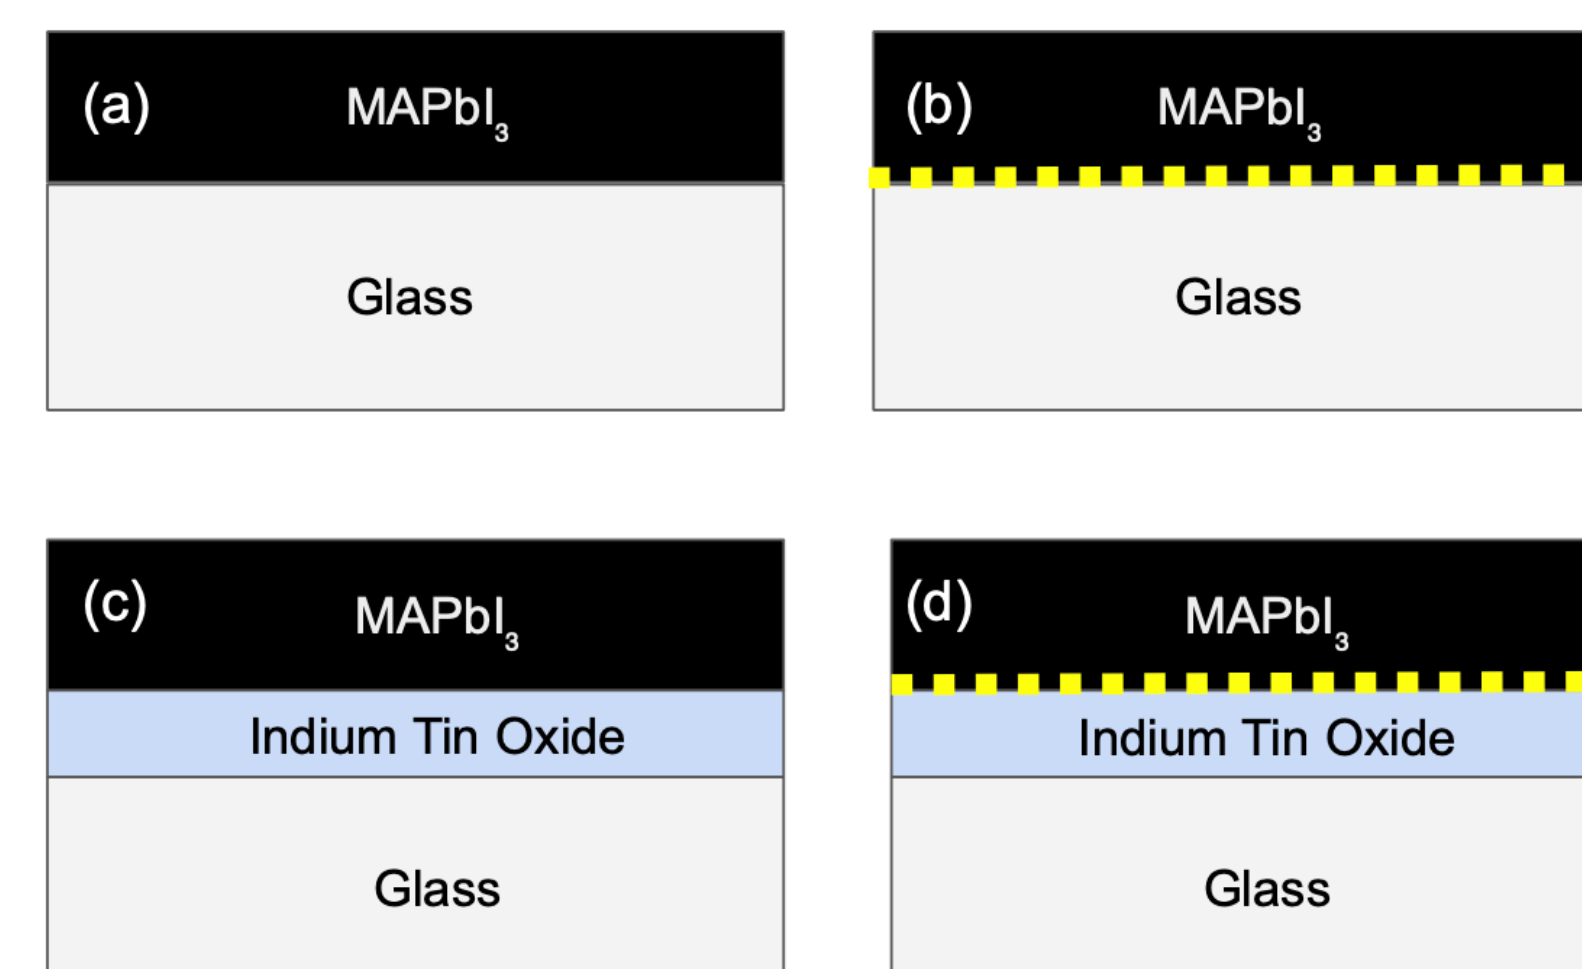


Dashed line indicates organofunctional silane layer.

Substrate	Thickness, Å	Contact Angle, degrees
Silicon	11 ± 1	62 ± 3
	24 ± 1	81 ± 2
ITO	34 ± 2	84 ± 1
	6 ± 1	72 ± 2

Left: Characteristics of BPTMS modified ITO and silicon. Silane thickness is modelled from spectroscopic ellipsometry measurements.

Right: SE characterization of perovskite films

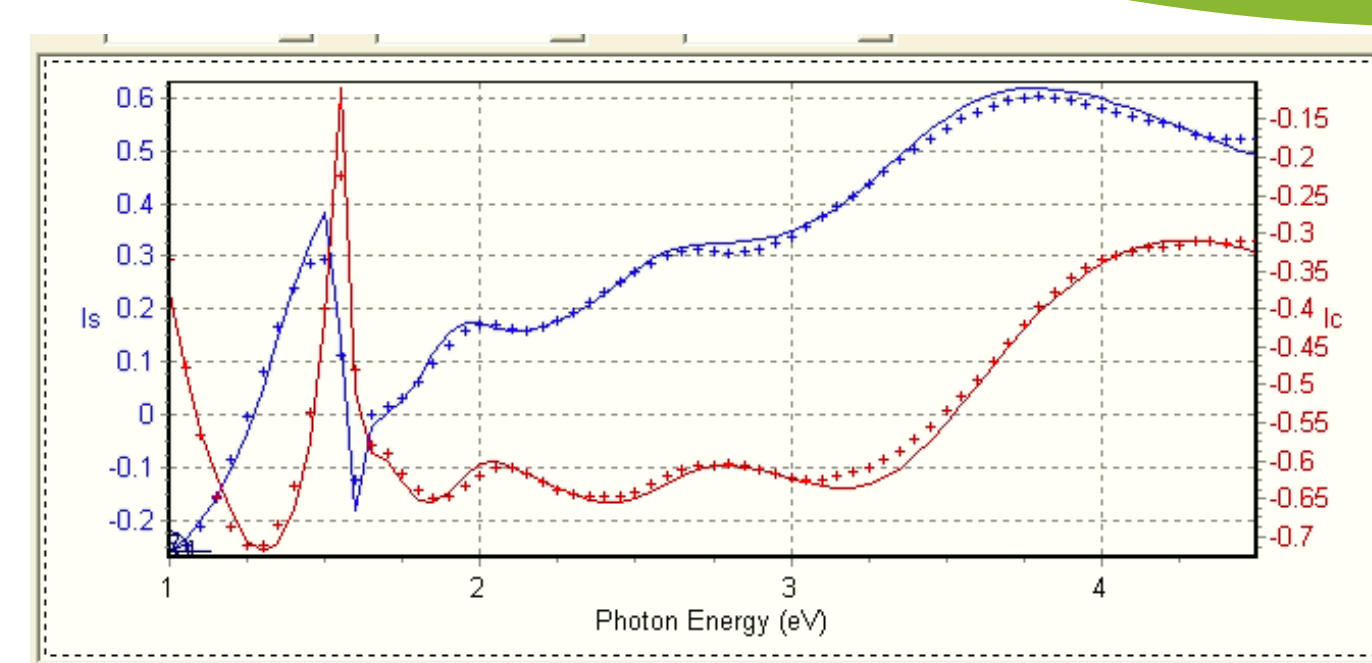

## Silane and Perovskite Deposition

## Conclusions and Future Directions