

Home > Vol 15, No 5 (2019)

## Malaysian Journal of Fundamental and Applied Sciences



### MJFAS promotes and supports I'M Research Consortium



MJFAS is the recipient of Current Research in Malaysia (CREAM 2018) Awards by the Ministry of Education Malaysia.



Journal abbreviation: **Mal. J. Fund. Appl. Sci.**  
ISSN: 2289-5981. e-ISSN: 2289-599X.

Citations	h-index	i10-index
1187	14	23

2019 [Google Scholar](#) Citation Reports



The Malaysian Journal of Fundamental and Applied Sciences (MJFAS) (formerly known as Journal of Fundamental Sciences (2005-2011), ISSN: 1823-626X) is a refereed research journal published by Penerbit UTM Press, Universiti Teknologi Malaysia. The aims and scope of the journal encompass research articles, original research reports, reviews, short communications and scientific commentaries from fundamental principles to practical applications in the broad field of mathematics, physics, chemistry, and biology. All manuscript submissions must be made through the journal's online manuscript system at [Online Submissions](#). This journal is indexed by [Clarivate Analytics](#) (formerly Thomson Reuters) and [Google Scholar](#).

Starting in the year 2019, MJFAS is published online with a frequency of six (6) issues per year (February, April, June, August, October, and December). Besides that, special issues of MJFAS will be published non-periodically from time to time.

The Malaysian Journal of Fundamental and Applied Sciences (MJFAS) is now entering its fourteen years and it is now the official journal of the [Indonesia-Malaysia Research Consortium](#) (I'M Research Consortium). The consortium's aims are to foster the development of the field through a cross-disciplinary approach and to reach consensus in areas of common interest in fundamental and applied sciences field. By making The Malaysian Journal of Fundamental and Applied Sciences the official journal of the I'M Research Consortium, we hope to provide a forum to bring together society members and to publish peer-reviewed consensus documents that emerge from the activities of the consortium.




### The Publishing Process of MJFAS and its Requirements

Below are the new requirements and other guidelines related to publication as well as communicating your results.

JOURNAL CONTENT  
Search

[Click image to enlarge]

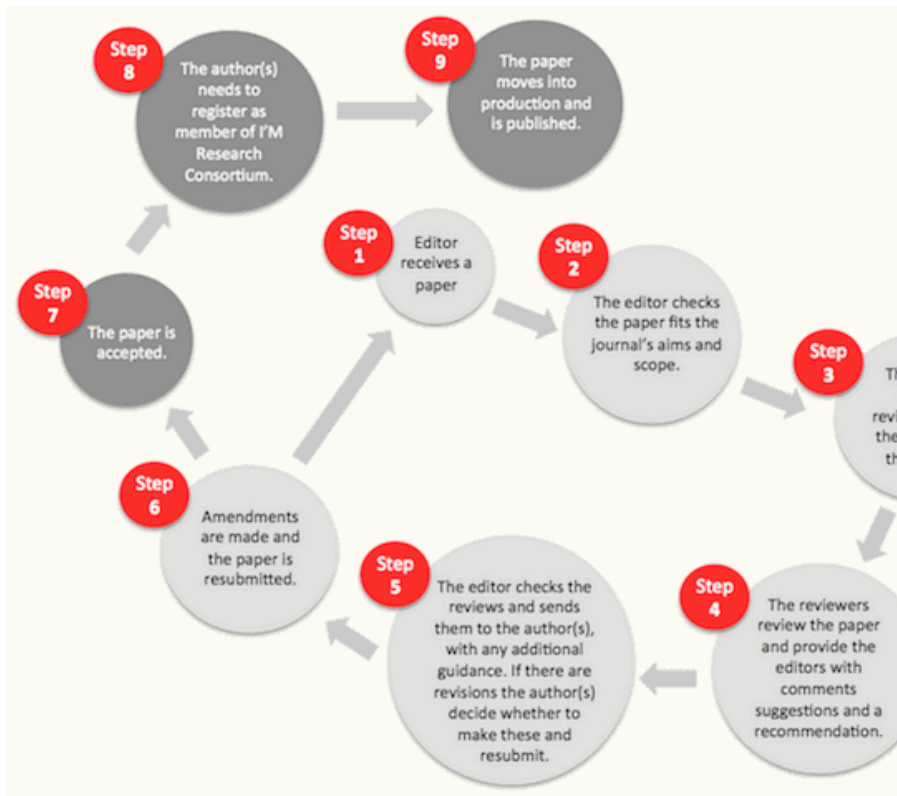

Search Scope

All

Search

Browse

- [By Issue](#)
- [By Author](#)
- [By Title](#)

INFORMATION

- [For Readers](#)
- [For Authors](#)
- [For Librarians](#)

USER

Username

Password

Remember me

Login

FONT SIZE

Before the paper moves into production and is published (**Step 9**), if the author(s) is interested, the author(s) needs to register as a member of I'M Research Consortium (**Step 8**) through the following website:

<http://imresearchconsortium.ning.com/main/authorization/signUp>

The MJFAS is an Open Access journal. Publishing an article in the MJFAS requires article processing charges that will be billed to the submitting author following the acceptance of an article for publication. Apart from these article processing charges, there are no submission charges, page charges, or color charges. The fee to be paid following the acceptance of an article. The fee is **300 Malaysian Ringgit**. Article processing charges will be used for operating expenses of the journal.

For a detailed guideline for submission of an article please refer to [Online Submission](#). Please follow these guidelines to prepare and upload your article.

## Editor's Message

Dear Colleagues,



As the Editor-in-Chief of the Malaysian Journal of Fundamental and Applied Sciences, I am writing to invite you to submit your most important research to the Journal. We envision the Journal as the best place to publish all of the levels of research in fundamental and applied sciences from all over the world, especially from researchers in Malaysia dan Indonesia.

Working with our knowledgeable and international Editorial Board members and I can assure you of a rapid, robust and fair peer-review process. As the Malaysian Journal of Fundamental and Applied Sciences is now indexed by [Clarivate Analytics](#) (formerly Thomson Reuters), we are especially aiming to reduce time to decision. We also have begun to work towards raising the Journal's impact factor.

For the coming submissions, the MJFAS will start implementing the "Your Paper, Your Way" initiative. In this way, authors can focus on the scientific quality of the paper. Journal-specific formatting such as reference style is no longer needed.

Thank you in advance for your valuable contributions to the Malaysian Journal of Fundamental and Applied Sciences.

Sincerely,

**Prof. Dr. Hadi Nur** ([short bio](#))  
 Editor-in-chief  
 e-mail: [hadi@ibnusina.utm.my](mailto:hadi@ibnusina.utm.my)  
 website: <http://hadinur.com>

Home > About the Journal > **Editorial Team**

## Editorial Team

### Editor-in-Chief

[Prof Dr Hadi Nur](#), Ibnu Sina Institute for Scientific and Industrial Research, Universiti Teknologi Malaysia

### Regional Managing Editor for North America and Europe

[Assoc Prof Dr Hendra Hermawan](#), Department of Mining, Metallurgical and Materials Engineering & CHU de Québec Research Center, Laval University, Canada

### Regional Managing Editor for the Middle East and Africa

[Assoc Prof Dr Oki Muraza](#), Chemical Engineering Department, King Fahd University of Petroleum & Minerals, Dhahran, Saudi Arabia

### Special Section Editor

[Dr Sheela Chandren](#), Universiti Teknologi Malaysia, Malaysia

### Editors

[Prof Dr Bassim H Hameed](#), School of Chemical Engineering, Universiti Sains Malaysia  
[Prof Dr Rafaqat Hussain](#), COMSATS Institute of Information Technology, Pakistan  
[Prof Dr Taufiq Yap Yun Hin](#), Department of Chemistry, Putra University, Malaysia  
[Prof Dr Tahir Ahmad](#), Universiti Teknologi Malaysia, Malaysia  
[Prof Dr Takashi Suzuki](#), Department of Information and Computer Sciences Mathematical Science Course, Osaka University School of Engineering Science  
[Assoc Prof Dr rer nat Rino R Mukti](#), Insitut Teknologi Bandung, Indonesia  
[Assoc Prof Dr KK Viswanathan](#), Kuwait College of Science and Technology, Kuwait  
[Assoc Prof Dr Sharif H Zein](#), University of Hull, UK  
[Assoc Prof Dr Riadh Sahnoun](#), Universiti Teknologi Malaysia, Malaysia  
[Assoc Prof Dr Norma Alias](#), Universiti Teknologi Malaysia, Malaysia  
[Assoc Prof Dr Siew Ling Lee](#), Universiti Teknologi Malaysia, Malaysia  
[Assoc Prof Dr Sib Krishna Ghoshal](#), Dept. of Physics, Fac. of Science, Universiti Teknologi Malaysia, Malaysia  
[Assoc Prof Dr Suhairul Hashim](#), Universiti Teknologi Malaysia, Malaysia  
[Assoc Prof Dr Yun Hau Ng](#), School of Energy and Environment, City University of Hong Kong  
[Assoc Prof Dr Hong Heng See](#), Universiti Teknologi Malaysia, Malaysia  
[Assoc Prof Dr Nik Ahmad Nizam Nik Malek](#), Universiti Teknologi Malaysia  
[Dr Dedy Hermawan Baqos Wicaksono](#), Swiss German University, Indonesia  
[Dr Hendrik Oktendy Lintang](#), Ma Chung University, Indonesia  
[Dr Yung Szen Yap](#), Universiti Teknologi Malaysia, Malaysia  
[Dr Wan Heng Fong](#), Universiti Teknologi Malaysia, Malaysia  
[Dr Eng Ferry Iskandar](#), Physics of Electronic Materials Research Div. Department of Physics, Faculty of Mathematic and Natural Sciences, Institut Teknologi Bandung  
[Dr Leny Yuliat](#), Ma Chung University, Indonesia

### Editorial Office

[Ms Siti Nur Sakinah Ahmad](#)  
[Ms Sabariah Ajis](#)



Copyright © 2005-2019 Penerbit UTM Press, Universiti Teknologi Malaysia. Disclaimer: This website has been updated to the best of our knowledge to be accurate. However, Universiti Teknologi Malaysia shall not be liable for any loss or damage caused by the usage of any information obtained from this website.



MJFAS is the recipient of Current Research in Malaysia (CREAM 2018) Awards by the Ministry of Education Malaysia.



### JOURNAL CONTENT

Search   
 Search Scope: All

### Browse

- [By Issue](#)
- [By Author](#)
- [By Title](#)

### INFORMATION

- [For Readers](#)
- [For Authors](#)
- [For Librarians](#)

### USER

Username   
 Password   
 Remember me

### FONT SIZE





## Vol 15, No 1 (2019)

January - February

### Table of Contents

#### Research Article

<a href="#">Optimization of phenol adsorption onto biochar from oil palm empty fruit bunch (EFB)</a> Siti Hadjar Md Arshad, Norzita Ngadi, Syieluing Wong, Noraishah Saidina Amin, Fatin Amirah Razmi, Nurul Balqis Mohamed, Ibrahim Mohammed Inuwa, Astimar Abdul Aziz	PDF 1-5
<a href="#">Effect of cross-linked enzyme aggregates in hierarchically mesocellular mesoporous magnetic silica preparation conditions towards enzyme activity retention</a> Nurul Jannah Sulaiman, Roshanida Abdul Rahman, Rosli Md Illias	PDF 6-12
<a href="#">Development of missing data prediction model for carbon monoxide</a> Nurul Latiffah Abd Rani, Azman Azid, Muhamad Shirwan Abdullah Sani, Mohd Saiful Samsudin, Ku Mohd Kalkausar Ku Yusof, Siti Noor Syuhada Muhammad Amin, Saiful Iskandar Khalit	PDF 13-17
<a href="#">Structural and characterization studies of insoluble thai bombyx mori silk fibroin films</a> Noor Izyan Syazana Mohd Yusoff, Mat Uzir Wahit, Juhana Jaafar, Tuck-Whye Wong	PDF 18-22
<a href="#">Preparation and characterization of superparamagnetic magnetite (Fe3O4) nanoparticles: A short review</a> Khong Nee Koo, Ahmad Fauzi Ismail, Mohd Hafiz Dzarfah Othman, Noriah Bidin, Mukhlis A Rahman	PDF 23-31
<a href="#">Simultaneous action of surfactant modified sugarcane bagasse: Adsorbent and antibacterial agent</a> Nik Ahmad Nizam Nik Malek, Muhammad Hafizuddin Yusof, Auni Afiqah Kamaru	PDF 32-37
<a href="#">A generalized bivariate copula for flood analysis in Peninsular Malaysia</a> Izzat Fakhruddin Kamaruzaman, Wan Zawiah Wan Zin, Noratqiah Mohd Ariff	PDF 38-49
<a href="#">Preparation and characterization of polysulfone membrane coated with poly(ether block amid) for oxygen enrichment process</a> Kok Chung Chong, Yin Yin Chan, Wei Jye Lau, Soon Onn Lai, Ahmad Fauzi Ismail, Hui Shan Thiam	PDF 50-53
<a href="#">Development of water quality index of ex-mining ponds in Malaysia</a> Isa Baba Koki, Sharifuddin Md Zain, Low Kah Hin, Azman Azid, Hafizan Juahir, Munirah Abdul Zali	PDF 54-60
<a href="#">Development and oviposition preferences of field collected Aedes albopictus based on different water characteristics</a> Nazri Che Dom, Megat Azman Megat Mokhtar, Cornelia Tata Australia	PDF 61-64
<a href="#">Measurement of trabecular bone parameters with different bone thickness and voxel size in mice using micro CT</a> Nurin Nadzlah Abu Bakar, Basri Saidi, Lyana Shahirah Mohamad Yamin	PDF 65-68
<a href="#">Study of packed sieve tray column in ethanol purification using distillation process</a> Tarikh Aziz Ramadani, Fadiatul Taufany, Siti Nurkhamidah	PDF 69-74
<a href="#">Biomechanical evaluation of pin placement of external fixator in treating tranverse tibia fracture: Analysis on first and second cortex of cortical bone</a> Muhammad Hanif Hanif Ramlee, Nur Amalina Zainudin, Hadafi Fitri Mohd Latip, Gan Hong Seng, Evelyn Garcia-Nieto, Mohammed Rafiq Abdul Kadir	PDF 75-79
<a href="#">An experimental analysis on the performance of single mode-multimode-single mode and multimode- single mode-multimode fiber optic sensor</a> Hanim Abdul Razak	PDF 80-84
<a href="#">Surface water quality in palm oil plantation</a> Nur Syakira Che Nadzir, Mohd Zahari Abdullah, Fazrul Razman Sulaiman	PDF 85-87
<a href="#">Isomorphism and matrix representation of point groups</a> Wan Heng Fong, AqilahFarhana Abdul Rahman, Nor Haniza Sarmin	PDF 88-92
<a href="#">The Effect of Time and H2O/CTAB Ratio in Synthesis of Mesoporous Alumina from Bauxite Residue</a> Omita Riski, Didik Prasetyoko, Dwi Kumala Febrianti, Yatim Lailun Nikmah, Vita Nur Iffritahyah, Hartati Hartati, Imroatul Qoniah, Eko Santoso	PDF 93-98
<a href="#">Pre-drilling and self-drilling pins screw-bone fixation stress interaction analysis induced by uniaxial compression loading</a> Lim Pei Chee, Ruslizam Daud, Shah Fenner Khan Mohamad Khan, Nurul Alia Md Zain, Yazid Bajuri	PDF 99-108
<a href="#">Development of optical fibers for food irradiation dosimeter</a> Hamiza Ahmad Tajuddin, Wan Muhamad Saridan Wan Hassan, Siti Fairus Abdul Sani, Siti Aiasah Hashim	PDF 109-111
<a href="#">Analysis of controllers in suppressing the structural building vibration</a> Normaisharah Mamat, Fitri Yakub, Sheikh Ahmad Zaki Sheikh Salim	PDF 112-116
<a href="#">Improved quasi-newton method via SR1 update for solving symmetric systems of nonlinear equations</a> Muhammad Kabir Dauda, Mustafa Mamat, Mohamad Afendee Mohamed, Mahammad Yusuf Waziri	PDF 117-120
<a href="#">PET-CT in Esophageal Cancer Management: A Cost Effectiveness Analysis Study</a> Nor Aniza Azmi, Hairil Rashmizal Abdul Razak, Sobhan Vinjamuri	PDF 121-124
<a href="#">Organic rankine cycle and steam turbine for intermediate temperature waste heat recovery in total site integration</a> Norhafiza Kamarudin, Liew Peng Yen, Nurfatehah Wahyuni Che Jusoh, Wai Shin Ho, Jeng Shiun Lim	PDF 125-130



MJFAS is the recipient of Current Research in Malaysia (CREAM 2018) Awards by the Ministry of Education Malaysia.



#### JOURNAL CONTENT

Search

Search Scope

#### Browse

- [By Issue](#)
- [By Author](#)
- [By Title](#)

#### INFORMATION

- [For Readers](#)
- [For Authors](#)
- [For Librarians](#)


#### USER

Username

Password

Remember me

#### FONT SIZE





Home > Vol 15, No 4 (2019)

## Malaysian Journal of Fundamental and Applied Sciences



### MJFAS promotes and supports I'M Research Consortium



MJFAS is the recipient of Current Research in Malaysia (CREAM 2018) Awards by the Ministry of Education Malaysia.



Journal abbreviation: **Mal. J. Fund. Appl. Sci.**  
ISSN: 2289-5981. e-ISSN: 2289-599X.

Citations	h-index	i10-index
1164	14	23

2019 [Google Scholar](#) Citation Reports



The Malaysian Journal of Fundamental and Applied Sciences (MJFAS) (formerly known as Journal of Fundamental Sciences (2005-2011), ISSN: 1823-626X) is a refereed research journal published by Penerbit UTM Press, Universiti Teknologi Malaysia. The aims and scope of the journal encompass research articles, original research reports, reviews, short communications and scientific commentaries from fundamental principles to practical applications in the broad field of mathematics, physics, chemistry, and biology. All manuscript submissions must be made through the journal's online manuscript system at [Online Submissions](#). This journal is indexed by [Clarivate Analytics](#) (formerly Thomson Reuters) and [Google Scholar](#).

Starting in the year 2019, MJFAS is published online with a frequency of six (6) issues per year (February, April, June, August, October, and December). Besides that, special issues of MJFAS will be published non-periodically from time to time.

The Malaysian Journal of Fundamental and Applied Sciences (MJFAS) is now entering its fourteen years and it is now the official journal of the [Indonesia-Malaysia Research Consortium](#) (I'M Research Consortium). The consortium's aims are to foster the development of the field through a cross-disciplinary approach and to reach consensus in areas of common interest in fundamental and applied sciences field. By making The Malaysian Journal of Fundamental and Applied Sciences the official journal of the I'M Research Consortium, we hope to provide a forum to bring together society members and to publish peer-reviewed consensus documents that emerge from the activities of the consortium.



### The Publishing Process of MJFAS and its Requirements

Below are the new requirements and other guidelines related to publication as well as communicating your results.

JOURNAL CONTENT

Search



About

General Information

Web of Science Coverage

Peer Review Information

[← Return to Search Results](#)

## MALAYSIAN JOURNAL OF FUNDAMENTAL AND APPLIED SCIENCES

ISSN / eISSN **2289-5981 / 2289-599X**

Publisher **PENERBIT UTM PRESS, PENERBIT UTM PRESS, SKUDAI, JOHOR, MALAYSIA, 81310**

### About

Malaysian Journal of Fundamental and Applied Sciences is ready to receive papers on all aspects of fundamental science research in the field of mathematics, physics, chemistry and biology.

### General Information

<b>Frequency</b>	Quarterly
<b>Issues Per Year</b>	4
<b>Country / Region</b>	MALAYSIA

Web of Science Coverage

[Scope Notes](#)

#### Web of Science Core Collection

Emerging Sources Citation Index

**Categories:** Multidisciplinary | Multidisciplinary Sciences

Log into [Web of Science](#) to discover research literature from this journal.

### Our policy towards the use of cookies

All Clarivate Analytics websites use cookies to improve your online experience. They were placed on your computer when you launched this website. You can change your cookie settings through your browser.

[Ok to Continue](#)

[Cookie Policy](#)

<b>Publish Report</b>	No
<b>Publons Reviews</b>	21
<b>Publons Endorsements</b>	2
<b>Publons Partner</b>	No

register for a free [Publons](#) account for more peer review information out this journal.

**Editorial Disclaimer:** As an independent organization, Clarivate Analytics does not become involved in and is not responsible for the editorial management of any journal or the business practices of any publisher. Publishers are accountable for their journal performance and compliance with ethical publishing standards. The views and opinions expressed in any journal are those of the author(s) and do not necessarily reflect the views or opinions of Clarivate Analytics.

Criteria for selection of newly submitted titles and re-evaluation of existing titles in the Web of Science are determined by the Web of Science Editors in their sole discretion. If a publisher's editorial policy or business practices negatively impact the quality of a journal, or its role in the surrounding literature of the subject, the Web of Science Editors may decline to include the journal in any Clarivate Analytics' product or service. The Web of Science Editors, in their sole discretion, may remove titles from coverage at any point if the titles fail to maintain our standard of quality, do not comply with ethical standards, or otherwise do not meet the criteria determined by the Web of Science Editors. If a journal is deselected or removed from coverage, the journal will cease to be indexed in the Web of Science from a date determined by the Web of Science Editors in their sole discretion – articles published after that date will not be indexed. The Web of Science Editors' decision on all matters relating to journal coverage will be final.

## Clarivate

Accelerating innovation

© 2019 Clarivate

[Copyright Notice](#)

[Terms of Use](#)

[Privacy Notice](#)

[Cookie Policy](#)

[Help Center](#)

Follow us:



### Our policy towards the use of cookies

All Clarivate Analytics websites use cookies to improve your online experience. They were placed on your computer when you launched this website. You can change your cookie settings through your browser.

[Ok to Continue](#)

[Cookie Policy](#)



# The effect of crystallization time and H<sub>2</sub>O/CTAB ratio in the synthesis of mesoporous alumina from bauxite residue (red mud)

Omita Riski<sup>a</sup>, Didik Prasetyoko<sup>a,\*</sup>, Dwi Kumala Febrianti<sup>a</sup>, Yatim Lailun Ni'mah<sup>a</sup>, Vita Nur Iftitahiyah<sup>a</sup>, Hartati<sup>b</sup>, Imroatul Qoni'ah<sup>a</sup>, Eko Santoso<sup>a</sup>

<sup>a</sup> Department of Chemistry, Faculty of Science, Institut Teknologi Sepuluh Nopember, 60111 Sukolilo, Surabaya, Indonesia

<sup>b</sup> Department of Chemistry, Faculty of Science and Technology, Universitas Airlangga, Kampus C UNAIR, Jl. Mulyorejo, Surabaya, 60115, Indonesia

\* Corresponding author: didikp@chem.its.ac.id

## Article history


Submitted 23 January 2018

Revised 15 March 2018

Accepted 11 July 2018

Published Online 4 February 2019

## Graphical abstract

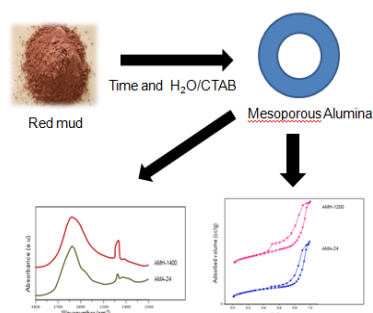

## Abstract

Mesoporous alumina has been successfully synthesized from bauxite residues (red mud) as raw material and cetyltrimethylammonium bromide (CTAB) as template at room temperature. The effects of crystallization time and molar ratio of H<sub>2</sub>O/CTAB on structural and textural properties of mesoporous alumina were investigated. The synthesized product was characterized by XRD, FTIR, SEM-EDX, TEM, N<sub>2</sub> adsorption-desorption and acidity test using pyridine adsorption. The XRD pattern and SEM micrograph showed that the synthesized product possessed an amorphous phase and irregular shapes. From obtained results, it could be observed that crystallization time and H<sub>2</sub>O/CTAB ratio influenced the surface acidity of mesoporous alumina.

**Keywords:** Red mud, mesoporous, alumina materials, surface acidity

© 2019 Penerbit UTM Press. All rights reserved

## INTRODUCTION

Red mud is a waste material or residue derived from the alumina (Al<sub>2</sub>O<sub>3</sub>) production from bauxite. The Al<sub>2</sub>O<sub>3</sub> production uses Bayer Process in which sodium hydroxide (NaOH) is added to produce Al<sub>2</sub>O<sub>3</sub> from bauxite, as well as solid residue called red mud (Kumar, 2015). In average, 1-1.5 tons of red mud may be generated after producing 1 ton of alumina (Brunori *et al.*, 2005). Red mud is comprised from some metal oxides such as iron oxides, silicon oxides and undissolved alumina with a wide range that depended on the ore used (Snars and Gilkes, 2009). The concentration of alumina in red mud is about 25-30% (Liang, 2014). Therefore, red mud can be used as an alumina source to synthesize alumina-based materials.

Alumina has been applied as catalyst, ceramic, catalyst support, conductor and strengthener in composite because of its uniform channels, good thermal conductivity, high Lewis acidity and high specific area (Xia *et al.*, 2003). Red mud from Bintan has been successfully used as raw material to synthesize a mesoporous alumina by adding CTAB as template at room temperature using sol-gel method. Mesoporous alumina from Bintan's red mud confirmed to have a mesoporous structure with BET surface area of 241 m<sup>2</sup>/g and pore size of 3.820 nm with ratio CTAB/Al of 0.32 as optimal ratio (Ramdhani *et al.*, 2018).

Sol-gel method is an easy yet cheap method to synthesize mesoporous alumina. Some parameters such as time and water content can be used to optimize the synthesis process. It has been reported that the synthesized product with longer time of aging has bigger particle size (Rousseaux *et al.*, 2002). Water content is proven to give effects

on the particle size, crystallinity and specific area of synthesized product (Isley and Penn, 2008).

Here, the synthesis of mesoporous alumina using red mud from Bintan as alumina source and CTAB as template was conducted in room temperature. The effects of crystallization time and molar ratio of H<sub>2</sub>O/CTAB on surface acidity of the synthesized product were studied.

## EXPERIMENTAL

### Materials

The starting materials, the powders of red mud were obtained from Bintan Island of Indonesia, cetyltrimethylammonium bromide (CTAB, Merck, 99%), sodium hydroxide (NaOH, Merck, 99%), hydrochloric acid (HCl, SAP, 37%) and deionized water were used in this study. The chemical composition of Bintan's red mud was shown in Table 1.

### Preparation of precursor

The process of extraction and synthesis were adopted from Ramdhani *et al.* (2018). Red mud was leached with HCl 6N solution (solid/liquid ratio 1:5 g/mL) at 90 °C under stirring for 2 h, and then filtered and washed with deionized water. The leachate was collected as aluminum source. Then NaOH 5 N solution was dropped into filtrate under stirring. The NaAlO<sub>2</sub> was filtered to separate the precipitate of impurities (Fe<sup>3+</sup>, Ca<sup>2+</sup>, etc). HCl 6 N was added to the solution with stirring until the precipitate was completely formed. The

precipitate was used as alumina source in synthesis of mesoporous alumina.

**Table 1** Chemical composition analysis by XRF for red mud.

Chemical composition	Mass %
Fe <sub>2</sub> O <sub>3</sub>	49.87
Al <sub>2</sub> O <sub>3</sub>	31.39
SiO <sub>2</sub>	15.03
TiO <sub>2</sub>	1.57
P <sub>2</sub> O <sub>5</sub>	0.56
K <sub>2</sub> O	0.54
CaO	0.15
Cr <sub>2</sub> O <sub>3</sub>	0.10
V <sub>2</sub> O <sub>5</sub>	0.08
NiO	0.07
CuO	0.05
ZnO	0.02
Other compound	0.57

### Synthesis of mesoporous alumina from red mud

The precipitate from previous steps was mixed with CTAB and water with molar ratio H<sub>2</sub>O/CTAB of 600, 800, 1012, 1200 and 1400. The mixture was stirred for 1 h for all samples and then aged for 72 h at room temperature. The final product was recovered by filtration, washed with deionized water and dried at 120 °C for 24 h. The dried product was calcined at 550 °C for 6 h. The effect of crystallization time was studied with molar ratio H<sub>2</sub>O/CTAB = 1012. The mixture was stirred for 1 h for all samples and then aged for 3, 12, 24, 48 and 72 h at room temperature. The final product was recovered by filtration, washed with deionized water and dried at 120 °C for 24 h. The dried product was calcined at 550 °C for 6 h. The general method (molar ratio H<sub>2</sub>O/CTAB 1012 and aging time 72 h) was adopted from Ramdhani *et al.* (2018). The synthesized sample with variation of crystallization time was labeled as AMA-(crystallization time, h.) for example AMA-24, while sample synthesized with variation of H<sub>2</sub>O/CTAB molar ratio was labeled as AMH-(molar ratio of H<sub>2</sub>O/CTAB) for example AMH-1200.

### Characterization of mesoporous alumina

X-ray powder diffraction patterns of the samples were recorded on a Philips Expert with Cu K<sub>α</sub> (40kV, 30 mA) radiation in the range 2θ = 5-50°. The infrared spectra (wavenumber range 400-1400 cm<sup>-1</sup>) of characteristic vibration bands were monitored by FTIR Shimadzu Instrument Spectrum One 8400S. The specific surface area and pore size distribution were determined from N<sub>2</sub> adsorption-desorption using a Quantachrome Instruments Nova 1200. SEM images and elemental analysis were recorded using Zeiss EVO MA 10 instrument. TEM images were recorded using Hitachi TEM HT7700.

The surface acidity of mesoporous alumina synthesized from red mud was measured by pyridine adsorption using FTIR spectrometer. Calcined samples were pressed into a pellet and then placed in homemade glass transmission cell and outgassed at 400 °C for 4 h under N<sub>2</sub> flow. The pyridine was adsorbed at room temperature for 1 h. Subsequently, the sample was purged under N<sub>2</sub> flow at 150 °C for 3 h. The infrared spectra (range 1300-1800 cm<sup>-1</sup>) of characteristic vibration band were recorded by FTIR spectrometer.


## RESULTS AND DISCUSSION

### Synthesis of mesoporous alumina from red mud

Mesoporous alumina has been synthesized from Bintan's red mud with sol-gel method. There were some steps involved to prepare the precursor since red mud contained other compounds aside Al<sub>2</sub>O<sub>3</sub> such as Fe<sub>2</sub>O<sub>3</sub> and SiO<sub>2</sub>. The preparation has two steps. The first one was the removal of SiO<sub>2</sub> by adding acid, while the second one was the removal of Fe<sub>2</sub>O<sub>3</sub> by adding base. This procedure has been successfully done by Pan *et al.* (2013) to obtain alumina from coal kaolin and Ramdhani *et al.* (2018) to obtain alumina from Bintan's red mud. Precipitate alumina was formed after adding acid into filtrate from removal Fe<sub>2</sub>O<sub>3</sub> process, in which aluminum hydroxide precipitate would form completely in pH ~7 (Pan *et al.*, 2013). This precipitate

was used as precursor in synthesis of mesoporous alumina. Fig 1 shows the SEM image and EDX graph for each step in preparation of precursor. As observed from SEM images in Fig 1, all of the residues have an irregular shape and size. According to EDX graph, residue from SiO<sub>2</sub> removal (RSD1) and Fe<sub>2</sub>O<sub>3</sub> removal (RSD2) still contained aluminum. This finding was caused by unfinished washing step in each process. Therefore, the residue still contained aluminum. Otherwise, the alumina precipitate (GM-AL) didn't contain any Si or Fe elements which indicated that this process was good enough to obtain alumina from Bintan's red mud.

Alumina salt from previous steps was used as alumina source in synthesis of mesoporous alumina. The mass ratio of CTABr and alumina salt used was 1.57, as reported by Ramdhani *et al.* (2018). The water content inside the alumina salt has been calculated by comparing mass of the salt before and after drying. Alumina salt from the previous steps contained 93.97% of water content that could predict the mass of product to be low. This wet precipitate was added into CTAB solution under stirring for 1 h. The purpose of using wet precipitate was to facilitate the distribution of alumina inside the solution (Ramdhani *et al.*, 2018). The solution was aged for 3, 12, 24, 48 and 72 h. This variation was used to optimize the polymerization process of Al-O-Al so the product would possess stable structure (Moatti *et al.*, 2014). The removal of CTAB was done by calcination at 550 °C for 6 h. There were three steps of CTAB decomposition i.e. ammonia removal at 200-320 °C, structural decomposition of CTAB at 320 °C and removal of the remaining CTAB from alumina structure to form a pore at 395 °C (Liu *et al.*, 2007). Solid product after calcination process was collected. The mass of the product was shown in Table 2. According to Table 2, the mass of product was increased for longer crystallization time. It could be concluded that the effectiveness of polymerization process could be increased for 72 h of crystallization time, as reported by Pan *et al.* (2013) and Ramdhani *et al.* (2018). Sample AMA-72 has the highest mass, due to the synthesis of mesoporous alumina with certain H<sub>2</sub>O/CTAB molar ratio at crystallization time for 72 h.

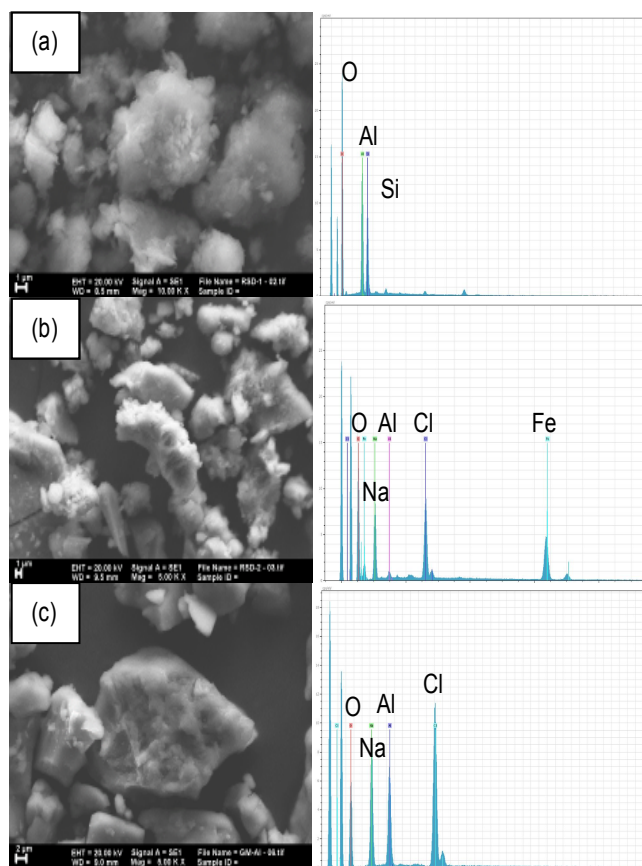

**Fig 1.** SEM images and EDX graphs of (a) RSD1, (b) RSD2 and (c) GM-AL.

**Table 2** Mass of synthesized product with variation of time.

Sample	Mass (g)
AMA-3	0.1810
AMA-12	0.1868
AMA-24	0.1871
AMA-48	0.1932
AMA-72	0.2079

Wang and Ying (1999) have reported that the higher ratio of H<sub>2</sub>O could help the hydrolysis process and interfere the particle growth at the same time. Li *et al.* (2004) also confirmed that the higher amount of H<sub>2</sub>O in synthesis process, the hydrolysis and polycondensation processes also got faster so the mass of the product could be increased. In this study, the mass of synthesized product was tended to increase with increasing of the molar ratio of H<sub>2</sub>O/CTAB. The mass of product with variation of H<sub>2</sub>O/CTAB molar ratio was shown in Table 3.

**Table 3** Mass of synthesized product with variation of H<sub>2</sub>O/CTAB ratio.

Sample	Mass (g)
AMH-600	0.1272
AMH-800	0.1282
AMH-1012	0.1267
AMH-1200	0.1324
AMH-1400	0.1352

#### Characterization of mesoporous alumina from red mud

XRD pattern of fresh red mud was shown in Fig. 2. As observed, the Bintan's red mud contained some minerals such as hematite (Fe<sub>2</sub>O<sub>3</sub>), goethite (FeOOH), gibbsite (Al(OH)<sub>3</sub>), boehmite ( $\gamma$ -AlO(OH)), anatase (TiO<sub>2</sub>) and quartz (SiO<sub>2</sub>). This result was confirmed by the elemental analysis of Bintan's red mud with XRF technique (Table 1). The XRD pattern of red mud has a similar pattern as reported by Liang *et al.* (2014), Sushil and Batra (2012), and Ghosh *et al.* (2010).





**Fig. 2** XRD pattern of red mud.

Fig. 3 and Fig. 4 show the XRD pattern of mesoporous alumina from red mud with variation of crystallization time and H<sub>2</sub>O/CTAB molar ratio after calcination at 550 °C for 6 h. There was no characteristic peak detected in XRD pattern for all samples. The absence of the characteristic peak indicated that the material has bimodal porous with amorphous wall (Pan *et al.*, 2013). According to Cheng *et al.* (1995), when synthesis has been done with concentration of CTAB under 40%, the synthesized product has irregular mesopore. Therefore, no peak was detected for all of the samples.

The samples of red mud, as-synthesized alumina, and calcined alumina were investigated by infrared spectroscopy (Fig. 5). Infrared spectra for all calcined samples showed similar spectra, i.e. peak at around 3450 and 1635 cm<sup>-1</sup> for stretching and bending vibrations of O-H groups, and also at 729 and 590 cm<sup>-1</sup> for Al-O vibration. Similar

infrared spectra were stated by Pan *et al.* (2013). In addition, there was no sharp peak at around 1200-1000 cm<sup>-1</sup> characteristic for stretching vibration of Si-O (Qoniah *et al.*, 2015), which only appeared in red mud sample. This finding concluded that the solid sample only consisted of alumina. Meanwhile, infrared spectra of as-synthesized sample only showed a peak at around 1400 cm<sup>-1</sup>, characteristic for bending vibration of -CH<sub>2</sub> and -CH<sub>3</sub> from cetyltrimethylammonium (Yue *et al.*, 2010). The absence of this peak in all infrared spectra of calcined product indicated that cetyltrimethylammonium was completely removed from the solid product.

**Fig. 3** XRD pattern of mesoporous alumina from red mud with variation of time.**Fig. 4** XRD pattern of mesoporous.**Fig. 5** FTIR Spectra for (a) red mud, (b) As-synthesized mesoporous alumina (AM as-synthesized), (c) AMA-72 and (d) AMH-1400.

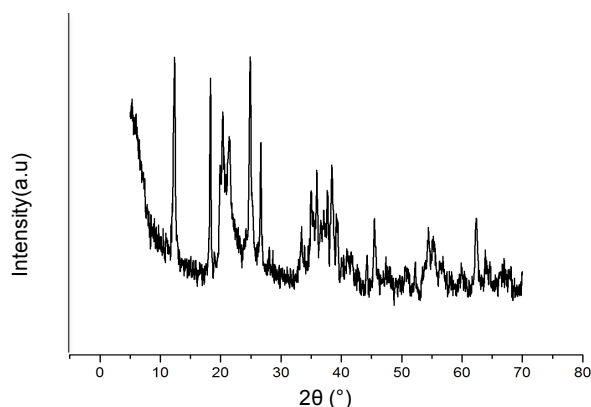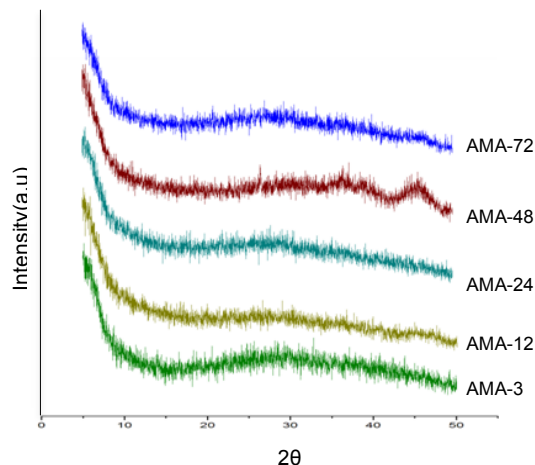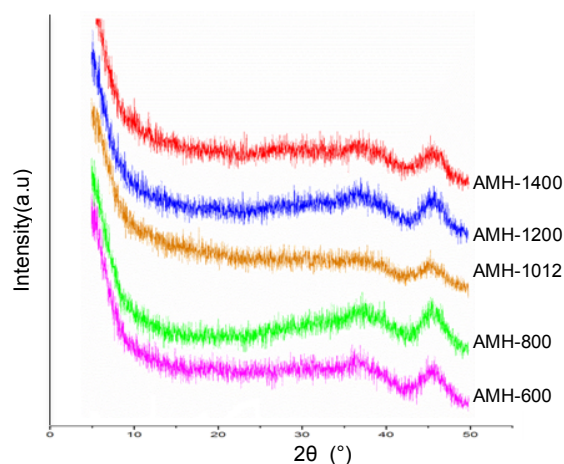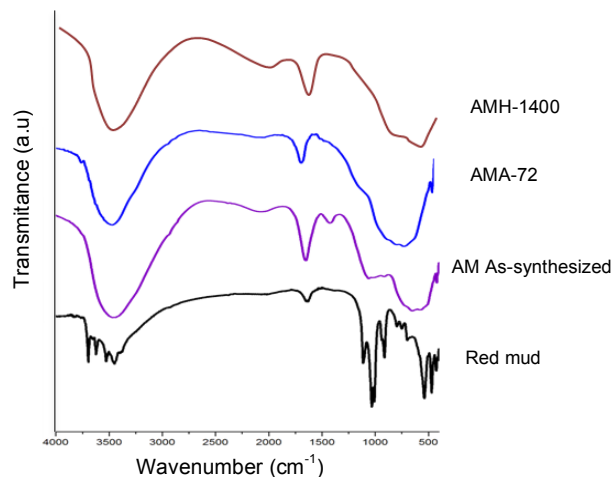

The N<sub>2</sub> adsorption-desorption isotherms of the synthesized-alumina from red mud has been carried out to determine the specific surface area, pore size distribution and pore volume of the synthesized materials (Fig. 6). The N<sub>2</sub> adsorption-desorption isotherm for sample AMA-24 showed hysteresis at p/p<sub>0</sub> = 0.4-0.9, indicating that the sample has isotherm type IV. According to the isotherm type by IUPAC, it was confirmed that the synthesized-alumina from red mud contained mesopore. The isotherm adsorption for AMH-1200 also indicated the type IV isotherm based on the presence of H3 hysteresis loop. According to IUPAC classification, the hysteresis loops for AMA-24 and AMH-1200 were apparently composite of H1 and H3 type hysteresis loops, indicating the samples to consist of a plate-like particles and slit-like pores. The type of hysteresis confirmed that the synthesized product has a mesopore and synthesized sample from a clay usually has slit like pores. The pore structure parameters were calculated according to the mathematical models from the N<sub>2</sub> adsorption-desorption. The data were given in Table 4. According to BJH calculation, AMA-24 has 132.122 m<sup>2</sup>/g mesoporous surface area with pore size of 3.831 nm and AMH-1200 has 184.474 m<sup>2</sup>/g mesoporous surface area with pore size of 3.833 nm. The pore size distribution for AMA-24 and AMH-1200 were shown at Fig. 7. This result showed the similar profiles as reported by Ramdhani *et al.* (2018) with a larger mesoporous surface area. It was interesting to note that AMA-24 and AMH-1200 also have microporous structure since they have pretty high adsorption in p/p<sub>0</sub> < 0.3. The BET calculation showed that the microporous surface area for AMA-24 and AMH-1200 were 212.485 m<sup>2</sup>/g and 168.311 m<sup>2</sup>/g, respectively. The pore volume for AMA-24 and AMH-1200 were 0.426 cc/g and 0.363 cc/g.

Table 4. Pore structure properties of AMA-24 and AMH-1200.

Sample	Mesoporous Surface Area <sup>a</sup> (m <sup>2</sup> /g)	Microporous Surface Area <sup>b</sup> (m <sup>2</sup> /g)	Pore volume <sup>a</sup> (cc/g)	Pore diameter <sup>a</sup> (nm)
AMA-24	132.122	212.485	0.426	3.831
AMH-1200	184.474	168.311	0.363	3.833

<sup>a</sup> determined by BJH

<sup>b</sup> determined by BET at P/P<sub>0</sub> = 0.3

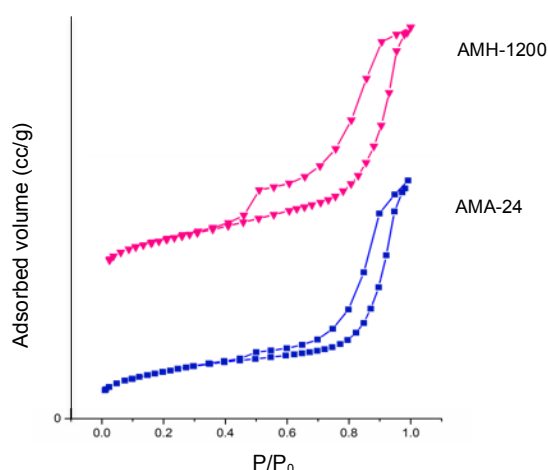


Fig. 6 Nitrogen adsorption-desorption of the samples: (a) AMA-24 and (b) AMH-1200.

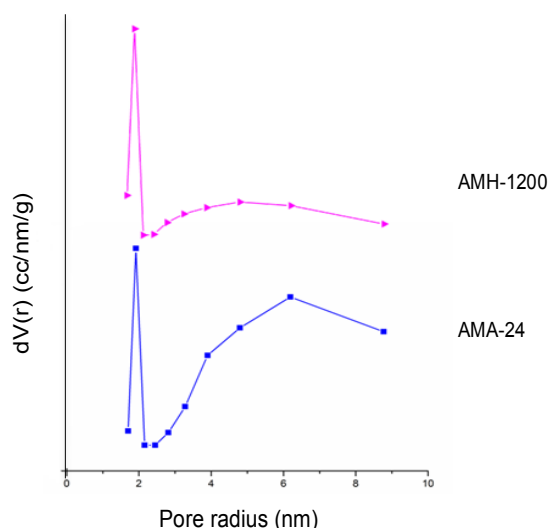


Fig. 7 Pore size distribution of the samples: (a) AMA-24 and (b) AMH-1200.


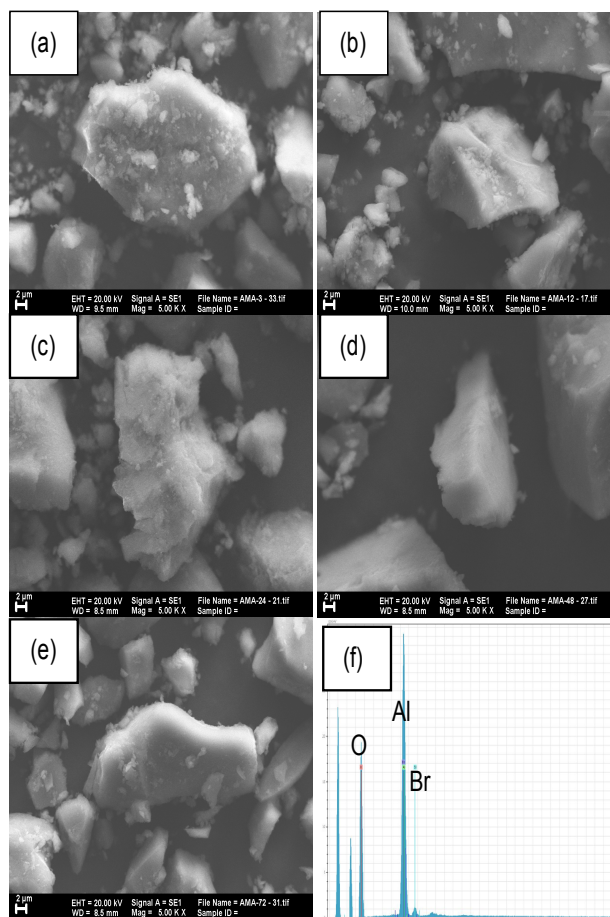


Fig 8. SEM images of (a) AMA-3, (b) AMA-12, (c) AMA-24, (d) AMA-48, (e) AMA-72 and EDX graph of (f) AMA-72.

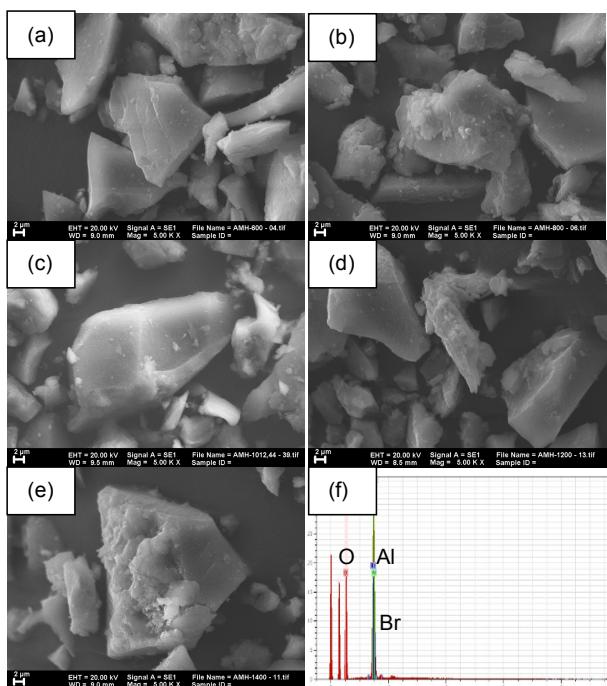


**Fig 9.** SEM images of (a) AMH-600, (b) AMH-800, (c) AMH-1012, (d) AMH-1200, (e) AMH-1400 and EDX graph of (f) AMH-1200.

The morphology and the elemental analysis of the alumina samples were investigated with SEM-EDX. Morphologies of mesoporous alumina synthesized with variation of crystallization times were shown in Fig 8. The particle size and the formation of mesoporous aggregates were controlled by the reaction condition, such as time, pH and addition of structure directing agent (Petushkov *et al.*, 2011). In this study, the size and shape for all samples were irregular without any particular differences. Meanwhile, morphology of the mesoporous alumina samples synthesized with variation of H<sub>2</sub>O/CTAB molar ratios were shown in Fig 9. The obtained result was similar with the result for variation of time. There was no significant difference in the particle size reported by Isley and Penn (2008). It might be caused by the precursors that did not have regular shape to start off. The EDX graph showed peak for bromine for AMA-72 and AMH-1200 samples. The peak for bromine might appear due to unfinished washing procedure, causing the ions to stay still inside the pore even though calcination was already done.

AMA-72 was investigated with TEM to monitor the morphology of the product as shown in Fig. 10. As observed, AMA-72 has morphology of both wormlike structure (Fig 10 a and b) and thin sheet-like structure (Fig. 10 c and d). In this paper, alumina was synthesized from wet precipitate alumina salt. The water content in the alumina salt was pretty high. Huang *et al.* (2014) reported that the molar ratio of H<sub>2</sub>O/Al from the precursor could give an impact to the morphology of the synthesized product. When the water content was increased, the Boehmite plates would get larger and have thin sheet-like structure. It was confirmed that mesoporous alumina from red mud has an excess water content. The wormlike structure from AMA-72 was a characteristic structure from alumina that synthesized by adding surfactant (de Llobet *et al.* 2013). The porous structure of alumina (Fig. 10 (a) and (b)) resulted the formation of irregular pores. Beck *et al.* (1992) reported that molar ratio of surfactant and aluminum < 1 would make hexagonal surfactant system with a regular pore structure. It might be different case since the surfactant used in this study was CTAB. According to Cheng *et al.* (1995), when synthesis has been done with concentration of CTAB < 40%, the synthesized product would exhibit irregular mesopore. Since the mass ratio of CTAB and alumina salt was 1.57, it could be understood that the concentration of CTAB inside the precursor was way below 40% so the product would be expected to possess an irregular pores and shape. These findings also have been reported by Ramdhani *et al.* (2018). The dark part from the AMA-72 showed the close packed of

platelets created by random stacking of nano-platelets. The higher water content from precursor, the tighter agglomeration was formed (Huang *et al.*, 2014). We predicted that the slit-like pore that was seen from hysteresis loop (Fig. 6) resulted from this randomly stacked of nano-platelets.

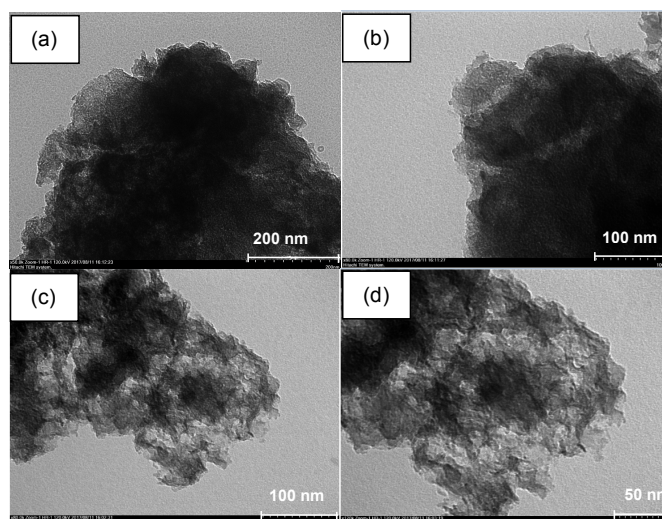


**Fig 10.** TEM images of AMA-72.

#### Acidity study

Alumina is one of the solids that has a strong Lewis acid site (Parry, 1963). In this study, the synthesized product was tested using pyridine to identify the surface acidity. After pre-treatment using pyridine sorption, the product was characterized with FTIR and the results were showed in Fig. 11 and Fig. 12.

The infrared spectra showed peak in the range wavenumber of 1447-1440 cm<sup>-1</sup> for all samples. This peak was identified as characteristic peak for Lewis acid that indicated interaction of pyridine and alumina acid sites (Platon and Thomson, 2003). The peak for Brønsted acid was not found in the wavenumber ~1550 cm<sup>-1</sup>. This result showed that the product has Lewis acid sites on the surface but not Brønsted acid sites. We concluded that mesoporous alumina synthesized from red mud still has Lewis acid site even though not as strong as mesoporous alumina synthesized from commercial material. Therefore, mesoporous alumina has potential to be catalyst support for increasing surface area and Lewis acid sites of the catalyst.

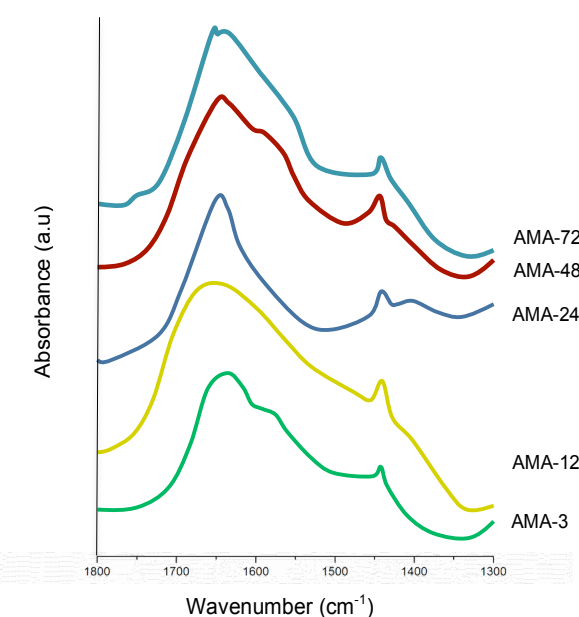

**Fig 11.** Pyridine-FTIR Spectra of mesoporous alumina from red mud with variation of crystallization time.

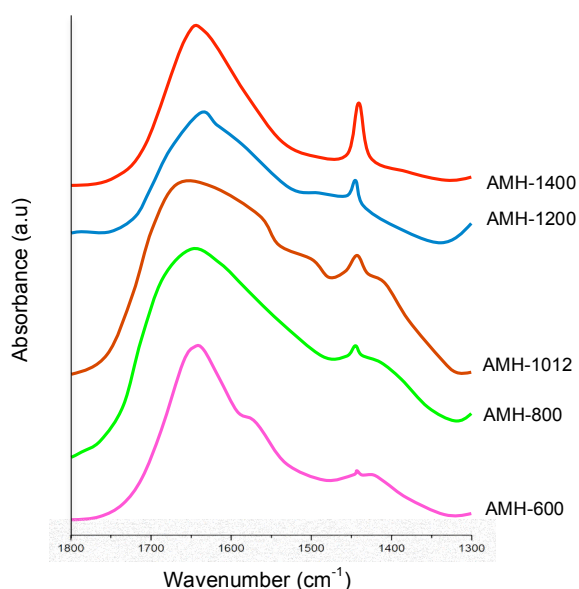


Fig 12. Pyridine-FTIR Spectra of mesoporous alumina from red mud with variation of H<sub>2</sub>O/CTAB molar ratio.

## CONCLUSION

This study has been proved that bauxite residue (red mud) could be employed as alumina source for synthesis of mesoporous alumina with CTAB as template. The effects of crystallization time and H<sub>2</sub>O/CTAB molar ratio were investigated and the obtained results showed the significant effects on mass of product and acidity of surface. Increasing time of synthesis and H<sub>2</sub>O/CTAB molar ratio caused the increase in mass of product and presence of Lewis acid sites on the surface.

## ACKNOWLEDGEMENT

The authors gratefully acknowledge the research funding provided by the Ministry of Research, Technology and Higher Education of Indonesia 2017-2018. They would also like to thank the Research Center for Nanoscience and Nanotechnology (RCNN), Institut Teknologi Bandung for TEM measurement.

## REFERENCES

- Beck, J., Vartuli, J., Roth, W., Leonowicz, M., Kresge, C., Schmitt, K., et al. (1992). A new family of mesoporous molecular sieves prepared with liquid crystal templates. *Journal of American Chemistry Society*, 114, 10834-10843.
- Brunori, C., Cremisini, C., Massanisso, P., Pinto, V., & Torricelli, L. (2005). Reuse of a treated red mud bauxite waste: Studies on environmental compatibility. *Journal of Hazardous Materials*, B117, 55-63.
- Cheng, C. F., He, H., Zhou, W., & Klinowski, J. (1995). Crystal morphology supports the liquid crystal formation mechanism for the mesoporous molecular sieve MCM-41. *Chemical physics letters*, 244(1), 117-120.
- de Llobet, S., Purón, H., Pinilla, J., Moliner, R., Millán, M., & Suelves, I. (2013). Tailored synthesis of organised mesoporous aluminas prepared by non-ionic surfactant templating using a Box-Wilson CCF design. *Microporous and Mesoporous Materials*, 179, 69-77.

- Ghosh, I., Guha, S., Balasubramaniam, R., & Kumar, A. V. (2011). Leaching of metals from fresh and sintered red mud. *Journal of Hazardous Materials*, 185, 662-668.
- Huang, B., Bartholomew, C. H., & Woodfield, B. F. (2014). Facile synthesis of mesoporous  $\gamma$ -alumina with tunable pore size: The effects of water to aluminum molar ratio in hydrolysis of aluminum alkoxides. *Microporous and Mesoporous Materials*, 183, 37-47.
- Isley, S.L., & Penn, R.L. (2008). Titanium dioxide nanoparticle: Effect of sol-gel pH on phase composition, particle size, and particle growth mechanism. *The Journal of Physical Chemistry C*, 112, 4469-4474.
- Kumar, S. (2015). The properties and performance of red mud-based geopolymeric Masonry blocks. In Pacheco-Torgal, F., Lourenço, P.B., Labrincha, J.A., Kumar, S., & Chindaprasirt, P. (Ed.) *Eco-Efficient Masonry Bricks and Blocks* (pp. 311-328), Woodhead Publishing, Elsevier.
- Li, Y., White, A., & Lim, S. (2004). Low temperature synthesis and microstructural control of titania nano-particles. *Journal of Solid State Chemistry*, 177, 1372-1381.
- Liang, W. T., Couperthwaite, S. J., Kaur, G., Yan, C., Johnstone, D. W., & Millar, G. J. (2014). Effect of strong acids on red mud structural and fluoride adsorption properties. *Journal of Colloid and Interface Science*, 423, 158-165.
- Liu, Q., Wang, A., Wang, X., & Zhang, T. (2007). Morphologically controlled synthesis of mesoporous alumina. *Microporous and Mesoporous Materials*, 100, 35-44.
- Moatti, A., Javadpour, J., Anbia, M., & Badiei, A. (2014). The correlation between aging time and pore characteristics in the synthesis of mesoporous Al<sub>2</sub>O<sub>3</sub>. *Ceramics International*, 40, 10231-10236.
- Pan, F., Lu, X., Wang, T., Wang, Y., Zhang, Z., & Yan, Y. (2013). Triton X-100 directed synthesis of mesoporous  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> from coal-series kaolin. *Applied Clay Science*, 85, 31-38.
- Pan, F., Lu, X., Wang, T., Wang, Y., Zhang, Z., Yan, Y., et al. (2013). Synthesis of large-mesoporous  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> from coal-series kaolin at room temperature. *Materials Letters*, 91, 136-138.
- Parry, E. P. (1963). An infrared study of pyridine adsorbed on acidic solids. Characterization of surface acidity. *Journal of Catalysis*, 2(5), 371-379.
- Petushkov, A., Yoon, S., & Larsen, S. (2011). Synthesis of hierarchical nanocrystalline ZSM-5 with controlled particle size and mesoporosity. *Microporous Mesoporous Materials*, 137, 92-100.
- Platon, A., & Thomson, W. (2003). Quantitative Lewis/Bronsted ratios using DRIFTS. *Applied Catalysis in Industrial Engineering: Chemical Research*, 42, 5988-5992.
- Qoniah, I., Prasetyoko, D., Bahruji, H., Triwahyono, S., Jalil, A. A., Suprpto, et al. (2015). Direct synthesis of mesoporous aluminosilicates from Indonesian Kaolin clay without calcination. *Applied Clay Science*, 118, 290-294.
- Ramdhani, E. P., Suprpto, Prasetyoko, D., & Hartati. (2018). Synthesis of mesoporous alumina from red mud. *Indonesian Journal of Chemistry. in press*.
- Rousseaux, J. M., Weisbecker, P., Muhr, H., & Plasari, E. (2002). Aging of precipitated amorphous alumina gel. *Industrial & Engineering Chemistry Research*, 41(24), 6059-6069.
- Snars, K., Gilkes, R., & Wong, M. (2004). The liming effect of bauxite processing residue (red mud) on sandy soils. *Soil Research*, 42 (3), 321-328.
- Sushil, S., & Batra, V. S. (2012). Modification of red mud by acid treatment and its application for CO removal. *Journal of Hazardous Materials*, 203, 264-273.
- Wang, C.C., & Ying, J.Y. (1999). Sol-gel synthesis and hydrothermal processing of anatase and rutile titania nanocrystals. *Chemistry of Materials*, 11(11), 3113-3120.
- Xia, Y., Yang, P., Sun, Y., Wu, Y., Mayers, B., & Gates, B. (2003). One-dimensional nanostructures synthesis, characterization, and applications. *Advance Materials*, 15, 353-390.
- Yue, M. B., Jiao, W. Q., Wang, Y. M., & He, M. Y. (2010). CTAB-directed synthesis of mesoporous  $\gamma$ -alumina promoted by hydroxy polyacids. *Microporous and Mesoporous Materials*, 132, 226-231.