

# Compressive strength and porosity tests on bovine hydroxyapatite-gelatin-chitosan scaffolds

*by* Nadia Kartikasari

---

FILE	NADIA_KARTIKASARI_AUP_1_FEB_2017.DOC (1.29M)		
TIME SUBMITTED	17-FEB-2017 10:42AM	WORD COUNT	3228
SUBMISSION ID	772253088	CHARACTER COUNT	18308

## Compressive strength and porosity tests on bovine hydroxyapatite-gelatin-chitosan scaffolds

Nadia Kartikasari,<sup>1</sup> Anita Yuliati,<sup>2</sup> and Indah Listiana<sup>3</sup>

<sup>1</sup>Graduate student of Dental Health Science

<sup>2</sup>Department of Dental Materials

<sup>3</sup>Department of Oral Biology

Faculty of Dental Medicine, Universitas Airlangga  
Surabaya - Indonesia

### ABSTRACT

**Background:** Degenerative diseases, aggressive periodontitis, trauma, jaw resection, and congenital abnormalities can cause defects in jaw bone. The surgical procedure for bone reconstruction currently performed is Bone Regeneration Graft (BRG). Unfortunately, this procedure still has many disadvantages. Thus, tissue engineering approach is necessary to be conducted. The main component used in this tissue engineering is scaffolds. Scaffolds used in bone regeneration is expected to have appropriate characteristics with bone, such as high porosity and swelling ratio, low degradation rates, and good mechanical properties. For those reasons, this research used scaffolds made from bovine hydroxyapatite (BHA), gelatin (GEL), and chitosan (K) /BHA-GEL-K as one of biomaterial candidates for bone regeneration. **Purpose:** This research aimed to determine compressive strength value and porosity size of BHA-GEL-K scaffolds. **Method:** Compressive strength of BHA-GEL-K scaffolds was tested using autograph, while porosity size was measured using SEM. **Result:** BHA-GEL-K scaffolds had a mean compressive strength value of 174.29 kPa and a porosity size of  $31.62 + 147.06 \mu\text{m}$ . **Conclusion:** It can be concluded that BHA-GEL-K scaffolds has a good compressive strength, but not yet resemble real bone mass, while porosity of BHA-GEL-K scaffold is appropriate for bone tissue regeneration application.

**Keywords:** scaffolds; bovine hydroxyapatite; gelatin; chitosan; compressive strength; porosity

**Correspondence:** Nadia Kartikasari, <sup>2</sup>Graduate student of Dental Health Science, Faculty of Dental Medicine, Universitas Airlangga. Jl. Mayjend. Prof. Dr. Moestopo no. 47, Surabaya 60132, Indonesia. E-mail: nadiakartikasari88@gmail.com

### INTRODUCTION

Degenerative diseases, aggressive periodontitis, trauma, jaw resection, and congenital abnormalities can cause defects in jaw bone.<sup>1,2</sup> In a massive bone defect, space (gap) can emerge. Massive bone defect is still a major challenge in the field of dentistry since bone healing process often cannot successfully restore the shape and size of the jaw bone as the same as the previous ones.<sup>3</sup>

A surgical procedure for bone reconstruction currently performed is bone regeneration graft (BRG). Unfortunately, this procedure still has many disadvantages. Thus, tissue engineering approach is necessary to be conducted. Tissue engineering aims to regenerate damaged structures and tissues. The concept of tissue engineering is combining three basic components of a cell, scaffolds, and signal regulator, called as triad tissue engineering.<sup>1</sup>

Scaffolds are three-dimensional structure used as temporary replacement for damaged natural extra cellular matrixes (ECM). Consequently, the attachment, anchoring, proliferation, migration, and differentiation of cells as well as regeneration of tissue can occur. Scaffolds for bone regeneration have some criteria, such as good mechanical properties, high porosity and swelling ratio, and low degradation.<sup>4,5</sup>

The mechanical properties of scaffolds are expected equal with mechanical properties in normal bone. The mechanical properties can be measured by several parameters. The most widely used parameter is compressive strength. Compressive strength is an ability of a material to withstand the burden of pressure. Meanwhile, porosity of scaffolds is required for cell attachment. Porosity can also determine the mechanical properties of scaffolds. The size of the scaffolds porosity can be observed using a scanning electron microscope (SEM).<sup>6</sup>

In the last few years, biomimetic scaffolds made of hydroxyapatite (HA), gelatin (GEL), and chitosan (K) /HA-GEL-K scaffolds began to be developed. Scaffolds with the composition of HA-GEL-K is expected to resemble ECM bone, which consists of inorganic components (70%) and organic components (30%).<sup>7</sup> Hydroxyapatite ( $\text{Ca}_{10}(\text{PO}_4)_6(\text{OH})_2$ ) is the biggest inorganic component. HA is osteoconductive and biocompatible, that is able to integrate well and strongly in the host bone.<sup>8</sup> Hydroxyapatite can also be obtained from synthesis and natural materials, such as bovine hydroxyapatite (BHA). Bovine hydroxyapatite has similarities with HA in humans, and is considered as non-toxic material.<sup>3</sup>

Gelatin is a type-I collagen considered as the major organic component in bone (90%). The main advantage of the GEL is increasing attachment and growth of cells since GEL has many arginine-glycine-aspartic acid (RGD) protein chains and sequences. Gelatin is also biodegradable and biocompatible, but has low biomechanical properties.<sup>9</sup>

In addition, chitosan has the same structure as glycosaminoglycans (GAG), a non-collagen organic component of bone. Chitosan is biocompatible, biodegradable, bioactivity, and osteoconductive. Chitosan also has anti-microbial activity. Chitosan can help cell attachment, differentiation, and migration.<sup>6</sup> Thus, integration of HA, GEL, and K in scaffolds is expected to improve the mechanical and biological properties so that it can be considered as ideal scaffolds used for bone regeneration. GEL HA-K scaffolds with a ratio of 70:15:15 (w/ w/ w) is a good biomaterial candidate for tissue engineering in bone.<sup>10</sup>

Unfortunately, there are still no recent researches on GEL HA-K scaffolds explaining the origin of the HA used. Therefore, this research focused on the use of HA derived from bovine bones developed by Bank of Tissue in Dr. Soetomo Hospital, Surabaya. This research aimed to determine the value of compressive strength and the size of porosity derived from BHA-GEL-K scaffolds with ratio 70:15:15 (w/ w/ w). BHA-GEL-K scaffolds are expected to be biomaterials for regenerative therapy development in bone defects in the field of dentistry.

## MATERIALS AND METHODS

Materials used were BHA (a particle size of <150 µm made from bovine bones produced by Bank of Tissue in Dr. Soetomo Hospital, Surabaya), gelatin (ROUSSELOT, Ghuangdong, China), chitosan (Sigma 93646, USA), a deacetylation degree of >81%, 10% NaOH (PT. Brataco), 2% acetic acid, and distilled aqua (PT. Duta Farma).

BHA-GEL-K scaffolds conducted in this research were based on a modification of procedures for producing scaffolds from previous research. 9 ml of 2% acetic acid was mixed with 0.375 grams of gelatin using magnetic stirrer (DragonLab, MS-Pro-H280). 1.75 grams of BHA was mixed with 5 ml of distilled aqua, and allowed to settle. The sedimented BHA that had already been wet was soaked into the mixture, and then added 0.375 gram of chitosan and 2 ml of 10% NaOH. The mixture was put into scaffolds molds. Scaffolds were made with two different sizes diameter of 8 mm and a height of 10 cm, and diameter of 5 mm and a height of 5 mm. Scaffolds in molds then was frozen -80° C for 24 hours and then dried using freeze dryer (VirTis Bechtol "K" Series) for 2 x 24 hours.<sup>10,11</sup>

Compressive strength test was performed on scaffolds with a diameter of 8 mm and a height of 10 cm. The sizes of scaffolds used were adjusted with the specification of the tools used. The sizes of the surface area of BHA-GEL-K scaffolds were measured. Autograph table (Shimadzu Ag-10 TE) was covered with paper. Scaffolds were placed in the middle of the table with the vertical axis position, perpendicular to the plane of the samples. Autograph tool was switched on, and the samples were pressed with a speed of 10 mm/ min with a load cell compress machine of 100 kN until scaffolds were distorted. The tool then automatically stopped, and the number figured out was noted.<sup>12</sup> Compressive strength value then was calculated using the following formula.<sup>13</sup>

$$\text{Compressive strength (N/mm}^2\text{)} = \frac{\text{Force (Newton)}}{\text{Surface area (mm}^2\text{)}}$$

In this research, the number generated by the autograph tool was in a unit of kgf (kilogram force). The compressive strength value was in a unit of N/ mm<sup>2</sup>, so this value had to be converted to Newton first before compressive strength value was calculated. Compressive strength value

commonly used is in a standard unit of Pascal (Pa), so the final compressive strength value then had to be converted into kPa.<sup>12</sup>

Scaffolds used for porosity test was scaffolds with a diameter of 5 mm and a height of 5 mm. Porosity size measurement procedure was performed by using SEM (FEI, Inspect-S50). In the initial preparation, SEM holders were taken and coated with carbon tape. Carbon tape used was double-sided carbon tape. One side was attached to the SEM holders, and the other side was attached to the scaffolds. Samples in the form of scaffolds were non-conductor materials that had to be coated before. Coating was conducted using a sputter coater (Qourum) by inserting BHA-GEL-K scaffolds and their holders in the sputter coater, and vacuum then was performed for 30 minutes. After the vacuum was done, plasma coating was conducted for 3 seconds using Au and Pb. The samples having coating were put into the SEM holders, and vacuum was carried out for 5 minutes. After that, the program for the SEM was started, and then SEM images appeared on the monitor. Pictures were taken at a magnification of 75x, 100x, and 250x. Scaffolds porosity measurement was performed on pictures with a magnification of 100x. In one field of view, the largest porosity size was selected corresponded to the number of samples required. Porosity size was measured by drawing a line on the selected porosity.

## RESULTS

Scaffolds were made by mixing powdered bovine hydroxyapatite (BHA), gelatin (GEL), and chitosan (K) as seen in Figure 1. The results of compressive strength and porosity tests on BHA-gel-K scaffolds can be seen in Table 1. The mean value of compressive strength was  $174.29 + 31.62$  kPa, while the mean porosity size was  $147.06 \mu\text{m} + 27.02$  ( $n = 7$ ).

Porosity size was measured based on the pore diameter of the SEM image. Eleven porosity sizes were measured and used as samples. SEM images with a magnification of 75x resulted can be seen in Figure 2. With the magnification of 75x, almost the entire porosity surface of BHA-GEL-K scaffolds could be seen. With a magnification of 100x and 250x, porosity sizes seemed much larger. The blue arrow indicates porosity on the surface of the scaffolds.

Figure 3 shows SEM images at 100x magnification used in this research. In the picture, how porosity measurements conducted can also be seen. Porosity measurements were performed by selecting the largest porosity to represent the scaffolds porosity. Green lines were drawn from one point to another. The length of the green lines was the size of pores in the scaffolds. The length of the green line then was calculated using a unit of  $\mu\text{m}$ . The total number of the measured porosity size was 11.

## DISCUSSION

Tissue engineering is one of therapeutic methods that have been widely used and developed recently. Tissue engineering is regarded as a promising procedure for a biological component of a bone substitute that can be used in all kinds of bone damage.<sup>6</sup> Scaffolds is also considered as an important component in tissue engineering. Scaffolds act as substitute for ECM so that bone regeneration can occur. Every tissue actually needs scaffolds that has different biomechanical and biological properties from others.<sup>14</sup> Thus, selection of materials used for composing scaffolds is an important factor in the success of using scaffolds since the materials selected will affect the final and functional characteristics of the tissue formed.

In this research, scaffolds was made of mixed materials derived from bovine HA/ bovine hydroxyapatit (BHA), GEL, and K. HA is an osteoconductive material with the main composition of calcium (Ca) and phosphate (P). Calcium and phosphate in HA can act as regulators of signal in bone tissue engineering, as well as basic ingredients in formation of new bone tissue.<sup>15</sup> In this research, a natural HA used was derived from bovines. BHA used was manufactured by Bank of Tissue in Dr. Soetomo Hospital, Surabaya with product validation in accordance with the standards set by the Ministry of Health and APASTB (Asian Pacific Association of Surgical Tissue Bank).<sup>16</sup> BHA has no toxic properties, but similar to human HA, it has a porosity size of 150-360  $\mu\text{m}$  and high osteoconductivity, as well as can easily integrate with the surrounding bones.<sup>17</sup> BHA, consequently, has been widely studied and applied for bone tissue regeneration. A previous research even indicates that the use of BHA scaffolds planted with MSC on rabbit defected bone can regenerate the bone well. It is characterized by an increase in type I collagen and osteocalcin.<sup>2</sup>

Other main components in this research were gelatin and chitosan. The objectives of adding gelatin and chitosan as adhesive materials for binding BHA is to improve the effectiveness of BHA in binding the active ingredients and to reduce the fragility of BHA. Gelatin is a denatured collagen product that plays an important role in cell adhesion and proliferation. Application of gelatin for bone regeneration is generally combined with other materials since gelatin has a low mechanical property. Scaffolds made of HA-GEL is considered as a suitable environment for the growth of periodontal ligament fibroblasts, Human Mesenchymal Stem Cells (HMSC), and primary cells from human pelvic bone.<sup>18</sup> Chitosan, on the other hand, is a deacetylation product of chitin which has a structure similar to glycosaminoglycans (GAG), a non-organic component in bone collagen. GAG modulates bone precursor cells to the defect area, and helps cell differentiation to regulate protein that is essential for the bone regeneration.<sup>19</sup>

Consequently, the combination of BHA, GEL, and K is expected to form scaffolds similar to ECM in the bones. Those components of scaffolds interact with each other. Organic signals of

chitosan and gelatin then will cover HA particles. This is consistent with interactions that occur in normal bone components, in which organic components will cover inorganic components.<sup>11</sup>

Moreover, the mechanical properties of scaffolds are factors that also must be taken into account in the process of making scaffolds. Scaffolds must be strong enough to withstand mechanical stresses derived from the surrounding tissue. Therefore, the low mechanical properties on scaffolds can cause dimensional changes in scaffolds. The value of compressive strength in this research was lower than the value of compressive strength in cancellous bone, 2-12 MPa.<sup>20</sup> This can happen because in this research there was no crosslink agent added. The addition of crosslink agent will trigger crosslinking between molecules of the materials forming scaffolds.<sup>21</sup> In addition, the materials can also make crosslink bonds between the molecules stronger and prevent molecular bonds between the molecules shifting. The stronger bonds between the molecules then will improve the mechanical and biological properties of scaffolds.<sup>22</sup>

Another important property that should be owned by scaffolds is an appropriate size of porosity. Porosity size is related to cell adhesion and migration as well as diffusion of nutrients and removal of metabolic waste. In this research, all samples had a pore size of more than 100  $\mu\text{m}$ , and the mean porosity size of BHA-GEL-K scaffolds was 147.06  $\mu\text{m}$ . This is consistent with a previous research stating that the minimal pore size of scaffolds is 100-150  $\mu\text{m}$ .<sup>6</sup> The appropriate porosity size is used for the attachment of MSC-sized 17.9 - 30.4  $\mu\text{m}$ .<sup>23</sup> The porosity size that is too small will lead to limited cell migration as well as disrupted nutrient and metabolic waste diffusion. When this occurs, it will cause necrosis of scaffolds. Meanwhile, the porosity size of scaffolds that is too big will cause the cells to be easily separated from the scaffolds.

It can be concluded that BHA-GEL-K scaffolds has a good value of compressive strength, but not yet resemble bone mass. Therefore, further researches use BHA-GEL-K scaffolds with addition of cross linking agent should be conducted to increase the value of compressive strength. However, porosity of BHA-GEL-K scaffolds is suitable for bone tissue regeneration application.


## REFERENCES

1. Lanza R, Langer R, Vacanti J. Principles of tissue engineering. 3<sup>rd</sup> ed. UK: Elsevier Academic Press; 2007. p. 845-56, 861-3, 1095-103.
2. Wattanutchariya W, Changkowchai W. Characterization of porous scaffolds from chitosan-gelatin/hydroxyapatite for bone grafting. International multi-conference of engineers and computer scientists volume II. Hong Kong, March 12–14 2014; p 1-5
3. Ferdiansyah, Rushadi D, Rantam FA, Aulani'am. Regenerasi pada massive bone defect dengan bovine hydroxyapatite sebagai scaffolds mesenchymal stem cell. JBP 2011; 13(3): 179-195.

4. Peter M, Binulai NS, Nair SV, Selvamurugan N, Tamura H, Jayakumar R. Novel biodegradable chitosan-gelatin/nano-bioactive glass ceramis composite scaffolds for alveolar bone tissue engineering. *Chemical Engineering J* 2010; 353-61.
5. Sadeghi D, Nazarian H, Nazanin M, Aghalu F, Nojehdehyan H, Dastjerdi EV. Alkaline phosphatase activity of osteoblast cells on three-dimensional chitosan-gelatin/hydroxyapatite composite Scaffolds. *Journal Dental School* 2013; 30(4): 203-9.
6. Costa-Pinto AR, Reis RL, Neves NM. Scaffolds based bone tissue engineering: the role of chitosan. *Tissue Engineering J* 2011; 17(5): 1-17.
7. Sobczak A, Kowalski Z, Wzorek Z. Preparation of hydroxyapatite from animal bones. *Acta of Bioengineering and Biomechanics J* 2009; 11(4): 23-28.
8. Li J, Dou Y, Yang J, Yin Y, Zhang H, Yao F, Wang H, Yao K. Surface characterization and biocompatibility of micro- and nano-hydroxyapatite/chitosan-gelatin network films. *Materials Science and Engineering C J* 2009; 29: 1207–15.
9. Rodriguez I. Tissue engineering composite biomimetic gelatin sponges for bone regeneration. Thesis. Richmond, Virginia: Virginia Commonwealth University; 2013.
10. Mohamed KR, Beherei HH, El-Rashidy ZM. In vitro study of nano-hydroxyapatite/chitosan–gelatin composites for bio-applications. *Journal of Adv Res* 2014; 5(2): 201–8.
11. Zhao F, Grayson WL, Ma T, Bunnell B, Lu WW. Effects of hydroxyapatite in 3-D chitosan–gelatin polymer network on human mesenchymal stem cell construct development. *Biomaterials J* 2006; 27(9): 1859–67.
12. Budiadin AS. Pengaruh glutaraldehid sebagai crosslink agent gentamisin dengan gelatin terhadap efektifitas bovine hydroxyapatite- gelatin sebagai sistem pengantaran obat dan pengisi tulang. Disertasi. Surabaya: Pascasarjana Universitas Airlangga; 2014.
13. Anusavice KJ, Shen, Rawls. Phillips: science of dental materials. 12<sup>th</sup> ed. China: Elsevier; 2013. p. 50-3.
14. Sadeghi D, Nazarian H, Nazanin M, Aghalu F, Nojehdehyan H, Dastjerdi EV. Alkaline phosphatase activity of osteoblast cells on three-dimensional chitosan-gelatin/hydroxyapatite composite scaffolds. *Journal Dental School* 2013; 30: 203-9.
15. Murphy CM, O'Brien FJ, Little DG, Schindeler A. Cell-scaffolds interactions in the bone tissue engineering triad. *Eur Cell Mater* 2013; 26: 120-32.
16. Ferdiansyah. Ilmu kedokteran regeneratif (regeneratif medicine): inovasi terapi masa depan. Surabaya: Airlangga University Press; 2010. p. 3-18.
17. Ferdiansyah. Regenerasi pada massive bone defect dengan bovine hydroxyapatite sebagai scaffolds stem sel mesenkimal. Disertasi. Surabaya: Pascasarjana Universitas Airlangga; 2010.



18. Rungsiyanont S, Dhanesuan N, Swadison S, Kasugai S. Evaluation of biomimetic scaffolds of gelatin-hydroxyapatite crosslink as a novel scaffolds for tissue engineering: biocompatibility evaluation with human PDL fibroblasts, human mesenchymal stromal cells, and primary bone cells. *J Biomater Appl* 2012; 27(1):47-54.
19. Salbach J, Rachner TD, Rauner M, Hempel U, Anderegg U, Franz S, Simon JC, Hofbauer LC. Regenerative potential of glycosaminoglycans for skin and bone. *J Mol Med* 2012; 90(6): 625-35.
20. Ficai A, Andronescu E, Voicu G, Ficai D. Advances in collagen/hydroxyapatite composite materials: advances in composite materials for medicine and nanotechnology. Rijeka: IN TECH d.o.o; 2011. p. 1-32.
21. Budiati AS. Pengaruh glutaraldehid sebagai crosslink agent gentamisin dengan gelatin terhadap efektifitas bovine hydroxyapatite- gelatin sebagai sistem pengantaran obat dan pengisi tulang. Disertasi. Surabaya: Fakultas Kedokteran Universitas Airlangga; 2014.
22. Haugh MG, Murphy CM, McKiernan RC, Altenbuchner C, O'Brien FJ. Crosslinking and mechanical properties significantly influence cell attachment, proliferation, and migration within collagen glycosaminoglycan scaffolds. *Tissue Engineering* 2011; Part A: 1-8.
23. Ge J, Guo L, Wang S, Zhang Y, Cai T, Zhao RC, Wu Y. The size of mesenchymal stem cells is a significant cause of vascular obstructions and stroke. *Stem Cell Rev J* 2014; 10(2): 295-303.

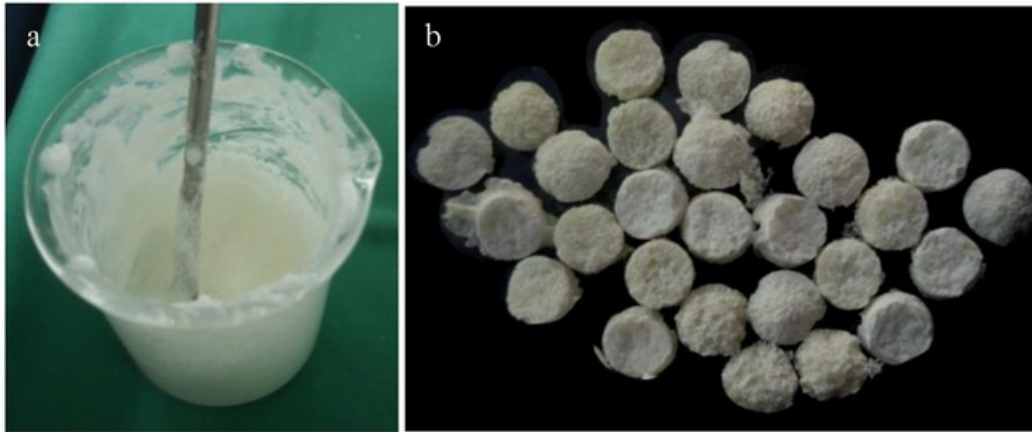




**Figure 1.** (a) White gel derived from the mixing of BHA-GEL-K; and (b) BHA-GEL-K scaffolds.

**Table 1.** Results of compressive strength and porosity tests on BHA-Gel-K scaffolds


Characteristics	Minimal value	Maximal value	Mean $\pm$ SD*
Compressive strength values (kPa)	120.00	200.00	174.29 $\pm$ 31.62
Porosity size ( $\mu\text{m}$ )	107.20	208.60	147.06 $\pm$ 27.02

\* SD: Standard Deviation

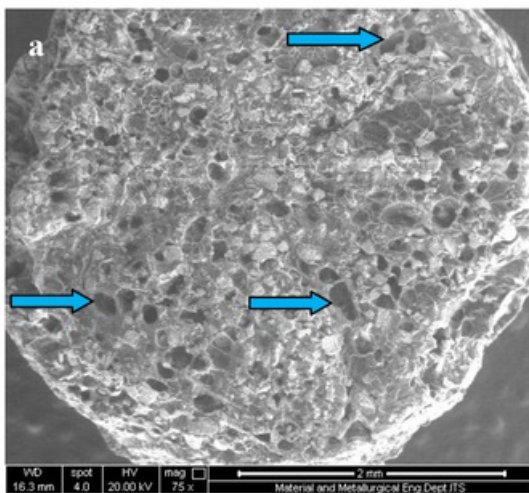

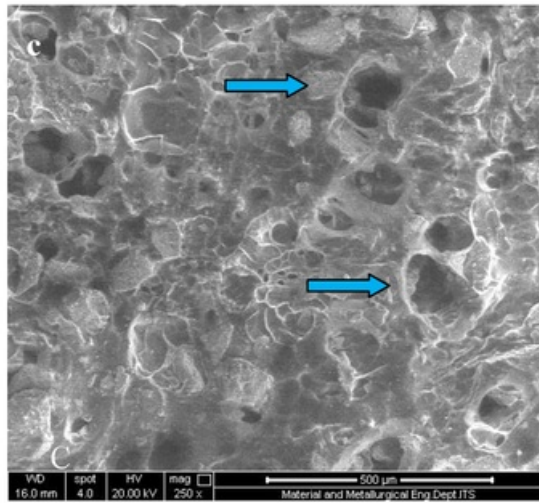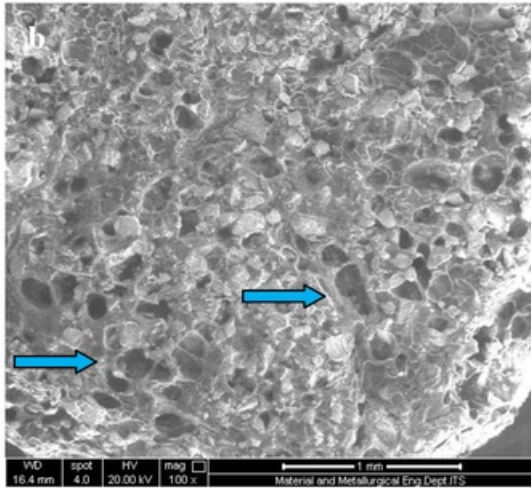

**Figure 2.** (a) Results of SEM test and porosity measurement test at the magnification of 75x; (b)100x; and (c) 250x.

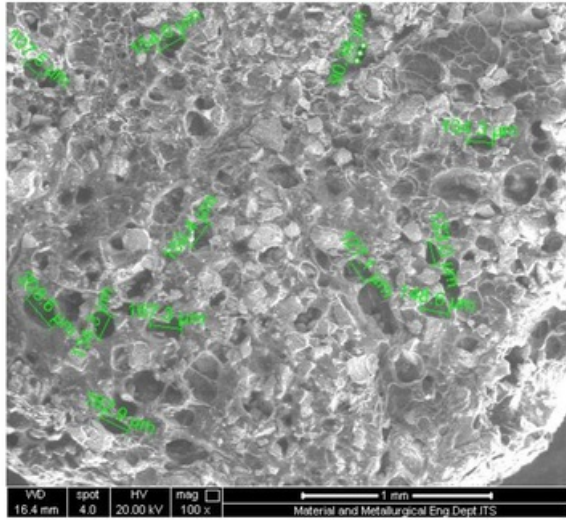

**Figure 3.** Porosity measurement process of BHA-GEL-K scaffolds.

# Compressive strength and porosity tests on bovine hydroxyapatite-gelatin-chitosan scaffolds

---

## GRADEMARK REPORT

---

FINAL GRADE

**/0**

GENERAL COMMENTS

**Instructor**

---

PAGE 1

---

PAGE 2

---

PAGE 3

---

PAGE 4

---

PAGE 5

---

PAGE 6

---

PAGE 7

---

PAGE 8

---

PAGE 9

---

PAGE 10

---

PAGE 11

---

# Compressive strength and porosity tests on bovine hydroxyapatite-gelatin-chitosan scaffolds

## ORIGINALITY REPORT

15%

SIMILARITY INDEX

3%

INTERNET SOURCES

13%

PUBLICATIONS

3%

STUDENT PAPERS

## PRIMARY SOURCES

- 1** Nadia Kartikasari, Anita Yuliati, Indah Listiana, Darmawan Setijanto, Ketut Suardita, Maretaningtyas, Dwi Ariani, Agung Sosiawan. "Characteristic of bovine hydroxyapatite-gelatin-chitosan scaffolds as biomaterial candidate for bone tissue engineering", 2016 IEEE EMBS Conference on Biomedical Engineering and Sciences (IECBES), 2016  
Publication 7%
- 2** Submitted to iGroup  
Student Paper 2%
- 3** Krause, M., R. Oheim, P. Catala-Lehnen, J. M. Pestka, C. Hoffmann, W. Huebner, F. Peters, F. Barvencik, and M. Amling. "Metaphyseal bone formation induced by a new injectable -TCP-based bone substitute: A controlled study in rabbits", Journal of Biomaterials Applications, 2013.  
Publication 1%
- 4** Submitted to University of Charleston  
Student Paper 1%

5	<a href="http://epubs.rcsi.ie">epubs.rcsi.ie</a> Internet Source	1%
6	Springer Series on Polymer and Composite Materials, 2016. Publication	1%
7	Rungsiyanont, S., N. Dhanesuan, S. Swasdison, and S. Kasugai. "Evaluation of biomimetic scaffold of gelatin-hydroxyapatite crosslink as a novel scaffold for tissue engineering: Biocompatibility evaluation with human PDL fibroblasts, human mesenchymal stromal cells, and primary bone cells", Journal of Biomaterials Applications, 2012. Publication	<1%
8	Ana Rita Costa-Pinto. "Scaffolds Based Bone Tissue Engineering: The Role of Chitosan", Tissue Engineering Part B Reviews, 08/02/2011 Publication	<1%
9	<a href="http://www.interceram-review.info">www.interceram-review.info</a> Internet Source	<1%
10	<a href="http://www.ncbi.nlm.nih.gov">www.ncbi.nlm.nih.gov</a> Internet Source	<1%
11	Tong, Shuang, Da-Peng Xu, Zi-Mei Liu, Yang Du, and Xu-Kai Wang. "Synthesis of and in vitro and in vivo evaluation of a novel TGF- $\beta$ 1-SF-CS three-dimensional scaffold for	<1%

bone tissue engineering", International Journal of Molecular Medicine, 2016.

Publication

---

12

Qing Lv. "Fabrication, characterization, and *in vitro* evaluation of poly(lactic acid glycolic acid)/nano-hydroxyapatite composite microsphere-based scaffolds for bone tissue engineering in rotating bioreactors", Journal of Biomedical Materials Research Part A, 12/01/2009

<1%

Publication

---

13

Farshi Azhar, Fahimeh, Ali Olad, and Roya Salehi. "Fabrication and characterization of chitosan–gelatin/nanohydroxyapatite–polyaniline composite with potential application in tissue engineering scaffolds", Designed Monomers & Polymers, 2014.

<1%

Publication

---

14

V.M. Correlo. "Natural Origin Materials for Bone Tissue Engineering – Properties, Processing, and Performance", Principles of Regenerative Medicine, 2011

<1%

Publication

---

15

"Bone and Cartilage Regeneration", Springer Nature, 2016

<1%

Publication

---



EXCLUDE QUOTES ON

EXCLUDE ON

BIBLIOGRAPHY

EXCLUDE MATCHES < 5 WORDS