

# Kinetics of Self-Hydrolysis of Concentrated Sodium Borohydride Solutions at High Temperatures

Rajasree Retnamma<sup>1</sup>, Lin Yu<sup>2</sup>, Carmen M. Rangel<sup>3</sup>, Augusto Q. Novais<sup>1</sup>, Karl Johnson<sup>4</sup>,  
Michael A. Matthews<sup>2</sup>

<sup>1</sup>Energy Systems Modeling and Optimization Unit, National Laboratory of Energy and Geology, Lisbon, Portugal

<sup>2</sup>Department of Chemical Engineering, University of South Carolina, USA

<sup>3</sup>Fuel Cells and Hydrogen Unit, National Laboratory of Energy and Geology, Lisbon, Portugal

<sup>4</sup>Department of Chemical and Petroleum Engineering, University of Pittsburgh, USA


## 1. Introduction

Hydrolysis of sodium borohydride (NaBH<sub>4</sub>) solution over metal catalyst is accepted as a potential technology for delivering H<sub>2</sub> to portable fuel cells. However, unresolved issues such as minimizing the amount of water and the nature of hydration of metaborate by-products limit its hydrogen storage capacities. An alternative method, steam/water vapor hydrolysis, can enhance the hydrogen storage capacities without catalyst, if operating conditions can be optimized [1]. In this approach, solid NaBH<sub>4</sub> absorbs water and deliquesces, forming a highly concentrated viscous solution at near boiling point of water, followed by hydrogen evolution from the concentrated viscous solution. It is also well understood that self-hydrolysis occurs even at room temperature when NaBH<sub>4</sub> is mixed with water and the rate becomes significant at high temperatures. Self-hydrolysis must be arrested to increase the shelf-life of the solution.

The knowledge of the kinetics of self-hydrolysis of concentrated solutions at elevated temperature is thus crucial for: (1) developing steam/water vapor hydrolysis technology; and (2) handling and storage of NaBH<sub>4</sub> solutions. Concentrated solutions have not been studied extensively so far and the reported studies, except two [2, 3], were for buffered dilute solutions of NaBH<sub>4</sub> (< 0.4 wt%) at low temperatures (< 25°C). The present study reports the kinetics of self-hydrolysis of unbuffered, unstabilized concentrated NaBH<sub>4</sub> solutions (10-20 wt%) at high temperatures (25-80 °C) by a differential isothermal isoconversional method.

## 2. Theoretical

The NaBH<sub>4</sub> hydrolysis (self or catalytic) reaction occurs according to[4]:



Where, x is the excess hydration factor.

The mechanism of this process is highly complex and too complicated to be described by a kinetic model within the practical operating conditions [5]. The

isoconversional method is often used to describe such kinetics, where, assuming a single step kinetic approximation, the rate expression is [6].

$$\frac{d\alpha}{dt} = k'_{ap}(T, C_0) f(\alpha) \quad (2)$$

$k'_{ap}(T, C_0)$  is the apparent rate constant, which depends on temperature  $T$  and initial reactant concentration  $C_0$ ,  $\alpha$  is the extent of conversion and  $f(\alpha)$  the conversion function representing the mechanism of the process.

The  $\text{NaBH}_4$  hydrolysis process exhibits maximum rate at the beginning of the reaction, which decreases continuously with the extent of conversion. The most appropriate form of  $f(\alpha)$  for such decelerating type process is the 'reaction order model' [7]:

$$f(\alpha) = (1 - \alpha)^m \quad (3)$$

Where,  $m$  is the reaction order.

Combining Eqs. (2)- (3), and considering the definition of extent of reaction  $\alpha$  gives:

$$\frac{d\alpha}{dt} = k_{ap}(T) C_0^{m-1} (1 - \alpha)^m \quad (4)$$

Where,

$$k'_{ap}(T, C_0) = k_{ap}(T) * C_0^{m-1} \quad (5)$$

For a fixed conversion ( $\alpha$ ), Eq. (4) reduces to

$$\left( \frac{d\alpha}{dt} \right)_{\alpha} = k''_{ap}(T, \alpha) C_0^{m-1} \quad (6)$$

Where,

$$k''_{ap}(T, \alpha) = k_{ap}(T) * (1 - \alpha)^m \quad (7)$$

Equation (6), after a logarithmic transformation:

$$\ln \left( \frac{d\alpha}{dt} \right)_{\alpha} = \ln k''_{ap}(T, \alpha) + (m - 1) \ln C_0 \quad (8)$$

For an isothermal process, the values of  $\ln k''_{ap}(T, \alpha)$  and  $m$  are determined by Eq. (8) for each temperature and  $\alpha$ , for different initial borohydride concentrations.

The temperature dependence of the rate constant  $k_{ap}(T)$  is then expressed by Arrhenius relationship:

$$k_{ap}(T) = A_{ap} \exp\left(\frac{-E_{ap}}{RT}\right) \quad (9)$$

The apparent activation parameters, i.e. apparent activation energy ( $E_{ap}$ ) and pre-exponential factor ( $A_{ap}$ ) are estimated by linear regression of  $\ln k_{ap}(T)$  vs.  $1/T$  data.

### 3. Results and discussion

#### 3.1. Kinetic study

##### *Effect of NaBH<sub>4</sub> conversion and temperature on reaction rate*

The experimental kinetic data used were reported by Yu and Matthews [8], in which the evolution of metaborate formation and NaBH<sub>4</sub> consumption were generated *in-situ* by <sup>11</sup>B NMR technique for unbuffered, unstabilized 10, 15 and 20 wt% NaBH<sub>4</sub> solutions at 25, 60 and 80 °C. The estimated reaction rates from the experimental data for various NaBH<sub>4</sub> conversion, initial NaBH<sub>4</sub> concentration and temperature are given in Table 1. As evident, the reaction rate increases with both temperature and initial NaBH<sub>4</sub> concentration for a fixed NaBH<sub>4</sub> conversion and decreases with increase in NaBH<sub>4</sub> conversion for a fixed temperature and initial NaBH<sub>4</sub> concentration. Table 1 is then exploited to determine the reaction order and apparent activation parameters with respect to NaBH<sub>4</sub> conversion and temperature.

**Table 1.** Reaction rates for different NaBH<sub>4</sub> conversions at various temperatures and initial NaBH<sub>4</sub> concentrations.

NaBH <sub>4</sub> (wt %)	T(°C)	Reaction rates (r, mol L <sup>-1</sup> hr <sup>-1</sup> ) at various NaBH <sub>4</sub> conversions									
		5 %	10 %	15 %	20 %	25%	30 %	35 %	40 %	45%	50%
10			0.086	0.048	0.025	0.015					
15	25		0.136	0.080	0.037	0.027					
20			0.241	0.108	0.057	0.036					
10			0.637	0.559	0.485	0.415	0.345	0.273	0.210	0.158	0.110
15	60		0.740	0.654	0.569	0.483	0.398	0.317	0.242	0.181	0.144
20			0.897	0.797	0.697	0.598	0.499	0.402	0.310	0.227	0.160
10			2.209	2.089	1.970	1.848	1.723	1.597	1.468	1.340	1.201
15	80		2.384	2.241	2.130	1.981	1.862	1.720	1.687	1.470	1.352
20			2.698	2.555	2.410	2.264	2.115	1.964	1.810	1.653	1.493

##### *Effect of NaBH<sub>4</sub> conversion and temperature on reaction order*

Fig. 1 shows the reaction order as estimated by linear regression of rate versus NaBH<sub>4</sub> concentration for various NaBH<sub>4</sub> conversions and. As seen, the reaction order remains constant at a given temperature irrespective of NaBH<sub>4</sub> conversion, while it decreases with increase in temperature irrespective of NaBH<sub>4</sub> conversion. The order decreases from first to 0.25 with increase in temperature from 25 to 80 °C. The estimated

rate constant,  $k_{ap}(T)$  (not given), decreases with increase in  $\text{NaBH}_4$  conversion at constant temperature and increases with temperature at constant  $\text{NaBH}_4$  conversion. It is noteworthy that the variation of reaction order with temperature has been reported by Vyazovkin and Sbirrazzuoli [9] for complex epoxy-anhydride cure kinetics.

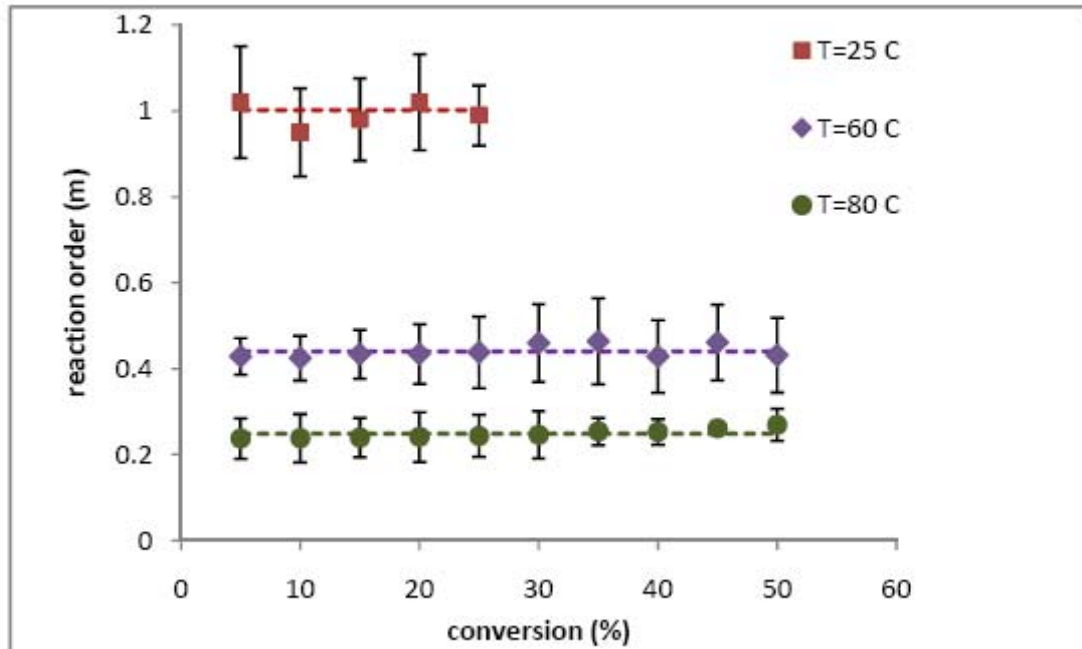


Figure 1. Effect of  $\text{NaBH}_4$  conversion (%) on reaction order

It is well known that the solution viscosity increases during the course of hydrolysis reaction and this has been considered the reason for the observed decrease in rate with reaction time or with  $\text{NaBH}_4$  conversion [5]. The effect of temperature on solution viscosity can be described in terms of Arrhenius-type relationships [10]:

$$\eta = \eta_0 \exp\left(\frac{E_{af}}{RT}\right) \quad (10)$$

where  $\eta$  is the viscosity,  $\eta_0$  the pre-exponential factor and  $E_{af}$  the activation energy of flow. This implies that increase in temperature decreases the solution viscosity. Viscosity is an indication of the solution resistance to flow, and reduced flow resistance at high temperature enhances the interaction between reactant molecules. This in turn lessens the relative contribution of the effect of the concentration on the reaction rate. The deviation from first-order kinetics at low temperatures to fractional-order kinetics at higher temperatures observed in the present study, is attributed to this difference in interaction between reactant molecules with respect to temperature due to change in solution viscosity. It is worthwhile noting that the earlier studies also reported first-order kinetics for self-hydrolysis of  $\text{NaBH}_4$  for lower conversions and temperatures and for buffered solutions [11-15]

### Effect of NaBH<sub>4</sub> conversion on activation energy

The classical kinetic theory defines reaction orders to be constant with temperature. In the present case the observed difference in the reaction order with temperature (Fig. 1) suggests a NaBH<sub>4</sub> conversion effect on the activation energy of the hydrolysis reaction ( $E_a$ ), as given in Table 2. As seen, activation energy increases with NaBH<sub>4</sub> conversion/with formation of metaborate by-products.

It is well documented in literature that the formation of highly basic metaborate by-products in the course of the hydrolysis reaction results in highly viscous solutions. Investigation on the influence of soluble solids content on viscosity, by various researchers, showed that depending on the type of soluble solids content the activation energy of flow ( $E_{af}$ ) might increase or decrease. The effects of soluble solid contents are described by the following expressions [10]:

$$\eta = \eta_1 C^{b_1} \quad (11)$$

$$\eta = \eta_2 \exp(b_2 C) \quad (12)$$

Where  $\eta_i$  and  $b_i$  are constants and  $C$  is the concentration. Hence one may assume that the activation energy of the flow increases with an increase in NaBH<sub>4</sub> conversion due to metaborate by-product formation, which in turn increases the activation energy of the hydrolysis reaction.

**Table 2.** Apparent activation energy determined for various NaBH<sub>4</sub> conversions

NaBH <sub>4</sub> Conversion (%)	<sup>a</sup> $E_{ap}$ (kJ mol <sup>-1</sup> )	R <sup>2</sup>	Standard error	F	P-value
5	64.43 ± 14.5	0.9944	1.14	3914.89	0.025
10	71.03 ± 11.5	0.9998	0.91	6721.39	0.038
15	82.50 ± 13.5	0.9998	1.03	6725.19	0.008
20	89.62 ± 12.5	0.9994	1.96	2152.88	0.013

<sup>a</sup>with ± 95% confidence interval

### 3.2. Modeling

The dependence of apparent activation energy ( $E_{ap}$ ) on  $\alpha$  (Table 2) is described by [16]:

$$E_{ap} = \varepsilon_0 + \varepsilon_1 \ln(1 - \alpha) \quad (13)$$

With  $\varepsilon_0 = 54.2 \pm 1.7$  kJ mol<sup>-1</sup> and  $\varepsilon_1 = -114 \pm 12.2$  kJ mol<sup>-1</sup> (within a 95% confidence interval)

The change in apparent reaction order with temperature (Fig. 1) can be evaluated if the parameters of the kinetic compensation effect (KCE) are known [16]. The present study shows that NaBH<sub>4</sub> hydrolysis follows the following KCE relationship:

$$\ln A_{ap} = \alpha^* + \beta^* E_{ap} \quad (14)$$

With  $\alpha^* = 0.84 \pm 1.2 \text{ (mol L}^{-1}\text{)}^{1-(m+n)} \text{ hr}^{-1}$  and  $\beta^* = 0.36 \pm 0.04 \text{ kJ mol}^{-1}$  (within a 95% confidence interval)

Combining Equations (4), (9), (13) and (14) results in:

$$\frac{d\alpha}{dt} = A_0 (1 - \alpha)^{(m+n)} \quad (15)$$

Where:

$$n = \beta^* \varepsilon_1 - \frac{\varepsilon_1}{RT} \quad (16)$$

$$A_0 = \exp\left(\alpha^* + \beta^* \varepsilon_0 - \frac{\varepsilon_0}{RT}\right) C_0^{m+n-1} \quad (17)$$

Equation (15) shows that the overall process is apparently described with a reaction order  $n+m$  as illustrated in Fig 1. If the values of  $n$  are estimated from equation (16) and  $n+m$  from Fig 1, the values for  $m$  obtained are given in Table 3. As expected,  $m$  tends to a constant value, i.e.  $0.22 \pm 0.01$ .

**Table 3.** Values of  $n$ ,  $n+m$  and  $m$  at different temperatures

T(°C)	$n^{(1)}$ (Eq. 16)	$n+m^{(2)}$ (Fig. 1)	$m^{(3,*)}$
25	0.820	1.04	0.214
60	0.222	0.44	0.218
80	0.024	0.245	0.220

<sup>1</sup> dependent on temperature, <sup>2</sup> apparent reaction order

<sup>3</sup> independent on temperature,  $m = 0.22 \pm 0.01$  (mean  $\pm$  standard deviation)

#### 4. Conclusions

The complex  $\text{NaBH}_4$  self-hydrolysis process is analyzed by a differential isothermal isoconversional method, based on a single-step kinetic approximation. The overall process is apparently described by a 'reaction order' model with temperature dependent reaction order in a wide practical operating window (10-20 wt%  $\text{NaBH}_4$  solution and 25-80 °C).

The apparent activation parameters, i.e. apparent activation energy and pre-exponential factor are conversion dependent and interrelated through the kinetic compensation effect, which explains the observed effect of the temperature on the reaction order.

The apparent activation parameters obtained provide some insight into the theoretical kinetic mechanism, which however remains a matter of heated debates.

## 5. References

- [1] Beaird AM, Davis TA, Matthews MA. Deliquescence in the hydrolysis of sodium borohydride by water vapor, *IndEngChem Res* 2010;49(20):9596-9599.
- [2] Gonçalves, A., Castro, P., Novais, A.Q., Fernandes, V., Rangel, C. and Matos, H., Dynamic modeling of hydrogen generation via hydrolysis of sodium borohydride, In *Proceedings of PRES'07, 24-28 June, Ischia, Italy, (In Chemical Engineering Transactions, Vol. 12, 2007. Editor: Jiri Klemes, AIDIC, Italy, 243.)*
- [3] Andrieux J, Demirci UB, Hannauer J, Gervais C, Goutaudier C, Miele P. Spontaneous hydrolysis of sodium borohydride in harsh conditions. *Int J Hydrogen Energy* 2011;36:224-233.
- [4] Cavaliere S, Hannauer J, Demirci UB, Akdim O, Miele P. Ex situ characterization of  $N_2H_4$ ,  $NaBH_4$  and  $NH_3BH_3$  reduced cobalt catalysts in  $NaBH_4$  hydrolysis. *Catal Today* 2011;170:3-12.
- [5] Retnamma R, Novais AQ, Rangel C.M. Kinetics of hydrolysis of sodium borohydride for hydrogen production in fuel cell applications: A review. *Int J Hydrogen Energy* 2011;36: 9772-9790 (and references thereof).
- [6] Simon P. Isoconversional methods: Fundamentals, meaning and application. *J. Therm. Anal. Calorimetry* 2004;76:123-132.
- [7] Vyazovkin S, Burnham AK, Criado JM, Perez-Maqueda AA, Popescu C, Sbirrazzuoli N. ICTAC Kinetics committee recommendations for performing kinetic computations on thermal analysis data. *ThermChimActa* 2011;520:1-9.
- [8] Yu Lin, Matthews MA. Hydrolysis of sodium borohydride in concentrated aqueous solution. *Int J Hydrogen Energy* 2011;36:7416-7422.
- [9] Vyazovkin S, Sbirrazzuoli N. Kinetic methods to study isothermal and nonisothermal epoxy-anhydride cure. *MacromolChemPhys* 1991;200:2294-2303.
- [10] Ibarz A, Garvin A, Costa J. Rheological behavior of sole (*prunus spinosa*) fruit juices. *J Food Engng* 1996;27:423-430.
- [11] Pecsok R. Polarographic studies on the oxidation and hydrolysis of sodium borohydride. *J AmeChemSoc* 1953;75:2862-2864.
- [12] Stockmayer WH, Miller RR, Zeto RJ. Kinetics of borohydride hydrolysis. *J. Phys. Chem* 1961;65:1076-1077.
- [13] Davis RE, Swain CG. General acid catalysis of the hydrolysis of sodium borohydride. *J AmeChemSoc* 1960;82(22):5949-5950.
- [14] Davis RE, Bromels E, Kibby CL. Borohydrides III. Hydrolysis of sodium borohydride in aqueous solution. *J AmeChemSoc* 1962;84:885-889.

[15] Mesmer RE, Jolly WL. The hydrolysis of aqueous hydroborate. *Inorg Chem* 1962;1:608-612.

[16] Budrugaec P, Popescu C, Segal E. Change of the apparent reaction order with temperature as a consequence of the reaction mechanism complexity. *J. Therm. Anal. Calorimetry* 2001;64:821-827.