

# Heptanuclear hydroxo-bridged copper cluster of the dicubane-like type: structural and magnetic characterisations of $[\text{Cu}_7(\text{OH})_6\text{Cl}_2(\text{pn})_6(\text{H}_2\text{O})_2](\text{C}(\text{CN})_3)_4\text{Cl}_2$ ( $\text{pn} = 1,3\text{-diaminopropane}$ )<sup>†</sup>

Smaïl Triki,<sup>a\*</sup> Franck Thétiot,<sup>a</sup> Jean Sala Pala,<sup>a</sup> Stéphane Golhen,<sup>b</sup> Juan M. Clemente-Juan,<sup>c</sup> Carlos J. Gómez-García<sup>c</sup> and Eugenio Coronado<sup>c</sup>

<sup>a</sup> UMR CNRS 6521, Univ. de Bretagne Occidentale, BP 809, 29285 Brest Cedex, France.

E-mail: [smaïl.triki@univ-brest.fr](mailto:smaïl.triki@univ-brest.fr)

<sup>b</sup> UMR CNRS 6511, Univ. de Rennes 1, 35042 Rennes Cedex, France

<sup>c</sup> Instituto de Ciencia Molecular, Univ. de Valencia, Dr. Moliner 50, 46100 Burjassot, Spain

Received (in Cambridge, UK) 14th June 2001, Accepted 12th September 2001

First published as an Advance Article on the web 5th October 2001


A new polynuclear copper(II) complex  $[\text{Cu}_7(\text{OH})_6\text{Cl}_2(\text{pn})_6(\text{H}_2\text{O})_2](\text{C}(\text{CN})_3)_4\text{Cl}_2$  with hydroxo-bridging ligands has been prepared; the centrosymmetric cluster cation can be described as two  $\text{Cu}_4\text{O}_3\text{Cl}$  distorted cubane units sharing one copper cation.

Various multinuclear copper(II) complexes have been reported in the last decade with a great number of simple and sophisticated bridging ligands;<sup>1–5</sup> however, some nuclearities remain comparatively scarce. In the case of tetranuclear complexes with  $\text{Cu}_4\text{O}_4$  cubane-like clusters some examples have been thoroughly described,<sup>2</sup> but to date little is known about clusters involving more than four metal centres.<sup>3,4</sup> Concerning the heptanuclear copper(II) clusters, as far as we are aware, only one example of the dicubane-like type has been described.<sup>5</sup> Here we report the structure and preliminary magnetic studies of a novel vertex sharing dicubane-like heptanuclear copper(II) cluster  $[\text{Cu}_7(\text{OH})_6\text{Cl}_2(\text{pn})_6(\text{H}_2\text{O})_2](\text{tcm})_4\text{Cl}_2$  (**1**) [ $\text{pn} = 1,3\text{-diaminopropane}$ ;  $\text{tcm}^- = \text{C}(\text{CN})_3^- = \text{tricyanomethanide}$ ] with chloro- and hydroxo-bridging ligands.


1.00 mL (12 mmol) of 1,3-diaminopropane ( $\text{pn}$ ) was slowly added to a warm aqueous solution of  $\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$  (12 mmol) and then an aqueous solution of sodium hydroxide (12 mmol) was added. To the resulting clear solution were immediately and consecutively added concentrated aqueous solutions of  $\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$  (2 mmol) and potassium tricyanomethanide (8 mmol). Slow evaporation gave prismatic blue crystals of  $[\text{Cu}_7(\text{OH})_6\text{Cl}_2(\text{pn})_6(\text{H}_2\text{O})_2](\text{tcm})_4\text{Cl}_2$  (yield 1.28 g, 42%) suitable for crystallography.<sup>‡</sup> The structure of **1** is unique and consists of a centrosymmetric hydroxo-bridged heptanuclear copper(II) cation (Fig. 1) which can be described as two  $\text{Cu}_4\text{O}_3\text{Cl}$  distorted cubanes which share one copper cation (Cu1) (Fig. 1 and 2). The four crystallographically independent Cu(II) centres differ markedly in their co-ordination geometry.

<sup>†</sup> Electronic supplementary information (ESI) available: detailed synthesis and X-ray crystallography of **1**. See <http://www.rsc.org/suppdata/cc/b1/b105231b/>


The central atom (Cu1) presents a strongly elongated octahedral coordination which involves a  $\text{CuO}_4$  equatorial plane with essentially equivalent Cu–O bonds [see Fig. 2(a)] and two semi-coordinated Cl anions in axial positions ( $\text{Cu} \cdots \text{Cl} = 3.029(2)$  Å). The Cu2 and Cu3 cations have distorted square pyramidal  $\text{CuO}_2\text{N}_2\text{Cl}$  environments. In both cases, the basal planes are occupied by two hydroxo bridging ligands (O1 and O3 for Cu2; O2 and O3 for Cu3) and two nitrogen atoms of the chelating  $\text{pn}$  ligand (Cu–O range 1.977–2.016 Å and Cu–N range 1.975–2.021 Å). Both pyramids share a strongly elongated axial position filled by the bridging Cl1 atom ( $\text{Cu2–Cl1} = 2.654(2)$  Å and  $\text{Cu3–Cl1} = 2.679(2)$  Å) (Fig. 1). The co-ordination

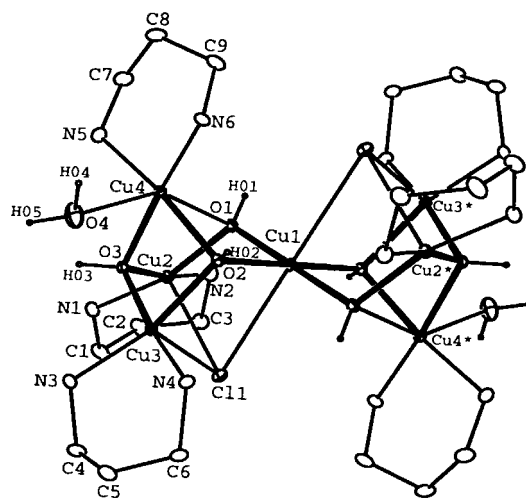

**Fig. 1** ORTEP of the heptanuclear cation in **1** showing atomic labelling scheme (30% probability ellipsoids). Shortest  $\text{Cu} \cdots \text{Cu}$  distances (Å) and selected bond angles ( $^\circ$ ): Cu1–Cu2 3.3796(5), Cu1–Cu3 3.3719(5), Cu1–Cu4 3.1873(5), Cu2–Cu3 3.2829(8), Cu2–Cu4 3.1607(8), Cu3–Cu4 2.9610(8); O1–Cu1–O2 83.9(1), O1–Cu2–O3 84.5(1), O2–Cu3–O3 80.1(1), O1–Cu4–O2 72.0(1), O1–Cu4–O3 73.7(1), O2–Cu4–O3 79.5(1). Code of equivalent positions: (\*)  $\frac{1}{2} - x, \frac{1}{2} - y, 1 - z$ .

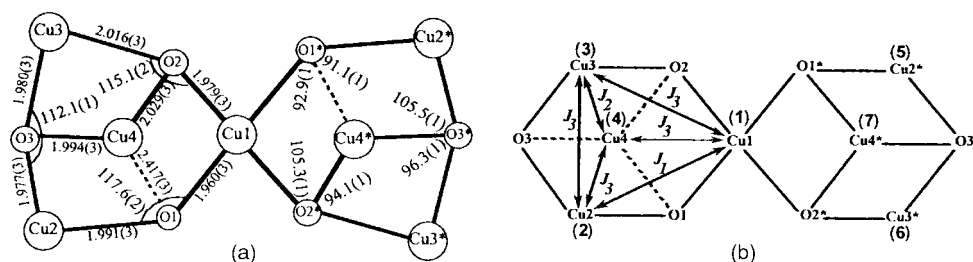

**Fig. 2** (a) Schematic projection of the copper cluster including pertinent bond lengths and bond angles; (b) schematic representation of the magnetic coupling model in **1**. Code of equivalent positions: (\*)  $\frac{1}{2} - x, \frac{1}{2} - y, 1 - z$ .

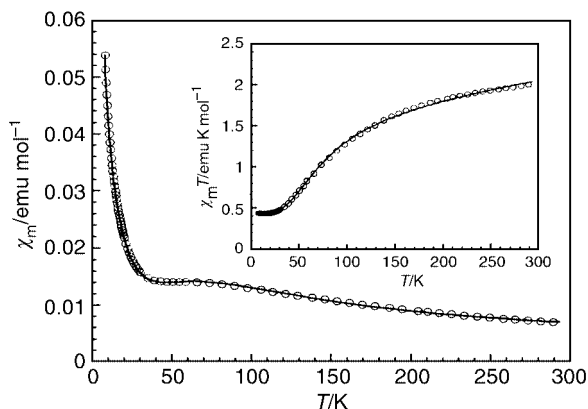

**Fig. 3** Plots of molar susceptibility  $\chi_m$  vs.  $T$  (the inset shows the  $\chi_m T$  product vs.  $T$ ) for **1** measured in a field of 1 T. The solid line was calculated using the magnetic coupling model (see text).

polyhedron of the Cu4 cation can be described as a  $\text{Cu}(\text{N}_2\text{O}_2)(\text{O}_2)$  pseudo-octahedron generated by a  $\text{CuN}_2\text{O}_2$  plane arising from two nitrogen atoms of the chelating pn ligand and the two  $\mu_3$ -hydroxo ligands (O2 and O3), and two axial positions filled by the O1 hydroxo ligand and a water molecule (O4) ( $\text{Cu}\cdots\text{O4} = 2.524(4)$  Å). Note that the O1 hydroxo ligand may be viewed as a  $\mu_2$ -bridging group since it involves two short and one long Cu–O distances as clearly shown on Fig. 2(a). Further examination of the structure shows that the tcm units, which usually act as  $\mu_2$ - or  $\mu_3$ -bridging ligands, are here uncoordinated; however, there are significant hydrogen bonds formed between their nitrogen atoms and the hydroxo-bridging ligands [ $\text{N7}(\text{tcm})\cdots\text{O2} = 2.826(6)$  Å,  $\text{O1-H}\cdots\text{N7} = 167.3(3)^\circ$  and  $\text{N8}(\text{tcm})\cdots\text{O1} = 2.961(6)$  Å,  $\text{O1-H}\cdots\text{N7} = 160.6(2)^\circ$ ]. Such intermolecular hydrogen bonds may contribute to the stabilisation of the cluster conformation.

Magnetic susceptibility data for **1** were collected in the temperature range 2–300 K, the  $\chi_m$  and  $\chi_m T$  product vs.  $T$  plots are depicted in Fig. 3. From room temperature down to 25 K the  $\chi_m T$  product decreases continuously and then reaches a plateau close to  $0.43$  emu K mol $^{-1}$ , which corresponds to an  $S = 1/2$  ground state. This behaviour is indicative of an overall antiferromagnetic coupling between the Cu(II) centres; this is in agreement with the strongly reduced magnetic moment at room temperature ( $\chi_m T = 2.01$  emu K mol $^{-1}$ ). Taking into account the cluster topology and connectivity (Fig. 2), it is possible to distinguish up to six different exchange pathways. However, in order to avoid an overparameterization and in view of the Cu–O–Cu angles and connectivity of the OH bridges ( $\mu_2$ -OH or  $\mu_3$ -OH), these six exchange pathways have been grouped into three averaged different exchange parameters. The magnetic data have been analysed with the following spin Hamiltonian:

$$\hat{H} = -2J_1(\hat{S}_1\hat{S}_2 + \hat{S}_1\hat{S}_5) - 2J_2(\hat{S}_3\hat{S}_4 + \hat{S}_6\hat{S}_7) - 2J_3(\hat{S}_1\hat{S}_3 + \hat{S}_1\hat{S}_4 + \hat{S}_2\hat{S}_3 + \hat{S}_2\hat{S}_4 + \hat{S}_1\hat{S}_6 + \hat{S}_1\hat{S}_7 + \hat{S}_5\hat{S}_6 + \hat{S}_5\hat{S}_7)$$

Calculations have been performed with the magnetism package MAGPACK.<sup>6</sup> The best fit obtained from a least-squares

analysis of the  $\chi_m T$  is  $J_1 = -188.4$  cm $^{-1}$ ,  $J_2 = -52.6$  cm $^{-1}$ ,  $J_3 = -10.8$  cm $^{-1}$  and  $g = 2.15$  ( $R = \sum [((\chi_m T)_{\text{obs}})^2 - (\chi_m T)_{\text{calc}}]^2 / (\chi_m T)_{\text{obs}}^2 = 7.8 \times 10^{-3}$ ). Attempts to fit with only one or two averaged exchange parameters failed. As expected from the structural parameters depicted in Fig. 2(a) (Cu–O distances and Cu–O–Cu angles), the results show the presence of two weak antiferromagnetic interactions ( $J_2$  and  $J_3$ ) associated to the interactions by  $\mu_3$ -OH as have been observed in previous cubane-type systems<sup>2,3</sup> and a strong one ( $J_1$ ) corresponding to the exchange interaction between the two Cu connected by O1 that has a main component of  $\mu_2$ -OH and a large Cu–O–Cu angle ( $117.6^\circ$ ).

This work was supported by CNRS (Centre National de la Recherche Scientifique, UMR 6521), the University of Brest (SUCRI 2E). F. T. thanks the ‘Ministère de l’Education Nationale, de la Recherche et de la Technologie’ for a postgraduate grant.

## Notes and references

‡ Anal. Calc. for  $\text{C}_{34}\text{H}_{70}\text{Cl}_4\text{Cu}_7\text{N}_{24}\text{O}_8$ : C, 26.7; H, 4.6; Cl, 9.3; Cu, 29.1; N, 22.0. Found: C, 26.9; H, 4.6; Cl, 9.2; Cu, 29.2; N, 21.9%. IR data:  $\nu/\text{cm}^{-1}$ : 3293m, 3247m, 2175s, 2168s, 1588m, 1195m, 1037w, 1023w, 900m, 561m, 494m.

Crystal data for **1**.  $\text{C}_{34}\text{H}_{70}\text{N}_{24}\text{O}_8\text{Cl}_4\text{Cu}_7$ ,  $M = 1529.68$ , monoclinic, space group  $C2/c$  (no. 15),  $a = 24.8994(3)$ ,  $b = 11.9801(2)$ ,  $c = 21.4298(3)$  Å,  $\beta = 112.14(6)^\circ$ ,  $U = 5920(2)$  Å $^3$ ,  $Z = 4$ ,  $D_c = 1.72$  g cm $^{-3}$ ,  $\mu(\text{Mo-K}\alpha) = 2.72$  mm $^{-1}$ ,  $T = 288$  K, final  $R = 0.044$ ,  $wR = 0.065$  for 3924 observed reflections [ $I > 4\sigma(I)$ ] and 351 variables.

CCDC reference number 165568. See <http://www.rsc.org/suppdata/cc/b1/b105231b/> for crystallographic data in CIF or other electronic format.

- G. Kolks, S. J. Lippard, J. V. Waszczak and H. R. Lilienthal, *J. Am. Chem. Soc.*, 1982, **104**, 717; S. Teipel, K. Griesar, W. Haase and B. Krebs, *Inorg. Chem.*, 1994, **33**, 456; S. S. Tandon, L. K. Thompson and D. O. Miller, *J. Chem. Soc., Chem. Commun.*, 1995, 1907; V. Tangoulis, C. P. Raptopoulou, S. Paschalidou, A. E. Tsohos, E. G. Bakalbassis, A. Terzis and S. P. Perleps, *Inorg. Chem.*, 1997, **36**, 5270.
- J. W. Hall, W. E. Estes, E. D. Estes, R. P. Scaringe and W. E. Hatfield, *Inorg. Chem.*, 1977, **16**, 1572; L. Walz, H. Paulus, W. Haase, H. Langhof and F. Nepveu, *J. Chem. Soc., Dalton Trans.*, 1983, 657; J. Sletten, A. Sørensen, M. Julve and Y. Journaux, *Inorg. Chem.*, 1990, **29**, 5054; L. P. Wu, T. Kuroda-Sowa, M. Maekawa, Y. Suenaga and M. Munakata, *J. Chem. Soc., Dalton Trans.*, 1996, 2179; X. S. Tan, Y. Fujii, R. Nukada, M. Mikuriya and Y. Nakano, *J. Chem. Soc., Dalton Trans.*, 1999, 2415.
- H. Muhonen, W. E. Hatfield and J. H. Helms, *Inorg. Chem.*, 1986, **25**, 800; V. Tangoulis, S. Paschalidou, E. G. Bakalbassis, S. P. Perlepes, C. P. Raptopoulou and A. Terzis, *Chem. Commun.*, 1996, 1297.
- V. Tangoulis, C. P. Raptopoulou, S. Paschalidou, E. G. Bakalbassis, S. P. Perleps and A. Terzis, *Angew. Chem., Int. Ed. Engl.*, 1997, **36**, 1083.
- J. A. Real, G. D. Munno, R. Chiappetta, M. Julve, F. Lloret, Y. Journaux, J.-C. Colin and G. Blondin, *Angew. Chem., Int. Ed. Engl.*, 1994, **33**, 1184.
- J. J. Borrás-Almenar, J. M. Clemente-Juan, E. Coronado and B. Tsukerblat, *Inorg. Chem.*, 1999, **38**, 6081; J. J. Borrás-Almenar, J. M. Clemente-Juan, E. Coronado and B. Tsukerblat, *J. Comput. Chem.*, 2001, **22**, 985.