

LA-UR- 98-194

Approved for public release;  
distribution is unlimited.

Title: FUNCTIONALLY GRADED BORON CARBIDE

CONF-980/10--

Author(s):

J. J. Petrovic  
K. J. McClellan  
C. D. Kise  
R. C. Hoover  
W. K. Scarborough

RECEIVED

MAY 28 1998

OSTI

Submitted to:

22nd Annual Cocoa Beach Conference and  
Exposition.

January 20-24, 1998

MASTER

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

**Los Alamos**  
NATIONAL LABORATORY

Los Alamos National Laboratory, an affirmative action/equal opportunity employer, is operated by the University of California for the U.S. Department of Energy under contract W-7405-ENG-36. By acceptance of this article, the publisher recognizes that the U.S. Government retains a nonexclusive, royalty-free license to publish or reproduce the published form of this contribution, or to allow others to do so, for U.S. Government purposes. Los Alamos National Laboratory requests that the publisher identify this article as work performed under the auspices of the U.S. Department of Energy. The Los Alamos National Laboratory strongly supports academic freedom and a researcher's right to publish; as an institution, however, the Laboratory does not endorse the viewpoint of a publication or guarantee its technical correctness.

### DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

## **DISCLAIMER**

**Portions of this document may be illegible in electronic image products. Images are produced from the best available original document.**

## FUNCTIONALLY GRADED BORON CARBIDE

J.J. Petrovic, K.J. McClellan, C.D. Kise, R.C. Hoover, and W.K. Scarborough,  
Materials Science & Technology Division, Los Alamos National Laboratory, Los  
Alamos, NM 87545

### ABSTRACT

Fabrication techniques were developed for producing graded porosity  $B_4C$ , and for producing aluminum- $B_4C$  and epoxy- $B_4C$  functionally graded materials. The key fabrication aspect was obtaining the graded porosity  $B_4C$ . The feasibility of producing graded porosity  $B_4C$  using a grading of carbon densification aid produced from a gradient of furfuryl alcohol carbon precursor was demonstrated. This approach is quite promising, but it was not optimized in the present investigation. Graded porosity  $B_4C$  materials were produced by a layering approach using different size distributions of  $B_4C$  powders in the green state, and then densifying the layered assembly by hot pressing at 1900 °C. The hardness of uninfiltated graded  $B_4C$ , aluminum infiltrated  $B_4C$ , and epoxy infiltrated  $B_4C$  was observed to be similar.

### INTRODUCTION

Lightweight body armor is important for the protection of U.S. soldiers in the field. Advanced body armor must satisfy a number of factors:

- Ballistic performance: It must defeat the specified threat in accordance with standards developed by the military and the National Institute of Justice (NIJ).
- Weight: Additional weight carried by the soldier should be minimized. At least a 40% reduction from the present weight at the same or greater threat level.
- Multi-hit capability: Ability of the armor to defeat multiple hits within an approximately 5 cm spacing of hits.
- Articulation: Comfort and ability to conform to body shape and movement.
- Heat load: Removal of body heat during periods of high stress or activity.
- Multi-threat capability: Provide protection from additional threats such as sharp penetrators.

- Protection of extremities: The armor should protect as much of the soldier as possible, including neck and extremities.
- Blunt trauma: A specification that the deflection of the back of the armor not exceed 44 mm. This requirement prevents damage to internal organs and is a major design requirement.
- Cost: For special military applications, cost is not an important factor compared to the value of the soldier, but in most cases cost is important.

The present top-of-the-line body armor vests are the Army PASGT and the Ranger vests. The Ranger vest is capable of defeating an NIJ Level III threat (high powered rifle, 7.62 NATO metal jacket (<2750 ft/s), 5.56 NATO metal jacket, 12 gauge shotgun rifled slug), but only with the use of  $Al_2O_3$  ceramic plate inserts and a vest areal density of greater than 6 pounds/square foot. At the current time, there is no body armor system capable of defeating NIJ Level IV threats, namely armor piercing rifle fire (.30 caliber armor piercing, <2850 ft/s).

The objective of the present work was to develop materials for an FGM-based armor concept, where a hard ceramic front face would transition gradually to an energy absorbing metal or polymer back face. In this concept, the hard ceramic face would blunt the projectile threat, while the tough back face would allow for energy absorption and shrapnel containment.

## MATERIALS

The materials chosen for the FGM-based armor were the following. Boron carbide ( $B_4C$ ) was chosen as the ceramic material since it is very lightweight (density  $2.52 \text{ gm/cm}^3$ ) and very hard (hardness of 30 GPa) (1). Commercial  $B_4C$  powders were obtained from the ESK Corporation. Aluminum was chosen as the metal material because of its light weight, and because of previous work on Al- $B_4C$  cermets (2). A Ciba Geigy 0510 epoxy was chosen as the polymer material, due to its low viscosity and good wetting behavior with  $B_4C$  (3).

## GRADED POROSITY $B_4C$

The key to producing boron carbide-to-aluminum and boron carbide-to-polymer FGM materials is the production of graded porosity  $B_4C$  microstructures. Two approaches were examined: 1) Densification aid gradients; 2) Green density gradients. These approaches were selected because they were considered to be cost effective and commercially viable.

### Densification Aid Gradients

Carbon is the major densification aid for  $B_4C$ . A carbon addition level of approximately 6 wt.% is indicated to be optimum for maximizing the sintered

density, for sintering temperatures in the range of 2170-2270 °C (4). Furfuryl alcohol ( $C_5H_7O_2$ ) was chosen as the source for the addition of carbon to the  $B_4C$  powders (5). Furfuryl alcohol is a liquid at room temperature and uniformly coats fine  $B_4C$  powder particles. This material decomposes to nanosize carbon when heated to 850 °C, producing a 40 wt.% carbon yield. It can be diluted with acetone.

To produce functionally graded porosity in  $B_4C$ , the approach adopted was to start with a 50% dense cold pressed powder disc (31.8 mm diameter x 6.35 mm thick), and then paint furfuryl alcohol layers on one side of the disc, using a simple paint brushing technique. The furfuryl alcohol would then penetrate the cold pressed disc in a graded manner, leading to a gradient in carbon content.  $B_4C$  discs coated in this manner were heat treated to carbonize the furfuryl alcohol (5), then hot pressed in graphite dies at 1900 °C and 20 MPa for one hour in an argon atmosphere, to densify the  $B_4C$ .

The feasibility of this approach was demonstrated, in that a  $B_4C$  pellet with 25% porosity on the painted face and 37% porosity on the unpainted face was produced. Thus, the furfuryl alcohol painting approach was promising. However, for programmatic reasons, it was not possible to optimize this approach to achieve a larger porosity gradient. Optimization of the furfuryl alcohol approach would require applying the furfuryl alcohol in a more controlled manner than hand painting, so that the graded carbon concentrations obtained from its decomposition would be reproducible and better characterized.

### Green Density Gradients

Three different grades of ESK commercial  $B_4C$  powders were used in the investigation. F400 powder had an average particle size of approximately 30  $\mu m$ . F1200 powder had an average particle size of approximately 5  $\mu m$ . 3000F powder had an average particle size of approximately 0.5  $\mu m$ .

These  $B_4C$  powders were employed to produce layered green density materials. Discs were prepared with five 1 mm thick layers of the following powders: 3000F, 3000F/F1200, F1200, F1200/F400, F400. The mixed-powder layers were a 50-50 wt.% mixture. The above five powder configurations were hand-layered in a graphite hot pressing die, and then hot pressed at 1900 °C and 20 MPa for one hour in argon, to densify the layered assembly.

$B_4C$  graded porosity microstructures obtained in this manner are shown in Figure 1. The percent densities of the various layers are: 3000F, 96%; 3000F/F1200, 90%; F1200, 87%; F1200/F400, 66%; F400, 49%. Thus, a substantial porosity gradient was achieved by this approach. Ultrasonic vibration of the green density layers for 30 seconds was effective in grading some of the layer boundaries, particularly at the lower density regions.

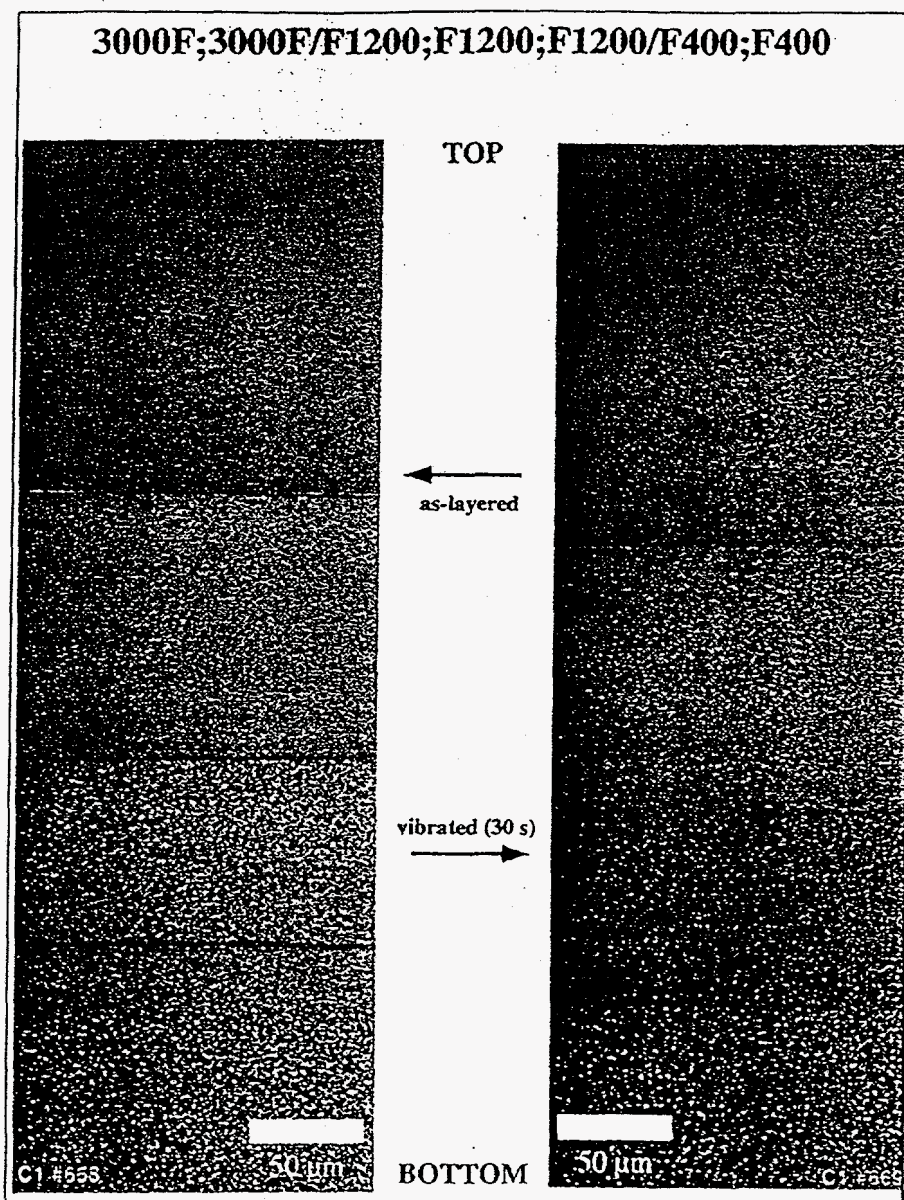


Figure 1: Graded porosity  $B_4C$  microstructures derived from the layering of  $B_4C$  powders. Microstructures for both as-layered and vibrated are shown.

#### INFILTRATION OF GRADED POROSITY $B_4C$


Molten aluminum infiltration of the graded porosity  $B_4C$  materials shown in Figure 1 was performed by the heating of pieces of aluminum stacked above the graded porosity  $B_4C$  pellet. The infiltration was performed by rapidly heating to

1300 °C in vacuum, then immediately cooling. The temperature of 1300 °C was chosen because previous work (2) indicated very low wetting contact angles for aluminum on B<sub>4</sub>C at this temperature. The short time was chosen to minimize the formation of reaction phases between the aluminum and the B<sub>4</sub>C (2).


Epoxy infiltration into the graded porosity B<sub>4</sub>C materials of Figure 1 was performed at room temperature under vacuum conditions. In this case, the graded porosity disc was immersed in the epoxy under vacuum, until the epoxy material hardened.

### PROPERTIES OF FGM B<sub>4</sub>C MATERIALS

The microhardness behavior of the graded porosity B<sub>4</sub>C and of the B<sub>4</sub>C-aluminum and B<sub>4</sub>C-epoxy FGM materials was examined. Figure 2 shows 10 kg Vickers microhardness indentations in the 49% dense layer and the 96% dense layer of the graded porosity B<sub>4</sub>C.

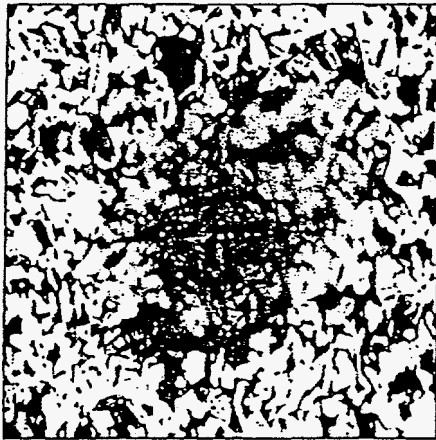

49 % dense

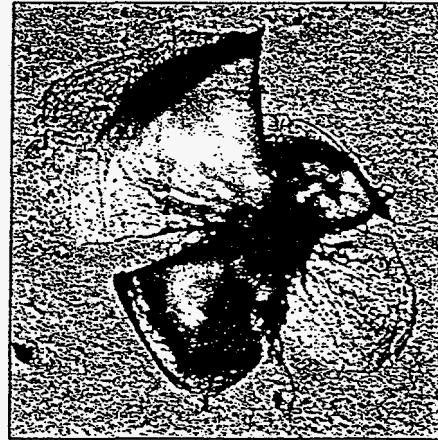

96% dense

Figure 2: 10 kg Vickers indentations in porous and dense layers of graded porosity B<sub>4</sub>C.

The 49% dense layer exhibits little cracking near the indentation, probably due to densification processes under the indentation. In contrast, the 96% dense B<sub>4</sub>C layer shows a highly brittle indentation, with extensive lateral cracking.

A comparison of uninfiltrated, aluminum infiltrated, and epoxy infiltrated B<sub>4</sub>C is shown in Figure 3. Plastic deformation of the aluminum in the aluminum infiltrated FGM is clearly evident in the light aluminum phase at the indentation. The epoxy infiltrated indentation is similar in appearance to the uninfiltrated indentation.



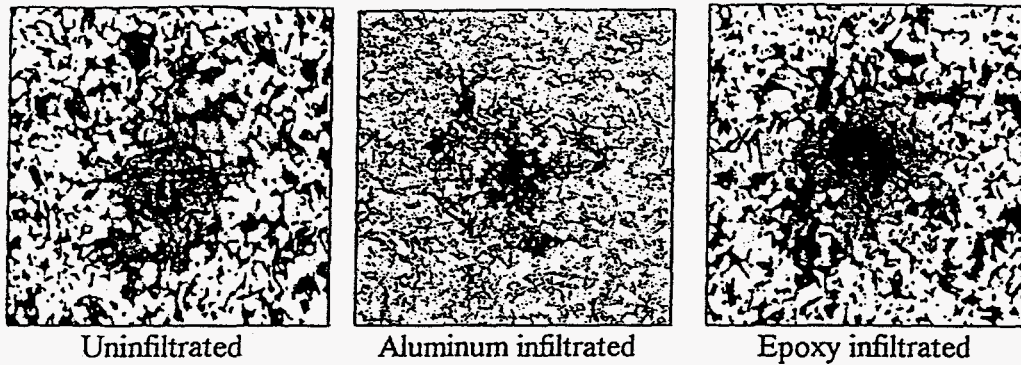


Figure 3: 10 kg Vickers indentations in  $B_4C$  region containing 51% porosity in the uninfiltrated condition.

Hardness versus  $B_4C$  % density is shown in Figure 4, for the uninfiltrated  $B_4C$ , the  $B_4C$ -aluminum FGM, and the  $B_4C$ -epoxy FGM.

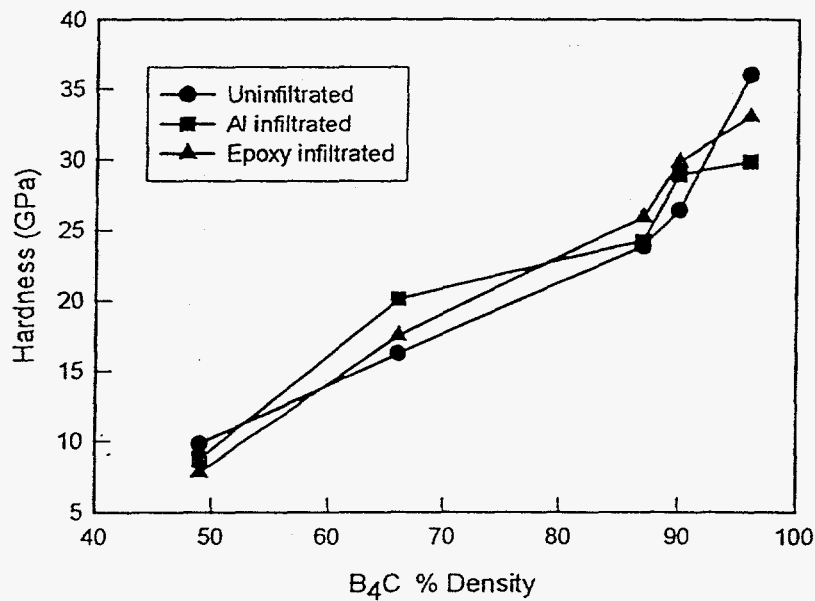


Figure 4: Hardness versus  $B_4C$  density for uninfiltrated, aluminum infiltrated, and epoxy infiltrated condition.

The hardness is little affected by infiltration with either the aluminum or the epoxy. This indicates that the  $B_4C$  is the only phase controlling the hardness, since it is much harder than either the aluminum or the epoxy. The hardness of 49% dense  $B_4C$  is approximately 10 GPa, while that of 96% dense  $B_4C$  is approximately 30-35 GPa.

#### REFERENCES

1. F. Thevenot, "Boron Carbide-A Comprehensive Review", J. European Ceram. Soc., 6, 205-225 (1990).
2. D.C. Halverson, A.J. Pyzik, I.A. Aksay, and W.E. Snowden, "Processing of Boron Carbide-Aluminum Composites", J. Am. Ceram. Soc., 72, 775-780 (1989).
3. D. Hemphill, Los Alamos National Laboratory, private communication.
4. S.L. Dole and S. Prochazka, "Densification and Microstructure Development in Boron Carbide", Proceedings, January 1985 American Ceramic Society Cocoa Beach Meeting, Cocoa Beach, Florida.
5. U.S. Patent No. 3,124,625, H. Sheinberg, J.R. Armstrong, and D.H. Schell, Los Alamos National Laboratory, 10 March 1964.

#### ACKNOWLEDGEMENTS

The authors would like to acknowledge the support of the Los Alamos National Laboratory for this work.