

ANL/ET/CP--89606 CONF-961107--8

RECEIVED

APR 14 1997

OSTI

LITHIUM-FERRATE-BASED CATHODES  
FOR MOLTEN CARBONATE FUEL CELLS

M. T. Lanagan, I. Bloom,\* T. D. Kaun,\* J. Wolfenstine,<sup>1</sup> and M. Krumpelt\*  
Energy Technology Division  
Chemical Technology Division\*  
Argonne National Laboratory  
Argonne, IL 60439

DISTRIBUTION OF THIS DOCUMENT IS UNLIMITED

MASTER

The submitted manuscript has been authored by a contractor of the U.S. Government under contract No. W-31-109-ENG-38. Accordingly, the U. S. Government retains a nonexclusive, royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for U. S. Government purposes.

Poster to be presented at the 1996 Fuel Cell Seminar to be held on November 17-20, 1996, Kissimmee, Florida.

## **DISCLAIMER**

**This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, make any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.**

**DISCLAIMER**

**Portions of this document may be illegible in electronic image products. Images are produced from the best available original document.**

## LITHIUM-FERRATE-BASED CATHODES FOR MOLTEN CARBONATE FUEL CELLS

M. T. Lanagan, I. Bloom,<sup>†</sup> T. D. Kaun,<sup>†</sup> J. Wolfenstine,<sup>1</sup> and M. Krumpelt<sup>†</sup>

Energy Technology Division, Chemical Technology Division<sup>†</sup>  
Argonne National Laboratory  
Argonne, IL 60439-4838

### Introduction

Argonne National Laboratory is developing advanced cathodes for pressurized operation of the molten carbonate fuel cell (MCFC) at  $\sim 650^\circ\text{C}$  [2-5]. To be economically viable for stationary power generation, molten carbonate fuel cells must have lifetimes of more than 25,000 h while exhibiting superior cell performance [6]. In the present technology, lithiated NiO is used as the cathode. Over the lifetime of the cell, however,  $\text{Ni}^{2+}$  ions tend to transport to the anode, where they are reduced to metallic Ni [7]. With increased  $\text{CO}_2$  partial pressure, the transport of Ni increases because of the increased solubility of NiO in the carbonate electrolyte. Although this process is slow in MCFCs operated at 1 atm and a low  $\text{CO}_2$  partial pressure (about 0.1 atm), transport of nickel to the anode may be excessive at a higher pressure (e.g., 3 atm) and a high  $\text{CO}_2$  partial pressure (e.g., about 0.3 atm). This transport is expected to lead eventually to poor MCFC performance and/or short circuiting.

Several alternative cathode compositions have been explored to reduce cathode solubility in the molten salt electrolyte [2-5,8]. For example,  $\text{LiCoO}_2$  has been studied extensively [8,9,10] as a potential cathode material. The  $\text{LiCoO}_2$  cathode has a low resistivity, about  $1 \Omega\text{-cm}$ , and can be used as a direct substitute for NiO. However, the high material cost may prevent large-scale implementation.

Argonne is developing advanced cathodes based on lithium ferrate ( $\text{LiFeO}_2$ ), which is attractive because of its very low solubility in the molten  $(\text{Li,K})_2\text{CO}_3$  electrolyte [11]. Because of its high resistivity (about  $300 \Omega\text{-cm}$ ), however,  $\text{LiFeO}_2$  cannot be used as a direct substitute for NiO. Cation substitution is, therefore, necessary to decrease resistivity.

We determined the effect of cation substitution on the resistivity and deformation of  $\text{LiFeO}_2$ . The substituents were chosen because their respective oxides as well as  $\text{LiFeO}_2$  crystallize with the rock-salt structure.

### Experimental

*Materials Synthesis and Characterization.* Stoichiometric amounts of  $\text{Li}_2\text{CO}_3$ ,  $\text{Fe}_2\text{O}_3$ ,  $\text{CoO}$ ,  $\text{NiO}$  and/or  $\text{MgO}$  were mixed and heat treated at  $825^\circ\text{C}$  for 4 h. The powders were pressed into disks and sintered at  $1000^\circ\text{C}$  for 4 h. Upon cooling, the phase distribution of the sintered disks was characterized by X-ray diffraction. The relative densities of the pellets were in the range of 60-90%;  $\text{LiCoO}_2$  had the highest (93% of theoretical) and pure  $\text{LiFeO}_2$ , the lowest (81%). All materials except  $\text{LiCoO}_2$  had equiaxed grains (0.96-1.43  $\mu\text{m}$ ).  $\text{LiCoO}_2$  had acicular grain morphology ( $5 \times 1.5 \mu\text{m}$ ).

*Resistivity and Deformation Rate Measurements.* Resistivity was determined using the four-wire, dc, van der Pauw method at  $650^\circ\text{C}$  in air. Parallelepipeds ( $2 \times 2 \times 4 \text{ mm}$ ) were cut from

the sintered pellets. The samples were deformed by compression at a constant deformation rate in air at 1000°C.

*Cell Tests.* Promising materials were tested in a 5 × 5-cm cell with a pressed (Li,K)<sub>2</sub>CO<sub>3</sub> electrolyte tile. The test cell was operated at 650°C using an O<sub>2</sub>-CO<sub>2</sub> gas mixture which simulated pressurized operation at 3–5 atm.

## Results and Discussion

*Materials.* We found that the range of homogeneity for Co-substituted LiFeO<sub>2</sub> is limited; several phases are formed during synthesis. All of the diffraction peaks for Mg-substituted LiFeO<sub>2</sub> were indexed to a rock-salt structure. Further analysis shows that the lattice parameter increases monotonically with MgO concentration, indicating a complete solid solution (Fig. 1). Fayard found that both CoO and MgO formed complete solid solutions with LiFeO<sub>2</sub> [12]. Apparently, Co solubility is affected by differences in synthesis conditions.

*Resistivity Measurements.* Resistivity results for MgO-substituted LiFeO<sub>2</sub> samples show that the minimum resistivity is approximately 100 Ω-cm (at 650°C in air) and appears in the MgO concentration range of 6–12 mol% (Fig. 2). Clearly, the resistivity of Mg-substituted LiFeO<sub>2</sub> is too high; lower resistivity values (~1 Ω-cm) are necessary for MCFC cathodes. By using different cation substituents, we lowered the resistivity of a LiFeO<sub>2</sub>-based material (designated Material 1) to 1.3 Ω-cm at 650°C.

*Deformation Rate Studies.* Figure 3 shows a log-log plot of the deformation rate vs stress at 1000°C for five materials: (a) pure LiFeO<sub>2</sub>, (b) 12.5 m/o NiO-LiFeO<sub>2</sub>, (c) 9 m/o MgO-LiFeO<sub>2</sub>, (d) pure LiCoO<sub>2</sub>, and (e) 5 m/o Li<sub>2</sub>O-NiO. Here, the deformation rate was normalized with respect to grain size and stress to the material density, and it was assumed that the deformation rate is controlled by lattice diffusion. The slope of all curves is close to unity, implying that they all exhibit the same deformation mechanism (e.g., diffusional creep and/or grain boundary sliding). Materials (a) and (d) have higher deformation rates than (e), lithiated NiO; Material (d) has the highest deformation rate. Doping LiFeO<sub>2</sub> with NiO or MgO decreases the deformation rate as compared to that of pure LiFeO<sub>2</sub>. Materials (a), (b), (c), and (d) will compact more than lithiated NiO at 650°C.

*Cell Tests.* A fibrous cathode of Material 1 was used in a cell test. The cell potential at 160 mA/cm<sup>2</sup> as a function of time is shown in Fig. 4. After an initial break-in period, a constant potential of 850 mV was observed for 1700 h. Polarization experiments showed a small degradation at 1706 h (see Fig. 5). These results show that LiFeO<sub>2</sub>-based cathodes have good performance and durability at high CO<sub>2</sub> partial pressures.

## Conclusions

Several LiFeO<sub>2</sub>-based materials with cation substitutions were synthesized and characterized. With the proper choice of substituents, the resistivity of LiFeO<sub>2</sub> was lowered to about 1 Ω-cm.

The LiCoO<sub>2</sub>- and LiFeO<sub>2</sub>-based cathode materials have deformation rates higher than that of lithiated NiO at 1000°C. They will compact more at 650°C. Doping the alternative cathodes decreases their deformation rates.

The  $\text{LiFeO}_2$ -based cathodes exhibit cell potentials which are stable for long periods of time under simulated pressurized operation.  $\text{LiFeO}_2$ -based materials continue to show promise as cathodes for the MCFC.

### Acknowledgments

The authors thank H. Wilson Abernathy III, Bryant Polzin, and Ryan Thayer for their assistance in sample preparation. This research was supported under a contract with M-C Power Corporation.

### References

1. Faculty Research Participant. Present address: Dept. of Chemical-Biochemical Engineering, University of California, Irvine, CA.
2. A. P. Brown, G. H. Kucera, M. F. Roche, D. D. Chu, and E. Indacochea, "Performance of Alternative Cathodes for Molten Carbonate Fuel Cells," *Fuel Cell Seminar Program and Abstracts*, November 29–December 2, 1992, Tucson, AZ, p. 125.
3. G. Kucera, A. Brown, D. Chu, and E. Indacochea, "Development of Alternative Components for Molten Carbonate Fuel Cells," presented at EPRI/GRI Fuel Cell Workshop on Fuel Cell Technology Research and Development, April 29–30, 1992, San Francisco, CA.
4. J. L. Smith, G. H. Kucera, and A. P. Brown, "Development of Cathode Materials and Structures for the Molten Carbonate Fuel Cell," *Proc. 2<sup>nd</sup> Symp. on Molten Carbonate Fuel Technology*, J. Selman, D. A. Shores, H. C. Maru and I. Uchida, eds., Vol. 90-16 (Oct. 1990), The Electrochemical Soc., p. 226–ff, and references cited therein.
5. G. H. Kucera and J. L. Smith, "Electronically Conductive Ceramics for High Temperature Oxidizing Environments," US Pat. No. 4,564,567 (January 1986).
6. C. Yuh, M. Faoouque, and H. Maru, "Selection of Materials for Carbonate Fuel Cell Use," *Electrochemical Society Extended Abstracts*, Vol. 94-2 (Oct. 1994).
7. N.Q. Minh, "Technological Status of Nickel Oxide Cathodes in Molten Carbonate Fuel Cells," *J. Power Sources*, Vol. 24, pp. 1-19 (1988).
8. L. Plomp, E. F. Sitters, J. B. J. Veldhuis, R. C. Makkus, and S. B. van der Molen, "Performance and Dissolution-Precipitation Behavior of Molten Carbonate Fuel Cell Cathodes," *Proc. Electrochem. Soc.*, Vol. 93-3, pp. 171-185 (1993) and L. Plomp, R. C. Makkus, E. F. Sitters, and G. Rietveld, "Endurance Issues and Materials Development in Molten Carbonate Fuel Cells," *Fuel Cell Seminar Program and Abstracts*, November 28–December 1, 1994, San Diego, CA, p. 164.
9. B. Bergman, E. Fontes, C. Lagergren, G. Lindbergh, A. Lundblad, S. Schwartz, D. Simonsson, and C. Sylwan, "Swedish Research on MCFC," *Fuel Cell Seminar Program and Abstracts*, November 29–December 2, 1992, Tucson, AZ, p. 73.
10. M. Carewska, S. Scaccia, G. Ghidelli, L. Giorgi and E. Simonetti, "Synthesis and Electronic Conductivity of  $\text{LiCoO}_2$  Materials for MCFC Alternative Cathodes," *Fuel Cell Seminar Program and Abstracts*, November 28–December 1, 1994, San Diego, CA, p. 176 and references cited therein.

11. D. Shores and Y. Qu, "Dissolution of Oxides in Molten Carbonates," *Proc. 3rd International Symp. on Carbonate Fuel Cell Technology*, Electrochem. Soc., Vol. 93-3, pp. 356-367 (1993).
12. M. Fayard, "Sur les Phénomènes Ordre-Désordre dans l'Oxyde Mixte  $\text{LiFeO}_2$  et sur les Propriétés de ses Solutions Solides avec Quelques Oxydes du Type  $\text{NaCl}$ ," *Annales de Chimie*, pp. 1313-1335 (1961).

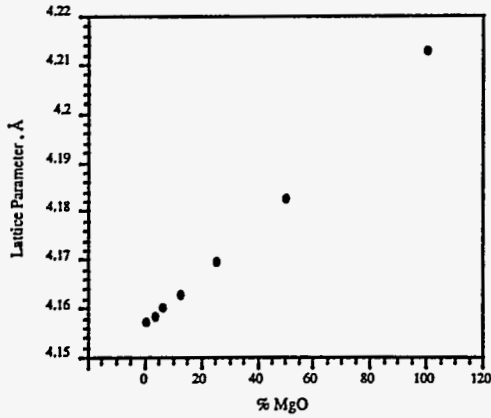


Fig. 1. Effect of MgO concentration on unit cell dimensions.

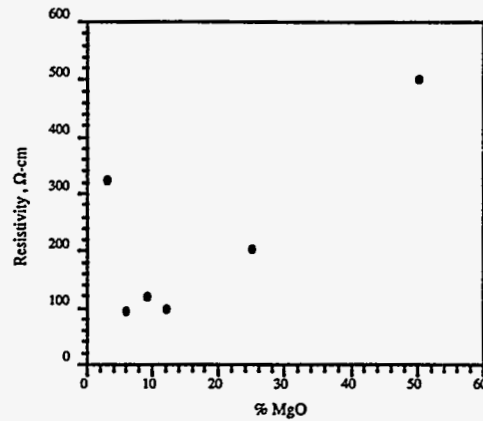


Fig. 2. Effect of MgO concentration on resistivity of  $\text{LiFeO}_2$  at  $650^\circ\text{C}$  in air.

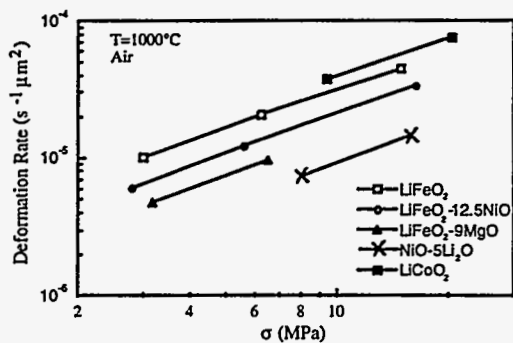


Fig. 3. Grain-size-compensated deformation rate vs density-compensated stress.

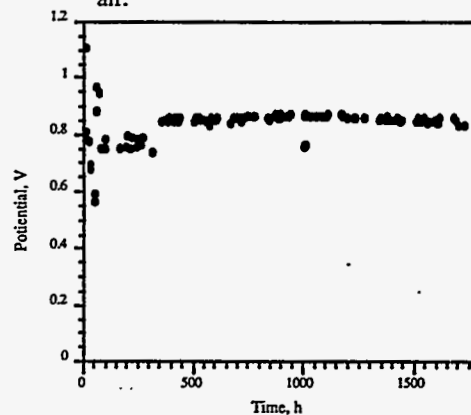


Fig. 4. Cell potential vs time of MCFC test cell containing Material 1 cathode.

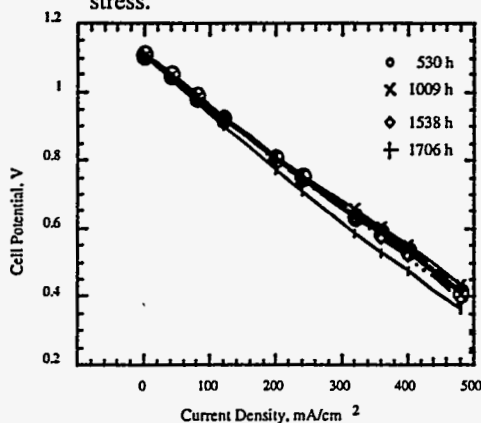


Fig. 5. Changes in polarization curves vs time of MCFC test cell containing Material 1 cathode.