

# Surface Modifications for Oxidation Resistance

*David E. Alman*

Paul D. Jablonski

**Office of Research &  
Development**



**National Energy Technology Laboratory**



8<sup>th</sup> Annual SECA Workshop – San Antonio, TX, August 7-9, 2007



# Accomplishments

- **Surface treatment developed at NETL based on CeO<sub>2</sub>**
  - Applied to over 50 commercial and experimental alloys including; T430, T441, Crofer22APU
  - For comparative purposes applied other RE surface treatment that are described in the literature.
  - RE Treatments are effective in enhancing oxidation resistance.
    - Initiated long term testing to determine effectiveness.
  - ASR measurements and single-cell test indicate surface treatment can enhance SOFC performance.
  - Modified NETL treatment to use La<sub>2</sub>O<sub>3</sub>
- **Investigated influence of Si levels on behavior of interconnect alloys**
  - Oxidation as a function of Si level in T430 (objective is to determine critical Si-level).



# Reactive Element (RE) Effect

- Well known that the addition of small amounts of RE (Ce, La, Y, etc) improves oxidation resistance
- Characteristics
  - Reduction in the oxidation rate
    - Change in scale growth mechanisms
      - cation transport → anion transport
    - Modification of scale microstructure
      - large columnar grains → small equiaxial grains
  - Stabilize Cr<sub>2</sub>O<sub>3</sub> scales at lower Cr levels
  - Improvement in scale adhesion

<i>Alloy</i>	<i>Fe</i>	<i>Cr</i>	<i>Mn</i>	<i>Si</i>	<i>Ti</i>	<i>Al</i>	<i>La</i>
<i>Crofer 22APU</i>	Bal	22.0	0.5	--	0.08	--	0.06 La
<i>ZMG232</i>	Bal	22.0	minor: Mn, Ni, Zr, La				




# RE Surface Additions

- **Melt addition**


- + Elements added during ingot production (single manufacturing step)
- Difficulty in melting (react with crucibles)
- Surface concentration limited by solubility and diffusivity

- **Surface treatments**

- + Rare Earth concentrated where needed (at surface)
- + Applied to any alloy
- (\$) “Extra” manufacturing step.
- ? Long term effectiveness (as with any coating or surface treatment)

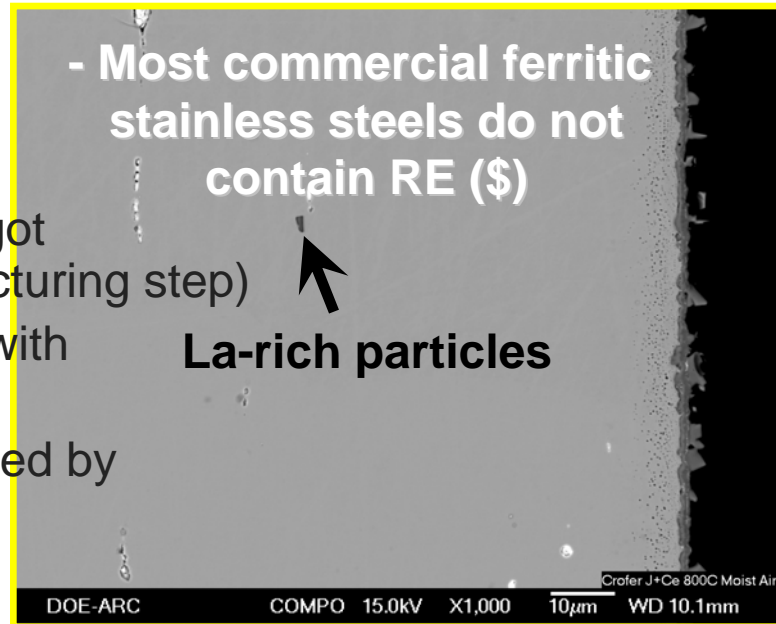

# Effect of RE on Oxidation

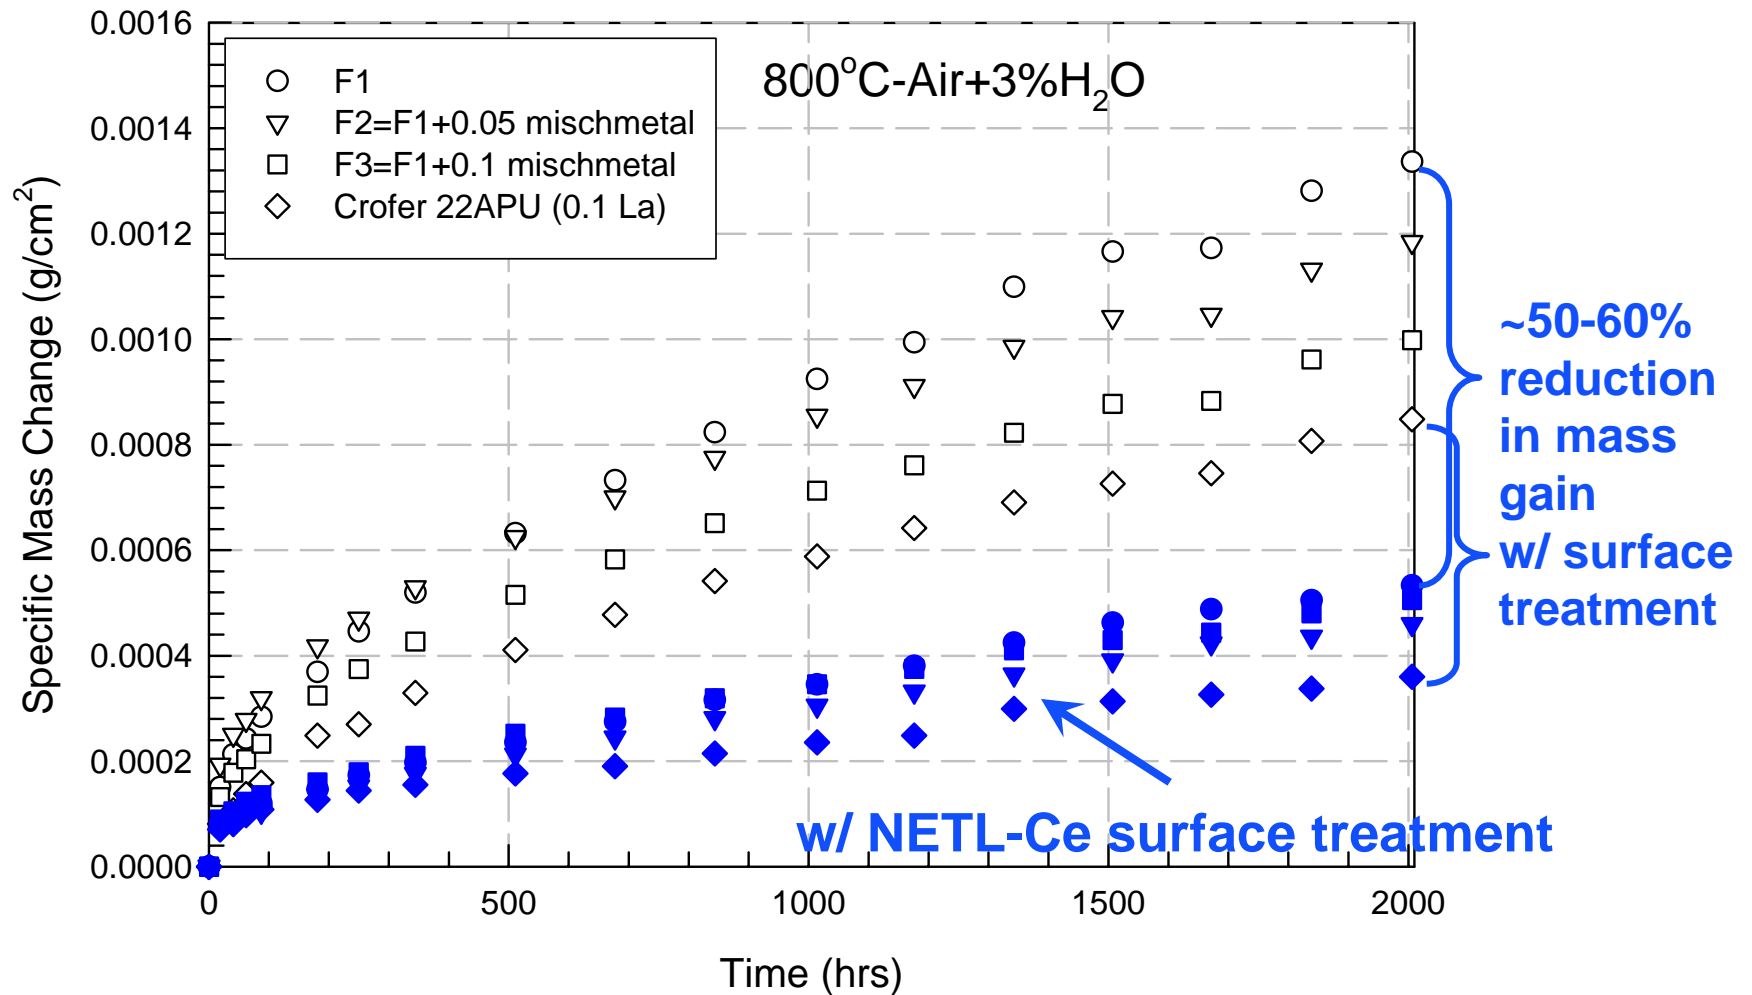

F1=Fe-22Cr-0.5Mn-0.1Ti Mischmetal is a combination of Ce, La and other RE



# Cerium Surface Treatments

- Developed a combination of **pack cementation** and **superficially applied** coating technique (NETL).
  - Coat surface with a slurry mixture: **CeO<sub>2</sub>** and halide (NaCl) activator.
  - Heat (**900°C**) in a controlled atmosphere ( $\times 10^{-3}$ Torr)
  - Residual “pack” coating is washed off the surface.
- **Applied treatment described by Hou & Stringer (H/S).**
  - J. Electrochem. Soc., Vol 134, No. 7, July 1987, pp. 1836-1849.
  - Coupons heated to 200°C were coated with a **cerium-nitrate** slurry (10w/o nitrate adjusted with HNO<sub>3</sub> to pH=2), followed by heating in air at **400°C** to decompose to CeO<sub>2</sub>.
  - Surface also cleaned in water after treatment.



## Surface After Treating (CeO<sub>2</sub>-NETL)

- The surface treatment pre-oxides the surface. Ce-rich oxide forms at the gas-substrate surface. A Cr-Mn oxide forms underneath the Ce-rich oxide.

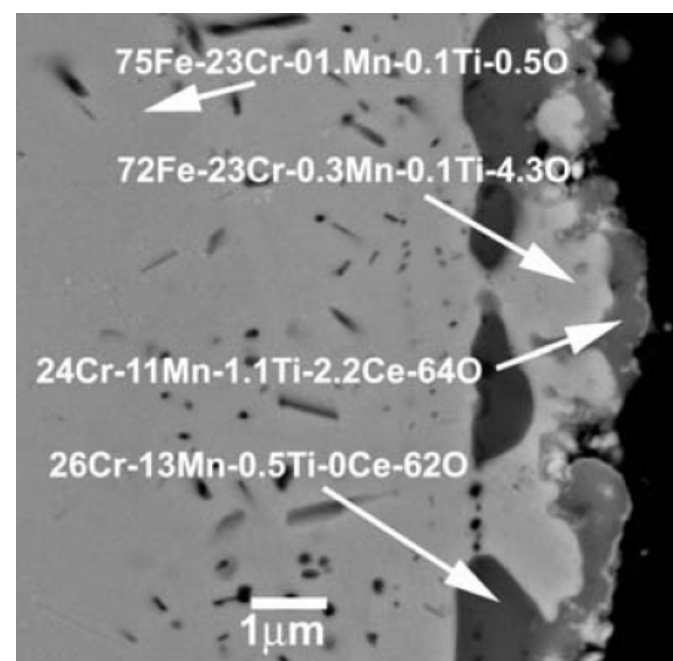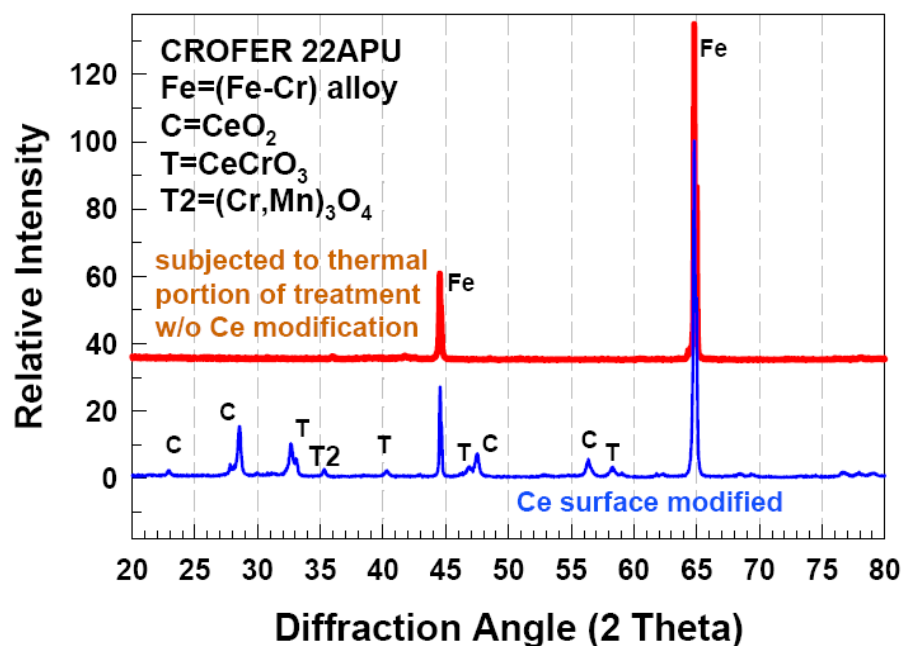

Crofer+Ce (NETL)



# Thermodynamics


**CeO<sub>2</sub> - Fe - Mn - Cr**

800°C, mole Cr/(CeO<sub>2</sub>+Fe+Mn) = 0.2

N:\myfiles\Months\2007\April 2007\David CeO2 Coating\May 4\CeO2-Fe-Mn-20Cr.emf  
5/4/2007



CeO<sub>2</sub> reacts with Cr during treatment to form CeCrO<sub>3</sub>

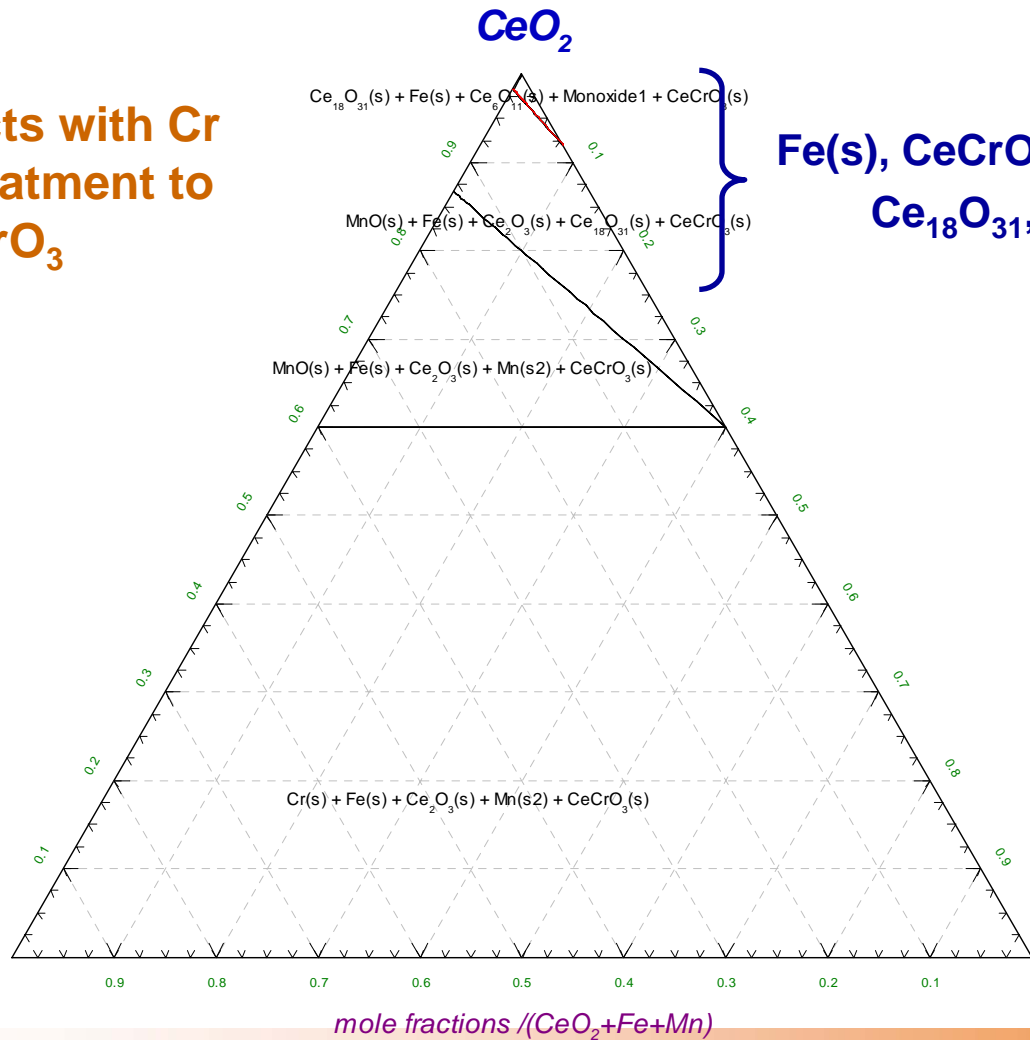

Fe(s), CeCrO<sub>3</sub>, Ce<sub>6</sub>O<sub>11</sub>,  
Ce<sub>18</sub>O<sub>31</sub>, MnO



Mn


Fe

mole fractions /(CeO<sub>2</sub>+Fe+Mn)





# Surfaces After Treating

CeN-based (H/S: 400°C)

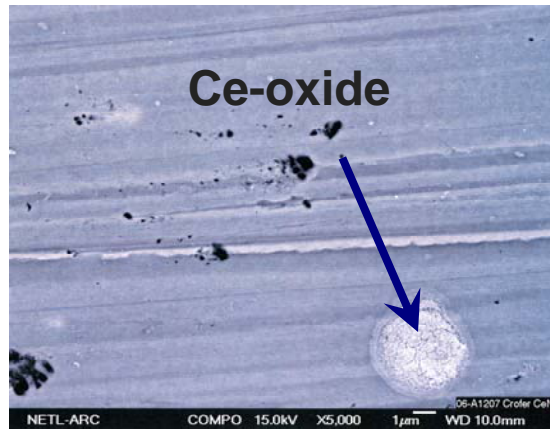


CeO<sub>2</sub>-based (NETL:900°C)

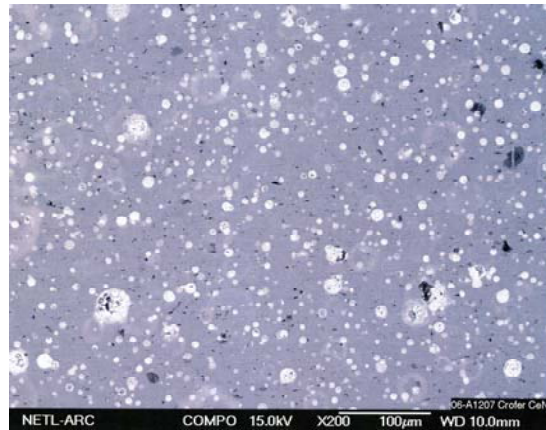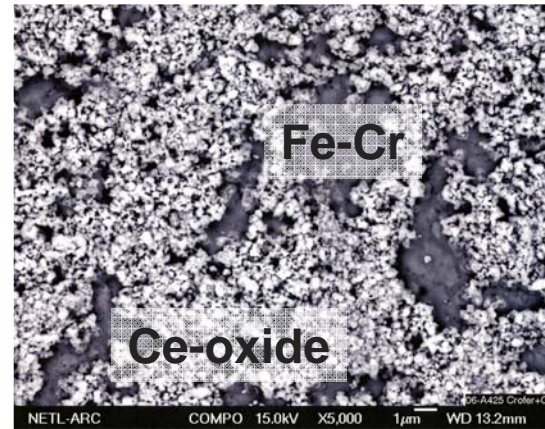


# Surfaces After Treating (Prior to Oxidation)

## Crofer+Ce (NETL)

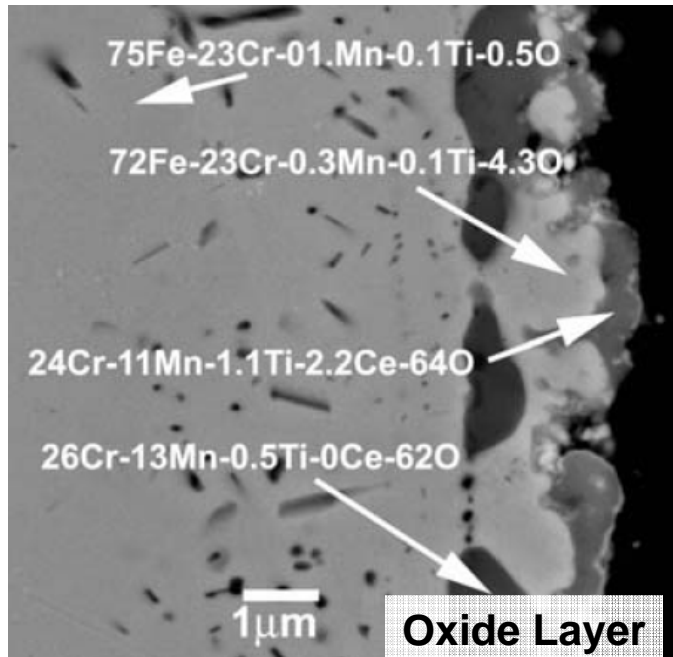

**CeO<sub>2</sub>-Based**  
**Max Temp 900°C**

## Crofer+Ce (H/S)

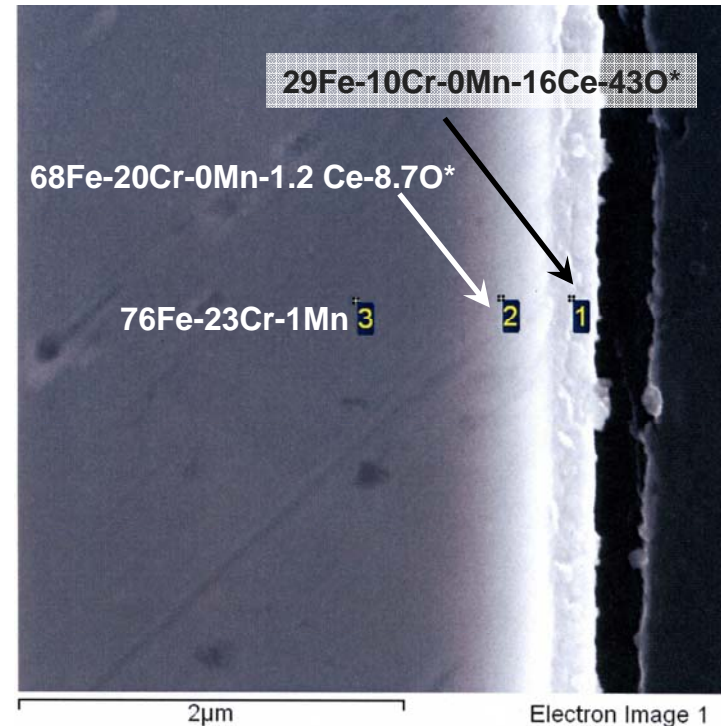


**CeN -Based**  
**Max Temp 400°C**


\*not accurate due to edge effect (rounding of edge during sample preparation), however, indicates Ce is present at the surface.




# Influence of Surface Treatment on Oxidation

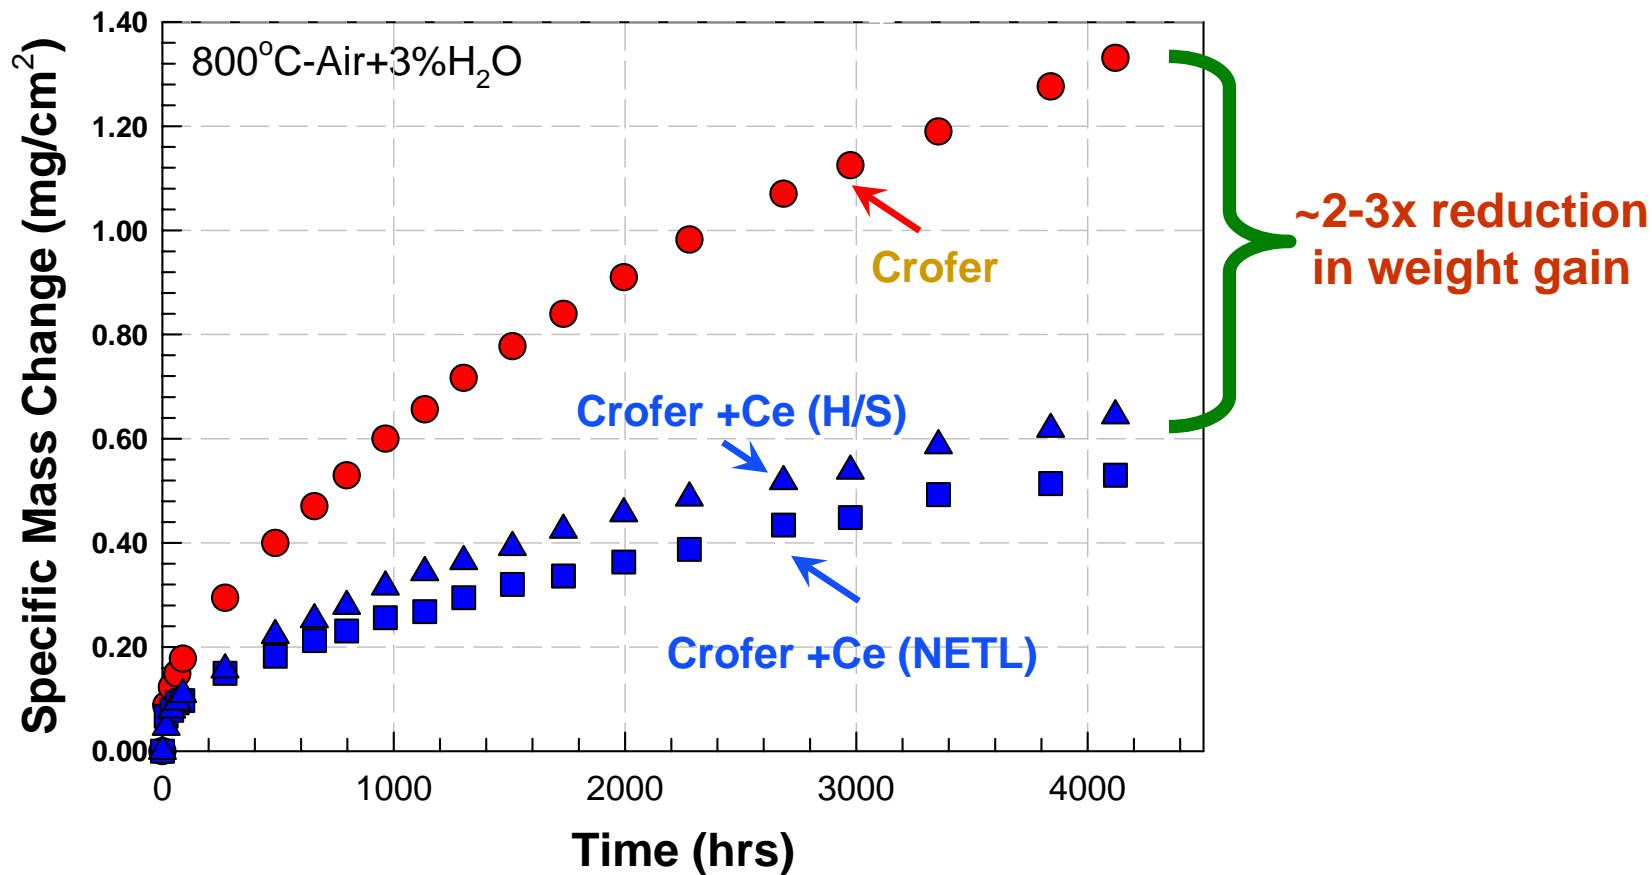


# Total Oxidation NETL Ce-Surface Treatment

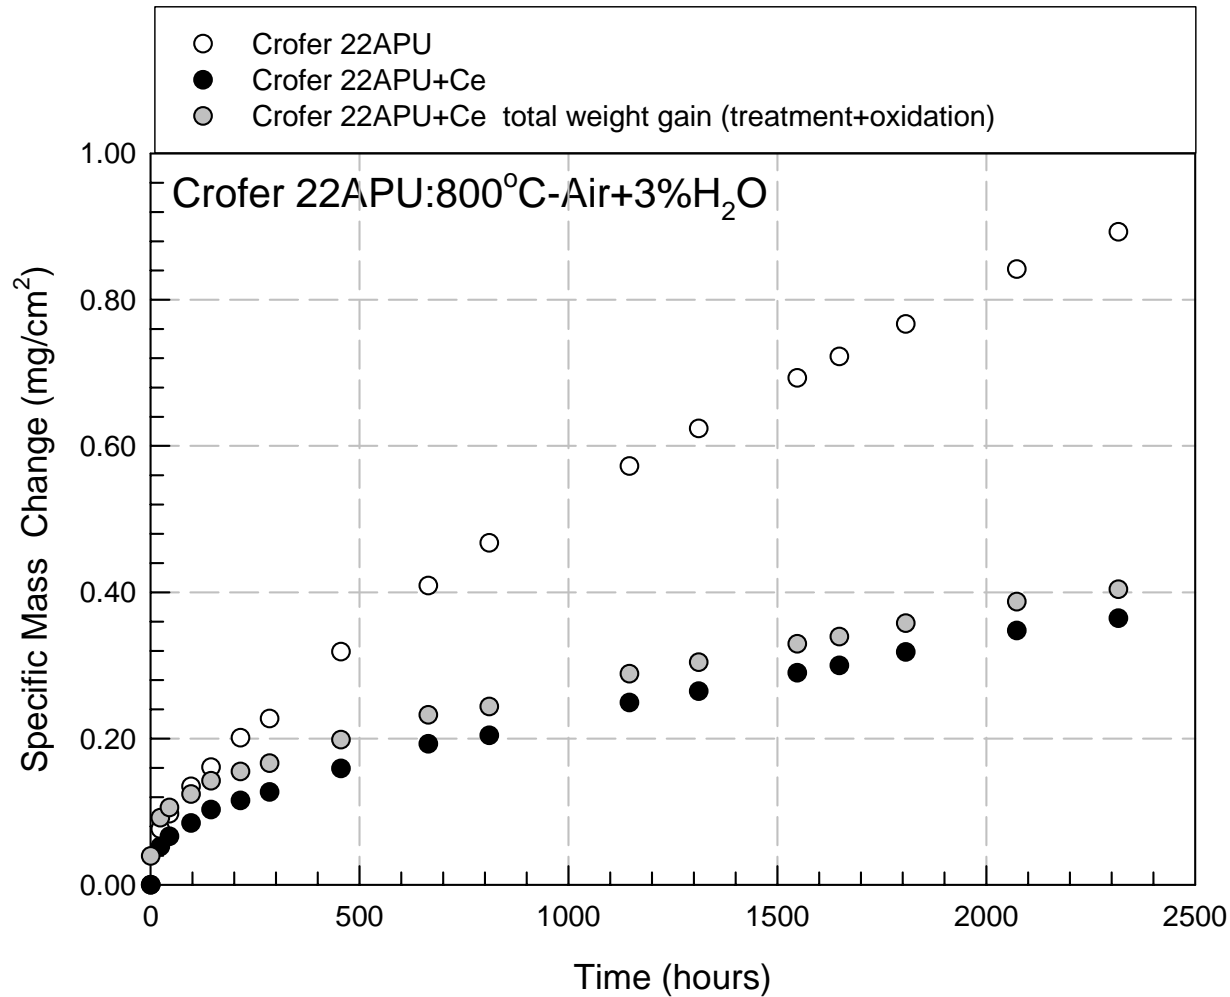

# Influence of Surface Treatment on Oxidation

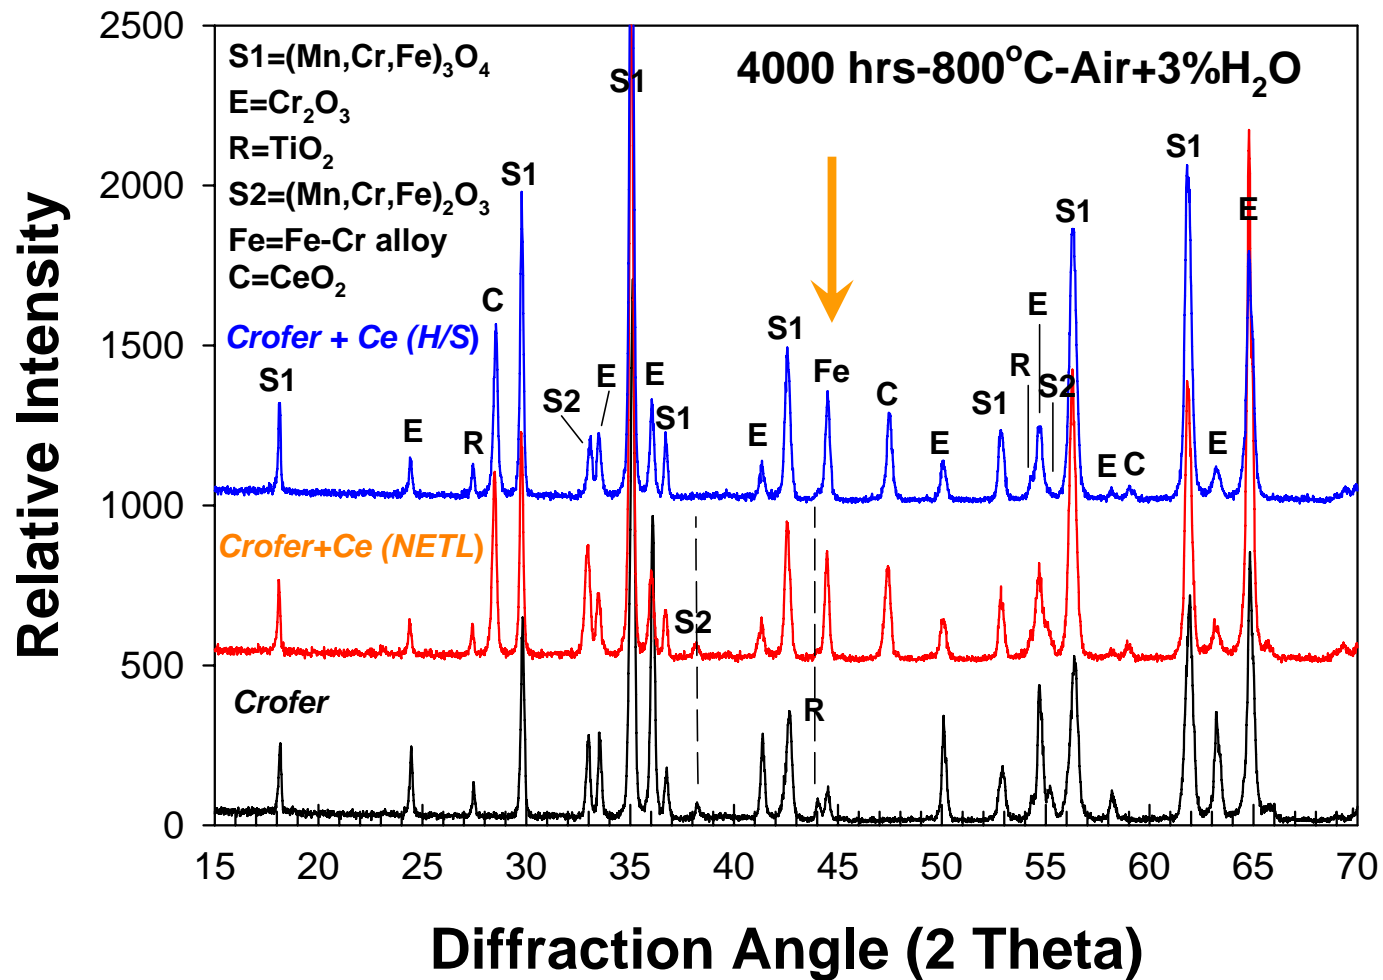


# Oxide Scale Formation

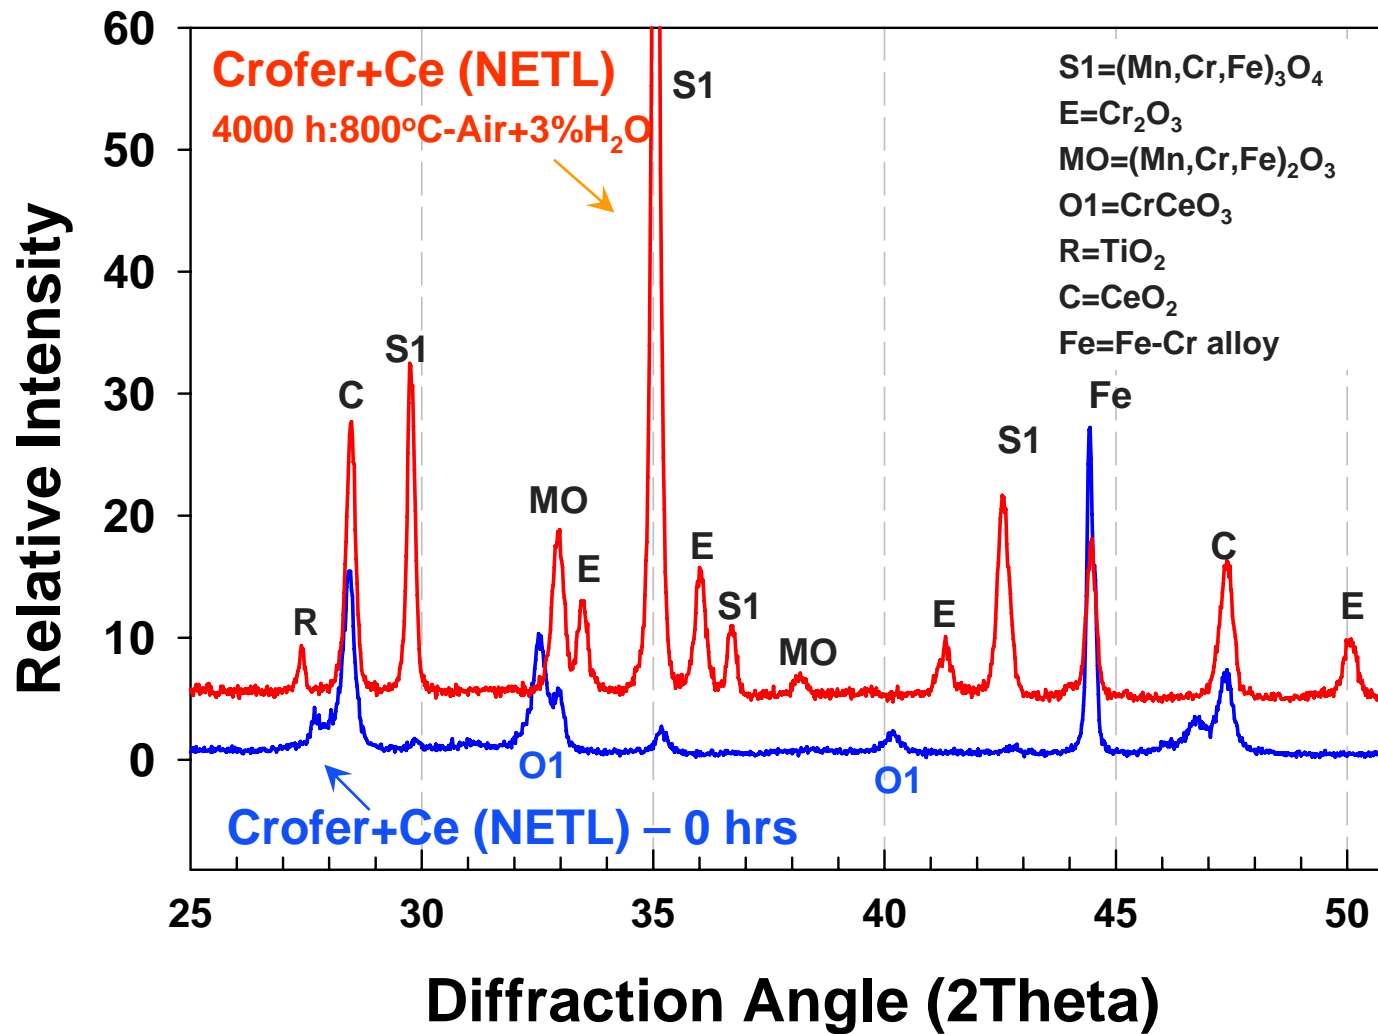

# Influence of Surface Treatment on Oxidation

800°C-2000h-Air+3% $H_2O$

*thinner oxide scales with surface treatments*

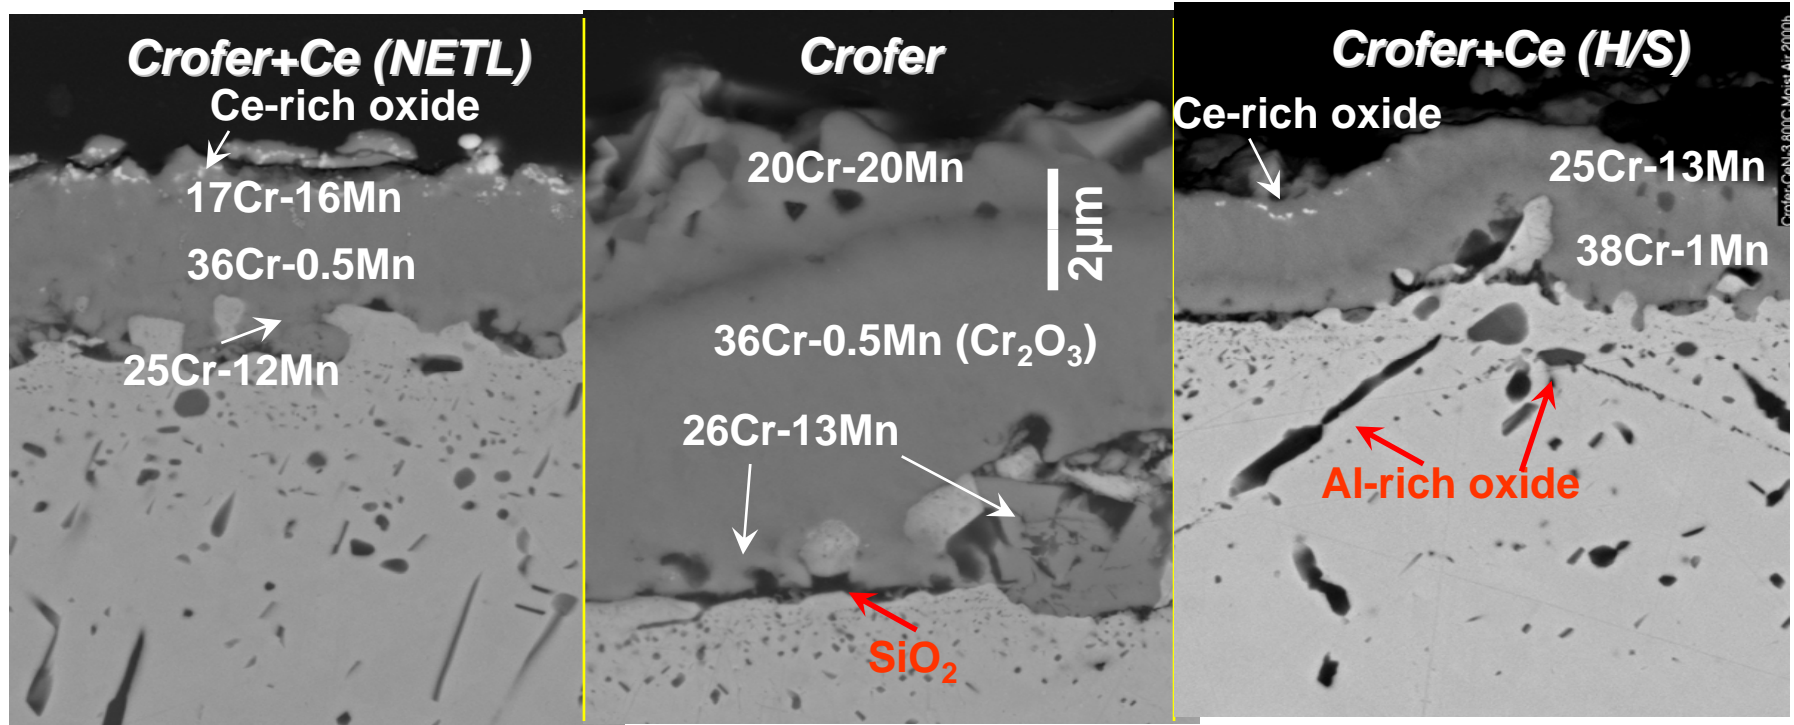


Detailed scale microstructures can be found in D.E. Alman and P.D. Jablonski, "Effect of Minor Elements and a Cerium Surface Treatment on the Oxidation Behavior of an Fe-22Cr-0.5Mn (Crofer 22APU) Ferritic Stainless Steel, *International Journal of Hydrogen Energy*, accepted for publication (2006), currently available on line at [www.sciencedirect.com](http://www.sciencedirect.com).



# Influence of Surface Treatment on Oxidation

800°C-4000hrs-Air+3%H<sub>2</sub>O

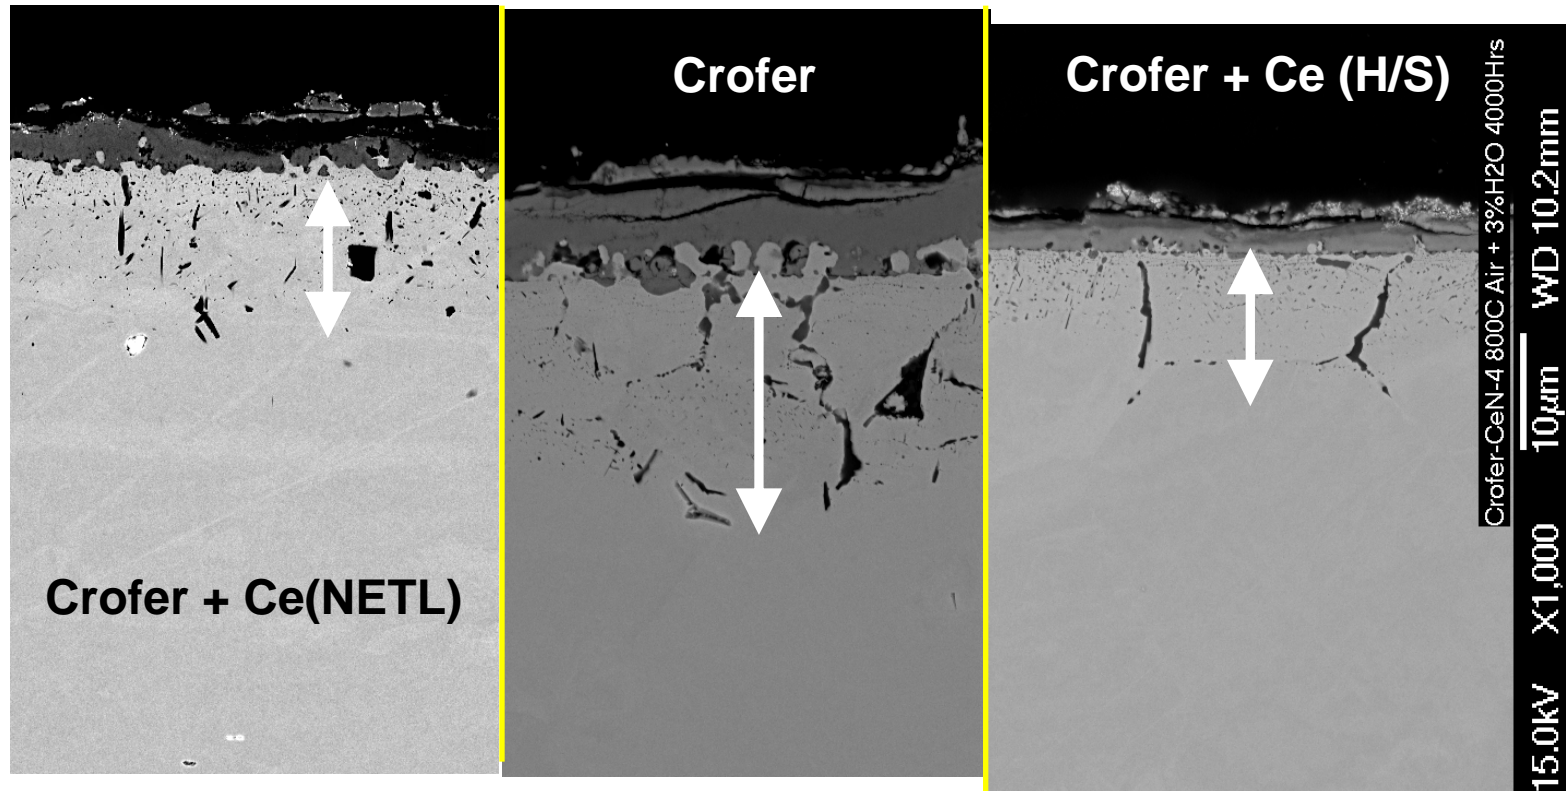

***Minimize internal oxidation***






# Surface Treatments

- **Slows scale growth**
  - Scale microstructures were similar with NETL and H/S treatment methods.
- **Minimizes internal oxidation.**
  - Indicates slows oxygen diffusion through the scale.
- **Ce at surface modifies initial stages of transient oxidation → alters the subsequent growth of the scale → enhanced oxidation resistance.**
  - formation of  $\text{CeCrO}_3$  – type oxide during transient oxidation.
  - Pre-oxidation during NETL treatment
    - (initial oxidation of H/S?)
- **Why?**
  - Scale microstructure is changed
    - (high diffusivity columnar to low diffusivity equiaxed)
  - Ce in oxide changes diffusion through oxide.
  - NETL-ORD IAES project at CMU to investigate influence of RE on transient oxidation.



# Coatings on T430 Stainless Steel

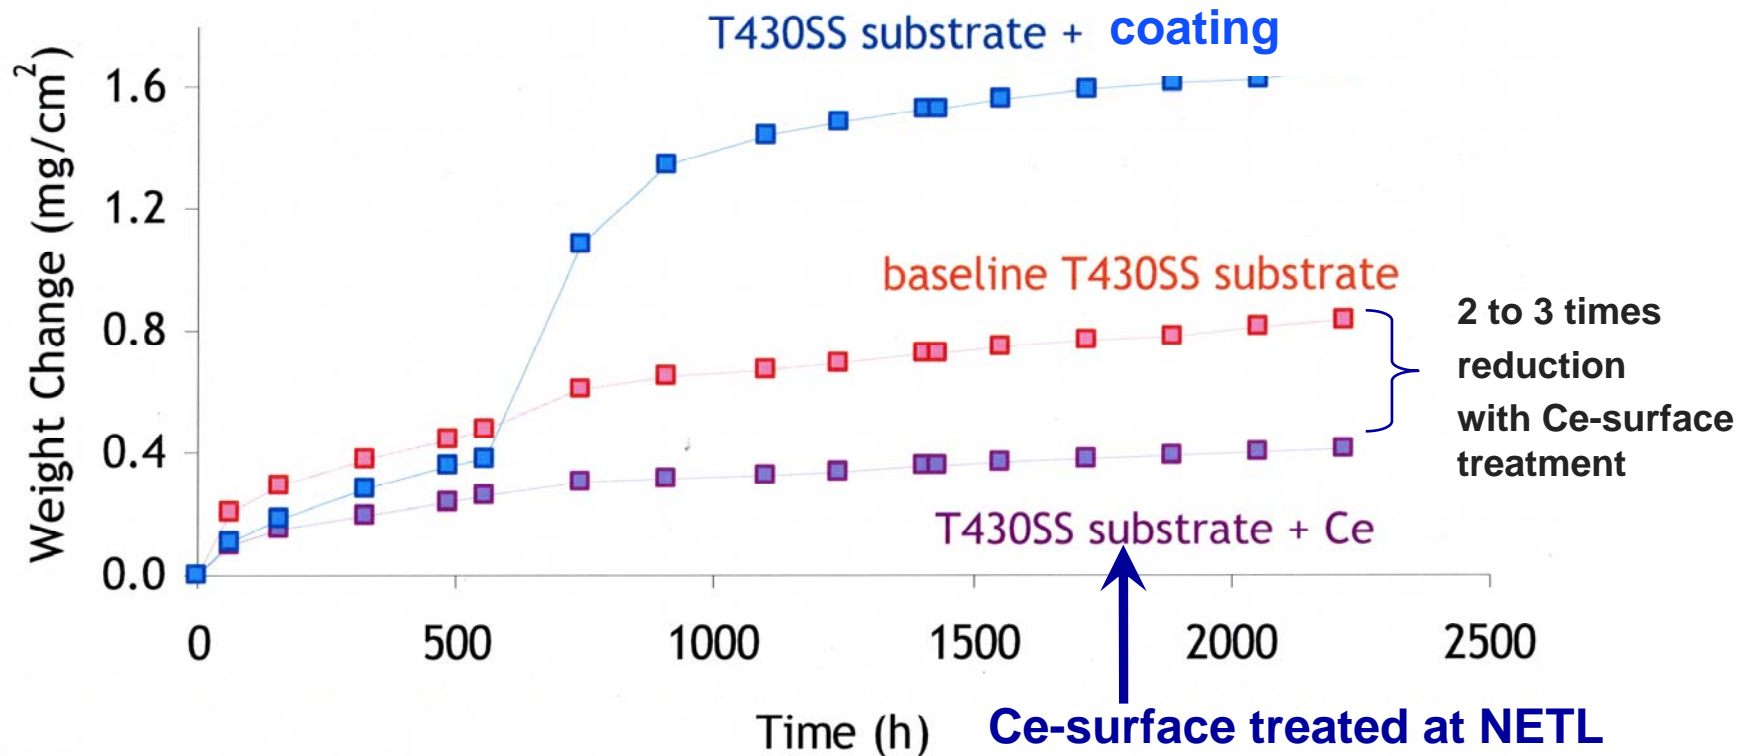

**ATI Allegheny Ludlum**  
Allegheny Technologies  
J. Rakowski, 2006




**Ce-surface treated at NETL  
Tested at Allegheny**

800°C in air+7%H<sub>2</sub>O

T430=Fe-17Cr-0.5Mn

# Long Term Exposure

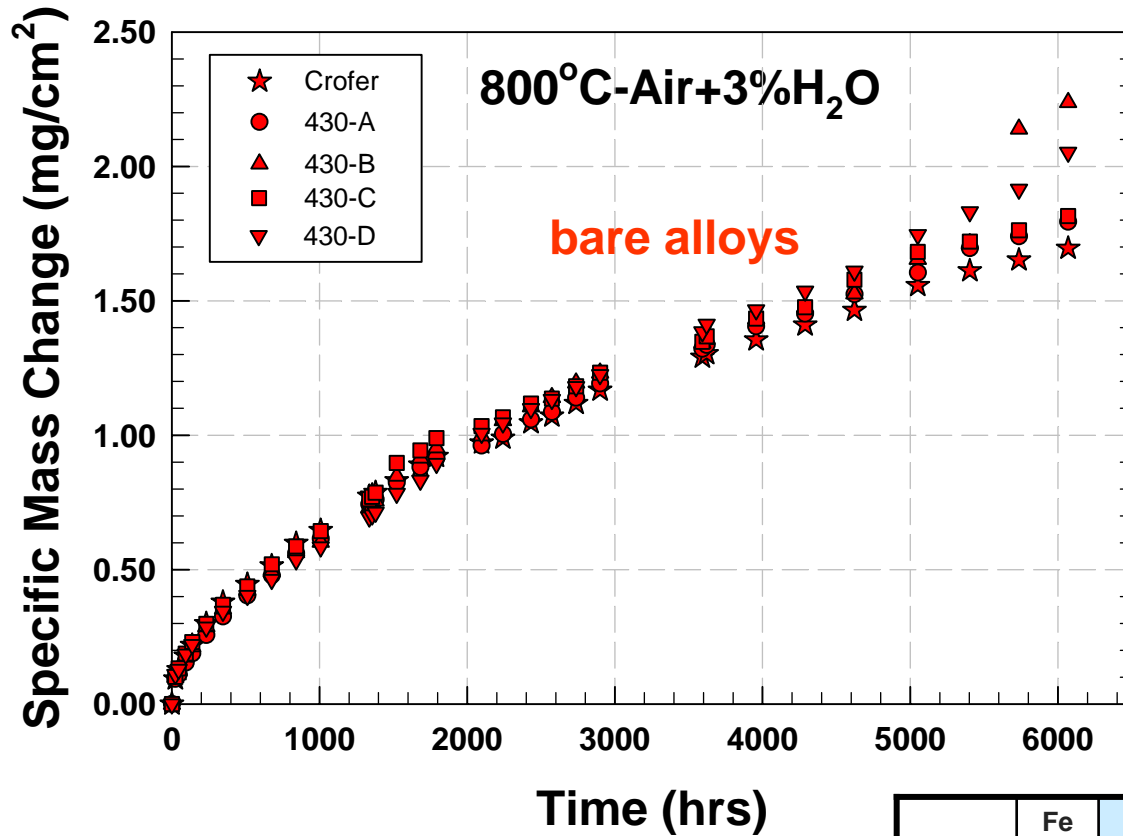


430 alloys produced at NETL  
Oxidation test in progress

	Fe	Cr	Mn	Ti	Si	Al
430-A	Bal	16.85	0.44	<0.01	<0.01	<0.01
430-B	Bal	17.03	0.47	<0.01	<0.01	<0.01
430-C	Bal	17.13	0.49	<0.01	<0.01	<0.01
430-D	Bal	17.11	0.52	0.080	<0.01	<0.01
Crofer	Bal	22.42	0.45	0.092	0.12	0.13



# Long Term Exposure

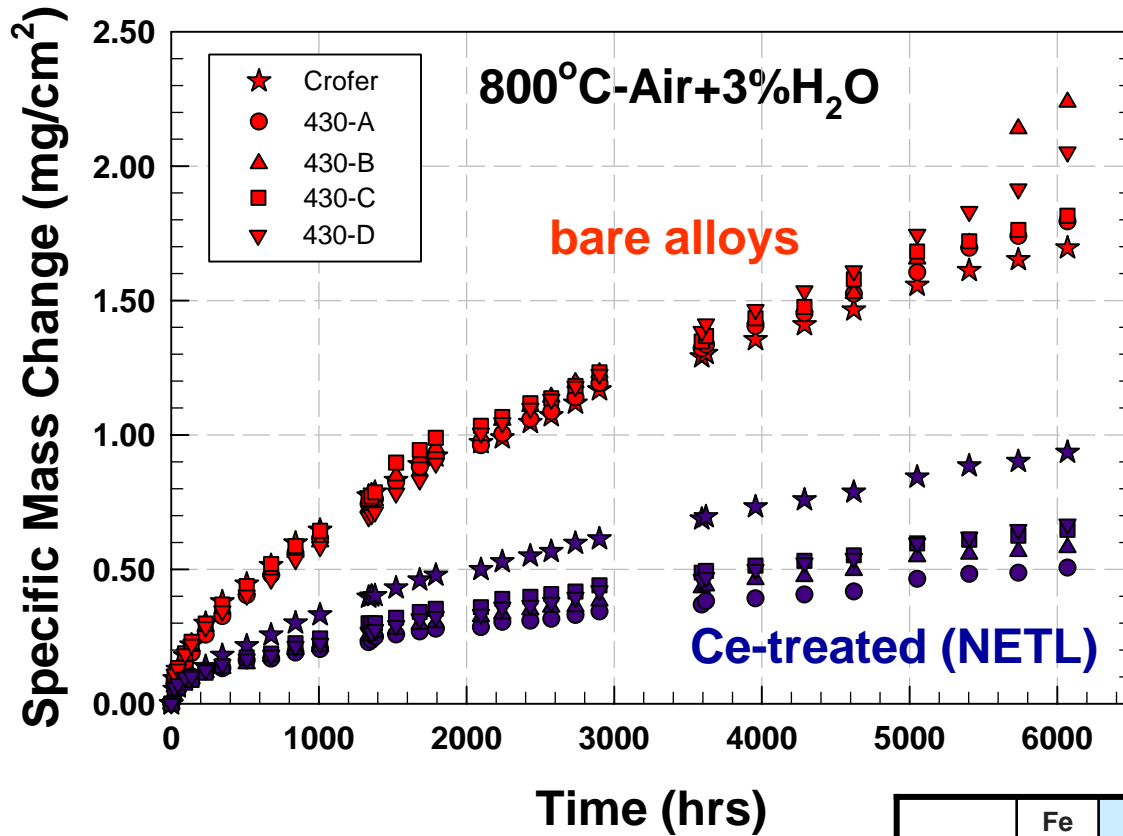


430 alloys produced at NETL  
Oxidation test in progress

	Fe	Cr	Mn	Ti	Si	Al
430-A	Bal	16.85	0.44	<0.01	<0.01	<0.01
430-B	Bal	17.03	0.47	<0.01	<0.01	<0.01
430-C	Bal	17.13	0.49	<0.01	<0.01	<0.01
430-D	Bal	17.11	0.52	0.080	<0.01	<0.01
Crofer	Bal	22.42	0.45	0.092	0.12	0.13



# Influence of Si Content: T430

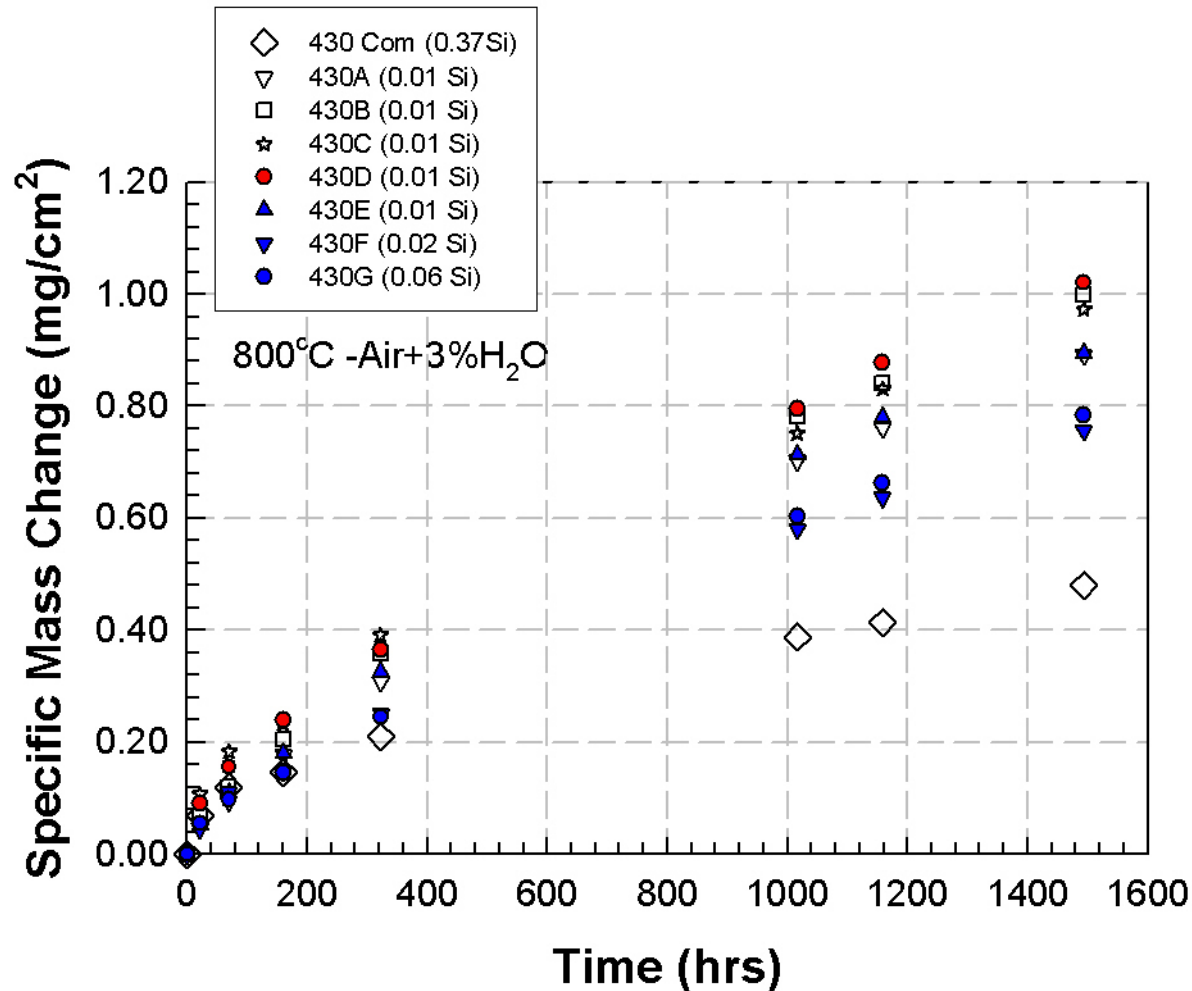


Testing is in progress



# Electrical Performance

*Lower ASR ✓ for SOFC interconnect*


Measurements made by G. Xia & Z.G. Yang, PNNL

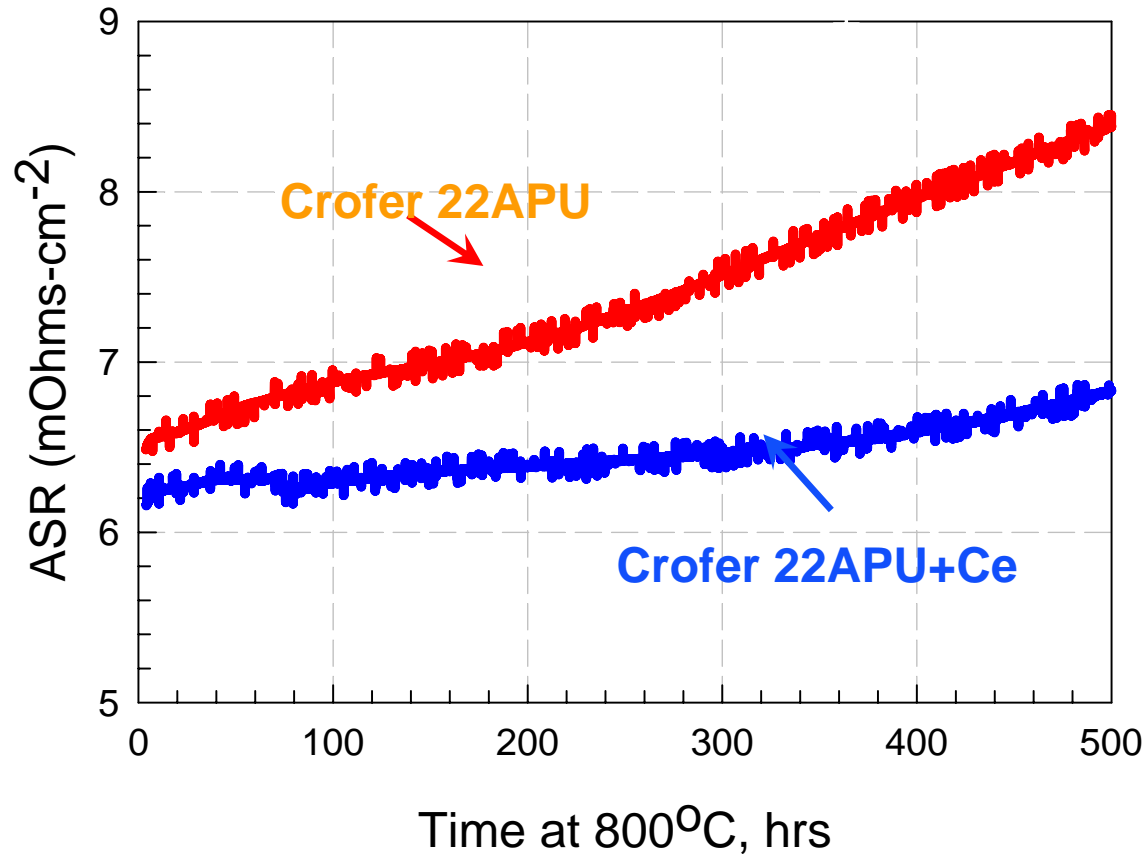

**Samples pre-oxidized at 800°C for 100 hours prior to testing**


# Electrical Performance

ASR Measurements performed by PNNL (Z.G. Yang)  
800°C, air; LSM cathode//LSM contact//interconnect

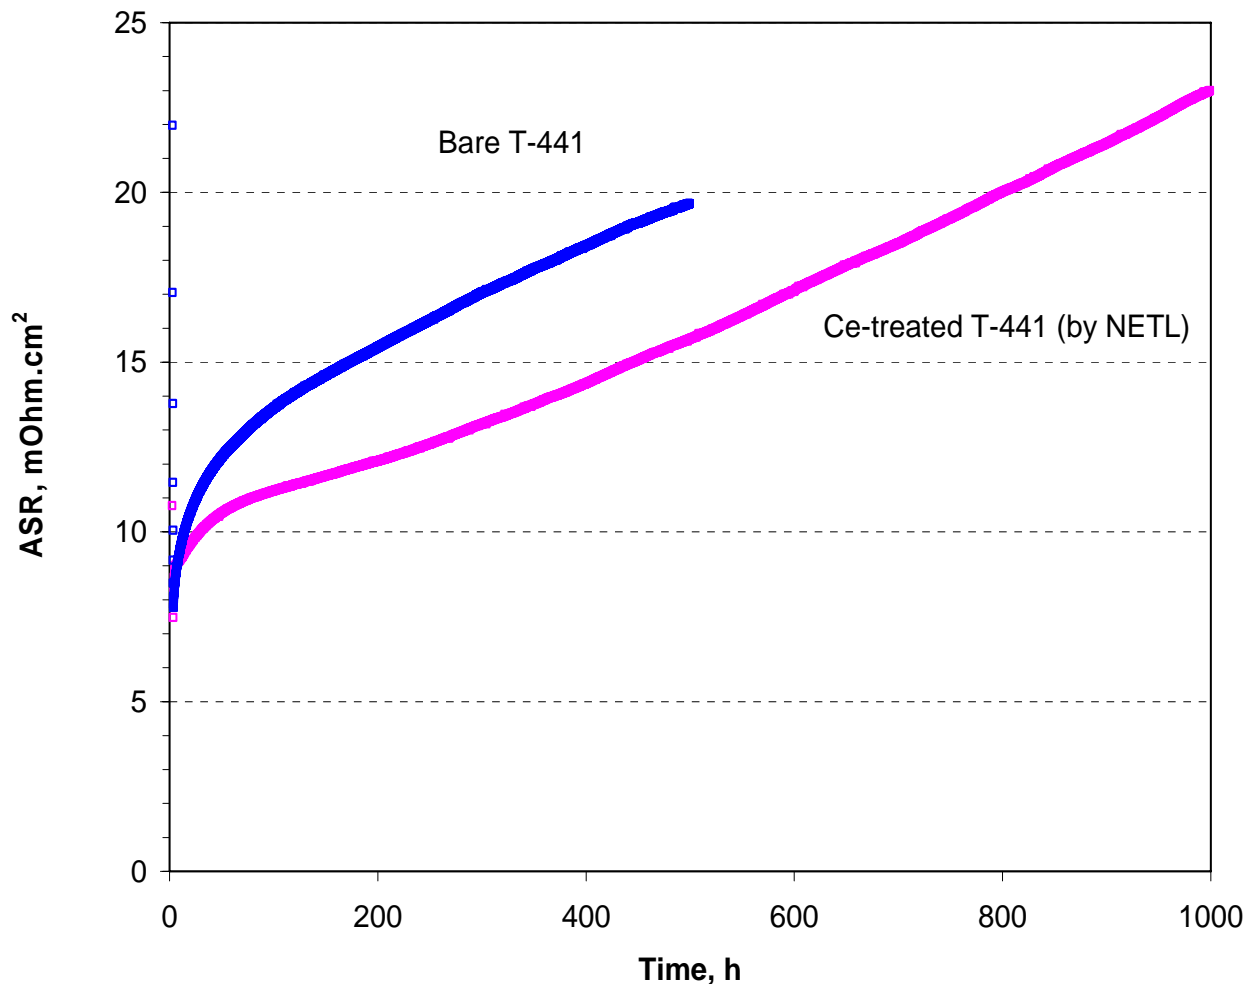

# Laboratory Scale Testing


- “Button” cell test frames in Morgantown
- Fe-22Cr-0.5Mn steel current collector was attached to the cathode with Pt paste (a Pt mesh placed between interconnect and cathode).
- Pt mesh attached to anode.
- Ag current cables and voltage taps spot welded to current collectors

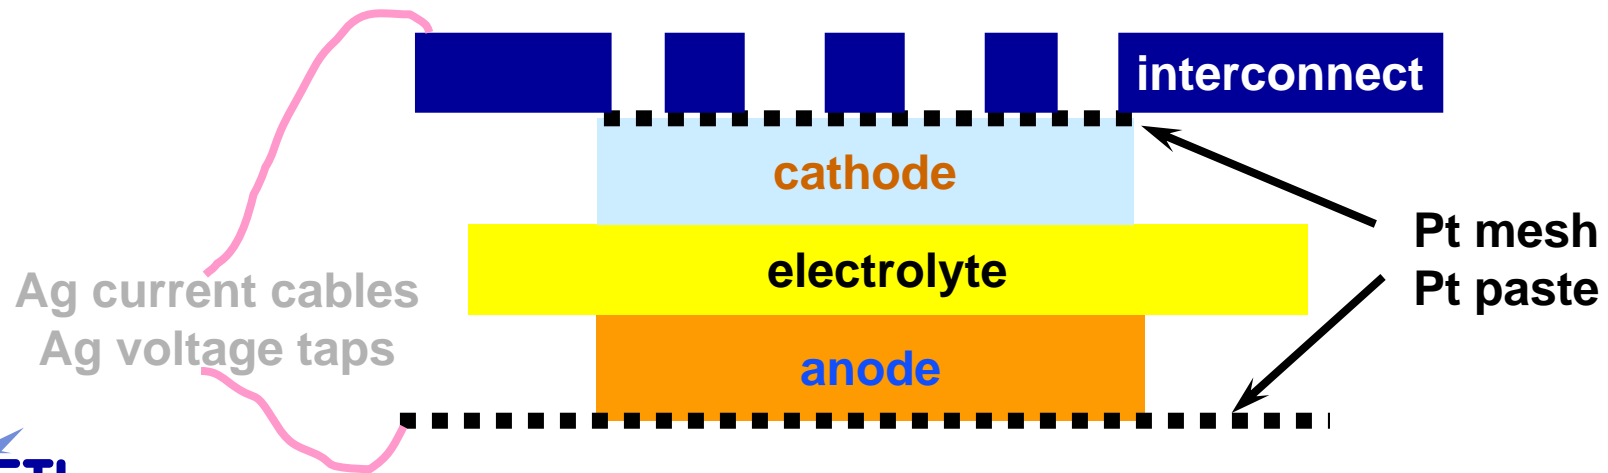



# Laboratory Scale Cell Performance

0.7V/800°C; Fuel: H<sub>2</sub>+3%H<sub>2</sub>O; Oxidant: Air +3% H<sub>2</sub>O  
LSM Cathode/Fe-22Cr-0.5Mn Interconnect

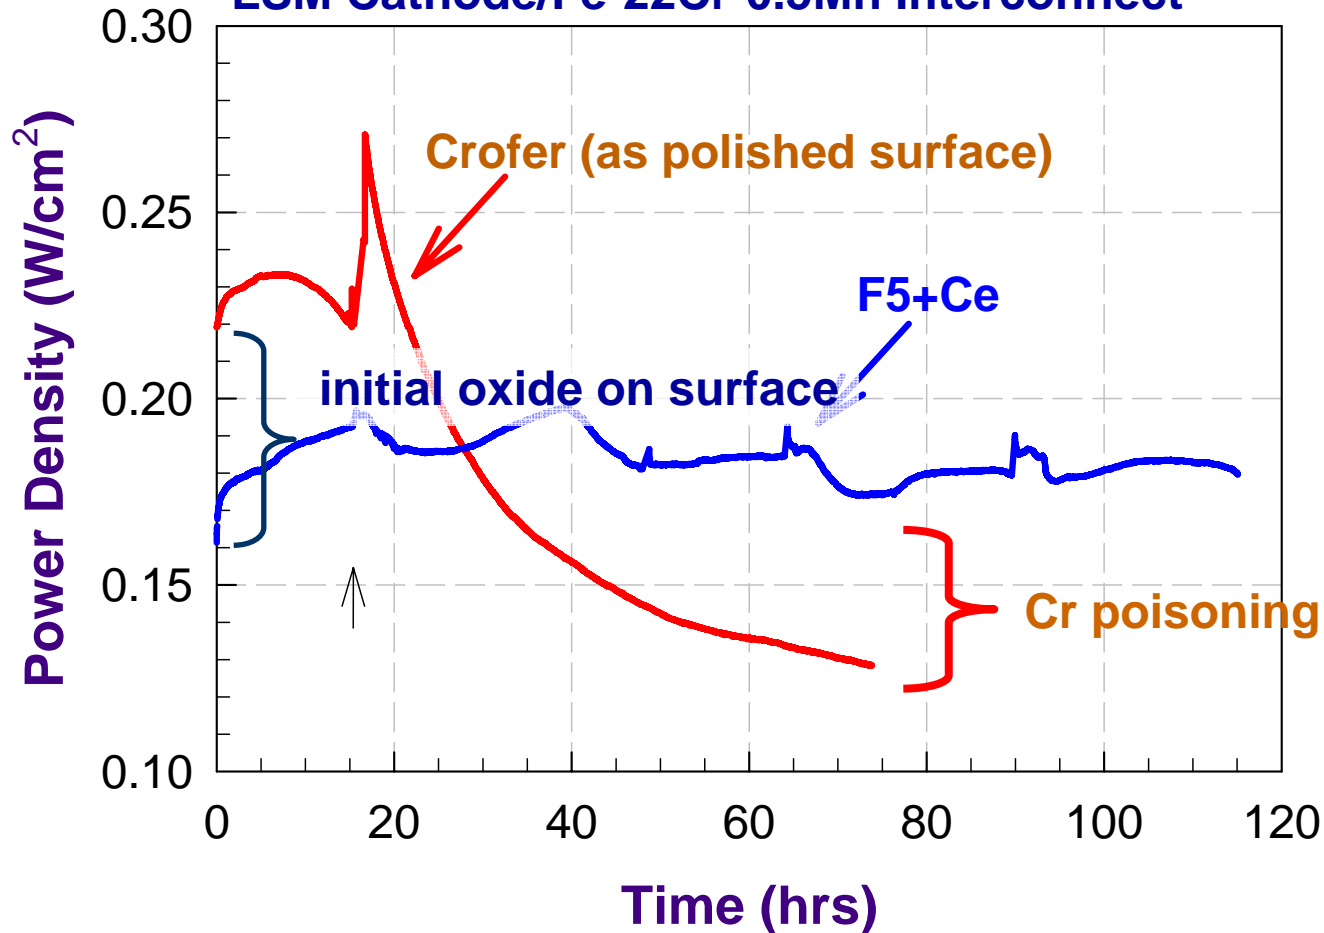


Results published: D.E. Alman, C.D. Johnson, W.K. Collins, and P.D. Jablonski, "The Effect of Cerium Surface Treated Ferritic Stainless Steel Current Collectors on the Performance of Solid Oxide Fuel Cells (SOFC)," *Journal of Power Sources*, Vol 168, 2007, pp. 351-355.



## Pre-Oxidized Current Collectors

- *S.P. Simner, Anderson, Xia, Yang, Pederson, Stevenson, J. Electrochemical Soc., vol 154 (4), pp. A740-A745, 2005*

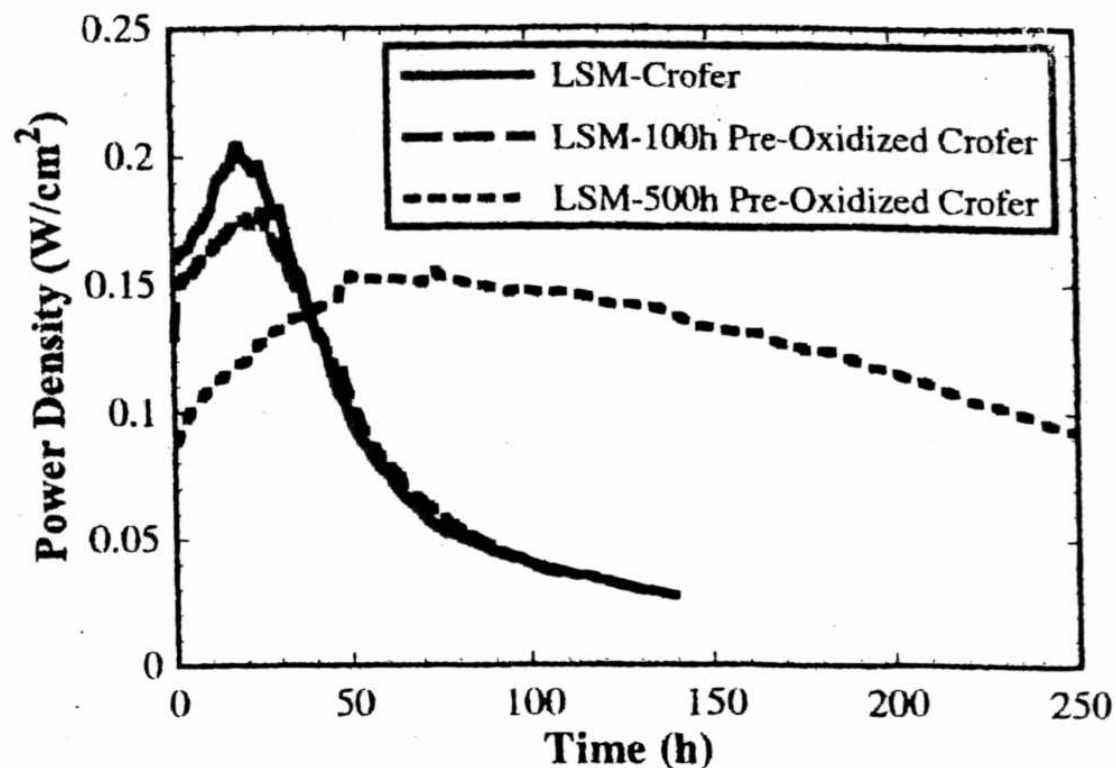


Behavior of cell with Ce-treated interconnect (previous slide) similar to behavior of cells with pre-oxidized interconnects.




# NETL Treatment with $\text{La}_2\text{O}_3$




CeN-based (H/S: 400°C)

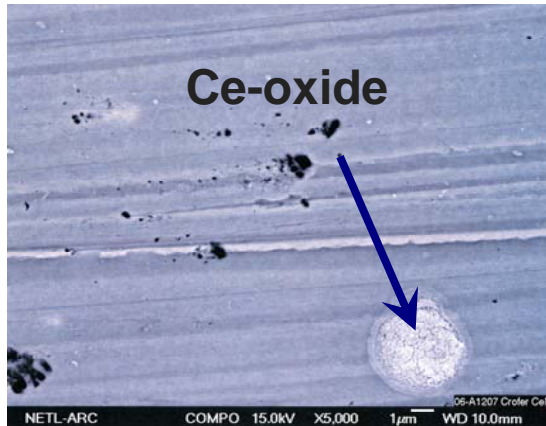

$\text{CeO}_2$ -based (NETL:900°C)

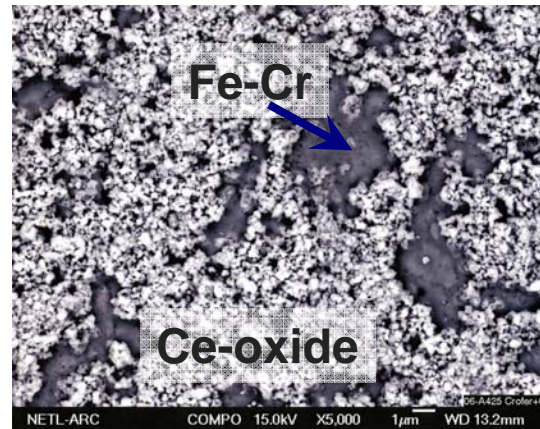


$\text{La}_2\text{O}_3$ -based (NETL:900°C)

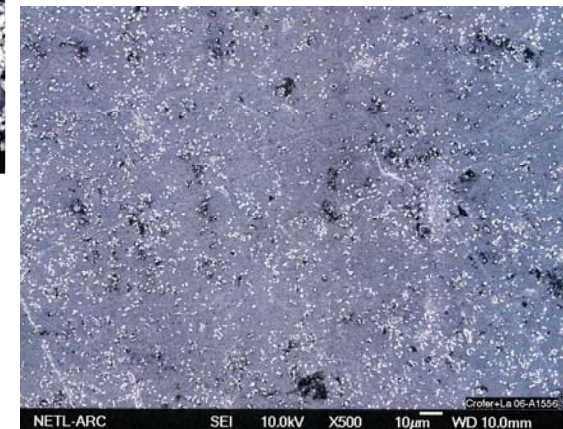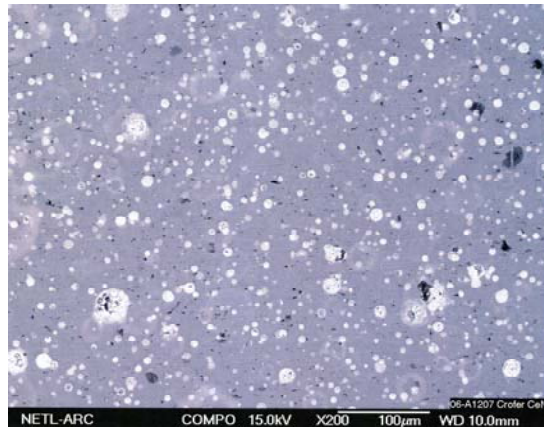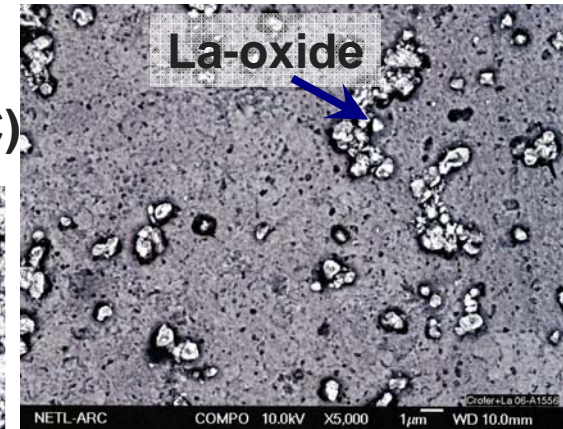


composition is at%




# Effect of Rare Earth

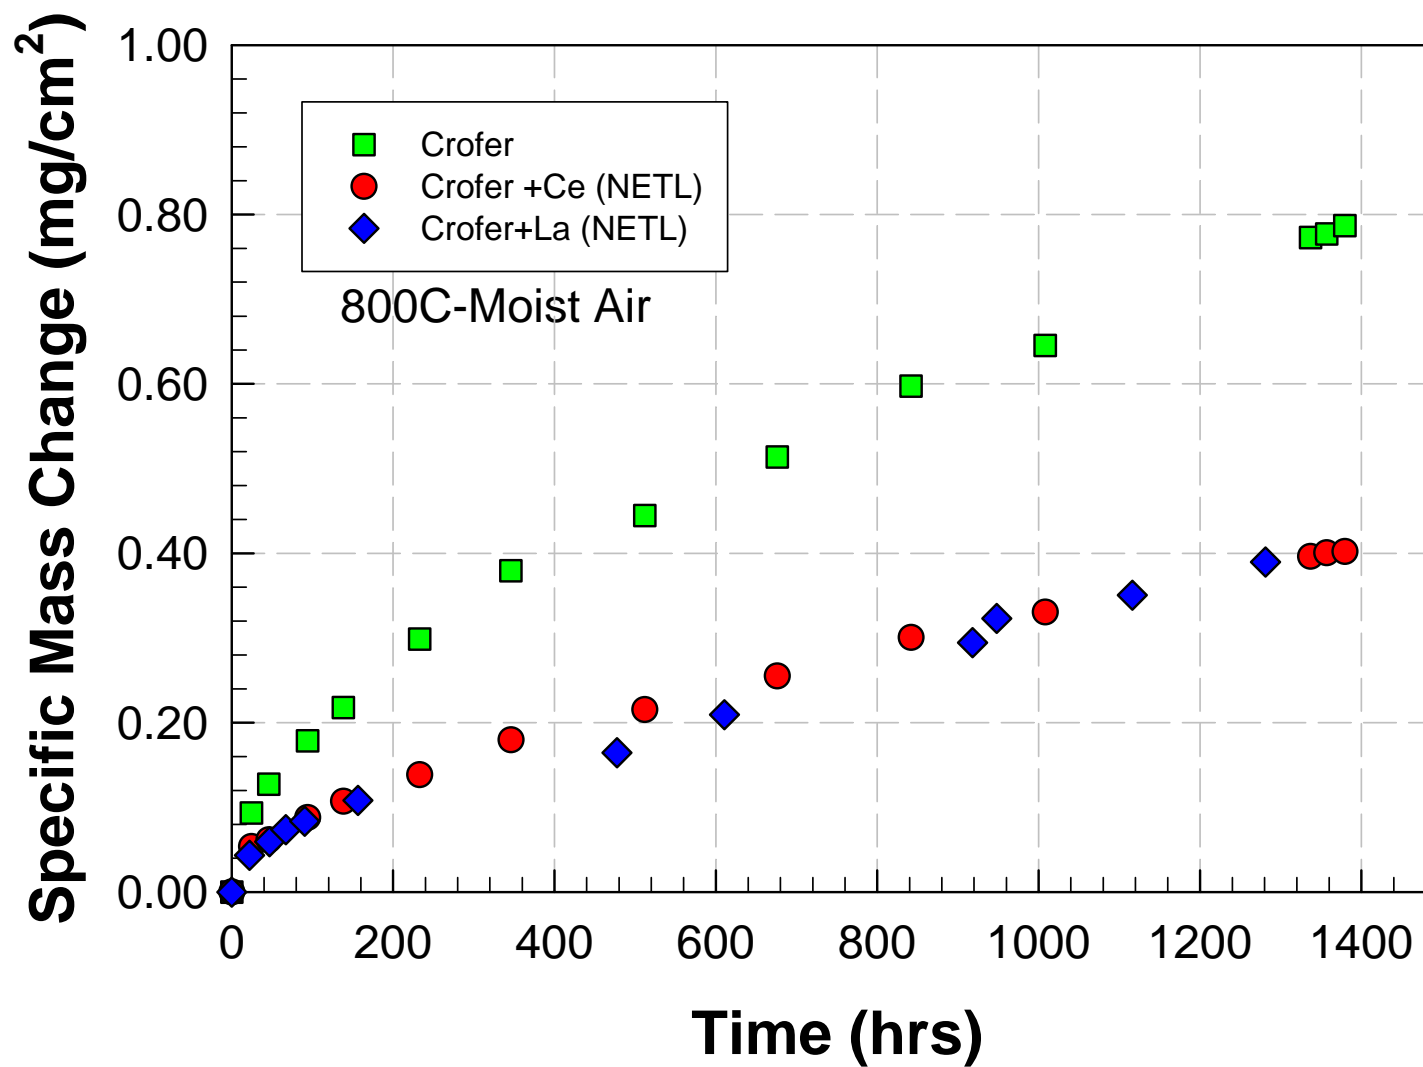

# Initial Conductivity: ASR Experimental Setup

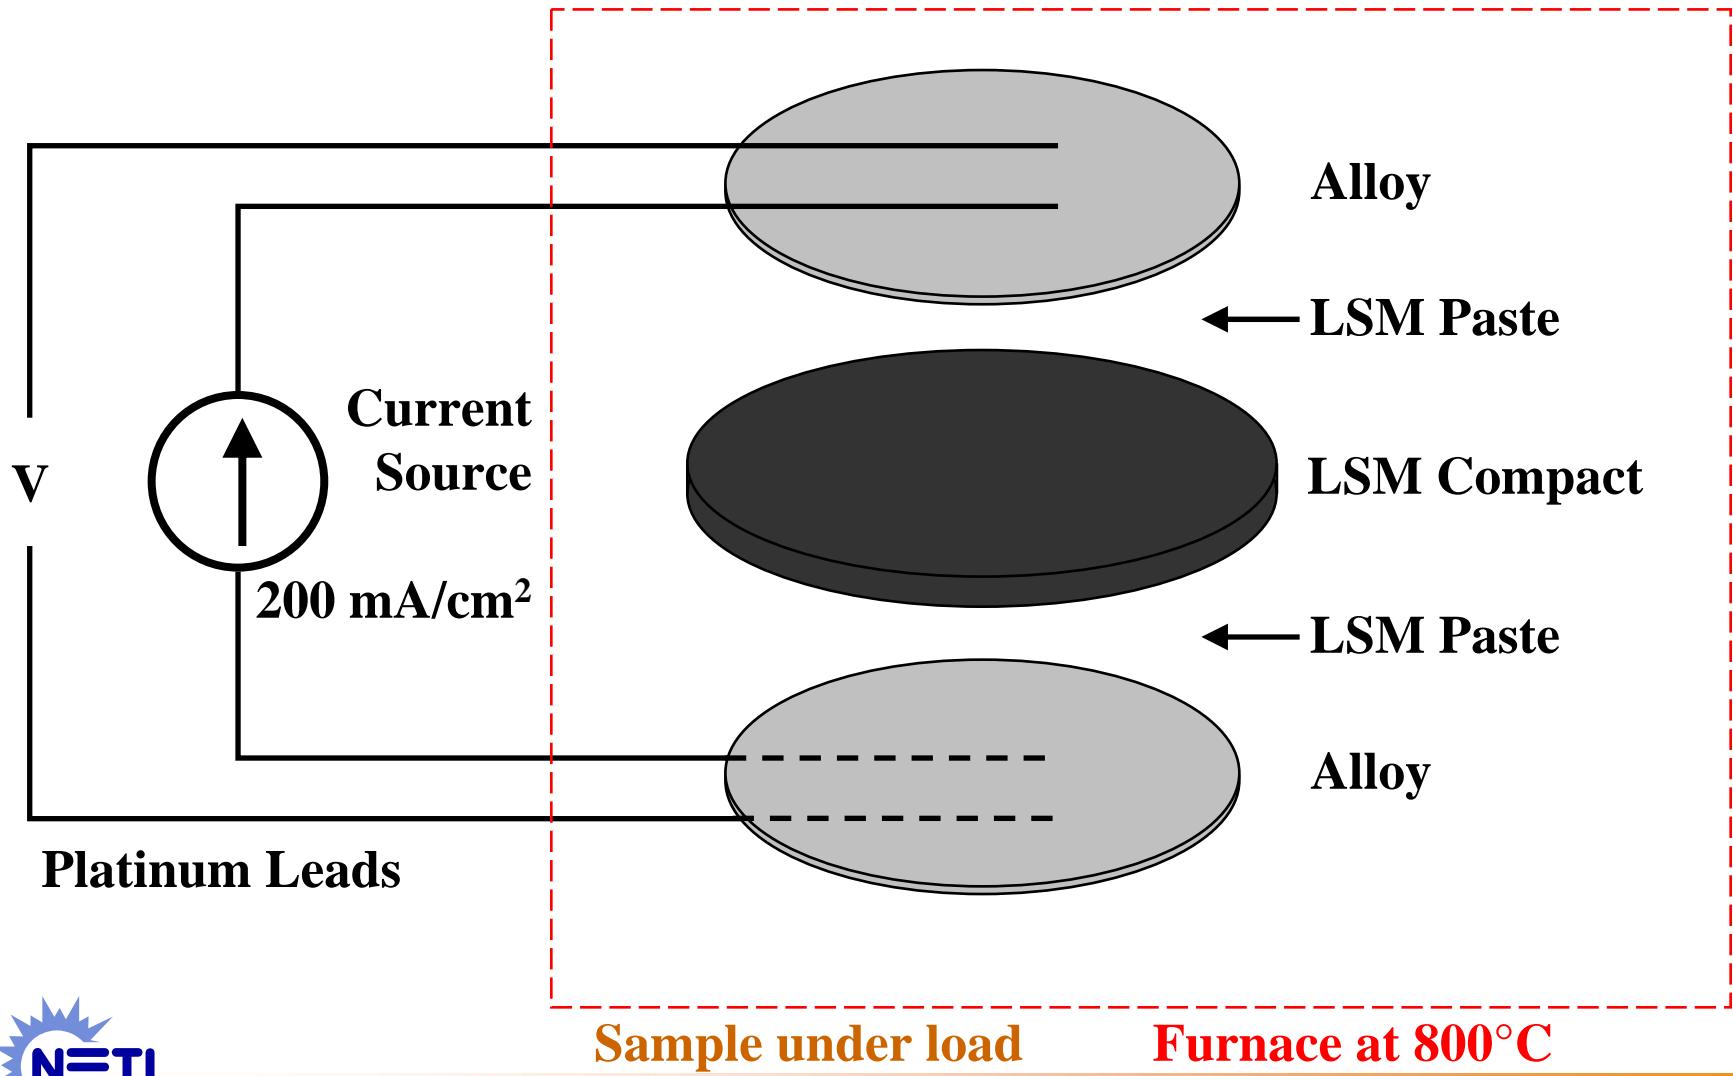

# Electrical Performance

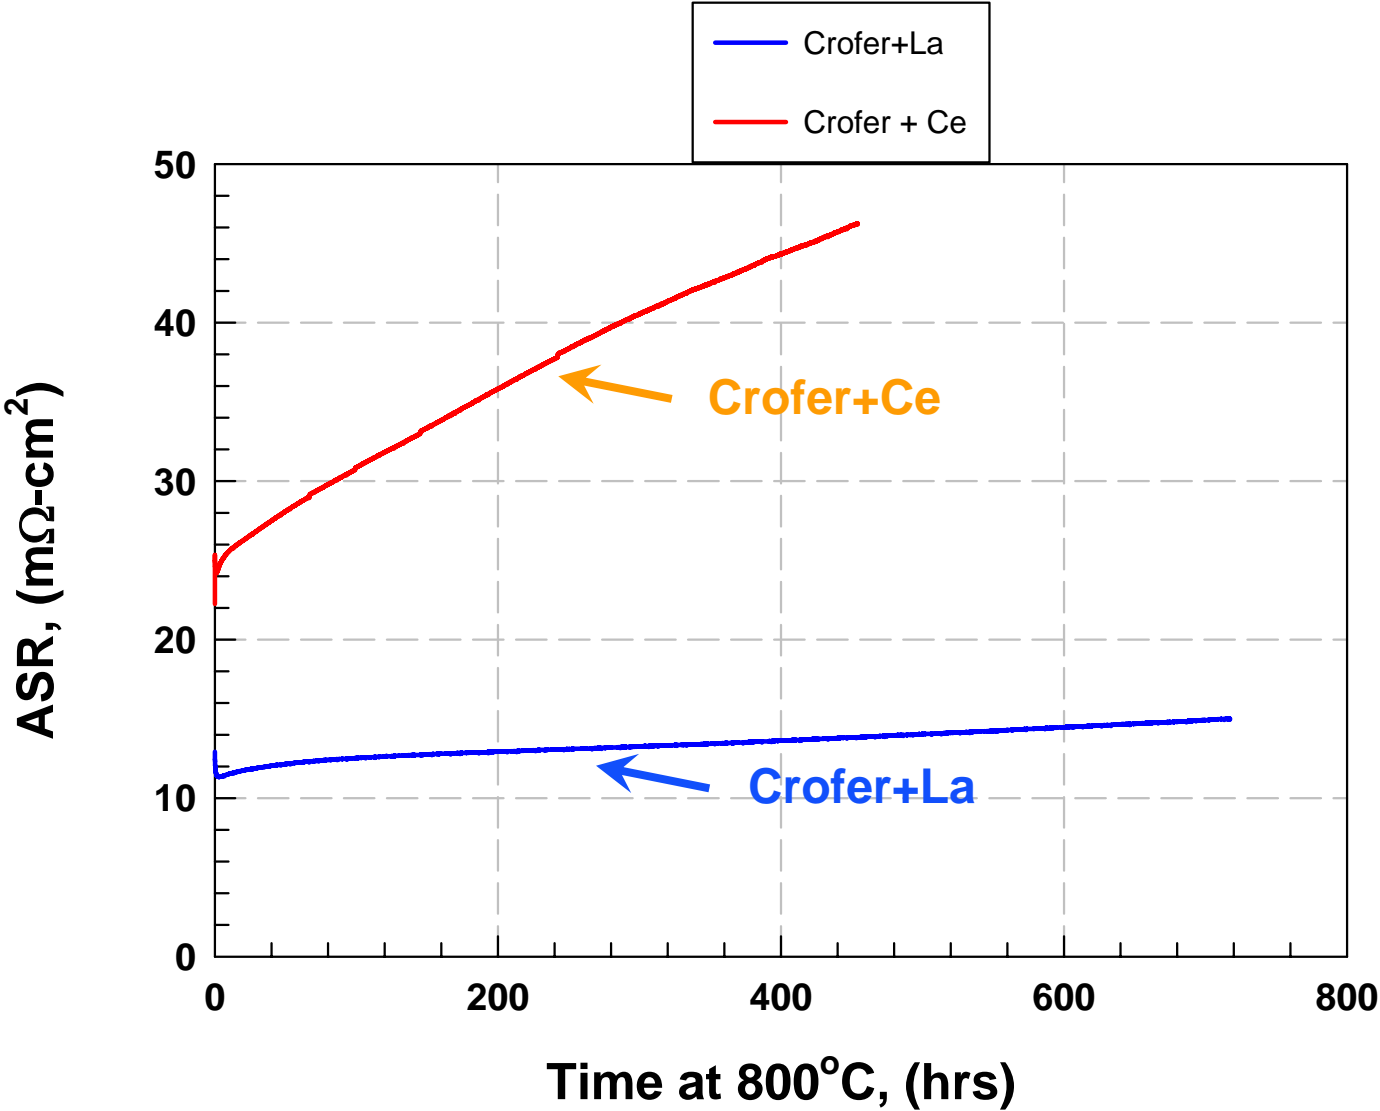

---

# Summary

- **RE surface treatments effective in improving oxidation resistance.**
  - Applied to ferritic stainless steels for interconnect application (Crofer and Type 430).
  - Both Ce-based methods (NETL and H/S) were effective.
  - La modification to the NETL method was effective.
- **ASR measurements indicate that slower scale growth will enhance SOFC performance.**



## On-Going and *Future Work*

- **Continue long term exposures on Ce- and La-treated samples**
  - to determine if and when breaks-down occurs
  - accelerated tests
  - *Analyze long term ASR (or cell tests)*
- **Continue investigation influence of Si content**
  - Determine critical Si level
  - *Low cost production of low Si steels using recycled scrap (develop innovative slag additives to getter Si during metling).*





# Experimental Alloys and RE Surface Treated Materials Available For Evaluation by SECA Participants



**Contact:**

**Paul D. Jablonski: 541.967.5982 or**

**David E. Alman: 541.967.5885**

