

# SIMS Study of Elemental Diffusion During Solid Phase Crystallization of Amorphous Silicon

R.C. Reedy, D. Young, H.M. Branz, and Q. Wang

*Presented at the 2005 DOE Solar Energy Technologies Program Review Meeting  
November 7–10, 2005  
Denver, Colorado*

**Conference Paper**  
**NREL/CP-520-38974**  
**November 2005**

NREL is operated by Midwest Research Institute • Battelle Contract No. DE-AC36-99-GO10337



## NOTICE

The submitted manuscript has been offered by an employee of the Midwest Research Institute (MRI), a contractor of the US Government under Contract No. DE-AC36-99GO10337. Accordingly, the US Government and MRI retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.osti.gov/bridge>

Available for a processing fee to U.S. Department of Energy and its contractors, in paper, from:

U.S. Department of Energy  
Office of Scientific and Technical Information  
P.O. Box 62  
Oak Ridge, TN 37831-0062  
phone: 865.576.8401  
fax: 865.576.5728  
email: <mailto:reports@adonis.osti.gov>

Available for sale to the public, in paper, from:

U.S. Department of Commerce  
National Technical Information Service  
5285 Port Royal Road  
Springfield, VA 22161  
phone: 800.553.6847  
fax: 703.605.6900  
email: [orders@ntis.fedworld.gov](mailto:orders@ntis.fedworld.gov)  
online ordering: <http://www.ntis.gov/ordering.htm>



# SIMS Study of Elemental Diffusion During Solid Phase Crystallization of Amorphous Silicon

Robert C. Reedy, David Young, Howard M. Branz, and Qi Wang  
National Renewable Energy Laboratory, Golden, Colorado, [bob\\_reedy@nrel.gov](mailto:bob_reedy@nrel.gov)

## ABSTRACT

Crystallization of hydrogenated amorphous silicon (a-Si:H) films deposited on low-cost substrates shows potential for solar cell applications. Secondary ion mass spectrometry (SIMS) was used to study impurity incorporation, hydrogen evolution, and dopant diffusion during the crystallization process.

## 1. Objectives

Thin-film silicon solar cells are produced on a variety of low-cost substrates by a variety of methods. Polycrystalline silicon has better electronic transport properties than hydrogenated amorphous silicon (a-Si:H)<sup>1</sup>, and solar cells produced from these films are not subject to light-induced degradation effects. Solar cell modules with adequate efficiency (8-9%) have been produced from crystallized hydrogenated amorphous silicon (a-Si:H) films grown by plasma-enhanced chemical vapor deposition (PECVD).<sup>2</sup> However, deposition of electronic-grade a-Si thin films by PECVD is typically done at a low rate, between 1 – 10 Å/s. Higher deposition rates (greater than 100 Å/s) of good quality a-Si:H films can be achieved by hot wire chemical vapor deposition (HWCVD).<sup>3</sup>

Low cost substrate materials e.g. glass and stainless steel, have constituents that can be detrimental to material quality if incorporated into the crystallized silicon, and dopant diffusion can diminish device quality. For these experiments, SIMS depth profile analysis after film crystallization is used to study hydrogen and dopant diffusion, substrate impurity incorporation and the effectiveness of barrier coatings.

## 2. Technical Approach

Films of a-Si:H were deposited by HWCVD and PECVD onto low-cost substrates. Solid phase crystallization (SPC) was achieved by annealing the films using a hot plate in an N<sub>2</sub> ambient and also by using a tube furnace. Determination of crystallinity is achieved in real-time by reflectance measurements<sup>4</sup> in the hot plate setup and verified by XRD.

SIMS was used to study the incorporation of impurities from the various substrate at different anneal times and temperatures. SIMS measurements were taken by a Cameca IMS-5F at 14.5keV Cs<sup>+</sup> for detection of light elements and dopants, and 8.0keV O<sub>2</sub><sup>+</sup> for detection of metals.

## 3. Results and Accomplishments

### 3.1 Crystallized Silicon on Stainless Steel Substrates

Initial experiments were conducted on a-Si:H films deposited directly on thin stainless steel substrates. Figure 1 shows that the crystallized a-Si:H films have large quantities of metallic impurities introduced during the anneal. A thin layer of SiN<sub>x</sub> deposited prior to the a-Si:H was discovered to provide an effective impurity diffusion barrier. However, the roughness of the steel substrate degrades the depth resolution in the SIMS depth profiles and complicates the understanding of diffusion measurements. Non-uniform lateral distribution of impurities and optical microscopy, indicated cracks in the film, most likely due to a large mismatch in the coefficient of thermal expansion (CTE) between silicon and steel. Poor depth resolution and film cracking during SPC shifted our focus to glass substrates.

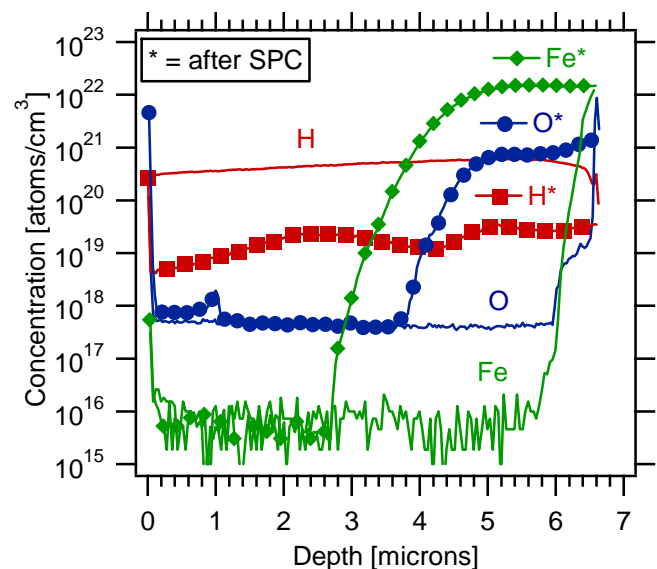


Fig. 1. SIMS impurity concentrations of the indicated elements in a 7-micron Si film on stainless steel that was crystallized from a-Si:H at 550°C for 91 hours.

### 3.2 Crystallized Silicon on Glass Substrates

Samples for SPC were grown directly on Corning 1737F glass. After film crystallization, no detectable impurities were introduced from the glass, even at temperatures up to 575°C. The oxygen content did not change during SPC, remaining at about 10<sup>18</sup> /cm<sup>3</sup>, lower than what is normally found in CZ-silicon.

Comparisons of different anneal temperatures were made on samples of a-Si:H deposited on SnO<sub>2</sub>-coated Corning-1737F glass, before and after SPC. SnO<sub>2</sub> is

commonly used as a transparent conducting oxide in a-Si:H solar cells. Textured SnO<sub>2</sub> aids in light trapping, but creates difficulties in for SIMS depth profiling; and even “smooth” SnO<sub>2</sub> contains some roughness. A thin layer of P-doped silicon (n-layer) was deposited prior to the intrinsic (i) layer. SIMS depth profiles showed approximately 100nm diffusion of P and O during SPC.

### 3.3 Hydrogen in Crystallized Silicon

Hydrogen is known to evolve from a-Si during high temperature anneals before crystallization and it is important to know at what point during nucleation and crystallization the H evolves. Experiments were performed to study the evolution of hydrogen in the SPC of a-Si:H process. Samples from multiple points in the crystallization process (indication from optical reflectance measurements) were measured. Figure 2 shows increasing H evolution with anneal T in samples that were annealed for 4 hours.

Comparisons were also made on samples of a-Si:H films containing 14 at.% (high) H and 4 at.% (low) hydrogen. The high hydrogen films were grown at a lower substrate temperature and have higher O contents. Even after crystallization, higher H levels were observed in the “high H” films than in the “low H” films. This suggests a higher defect density that traps hydrogen.

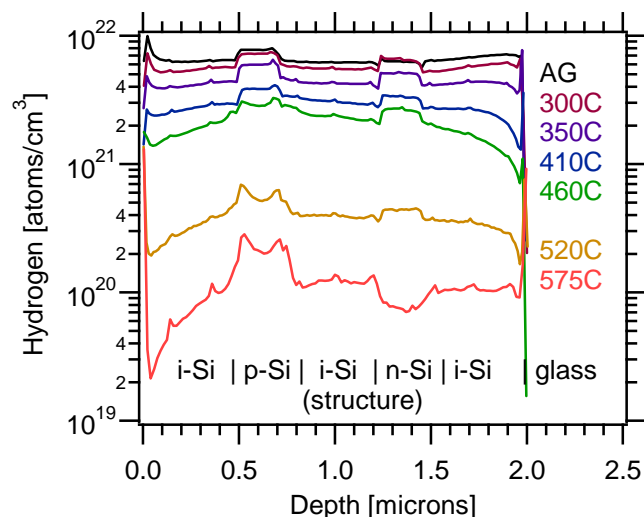


Fig. 2. a-Si:H (i-p-i-n-i) structure showing increased hydrogen evolution at higher anneal temperature.

### 3.4 Dopant Diffusion During the SPC Process

SIMS was also used to study B and P dopant diffusion during the anneal process. Structures were grown comprising both n-type and p-type a-Si:H layers sandwiched between intrinsic layers (i-p-i-n-i/glass). Samples were annealed at different temperatures for 4 hours and then depth-profiled by SIMS. We found that B (at  $\sim 2 \times 10^{19} \text{ cm}^{-3}$ ) did not move significantly during SPC. However, P (at  $\sim 10^{21} \text{ cm}^{-3}$ ) did diffuse considerably, as shown in Fig. 3. High mass

resolution measurements of <sup>31</sup>P in a-Si:H are also challenging due the high levels (1-10 at.%) of H, which can form <sup>31</sup>Si<sup>1</sup>H secondary ions.

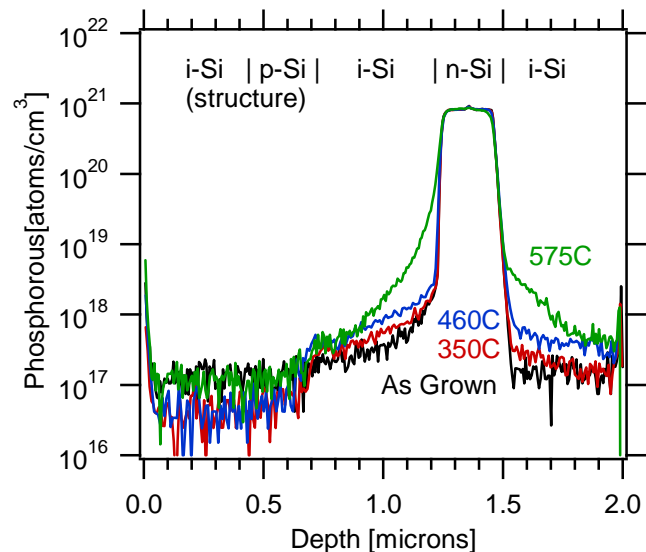


Fig. 3. SIMS P concentrations vs anneal temperature.

## 4. Conclusions

Problems with cracking occur with stainless steel as a substrate for a-Si:H crystallization, although SiN<sub>x</sub> performs well as a diffusion barrier. SPC of films on 1737F glass showed no evidence of impurities from the glass, even up to annealing temperatures of 575°C. P dopant diffusion occurs during SPC, and hydrogen release occurs prior to nucleation and crystal growth. Crystallization of these films shows potential for solar cell applications.

## ACKNOWLEDGEMENTS

This work was funded by the U.S. Department of Energy under Contract No. DE-AC36-99-GO10337. We thank P. Stradins for many helpful discussions.

## REFERENCES

1. K. Pangal, J. C. Sturm, and S. Wagner, Integrated amorphous and polycrystalline silicon thin-film transistors in a single silicon layer. *IEEE Transactions on Electron Devices* 48, 707 (2001).
2. M. A. Green, et al, Crystalline silicon on glass (CSG) thin-film solar cell modules. *Solar Energy Materials and Solar Cells* 77, 857 (2004).
3. A. H. Mahan, Y. Xu, D. L. Williamson, W. Beyer, J. D. Perkins, M. Vanecek, L. M. Gedvilas, and B. P. Nelson, Structural properties of hot wire a-Si:H films deposited at rates in excess of 100 Å/s. *Journal of Applied Physics* 90, 5038 (2001).
4. P. Stradins, D. Young, Y. Xu, H. Branz, and Q. Wang, Real time monitoring of the crystallization of hydrogenated amorphous silicon and its alloys. *MRS Spring Meeting, San Francisco, CA* (2005).

# REPORT DOCUMENTATION PAGE

Form Approved  
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Executive Services and Communications Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

**PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.**

<b>1. REPORT DATE (DD-MM-YYYY)</b> November 2005		<b>2. REPORT TYPE</b> Conference Paper		<b>3. DATES COVERED (From - To)</b>	
<b>4. TITLE AND SUBTITLE</b> SIMS Study of Elemental Diffusion During Solid Phase Crystallization of Amorphous Silicon				<b>5a. CONTRACT NUMBER</b> DE-AC36-99-GO10337	
				<b>5b. GRANT NUMBER</b>	
				<b>5c. PROGRAM ELEMENT NUMBER</b>	
<b>6. AUTHOR(S)</b> R.C. Reedy, D. Young, H.M. Branz, and Q. Wang				<b>5d. PROJECT NUMBER</b> NREL/CP-520-38974	
				<b>5e. TASK NUMBER</b> PVA6.3301	
				<b>5f. WORK UNIT NUMBER</b>	
<b>7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES)</b> National Renewable Energy Laboratory 1617 Cole Blvd. Golden, CO 80401-3393				<b>8. PERFORMING ORGANIZATION REPORT NUMBER</b> NREL/CP-520-38974	
<b>9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)</b>				<b>10. SPONSOR/MONITOR'S ACRONYM(S)</b> NREL	
				<b>11. SPONSORING/MONITORING AGENCY REPORT NUMBER</b>	
<b>12. DISTRIBUTION AVAILABILITY STATEMENT</b> National Technical Information Service U.S. Department of Commerce 5285 Port Royal Road Springfield, VA 22161					
<b>13. SUPPLEMENTARY NOTES</b>					
<b>14. ABSTRACT (Maximum 200 Words)</b> Crystallization of hydrogenated amorphous silicon (a-Si:H) films deposited on low-cost substrates shows potential for solar cell applications. Secondary ion mass spectrometry (SIMS) was used to study impurity incorporation, hydrogen evolution, and dopant diffusion during the crystallization process.					
<b>15. SUBJECT TERMS</b> Photovoltaics; solar; amorphous silicon; crystallization; PV; NREL					
<b>16. SECURITY CLASSIFICATION OF:</b>			<b>17. LIMITATION OF ABSTRACT</b> UL	<b>18. NUMBER OF PAGES</b>	<b>19a. NAME OF RESPONSIBLE PERSON</b>
<b>a. REPORT</b> Unclassified	<b>b. ABSTRACT</b> Unclassified	<b>c. THIS PAGE</b> Unclassified			<b>19b. TELEPHONE NUMBER (Include area code)</b>