


Effect of a Coadsorbent on the Performance of Dye-Sensitized TiO₂ Solar Cells: Shielding versus Band-Edge Movement

A.J. Frank, N.R. Neale, N. Kopidakis, and
J. van de Lagemaat
National Renewable Energy Laboratory


M. Grätzel
Swiss Federal Institute of Technology

*Presented at the 2005 DOE Solar Energy Technologies
Program Review Meeting
November 7–10, 2005
Denver, Colorado*

Conference Paper
NREL/CP-590-38978
November 2005



NREL is operated by Midwest Research Institute • Battelle Contract No. DE-AC36-99-GO10337



NOTICE

The submitted manuscript has been offered by an employee of the Midwest Research Institute (MRI), a contractor of the US Government under Contract No. DE-AC36-99GO10337. Accordingly, the US Government and MRI retain a nonexclusive royalty-free license to publish or reproduce the published form of this contribution, or allow others to do so, for US Government purposes.

This report was prepared as an account of work sponsored by an agency of the United States government. Neither the United States government nor any agency thereof, nor any of their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States government or any agency thereof.

Available electronically at <http://www.osti.gov/bridge>

Available for a processing fee to U.S. Department of Energy and its contractors, in paper, from:

U.S. Department of Energy
Office of Scientific and Technical Information
P.O. Box 62
Oak Ridge, TN 37831-0062
phone: 865.576.8401
fax: 865.576.5728
email: <mailto:reports@adonis.osti.gov>

Available for sale to the public, in paper, from:

U.S. Department of Commerce
National Technical Information Service
5285 Port Royal Road
Springfield, VA 22161
phone: 800.553.6847
fax: 703.605.6900
email: orders@ntis.fedworld.gov
online ordering: <http://www.ntis.gov/ordering.htm>



Effect of a Coadsorbent on the Performance of Dye-Sensitized TiO₂ Solar Cells: Shielding versus Band-Edge Movement

Arthur J. Frank,¹ Nathan R. Neale,¹ Nikos Kopidakis,¹ Jao van de Lagemaat,¹ and Michael Grätzel²

¹National Renewable Energy Laboratory, Golden, Colorado, arthur_frank@nrel.gov

²Swiss Federal Institute of Technology, Lausanne, Switzerland

ABSTRACT

The objective of this research is to determine the operational characteristics key to efficient, low-cost, stable solar cells based on dye-sensitized mesoporous films (in collaboration with DOE's Office of Science Program). Toward this end, we have investigated the mechanism by which the adsorbent chenodeoxycholate, cografted with a sensitizer onto TiO₂ nanocrystals, improves the open-circuit photovoltage (V_{OC}) and short-circuit photocurrent density (J_{SC}).¹ We find that adding chenodeoxycholate not only shifts the TiO₂ conduction-band edge to negative potentials but also accelerates the rate of recombination. The net effect of these opposing phenomena is to produce a higher photovoltage. It is also found that chenodeoxycholate reduces the dye loading significantly but has only a modest effect on J_{SC} . Implications of these results to developing more efficient cells are discussed.

1. Objectives

The dye-sensitized solar cell (DSC) is a promising future generation concept for achieving efficient solar-to-electric energy conversion with very inexpensive materials and manufacturing processes. These cells feature dye molecules chemisorbed on the surface of TiO₂ nanocrystals that have been sintered into a highly porous thin film. The pores of the film are filled with a hole-conducting electrolyte. Photoexcited dye molecules inject electrons into the conduction band of TiO₂, and species in the electrolyte transport the holes from the oxidized dye molecules to the counter electrode. While J_{SC} is mostly controlled by the light-harvesting and charge-injection efficiencies of the dye, V_{OC} is determined by the difference between the quasi-Fermi level of electrons in the TiO₂ film and the energy of the redox couple in the electrolyte.

Over the past decade, numerous studies have reported that chemically treating the TiO₂ surface with certain organic molecules influences the photovoltage and/or the photocurrent. Passivation or shielding of recombination centers by adsorbed molecules is generally given as the explanation for the observed effect. However, there is evidence that adsorbed molecules can improve the cell performance by inducing band-edge movement.² In most studies, the proposed mechanism for the improved cell performance is based on measurements that do not distinguish between shielding and band-edge

movement. To devise more effective surface treatment strategies, it is critical to understand the mechanism by which the surface treatment affects cell performance. In this paper, we examine the basic physical processes by which the adsorbent, chenodeoxycholate, affects V_{OC} and J_{SC} in dye-sensitized solar cells.¹ Chenodeoxycholate is a cholesterol-based molecule that has been shown to improve J_{SC} and V_{OC} .

Understanding the fundamental phenomena governing cell performance is critical for underpinning the development of this new solar cell technology. Of programmatic importance is that sensitized nanoparticle solar cells represent the distinct technological promise for achieving mass-produced, ultra-low-cost solar panels with good efficiency.

2. Technical Approach

J - V measurements combined with optical absorption studies of dye desorption were used to evaluate the influence of tetrabutylammonium chenodeoxycholate on dye coverage, binding strength of dye, extent of dye aggregation, and J_{SC} under a variety of conditions in which the TiO₂ films were exposed to the coadsorbent and sensitizing dye TBA₂[RuL₂(NCS)₂] (L = 4-carboxylic acid-4'-carboxylate-2,2'-bipyridine; TBA = tetrabutylammonium). These measurements and associated calculations were performed to quantify the relationship of dye coverage to the light-harvesting efficiency of the cells. Measurements of V_{OC} as a function of the photocharge density (determined by infrared transmittance) were conducted to determine whether the changes in J_{SC} and V_{OC} (resulting from surface treatment) were caused by altering the band edge position and/or the rate of recombination.

3. Results and Accomplishments

The influence of chenodeoxycholate on dye loading was investigated under a variety of conditions in which the TiO₂ film was exposed to the sensitizing dye and coadsorbent. J - V measurements and desorption studies revealed that adding chenodeoxycholate reduces the dye loading by as much as 60% while having a relatively small effect on J_{SC} . While twice exposing a TiO₂ film to dye solution had no effect on the amount of dye coverage relative to a single exposure, the resulting dye layer was more resistant to displacement by chenodeoxycholate. These observations suggest that single dyeing of a TiO₂ film

leads to strongly and weakly adsorbed forms of the dye resulting from either different binding conformations or aggregates. A comparison of adsorption conditions revealed that although chenodeoxycholate reduced the dye coverage by about 60%, J_{SC} decreased by only 14%, from 13.2 to 11.4 mA cm⁻². Calculations using the Beer-Lambert Law along with measurements suggest that even at low loading enough dye is present to account for the otherwise surprisingly small drop in J_{SC} .

Figure 1 shows that at the same photoinduced charge density (1.5×10^{17} cm⁻³) the photovoltage of the cell with the dye and chenodeoxycholate-covered film was about 80 mV higher than that of the cell with a film exposed to just the dye. This result indicates that the adsorbent causes the TiO₂ bands to move upward by about 80 mV.

Figure 2 shows that at the same photocharge density, the recombination rate for the cell with chenodeoxycholate was five times higher than that for the cell without chenodeoxycholate. At constant photocharge density, an upward shift of the conduction band edge (Figure 1) would be expected to increase the rate of recombination (Figure 2) because the driving force for recombination is determined by the difference between the electron quasi-Fermi level and the electrochemical potential of the electrolyte. These measurements along with J - V data indicate that the net increase of V_{OC} as a result of both band-edge movement and recombination was more than 40 mV and that recombination diminished the effect of band-edge movement on V_{OC} by more than 40 mV.

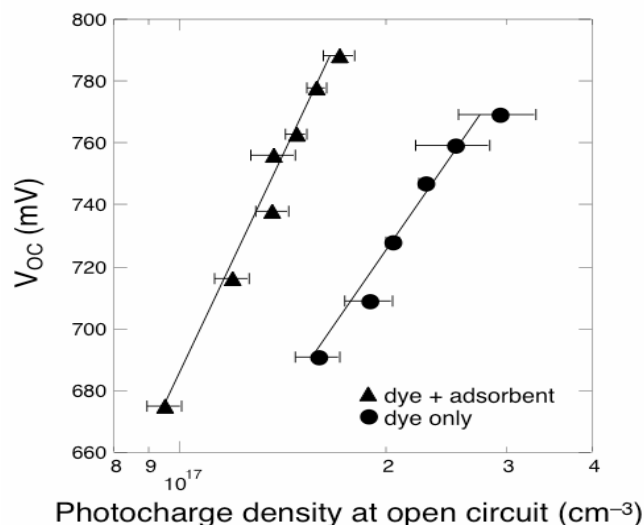


Fig. 1. Effect of chenodeoxycholate on the TiO₂ band-edge position.¹

4. Conclusions

The coadsorbent chenodeoxycholate is found to reduce the dye loading by about half but to have a disproportionately small effect on J_{SC} . Calculations reveal that even at such low dye loading enough dye

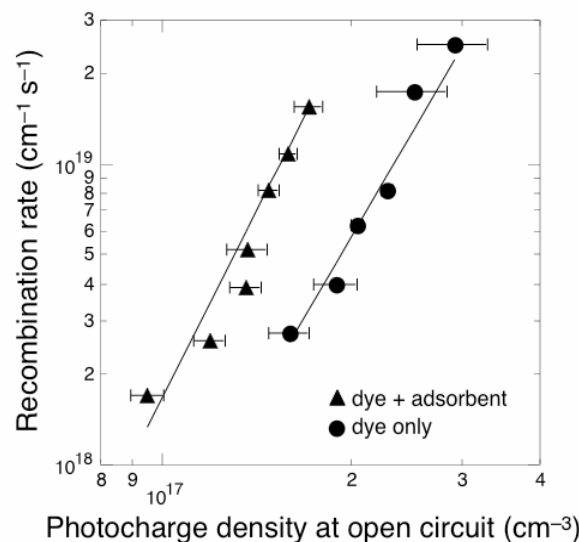


Fig. 2. Effect of chenodeoxycholate on the rate of recombination.¹

was present to absorb a significant fraction of incident light. Chenodeoxycholate is found to not only shift the band edges to negative potentials, but also to significantly increase the recombination rate. The net effect of adding chenodeoxycholate is, however, to improve the photovoltage. Future work will utilize the information from this study to devise a more effective surface treatment strategy for improved cell efficiency.

ACKNOWLEDGEMENTS

The NREL work was performed under DOE contract DE-AC36-99-GO10337.

REFERENCES

- N. R. Neale, N. Kopidakis, J. van de Lagemaat, M. Grätzel, and A. J. Frank, *J. Phys. Chem. B.*, in press.
- G. Schlichthörl, S. Huang, J. Sprague, and A. J. Frank, *J. Phys. Chem. B* **101**, 8141 (1997).

MAJOR FY 2005 PUBLICATIONS

N. Kopidakis, N. R. Neale, K. Zhu, J. van de Lagemaat and A. J. Frank, "Spatial Location of Transport-Limiting Traps in TiO₂ Nanoparticle Films in Dye-Sensitized Solar Cells," *Appl. Phys. Lett.*, in press.

N. Kopidakis, K. D. Benkstein, J. van de Lagemaat, A. J. Frank, Q. Yuan and E. A. Schiff, "Temperature Dependence of the Electron Diffusion Coefficient in Electrolyte-Filled TiO₂ Nanoparticle Films: Evidence Against Multiple Trapping In Exponential Conduction Band Tails," *Phys. Rev. B.*, submitted.

J. van de Lagemaat, N. Kopidakis, N. R. Neale, and A. J. Frank, "Effect of Nonideal Statistics on Electron Diffusion in Sensitized Nanocrystalline TiO₂," *Phys. Rev. B.* **71**, 035304 (2005).

REPORT DOCUMENTATION PAGE

Form Approved
OMB No. 0704-0188

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing the burden, to Department of Defense, Executive Services and Communications Directorate (0704-0188). Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.

PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ORGANIZATION.

1. REPORT DATE (DD-MM-YYYY) November 2005		2. REPORT TYPE Conference Paper		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE Effect of a Coadsorbent on the Performance of Dye-Sensitized TiO ₂ Solar Cells: Shielding versus Band-Edge Movement				5a. CONTRACT NUMBER DE-AC36-99-GO10337	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) A.J. Frank, N.R. Neale, N. Kopidakis, J. van de Lagemaat, and M. Grätzel				5d. PROJECT NUMBER NREL/CP-590-38978	
				5e. TASK NUMBER PVA6.0603	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) National Renewable Energy Laboratory 1617 Cole Blvd. Golden, CO 80401-3393				8. PERFORMING ORGANIZATION REPORT NUMBER NREL/CP-590-38978	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S) NREL	
				11. SPONSORING/MONITORING AGENCY REPORT NUMBER	
12. DISTRIBUTION AVAILABILITY STATEMENT National Technical Information Service U.S. Department of Commerce 5285 Port Royal Road Springfield, VA 22161					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT (Maximum 200 Words) The objective of this research is to determine the operational characteristics key to efficient, low-cost, stable solar cells based on dye-sensitized mesoporous films (in collaboration with DOE's Office of Science Program). Toward this end, we have investigated the mechanism by which the adsorbent chenodeoxycholate, cografed with a sensitizer onto TiO ₂ nanocrystals, improves the open-circuit photovoltage (V_{OC}) and short-circuit photocurrent density (J_{SC}). ¹ We find that adding chenodeoxycholate not only shifts the TiO ₂ conduction-band edge to negative potentials but also accelerates the rate of recombination. The net effect of these opposing phenomena is to produce a higher photovoltage. It is also found that chenodeoxycholate reduces the dye loading significantly but has only a modest effect on J_{SC} . Implications of these results to developing more efficient cells are discussed.					
15. SUBJECT TERMS Photovoltaics; solar; coadsorbent; die-sensitized TiO ₂ ; PV; NREL					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT UL	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT Unclassified	b. ABSTRACT Unclassified	c. THIS PAGE Unclassified			19b. TELEPHONE NUMBER (Include area code)