



The EBR-II X501 Minor Actinide Burning Experiment

Global Nuclear Energy Partnership

***Prepared for
U.S. Department of Energy
Transmutation Fuel Campaign***

***M. K. Meyer
S. L. Hayes
W. J. Carmack
H. Tsai***

January 2008

GNEP-FUEL-TD-RT-2008-000061



The EBR-II X501 Minor Actinide Burning Experiment

**M. K. Meyer
S. L. Hayes
W. J. Carmack
H. Tsai**

January 2008

**Idaho National Laboratory
Idaho Falls, Idaho 83415**

**Prepared for the
U.S. Department of Energy
Office of Nuclear Energy
Under DOE Idaho Operations Office
Contract DE-AC07-05ID14517**


DISCLAIMER

This information was prepared as an account of work sponsored by an agency of the U.S. Government. Neither the U.S. Government nor any agency thereof, nor any of their employees, makes any warranty, expressed or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or usefulness, of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. References herein to any specific commercial product, process, or service by trade name, trade mark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the U.S. Government or any agency thereof. The views and opinions of authors expressed herein do not necessarily state or reflect those of the U.S. Government or any agency thereof.

Reviewed by:

Transmutation Fuel Campaign


Transmutation Fuel Campaign Deputy Director



Jon Carmack 2/28/2008
Date

Transmutation Fuel Campaign

Technical Lead for Irradiation Testing



Steven Hayes 2/28/08
Date

INTENTIONALLY BLANK

SUMMARY

The X501 experiment was conducted in EBR-II as part of the Integral Fast Reactor program to demonstrate minor actinide burning through the use of a homogeneous recycle scheme. The X501 subassembly contained two metallic fuel elements loaded with relatively small quantities of americium and neptunium. Interest in the behavior of minor actinides (MA) during fuel irradiation has prompted further examination of existing X501 data and generation of new data where needed in support of the U.S. waste transmutation effort. The X501 experiment is one of the few MA-bearing fuel irradiation tests conducted worldwide, and knowledge can be gained by understanding the changes in fuel behavior due to addition of MAs. Of primary interest are the effect of the MAs on fuel-cladding-chemical-interaction and the redistribution behavior of americium. The quantity of helium gas release from the fuel and any effects of helium on fuel performance are also of interest. It must be stressed that information presented at this time is based on the limited PIE conducted in 1995–1996 and, currently, represents a set of observations rather than a complete understanding of fuel behavior.

This report provides a summary of the X501 fabrication, characterization, irradiation, and post-irradiation examination.

INTENTIONALLY BLANK

CONTENTS

SUMMARY	v
ACRONYMS.....	ix
1. INTRODUCTION.....	1
2. X501 FABRICATION	2
2.1 Materials and Methods.....	2
2.2 Fabrication Results.....	2
2.3 Bottom of Fuel Slug.....	3
2.4 Top of Fuel Slug	4
2.5 Fuel Slug Bulk Chemistry.....	5
2.6 X501 Experiment Irradiation	6
2.7 X501 Post-irradiation Examination.....	7
3. CONCLUSION	11
4. ACKNOWLEDGMENTS	11
5. REFERENCES.....	11

FIGURES

1. Microstructure of as-cast fuel pin: (a) top section, (b) lower section. Fiducial Bar = 500 μm	3
2. (a) Transverse optical micrograph of the bottom of the as-fabricated U-20.3%Pu-10.0% Zr-2.1%Am-1.3%Np fuel, and (b) wavelength dispersive spectroscopy of A – B line section.....	3
3. Individual features in bottom section of the fuel: (a) Secondary electron image of the two particle types; (b) higher magnification secondary electron image of area B.	4
4. (a) Transverse optical micrograph of the top of the as-fabricated U-20.3%Pu-10.0% Zr-2.1%Am-1.3%Np fuel casting, and (b) wavelength dispersive spectroscopy of A – B line section.....	4
5. Micrograph of as-fabricated U-20Pu-10Zr.	6
6. X501 experiment location in EBR-II.....	7
7. Example Cs-137 gamma scan of an X501 pin.	8
8. Optical micrograph of fuel/cladding interface.	8
9. (a) Post-irradiation optical image of MA-bearing fuel; (b) WDS line scans showing distribution of actinides and Zr.	9

TABLES

1.	Bulk chemical analysis of as-fabricated X501 fuel castings (in wt%).....	5
2.	Attributes of X501 minor actinide-bearing fuel elements.....	7
3.	X501 gas production and release	10
4.	Data and calculations for He production in ²⁴¹ Am-bearing fuels.....	10

ACRONYMS

EBR	Experimental Breeder Reactor
FCCI	Fuel-Cladding Chemical Interaction
HLW	high level waste
IFR	Integral Fast Reactor
INL	Idaho National Laboratory
LWR	light water reactor
MA	minor actinide
PIE	post-irradiation examination
WDS	wavelength dispersive spectroscopy

INTENTIONALLY BLANK

TRANSMUTATION FUEL CAMPAIGN

THE EBR-II X501 MINOR ACTINIDE BURNING EXPERIMENT

1. INTRODUCTION

The X501 experiment was conducted in Experimental Breeder Reactor (EBR)-II at the Idaho National Laboratory (INL) as part of the IFR (Integral Fast Reactor) program to demonstrate minor actinide (MA) burning through the use of a homogeneous recycle scheme. The X501 subassembly contained two metallic fuel elements loaded with relatively small quantities of americium and neptunium. Interest in the behavior of MAs during fuel irradiation has prompted further examination of existing X501 data and generation of new data, where needed, in support of the U.S. waste transmutation effort. The X501 experiment is one of the few MA-bearing fuel irradiation tests conducted worldwide, and knowledge can be gained by understanding the changes in fuel behavior due to addition of MAs. Of primary interest are the effect of the MAs on fuel-cladding-chemical-interaction and the redistribution behavior of americium. The quantity of helium gas release from the fuel and any effects of helium on fuel performance are also of interest. It must be stressed that information presented at this time is based on the limited post-irradiation examination (PIE) conducted in 1995–1996 and, currently, represents a set of observations rather than a complete understanding of fuel behavior.

The original concept of the IFR incorporated a passively safe reactor design with onsite fuel recycling.¹ The IFR process utilized pyroprocessing of metallic fuel to separate U, Pu, and the MAs (Am, Np, and Cm) from the non-actinide constituents. The actinides are reintroduced into the fuel and re-irradiated. Spent IFR fuel was expected to contain low levels of the MAs because the hard neutron spectrum should transmute these isotopes as they are produced. This opens the possibility of using an IFR to transmute actinide waste from spent light water reactor (LWR) fuel. Elimination of actinides from spent LWR fuel, which is destined for the high level waste (HLW) repository, would greatly reduce the amount of long-lived radioactive material requiring isolation of approximately 10 years or more.^{2,3} Reducing the levels of actinides in HLW would make the performance criteria of the repository easier to attain. A standard IFR fuel was based on the alloy U-20%Pu-10%Zr (in weight percent). The metallic fuel system eases the requirements for reprocessing methods and enables the MA metals to be incorporated into the fuel with simple modifications to the basic fuel casting process. The nominal fuel composition used in this experiment is U-20.3%Pu-10.0%Zr-2.1%Am-1.3%Np and is based on a concept where the standard IFR fuel is fabricated with Pu extracted from spent LWR fuel which has cooled 10 years. The LWR fuel is then envisioned to have gone through a reprocessing scheme during which the MAs accompany the Pu through the processing steps. About 0.12 wt% of Cm would also be present, but the radiation protection difficulties, created by handling Cm outside of a hot cell and the low alloying content, eliminated Cm from inclusion in these experiments. In this document, we report the initial casting experience of IFR fuel containing MAs, the irradiation conditions for the X501 experiment, and a summary of the PIE of the two MA-bearing pins of the X501 experiment.

2. X501 FABRICATION

Metallic U-20%Pu-10%Zr (by weight) nuclear fuel was cast, using differential pressure injection, into a vitreous silica mold with the addition of two MAs, 2.1% Am and 1.3% Np. Three full-length fuel slugs (4.3 mm OD × 340 mm) were successfully cast, incorporating both Np and Am. No unusual macrosegregation of the major constituents was observed. About 60% of the initial Am and 100% of the Np charge was present in the as-cast fuel. Am loss was attributed to volatile contaminants in the feedstock and evaporation at the casting temperature (1465°C). Microstructural and microchemical characterization of the as-cast fuel, along with bulk chemical analyses, are reported. Details of the casting process and resulting microstructure are given in Trybus et al. 1993.⁴ Considerable americium was lost due to volatilization during the casting fabrication process. The casting furnace used was not designed for use with Am-bearing alloys.

2.1 Materials and Methods

The typical injection casting temperature for U-20%Pu-10%Zr is 1465°C. The superheat is about 150°C, which is required to fill the molds that are 4.3 mm OD × 460 mm. The feedstock used was elemental metallic Np, U, Zr, and Pu. The Am feedstock was a metallic alloy of Pu-20%Am. Of concern in casting metallic fuels with MA elements is the wide variation in vapor pressure between Am, Np, Pu and U. Also, the very highly negative free energy of oxide formation for Am is a potential issue. Over the range of melting temperatures, Am has nearly three orders of magnitude higher vapor pressure than Pu and five orders of magnitude higher vapor pressure than Np or U.^{5,6} This implies that a significant amount of Am could be lost as a vapor at casting temperatures. The potential for Am oxidation arises because AmO is considerably more stable than ZrO, UO, or PuO at all temperatures.⁷ It is possible that the Am could become part of the casting dross and not be incorporated into the fuel. The challenge becomes how to cast these fuel alloys with minimum Am loss under the characteristic range of processing conditions.

In order to reduce Am loss through evaporation and reaction with oxygen, the time at elevated temperatures, where the Am evaporation and reaction rates are high, should be constrained to as short as possible. The fabrication facility (the Experimental Fuels Laboratory at Argonne National Laboratory in Idaho) was, therefore, modified to include a bucket device with a lid allowing the Pu-Am feed material to be added to molten fuel within the crucible late in the melt cycle to minimize the time at temperature. Furthermore, the atmosphere above the melt was extremely pure Ar (99.9997%), containing less than 1.5 ppm oxygen. The elements (U, Zr, Np and some Pu) were loaded into a Y₂O₃-coated graphite crucible and induction heated under an Ar atmosphere. After reaching a temperature of 1495°C, the melt was stirred, causing the temperature to drop to 1465°C. The melt was reheated and stirred again. At this point, the Pu-Am was added to the crucible via the bucket which sat next to and above the crucible, inside the furnace. When the Pu-Am feedstock was added, “sparks” were observed emerging from the melt. Casting proceeded, and three full-length pins were successfully cast into ZrO₂ coated quartz molds. The entire crucible charge was consumed during casting, and the pins were removed from the molds. Two pins were encapsulated and made ready for in-reactor (EBR-II) testing, while the remaining pin was sacrificed for metallographic and chemical characterization.

2.2 Fabrication Results

Figure 1 shows optical images of fuel cross-sections taken from locations near the top and bottom of a pin from the same casting batch as the irradiated fuel pins. Figure 1(a) was taken from the top section of the fuel pin, and shows the inhomogeneous structure typical of U-Pu-Zr fuel produced by this casting method. Figure 1(b) shows a micrograph of a section taken from the lower part of the fuel pin, in a region where cooling is slower after solidification due to proximity with the furnace internals.

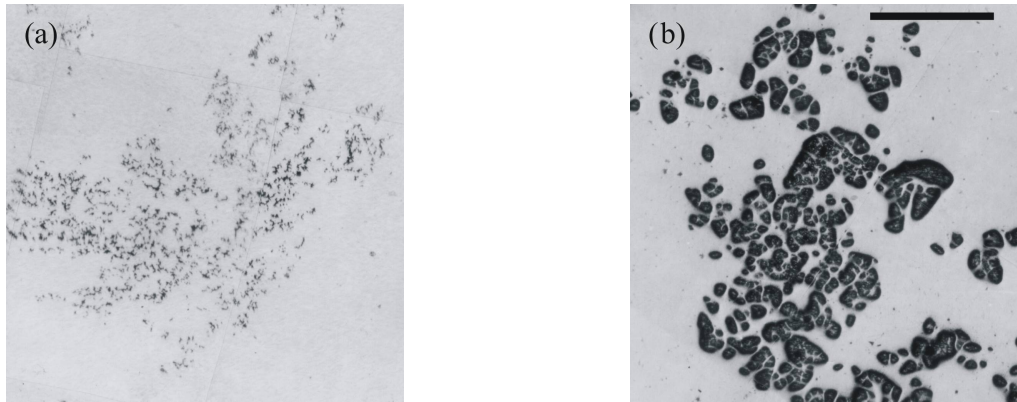


Figure 1. Microstructure of as-cast fuel pin: (a) top section, (b) lower section. Fiducial Bar = 500 μm.

2.3 Bottom of Fuel Slug

The as-cast microstructure at the bottom of the fuel is illustrated by the transverse view in Figure 2(a). The salient features are a darker gray, irregularly-shaped phase in a light matrix. Two areas of mold-melt interaction are indicated at A and B. At higher magnification (Figure 3), the irregular phase is found to be composed of a collection of two different smaller particles. Wavelength dispersive spectroscopy (WDS) analysis shown in Figure 2(b) indicates that the distribution of americium and neptunium is uniform across the section, and the light-colored, smaller (5-15 μm) particles are primarily composed of Zr, while the larger dark particles (30-60 μm) have a widely variable composition but contain, at most, only about 20% Zr. Very fine (0.5-1.5 μm), round particles termed “beads” were observed internal to the Zr-rich particles and found to be basically composed of U. Examination of the matrix by WDS revealed that the major constituents did not vary radially across the section. A few high Am peaks were detected, but could not be associated with any particular feature.

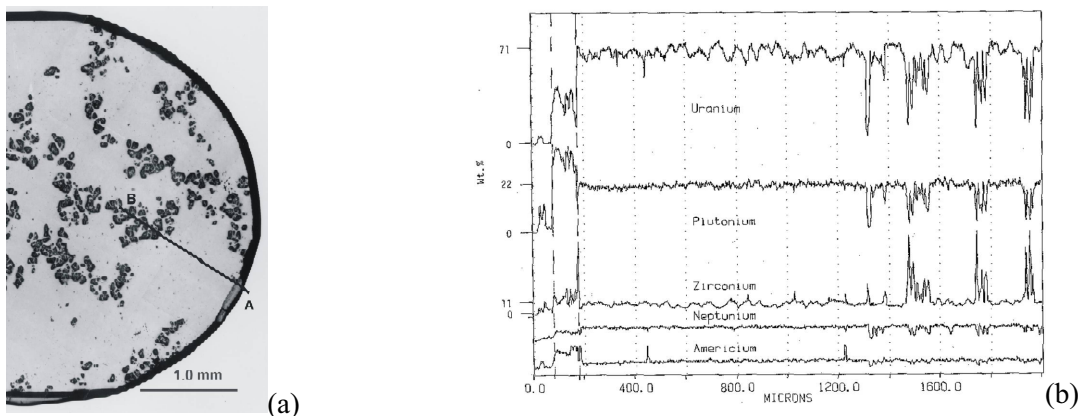


Figure 2. (a) Transverse optical micrograph of the bottom of the as-fabricated U-20.3%Pu-10.0% Zr-2.1%Am-1.3%Np fuel, and (b) wavelength dispersive spectroscopy of A – B line section.

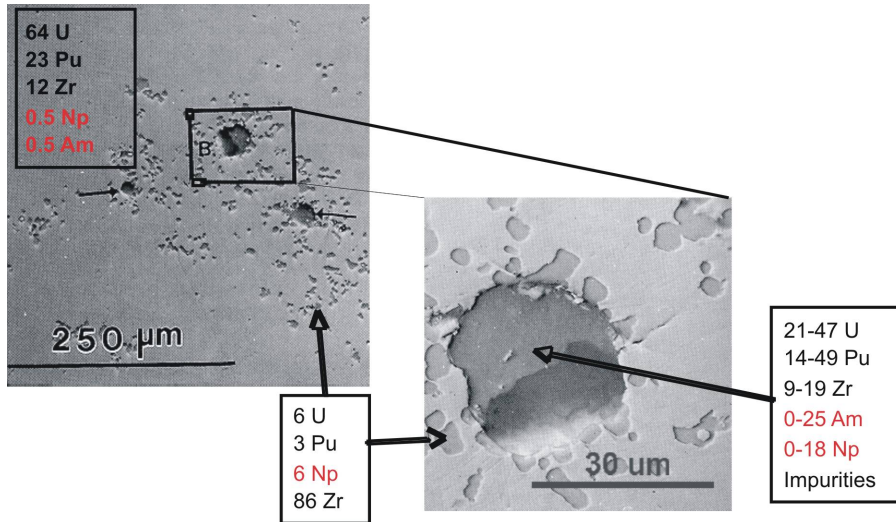


Figure 3. Individual features in bottom section of the fuel: (a) Secondary electron image of the two particle types; (b) higher magnification secondary electron image of area B.

2.4 Top of Fuel Slug

The microstructure in the top section of the fuel is shown in Figure 4(a). The microstructure in the top of the fuel slug was observed to be nearly the same as that in the center of the fuel slug. The Zr-rich regions were not collections of irregular particles as seen at the bottom of the fuel; rather, the Zr was present mainly in a dendritic morphology. No unusual mold-melt interaction layers were observed, and the matrix was uniform in composition as detected by WDS shown in Figure 4(b).

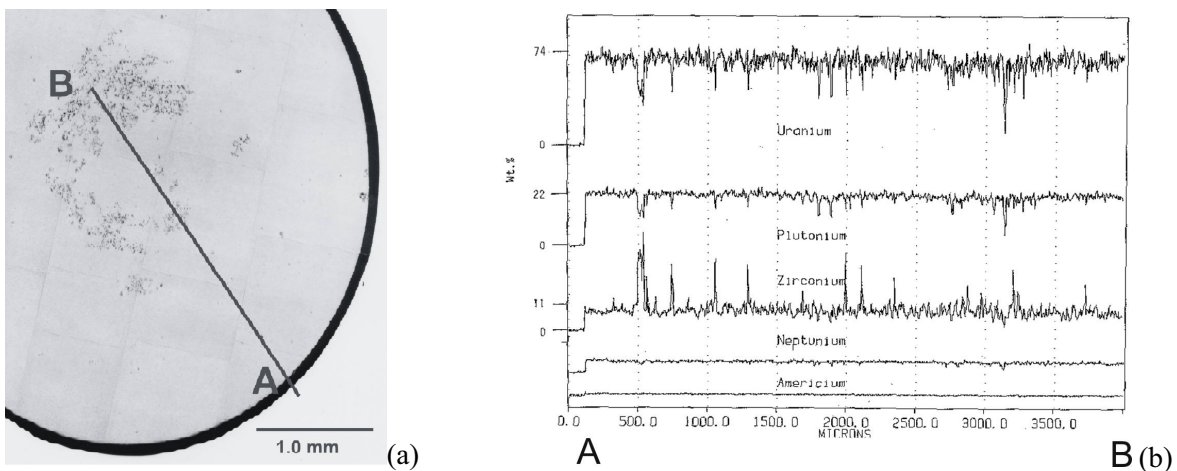


Figure 4. (a) Transverse optical micrograph of the top of the as-fabricated U-20.3%Pu-10.0% Zr-2.1%Am-1.3%Np fuel casting, and (b) wavelength dispersive spectroscopy of A – B line section.

2.5 Fuel Slug Bulk Chemistry

Sections from the top, center, and bottom of the fuel were chemically analyzed, and the results are given in Table 1. The U, Pu, Zr, and Np levels are axially uniform, within experimental error, while the Am level is low in the bottom section of the fuel. Some Am was lost as denoted by the low measured concentrations. Also, there is a notable increase in the amount of Si present in the bottom section versus the top and center sections. Increased Si levels are most likely due to the use of quartz (SiO₂) molds during fabrication. The ZrO wash does not completely protect the molds from the molten fuel, and some interaction occurs. Mold-melt interactions are most severe at the bottom of the molds because the mold ends are submerged in the melt for the entire casting time, and fuel located at the bottom of the slug cools last after injection casting.

Table 1. Bulk chemical analysis of as-fabricated X501 fuel castings (in wt%).

Element	Location			
	Top	Center	Bottom	Average
U	67.31	65.95	68.02	66.06
Pu	19.51	21.24	19.85	20.2
Zr	9.12	9.22	9.02	9.12
Am	1.33	1.32	1.03	1.23
Np	1.39	1.19	1.36	1.31
Si	0.179	0.179	0.422	0.26
Al	0.144	0.077	0.045	0.0887
Ca	0.189	0.0067	0.0046	0.0668
Mg	0.017	0.0028	0.0065	0.0088
Cr	0.0042	0.0018	0.0015	0.0025
Mn	0.0012	0.0009	0.0008	0.001
Fe	0.0018	0.0009	0.0007	0.0011
Ni	0.004	0.004	0.004	0.004

A representative transverse section from a U-20%Pu-10%Zr fuel slug without MA additions is shown in Figure 5. In this electron image, the dark phase is highly rich in Zr (~80% by weight) akin to the Zr-rich regions observed in the MA-bearing fuel; however, they differ morphologically. In conventional ternary fuel, the Zr-rich regions consist of contiguous globular features, but, in X501 castings, these “globular” regions were broken up into numerous small particles at the bottom of the fuel. This difference in shape could be the result of impurities in the melt.

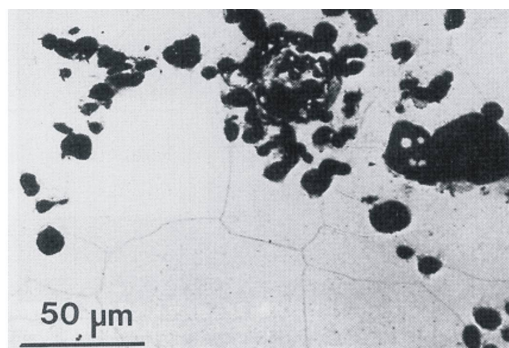


Figure 5. Micrograph of as-fabricated U-20Pu-10Zr.

Conventional U-Pu-Zr fuel contains, at most, about 300 ppm Si, while the fuel in X501 experiment contained up to 14 times more Si. The microchemical analysis revealed impurity segregation in the larger particles (Figure 3), i.e., Cl, Ca, Si, etc. This analysis is insensitive to light elements such as C, O, and N, and bulk chemical analysis of these elements was not available. Investigations into the U-Zr phase diagram⁸ uncovered significant changes in the phase relations at the U-rich end of the phase diagram due to small amounts of oxygen. It is reasonable to expect that the high Si content in the bottom of the fuel would influence the morphology of the Zr-rich phase. Further investigations into the phase relationships in fuel containing impurities, such as Si, O, C, N, and Ca, need to be done to determine what influence they have on microstructure and phase relationships. The sparking observed during the MA addition was found to be small droplets of the melt emerging from the crucible. Examinations of the inner furnace surfaces and exhaust lines after the casting revealed increased alpha activity from the Am. The “sparks” were induced by two factors: (1) contaminants in the Pu-Am feedstock with low boiling temperatures, and (2) the high vapor pressure of Am at the casting temperature 1465°C. The Pu-Am feedstock contained - 3 at% Ca and Mg (2000 ppm by weight). Both of these elements boil below 1440°C, causing the melt pool to become agitated. Secondly, the equilibrium vapor pressure of Am at 1465°C is 3.3 Torr, which yields an evaporation rate of about 0.1 g/cm²s using the Knudsen-Langmuir equation for pure Am in a vacuum. Considering a crucible with a surface area of 50 cm, an evaporation rate of about 0.1 g/cm²s yields a loss of 5 g per second in a perfect vacuum. The present controls on the casting furnace preclude an exact measurement or control of the pressure during casting, although a partial vacuum existed prior to placing the molds in the melt. The high vapor pressure of Am at the casting temperature cannot be altered, but large Am losses can be mitigated. Experimentation employing lower superheats would help but may not be feasible because a lower viscosity melt might not completely fill the molds. The total amount of Am lost could also be reduced by further limiting time at temperature and casting under more positive pressure.

2.6 X501 Experiment Irradiation

The X501 fuel slugs were fabricated into two EBR-II MkIV configuration fuel pins. The two MA-bearing pins were inserted into a standard EBR-II subassembly with the remainder of the fuel element locations filled with U-10Zr driver fuel. The X501 subassembly was inserted into EBR-II in the central core region, as shown in Figure 6, beginning in February 1993, and withdrawn just prior to EBR-II shutdown in August 1994. Total irradiation time was 339 EFPDs. Burnup, calculated on the basis of REBUS/RCT/ORIGEN calculations,⁹ was 7.6% HM with transmutation of 9.1% of ²⁴¹Am. Peak linear heat generation rate was estimated to be 45 kW/m (13.7 kW/ft), and peak fuel centerline and cladding inner surface temperatures were approximately 700°C and 540°C, respectively. The chemical analysis and physical attributes of the two X501 fuel elements are given in Table 2.

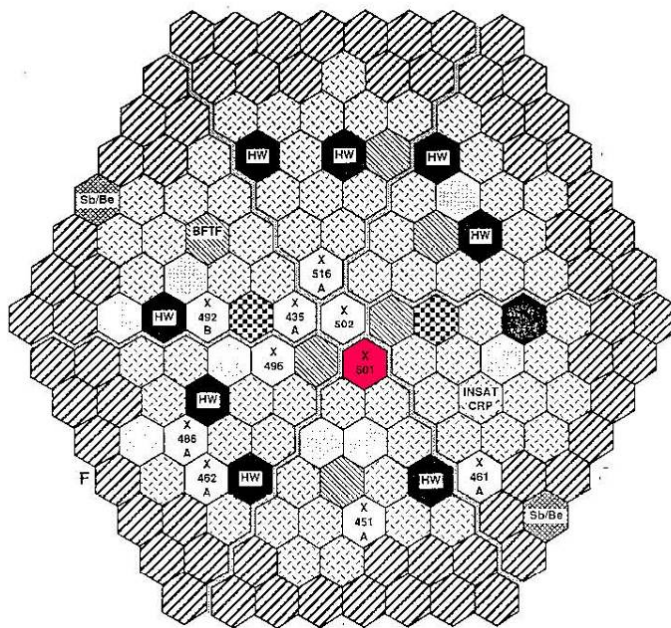


Figure 6. X501 experiment location in EBR-II.

Table 2. Attributes of X501 minor actinide-bearing fuel elements.

Composition (average analyzed wt%)	U-20.2Pu-9.1Zr-1.2Am-1.3Np
Major impurities (average wt%)	Si:0.26, Al:0.089, Ca:0.067, Cr:0.0025, Mg:0.009, Fe:0.001, Mn:0.001
U-235 enrichment (nominal)	60%
Fuel mass	77.5 g
Fuel length	34.3 cm (13.5 in.)
Element length (nominal)	74.9 cm (29.5 in.)
Cladding type	HT-9 steel
Cladding OD	5.84 mm (0.230 in.)
Cladding wall	0.457 mm (0.018 in.)
Slug diameter	4.27 mm (0.168 in.)
Plenum volume	7.1 cm ³
Plenum gas	75He-Ar
Smeared density	75%
Fuel slug density, % theoretical	99.5%

2.7 X501 Post-irradiation Examination

A partial PIE was completed on X501, including gamma scanning, optical microscopy, microprobe analysis, and metallography. The PIE indicated that the minor additions of Am and Np to the U-Pu-Zr matrix did not effect the irradiation behavior of the fuel.

Gamma scans (example shown in Figure 7) showed normal metallic fuel fission product behavior, with ¹³⁷Cs alloying with the bond sodium and migrating to the region near the top of the fuel slug.

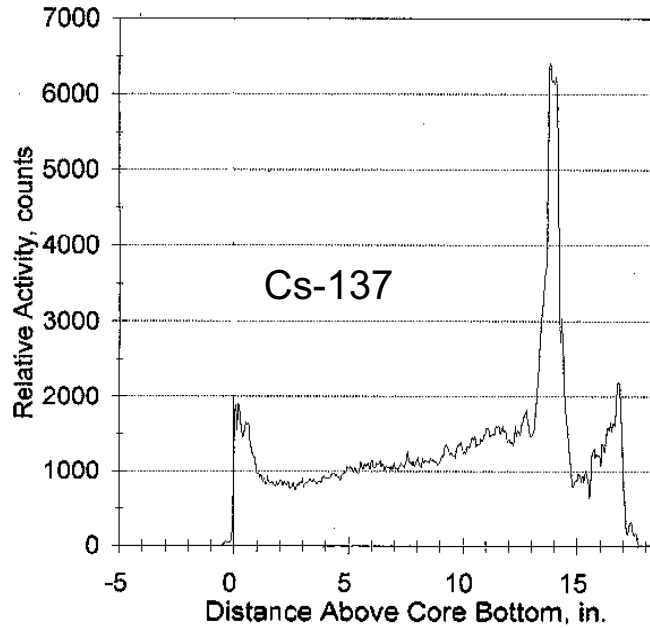


Figure 7. Example Cs-137 gamma scan of an X501 pin.

A microscopic examination of the inside cladding surface was made to determine if the inclusion of the MAs to U-Pu-Zr fuel has an effect on FCCI (Fuel-Cladding Chemical Interaction). The HT-9 cladding used for the X501 experiment is also the reference cladding for U.S. transmuter fuel. Optical microscopy (Figure 8) showed no evidence of reaction layer formation on the inner cladding wall or the outer surface of the fuel slug. A gap is visible between the fuel and the cladding wall at all locations. These preliminary results indicate that, under typical metal fuel operating conditions, FCCI of HT-9 is not strongly affected by small amounts of americium or neptunium.

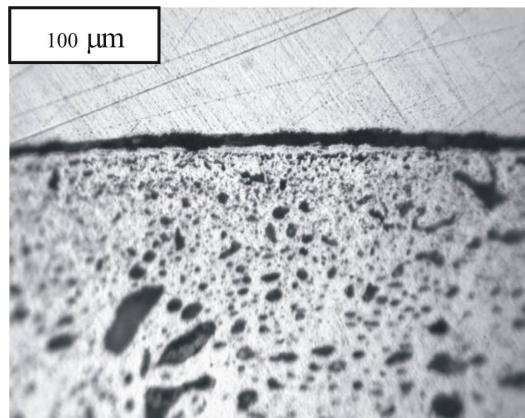


Figure 8. Optical micrograph of fuel/cladding interface.

Shown in Figure 9(a) is a post-irradiation optical micrograph of a cross-section near the center of element G582. The fuel shows a microstructure typical of U-20Pu-10Zr, where constituent radial redistribution has resulted in the formation of three microstructural zones within the fuel. Figure 9(b) is a comparison of the WDS traces of neptunium, americium, zirconium, plutonium, and uranium across the section shown in Figure 9(a). The outer zone, near the cladding, is enriched in zirconium, the intermediate zone is zirconium-depleted, and the central zone is enriched in zirconium and depleted in uranium. Plutonium content remains relatively uniform. Americium appears in the WDS traces as features with high elemental concentrations, generally depleted in U, Pu, and Zr (the other major elemental constituents). The morphology of the americium-rich phases cannot be determined from existing micrographs, and other elemental constituents, such as fission product and impurity elements, were not analyzed during the examination. Comparison of the pre-irradiation and post-irradiation WDS line scans suggests that the americium-rich features formed during irradiation. Americium is present only in the uranium-depleted central and outer zones, indicating that americium migration has occurred along with the migration of uranium and zirconium. Local radial redistribution of americium to the cladding inner wall does not occur; however, these results do not rule out the possibility of condensation of americium in the plenum region above the fuel column.

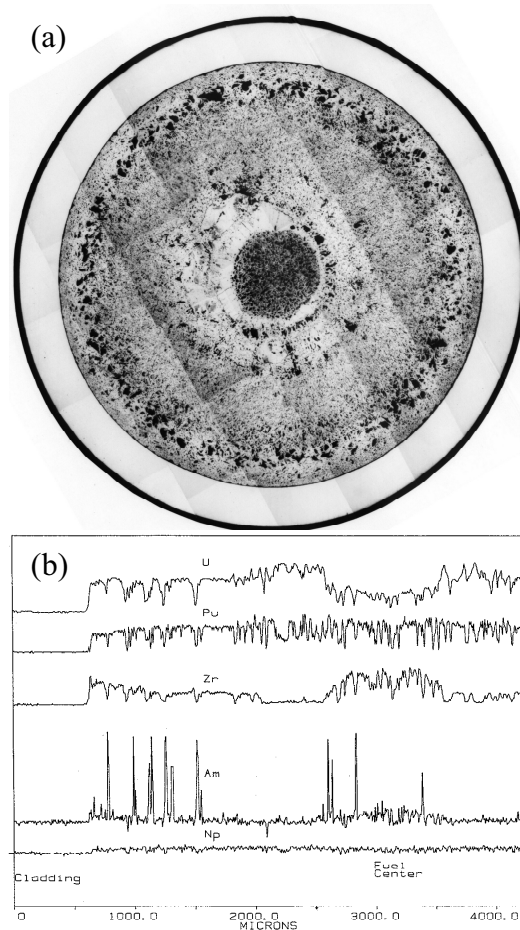


Figure 9. (a) Post-irradiation optical image of MA-bearing fuel; (b) WDS line scans showing distribution of actinides and Zr.

Plenum gas sampling results were combined with ORIGEN calculations to estimate the fission gas and helium release rates from the fuel. Results are shown in Table 3. Helium generation is principally due to a sequence of neutron capture by ^{241}Am , and subsequent decay of the ^{242}Cm product to ^{238}Pu by alpha particle emission. The amount of He introduced as plenum fill gas was estimated based on pressure ratios between fill gas and the quantity of radioactive Xe tag gas measured by counting Xe activity. Based on these estimates, it appears that approximately 90% of the helium gas produced was released to the plenum. Fission gas release was 79%, typical of U-Pu-Zr fuel at this burnup.

Table 3. X501 gas production and release.

BOL ^{241}Am content	0.972 g
EOL ^{241}Am content	0.884 g
^{241}Am transmutation	0.088 g (9.1%)
Measured He release	3.1 cm ³
Calculated He inventory, 1 year decay	3.4 cm ³
He release	90%
FG release	79%

The generation of helium gas during transmutation of ^{241}Am is a significant issue that must be considered in the design of transmuter fuel. In fuels with high americium content, helium generation is principally due to neutron capture by ^{241}Am and subsequent alpha decay of ^{242}Cm to ^{238}Pu . There are three known experiments involving transmutation of ^{241}Am . Helium release results from two, the EFTTRA-T4 test and the SUPERFACT-1 experiment, have been previously published. Some data on helium generation are available for each experiment, and results are presented in Table 4, along with ORIGEN calculations for the U.S. Na-cooled point design (Hill 2000¹⁰) and X501 data. The quality and completeness of data vary for each experiment; therefore, the results of this analysis contain a good deal of uncertainty and do not provide a good basis for extrapolation. A rule-of-thumb for estimating helium production from americium for the U.S. transmuter design, based on the results in Table 4 and calculations of compositions ranging from 6-40 wt% ^{241}Am , is 50 ml He per gram of transmuted americium. The wide range of possible fuel compositions leads to a wide range in the potential for helium production. Helium production is likely to be the most important fuel design consideration for transmutation scenarios with high MA content.

Table 4. Data and calculations for He production in ^{241}Am -bearing fuels.

Experiment	Specific He generation (ml per g gram ^{241}Am transmuted)
X501	38.6-44.8
SUPERFACT-1	33.3-63.4
EFTTRA-T4	44.8-59.9
Na point design¹⁰	58.1

3. CONCLUSION

The U.S. fast reactor fuel program demonstrated the use of americium-bearing fuel in the early 1990s. Three full-length fuel pins containing MA additions were successfully cast with no unusual macrosegregation of major constituents observed. The Zr-rich phase displayed an unconventional morphology in the bottom section of the castings, appearing as a dense collection of small particles instead of the usual contiguous globular shape. This is probably the result of significant levels of impurities present. Approximately 40% of the initial Am charge was lost during casting, due to volatile impurities (Ca and Mg) in the Am-Pu feedstock and through evaporation. Limited PIE results from the X501 experiment indicate that the addition of 1.2 wt % of americium did not alter the behavior of metallic U-Pu-Zr fuel.

4. ACKNOWLEDGMENTS

The authors wish to acknowledge C.L. Trybus for preparing the X501 experiment for irradiation. The work presented in this report represents the efforts of many researchers and technicians, as well as the efforts of EBR-II operations personnel. Their efforts should be recognized.

Work was supported by the U.S. Department of Energy, Office of Nuclear Energy, Science, and Technology, under DOE-NE Idaho Operations Office Contract DE-AC07-05ID14517.

5. REFERENCES

1. Chang, Y. I., 1989, Nuclear Technology 88 (1989) 129.
2. Croff, A. G., C. W. Forsberg, and S. B. Ludwig, 1990, Proceedings from ANS Meeting, November 1990, Washington DC, CONP-901101, p. 144.
3. Chang, Y. I., and C. E. Till, 1989, Proceedings from Annual WATtec Conference and Exhibition, February 1989, Knoxville, TN, CONF-890218-13, p. 129.
4. Trybus, C. L., J. E. Sanecki, and S. P. Henslee, 1993, "Casting of Metallic Fuel Containing Minor Actinide Additions," *Journal of Nuclear Materials*, 204, pp. 50-55.
5. Erway, N. D., and O. C. Simpson, 1953, *Journal of Chemical Physics*, 18 (1950) 953.
6. Alock, C. B., V. P. Itkin, and M.K. Horrigan, 1984, *Canadian Metallurgical Quarterly* 23(3) (1984), 309.
7. Cordfunke, E. H. P., and R. J. M. Konings (eds.), 1990, "Thermochemical Data for Reactor Materials and Fission Products," North-Holland, Amsterdam.
8. Zegler, S. T., 1962, "The Uranium-Rich End of the Uranium-Zirconium System," ANL-6055, February 1962.
9. McKnight, R., 2001, personal communication, Argonne National Laboratory.
10. Hill, R.N., 2000, "Physics Studies for a Sodium-Cooled ATW Design," Proceedings from IAEA Technical Committee Meeting on Core Physics and Engineering Aspects of Emerging Nuclear Energy Systems for Energy Generation and Transmutation, Argonne National Laboratory, U.S.A., Nov. 28 - Dec. 1, 2000.