

§27. Evaluation for Superconducting Property of Extruded MgB_2/Al Composite Material Wires Fabricated via 3 Dimensional Penetration Casting Method

Matsuda, K., Nishimura, K., Kawabata, T., Ikeno, S. (Univ. Toyama), Hishinuma, Y.

B, Mg and Al are low activation elements and these are possible to apply for a low activation superconducting magnet in the new advanced fusion reactor. MgB_2 superconductor is also one of those materials and its wires have been fabricated by the PIT method. Our research group is developing hybrid aluminum based composite materials reinforced by functional ceramic powders using by our special technique so-called 3 dimensional penetration casting (3DPC) method. Fabrication of a billet of MgB_2/Al composite materials by 3DPC method, extrusion of its billet to $10\text{mm}\phi$ rods, $3\text{mm}\phi$ and $1\text{mm}\phi$ wires have been succeeded. Their onset T_c have been confirmed about 39 K [1]. Our subject in this research is as follows:

1. Refinement of MgB_2 particles to improve extrudability of MgB_2/Al composite material.
2. Indium (In) addition to aluminum matrix to improve J_c .
3. Application of Mg for the matrix of the composite.

MgB_2 powders were provided by Kojundo Chemical Laboratory Co., Ltd., at purity higher than 99% and with size smaller than $40\ \mu\text{m}$. Received powders were gently ground in an agate mortar to break any aggregation, refined and filtered smaller than $25\ \mu\text{m}$. The procedure for forming a composite material billet by 3DPC method was described in our recent report in detail [1]. 99.9% In-ribbon was added in to the molten Al matrix before 3DPC method. The volume fraction of MgB_2 powders was about 40 - 60 %. Also this billet was extruded by a hot-extruding machine of 50 t or 400 t to a rod $10\text{mm}\phi$ in diameter, and to $3\text{mm}\phi$ and $1\text{mm}\phi$ wires. Superconducting, thermal properties and electrical resistivity were measured by means of the

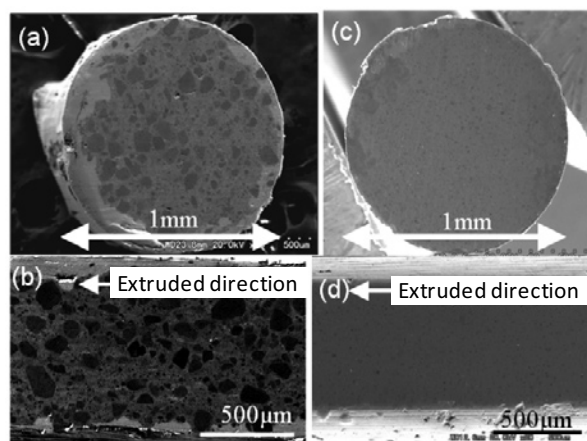


Fig. 1 SEM images of extruded $1\text{mm}\phi$ MgB_2/Al wires. (a) cross section and (b) longitudinal section obtained for normal particles. (c) cross section and (d) longitudinal section obtained for refined particles.

Physical Property Measurement system (PPMS) and SQUID (Quantum Design, Co., Ltd.).

Fig. 1 shows SEM images of extruded $1\text{mm}\phi$ MgB_2/Al wires. Comparing to normal particles of MgB_2 ((a), (b)) and refined MgB_2 ((c), (d)), no aggregation and cracks have been observed. Fig. 2 shows relation between J_c and applied magnetic field for In-free MgB_2/Al and In added MgB_2/Al composite materials. J_c was calculated using Bean's equation. J_c of In-added MgB_2/Al composite materials showed higher J_c at higher magnetic field than that of In-free MgB_2/Al composite material. This is suggested that In-addition to Al-matrix is effective for higher J_c of MgB_2/Al composite material. Fig. 3 shows the relation between temperature and for Mg-based MgB_2 composite materials. Mg- or Mg alloy-based MgB_2 composite materials fabricated our 3DPC method have been also showed drastic decreasing of T_c around 37-39K as well as MgB_2/Al composite materials, successfully.

[1] Matsuda K., et al., Mater.Trans. **47**, (2006) 1214.

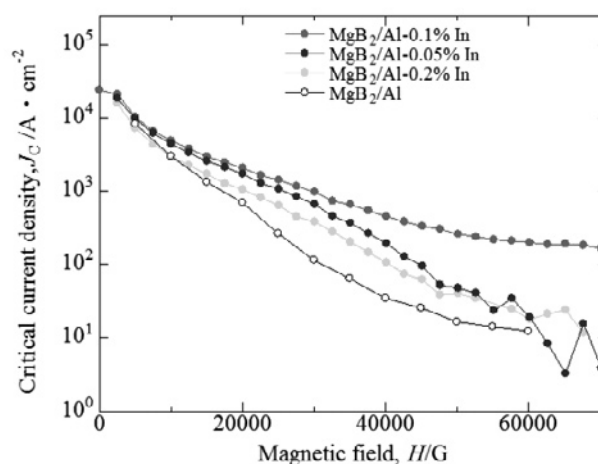


Fig. 2 Relation between J_c and applied magnetic field for In-free MgB_2/Al and In added MgB_2/Al composite materials.

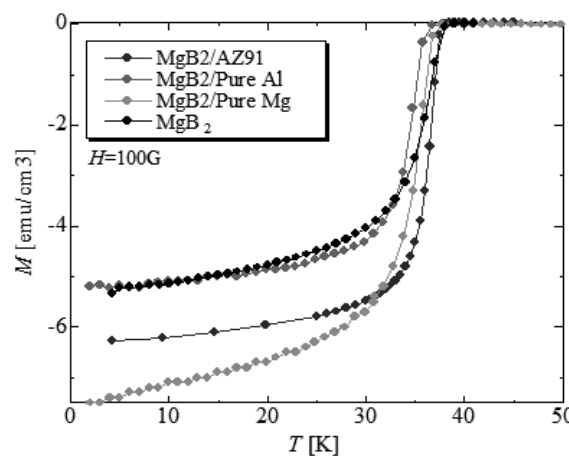


Fig. 3 Relation between temperature and for Mg-based MgB_2 composite materials.