



Biobased poly(ethylene furanoate-

DOI:

[10.1039/c6ra15994j](https://doi.org/10.1039/c6ra15994j)

Document Version

Accepted author manuscript

[Link to publication record in Manchester Research Explorer](#)

Citation for published version (APA):

Terzopoulou, Z., Tsanaktsis, V., Bikiaris, D. N., Exarhopoulos, S., Papageorgiou, D. G., & Papageorgiou, G. Z. (2016). Biobased poly(ethylene furanoate-: Co -ethylene succinate) copolyesters: Solid state structure, melting point depression and biodegradability. *RSC Advances*, 6(87), 84003-84015. <https://doi.org/10.1039/c6ra15994j>

Published in:

RSC Advances

Citing this paper

Please note that where the full-text provided on Manchester Research Explorer is the Author Accepted Manuscript or Proof version this may differ from the final Published version. If citing, it is advised that you check and use the publisher's definitive version.

General rights

Copyright and moral rights for the publications made accessible in the Research Explorer are retained by the authors and/or other copyright owners and it is a condition of accessing publications that users recognise and abide by the legal requirements associated with these rights.

Takedown policy

If you believe that this document breaches copyright please refer to the University of Manchester's Takedown Procedures [<http://man.ac.uk/04Y6Bo>] or contact uml.scholarlycommunications@manchester.ac.uk providing relevant details, so we can investigate your claim.



**Biobased poly(ethylene furanoate-co-ethylene succinate) copolyesters:
solid state structure, melting point depression and biodegradability**

Zoe Terzopoulou¹, Vasilios Tsanaktis¹, Dimitrios N. Bikiaris^{1*}, Stylianos Exarhopoulos^{2,3}, Dimitrios G. Papageorgiou⁴, George Z. Papageorgiou^{2*}

¹Laboratory of Polymer Chemistry and Technology, Department of Chemistry, Aristotle University of Thessaloniki, GR-541 24, Thessaloniki, Macedonia, Greece

²Chemistry Department, University of Ioannina, P.O. Box 1186, 45110 Ioannina, Greece

³Department of Food Technology, Technological Educational Institute of Thessaloniki, PO Box 141, GR-57400 Thessaloniki, Greece

⁴School of Materials and National Graphene Institute, University of Manchester, Oxford Road, Manchester M13 9PL, United Kingdom

Abstract

Poly(ethylene furanoate) (PEF) is a fully bio-based polyester with unique gas barrier properties, considered an alternative to poly(ethylene terephthalate) (PET) in food packaging applications. However, it is not biodegradable. For this reason copolymerization with the aliphatic succinic acid monomer, was followed. The respective poly(ethylene furanoate-co-ethylene succinate) (PEFSu) copolymers were prepared via melt polycondensation from 2,5-dimethylfuran-dicarboxylate, succinic acid and ethylene glycol at different ratios. ¹HNMR spectroscopy showed the copolymers are random. The crystallization and melting of the copolymers were thoroughly evaluated. Isodimorphic cocrystallization was concluded from both the

WAXD patterns and the minimum in the plots of melting temperature versus composition. The pseudo-eutectic melting point corresponded to an ethylene succinate content of about 30 mol%. The enzymatic hydrolysis tests using of *Rhizopus delemar* and *Pseudomonas Cepacia* lipase, revealed that the copolymers with up to 50 mol% ES units show measurable weight loss rates. For higher ES content, the copolymers showed fast hydrolysis.

Keywords: Poly(ethylene furanoate); poly(ethylene succinate); copolyesters; thermal properties; crystallization; enzymatic hydrolysis.

***Corresponding authors.** E-mail: dbic@chem.auth.gr (Dimitrios N. Bikiaris), gzpap@cc.uoi.gr (George Z. Papageorgiou)

1. Introduction

The global ecological problems which include the limited fossil fuels and the disadvantages that come with the widespread use of them (limited recyclability, relatively high cost and environmental impact) have led governments, academia and (in a lesser extent) industry to look for eco-friendly, alternative solutions. Bioplastics represent one of the most ambitious projects, since a lot of products have been grown over the last years and are focused on the use of renewable resources. Furanoate-based polyesters based on 2,5-furandicarboxylic acid are a viable candidate for the replacement of their naphthalate and terephthalate counterparts, since they originate from monomers derived straight from renewable resources like furfural and hydroxymethylfurfural. For this reason, several works have been dedicated on the detailed study of their production and properties for the use in a wide variety of applications ¹⁻²². Of special importance are the unique barrier properties of PEF and furanoates in general which enable uses as green food packaging materials ^{11,12,19}.

Poly(ethylene succinate) (PESu) is a semi-crystalline aliphatic polyester, which has been attracting attention since it exhibits excellent biodegradability due to its hydrolysable ester bonds, stability and favorable mechanical properties ²³⁻²⁶. It can be synthesized by either ring-opening polymerization of succinic anhydride or by polycondensation of succinic acid and ethylene glycol ²⁷. PESu has been successfully blended with a number of polymers in an attempt to improve its physical properties and increase its biodegradation rates, such as poly(ϵ -caprolactone) ²⁸, poly(butylene succinate) ^{29, 30}, poly(octamethylene succinate) ³¹, poly(decamethylene succinate) ^{32, 33}, poly(ethylene oxide) ³⁴, poly(ethylene terephthalate) ³⁵, poly(l-lactide) ²⁶, poly(diethylene glycol succinate) ³⁶, poly(ethylene adipate) ³⁷ and others. The majority of those materials exhibit good compatibility in blends and improved

biodegradation rates. That is the main reason why the specific polyester was carefully chosen in our attempts to prepare copolymers with PEF. In a similar work by Dubois and coworkers ³⁸ involving a member of the furanoates family that was copolymerized, the authors successfully prepared poly(butylene succinate-co-butylene furandicarboxylate) (PBSF) copolyesters with high thermal stability and adequate mechanical properties, displaying a potential for replacement of commodity thermoplastics or elastomers.

Basic research on the relationship between structure, morphology, and properties as well efforts to understand the biodegradation mechanism will enable us to design and synthesize a great variety of biodegradable polymers to fulfill the demands in practical applications ³⁹. Biodegradation rate is undoubtedly one of the most important properties of aliphatic polyesters, since the widespread use of those materials in packaging applications (amongst others) has already caused various environmental problems. The enzymatic degradation of polyesters is sensitive to their chemical structure, the hydrophilic/hydrophobic balance within the main chain, molecular weight, the specific solid-state morphology, crystallinity, and so forth. As for crystalline structure and morphology the spherulite size and the lamellar structure can greatly influence the rate of biodegradation ³⁹.

Higher degradation rates can be achieved by copolymers compared to the homopolymers, and this is basically attributed to the limited crystallinity ⁴⁰. In most of the copolymers where both components are crystallizable, the degree of crystallinity decreases as the minor component content increases, due to incompatibility in crystal lattices of the two components ⁴¹⁻⁴³.

On the contrary, if the two crystallizable units are compatible in each crystal lattice, cocrystallization can take place. Two cases of cocrystallization behavior have been

reported ⁴¹. For components with similar chemical structure isomorphism may occur meaning that only one crystalline phase containing both comonomer units is observed at all compositions ⁴⁴⁻⁴⁶. In isodimorphism two crystalline phases and pseudo-eutectic behavior are observed. Isodimorphism has been observed in most cases of random copolymers ⁴⁷⁻⁴⁹.

In terms of the thermodynamic parameters and the cocrystallization of copolymers, various models have been proposed, among them those of Flory ^{50, 51}, Sanchez-Eby ⁵², Baur ⁵³ as well as that of Wendling and Suter ^{54, 55}. Several of them have been applied to the experimental results of this work.

Based on the above mentioned facts, a series of copolymers based on poly(ethylene furanoate) (PEF) and poly(ethylene succinate) (PESu) have been prepared by the melt polycondensation method. The studies on the crystalline structure and crystallization kinetics of the copolymers are very important on a practical viewpoint since they determine the performance and biodegradability of end products. For this reason a variety of techniques and measurement types were applied on the produced materials, in order to export solid conclusions and evaluate the performance of those materials on packaging applications.

2. Experimental

2.1. Materials

2,5-furan dicarboxylic acid (2,5-FDCA, purum 97 %), succinic acid (purum 99 %), ethylene glycol and tetrabutyl titanate (TBT) catalyst of analytical grade were purchased from Aldrich Co. 2,5-dimethylfuran-dicarboxylate (DMFD) was synthesized from 2,5-FDCA and methanol as described in our previous work ⁵⁶. All other materials and solvents used were of analytical grade.

2.2. Copolymer synthesis

Neat PEF and PESu polyesters were prepared by the two-stage melt polycondensation method (esterification and polycondensation) in a glass batch reactor as described in our previous works ⁵⁷. The copolymers under study have been synthesized with the same procedure using different DMFD/succinic acid feeding ratios (Table 1) and ethylene glycol from the beginning of esterification procedure. After the polycondensation reaction was completed, the polyesters were easily removed, milled and washed with methanol.

2.3. Polyester characterization

2.3.1. Intrinsic viscosity measurement.

Intrinsic viscosity $[\eta]$ measurements were performed using an Ubbelohde viscometer at 30 °C in a mixture of phenol/1,1,2,2-tetrachloroethane (60/40, w/w).

2.3.2. Wide angle X-Ray diffraction patterns (WAXD).

X-ray diffraction measurements of the samples were performed using a MiniFlex II XRD system from Rigaku Co, with CuK_α radiation ($\lambda=0.154$ nm) in the angle (2θ) range from 5 to 65 degrees.

2.3.3. Differential Scanning Calorimetry (DSC).

A TA Instruments TMDSC (TA Q2000) combined with a cooling accessory was used for thermal analysis. The instrument was calibrated with indium for the heat flow and temperature, while the heat capacity was evaluated using a sapphire standard. Nitrogen gas flow of 50 ml/min was purged into the DSC cell. The sample mass was kept around 5 mg. The Al sample and reference pans were of identical mass with an error of ± 0.01 mg. The TMDSC scans were performed at a heating rate of $5^\circ\text{C}/\text{min}$, with temperature modulation amplitude of 1°C and period of 60 s. The samples were initially cooled to 0°C and then heated at a rate of $20^\circ\text{C}/\text{min}$ at temperatures 40°C higher than the melting temperature. In order to obtain amorphous materials, the samples were held there for 5 min, in order to erase any thermal history, before cooling in the DSC with the highest achievable rate.

Isothermal crystallization experiments of the polymers at various temperatures below the melting point were performed after self-nucleation of the polyester sample. Self-nucleation measurements were performed in analogy to the procedure described by Fillon et al.⁵⁸. The protocol used is a modification of that described by Müller et al.⁵⁹ and can be summarized as follows: a) melting of the sample at 40°C above the observed melting point for 5 min to erase any previous thermal history; b) cooling at 20°Cmin^{-1} to room temperature and crystallization; c) cold-crystallization to create a “standard” thermal history and partial melting by heating at 5°C min^{-1} up to a “self-nucleation temperature”, T_s which was 224°C for PEF and properly decreased for the

rest polymers; d) thermal conditioning at T_s for 1 min. Depending on T_s , the crystalline polyester will be completely molten, only self-nucleated or self-nucleated and annealed. If T_s is sufficiently high, no self-nuclei or crystal fragments can remain (T_s Domain I - complete melting domain). At intermediate T_s values, the sample is almost completely molten, but some small crystal fragments or crystal memory effects remain, which can act as self-nuclei during a subsequent cooling from T_s , (T_s Domain II-self - nucleation domain). Finally, if T_s is too low, the crystals will only be partially molten, and the remaining crystals will undergo annealing during the 5 min at T_s , while the molten crystals will be self-nucleated during the later cooling, (T_s Domain III - self-nucleation and annealing domain); e) cooling scan from T_s at $20\text{ }^\circ\text{Cmin}^{-1}$ to the crystallization temperature (T_c), where the effects of the previous thermal treatment will be reflected on isothermal crystallization; f) heating scan at $20\text{ }^\circ\text{Cmin}^{-1}$ for standard DSC scans, or heating at an underlying rate $5^\circ\text{C}/\text{min}$ in case of TMDSC studies, to 40°C above the melting point, where the effects of the thermal history will be apparent on the melting signals. Experiments were performed to check that the sample did not crystallize during the cooling to T_c and that a full crystallization exothermic peak was recorded at T_c . In case that some other method was applied, this will be discussed in the corresponding part.

2.3.4. Enzymatic hydrolysis.

Polyesters in the form of films with 5×5 cm in size and approximately 2 mm thickness, prepared by melt-pressing in a hydraulic press at 30°C higher than the melting point of each copolymer, were placed in petries containing phosphate buffer solution (pH 7.2) with 0.1 mg/mL *Rhizopus delemar* lipase and 0.01 mg/mL of *Pseudomonas Cepacia* lipase. The petries were then incubated at $50 \pm 1\text{ }^\circ\text{C}$ in an oven

for several days while the media were replaced every 5 days. After a specific period of incubation (every 5 days), the films were removed from the petri, washed with distilled water, **dried under vacuum** and weighted until constant weight. The degree of enzymatic hydrolysis was estimated from the mass loss of the samples.

2.3.5. Scanning Electron microscopy (SEM).

The morphology of the prepared films before and after enzymatic hydrolysis was examined in a scanning electron microscopy system (SEM) type Jeol (JMS-840). The films were covered with a carbon coating. Operating conditions included accelerating voltage 20KV, probe current 45 nA and counting time 60 seconds.


2.3.6. Polarizing Light Optical Microscopy (PLOM).

A polarizing optical microscope (Nikon, Optiphot-2) equipped with a Linkam THMS 600 heating stage, a Linkam TP 91 control unit and also a Jenoptic ProgRes C10plus camera were used for PLOM observations.

3. Results and Discussion

3.1 Synthesis and Molecular Characterization of the PEFS Copolymers

The PEF and PESu homopolymers along with the PEFSu copolymers were synthesized following the two-step melt polycondensation method. The feeding ratios between PEF/PESu monomers can be seen in [Table 1](#) with the measured intrinsic viscosity values. All synthesized copolymers exhibit very similar molecular weights since their IVs differ very slightly between each other. The chemical structures of PEF, PESu and the copolymers are shown in [Scheme 1](#).

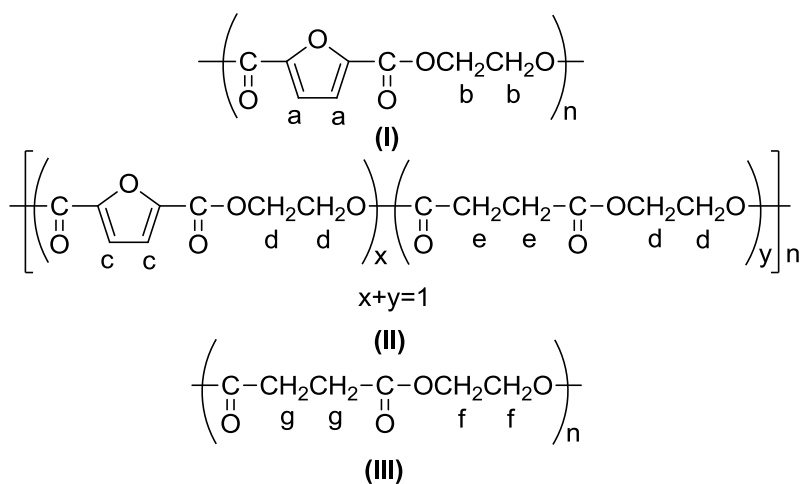

Scheme 1. Chemical structures of PEF (I), the PEFSu copolymers (II) and PESu (III).

The ^1H NMR spectra of the copolymers were used to elucidate their structure (Figure 1). The protons of the furanoate ring are the most deprotected in the macromolecules due to the carbonyl groups and the π electron system of the ring and they appear at about 7.45 ppm, (the a and c protons of PEF and PEFSu 50/50, respectively). On the other hand, the protons of the succinic moiety appear at 3.02 ppm (e and g protons), i.e. at lower values compared to the protons of the ethylene part which appear at 4.7 ppm giving the characteristic pattern which was used to calculate the real sequence of each comonomer in the macromolecular chain (d and f protons).

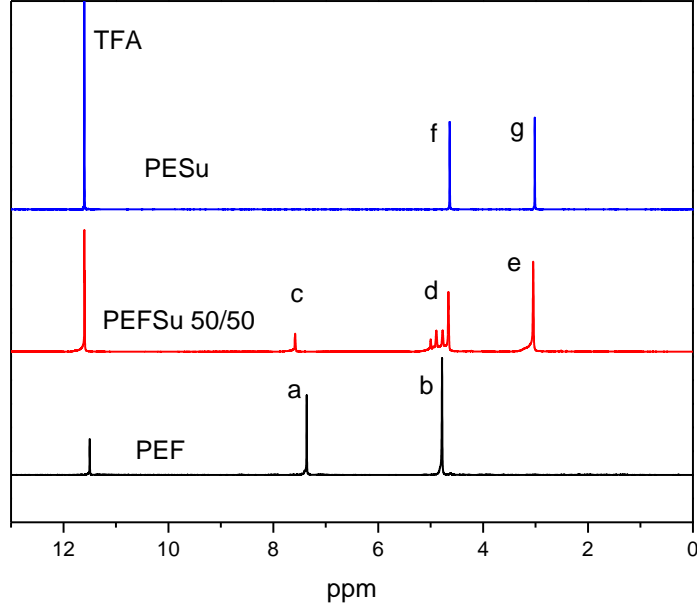


Figure 1. ^1H NMR spectra of PEF, PESu and the PEFSu 50/50 copolymer.

The degree of randomness (R) in the PEFSu copolyesters was calculated using the resonance peaks of the ethylene units' aliphatic protons (a). The degree of randomness is defined as ⁶⁰:

$$R = P_{FS} + P_{SF} \quad (1)$$

$$P_{FS} = \frac{\frac{(f_{FS} + f_{SF})}{2}}{\frac{(f_{FS} + f_{SF})}{2} + f_{FF}} = \frac{1}{L_{nF}} \quad (2)$$

$$P_{SF} = \frac{\frac{(f_{FS} + f_{SF})}{2}}{\frac{(f_{FS} + f_{SF})}{2} + f_{SS}} = \frac{1}{L_{nS}} \quad (3)$$

where P_{FS} and P_{SF} are the probability of finding a Furanoate (F) unit next to a Succinate (S) unit and the probability of finding a Succinate unit next to a Furanoate unit, respectively. Also f_{FF} , f_{FS} , f_{SF} , f_{SS} represent the dyads fraction, calculated from the integral intensities of the resonance signals FF, FS, SF and SS, correspondingly ⁶¹.

L_{nS} and L_{nF} stand for the number average sequence length, the so-called block length, of the S and F units, respectively. For random copolymers the degree of randomness R should be equal to 1, while for alternate copolymers equal to 2 and for block copolymers close to zero. Table 1 shows the calculated values for the degree of randomness. Practically these were equal to 1, indicating that the PEFS copolymers in this work were essentially random.

The number average sequence length or block length for Furanoate (L_{nF}) and Succinate (L_{nS}) units was calculated using equations 2 and 3 respectively, according to Yamadera and Murano⁶². Table 1 summarizes the corresponding values and it can be seen that by increasing the EF ratio in copolymers the corresponding block length is also increased and the same appears for ES blocks when the ES ratio was higher.

Table 1. Intrinsic viscosity values, feeding ratios, calculated compositions, degree of randomness (R) and average block length for succinate (L_{nS}) and furanoate (L_{nF}) blocks of the prepared copolymers.

| Sample | IV (dL/g) | PEFSu feed ratios | PEFSu ¹ HNMR | R | LnS | LnF |
|--------|--------------|-------------------------|----------------------------|------|------|------|
| 1 | 0.38 | 5/95 | 2/98 | 0.99 | 50 | 1.02 |
| 2 | 0.39 | 10/90 | 11/89 | 1.00 | 9.09 | 1.12 |
| 3 | 0.36 | 15/85 | 17/83 | 1.02 | 5.88 | 1.20 |
| 4 | 0.41 | 30/70 | 35/65 | 0.99 | 2.85 | 1.53 |
| 5 | 0.38 | 40/60 | 37/63 | 1.01 | 2.70 | 1.58 |
| 6 | 0.34 | 50/50 | 49/51 | 1.02 | 2.04 | 1.96 |
| 7 | 0.36 | 60/40 | 61/39 | 0.99 | 1.63 | 2.56 |

| | | | | | | |
|----|------|-------|-------|------|------|------|
| 8 | 0.42 | 80/20 | 81/19 | 0.99 | 1.23 | 5.26 |
| 9 | 0.40 | 90/10 | 87/13 | 1.00 | 1.14 | 7.69 |
| 10 | 0.36 | 95/5 | 92/8 | 1.01 | 1.08 | 12.5 |

Figures 2a and b show the DSC traces for the as received samples of ES rich copolymers and EF rich copolymers, respectively. Most of the copolymers crystallized after the solvent treatment. The copolymers with intermediate composition showed broad or multiple melting peaks on heating scans. However, the traces for PEFSu 35/65 and 37/63 samples were characterized by complete absence of melting, indicating their amorphous nature. The phase behavior is highly dependent on the comonomer content and the intense melting peaks decrease with increasing comonomer unit content as was expected. The samples with high EF content (>81 mol%) display peaks which represent the melting of PEF crystals from 185-220°C, while the peaks of respective ones with high ES content (>83 mol%) reflect the melting of the PESu crystals at 90-107°C.

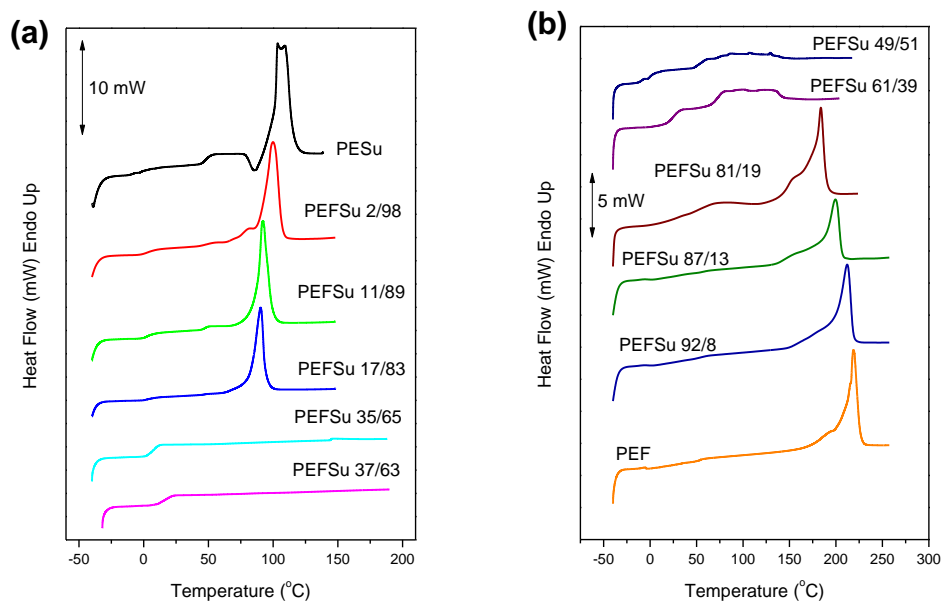


Figure 2. DSC traces of semicrystalline a) PESu and ES rich copolymers and b) PEF and EF rich copolymers.

Figure 3 shows the DSC traces for the quenched copolymer samples. In these curves a single glass transition can be seen for the copolymers. The presence of a single glass transition is another indication of random copolymers, which is in agreement with the results from $^1\text{H NMR}$. However, a single T_g can also be caused by miscible polymers and can be an indication of the state of miscibility of the blend ratios. The PESu sample and the 2/98 copolymer displayed cold crystallization during the heating scan at 20 °C/min. The rest of the samples could not crystallize upon heating at that rate, because of their relatively slow crystallization rates.

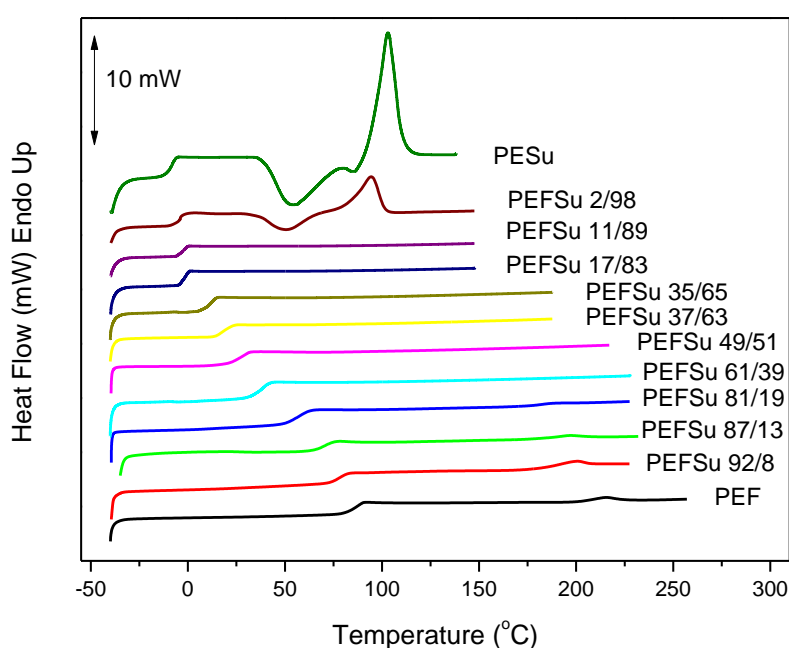


Figure 3. DSC traces of quenched PEF, PESu and PEFSu copolymers.

Melting temperature (T_m) and glass transition temperature (T_g) vs composition plots were constructed (Figure 4). A minimum was observed in the plot of the melting temperature vs composition showing that the copolymers followed a pseudo-eutectic behavior at a EF/ES molar ratio of 35/65. On the one side of the pseudo-eutectic point the crystalline lattice is the one of EF, while on the other side it is the one of ES. Therefore, the crystalline system under study is isodimorphic, implying cocrystallization as will be also discussed in the WAXD study section.

Glass transition temperatures (T_g) of the quenched samples decreased monotonically with ES content between the two values for the neat polymers, which were found to be 87°C for PEF and -8°C for PESu. T_g is usually a monotonic function of composition in amorphous random copolymers. The most common relationship for the prediction T_g as a function of comonomer content is the equation of Fox⁶³:

$$\frac{1}{T_g} = \frac{w_1}{T_{g1}} + \frac{w_2}{T_{g2}} \quad (4)$$

where w_1 and w_2 are the weight fractions of the comonomers and T_{g1} and T_{g2} the glass transition temperatures of the respective homopolymers. As can be seen in Figure 4, the equation of Fox **did not fit adequately the experimental values** of the glass transition temperatures of the copolymers.

The Couchman-Karasz equation was also tested for the case of the T_g variation for the PEFSu copolymers. The Couchman-Karasz (C-K) equation is given by⁶⁴:

$$\ln T_g = \frac{w_I \Delta C_{pI} \ln T_{gI} + w_{II} \Delta C_{pII} \ln T_{gII}}{w_I \Delta C_{pI} + w_{II} \Delta C_{pII}} \quad (5)$$

where w_I and w_{II} are the weight fractions of the comonomers and T_{gI} and T_{gII} the glass transition temperatures of the respective homopolymers. ΔC_{pI} and ΔC_{pII} are the values for the increase in heat capacity associated with the glass transition of the two

homopolymers, respectively. The ΔC_p values were experimentally measured at the glass transition temperatures of the polymers, and they were found 0.46 J/g °C and 0.67 J/g °C for neat PEF (ΔC_{pI}) and neat PESu (ΔC_{pII}), respectively. As it can be seen in [Figure 4](#), the C-K prediction did not fit very well the experimental values.

Finally, the Gordon-Taylor equation was elaborated ⁶⁵:


$$T_g = \frac{w_1 T_{g1} + k w_2 T_2}{w_1 + k w_2} \quad (6)$$

where T_{g1} and T_{g2} are the T_g for the two homopolymers, w_1 and w_2 are the weight fractions and k is the ratio of the heat capacity change of PEF over PESu, which is associated with the degree of phase homogeneity in polymer blends or with the intensity of the intermolecular interactions ⁶⁶. The Gordon Taylor model seemed to fit better the experimental data **than all the applied models**.

In general, PESu and especially PEF proved to be slowly crystallizing. As was expected, the related copolymers showed even slower crystallization rates. Therefore, a self-nucleation scheme was applied prior to accelerate the phenomena and test the isothermal crystallization of the copolymers within a reasonable experimental time-scale. Self-nucleated crystallization of several polymers has been studied recently. In fact, Muller and co-workers, as well as others, proved that measuring isothermal crystallization rates after self-nucleation with DSC, is a reliable method for evaluating crystallization rates even for the application of the Lauritzen-Hoffman analysis ⁶⁷.

Figure 4. Variation of the melting temperature (T_m) and glass transition temperature (T_g) of the PEFSu copolymers with composition.

Figure 5a shows the crystallization half-times for PEF and EF rich copolymers. The corresponding plots for PESu and ES rich copolymers are shown in Figure 5b. From the corresponding plots it is obvious that there is an increase of the crystallization half-times with increasing comonomer unit content, showing retardation in the phenomenon. Also, the temperature window for crystallization shifts to lower temperatures and it becomes narrower. This is caused by two factors. On the one hand, the melting temperatures of the copolymers were reduced with increasing content so, for given crystallization temperature, the degree of supercooling was reduced. On the other hand, incorporation of comonomer units in the macromolecular chain reduces symmetry which in turn causes restrictions in crystallizability.

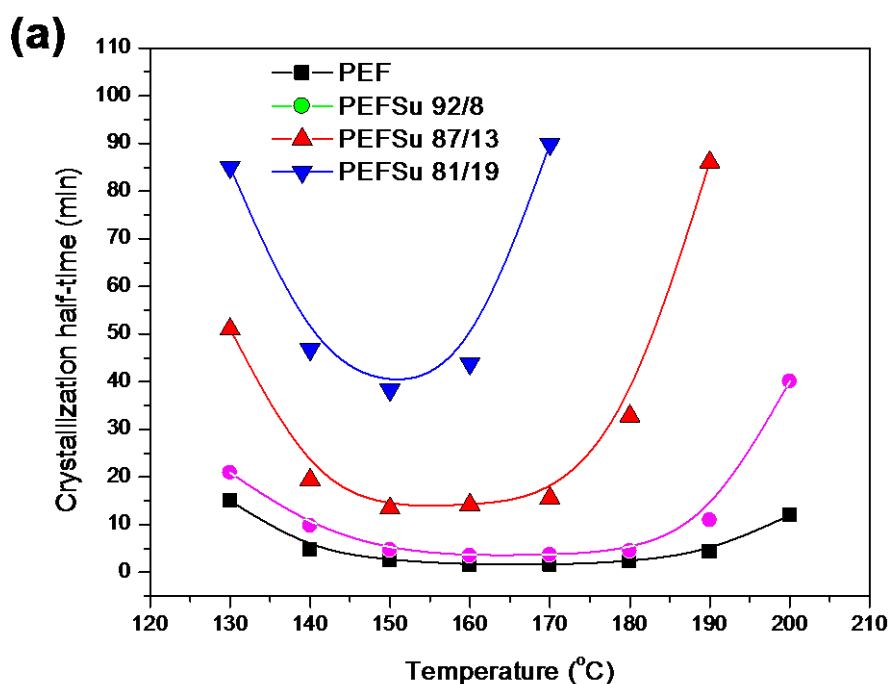

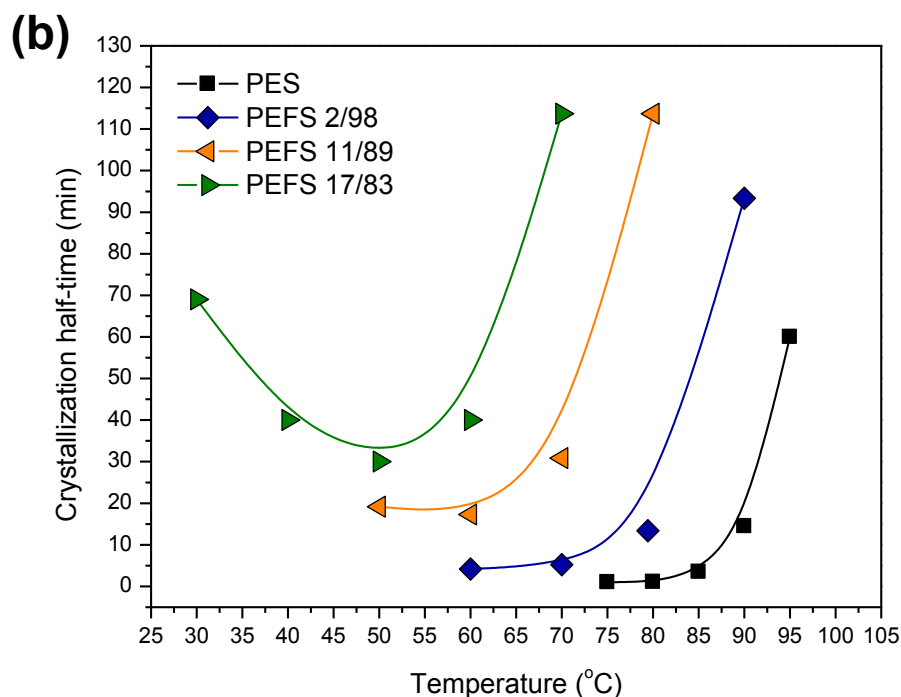
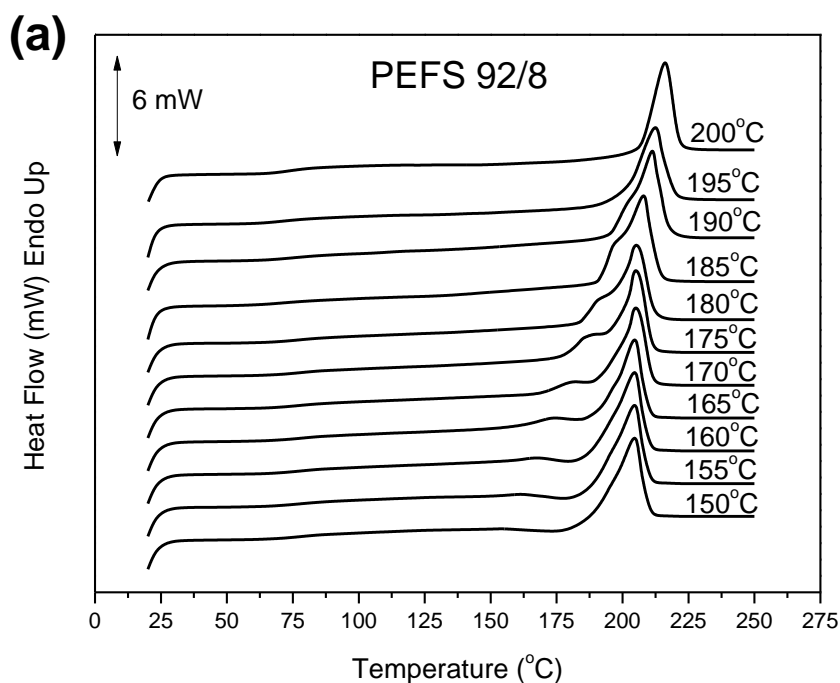


Figure 5. Isothermal crystallization half-times as a function of temperature: a) for PEF and EF rich copolymers and b) for PESu and ES rich copolymers.

3.2 Multiple melting behavior

Polyesters most commonly show multiple melting in subsequent heating scans after isotherm crystallization. For PEF it was found that appearance of multiple melting depends on the crystallization temperature^{56, 68, 69}. Sbirrazzuoli and coworkers have reported that the multiple melting of PEF occurs due to recrystallization during heating and not due to the different distributions of lamellar thickness of the material⁷⁰. Figure 6a shows the DSC heating scans of PEFSu 92/8 samples after isothermal crystallizations at different temperatures. The specific copolymer showed mainly double melting. Samples crystallized at lower temperatures (150-165°C) exhibited also a recrystallization peak in between the two melting peaks. In the traces of the samples crystallized at in the high T_c s region, above 180°C, a continuous shift of the

melting temperature towards higher temperatures could be observed with increasing T_c . This should be attributed to the higher degree of perfection of the generated crystals and to lamellar thickening. Moreover, in the DSC traces shown in Figure 6b, the melting behavior of the PEFSu 17/83 copolymer after isothermal crystallization at various temperatures can be also seen. Two things should be pointed out in these curves. Firstly, the melting temperature is substantially reduced compared to the neat PESu (Figure 6c). Secondly, there was a more pronounced multiple melting behavior in the case of the copolymer, but unlike neat PESu, the ultimate melting temperature was not dependent on the crystallization temperature. This should be associated with a much more pronounced crystal perfection and thickening in case of the neat PESu homopolymer. The presence of the comonomer units along the macromolecular chains seemed to restrict not only the crystallization rates but also the crystal stability.



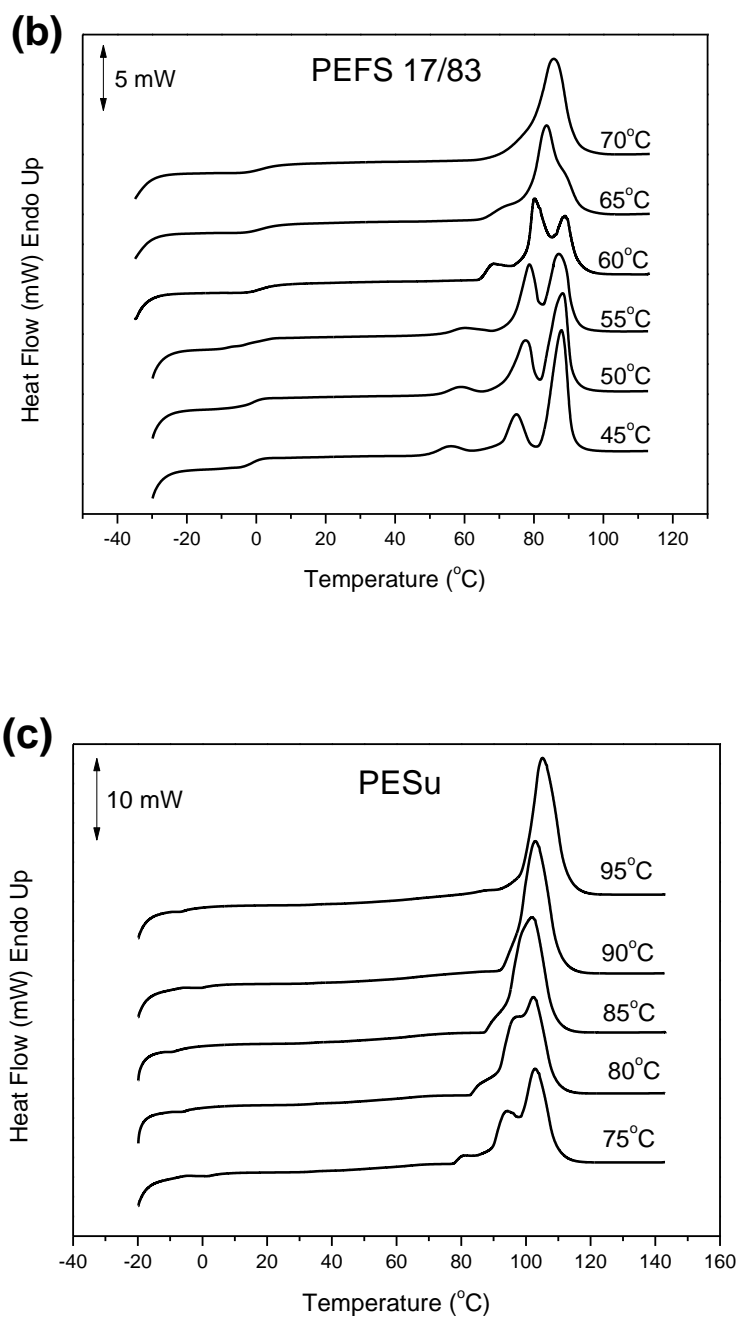


Figure 6. DSC traces of a) PEFSu 92/8, b) PEFSu 17/83 and c) neat PESu samples crystallized at different temperatures.

3.3 Cocrystallization behavior

As was reported before, in copolyesters where the two crystallizable components A and B, are also compatible in each crystal lattice, cocrystallization can be observed

which can be classified as isomorphism or isodimorphism ⁴¹. Isomorphism is met when the two components occupy about the same volume, so the chain conformations of both corresponding homopolymers are compatible with either crystal lattice and only one crystalline phase which contains both comonomer units is observed at all compositions. The phenomenon is evidenced by a clear melting temperature, or by the appearance of crystallinity over the entire copolymer composition.

In isodimorphism two crystalline phases are observed ⁷¹. Two sub cases are met in isodimorphism: a) each crystalline phase contains comonomer units; that is incorporation of B units in A crystal lattice can occur and vice versa and in b) case the A units can cocrystallize with the incorporation of the B comonomeric units, whereas B crystallizes with the complete rejection of the A units. Isodimorphism is associated with a minimum melting temperature in the plot of melting temperature versus copolymer composition (pseudo-eutectic behavior) and also with lowering in the degree of crystallinity.

For PEF, the crystal structure was estimated in an early study by Kazaryan and Medvedeva ⁷². According to them the PEF α crystal modification has a triclinic unit cell, with dimensions $a=0.575$ nm, $b=0.535$ nm, $c=2.010$ nm, $\alpha=133.3^\circ$, $\beta=90^\circ$ and $\gamma=112^\circ$, comprising two repeating units and crystal density of 1.565 g /cm³. The density of the amorphous phase is 1.4299 g /cm³ ¹⁰. In a previous work it was shown that when PEF crystallizes from solution or after solvent treatment it shows a different crystal modification, called β modification ⁶⁹.


The crystal structure of PESu was first studied by Fuller and Erickson ⁷³. They proposed a monoclinic unit cell with dimensions $a=0.905$ nm, $b=1.109$ nm and $c=0.832$ nm (c being the fiber axis), and $\beta=102.8^\circ$. Later, Ueda *et al.* determined the crystal and molecular structures of PESu and they proposed slight modification of the

crystallographic data ⁷⁴. Thus, PESu was found to crystallize as a $Pbnb-D_{2b}^{10}$ space group with unit cell parameters $a=0.760$ nm, $b=1.075$ nm and $c=0.833$ nm (c being the fiber axis), and four macromolecular chains pass through the unit cell. Ichikawa *et al.* reported the crystal modification of strained PESu fiber ⁷⁵. This modification was recognized as β form having a 0.95 nm fiber repeat period. In our case, neat PESu showed two strong peaks at 20.1° and 23.3° which correspond to reflections from (120) and (200) planes, respectively ⁷⁴.

The crystalline structure of the PEFSu copolymers was studied by means of WAXD. The comonomer concentration in crystal lattice of the copolymers is strongly dependent on the copolymer composition in both bulk and crystallization conditions, however crystalline reflection peaks were observed for most compositions. The reflections for the EF rich copolymers (EF content higher than 83 mol%) are associated with the PEF β -crystalline form, which is usually observed after solution crystallization. Moreover, for the EF-rich copolymers, the peaks became broader with increasing EF-content, indicating the presence of smaller crystalline size and decreasing crystallinity. In addition, a shift of the peaks towards higher angles can be observed, as a result of the distortion of the a -form PEF unit cell, caused by the presence of the ES co-unit. The PEFSu 35/65 and 37/63 copolymers did not crystallize even from solution since they exhibited the amorphous halo on their diffractograms while crystalline peaks were not clearly evidenced. The results are in agreement with DSC study, where the pseudo-eutectic point was observed on the melting temperatures of the specific samples. On the other hand, the copolymers with ES content higher than 81 mol% preferentially crystallize in the PESu a -crystal structure. The peak positions did not seem to be affected by the presence of the EF co-unit. Interestingly, the PEFSu 49/51 and 61/39 copolymers showed weak crystal

reflection peaks at positions consistent with those of both PEF and PESu. In intermediate compositions short comonomer block lengths are expected to lead in comonomer inclusion. This is also associated with lower degree of crystallinity and defective crystal structures. It should be noticed here that these two copolymers showed a broad melting temperature range, with the ultimate melting temperature to be higher than that of pure PESu.

The interplanar spacing was calculated for all copolymers based on the main reflections of the diffractograms presented in [Figure 7a](#). As it can be seen in [Figure 7b](#), an increase in the d-spacing and subsequently to the cell unit dimensions, is recorded for most reflection angles with decreasing EF content, as a result of the increasing ES comonomer, which is bulkier than the one of EF. The specific behavior is associated with isodimorphic cocrystallization, as was expected from the study of the melting point and the appearance of a pseudo-eutectic behavior.

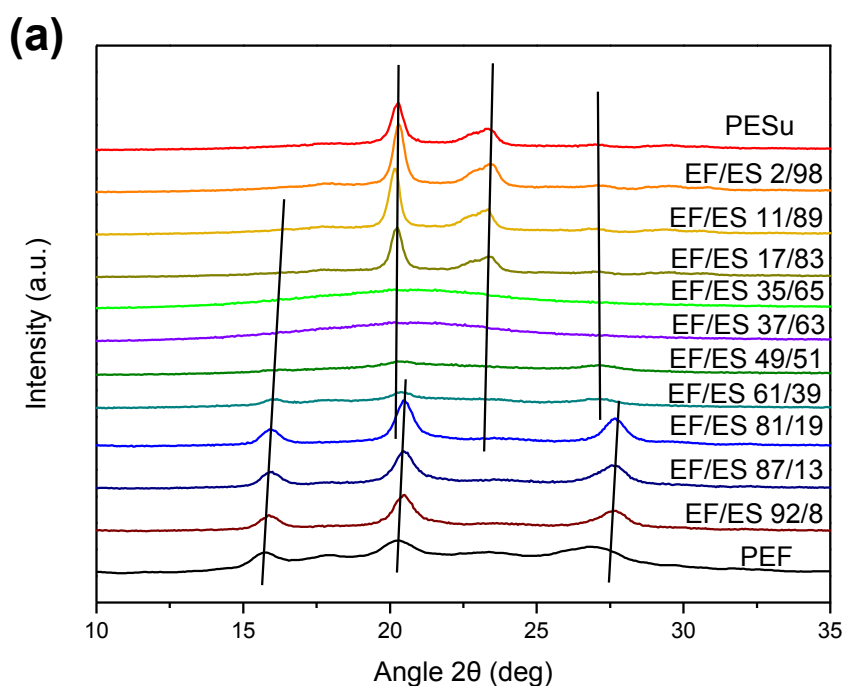

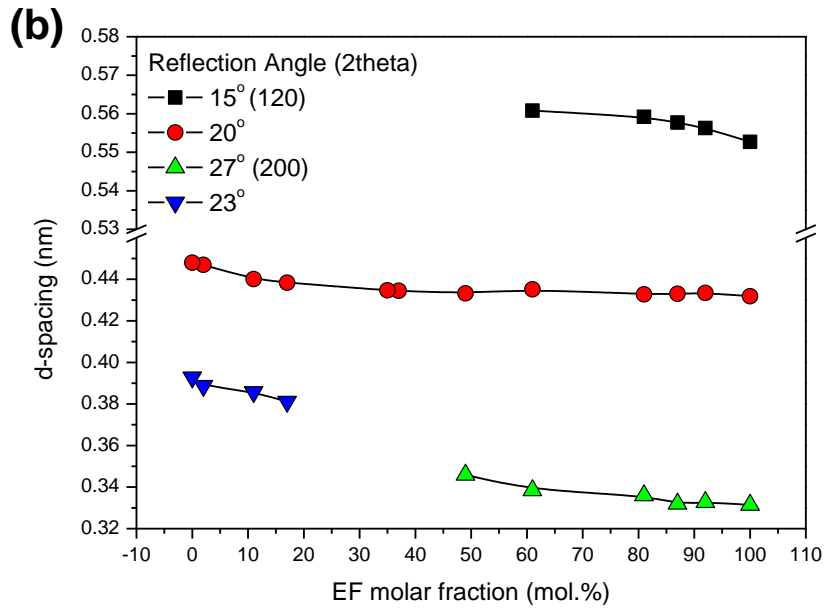


Figure 7. a) WAXD patterns of the PEFSu copolymers and the PEF and PESu homopolymers, b) variation of the interplanar distances (d-spacing) with the composition of PEFSu copolymers

3.4 Thermodynamics of Melting point depression

The melting point depression can be used for the thermodynamics analysis of cocrystallization in random copolymers. Several theories have been introduced for the copolymer crystallization. There is distinction between those which assume comonomer exclusion like those of Flory^{50, 51} or Baur⁵³ and those which assume comonomer inclusion in the crystal such as those of Inoue⁷⁶, Helfand-Lauritzen⁷⁷ and Sanchez-Eby⁵².

In the equation of Flory⁵⁰:

$$\frac{1}{T_m^o} - \frac{1}{T_m(X_B)} = \frac{R}{\Delta H_m^o} \ln(1 - X_B) \quad (7)$$

X_B is the concentration of the minor comonomer B units in the polymer and $\ln(1 - X_B)$ equals the collective activities of A sequences in the limit of the upper bound of the melting temperature. T_m^o and ΔH_m^o are the homopolymer equilibrium melting temperature and heat of fusion and R is the gas constant.

The Sanchez-Eby model assumes that B comonomer units are included into the crystals of A forming defects. The corresponding equation is ⁵²:

$$\frac{1}{T_m^o} - \frac{1}{T_m(X_B)} = \frac{R}{\Delta H_m^o} \ln(1 - X_B + X_B e^{-\epsilon/RT}) \quad (8)$$

where, $X_B e^{-\epsilon/RT}$ is the equilibrium fraction of repeat units B that are able to crystallize, and ϵ is the excess free energy of a defect created by the incorporation of one B unit into the crystal.

The basic concept in the theory of Baur, is that homopolymer sequences of length ξ may be included into crystals of lamellar thickness corresponding to that length ⁵³:

$$\frac{1}{T_m^o} - \frac{1}{T_m(X_B)} = \frac{R}{\Delta H_m^o} [\ln(1 - X_B) - \langle \xi \rangle^{-1}] \quad (9)$$

where $\langle \xi \rangle = [2X_B(1 - X_B)]^{-1} \quad (10)$

is the average length of homopolymer sequences in the melt.

Wendling and Suter combined both inclusion and exclusion models to arrive to the following equation ^{54, 78, 79}:

$$\frac{1}{T_m^o} - \frac{1}{T_m(X_B)} = \frac{R}{\Delta H_m^o} \left[\frac{\epsilon X_{CB}}{RT} + (1 - X_{CB}) \ln \frac{1 - X_{CB}}{1 - X_B} + X_{CB} \ln \frac{X_{CB}}{X_B} + \langle \tilde{\xi} \rangle^{-1} \right] \quad (11)$$

where X_{CB} is the concentration of the B units in the crystal. In the equilibrium comonomer inclusion, the concentration of B units in the crystal is given by:

$$X_{CB}^{eq} = \frac{X_B e^{-\epsilon/RT}}{1 - X_B + X_B e^{-\epsilon/RT}} \quad (9)$$

Substitution of X_{CB} in equation 8 by equation 9, gives a simplified equation following equilibrium inclusion model:

$$\frac{1}{T_m^o} - \frac{1}{T_m(X_B)} = \frac{R}{\Delta H_m^o} \{ \ln(1 - X_B + X_B e^{-\epsilon/RT}) - \langle \tilde{\xi} \rangle^{-1} \} \quad (12)$$

where

$$\langle \tilde{\xi} \rangle^{-1} = 2(X_B - X_B e^{-\epsilon/RT}) \cdot (1 - X_B + X_B e^{-\epsilon/RT}) \quad (13)$$

Uniform inclusion is reached if $X_{CB} = X_B$ while for $X_{CB} = 0$ equation 8 is reduced to the exclusion model.

Various thermodynamic models were tested for the melting point depression of PEFSu. The temperature corresponding to the end of the melting peak was used, as

an approach of the equilibrium melting temperature. Also, in our calculations, the equilibrium melting enthalpy was taken to be 25 kJ/mol for PEF⁵⁶ and 26 kJ/mol for PESu⁵⁷.

As can be seen in Figure 8 the Wendling-Suter model showed the best fit to the experimental data in the range of low comonomer content. The value of the function ϵ/RT is determined as an adjustable parameter. A constant ϵ/RT value is given by the model regardless of the comonomer composition. For PEF best fit was found for $\epsilon/RT=1.8$ which results in a value $\epsilon = 7.6$ kJ/mol for the average defect free energy in case of incorporation of ES unit into the PEF crystal, in the limiting case of $X_{ES} = 0$. In the opposite case of incorporation of EF units in the PESu crystal a value $\epsilon/RT=2.5$ was needed for best fit, giving $\epsilon = 8.1$ kJ/mol for the average defect free energy. The ϵ in this case is slightly higher than in case of incorporation of ES units in the PEF crystal.

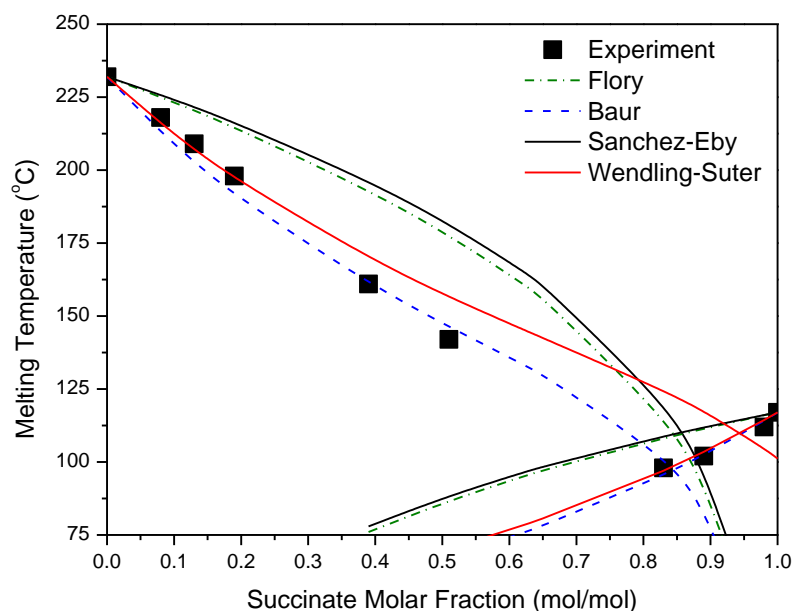
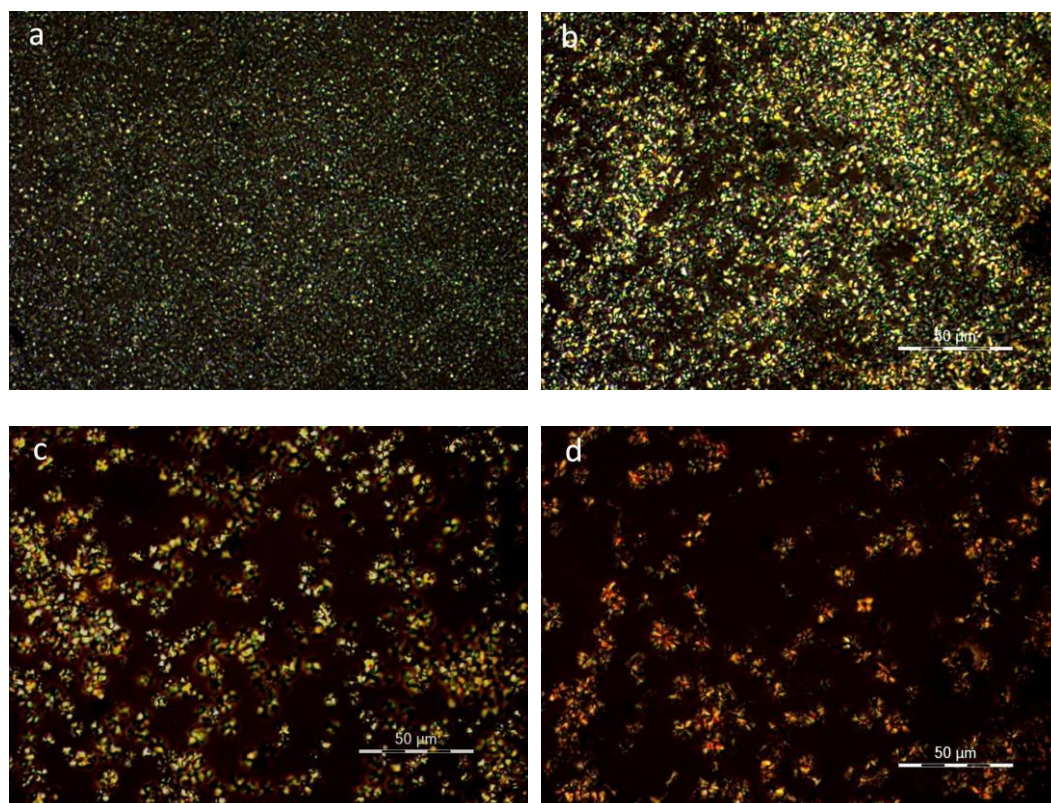


Figure 8. Experimental and predicted melting point as a function of the succinate molar fraction.

3.5 PLOM observations during melt crystallization

Polarized light optical microscopy was utilized for the observation of the spherulitic structure of the copolymers after isothermal crystallization at various temperatures. As it can be seen in Figure 9a-d, PEF exhibited the characteristic small spherulites with a very high density at all crystallization temperatures⁵⁶. On the other hand, PESu displayed significantly larger spherulites with the characteristic maltese cross, while there is a gradual increase in the size with increasing crystallization temperature (Figure 10a-d). The presence of PESu even at a small percentage on the PEFSu 92/8 sample, increased slightly the sizes of the spherulites, while the nucleation density of the materials remained very high (Figure 9e, f). On the contrary, as it was expected, the presence of a small amount of PEF on the ES rich samples, affected marginally the spherulitic morphology of the materials, since the nucleation density and the size of the spherulites decreased.



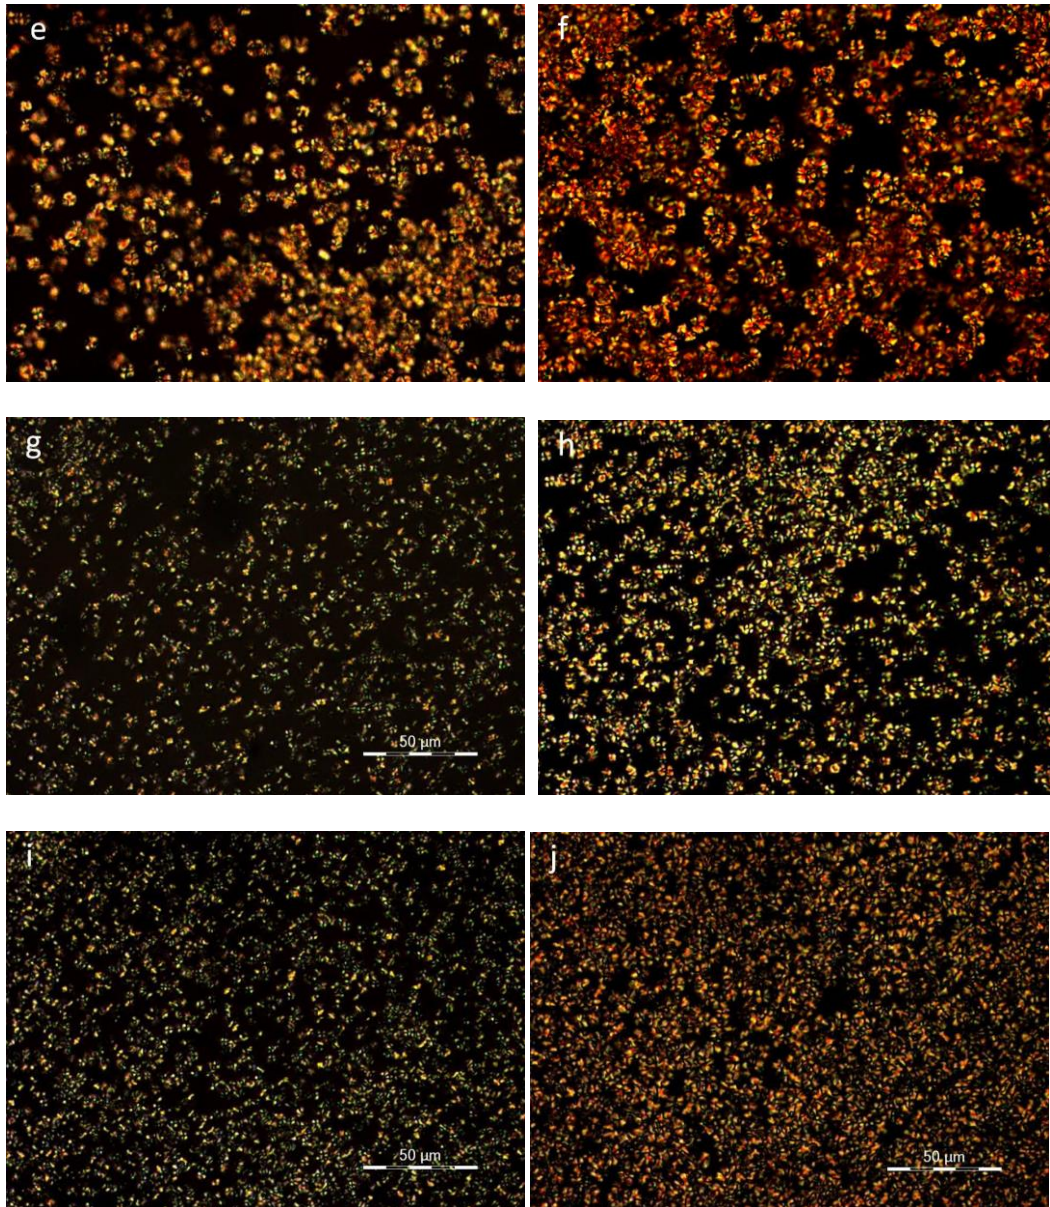
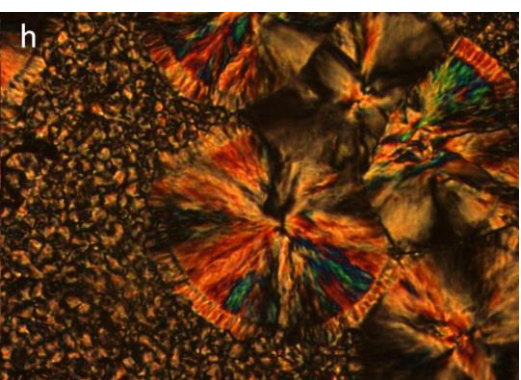
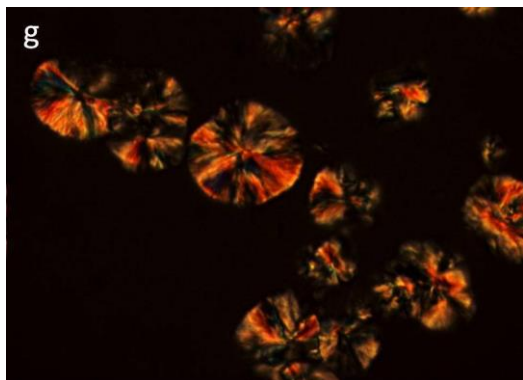
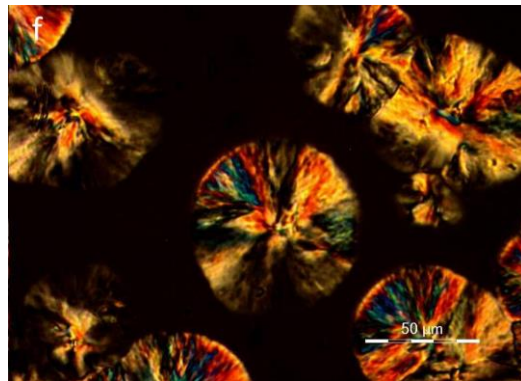
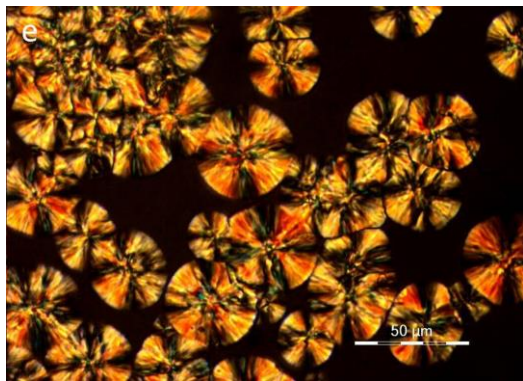
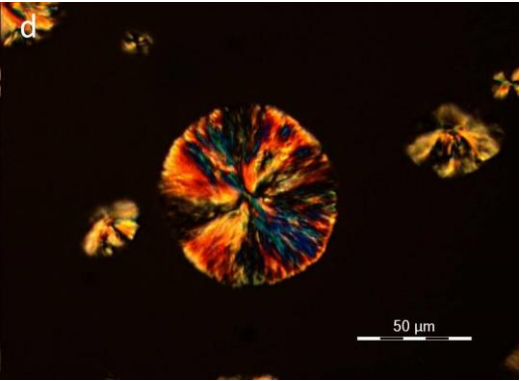
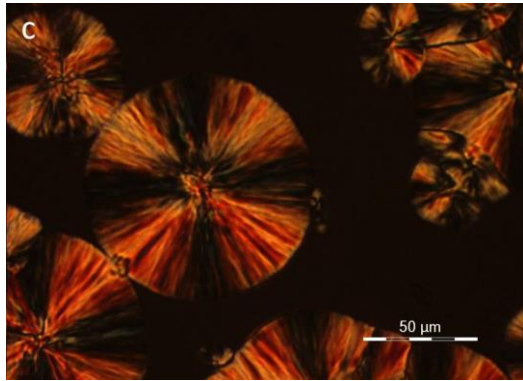
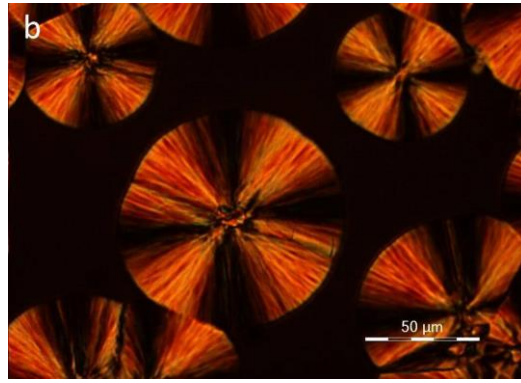
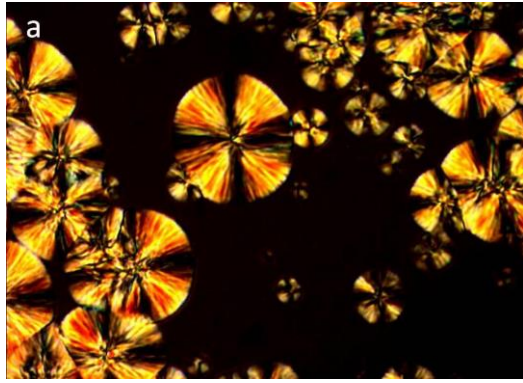


Figure 9. PLOM photos of a) PEF at 160°C, 10 min, b) PEF at 180°C, 15 min, c) PEF at 200°C, 20 min, d) PEF at 210°C, 30 min, e) PEFSu 92/8 at 150°C, 20 min, f) PEFSu 92/8 at 160°C, 20 min, g) PEFSu 87/13 at 140°C, 20 min, h) PEFSu 87/13 at 160°C, 20 min, i) PEFSu 81/19 at 130°C, 20 min and j) PEFSu 81/19 at 140°C, 20 min.



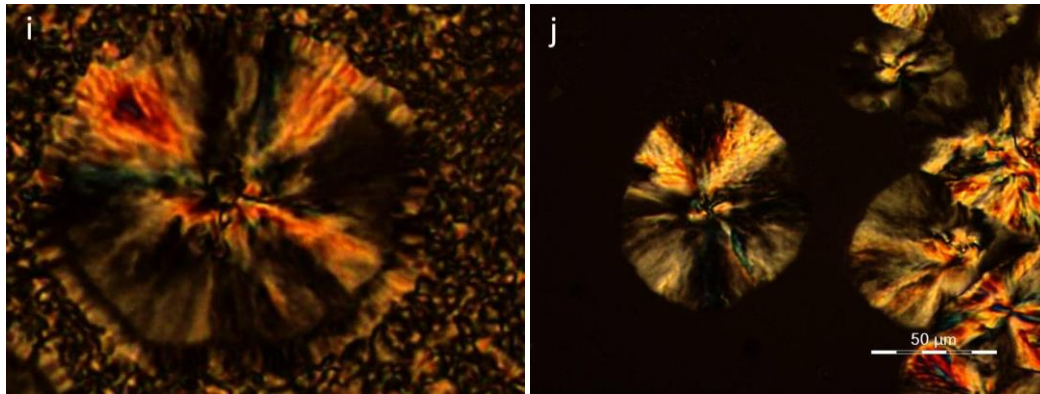


Figure 10. PLOM photos of a) PESu at 50 °C, 5 min, b) PESu at 60 °C, 5 min, c) PESu at 70 °C, 5 min, d) PESu at 80 °C, 5 min, e) PEFSu 2/98 at 50 °C, 5 min, f) PEFSu 2/98 at 60 °C, 7 min g) PEFSu 11/89 at 60 °C, 7 min, h) PEFSu 11/89 cooled to room temperature after crystallization at 60 °C for 7 min, i) PEFSu 11/89 cooled to room temperature after crystallization at 60 °C for 7 min and j) PEFSu 17/83 at 50 °C, 10 min.

3.6 Enzymatic hydrolysis

As the amount of plastic waste continually grows, the use of biodegradable polymers is becoming more and more essential. 2,5-FDCA-based polyesters can be prepared from monomers derived from renewable resources but these polyesters are not biodegradable materials. However, from soil-burial tests along with enzymatic degradation experiments, it was proposed that these polyesters could be potentially biodegradable⁸⁰. In a recent study, PEF powders of various molecular weights (6, 10 and 40 kDa) were synthesized and their susceptibility to enzymatic hydrolysis was investigated⁸¹. According to LC/TOF-MS analysis, it was found that cutinase 1 from *Thermobifida cellulosilytica* liberated both 2,5-furandicarboxylic acid and oligomers of up to DP4. The enzyme preferentially hydrolyzed PEF with higher molecular weights but was active on all tested substrates. However, this is not a proof the PEF is

a biodegradable polyester. On the other hand, while aliphatic polyesters such as PESu are easily **hydrolysed**, their mechanical properties are poor. Therefore copolymerizing it with aromatic moieties can result in both better properties and acceptable **enzymatic hydrolysis rates** ⁸². Commercial aliphatic-aromatic copolyesters are available in the market, for example Ecoflex[®] which is a product of BASF. Aromatic polyesters such as PET or PEF are regarded as non-biodegradable, so the copolymerization of FDCA with aliphatic acids is expected to induce biodegradability. Enzymatic hydrolysis rate is known to depend on the hydrophilicity, the chemical structure, the mobility of the amorphous phase and also the crystallinity ^{83, 84}.

The weight loss % of the copolyesters during enzymatic hydrolysis over a course of 30 days is presented in **Figure 11**. While PESu lost 30% of its initial weight after a month, copolymers containing furanoate units showed negligible **hydrolysis** rates. As the content in succinate increases, the **enzymatic hydrolysis** rate is also increased. In succinate contents up to 50%, weight loss is relatively small (maximum 6%) but measureable within the first month. Significant hydrolysis can be induced at higher contents. PEFSu 17/3 and PEFSu 11/89 lost 15% and 12.5% of their initial weights in 1 month. **The furan ring makes the access of enzymes to the ester group more difficult, because it causes the macromolecular chain of PEF to be rigid since ring-flipping is hindered by the nonlinear axis of furan ring rotation coupled with the ring polarity.** Additionally, melting temperature and glass transition temperature of the copolymers increase with increasing the furanoate content, so the mobility of the macromolecular chains is decreased, further reducing the **hydrolysis** rates. Similar results were obtained in our previous work with aliphatic-aromatic copolymers ⁶¹, as also by other researchers ^{82, 85}. In the case of furanoate copolymers it was found that copolymerization of PEF with lactic acid enhanced its **hydrolysis** rate ^{86, 87}, as also the

presence of butylene adipate in poly(butylene furanoate) polyester resulted in accelerated hydrolysis by lipase⁸⁸. This behavior is attributed to the higher hydrophobicity of the furanoate units and the increased rigidity they provide, therefore less mobility of the macromolecular chains.

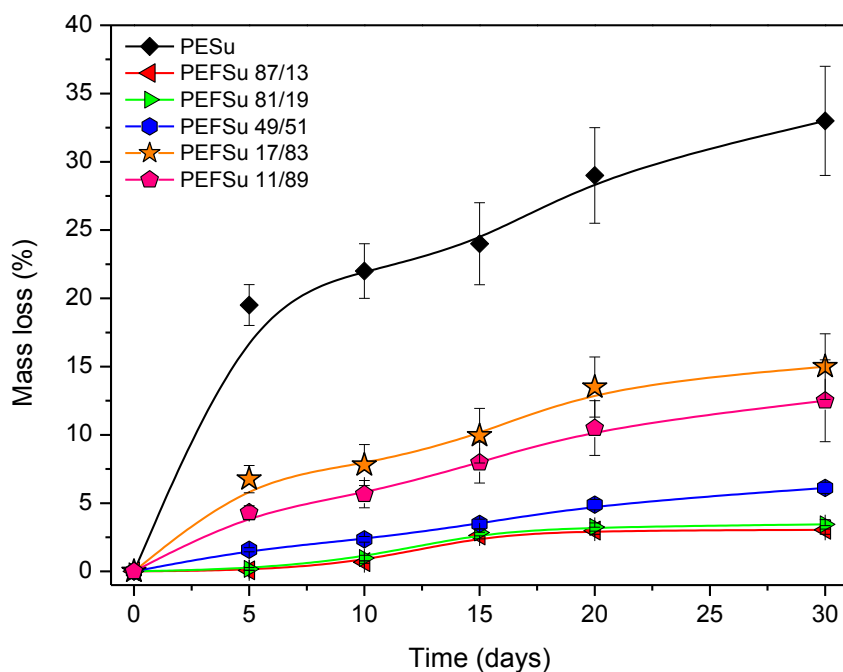
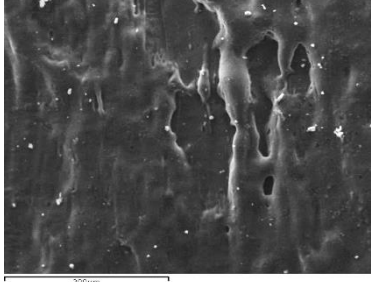

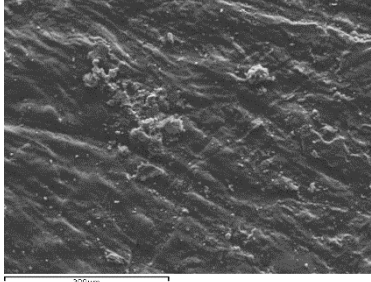
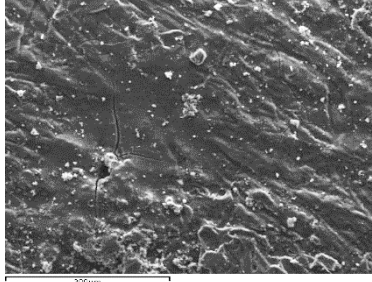
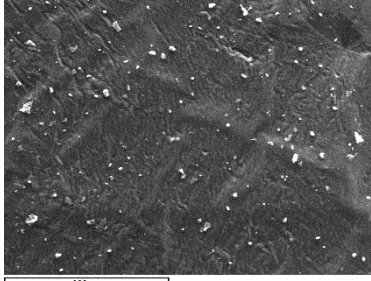
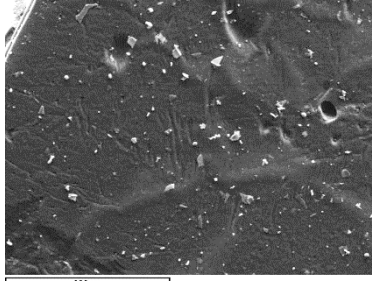
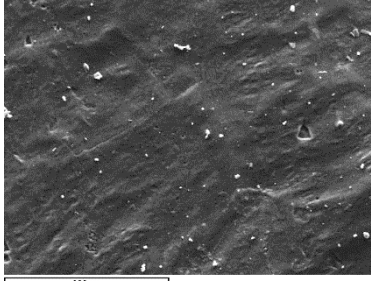
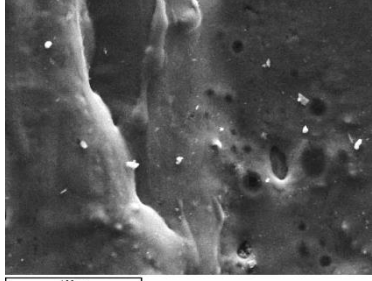
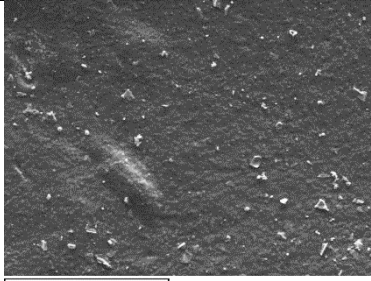
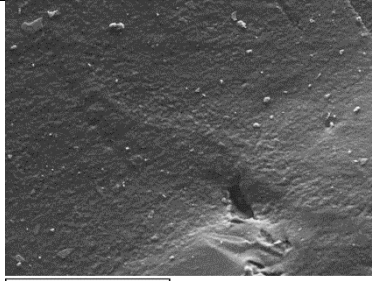


Figure 11. Weight loss plots during enzymatic hydrolysis.

Besides weight loss measurements, SEM micrographs were also obtained after enzymatic hydrolysis of the polyesters for 15 and 30 days, and are presented in [Figure 12](#). They are in agreement with mass loss, as more abnormalities, gaps and holes are observed in copolyesters with high succinate contents, while surfaces of the polyesters with more furanoate units are not altered significantly. The roughness of surfaces becomes more prominent over the course of enzymatic hydrolysis time.

| Sample | 15 days | 30 days |
|-------------------------------|---|--|
| <p>PESu</p> |  |  |
| <p>PEFSu 11/89</p> |  |  |
| <p>PEFSu 17/83</p> |  |  |
| <p>PEFSu 49/51</p> |  |  |
| <p>PEFSu 17/83</p> |  |  |

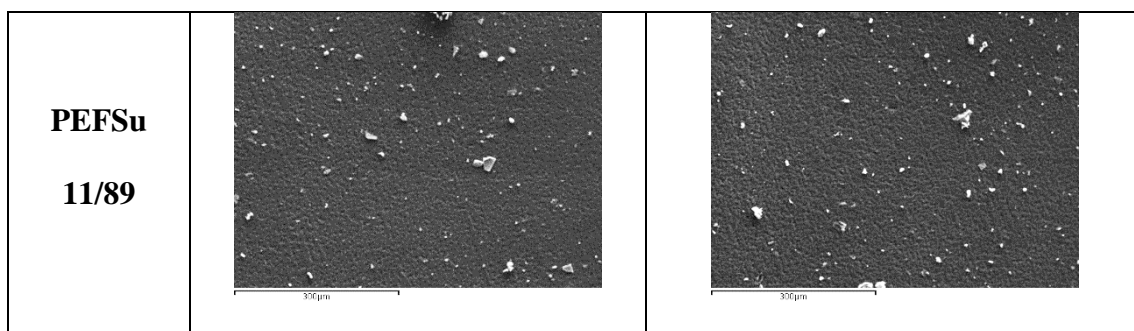


Figure 12. SEM micrographs of the copolyesters after enzymatic hydrolysis for 15 and 30 days.

4. Conclusions

Random poly(ethylene furanoate-co-ethylene succinate) copolymers with several furanoate/succinate molar ratios have been successfully prepared by melt polycondensation procedure. The influence of the increasing EF (or ES) content on the melting and crystallization behavior, crystalline structure and enzymatic hydrolysis were studied in detail. Most of the produced copolymers are semicrystalline materials with thermal properties depending directly on the composition. The melting and glass transition temperatures were found to decrease with increasing ES content, while increase in the EF content caused a slight decrease in the cell dimensions of the copolymers. Moreover, from the study of the melting point of the copolymers, a pseudo-eutectic behavior was observed at ED/ES fraction of 30/70, which was further confirmed by WAXD. The specific behavior is associated with isodimorphic cocrystallization. From the enzymatic hydrolysis study, the copolymers with high succinic acid amounts are hydrolysable materials with the help of *Rhizopus delemar* lipase and *Pseudomonas Cepacia* lipase. However, up to a 50 mol% PEF content, measurable losses in weight were shown. Thus, these copolymers are excellent biodegradable materials, which along with the fact that they can be

prepared directly from monomers derived from renewable resources, makes them attractive for various applications and uses.

References

1. E. de Jong, M. Dam, L. Sipos and G. Gruter, *Biobased monomers, polymers, and materials*, 2012, **1105**, 1-13.
2. C. Vilela, A. F. Sousa, A. C. Fonseca, A. C. Serra, J. F. Coelho, C. S. Freire and A. J. Silvestre, *Polymer Chemistry*, 2014, **5**, 3119-3141.
3. A. F. Sousa, C. Vilela, A. C. Fonseca, M. Matos, C. S. Freire, G.-J. M. Gruter, J. F. Coelho and A. J. Silvestre, *Polymer Chemistry*, 2015, **6**, 5961-5983.
4. A. Gandini, *Polymer Chemistry*, 2010, **1**, 245-251.
5. A. Gandini, A. J. Silvestre, C. P. Neto, A. F. Sousa and M. Gomes, *Journal of Polymer Science Part A: Polymer Chemistry*, 2009, **47**, 295-298.
6. M. Gomes, A. Gandini, A. J. Silvestre and B. Reis, *Journal of Polymer Science Part A: Polymer Chemistry*, 2011, **49**, 3759-3768.
7. J. Ma, X. Yu, J. Xu and Y. Pang, *Polymer*, 2012, **53**, 4145-4151.
8. M. Jiang, Q. Liu, Q. Zhang, C. Ye and G. Zhou, *Journal of Polymer Science Part A: Polymer Chemistry*, 2012, **50**, 1026-1036.
9. V. Tsanakis, G. Z. Papageorgiou and D. N. Bikiaris, *Journal of Polymer Science Part A: Polymer Chemistry*, 2015, **53**, 2617-2632.
10. S. K. Burgess, J. E. Leisen, B. E. Kraftschik, C. R. Mubarak, R. M. Kriegel and W. J. Koros, *Macromolecules*, 2014, **47**, 1383-1391.
11. S. K. Burgess, O. Karvan, J. Johnson, R. M. Kriegel and W. J. Koros, *Polymer*, 2014, **55**, 4748-4756.
12. S. K. Burgess, R. M. Kriegel and W. J. Koros, *Macromolecules*, 2015, **48**, 2184-2193.
13. G. Z. Papageorgiou, V. Tsanakis, D. G. Papageorgiou, S. Exarhopoulos, M. Papageorgiou and D. N. Bikiaris, *Polymer*, 2014, **55**, 3846-3858.
14. G. Z. Papageorgiou, D. G. Papageorgiou, V. Tsanakis and D. N. Bikiaris, *Polymer*, 2015, **62**, 28-38.
15. G. Z. Papageorgiou, V. Tsanakis, D. G. Papageorgiou, K. Chrissafis, S. Exarhopoulos and D. N. Bikiaris, *European Polymer Journal*, 2015, **67**, 383-396.
16. G. Z. Papageorgiou, N. Guigo, V. Tsanakis, D. G. Papageorgiou, S. Exarhopoulos, N. Sbirrazzuoli and D. N. Bikiaris, *European Polymer Journal*, 2015, **68**, 115-127.
17. V. Tsanakis, D. N. Bikiaris, N. Guigo, S. Exarhopoulos, D. G. Papageorgiou, N. Sbirrazzuoli and G. Z. Papageorgiou, *RSC Advances*, 2015, **5**, 74592-74604.
18. V. Tsanakis, Z. Terzopoulou, S. Exarhopoulos, D. N. Bikiaris, D. S. Achilias, D. G. Papageorgiou and G. Z. Papageorgiou, *Polymer Chemistry*, 2015, **6**, 8284-8296.
19. M. Vannini, P. Marchese, A. Celli and C. Lorenzetti, *Green Chemistry*, 2015, **17**, 4162-4166.

20. A. Gandini, *Green Chemistry*, 2011, **13**, 1061-1083.
21. S. Thiagarajan, W. Vogelzang, R. J. I. Knoop, A. E. Frissen, J. van Haveren and D. S. van Es, *Green Chemistry*, 2014, **16**, 1957-1966.
22. A. F. Sousa, A. C. Fonseca, A. C. Serra, C. S. R. Freire, A. J. D. Silvestre and J. F. J. Coelho, *Polymer Chemistry*, 2016, **7**, 1049-1058.
23. K. Chrissafis, K. Paraskevopoulos and D. Bikiaris, *Thermochimica acta*, 2005, **435**, 142-150.
24. Z. Gan, H. Abe and Y. Doi, *Biomacromolecules*, 2000, **1**, 704-712.
25. Z. Qiu, M. Komura, T. Ikehara and T. Nishi, *Polymer*, 2003, **44**, 7781-7785.
26. J. Lu, Z. Qiu and W. Yang, *Polymer*, 2007, **48**, 4196-4204.
27. Y. Tokiwa, B. Calabia, C. Ugwu and S. Aiba, *International Journal of Molecular Sciences*, 2009, **10**, 3722.
28. G. Seretoudi, D. Bikiaris and C. Panayiotou, *Polymer*, 2002, **43**, 5405-5415.
29. D. P. Kint, A. Alla, E. Deloret, J. L. Campos and S. Muñoz-Guerra, *Polymer*, 2003, **44**, 1321-1330.
30. M. Mochizuki, K. Mukai, K. Yamada, N. Ichise, S. Murase and Y. Iwaya, *Macromolecules*, 1997, **30**, 7403-7407.
31. X. Li and Z. Qiu, *Polymer Testing*, 2015, **48**, 125-132.
32. X. Li and Z. Qiu, *Industrial & Engineering Chemistry Research*, 2016, **55**, 3797-3803.
33. X. Li and Z. Qiu, *RSC Advances*, 2015, **5**, 103713-103721.
34. Z. Qiu, T. Ikehara and T. Nishi, *Macromolecules*, 2002, **35**, 8251-8254.
35. F. Kondratowicz and R. Ukielski, *Polymer Degradation and Stability*, 2009, **94**, 375-382.
36. P. Xue and Z. Qiu, *Thermochimica acta*, 2015, **606**, 45-52.
37. H. Wu and Z. Qiu, *CrystEngComm*, 2012, **14**, 3586-3595.
38. L. Wu, R. Mincheva, Y. Xu, J.-M. Raquez and P. Dubois, *Biomacromolecules*, 2012, **13**, 2973-2981.
39. K. Kuwabara, Z. Gan, T. Nakamura, H. Abe and Y. Doi, *Biomacromolecules*, 2002, **3**, 390-396.
40. G. Z. Papageorgiou and D. N. Bikiaris, *Biomacromolecules*, 2007, **8**, 2437-2449.
41. G. Allegra and I. W. Bassi, in *Fortschritte der Hochpolymeren-Forschung*, Springer Berlin Heidelberg, Berlin, Heidelberg, 1969, pp. 549-574.
42. C. Lavilla, E. Gubbels, A. Alla, A. Martinez de Ilarduya, B. A. J. Noordover, C. E. Koning and S. Munoz-Guerra, *Green Chemistry*, 2014, **16**, 1789-1798.
43. C. Lavilla and S. Munoz-Guerra, *Green Chemistry*, 2013, **15**, 144-151.
44. G. Ceccorulli, M. Scandola, A. Kumar, B. Kalra and R. A. Gross, *Biomacromolecules*, 2005, **6**, 902-907.
45. Z. Liang, P. Pan, B. Zhu and Y. Inoue, *Polymer*, 2011, **52**, 2667-2676.
46. G. Z. Papageorgiou, A. A. Vassiliou, V. D. Karavelidis, A. Koumbis and D. N. Bikiaris, *Macromolecules*, 2008, **41**, 1675-1684.
47. W. J. Orts, R. H. Marchessault and T. L. Bluhm, *Macromolecules*, 1991, **24**, 6435-6438.
48. G. Z. Papageorgiou and D. N. Bikiaris, *Macromolecular Chemistry and Physics*, 2009, **210**, 1408-1421.
49. G. Z. Papageorgiou, V. Tsanaktsis and D. N. Bikiaris, *CrystEngComm*, 2014, **16**, 7963-7978.
50. P. J. Flory, *The Journal of Chemical Physics*, 1949, **17**, 223-240.
51. P. J. Flory, *Transactions of the Faraday Society*, 1955, **51**, 848-857.

52. I. C. Sanchez and R. K. Eby, *Macromolecules*, 1975, **8**, 638-641.
53. V. H. Baur, *Die Makromolekulare Chemie*, 1966, **98**, 297-301.
54. J. Wendling, A. A. Gusev and U. W. Suter, *Macromolecules*, 1998, **31**, 2509-2515.
55. J. P. Penning and R. St. John Manley, *Macromolecules*, 1996, **29**, 77-83.
56. G. Z. Papageorgiou, V. Tsanaktis and D. N. Bikiaris, *Physical Chemistry Chemical Physics*, 2014, **16**, 7946-7958.
57. D. N. Bikiaris, G. Z. Papageorgiou and D. S. Achilias, *Polymer degradation and stability*, 2006, **91**, 31-43.
58. B. Fillon, J. Wittmann, B. Lotz and A. Thierry, *Journal of Polymer Science Part B: Polymer Physics*, 1993, **31**, 1383-1393.
59. D. Cavallo, L. Gardella, G. Portale, A. J. Müller and G. C. Alfonso, *Polymer*, 2014, **55**, 137-142.
60. M. Soccio, L. Finelli, N. Lotti, M. Gazzano and A. Munari, *Journal of Polymer Science Part B: Polymer Physics*, 2007, **45**, 310-321.
61. G. Z. Papageorgiou, A. A. Vassiliou, V. D. Karavelidis, A. Koumbis and D. N. Bikiaris, *Macromolecules*, 2008, **41**, 1675-1684.
62. R. Yamadera and M. Murano, *Journal of Polymer Science Part A-1: Polymer Chemistry*, 1967, **5**, 2259-2268.
63. T. G. Fox, *Bull Am Phys Soc*, 1956, **1**, 123-135.
64. P. Couchman and F. Karasz, *Macromolecules*, 1978, **11**, 117-119.
65. M. Gordon and J. S. Taylor, *Journal of Applied Chemistry*, 1952, **2**, 493-500.
66. R. E. Prud'homme, *Polymer Engineering and Science*, 1982, **22**, 90-95.
67. A. J. Müller, R. M. Michell, R. A. Pérez and A. T. Lorenzo, *European Polymer Journal*, 2015, **65**, 132-154.
68. G. Stoclet, G. G. du Sart, B. Yeniad, S. de Vos and J. Lefebvre, *Polymer*, 2015, **72**, 165-176.
69. V. Tsanaktis, D. G. Papageorgiou, S. Exarhopoulos, D. N. Bikiaris and G. Z. Papageorgiou, *Crystal Growth & Design*, 2015, **15**, 5505-5512.
70. L. Martino, N. Guigo, J. G. van Berkel, J. J. Kolstad and N. Sbirrazzuoli, *Macromolecular Materials and Engineering*, 2016, n/a-n/a.
71. G. P. Karayannidis, N. Papachristos, D. N. Bikiaris and G. Z. Papageorgiou, *Polymer*, 2003, **44**, 7801-7808.
72. L.G. Kazaryan and F. M. Medvedeva, *Vysokomolekulyarnye Soedineniya, Seriya B: Kratkie Soobshcheniya*, 1968, 305-306.
73. C. Fuller and C. Erickson, *Journal of the American Chemical Society*, 1937, **59**, 344-351.
74. A. S. Ueda, Y. Chatani and H. Tadokoro, *Polymer Journal*, 1971, **2**, 387-397.
75. Y. Ichikawa, K. Noguchi, K. Okuyama and J. Washiyama, *Polymer*, 2001, **42**, 3703-3708.
76. N. Kamiya, M. Sakurai, Y. Inoue and R. Chujo, *Macromolecules*, 1991, **24**, 3888-3892.
77. E. Helfand and J. I. Lauritzen, *Macromolecules*, 1973, **6**, 631-638.
78. J. Wendling, A. A. Gusev, U. W. Suter, A. Braam, L. Leemans, R. J. Meier, J. Aerts, J. v. d. Heuvel and M. Hottenhuis, *Macromolecules*, 1999, **32**, 7866-7878.
79. J. Wendling and U. W. Suter, *Macromolecules*, 1998, **31**, 2516-2520.
80. M. Okada, K. Tachikawa and K. Aoi, *Journal of Polymer Science Part A: Polymer Chemistry*, 1997, **35**, 2729-2737.

81. A. Pellis, K. Haernvall, C. M. Pichler, G. Ghazaryan, R. Breinbauer and G. M. Guebitz, *Journal of Biotechnology*.
82. E. Marten, R.-J. Müller and W.-D. Deckwer, *Polymer Degradation and Stability*, 2003, **80**, 485-501.
83. D. N. Bikiaris, N. P. Nianias, E. G. Karagiannidou and A. Docoslis, *Polymer degradation and stability*, 2012, **97**, 2077-2089.
84. S. Mizuno, T. Maeda, C. Kanemura and A. Hotta, *Polymer degradation and stability*, 2015, **117**, 58-65.
85. K. Herzog, R.-J. Müller and W.-D. Deckwer, *Polymer degradation and stability*, 2006, **91**, 2486-2498.
86. M. Matos, A. F. Sousa, A. C. Fonseca, C. S. Freire, J. F. Coelho and A. J. Silvestre, *Macromolecular Chemistry and Physics*, 2014, **215**, 2175-2184.
87. H. Wu, B. Wen, H. Zhou, J. Zhou, Z. Yu, L. Cui, T. Huang and F. Cao, *Polymer Degradation and Stability*, 2015, **121**, 100-104.
88. W. Zhou, X. Wang, B. Yang, Y. Xu, W. Zhang, Y. Zhang and J. Ji, *Polymer Degradation and Stability*, 2013, **98**, 2177-2183.

