

1 Cavalli A., Cibecchini D., Togni M., Sousa H.S. (2016). A review on the mechanical properties of aged wood
2 and salvaged timber. *Construction and Building Materials* 114. pp 681-687
3 (doi.org/10.1016/j.conbuildmat.2016.04.001)

4 The final publication is available at sciencedirect.com: <http://doi.org/10.1016/j.conbuildmat.2016.04.001>
5

6

7 **A review on the mechanical properties of aged wood and salvaged**

8 **timber**

9

10 Alberto Cavalli¹, Daniele Cibecchini¹, Marco Togni¹, Hélder S. Sousa²

11 University of Florence, Florence, Dep. of Agriculture, Food and Forestry Systems.

12 University of Minho, Guimarães, ISISE – Institute for Sustainability and Innovation in Structural
13 Engineering.

14 Corresponding author: Alberto Cavalli

15

16 **Abstract**

17 The effect of time on the mechanical properties of wood is of interest for structural engineers, wood
18 technologists and conservators; for the old timber structure assessment, for the potential reuse of
19 salvaged timbers and poles and for the conservation of wooden artefacts as well. The topic was
20 investigated since the 50's, but the results reported in literature are not always concordant. This is
21 a consequence of the fact that this kind of research works are quite difficult, as a consequence of
22 the material characteristics itself: mechanical properties variability, low availability of material,
23 uncertainty about the “history” of the tested material, unknown original mechanical properties.
24 Another source of uncertainty between the research works is a consequence of the different
25 research approaches: some have investigated only the effect of the time passing (therefore,
26 aging), others consider the aging effect together with other effects, like the state of conservation

27 and the duration of load. The main interest of the researchers was in the bending properties
28 variation, while for other mechanical properties less information is available. In this paper, the
29 results of several research works are presented and analysed regarding the differences in the
30 mechanical properties for elements with different age levels. Moreover, recommendations for
31 future research are included attending to the conclusions drawn from the analysed literature.

32 Keywords: old timber; old wood; aging effect; salvaged timber.

33 **1. Introduction**

34 A very common question on wood is if its mechanical properties are affected by time. This question
35 is of interest for both timber structures conservation and assessment, as well as in wooden artefact
36 conservation field. Many factors affect the structural health of timber and the mechanical properties
37 of wood, as instance: the presence and extension of biological attacks (insects degradation or
38 decay), the material quality, the history and duration of load acting on the structure (is it the original
39 one or has it changed during time?). However the problem must be distinguished: mechanical
40 properties of wood affected by decay decrease strongly, but decay is a consequence of the state of
41 conservation, not a consequence of the wood age itself. Similarly, the effect of the load history is
42 related to the age of wood, but it is not a consequence of the wood's age [1]. The first systematic
43 research works on aged wood mechanical properties were carried out in Japan during the 50's [2–
44 9]. The aim of these works was to investigate only the effect of time passing on the mechanical
45 properties of wood.

46 Later, many research works were published also in Europe, especially in Germany [10–15]. Since
47 the 90's large testing campaigns were carried out, mainly in the United States of America, although
48 with slightly different aims: not only the effect of the aging was investigated [16], but also the effect
49 of the load history on the timber mechanical properties [17] and the potential reuse of reclaimed
50 timber [18–23] or poles [24,25] were studied.

51 In recent years, Japanese researchers demonstrated an increased interest in this field [26–36].

52 Nevertheless, the published results raise several questions because testing aged wood or timber is
53 influenced by different factors, such as:

54 1. initial properties (past) of the tested material are unknown, so it is difficult to compare them to
55 the actual properties (present).

56 2. the inherent natural wood variability may cover the influence of aging and preclude any definitive
57 conclusions. For instance, for small and clear specimens of the same species, bending strength
58 (MOR) and bending stiffness (MOE) can vary in the range of approximately 7-20% [37].

59 3. it is difficult to test large quantities of old material, as it is not easily available, especially
60 structural timber.

61 4. no single standardized procedure has been adopted for testing, so it may be difficult to find basis
62 of comparison between different works.

63 5. aging has a different effect on different species. For example, when testing small and clear
64 specimens of keyaki (*Zelkova serrata*, Makino) and hinoky (*Chamaecyparis obtusa*, Siebold &
65 Zucc), Kohara [8] obtained a MOE reduction of about 30% for the first species, and a MOE
66 increase for the second species during the first 300 years.

67 6. if the tested materials were exposed to particular environmental conditions allowing decay, their
68 mechanical properties can be affected even at an early stage [38]. However, early stage decay can
69 only be detected at microscopy level.

70 7. for structural timber damage resulting from the mounting/dismantling operations may affect the
71 original mechanical properties of timber [18,20,22,29,31,39].

72 8. the effect of the load history (duration of load) is well known for structural timber that remain in
73 service for long periods of time [40–42]. This effect must be taken into account when testing
74 material that has been in service, but it is erroneous to consider it as an aging effect [1].

75 Another important aspect concerning old timber structures is the possibility to assess the residual
76 mechanical properties of timber by means of visual inspection and non-destructive/semi-
77 destructive techniques. For example, the work of Sandoz and Vanackere [43] considers the use of
78 non-destructive measurements of moisture content and density in order to estimate the residual
79 strength of wood poles, whereas in Ross and Pellerin [44] a review is provided for non-destructive
80 assessment methods for testing wood members in structures, and in Baraneedaran et al. [45] a
81 review of methods including drilling, sounding, modal testing and stress wave propagation

82 technique are discussed for the assessment of in-service timber poles. More recent works have
83 provided guidelines and general information on both the prediction of the mechanical properties of
84 wood by use of semi-destructive methods [46] and also about the in situ assessment of historic
85 timber structures [47]. The application of these methods to in situ assessment and some of its
86 limitations are further discussed in [48] and in [49]. Globally it is accepted that the results obtained
87 through these methods have large variability, therefore they must be combined together as to
88 decrease its subjectivity for both an initial survey, as well as in more detailed surveys [50].
89 Moreover, the combination of methods should consider the mechanical property that is being
90 assessed, as well as the size scale of the analysis [51]. Nevertheless, it is common to use non-
91 destructive methods to assess the residual cross-section and also durability related issues (e.g.
92 level of biological attack) [52,53], therefore its present conditions, rather than to assess the effect
93 of the aging phenomena which must also consider the wood structure and its chemistry [54].
94 The goal of this paper is to discuss the relevant primary research literature, and summarize the
95 current understanding of the problem, as well as to provide recommendations for future research
96 on this topic. Literature investigating the mechanical properties affected by aging effects is
97 summarized in Table 1.

98 It can be perceived that different researchers understand the effect of aging in very different
99 perspective by simply reading the titles of the referenced works. The terms old wood/old timber,
100 historical timber, aging of wood, effect of time, are used in research works carried out with the
101 same aim: to compare the mechanical properties of wood of different ages. However, there are
102 differences between these concepts that should be considered. What can be considered as old
103 wood (or old timbers)? When a timber element should be considered historical or remain simply
104 old?. Some have investigated the aging phenomena, including the effect of the load history and in-
105 service condition on the mechanical properties of timber [36,55,56]; while others have investigated
106 aging of wood, considering only the effect of the “age” on the mechanical properties of wood
107 [1,30,57]. In literature two main approaches were found: i) consideration of small clear specimens,
108 and ii) consideration of structural size elements with intended use of reutilization. The research
109 works using small and clear specimens were carried out aiming at the analysis of the aging effect

110 on the wood mechanical properties for different grain directions. The advantages using such
111 specimens are related to their lower variability and wider availability comparing to larger size
112 elements including natural defects. Moreover, small test samples allow for easier, cheaper and
113 more standardized test setups. Anyway, when small specimens are extracted from timber
114 elements that had been in service, the duration of load effect must be taken into account, as well
115 as the position of the specimens inside the original element.

116 On the other hand, research works were carried out on structural size elements in order to
117 investigate the perspective to reuse them (for instance for salvaged poles or timbers), including not
118 only the analysis of the mechanical properties, but also aiming at the development of applicable
119 visual strength grading rules. In this case, the mechanical properties of the element are not only
120 affected by the natural aging phenomena, , but also by other factors like the duration of load
121 (DOL), the state of conservation and the presence of damages.

122

123 **2. Mechanical properties variation**

124 **2.1 Bending stiffness (MOE)**

125 A large number of authors agree on the fact that the MOE remains unchanged, or that it is not
126 significantly affected, over time. In the analysed literature, 20 research works reported that MOE
127 increased or remained unchanged over time, while only 5 reported a MOE decrease. The average
128 MOE variation between old and new wood/timber is summarized in Fig. 1.

129 The highest MOE increase, of about 11% and 27%, is reported in [27] where the authors compared
130 new and 270/290 years old small specimen of akamatsu (*Pinus densiflora*, Siebold & Zucc).

131 Contrary results are reported in [4] where Kohara reported a MOE decrease of about 25% for
132 keyaki. Later, Kohara [8] found that the MOE increased during the first 300 years testing hinoki
133 small specimens.

134 The highest MOE decrease was found in [58] where Cai et al. compared the edgewise and flatwise
135 bending MOE of 9 old Loblolly pine (*Pinus taeda* L.) joists 90 years old, to new timber of southern
136 pine. The new and old joists were tested in similar conditions of density and moisture content (MC).

137 The old joists' MOE was of approximately 15 and 42% lower for the flatwise and edgewise MOE,
138 respectively.

139 Smith [23] tested 200 structural joists and small specimens (species not identified) from 40 to 160
140 years old, for the calculation of bending MOE and MOR. A comparison between old wood and new
141 wood was made to infer about the mechanical properties variation. In that work, new wood was
142 selected on the basis of similarity to the density range of the salvaged timber, without considering
143 the species itself, so it is not possible to prove that the salvaged timber and new timber were from
144 the same species (nor that the salvaged species were the same species or not). Moreover, the
145 density of the new timber was between 433 and 490 kg/m³ while the salvaged joist density varied
146 in the range of 400-750 kg/m³. Additionally, the MOE was calculated incrementing the load from
147 1000 to 10000 N (1000 N for each increment), waiting 30 seconds from one step to the following.
148 The final load-displacement graph used for the MOE calculation is biased from the viscoelastic
149 deformation of wood under load, and the MOE is not calculated on the base of a pure elastic
150 deformation.

151 It is interesting to note that, among the carried out research works on old structural timber, no one
152 recorded a higher MOE compared to new timber, confirming the in-service influence on the
153 mechanical properties.

154 MOE decrease was also observed by several authors testing small and clear specimens: -15%
155 [27]; -25% [4]; -12% [25].

156

157 **2.2 Bending strength (MOR)**

158 Larger part of literature reported no MOR decrease. The other ones reported a MOR decrease
159 between 7 to 60% (Fig. 2). A clear trend cannot be found for small specimens nor for structural
160 timber.

161 Chini et al. [21] tested 32 structural members of southern pine with around 85 years in 3 point
162 bending tests. The timber elements were obtained from different buildings. The average allowable
163 MOR for salvaged timber was around 15% higher than new wood, showing a very high variability in
164 function of the timber construction origin (from 67-117% of the new timber MOR). For this

165 research, the great difference in density, between old timber and new timber (new wood density
166 was more than 50% lower), does not allow to make any consistent conclusion about the results.
167 Similarly Falk et al [19] tested 100 old joists with 90 years (53 were of Douglas-fir and 25 of Hem-
168 fir) for the MOE and MOR calculation. The elements have been dismantled from military buildings.
169 The calculated data were compared to the characteristics value for the in-grade study, assigned to
170 the tested material according to the applied grading rule. According to that comparison, the authors
171 concluded that strength parameters were lower than expected.

172 Falk [18] performed bending tests in 90 timber beams with 55 years old, where 30 of them
173 presented heart checks and 60 did not. It was found that the bending strength of checked beams
174 was 15% lower than the beams without checks.

175 Nakajima [31] tested 633 lumbers salvaged from two different deconstructed buildings. All the
176 lumbers were visually graded and the bending strength calculated in 4 point bending tests. The
177 mechanical properties were compared to the ones reported for new solid timber by Japanese
178 grading rules resulting in a 13% lower bending strength for salvaged timber. Moreover, a relation
179 between lower bending strength and nail holes was found.

180 Rammer [20] tested 69 Douglas fir lumbers salvaged from a dismantled military building. 40 pieces
181 were tested in 5 point bending test as to calculate the shear strength, whereas 29 pieces were
182 tested in four point bending tests as to calculate the bending strength. The research was carried
183 out to investigate the effect of split and checks on both the shear and bending strength. The author
184 observed that the bending strength decreased significantly. and that shear strength was negatively
185 affected by the presence of split and checks.

186 In the case of Schultz et al [59], no difference was found for MOR between new and 300 years old
187 Norway spruce (*Picea abies*, Karst.) structural timber. Whereas, Hirashima et al [27] observed a
188 MOR increase for 270 and 290 years old akamatsu specimens (17 and 42%, respectively), when
189 testing small size specimens.

190 Crews and Mackenzie [22] investigated the possibilities to reuse salvaged timber testing 90
191 specimens extracted from structural timber considering the extraction of specimens from different
192 cross section locations (from the compressed face, from the tensioned face and from the lateral

193 faces). The timber elements came from different structures that had been subjected to different
194 load levels. The specimens were graded and tested in bending with results evidencing a lower
195 MOR (35-50%) compared to new timber, also attending to different load magnitudes. Similarly,
196 Smith [23] reported that MOR decreased about 20% as a consequence of the load history effect for
197 both structural timber and small specimens.

198 Except for [20,22,31], that reported only MOR reduction but no MOE reduction, in the other cases
199 MOE and MOR evidenced the same behaviour: i) no variation was found in [1,17,24,26,27,36,60];
200 ii) minor variation was found in [30,34]; iii) decrease for both MOR and MOE was found in
201 [4,27,55]. Since the MOE and MOR are related, this seems to suggest that the differences
202 between old and new wood are much more related to the original quality of the tested material,
203 rather than to the effect of aging itself. The research works in which MOR reduction is observed
204 and MOE remains unchanged [20,31] were carried out on structural timber, confirming that load
205 history has a more significant influence on MOR rather than on MOE.

206

207 **2.3 Compressive strength**

208 Kohara [4] reported a compressive strength reduction of about 15% testing small and clear
209 specimens. Also, Yorur et al. [56] reported a compressive strength reduction up to 27%, testing
210 small specimens of *Pinus sylvestris*, L., but in this case the results are compromised by different
211 densities ranges between the old and new wood specimens (new wood was 18% denser).

212 The comparison between new and old wood is quite difficult because compressive strength is
213 largely affected by density. The already mentioned work by Kohara [4] reports a compressive
214 strength reduction, obtained comparing new and aged specimens with a different mean density of
215 about 12% on the new wood side, probably explaining a large part of the reported strength
216 difference.

217 The other analyzed researches reported no compressive strength variation [12–15,36], a slight
218 increase [11,55,61] or a significant compressive strength increase [62,63].

219 On the structural size, Falk [18] selected around 60 timber columns, with and without checks, and
220 tested them in compression. On that study, all columns were found to have higher strength than

221 expected by the specific grading rule [64]. A schematic representation of the compressive strength
222 variation is showed in Fig. 3.

223

224

225

226 **2.4 Tensile strength**

227 Since the tensile strength of wood in longitudinal direction is very high compared to the other
228 directions, only occasionally it is a limiting design factor, and thus few research works were made
229 regarding the age effect on this property. Only Attar-Hassan [55] reports a clear tensile strength
230 reduction of about 29%, observed while testing small clear specimens. However, other works
231 present significant different outcomes on their results. In [11] a lower tensile strength, comparing
232 old wood to new wood, was reported for Norway spruce with density up to 520 kg/m^3 , whereas
233 higher tensile strength for density above 520 kg/m^3 was found. Hirashima [57] did not found a clear
234 relation between age and tensile strength on akamatsu specimens, as no variation was found for
235 115 years old specimens comparing to new wood, while 29% reduction for 270 years old
236 specimens and 18% reduction for 290 years old specimens was found.

237 The low number of research works and the discordant results do not allow to draw a clear
238 conclusion about the aging phenomena effect on tensile strength.

239

240 **2.5 Tensile and compressive MOE**

241 Ooka et al [36] tested small specimens of keyaki, hinoki and akamatsu in compression
242 perpendicular to the grain, aiming at calculating the MOE. The specimens were taken from timber
243 members rescued from Japanese traditional buildings, with 90 to 365 years old. In this case, the
244 calculated MOE was found to be similar to the one of new wood.

245 Froidevaux et al [65] tested 200-500 years old Norway spruce small and clear radial specimens in
246 tensile test, in order to verify the elastic, creep, relaxation and rupture behaviour under controlled
247 temperature and relative humidity. Authors reported that it was not possible to observe a clear
248 aging effect. Moreover, a significant higher MOE was obtained for the specimens from wood

249 coming from a parquet floor, compared to wood coming from structural timber, suggesting a
250 combined effect of age, load history and defect presence also on tensile properties.

251

252

253

254 **2.6 Shear strength**

255 Also in the case of shear strength the results are not concordant between different researches. In
256 [12,28] no shear strength variation was reported comparing new and old specimens of respectively
257 120 and 270 years, while Attar-Hassan [55] reported a shear strength increase of about 17%. Only
258 Chini et al [21] and Kohara [4] agreed, reporting a shear strength reduction of about 25%.

259 However, the causes of this reduction were attributed to more reasons rather than solely to aging.

260 As instance, the first author obtained its results by testing 32 small specimens extracted from 4

261 different old beams, ascribing the reduction in shear strength, mainly, to the presence of bolt and

262 nails hole.

263 Rammer [20] records that shear strength is negatively affected by the presence of split and checks

264 on salvaged Douglas fir lumbers.

265

266 **2.7 Impact bending strength**

267 Impact bending strength calculated on small specimens is affected by density and MC, but the
268 effect of the testing methods is much more important than the mentioned factors [66]. Although it is
269 quite difficult to compare the different research works, due to the different materials and
270 methodologies (meaning different MC, density and test methods), the analyzed literature
271 evidences that impact bending strength is largely affected by aging, as only Kränitz [1] reported no
272 significant variation for aged specimens impact bending strength. All the other authors reported a
273 significant reduction [4,50,57] with values up to 70% [9] obtained while testing small and clear
274 specimens of hinoki and keyaki aged up to 1300 and 650 years respectively. Also, Kollmann and
275 Schmidt [10] observed an impact bending strength reduction when testing small specimens of pitch
276 pine, extracted from 30 years old damaged wooden pillars.

277

278 **3. Salvaged timber**

279 A significant number of the research works investigated the performance of salvaged materials
280 comparing their properties to new timber, testing structural members. In this case the effect of age
281 is not always an important parameter as mentioned by [29,31,68] when testing material up to 20
282 years old.

283 In the work of [69], the main goal was to assess the potential reuse of rescued timber or poles,
284 according to their positive environmental effect and economical, direct and indirect, benefits. In this
285 case the mechanical properties variation is influenced by different factors, such as the duration of
286 load, aging, in-service conditions and the state of conservation. All the researchers tested the
287 bending mechanical properties of the rescued materials founding that the bending strength
288 decreases. This is probably a consequence of the DOL effect, and of the damages due to
289 mounting and dismantling operations. Only Cai et al [58] observed a MOE reduction testing
290 salvaged joists, the other researchers found no MOE variation.

291 Anyway, the research works outlined that many of the dismantled timber members can be reused,
292 according to the residual mechanical properties and effective cross-section.

293

294 **4. Strength reduction causes**

295 Kohara and Okamoto [9] speculated that the mechanical properties variation of wood due to aging,
296 is a consequence of the change in the microstructure of wood. They reported a decrease in the
297 amount of “cellulosic materials”, attributing the enhanced stiffness of aged wood to the cellulose
298 crystallinity, observing an increment in the crystallinity for the first 100 years, followed by a
299 progressive decrease.

300 This hypothesis was not confirmed by other studies, as instance Noguchi et al [35] reported that
301 the Kohara’s hypothesis does not sufficiently explain the aging process, because the viscoelastic
302 properties of amorphous matrix substances in the wood cell wall also play an important role on
303 variation of the mechanical properties. Additionally, other authors report no significant variation in
304 crystallinity between aged and new wood of hinoki [70] or for other wood species [28,32,71].

305 Krånitz [1], analysing the relevant literature, reports that many authors confirm the general increase
306 of cellulose crystallinity over the long term.

307 The other principal source of strength reduction is related to the load history effect and confirmed
308 by the studies carried out on structural material [17,40,42].

309 **5. Testing recommendations**

310 The various ways in which the tests were carried out, and the lack of information about the
311 specimens, makes it difficult to compare the results of different research works. Therefore, it will be
312 useful, for further works, to follow a common approach that may be based on the following
313 recommendations:

- 314 a. The tested species should be reported as well as the dimensions of the specimens. The
315 size of the specimens affects the prediction of the mechanical properties and should,
316 therefore, be considered in the grading protocol [72].
- 317 b. Since different research works use the term “old” in different way, also the age of the
318 material used for testing should be reported.
- 319 c. Origin of the elements should be reported with respect to the provenience of the wood and
320 the location of the structure where they were used.
- 321 d. When new and old wood is compared, they should be as similar as possible for basic
322 characteristics, like density, moisture content and overall quality; otherwise it could be
323 difficult to ascribe any difference, in the mechanical properties, to other factors.
- 324 e. For small specimens it is useful to know from which kind of material they were extracted
325 from, and its location on the original element, to take into account the potential DOL effect.
- 326 f. Since early stage decay has a significant effect on some mechanical properties, it should
327 be assessed carefully.
- 328 g. For long-term experimental campaigns, a sample of elements should be used for
329 determination of a reference property using non-destructive testing (e.g. determination of
330 bending MOE in elastic field) as to allow for a basis of comparison and correlation between
331 tests made at different ages.

- 332 h. Methods of survey may limit the quality of the assessment of the mechanical properties,
333 therefore the same procedure and methods must be considered to assess old and new
334 wood, as to obtain a reliable basis for comparison.
- 335 i. A combination of different measuring methods is recommendable in order to decrease the
336 variability of the analysis.

337 **6. Conclusions**

338 Many research works investigated the mechanical properties variation of wood over time, on
339 different scales (small specimens and structural timber), and the possibilities to reuse salvaged
340 timber. The results are not always in agreement, as a consequence of the complexity to compare
341 the mechanical properties of old and new wood/timber due to the high variability on the mechanical
342 properties, the uncertainty about the original mechanical properties of old wood and timber, and
343 the effect of different factors, like the duration of load and the state of conservation. Additionally, in
344 many cases, the lack of information and the use of non-standardized tests makes it difficult to
345 make solid comparisons.

346 The mechanical properties in bending were largely investigated and the majority of research works
347 agreed on the fact that the bending strength and bending stiffness remain unchanged over the
348 time, or decrease in a not significant way. Highest bending MOE and MOR reductions are reported
349 for structural timber, which is affected by the in-service condition, such as duration of load, state of
350 conservation and dismantling damages, that are not a direct consequence of aging.

351 Besides bending MOE and MOR, only a reduced number of research works investigated other
352 mechanical properties variation, so it is not possible to draw definite conclusions. The compressive
353 strength seems to remain unchanged, although the published results are, sometimes, influenced
354 by an important density difference between the compared new and old specimens. Few
355 researchers investigated the tensile strength obtaining completely different results. Nevertheless,
356 tensile and compressive MOE seem to remain unchanged over time. Also for shear strength it was
357 not possible to reach a definite conclusion due to the limited number of research works. The
358 published research works seem to agree on the fact that the impact bending strength is largely
359 affected by aging.

360 The effect of time on the mechanical properties of salvaged timber and poles is quite complex,
361 because the mechanical properties of timber that remained in service for many years, are a
362 consequence of several interacting factors, namely the state of conservation, the load history, the
363 original quality of the material and the damages occurred during the service life or the
364 mounting/dismantling operations. However, this material can still be reused in structures, according
365 to the residual mechanical properties and effective cross-section.

366

367

368 **References**

- 369 [1] K. Kranitz, Effect of natural aging on wood. Doctoral thesis, University of West Hungary,
370 2014.
- 371 [2] J. Kohara, Studies on the durability of wood I, mechanical properties of old timbers, , vol. 2,
372 1, Bull. Kyoto Prefect. Univ. 2 (1952) 116–131.
- 373 [3] J. Kohara, Studies on the permanence of wood V, shrinkage and swelling of old timbers
374 about 300-1300 years ago (in Japanese), Bull. Kyoto Prefect. Univ. 5 (1953) 81–88.
- 375 [4] J. Kohara, Studies on the durability of wood III: mechanical properties of old timbers, Sci.
376 Reports Saikyo Univ. 4 (1953) 98–109.
- 377 [5] J. Kohara, Studies on the permanence of wood VI, the changes of mechanical properties of
378 old timbers (in Japanese), Bull. Kyoto Prefect. Univ. 6 (1954) 164–174.
- 379 [6] J. Kohara, Studies on the permanence of wood VII, the influence of age on the components
380 of wood (*Chamaecyparis obtusa* Endlicher) (in Japanese), Bull. Kyoto Prefect. Univ. 6
381 (1954).
- 382 [7] J. Kohara, Studies on the permanence of wood XV, the influence of age on the components
383 of wood (*Zelkova serrata* Makino) (in Japanese), Mokuzaï Gakkaishi. 1 (1955) 21–24.
- 384 [8] J. Kohara, On permanence of wood II, differences between the ageing processes of cypress
385 wood and zelkova wood (in Japanese), Wood Ind. 10 (1955) 395–399.
- 386 [9] Kohara, Okamoto, Studies of Japanese old timbers, Sci Rep Saikyo Univ 7(1a) 9-20. 7
387 (1955) 9–20.
- 388 [10] F. Kollmann, E. Schmidt, Gefügezerrüttung und festigkeitseinbuße von
389 dauerbeanspruchtem nadelholz, Holz Als Roh- Und Werkst. 20 (1962) 333–338.
- 390 [11] H. Schultz, H. von Aufseb, T. Verron, Eigenschaften eines fichtenbalkens aus altem
391 dachstuhl, Holz Als Roh- Und Werkst. 19 (1979) 47–50.
- 392 [12] J. Kuipers, Effect of age and/or load on timber strength, in: CIB W18, Meet. 18, Florence,
393 Italy, 1986.
- 394 [13] J. Ehlbeck, R. Grolacher, Die tragfähigkeit von altem konstruktionsholz - Problematik der
395 beurteilung, in: Bau. Mit Holz, 1990.
- 396 [14] W. Rug, A. Seemann, Strength of old timber, Build. Res. Inf. 19 (1991) 31–37.
- 397 [15] H.J. Deppe, H. Ruhl, Evaluation of historical construction timber. 1. Density and
398 compression, Holz Als Roh- Und Werkst. 51 (1993) 379–383.
- 399 [16] D. Erhardt, M.F. Mecklenburg, C.S. Tumosa, T.M. Olstad, New versus old wood: differences

- 400 and similarities in physical, mechanical, and chemical properties, in: Int. Counc. Museums-
401 Committee Conserv. 11th Trienn. Meet., London, UK, 1996: pp. 903–910.
- 402 [17] K. Fridley, J. Mitchell, M. Hunt, J. Senft, Effect of 85 years of service on mechanical
403 properties of timber roof members 1 Experimental observations, *For. Prod. J.* 46 (1996) 72–
404 78.
- 405 [18] R.H. Falk, The properties of lumber and timber recycled from deconstructed buildings, in:
406 PTEC 99 - PACIFIC TIMBER Eng. Conf., G. B. Walford and D. J. Gaunt, Rotorua, New
407 Zeland, 1999: pp. 255–258.
- 408 [19] R.H. Falk, D. DeVisser, S. Cook, D. Stansbury, Effect of damage on the grade yield of
409 recycled lumber, *For. Prod. J.* 49 (1999) 71–79.
- 410 [20] D.R. Rammer, Evaluation of recycled timber members, in: L.C. Bank (Ed.), 5th ASCE Mater.
411 Eng. Congr., ASCE, Cincinnati, Ohio, 1999: p. 7.
- 412 [21] A.R. Chini, L. Acquaye, M.E. Rinker, Deconstruction and materials reuse: technology,
413 economic, and policy (CIB Publication 266), in: C.R. Abdol (Ed.), CIB Task Gr. 39
414 Deconstruction Meet., Wellington, 2001: pp. 138–161.
- 415 [22] K. Crews, C. Mackenzie, Development of grading rules for re-cycled timber used in
416 structural applications, in: WCTE2008 - 10th World Conf. Timber Eng., 2008.
- 417 [23] M.J. Smith, An investigation into the strength properties of reclaimed timber joists. Doctoral
418 Thesis, Northumbria University, 2012.
- 419 [24] R.J. Leichti, M. Meisenzahl, D. Parry, Structural timbers from retired Douglas-fir utility poles.,
420 *For. Prod. J.* 55 (2005) 61–65.
- 421 [25] C. Piao, T.F. Shupe, L. Groom, W.A. Nipper, Research update for the treated wood reusing
422 program at the Calhoun Research Station, in: 105th Annu. Meet. Am. Wood Prot. Assoc.,
423 2009: pp. 209–215.
- 424 [26] H. Horie, Strength deterioration of recycled lumber collected from demolition wooden
425 buildings in Hokkaido, *Mokuzai Gakkaishi.* 48 (2002) 280–287.
- 426 [27] Y. Hirashima, M. Sugihara, Y. Sasaki, A. Kosei, M. Yamasaki, Strength properties of aged
427 wood III: static and impact bending strength properties of aged keyaki and akamatsu woods,
428 *Mokuzai Gakkaishi.* 51 (2005) 146–152.
- 429 [28] K. Ando, Y. Hirashima, M. Sugihara, S. Hirao, Y. Sasaki, Microscopic processes of shearing
430 fracture of old wood, examined using the acoustic emission technique, *J. Wood Sci.* 52
431 (2006) 483–489. doi:10.1007/s10086-005-0795-7.
- 432 [29] C.J. Lin, T.H. Yang, D.Z. Zhang, S.Y. Wang, F.C. Lin, Changes in the dynamic modulus of
433 elasticity and bending properties of railroad ties after 20 years of service in Taiwan, *Build.*
434 *Environ.* 42 (2007) 1250–1256. doi:10.1016/j.buildenv.2005.11.031.
- 435 [30] S. Kawai, M. Yokoyama, M. Matsuo, J. Sugiyama, Research on the aging of wood in rish, in:
436 *Wood Sci. Conserv. Cult. Herit.*, 2008: pp. 52–56.
- 437 [31] S. Nakajima, Comparison of two structural reuse options of two-by-four salvaged lumbers,
438 in: WCTE 2010 - World Conf. Timber Eng. - World Conf. Timber Eng., 2008: pp. 1085–1090.
- 439 [32] Y. Saito, S. Shida, M. Ohta, H. Yamamoto, T. Tai, W. Ohmura, et al., Deterioration character
440 of aged timbers insect damage and material aging of rafters in a historic building of
441 Fukushoji-temple, *Mokuzai Gakkaishi.* 54 (2008) 255–262.
- 442 [33] E. Obataya, Effects of ageing and heating on the mechanical properties of wood, *Wood Sci.*
443 *Conserv. Cult. Herit.* 8 (2009) 16–23.
- 444 [34] M. Yokoyama, J. Gril, M. Matsuo, H. Yano, J. Sugiyama, B. Clair, et al., Mechanical
445 characteristics of aged Hinoki wood from Japanese historical buildings, *Phys. Herit.* 10
446 (2009) 601–611.
- 447 [35] T. Noguchi, E. Obataya, K. Ando, Effects of ageing on the vibrational properties of akamatsu

- 448 (Pinus densiflora) wood, Wood Cult. Sci. Kyoto. (2011) 6.
- 449 [36] Y. Ooka, H. Tanahashi, K. Izuno, Y. Suzuki, K. Toki, Effects of aged wooden members on
450 seismic performance of old traditional wooden structures, in: 15th World Conf. Earthq. Eng.,
451 2012.
- 452 [37] F.P.L. Department of Agriculture, Forest Service, Wood Handbook, Wood as an Engineering
453 Material, Madison, WI: U.S., 2010.
- 454 [38] W.W. Wilcox, Review of literature on the effects of early stages of decay on wood strength,
455 Wood Fiber. 9 (1978) 252–257.
- 456 [39] A. Ceccotti, M. Togni, NDT on ancient timber beams: assessment of strength/ stiffness
457 properties combining visual and instrumental methods, in: 10th Int. Symp. Nondestruct.
458 Test. Wood, 1996.
- 459 [40] L.W. Wood, Relation of strength of wood to duration of load, For. Prod. Lab. Serv. U. S.
460 Dep. Agric. R1916 (1951) 10.
- 461 [41] C.C. Gerhards, Effect of Duration and Rate of Loading on Strength of Wood and Wood-
462 Based Materials, USDA For. SERVICE Res. FPL 283. FPL 283 (1977) 26.
- 463 [42] P. Hoffmeyer, J.D. Sørensen, Duration of load revisited, Wood Sci. Technol. 41 (2007) 687–
464 711. doi:10.1007/s00226-007-0154-5.
- 465 [43] J.L. Sandoz, O. Vanackere, Wood poles ageing and non destructive testing tool. In
466 Electricity Distribution CIRED. 14th International Conference and Exhibition on (IEE Conf.
467 Publ. No. 438) (Vol. 3, pp. 26-1). IET., in: CIRED -14th Int. Conf. Exhib. Electr. Distrib. (IEE
468 Conf. Publ. No. 438), 1997: pp. 26–1.
- 469 [44] R.J. Ross, R.F. Pellerin, Nondestructive Testing for Assessing Wood Members in Structures
470 A Review, Madison, WI: U.S., 1994.
- 471 [45] S. Baraneedaran, E.F. Gad, I. Flatley, A. Kamiran, J.L. Wilson, Review of in-service
472 assessment of timber poles, in: Proc. Aust. Earthq. Eng. Soc., Newcastle, 2009.
- 473 [46] M. Kloiber, M. Drdàckya, J.S. Machado, M. Piazza, N. Yamaguchi, Prediction of mechanical
474 properties by means of semi-destructive methods: A review, Constr. Build. Mater. 101 (2015)
475 1215–1234.
- 476 [47] H. Cruz, D. Yeomans, E. Tsakanika, N. Macchioni, A. Jorissen, M.C. Touza Vazquez, et al.,
477 Guidelines for the on-site assessment of historic timber structures, Int. J. Archit. Herit. 9
478 (2015) 277–289. doi:10.1080/15583058.2013.774070.
- 479 [48] L. Yan, Z. Houjiang, Research Situation and Trend on Non-Destructive Testing Method of
480 Wood Material Mechanical Properties [J], For. Eng. 04 (2010) 12.
- 481 [49] P. Niemz, D. Mannes, Non-destructive testing of wood and wood-based materials, J. Cult.
482 Herit. 13 (2012) s26–s34.
- 483 [50] A.O. Feio, J.S. Machado, In-situ assessment of timber structural members: Combining
484 information from visual strength grading and NDT/SDT methods—A review, Constr. Build.
485 Mater. 101 (2015) 1157–1165.
- 486 [51] H.S. Sousa, J.S. Machado, J.M. Branco, P.B. Lourenço, Onsite assessment of structural
487 timber members by means of hierarchical models and probabilistic methods, Constr. Build.
488 Mater. 101 (2015) 1188–1196.
- 489 [52] D. Hunt, Properties of wood in the conservation of historical wooden artifacts, J. Cult. Herit.
490 13 (2012) s10–s15.
- 491 [53] H.S. Sousa, J.M. Branco, P.B. Lourenço, Characterization of cross-sections from old
492 chestnut beams weakened by decay, Int. J. Archit. Herit. 8 (2014) 436–451.
- 493 [54] T. Nilsson, R. Rowell, Historical wood—structure and properties, J. Cult. Herit. 13 (2012) s5–
494 s9.
- 495 [55] G. Attar-Hassan, The effect of ageing on the mechanical properties of eastern white pine,


- 496 Assoc. Preserv. Technol. Int. 8 (1976) 64–73.
- 497 [56] H. Yorur, S. Kurt, I. Yumrutas, The Effect of Aging on Various Physical and Mechanical
498 Properties of Scotch Pine Wood Used in Construction of Historical Safranbolu Houses, *Drv.*
499 *Ind.* 65 (2014) 191–196. doi:10.5552/drind.2014.1328.
- 500 [57] Y. Hirashima, M. Sugihara, Y. Sasaki, K. Ando, M. Yamasaki, strenght propoerties of aged
501 wood,l: tensile strength properties of aged keyazi [*Zelkova serrata*] and akamatsu [*Pinus*
502 *densiflora*] woods, *Mokuzai Gakkaishi.* 50 (1955).
- 503 [58] Z. Cai, M.O. Hunt, R.J. Ross, L. a Soltis, Static and vibration moduli of elasticity of salvaged
504 and new joists, *For. Prod. J.* 50 (2000) 35–40.
- 505 [59] D. Nicholas, J. Shi, T. Schultz, Evaluation of variables that influence dynamic moe in wood
506 decay studies, in: *Int. Res. Gr. WOOD Prot. - 40th Annu. Meet., Beijing, China, 2009:* p. 8.
- 507 [60] W. Sonderegger, K. Kránitz, C.-T. Bues, P. Niemz, Aging effects on physical and
508 mechanical properties of spruce, fir and oak wood, *J. Cult. Herit.* (2015).
509 doi:10.1016/j.culher.2015.02.002.
- 510 [61] D. Narayanamurti, S.S. Ghosh, B.N. Prasad, J. George, Untersuchungen an einer alten
511 Holzprobe, *Holz Als Roh- Und Werkst.* 16 (1958) 19–21.
- 512 [62] A.O. Feio, P.B. Lourenço, J.S. Machado, Non-Destructive Evaluation of the Mechanical
513 Behavior of Chestnut Wood in Tension and Compression Parallel to Grain, *Int. J. Archit.*
514 *Herit.* 1 (2007) 272–292. doi:10.1080/15583050701300475.
- 515 [63] P. Witomski, A. Krajewski, P. Kozakiewicz, Selected mechanical properties of Scots pine
516 wood from antique churches of Central Poland, *Eur. J. Wood Wood Prod.* 72 (2014) 293–
517 296. doi:10.1007/s00107-014-0783-y.
- 518 [64] WCLIB, Grading rules for West Coast lumber. Standard No. 17. West Coast Lumber
519 Inspection Bureau, Portland, Oreg, West Coast Lumber Insp. Bur. Portland, Oreg. (1996).
- 520 [65] J. Froidevaux, T. Volkmer, K. Anheuser, P. Navi, Viscoelasticity behavior of modern and
521 aged wood, in: *COST Action IE0601, Izmir Int. Conf. Viscoelasticity Behav. Mod. Aged*
522 *Wood Julien, 2010.*
- 523 [66] N.H. Kloot, The effect of moisture content on the impact strength of wood, *Aust. J. Appl. Sci.*
524 5 (1954) 183–186.
- 525 [67] H. Weimar, Aspekte der stofflichen charakterisierung von altholz. MSc thesis. Hamburg,
526 Universität Hamburg., 2000.
- 527 [68] C. Piao, T.F. Shupe, C.Y. Hse, R.C. Tang, Nondestructive Evaluation of Young ' s Moduli of
528 Full-Size Wood Laminated Composite Poles, in: *7th Pacific Rim Bio-Based Compos. Symp.,*
529 *Science & Tecnique Literature Press, Nanjing, China, 2004:* pp. 291–298.
- 530 [69] J. Brandon Davis, Suitability of Salvaged Timber in Structural Design. Master Thesys. Civil
531 and Environmental Engineering. United States Military Academia. Massachussetts Institute
532 of Technology, 42 pp., Massachusetts Institute of Technology, 2012.
- 533 [70] M. Yokoyama, J. Sugiyama, S. Kawai, Mechanical characteristics of aged Hinoki
534 (*Chamaecyparis obtusa* Endl.) wood from Japanese historical buildings, in: *Multidiscip.*
535 *Conserv. a Holist. View Hist. Inter., 2010:* pp. 1–10.
- 536 [71] T. Inagaki, H. Yonenobu, S. Tsuchikawa, Near-infrared spectroscopic monitoring of the
537 water adsorption/desorption process in modern and archaeological wood, *Appl. Spectrosc.*
538 62 (2008) 860–865.
- 539 [72] R.W. Anthony, K.D. Dugan, D.J. Anthony, A grading protocol for structural lumber and
540 timber in historic structures, *APT Bull.* 40 (2009) 3–9.
- 541

Table 1 – Summary of the literature investigating the aging effect on the mechanical properties of wood and timber.

reference	species	approximate age	mechanical properties*	specimens dimensions (wxhxL - cm ³)**
Ando et al. (2006)	<i>Pinus densiflora</i> , Sieb. et Zucc.	270	f_v	3x3x3
Attar-Hassan G (1976)	<i>Pinus strobus</i> , L.	142	E_t, f_c, f_m, f_v, f_t	12x15x230 (A)
Cai et al. (2000)	<i>Pinus taeda</i> , L.	90	E_t	5x3x90 (A)
Chini et al. (2001)	Southern pine	85	E_t, f_m, f_v	4.8x9.7x60 (A)
Crews et al. (2008)	hardwood	?	E_t, f_m	5x5x300-5x19x300
Deppe et al. (1993)	<i>Pinus sylvestris</i> , L.	600	f_c	-
Ehlbeck et al. (1990)	softwood	?	f_c	-
Erhardt et al. (1996)	<i>Pinus sylvestris</i> , L.	300-400	E_t	S
Falk (1999)	<i>Pseudotsuga menziesii</i> , (Mirb.) Franco	55	f_c, f_m	14x19x330 19x19x320
Falk et al. (1999)	<i>Pseudotsuga menziesii</i> , (Mirb.) Franco; <i>Tsuga heterophylla</i> (Raf.) Sarg.	90	E_t, f_m	5x25x490
Feio et al. (2007)	<i>Castanea sativa</i> , Mill.	?	f_c	5x5x10
Fridley et al. (1996)	?	85	E_t, f_m	S
Froidevaux et al. (2010)	<i>Picea abies</i> , Karst.	100-700	E_t, E_c	0.3x0.3x5
Hirashima et al. (1955)	<i>Zelkova serrata</i> , Makino; <i>Pinus densiflora</i> , Siebold & Zucc	115-290	f_t	S
Hirashima et al. (2005)	<i>Zelkova serrata</i> , Makino; <i>Pinus densiflora</i> , Siebold & Zucc	115-290	E_t, f_m, w	S
Horie (2002)	<i>Picea jezoensis</i> , (Siebold & Zucc.) Carr.; <i>Abies sachalinensis</i> , F.Schmidt	27 a 83	E_t, f_m	S
Kawai et al. (2008)	<i>Chamaecyparis obtusa</i> , (Siebold & Zucc.) Endl.	up to 1600	E_t, f_m, w	S
Kohara (1953-1955)	<i>Zelkova serrata</i> , Makino; <i>Chamaecyparis obtusa</i> , Siebold & Zucc	310-530	E_t, f_c, h, f_m, f_v, w	S
Kollmann et al. (1962)	pitch pines	30	E_t, w	L
Kranitz (2014)	<i>Picea abies</i> , Karst.; <i>Abies alba</i> , Mill.; oak	90-250	E_t, f_m, w	2x2x30
Kuipers (1986)	?	100-120	f_c, f_v	L
Leichti et al. (2005)	<i>Pseudotsuga menziesii</i> , (Mirb.) Franco	20-90	E_t, f_m	5x5x30
Lin et al. (2007)	<i>Cyclobalanopsis longinux</i> , (Hayata) Schottky; <i>Schima superba</i> , Gardner & Champ; <i>Castanopsis carlesii</i> , Hayata; <i>Litsea acuminata</i> (Teschner) Kosterm; <i>Cyclobalanopsis gilva</i> (Blume) Oerst.; <i>Pasania harlandii</i> , Hance	20	E_t, f_m	2x2x32

Nakajima (2008)	?	≈ 20	E_f, f_m	3.8x8.9x236
Narayanamurti et al. (1958)	<i>Tectona grandis</i> , L.f.	1800	f_c	S
Ooka et al. (2012)	<i>Zelkova serrata</i> , Makino; <i>Cryptomeria japonica</i> (L.f.) D.Don, <i>Chamaecyparis obtusa</i> , (Siebold & Zucc.) Endl.; <i>Pinus densiflora</i> , Siebold & Zucc	90-375	E_f, f_m, f_c, E_t, E_c	3x3x60
Piao et al. (2009)	southern pines	8 a 17	E_f, f_m	2x2x41
Rammer (1999)	<i>Pseudotsuga menziesii</i> , (Mirb.) Franco	?	E_f, f_m	15x35x540 25x46x530
Rug et al. (1991)	pine, oak, <i>Picea abies</i> , Karst.; <i>Fagus sylvatica</i> , L.	60-140	f_c	1.5 (diameter) x4 2x2x3
Schultz et al. (1979)	<i>Picea abies</i> , Karst.	>300	f_c, f_m, f_t	16x16x230


544 * E_f = bending MOE; f_m = bending strength; f_c = compressive strength; h = hardness parallel to the
545 grain; f_v = shear strength; f_t = tensile strength; w = impact bending strength; E_t/E_c = tensile or
546 compressive MOE; ? = unknown data. **A = average dimensions; S= small and clear specimens
547 (unknown dimensions); L= structural timber (unknown dimensions).

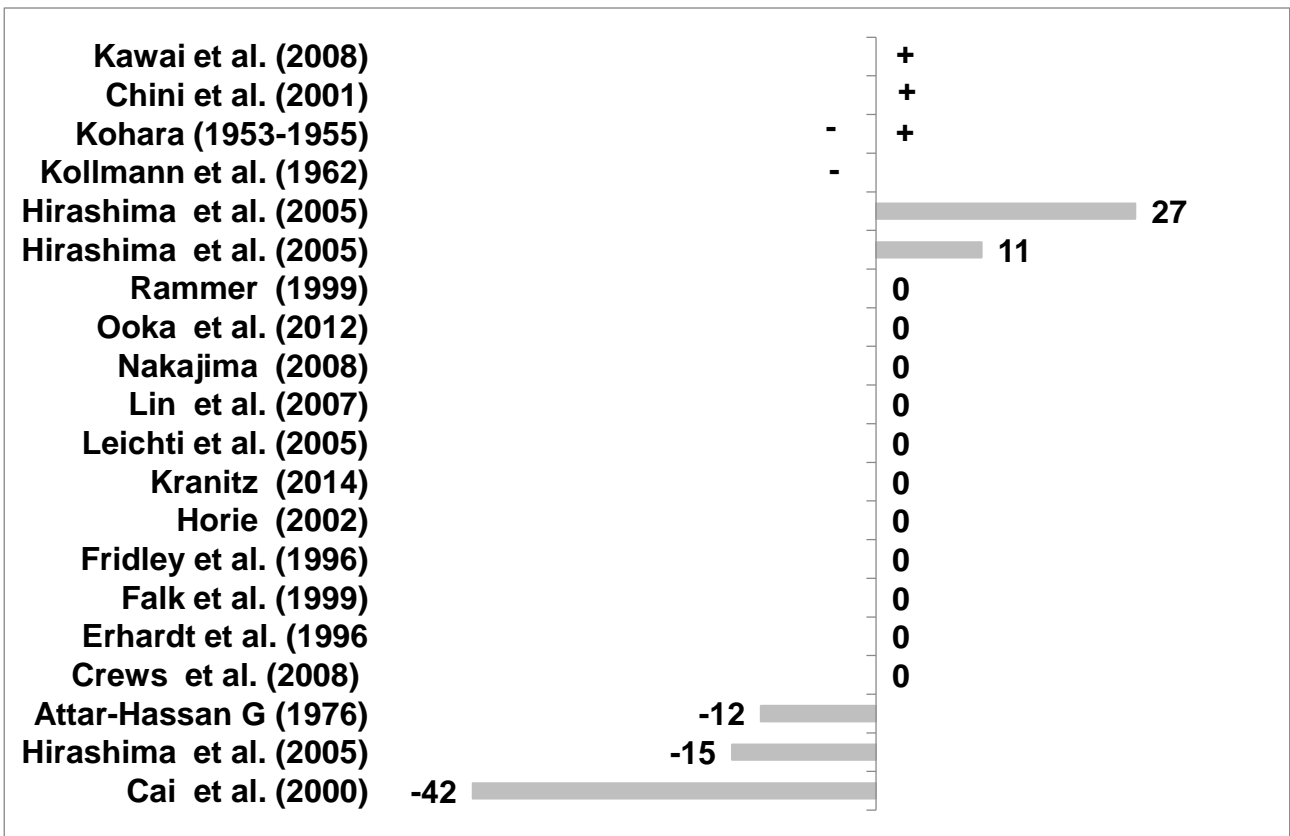

548

549
550
551

Fig. 1 – percentage difference between old and new wood/timber bending MOE. Positive values indicate higher MOE for old timber. When a specific value is not indicated in the research work, the trend is indicated as increment (+) or decrement (-).

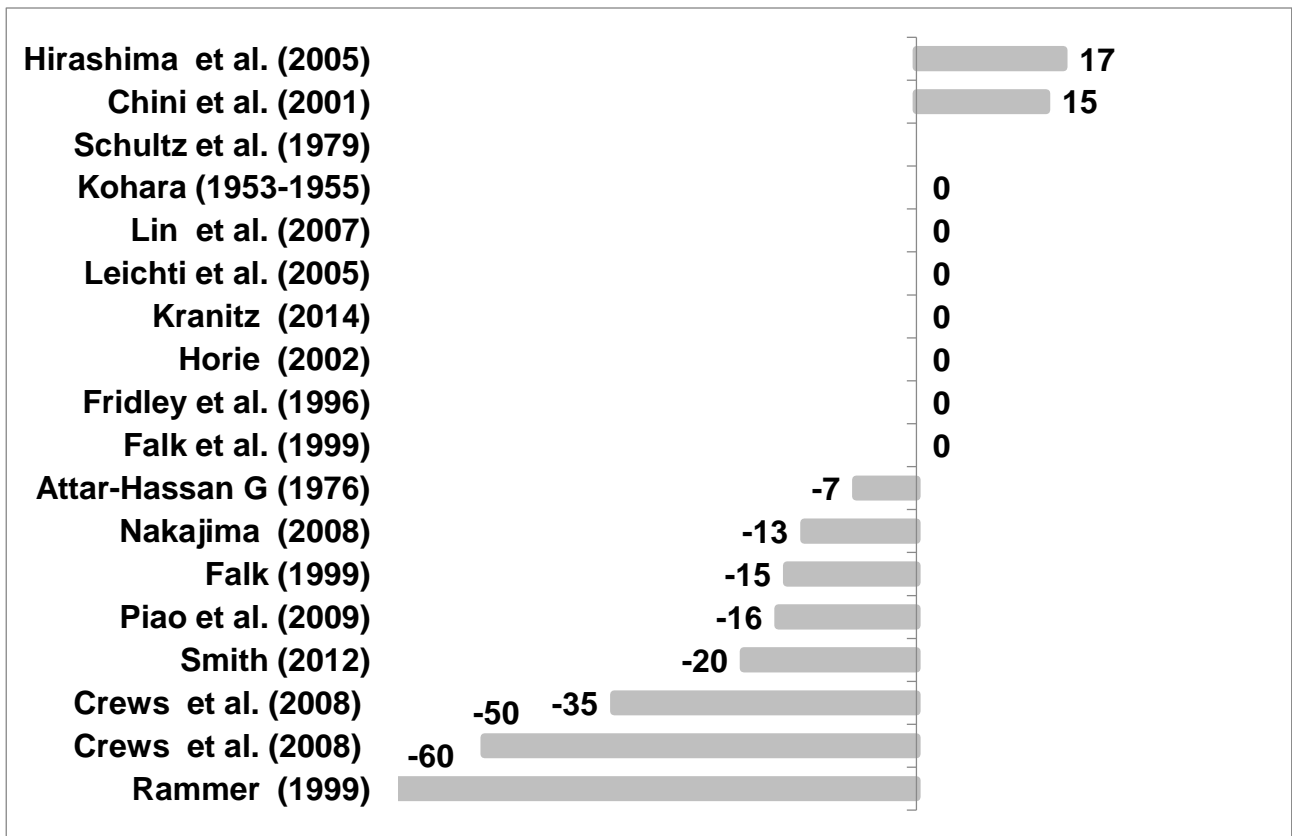


552

553

554

Fig 2 – percentage difference between old and new wood/timber bending strength (MOR). Positive values indicates higher MOR for old timber.

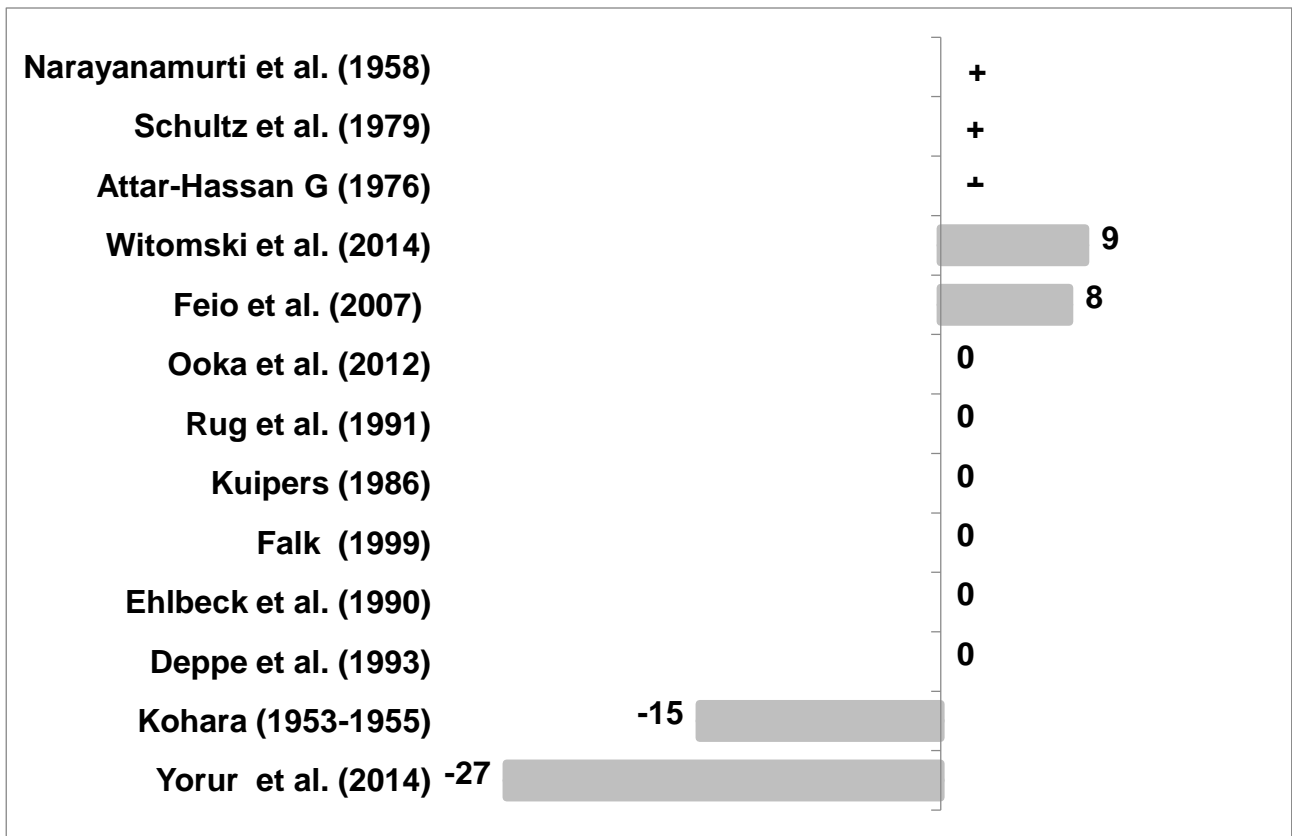

555

556
557
558

Fig 3 – percentage difference between old and new wood/timber compressive strength. Positive values indicates higher compressive strength for old timber. When a specific value is not indicated in the research work, the trend is indicated as increment (+) or decrement (-).