



University of Pennsylvania
ScholarlyCommons

Department of Physics Papers

Department of Physics

5-7-2010

NMR Measurements of Power-law Behavior in the Spin-wave and Critical Regions of Ferromagnetic EuO

N. Bykovetz

CECOM LCMC, AMSEL-SF-R

B. Birang

Brandeis University

J. Klein

University of Pennsylvania

C. L. Lin

Temple University

Follow this and additional works at: http://repository.upenn.edu/physics_papers

 Part of the [Physics Commons](#)

Recommended Citation

Bykovetz, N., Birang, B., Klein, J., & Lin, C. L. (2010). NMR Measurements of Power-law Behavior in the Spin-wave and Critical Regions of Ferromagnetic EuO. Retrieved from http://repository.upenn.edu/physics_papers/23

Suggested Citation:

Bykovetz, N., B. Birang, J. Klein, and C.L. Lin. (2010). "NMR measurements of power-law behavior in the spin-wave and critical regions of ferromagnetic EuO." *Journal of Applied Physics*. 107, 09E142.

© 2010 American Institute of Physics. This article may be downloaded for personal use only. Any other use requires prior permission of the author and the American Institute of Physics.

The following article appeared in *Journal of Applied Physics* and may be found at <http://dx.doi.org/10.1063/1.3367965>.

NMR Measurements of Power-law Behavior in the Spin-wave and Critical Regions of Ferromagnetic EuO

Abstract

Precision continuous-wave NMR measurements have been carried out over the entire magnetization curve of EuO and are presented in tabular form. Two very closely spaced resonances are observed and are attributed to domain and domain-wall signals. Both of the signals are useful for analysis in the spin-wave region. Only the domain signal is measurable above ~ 50 K. The latter is used for fitting T_c and the critical exponent β . The critical-region fits agree with previous measurements within experimental error. The low-temperature data exhibit a clear-cut T^2 behavior, at variance with the expectations of conventional spin-wave theory. This result is discussed in relation to two semiempirical spin-wave schemes, one formulated by Bykovetz, and one by Koebler. The NMR signal at 4.2 K give no indication of a quadrupole splitting in contradiction to the interpretation of several previous spin-echo NMR spectra observed in EuO. This issue remains unresolved.

Disciplines

Physical Sciences and Mathematics | Physics

Comments

Suggested Citation:

Bykovetz, N., B. Birang, J. Klein, and C.L. Lin. (2010). "NMR measurements of power-law behavior in the spin-wave and critical regions of ferromagnetic EuO." *Journal of Applied Physics*. 107, 09E142.

© 2010 American Institute of Physics. This article may be downloaded for personal use only. Any other use requires prior permission of the author and the American Institute of Physics.

The following article appeared in *Journal of Applied Physics* and may be found at <http://dx.doi.org/10.1063/1.3367965>.

NMR measurements of power-law behavior in the spin-wave and critical regions of ferromagnetic EuO

N. Bykovetz,¹ B. Birang,² J. Klein,³ and C. L. Lin^{4,a)}

¹Department of the Army, CECOM LCMC, AMSEL-SF-R, Fort Monmouth, New Jersey 07703-5024, USA

²Department of Physics, Brandeis University, Waltham, Massachusetts 01742, USA

³Physics and Astronomy, University of Pennsylvania, Philadelphia, Pennsylvania 19104-6396, USA

⁴Department of Physics, Temple University, Philadelphia, Pennsylvania 19122-6082, USA

(Presented 21 January 2010; received 4 November 2009; accepted 14 December 2009; published online 7 May 2010)

Precision continuous-wave NMR measurements have been carried out over the entire magnetization curve of EuO and are presented in tabular form. Two very closely spaced resonances are observed and are attributed to domain and domain-wall signals. Both of the signals are useful for analysis in the spin-wave region. Only the domain signal is measurable above ~ 50 K. The latter is used for fitting T_c and the critical exponent β . The critical-region fits agree with previous measurements within experimental error. The low-temperature data exhibit a clear-cut T^2 behavior, at variance with the expectations of conventional spin-wave theory. This result is discussed in relation to two semiempirical spin-wave schemes, one formulated by Bykovetz, and one by Koebler. The NMR signal at 4.2 K gives no indication of a quadrupole splitting in contradiction to the interpretation of several previous spin-echo NMR spectra observed in EuO. This issue remains unresolved. © 2010 American Institute of Physics. [doi:10.1063/1.3367965]

I. INTRODUCTION

Precision continuous-wave (CW) nuclear magnetic resonance (NMR) measurements over the entire magnetization curve of EuO have been carried out and the behavior of these data is analyzed both in the spin-wave and in the critical regions. The low-temperature data exhibit a clear-cut T^2 behavior at variance with the expectations of conventional spin-wave theory. The critical-region power-law fit, however, agrees with other previous measurements within experimental error.

Currently, there is still great interest in the study of EuO because of the varied and multifaceted characteristics it displays. Among others, oxygen-rich or Gd-doped EuO shows colossal magnetoresistance while Eu-rich EuO exhibits a change in conductivity of 13 orders of magnitude in its insulator to metal transition.¹ Some current studies of EuO have a practical angle (spintronics) while others focus on testing theories (such as the Kondo-lattice model). While much is not yet clear in this broader area, the fundamental behavior of the localized-spin (pure Heisenberg) model in EuO is also being put into question by recent measurements.² The results of the current low-temperature data will hopefully shed additional light on this latter issue. The principal focus of this paper is the unconventional (spin-wave) behavior of EuO at low temperatures in the context of a pattern of such behavior in other simple magnetic systems. In addition, the critical-region parameters are examined.

While a strict T^2 low-temperature behavior in pure EuO was reported³ early on, those measurements were not backed up with numerical evidence. The current measurements are presented in tabular form (see Table I) and show a linear-fit

to T^2 with an excellent $R^2=0.9999$. In recent years, two alternative semiempirical spin-wave schemes have been proposed to explain the simple power-law behaviors displayed by magnetic systems (in many cases not recognized by the original authors), beginning with the very first NMR measurement of a magnetically ordered system, $\text{CuCl}_2 \cdot 2\text{H}_2\text{O}$.⁴ One scheme was developed by Koebler⁵ and one by Bykovetz.⁶⁻⁸ The T^2 behavior found in the current EuO NMR data is consistent with both schemes. Using the scheme of Bykovetz, it is argued here that the T^2 behavior

TABLE I. NMR Frequency (MHz) versus T (K) for ^{153}EuO .

T_H	Freq.	T_L	Freq.	T_L	Freq.	T_L
4.200	138.500		69.703	62.519	41.715	67.570
13.981	136.080		68.562	62.807	40.151	67.741
17.990	134.190	17.830	66.654	63.286	38.681	67.882
21.269	132.240	21.127	65.730	63.507	38.654	67.888
25.850	129.050	25.701	63.776	63.973	37.674	67.974
26.991	128.090	26.838	60.773	64.608	37.230	68.015
28.637	126.715	28.491	58.989	64.976	36.833	68.055
32.188	123.523	32.014	57.067	65.347	36.471	68.082
34.360	121.370	34.189	53.371	65.993	35.736	68.144
38.075	117.352	37.945	52.340	66.160	34.782	68.221
38.926	116.350	38.773	51.135	66.357	34.442	68.250
42.402	112.020	42.277	51.019	66.369	34.121	68.271
43.180	111.000	43.023	49.248	66.643	33.663	68.312
47.488	104.720	47.357	47.544	66.852	33.086	68.357
	98.822	50.873	46.182	67.044	32.585	68.397
	92.680	54.130	46.088	67.060	31.903	68.439
	78.507	59.914	44.385	67.266	31.812	68.445
	73.502	61.444	43.945	67.322	31.748	68.451
	71.795	61.933	43.275	67.399	31.600	68.460
	70.723	62.223	43.154	67.411		

^{a)}Electronic mail:clin@temple.edu.

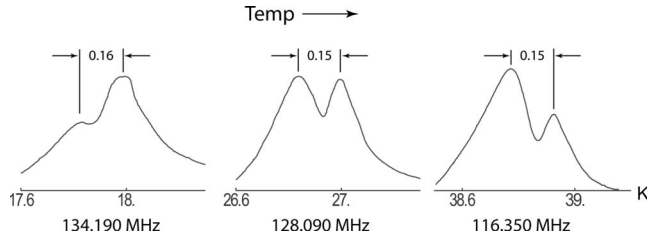


FIG. 1. NMR temperature-scans of EuO at fixed frequencies at ~ 17 , 27, and 39 K shown with the intensities normalized to the same height. The left peak (T_L) increases while the right peak (T_H) decreases with increasing temperature.

seen in the EuO NMR constitutes evidence against a pure localized-spin model as conceived in the conventional Dyson picture and formalism of magnetic interactions in ferromagnets.

Our NMR determination of critical parameters agrees with previous results using non-NMR methods.^{9,10} However, it is an open question why the two so-called ideal Heisenberg ferromagnets EuO and EuS do not have more nearly identical critical exponents β ($\beta=0.368$ in EuO and 0.33 in EuS). EuS appears to exhibit the same β as does MnF₂ (Ref. 11) at variance with most isotropic 3D magnets.

Lastly, we note that a discrepancy still appears to exist between CW and spin-echo NMR measurements in EuO. The current NMR data, like the original CW data of Boyd,¹² give no indication of significant quadrupole splitting of the NMR resonance, whereas spin-echo measurements which involve multilayered processing of the raw data,¹ appear to show the presence of a substantial electric field gradient. An extensive discussion of this issue was presented in Ref. 1 but the issue still remains unresolved.

II. EXPERIMENT

NMR measurements on polycrystalline EuO were carried out using a frequency-modulated spectrometer in zero external field. The temperature was determined by means of a platinum resistance thermometer. Because of the strong broadening of the NMR signal on approaching T_c , it was decided to carry out the measurements by controlled temperature sweeps at fixed frequencies [similar to the method used in Refs. 11 and 13]. For consistency, all data, except the helium-bath (4.2 K) data point, were determined in this way.

III. RESULTS AND DISCUSSION

A single narrow (~ 25 kHz) NMR line was observed at 4.2 K by sweeping the frequency as was the case in the original CW measurement of Boyd.¹² No indication of quadrupolar splitting was evident. At temperatures above 17 K, where the frequency was kept constant and the NMR signal observed by sweeping the temperature, two closely spaced and overlapping signals were observed all the way up to ~ 50 K. The signal that peaks at the lower temperatures will be designated as T_L and at higher temperatures as T_H . Figure 1. shows the behavior of the T_H signal relative to T_L at three representative temperatures. One can see that the T_L peak tapers off in intensity relative to the T_H peak and becomes undetectable at 4.2 K, whereas the T_H peak becomes progres-

TABLE II. T versus ν for ^{153}Eu and ^{151}Eu .

T (K)	ν_{153}	ν_{151}	ν_{151}/ν_{153}
67.971	37.718	84.875	2.250
65.811	54.451	122.665	2.252
65.036	58.690	132.312	2.254
64.566	60.991	136.741	2.242

sively smaller as 50 K is approached and is undetectable above this temperature where only the T_L signal is observable. Near 27 K, the signals have equal intensities.

The T_H signal is ascribed to NMR from domain walls since the domain-wall enhancement of NMR signals is strongest at lowest temperatures. The T_L signal must, therefore come from the nuclei in the domains, since the domain walls become less extensive and their enhancement factor decreases as T_c is approached. Comment *et al.*¹ presented an argument that in EuO, the domain-wall signal enhancement should be relatively small but our results do not seem to support this contention.

Additional support for the assignment of the two NMR signals as originating in domain and domain-wall nuclei comes from the temperature independence of the separation of the peaks in the doublet. It can be seen from the data in Table I that the separation $\Delta T = T_H - T_L$ between the observed double peaks (see Fig. 1) is constant with $\Delta T = 0.149 \pm 0.0124$ K (on the average), over the temperature range where both signals could be measured. As will be seen, both the T_H and the T_L curves give an excellent fit to a T^2 power-law. Consequently, it can be shown that a constant temperature separation translates into a curve separation $\Delta\nu \propto T$. A similar $\Delta\nu = \nu_H - \nu_L \propto T$ separation was observed in CrBr₃,¹⁴ where the identification of which resonance came from domain walls and which from within the domains was more clear-cut. It is to be noted that, as a consequence, if one of the curves (ν versus T_L or T_H) goes as BT^2 , the other cannot be a pure T^2 curve but must have an additional small corrective term $(2B\Delta T)T$. It is conjectured that this term should be part of the T_L curve, although the data are not precise enough to make a definitive determination using fitting techniques.

Focusing on data in the critical-region, the following can be seen. Fits¹⁵ of the data [to the standard equation $D(1 - T/T_c)^\beta$ recast in the form of a power-law] give a β of 0.366 for T data points within 10% of T_c and a T_c of 69.23 K. The parameter $D=1.18$. Fitting only points closer to T_c , results in a small but not a significant increase in β as well as T_c . Thus, for the temperature interval within 3% of T_c , β becomes 0.378 and T_c 69.28 K. The determinations of β agree with previous macroscopic⁹ and neutron-scattering¹⁰ results but are at odds with the Mossbauer¹⁶ determination. A check for frequency-pulling effects near T_c was made by measuring the temperature dependence of the ratio of NMR frequencies in ^{151}EuO to that in ^{153}EuO (see Table II). The lack of a systematic dependence of the ratio on temperature proves that any such effect is negligible. The value of the ratio of ^{151}Eu

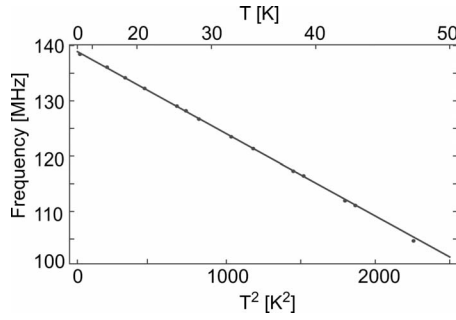


FIG. 2. ν vs T^2 in the spin-wave region. Deviation below the T^2 line begins above ~ 43 K.

to ^{153}Eu frequencies is, however, lower than in EuS ,¹³ but agrees with the EuO measurement at 4.2 K in Ref. 1 (see footnote 40).

In the low-temperature (spin-wave) regime, both the T_H and the T_L data can be fitted with a simple power-law of the form $\nu = A + BT^c$. For the domain-wall T_H data, one obtains a power-law with an exponent of 2.04 ± 0.01 by including all data points except the one at 47.488 K, which is already showing deviation to below the spin-wave T^2 curve. Figure 2 shows a plot of the ν versus T_H^2 , displaying the excellent fit. When this data set is fit to a T^2 power-law, one gets $\nu_0 = 138.93$ MHz and an R^2 of 0.999 92. For the T_L data below ~ 43 K, the best-fit exponent is 2.035 ± 0.011 . When fitted to a straight line as a function of T^2 , one obtains $\nu_0 = 138.96$ MHz and an R^2 of 0.999 94.

The T^2 behavior is in agreement with the expectations of Koebler's scheme,⁵ wherein it is claimed that all isotropic three-dimensional (3D) magnetic systems should exhibit a T^2 behavior in the low-temperature region. We disagree with the generalization to all magnets, the prime counterexample being the $T^{1.71}$ behavior of CrBr_3 . (See Ref. 6.) However, the T^2 spin-wave region behavior of EuO follows the $n=2$ behavior described within the broader semiempirical scheme devised by Bykovetz,⁶ wherein both 3D and two-dimensional (2D) ferromagnets show power-law behaviors depicted in Table III. The power-law behaviors are derivable from the formula $\Delta M \propto (T^{3/2})^{f(n)}$, where $f(n) = 1/[1 - (1/2)^n]$, with $n=1, 2$, and 3 for 3D and $n=1$ and 2 for 2D magnets, where $T^{3/2}$ is replaced by T . Note that other ferromagnets, e.g., CrI_3 ,¹⁷ and

TABLE III. Ferromagnetic exponents.

n	D=3	D=2	D=1
3	$T^{1.71}$		
2	T^2	$T^{1.33}$	
1	T^3	T^2	T

the near bcc structured compounds $\text{M}_2\text{CuX}_4 \cdot 2\text{H}_2\text{O}$,¹⁸ exhibit a T^2 behavior not noticed by the original authors.¹⁹

The scheme of Bykovetz, if further validated, implies that the conventional Bloch result ($T^{3/2}$ for 3D and T^1 for 2D) determines the power-law behaviors, but with an absence of any lattice-dependent effects (i.e., the Dyson $T^{5/2}$ term, expected in 3D ferromagnets, is missing). The general implication would be that even in localized-spin magnetic systems such as the europium chalcogenides, the exchange interactions are somehow long-ranged and/or the spin waves propagate in a spin-density-polarized medium (band). It is well known that a model of ferromagnetism, in which the magnetization can vary continuously (as opposed to having discrete spins at localized sites), results in spin waves that display a pure $T^{3/2}$ behavior with no "lattice-correction" terms. The recent optical measurements by Miyazaki *et al.*² suggest that, in fact, the Heisenberg–Dyson picture of localized exchange interactions may not be quite correct.

Last but not least, the measurements above, particularly the 4.2 K domain-wall measurement as well as those of Boyd,¹² give no evidence of a quadrupole splitting whereas spin-echo NMR measurements invariably do. An extended discussion of this problem is given in Ref. 1. The issue at this point is unresolved. One could conjecture that the domain-wall resonance in CW measurements somehow averages over the electric field gradients. On the spin-echo side, the source of the difficulty may lie in the uncertainties of the multilayered analyses of the complex spin-echo measurements (see Ref. 1).

¹A. Comment, J. P. Ansermet, C. P. Slichter, H. Rho, C. S. Snow, and S. L. Cooper, *Phys. Rev. B* **72**, 014428 (2005).

²H. Miyazaki, T. Ito, H. J. Im, S. Yagi, M. Kato, K. Soda, and S. Kimura, *Phys. Rev. Lett.* **102**, 227203 (2009).

³C. Kuznia, H. Pink, W. Zinn, and X. Colloque Ampere, (North-Holland, Amsterdam, 1967) Vol. IV, p. 1216.

⁴N. J. Poulis and G. E. G. Hardeman, *Physica* **19**, 391 (1953).

⁵U. Köbler, A. Hoser, and W. Schäfer, *Physica B* **364**, 55 (2005).

⁶N. Bykovetz, J. Klein, and C. L. Lin, *J. Appl. Phys.* **105**, 07E103 (2009).

⁷N. Bykovetz, *J. Appl. Phys.* **55**, 2062 (1984).

⁸N. Bykovetz, Ph. D. dissertation, University of Pennsylvania, 1976.

⁹B. Menyuk, K. Dwight, and T. B. Reed, *Phys. Rev. B* **3**, 1689 (1971).

¹⁰J. Als-Nielsen, O. W. Dietrich, and L. Passell, *Phys. Rev. B* **14**, 4908 (1976).

¹¹P. Heller, *Phys. Rev.* **146**, 403 (1966).

¹²E. L. Boyd, *Phys. Rev.* **145**, 174 (1966).

¹³P. Heller and G. B. Benedek, *Phys. Rev. Lett.* **14**, 71 (1965).

¹⁴A. C. Gossard, V. Jaccarino, and J. P. Remeika, *J. Appl. Phys.* **33**, 1187 (1962).

¹⁵All fits in this paper were made using MATHEMATICA.

¹⁶G. Groll, *Z. Phys. A: Hadrons Nucl.* **243**, 60 (1971).

¹⁷A. Narath, *Phys. Rev.* **140**, A854 (1965).

¹⁸E. Velu, J. P. Renard, and B. Lecuyer, *Phys. Rev. B* **14**, 5088 (1976).

¹⁹The low-temperature data from Ref. 18 appear in tabular form in Ref. 8.