



University of Pennsylvania
ScholarlyCommons

Tool Data

Browse by Type

5-6-2015

Statistical Process Control of 80plus Reactive Ion Etcher

Hiromichi Yamamoto

Singh Center, hyam@seas.upenn.edu

Follow this and additional works at: http://repository.upenn.edu/scn_tooldata

Yamamoto, Hiromichi, "Statistical Process Control of 80plus Reactive Ion Etcher", *Tool Data*. Paper 28.
http://repository.upenn.edu/scn_tooldata/28

This paper is posted at ScholarlyCommons. http://repository.upenn.edu/scn_tooldata/28
For more information, please contact libraryrepository@pobox.upenn.edu.

Statistical Process Control of 80plus Reactive Ion Etcher

Keywords

Statistical Process Control, 80plus

Creative Commons License



This work is licensed under a [Creative Commons Attribution-Share Alike 4.0 License](https://creativecommons.org/licenses/by-sa/4.0/).

Statistical Process Control of 80plus Reactive Ion Etcher

Hiromichi Yamamoto (5/6/2015)


Note: Etch rate also depends on the sample size and percentage of the open area, which is not covered by resist film.

1. SiO₂ etch

- Default Recipe
Ar = 38 sccm
CHF₃ = 12 sccm
Pressure = 30 mTorr
Power = 200 W
T = 17.5 °C

Date	Etching Rate (nm/min)
5/19/2010	45
12/6/2013	33
10/29/2014	42
4/17/2015	42

Statistical Process Control

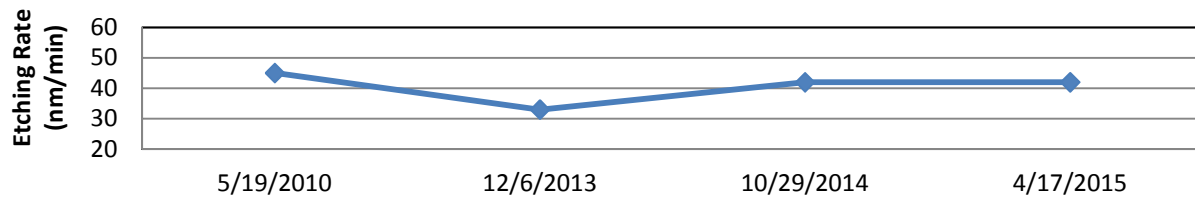

2. SiNx etch

- Default Recipe

O₂ = 5 sccm

CHF₃ = 50 sccm


Pressure = 20 mTorr

Power = 150 W

T = 17.5 °C

Date	Etching Rate (nm/min)
5/19/2010	80
12/9/2013	61
10/29/2014	73
4/17/2015	76

Statistical Process Control

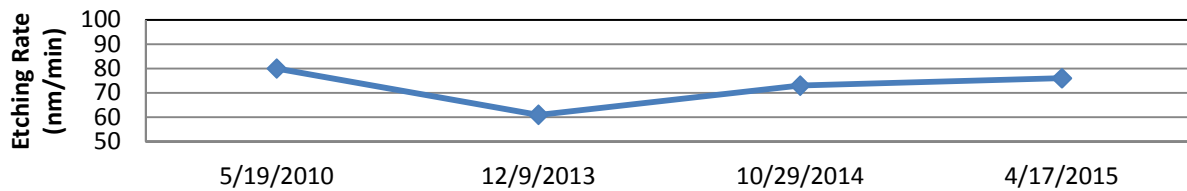

3. Shallow Si etch

Pressure: 10 mTorr

CHF3: 35 sccm


SF6: 14 sccm

RF power: 100 W

T = 17.5 °C.

Etch rate in the brochure of Oxford = 35 nm/min

Date	Etching Rate (nm/min)
4/3/2014	140
10/29/2014	123
4/17/2015	100

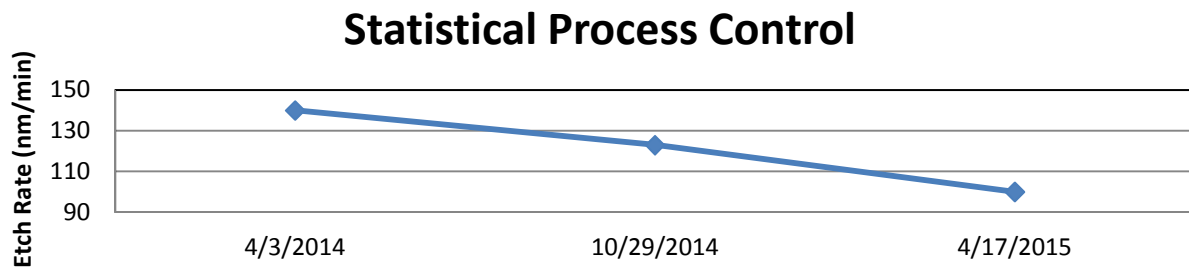

4. Deep Si etch

SF6 = 50 sccm

O2 = 10 sccm

Pressure = 150 mTorr

RF power = 100 W

T = 20 °C

Etch rate 500-700 nm/min (in the brochure)

Selectivity to SiO2 mask: >50:1

Date	Etching Rate (nm/min)
4/3/2014	505
10/29/2014	515
4/17/2015	741

