

Tailoring the optical properties of poly(3-hexylthiophene) by emulsion processing using polymeric macrosurfactants

F.D. Fleischli^{a,b},* N. Ghasdian^c, T.K. Georgiou^a and N. Stingelin^{a,b}

Here we demonstrate that the use of macrosurfactants in the production of poly(3-hexylthiophene) (P3HT):water dispersion allows to drastically change the semiconductor's molecular aggregation, leading to pronounced H- or J-like behaviour depending on the macrosurfactant used and the conditions selected to produce the dispersions. No correlation with the particle size and optical response is found, indicating that it is the pre-assembly in the initial emulsion and possibly additional features such as the thermoresponsiveness of one of the macrosurfactants that lead to the specific molecular arrangement of the P3HT. Considering the broad variety of macrosurfactants that can be synthesised based already on the building blocks (co-polymer units) used here, it is clear that this approach can widen the tool box towards structural control of organic semiconductors, and macromolecular materials especially.

Introduction

In recent years, there has been increasing interest in organic semiconductors, as these materials allow fabrication of discrete thin-film field-effect transistors (FETs), light-emitting diodes (LEDs), photovoltaic cells (OPVs), sensors, or integrated structures such as radio-frequency identification tags,¹⁻⁸ to name a few applications. These optoelectronic devices consist of a variety of different materials, each of them chosen due to its specific properties. However, often, the processing steps (including solvent and/or temperature treatments) necessary to reach the best performance of one material, derogate the properties of another component. This is especially true for the semiconductors forming the active layer. They are highly sensitive to changes in the selection of processing conditions because these can drastically affect their molecular order and packing on all length scale and, hence, their macroscopic properties.^{1,9-17}

Emulsions and dispersions can offer an alternative approach towards (self-)assembling — as well as patterning — of multifunctional systems including organic semiconductors. The reason is that particles of different size, consisting of different materials and/or with pre-defined properties can be realised using this approach, and the constituting components may be directed to adopt the desired structure and molecular arrangement prior to the final device fabrication.

In the 'plastic electronics' area, previous studies have demonstrated that particles consisting of conjugated polymers can be successfully made via emulsion routes; however it seems that the full potential of this approach has not yet been fully exploited. For instance, most often, the commercially available surfactant sodium dodecylsulphate (SDS) was employed to produce organic semiconducting dispersions and nanoparticles,¹⁸⁻²² while many other systems have remained uninvestigated. We therefore aim here at expanding the library of surfactants used in combination with organic semiconducting matter and explore utilisation of polymeric macrosurfactants with the goal to realise emulsions comprising tunable semiconductor structures, with focus on manipulating the optical characteristics of the active material(s).

We selected polymeric macrosurfactants, which generally are based on amphiphilic block copolymers, as 'emulsifiers' because they offer advantages compared to the traditional small molecular weight surfactants. Specifically, with a smaller quantity they are able to stabilise emulsions or dispersion,^{23,24} promising therefore to only have a minor impact (if any) on the optoelectronic properties of the semiconducting material(s) that is (are) being 'encapsulated'. Moreover, polymer macrosurfactants are usually easier to manipulate and to tailor compared to traditional surfactants, thus, often lead to a better stability of the emulsions.^{23,25-28}

Two polymeric macrosurfactants were chosen that are based on block copolymers with the same hydrophobic block, *n*-butyl methacrylate (BuMA), and different hydrophilic moieties (poly(ethylene glycol) methyl methacrylate (PEGMA) and 2-(dimethylamino)ethyl methacrylate (DMAEMA)). Specifically, we selected BuMA₅₉-*b*-DMAEMA₈₃, a macrosurfactant that is both pH- and thermo-responsive due to the presence of the DMAEMA groups²⁹⁻³² and PEGMA₁₆-*b*-BuMA₄₂, which is based on two non-ionic monomers. In an organic solvent, these macrosurfactants are expected to form inverse micelles with the hydrophobic block (BuMA) forming the shell (stretched chains) and the hydrophilic block (PEGMA or DMAEMA) coiled in the core. Schematics of the chemical structures of BuMA₅₉-*b*-DMAEMA₈₃ and PEGMA₁₆-*b*-BuMA₄₂ are shown in Fig. 1.

As the active material we choose to use poly(3-hexyl thiophene) (P3HT) as model system because it is one of the most investigated semiconducting polymer.³³ Moreover, the selection of solvents (quality, evaporation kinetics), use of specific temperature treatment and/or deposition onto certain substrates (e.g., substrates that are covered with self-assembled monolayers, patterned with surface structures, or allowing confined solidification) were shown to affect the ordering and arrangement of P3HT from the molecular level to the macro-scale.^{10,34-42} Processing can, thus, have a drastic effect on the optoelectronic features of the resulting structures and lead to significant changes in the photophysical aggregation of the P3HT molecules.

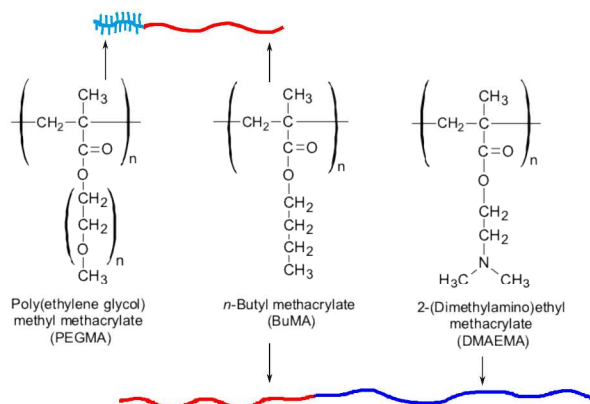


Fig. 1: Schematic illustration and chemical structures of the diblock copolymer macrosurfactants used here. The BuMA-, DMAEMA- and PEGMA-blocks are coloured in red, dark blue and light blue, respectively.

The photophysical aggregation of P3HT can, according to Spano and coworkers, be explained as a result of the competition of interchain and intrachain exciton coupling that is believed to be highly sensitive to the short- and, possibly, long-range ordering of the P3HT molecules.^{43,44} H-aggregate like behaviour results from a dominant interchain coupling and leads, amongst other things, to a low A_{0-0} transition in the UV-

Vis absorption.⁴³ If the intrachain coupling is dominant, the material shows J-aggregate-like behaviour with a pronounced A_{0-0} transition. Generally, P3HT structures display H-like aggregation, however, in certain scenarios, they have been found to feature J-aggregate-like behaviour: e.g., in nanofibres produced during slow solidification from a good solvent,⁴² or in films blended with a polar polymer such as poly(ethylene oxide) (PEO) (i.e., the long-chain derivative of the PEG moiety selected in one of our macrosurfactant).⁴⁵ This should allow us to monitor changes in short- and possibly long-range order induced by the nanoparticle formation through emulsion processing, which is believed to lead to these two different aggregation states.⁴⁶

Materials and Methods

Materials

Synthesis of polymeric macrosurfactants. Two different block copolymers were used as macrosurfactants. They were synthesised as outlined below. 1-Methoxy-1(trimethylsiloxy)-2-methyl propene (MTS, initiator, 99%), sodium metal, 2,2-diphenyl-1-picrylhydrazyl hydrate (DPPH, free radical inhibitor, 99%), and (PEGMA ($M_w = 300 \text{ gmol}^{-1}$, monomer) were purchased from Aldrich, UK. Tetrabutylammonium hydroxide (40% in water), basic alumina (Al_2O_3 , 95%), potassium metal, DMAEMA (monomer, 99%) and BuMA (monomer, 99%) were purchased from Acros Organics, UK. Tetrahydrofuran (THF, polymerisation solvent, 95%) and *n*-hexane (precipitation solvent, 95%) were purchased from Fisher Scientific.

DMAEMA and BuMA monomers were passed twice through basic alumina to remove inhibitors and protic impurities and stirred over CaH_2 for 3 hours in the presence of DPPH. Both monomers were kept refrigerated until distillation before use. PEGMA was passed twice through basic alumina as a 50% v/v solution in THF and stirred overnight over CaH_2 . No DPPH was added to the PEGMA monomer solution due to the inability to distil PEGMA prior to use. The solution was refrigerated until the polymerisation and it was filtered directly into the reaction flask with a $0.45 \mu\text{m}$ syringe filter.

The initiator was distilled once before polymerisation and kept sealed under argon until use. Tetrabutylammonium bibenzoate (TBABB) was the polymerisation's catalyst and was synthesised by the reaction of tetrabutylammonium hydroxide and benzoic acid, as described by Dicker et al.⁴⁷ The catalyst was dried and stored under vacuum until use. THF was refluxed over a potassium/sodium amalgam for 3 days to dry before polymerisation. All glassware was dried overnight at $140 \text{ }^\circ\text{C}$ and assembled hot under dynamic vacuum before use.

The synthetic procedure for the two macrosurfactants was similar. Specifically, a typical sequential group transfer polymerisation (GTP) procedure was followed for both of

Table 1: Structure of the block copolymers and single blocks including number and weight average molecular weights, M_n and M_w , respectively, and weight block fraction.

Polymer structure	M_n (g mol ⁻¹)	M_w/M_n (-)	Block content (wt%)*		
			PEGMA	BuMA	DMAEMA
PEGMA ₁₆	4100	1.11	1.00	-	-
PEGMA ₁₆ - <i>b</i> -BuMA ₄₂	10000	1.06	0.44	0.56	-
BuMA ₅₉	7200	1.16	-	1.00	-
BuMA ₅₉ - <i>b</i> -DMAEMA ₈₃	19100	1.12	-	0.39	0.61

*Based on NMR results

them.^{25, 29-32,48} The synthesis of PEGMA₁₆-*b*-BuMA₄₂ is given below as an example. The polymerisation exothermal was monitored using a digital thermometer to identify whether the polymerisation was successful and when it was finished.

Freshly distilled THF (124 mL) and MTS (0.50 mL, 0.43 g, 2.46 mmol) were syringed into a 250 mL round bottom flask containing TBABB (~10 mg) previously sealed with a septum and purged with argon. Firstly a PEGMA solution in THF was added (35 mL of a 50 vol % solution, 18.5 g, 61.5 mmol) using a syringe and a filter. The temperature rose by 4.7 °C. After 10 minutes the exothermic reaction had abated and two 0.1 mL aliquots of the reaction solution were extracted for GPC and ¹H NMR analysis. Then BuMA (13.5 mL, 12.3 g, 86.1 mmol) was added using a syringe and the temperature rose by 5.5 °C. Subsequently two more 0.1 mL aliquots were collected for GPC and ¹H NMR analysis. For the BuMA₅₉-*b*-DMAEMA₈₃ synthesis, the BuMA monomer was polymerised first and the DMAEMA monomer second. After the polymerisations were completed both macrosurfactants were recovered by precipitation through *n*-hexane and dried at room temperature in a vacuum oven for two days. Table 1 summarises the number-average molecular weights M_n , the molecular weight distribution, MWD, and compositions of the precursors to the macrosurfactants and the macrosurfactants as determined by GPC and NMR, respectively.

Micelle formation. The behaviour of macrosurfactants in a solvent provides an indication of their behaviour in an emulsion. Therefore, we dissolved both macrosurfactants (which distinguish in the type of the hydrophilic block and block length) in water, cyclohexane and chloroform, the same

solvents as we used for the production of the emulsions with P3HT. Reassuringly, according to dynamic light scattering measurements, micelle/aggregate formation does occur (see Supplementary Information) for both materials in all three selected solvents, although in chloroform a high fraction of the surfactants, especially PEGMA₁₆-*b*-BuMA₄₂, appeared to be present as single-coiled molecules, likely due to the good solubility of the co-polymer blocks in this solvent.

Dispersions of P3HT. Regioregular poly(3-hexyl thiophene) (P3HT; $M_w = 31$ kg mol⁻¹) was purchased from *Sigma-Aldrich* (batch LF430202). Chloroform and cyclohexane were purchased from *Sigma-Aldrich* and used without further purification.

P3HT dispersions were produced via an emulsion route. P3HT was dissolved in the organic solvent (chloroform or cyclohexane, 2 mg mL⁻¹) forming the organic phase of the emulsion. The water phase was based on distilled water. One of the macrosurfactants (20 mg mL⁻¹) was then dissolved either in the organic (chloroform or cyclohexane) or water phase (see Fig. 2). The water and organic phase were subsequently stirred over night before they were mixed together (see below).

Emulsions were formed by mixing the oil and water phase at a ratio of 1:3 by volume at either room temperature (RT) or 80 °C. The total liquid volume was 2 mL. For emulsification, they were homogenised ultrasonically (*Hielscher UP50H*, 50 W, 30 kHz) or mechanically (*Cole-Palmer LabGEN 7*, 125 W, up to 35'000 rpm) for 60 s. Subsequently, these oil-in-water emulsions were poured into 20 mL of distilled water, kept at the same temperature as the emulsions, to further separate the dispersed 'oil' droplets. These diluted emulsions were then

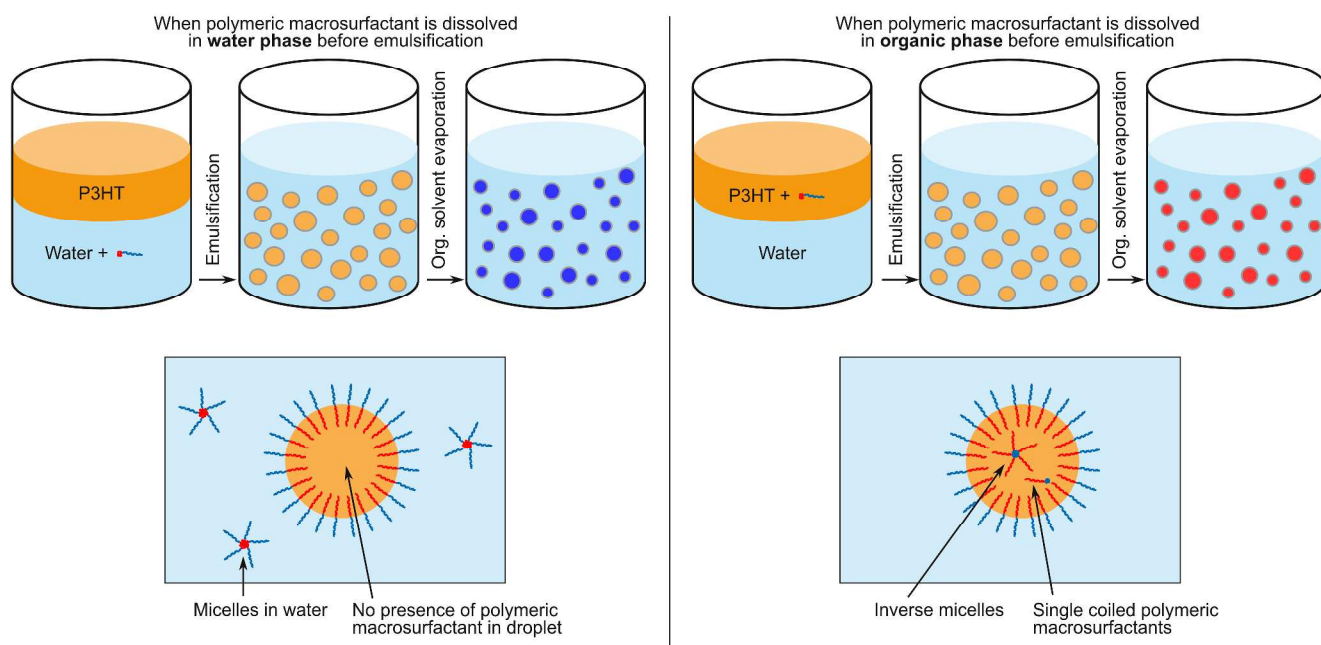


Fig. 2: Schematic illustration of the route used to produce P3HT:water dispersions. The polymeric macrosurfactant is dissolved either a) in the water or b) organic phase, respectively, before emulsification via mechanical stirring or ultrasonification. In the final step the organic solvent is removed, leading to solid P3HT particles dispersed in water.

stirred – and if processed at 80°C let cool down to RT – until all organic solvent evaporated, leading to the formation of P3HT particles. The resulting dispersions of P3HT particles in water could readily be stored in glass vials in the dark.

Methods

Dynamic light scattering. The average particle size in the P3HT dispersions was determined by dynamic light scattering using a *ZetasizerNano S*. For this purpose, 20 measurements were averaged; the P3HT dispersions were diluted to minimize the interaction between the particles.

UV-Vis absorption. The absorption spectra of the P3HT dispersions were recorded using a *Perkin Elmer Lambda 25* UV-Vis spectrometer. If necessary, the P3HT dispersions were diluted.

Gel Permeation Chromatography. The molecular weights (MWs) and the molecular weight distribution (MWDs, M_w/M_n) of all the linear precursors to the copolymers and all the copolymers were determined by gel permeation chromatography (GPC) using a single *PL-Mixed "E" Polymer*

Laboratories column. THF containing 5% triethylamine was the mobile phase and was pumped with a flow rate at 1 mL min⁻¹ using a *Viscotek vt7510* pump. A *Viscotek 3580 differential refractometer* was used to measure the refractive index signal. The calibration curve was based on nine linear and low-dispersity poly(methyl methacrylate)s (PMMA) of a M_w of 690, 5720, 1020, 1200, 1960, 4000, 8000, 13300 and 20010 g mol⁻¹.

Proton Nuclear Magnetic Resonance Spectroscopy (¹H-NMR). A *JEOL* 400 MHz spectrometer instrument was used to acquire the proton NMR spectra of the copolymers and their precursors in CDCl₃.

Results and Discussion

In order to probe an as broad parameter space as possible, we prepared emulsions with both selected macrosurfactants and varied i) the organic solvent in the oil phase (i.e. chloroform or cyclohexane), ii) the phase in which the macrosurfactant was dissolved (i.e. water or organic phase (see Fig. 2)), iii) the temperature at which the emulsion was produced (i.e. the temperature at which the water and organic phase were mixed),

and iv) the homogenisation technique (mechanically vs. ultrasonically). All routes let to stable dispersions of P3HT particles in water, allowing after evaporation of the organic solvent straight-forward measurements of the respective UV-Vis absorption spectra.

Intriguingly, for systems using PEGMA₁₆-*b*-BuMA₄₂ as macrosurfactant, large variations in the optical response can already be observed when the solvent used for the preparation of the oil phase was varied (see Fig. 3b). Indeed, comparing dispersion where the 'oil' and water phase were mixed at 80 °C and then were homogenised ultrasonically, we find large differences in the A_{0/0} absorption transition depending whether chloroform or cyclohexane was used in the organic phase — indication of the promise of this strategy to manipulate the P3HT arrangement and order at small length scale. More specifically, using chloroform for dissolving P3HT leads in combination with this surfactant to a high A_{0/0} transition, i.e. a strong J-like character (A_{0/0}/A_{0/1} ≈ 0.98), especially when the dispersions were prepared from an emulsion where the macrosurfactant was dissolved in the water phase (see Fig. 3b). In contrast, with cyclohexane as the solvent for the organic phase, dispersions with the optical behaviour typical for H-like P3HT aggregates were obtained with PEGMA₁₆-*b*-BuMA₄₂, again with a somewhat higher A_{0/0} absorption transition when they were processed with the macrosurfactant dissolved in the water phase.

Somewhat surprisingly, no drastic differences were observed in the UV-vis spectra of the P3HT dispersions when the other macrosurfactant, i.e. BuMA₅₉-*b*-DMAEMA₈₃ was used (see Fig. 3a). We therefore went on and investigated whether we can induce J-like aggregation in these systems by changing the method of stirring of the emulsions as well as the emulsion temperature while stirring (80 °C vs. RT). We used for this purpose dispersion with cyclohexane as the solvent for the organic phase and dissolved the macrosurfactant in water because under these conditions, we have observed rather H-like aggregation in our first set of experiments. For comparison, we prepared additional emulsions with PEGMA₁₆-*b*-BuMA₄₂ employing the same parameters.

A few striking observations can be made (see Fig. 3c,d): i) Using mechanical homogenisation of the emulsions at 80 °C, we can change the generally H-like absorption of dispersions, which were produced with BuMA₅₉-*b*-DMAEMA₈₃ dissolved in the water phase, to J-like-aggregate behaviour with a very pronounced A_{0/0} absorption transition. ii) Similarly, for systems prepared with the other surfactant, PEGMA₁₆-*b*-BuMA₄₂, (P3HT dissolved in cyclohexane as organic phase; PEGMA₁₆-*b*-BuMA₄₂ dissolved in water), when mechanically homogenised, a significantly higher A_{0/0}/A_{0/1} ≈ 0.94 is obtained compared to dispersions of identically composition but mixed ultrasonically; that is a high A_{0/0} transition, characteristic for J-like aggregates, is induced that is approaching the one found in dispersions made from a chloroform-based organic phase.

The above shows that following an emulsion route, we apparently gain the capability to manipulate the molecular ordering of P3HT and, hence, their photophysical properties such as H- vs. J- aggregation. The question remains what leads to the change in optical behaviour of the various P3HT-in-water dispersions. One factor could be the particle size. DLS data collected on the various systems are displayed in Fig. 4. We find that for BuMA₅₉-*b*-DMAEMA₈₃-based systems, the particle size does not drastically vary and in average is around 300 to 400 nm, although some particles in the 60 to 80 nm-

range are present in dispersions prepared with cyclohexane as solvent for the oil phase, the macrosurfactant having been dissolved in water, and the emulsion having been mechanically stirred at 80 °C. The observed discrepancy in the A_{0/0} absorption transition in the dispersions produced with this macrosurfactant may, thus, likely origin from other effects, e.g., its thermo-responsiveness. In contrast, for the dispersions fabricated with PEGMA₁₆-*b*-BuMA₄₂ noticeably different particle sizes are measured, with sizes ranging from 100 nm to more than 1 μm. In addition, bi-modal or even more complex size distributions are observed. Yet, again, no obvious correlation with particle size can be deduced, although the most J-like-aggregate behaviour is found for dispersion comprising particles of a relatively monodisperse particle size distribution around 200 nm.

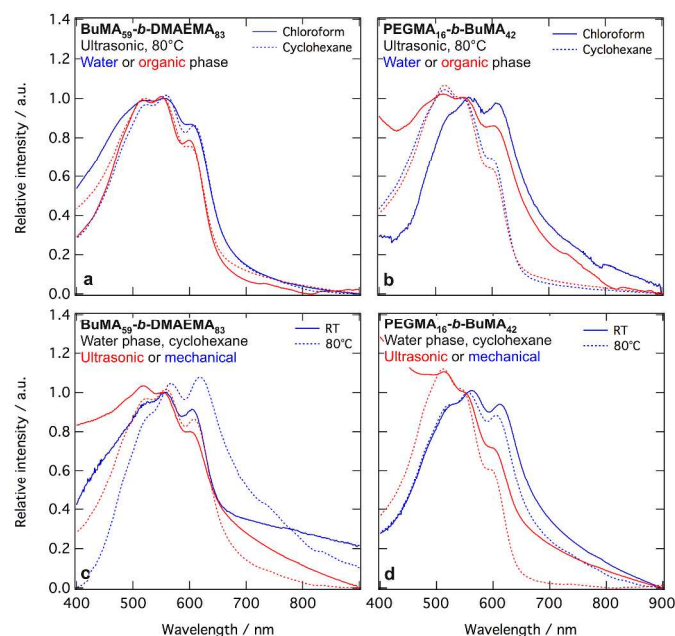


Fig. 3: UV-Vis absorption spectra of P3HT dispersions made with a) BuMA₅₉-*b*-DMAEMA₈₃ and b) PEGMA₁₆-*b*-BuMA₄₂, respectively, whereby the macrosurfactant was dissolved in the water- (blue) or oil phase (red), chloroform (solid line) or cyclohexane (dotted line) was used as the solvent for P3HT. UV-Vis absorption spectra of P3HT dispersions made with c) BuMA₅₉-*b*-DMAEMA₈₃ and d) PEGMA₁₆-*b*-BuMA₄₂, respectively. These emulsions were homogenised ultrasonically (red) or mechanically (blue) at RT (solid line) or 80 °C (dotted line). Thereby, the macrosurfactant was dissolved in the water phase and cyclohexane was used to dissolve P3HT.

Conclusions

We have demonstrated that use of macrosurfactants open new opportunities in the assembly of P3HT in solution prior to device fabrication. Changes in the emulsion production, including selection of macrosurfactant, method used to homogenise the initial emulsion, the choice of emulsion temperature, etc., have a significant effect on the photophysical aggregation of the P3HT macromolecules, from pronounced H-like to J-like character, as deduced from UV-Vis spectroscopy. No direct correlation with particle size and aggregation behaviour could be made indicating that there are other

important parameters that influence the assembly of the P3HT macromolecules in such dispersions, which requires more detailed investigations. Nonetheless, it is clear that the wide variety of macrosurfactants available and the ease to modify them, will open entirely new pathways for the assembly of organic semiconducting structures and, in particular, polymeric semiconductors.

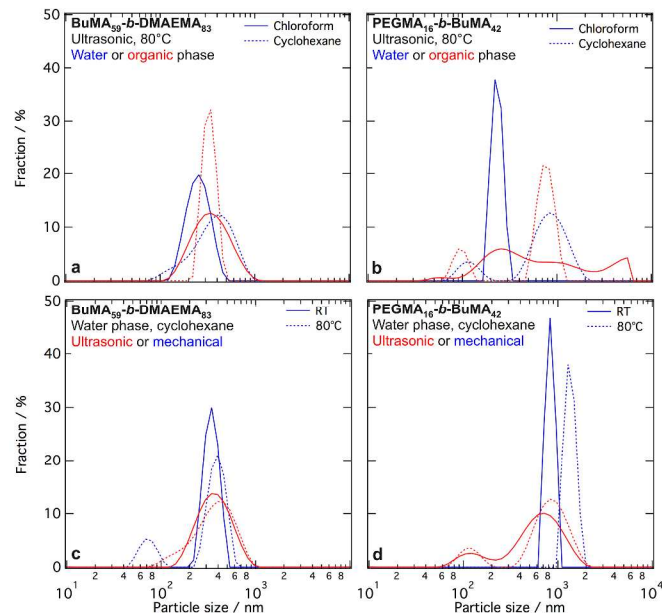


Fig. 4: Size distribution of P3HT particles in dispersions made with a) BuMA₅₉-b-DMAEMA₈₃ and b) PEGMA₁₆-b-BuMA₄₂, respectively, where the macrosurfactant was dissolved in the water- (blue) or oil phase (red) and chloroform (solid line) or cyclohexane (dotted line) was used to dissolve the P3HT. Size distribution of P3HT particles in dispersions made with c) BuMA₅₉-b-DMAEMA₈₃ and d) PEGMA₁₆-b-BuMA₄₂, respectively, whereby the emulsions were homogenised ultrasonically (red) or mechanically (blue) at RT (solid line) or 80°C (dotted line), with the macrosurfactant being dissolved in the water phase and cyclohexane as solvent for P3HT.

Acknowledgements

We thank the Swiss National Science Foundation for the Fellowship for prospective researchers (for F.D.F) and the University of Hull for providing Ph.D. Studentship funding (for N.G.) and Funds for Women Graduates for additional financial support. N.S. in addition is supported by a European Research Council (ERC) Starting Independent Research Fellowship under the grant agreement no. 279587

Notes and references

^a Department of Materials, Imperial College London, London - UK


^b Centre of Plastic Electronics, Imperial College London, London - UK

^c Department of Chemistry, University of Hull, Hull - UK

- 1 H. Sirringhaus, *Adv. Mater.*, 2014, **26**, 1319–1335.
- 2 H. Sasabe and J. Kido, *Eur. J. Org. Chem.*, 2013, **34**, 7653–7663.
- 3 C. Murawski, K. Leo and M.C. Gather, *Adv. Mater.*, 2013, **25**, 6801–6827.

- 4 L. Dou, J. You, Z. Hong, Z. Xu, G. Li, R.A. Street and Y. Yang, *Adv. Mater.*, 2013, **25**, 6642–6671.
- 5 B.K. An, R. Mulherin, B. Langley, P. Burn and P. Meredith, *Org. Electron.*, 2009, **10**, 1356–1363.
- 6 L. Torsi, M. Magliulo, K. Manoli and G. Palazzo, *Chem Soc Rev.*, 2013, **42**, 8612–8628.
- 7 B. Crone, A. Dodabalapur, Y. Y. Lin, R. W. Filas, Z. Bao, A. La Duca, R. Sarpeshkar, H. E. Katz and W. Li, *Nature*, 2000, **403**, 521–523.
- 8 S. Jacob, S. Abdinia, M. Benwadih, J. Bablet, I. Chartier, R. Gwoziecki, E. Cantatore, A.H.M. van Roermund, L. Maddiona, F. Tramontana, G. Maiellaro, L. Mariucci, M. Rapisarda, G. Plmisano and R. Coppard, *Solid-State Electronics*, 2013, **84**, 167–178.
- 9 A. Salleo, R.J. Kline, D.M. DeLongchamp and M.L. Chabinyc, *Adv. Mater.*, 2010, **22**, 3812–3838.
- 10 O.G. Reid, J.A. Nekuda Malik, G. Latini, S. Dayal, N. Kopidakis, C. Silva, N. Stingelin and G. Rumbles, *J. Polym. Sci. Part B: Polym Phys.*, 2012, **50**, 27–37.
- 11 I. McCulloch, M. Heeney, M.L. Chabinyc, D. DeLongchamp, R.J. Kline, M. Coelle, W. Duffy, D. Fischer, D. Gundlachm B. Hamadani, R. Hamilton, L. Richter, A. Salleo, M. Shkunov, D. Sporrowe, S. Tierney and W. Zhong, *Adv. Mater.*, 2009, **21**, 1091–1109.
- 12 A.A. Virkar, S. Mannsfeld, Z. Bao and N. Stingelin, *Adv. Mater.*, 2010, **22**, 3857–3875.
- 13 M. Brinkmann, *J PolymSci B*, 2011, **49**, 1218–1233.
- 14 H. Li, G. Giri, J.B.H. Tok and Z. Bao, *MRS Bulletin*, 2014, **38**, 34–42.
- 15 R. Noriega, J. Rivnay, K. Vandeval, F.P.V. Koch, N. Stingelin, P. Smith, M.F. Toney, A. Salleo, *Nature Materials*, 2013, **12**, 1038
- 16 N. Shin, L.J. Richter, A.A. Herzing, J.R. Kline, D.M. DeLongchamp, *Adv. Energy Materials*, 2013, **3**, 938–948.
- 17 W. Ma, J.R. Tumbleston, L. Ye, C. Wang, J. Hou, H. Ade, *Adv. Materials*, 2014, **26**, 4234–4241.
- 18 D. Darwis, D. Elkington, S. Ulum, A. Stapleton, G. Bryant, X. Zhou, W. Belcher and P. Dastoor, *AIP Conf. Proc.*, 2011, **1415**, 124–127.
- 19 T. Kietzke, D. Neher, K. Landfester, R. Montenegro, R. Guentner and U. Scherf, *Nature Materials*, 2003, **2**, 408–412.
- 20 G. Nagarjuna, M. Baghgar, J.A. Labastide, D.D. Algaier, M.D. Barnes, D. Venkataraman, *ACS Nano*, 2012, **6**, 10750–10758.
- 21 A. Stapleton, B. Vaughan, B. Xue, E. Sesa, K. Burke, X. Zhou, G. Bryant, O. Werzer, A. Nelson, A.L.D. Kilcoyne, L. Thomsen, E. Wanless, W. Belcher and P. Dastoor, *Solar Energy Materials and Solar Cells*, 2012, **102**, 114–124.
- 22 J.J. Richards, K.M. Weigandt and D.C. Pozzo, *J. Colloids Interf. Sci.*, 2011, **364**, 341–350.
- 23 S. Garnier and A. Laschewsky, *Langmuir*, 2006, **22**, 4044–4053.
- 24 S.C. Hadjiyannakou, M. Vamvakaki, and C.S. Patrickios, *Polymer*, 2004, **45**, 3681–3692.
- 25 N.H. Raduan, T.S. Horozov and T.K. Georgiou, *Soft Matter*, 2010, **6**, 2321–2329.
- 26 S. Liu and S.P. Armes, *Curr. Opin. Colloid Interface Sci.*, 2001, **6**, 249–256.
- 27 T. Tadros, *Adv. Colloid Interface Sci.*, 2009, **147–148**, 281–299.

- 28 A.T. Nikova, V.D. Gordon, G. Cristobal, M.R. Talingting, D.C. Bell, C. Evans, M. Joanicot, J.A. Zasadzinski and D.A. Weitz, *Macromolecules*, 2004, **37**, 2215-2218.
- 29 M. A. Ward and T. K. Georgiou, *J. Polym. Sci., Part A: Polym. Chem.*, 2010, **48**, 775-783.
- 30 M. A. Ward and T. K. Georgiou, *Soft Matter*, 2012, **8**, 2737-2745.
- 31 M. A. Ward and T. K. Georgiou, *J. Polym. Sci., Part A: Polym. Chem.*, 2013, **51**, 2850-2859.
- 32 M. A. Ward and T. K. Georgiou, *Polym. Chem.*, 2013, **4**, 1893-1902.
- 33 B. DeBoer, A. Facchetti, *Polymer Reviews*, 2008, **48**, 423-431.
- 34 A.R. Aiyar, J.I. Hong, R. Nambiar, D.M. Collard and E. Reichmanis, *Adv. Funct. Mater.*, 2011, **21**, 2652-2659.
- 35 J.F. Chang, J. Clark, N. Zhao, H. Sirringhaus, D.W. Breiby, J.W. Andreasen, M.M. Nielsen, M. Giles, M. Heeney and I. McCulloch, *Phys. Rev. B*, 2006, **74**, 115318.
- 36 F.S.U. Fischer, K. Tremel, M. Sommer, E.J.C. Crossland and S. Ludwigs, *Nanoscale*, 2012, **4**, 2138-2144.
- 37 R.J. Kline, M.D. McGehee, E.N. Kadnikova, J. Liu, J.M.J. Frechet and M.F. Toney, *Macromolecules*, 2005, **38**, 3312-3319.
- 38 B. OConnor, R.J. Kline, B.R. Conrad, L.J. Richter, D. Gundlach, M.F. Toney and D.M. DeLongchamp, *Adv. Funct. Mater.*, 2011, **21**, 3697-705
- 39 B. Park, A. Aiyar, M.S. Park, M. Srinivasarao and E. Reichmanis, *J. Phys. Chem. C*, 2011, **115**, 11719-11726.
- 40 W. Porzio, G. Scavia, L. Barba, G. Arrighetti and S. Milita, *Europ. Polym. J.*, 2011, **47**, 273-283.
- 41 C. Scharsich, R.H. Lohwasser, M. Sommer, U. Asawapirom, U. Scherf, M. Thelakkat, D. Neher and A. Koehler, *J. Polym. Sc. B*, 2012, **50**, 442-453.
- 42 T.P. Martin, A.J. Wise, E. Busby, J. Gao, J.D. Roehling, M.J. Ford, D.S. Larsen, A.J. Moule and J.K. Grey, *J Phys Chem B*, 2013, **117**, 4478-4487.
- 43 F.C. Spano and C. Silva, *Annu. Rev. Phys. Chem.*, 2014, **65**, 477-500.
- 44 H. Yamagata and F.C. Spano, *J. Chem. Phys.*, 2012, **136**, 184901.
- 45 C. Hellmann, F. Paquin, N.D. Treat, A. Bruno, L.X. Reynolds, S.A. Haque, P.N. Stavrinou, C. Silva and N. Stingelin, *Adv. Mater.*, 2013, **25**, 4906-4911.
- 46 E.T. Niles, J.D. Roehling, H. Yamagata, A.J. Wise, F.C. Spano, A.J. Moule, J.K. Grey, *J. Phys. Chem. Lett.*, 2012, **3**, 259-263.
- 47 I. B. Dicker, G. M. Cohen, W. B. Farnham, W. R. Hertler, E. D. Laganis and D. Y. Sogah, *Macromolecules*, 1990, **23**, 4034-4041.
- 48 D. M. A. Buzza, P. D. I. Fletcher, T. K. Georgiou and N. Ghasdian, *Langmuir*, 2013, **29**, 14804-14814.

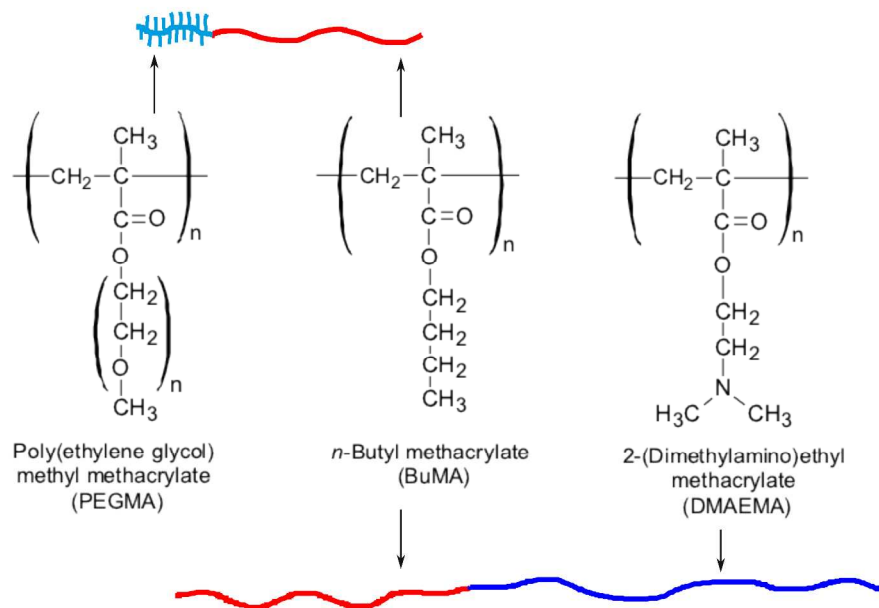

Schematic illustration and chemical structures of the diblock copolymer macrosurfactants used here. The BuMA-, DMAEMA- and PEGMA-blocks are coloured in red, dark blue and light blue, respectively.

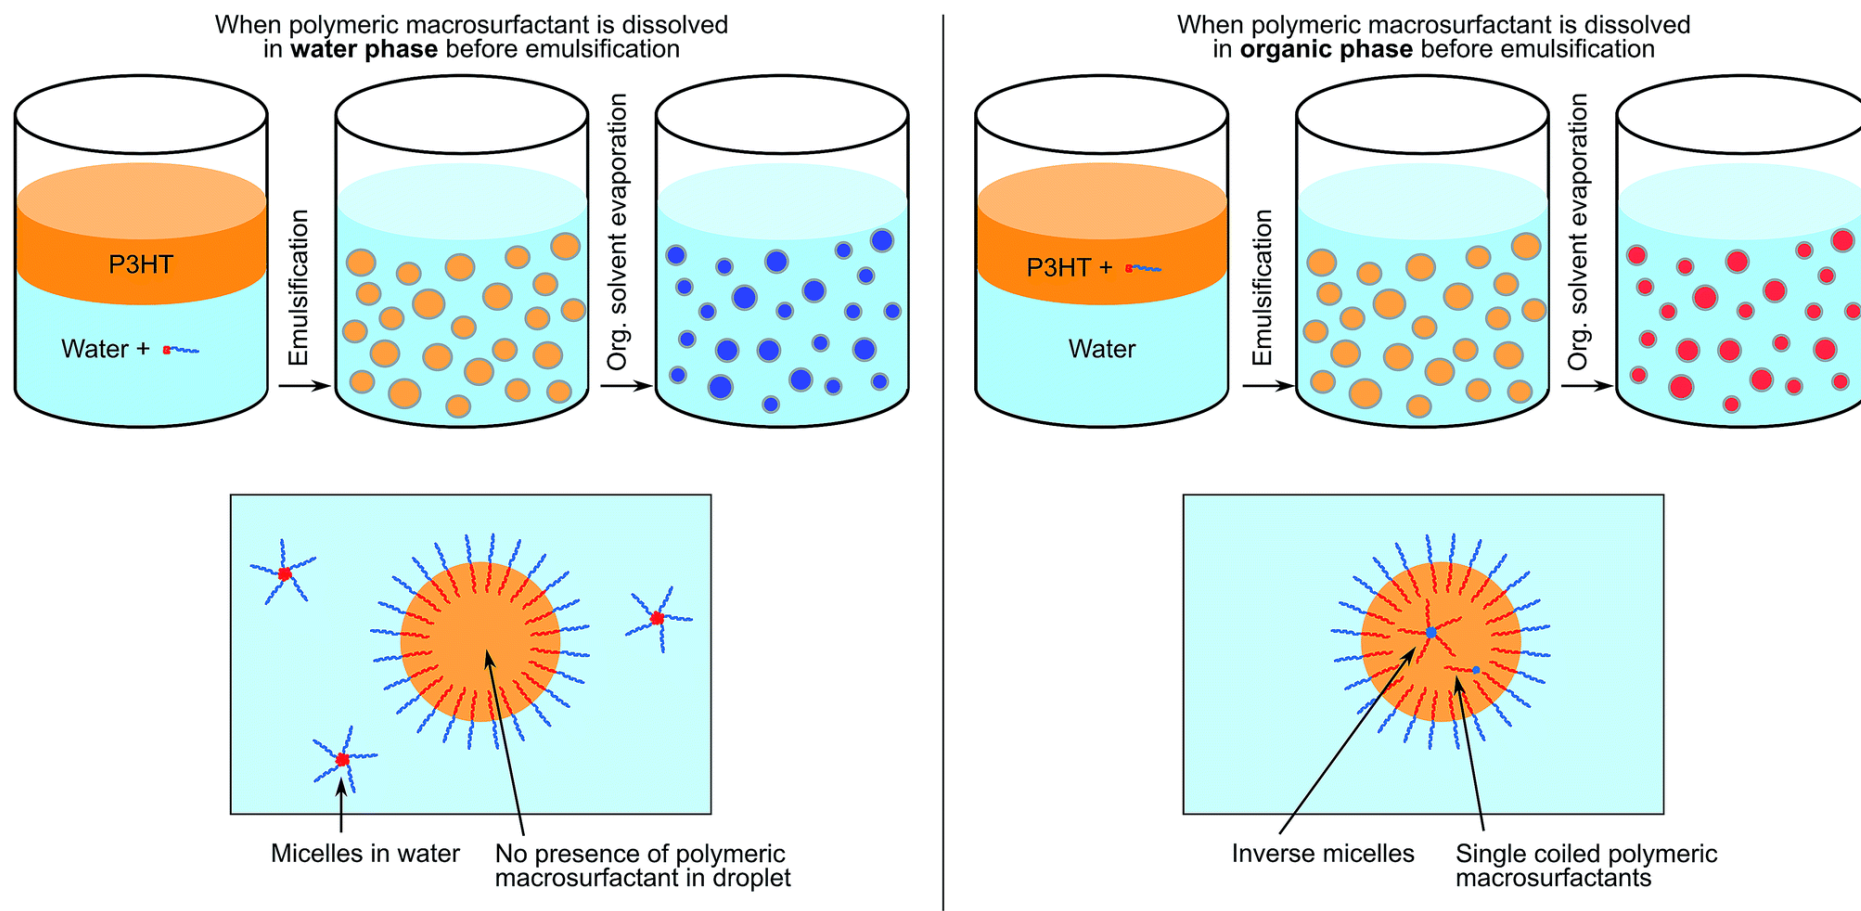


Fig. 2 Schematic illustration of the route used to produce P3HT:water dispersions. The polymeric macro surfactant is dissolved either (a) in the water or (b) organic phase, respectively, before emulsification via mechanical stirring or ultrasonification. In the final step the organic solvent is removed, leading to solid P3HT particles dispersed in water.

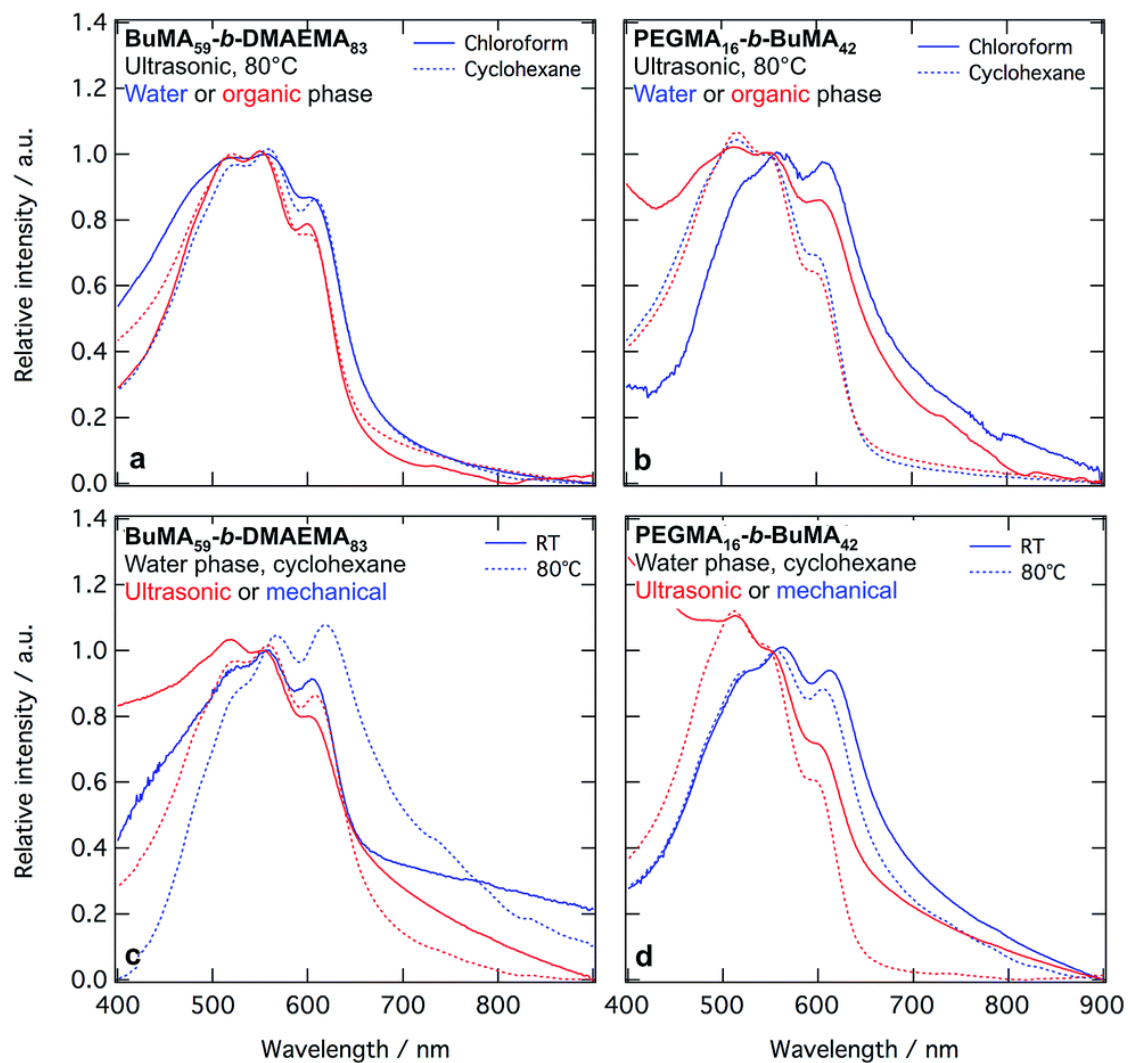


Fig. 3 UV-vis absorption spectra of P3HT dispersions made with (a) BuMA₅₉-b-DMAEMA₈₃ and (b) PEGMA₁₆-b-BuMA₄₂, respectively, whereby the macrosurfactant was dissolved in the water- (blue) or oil phase (red), chloroform (solid line) or cyclohexane (dotted line) was used as the solvent for P3HT. UV-vis absorption spectra of P3HT dispersions made with (c) BuMA₅₉-b-DMAEMA₈₃ and (d) PEGMA₁₆-b-BuMA₄₂, respectively. These emulsions were homogenised ultrasonically (red) or mechanically (blue) at RT (solid line) or 80 °C (dotted line). Thereby, the macrosurfactant was dissolved in the water phase and cyclohexane was used to dissolve P3HT.

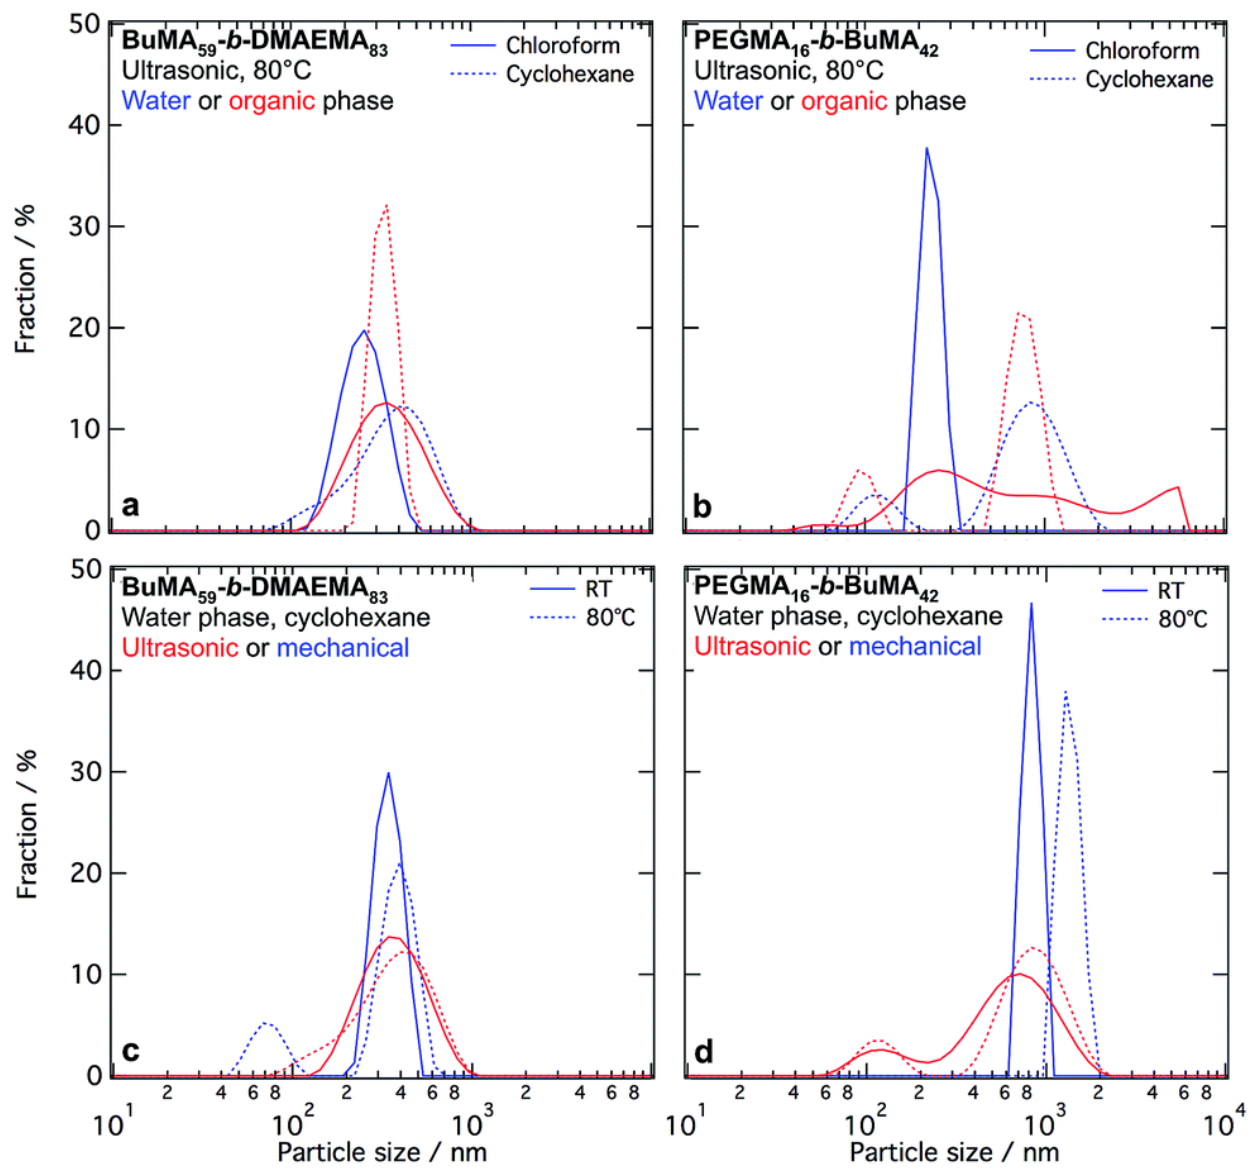


Fig. 4 Size distribution of P3HT particles in dispersions made with (a) BuMA₅₉-b-DMAEMA₈₃ and (b) PEGMA₁₆-b-BuMA₄₂, respectively, where the macrosurfactant was dissolved in the water- (blue) or oil phase (red) and chloroform (solid line) or cyclohexane (dotted line) was used to dissolve the P3HT. Size distribution of P3HT particles in dispersions made with (c) BuMA₅₉-b-DMAEMA₈₃ and (d) PEGMA₁₆-b-BuMA₄₂, respectively, whereby the emulsions were homogenised ultrasonically (red) or mechanically (blue) at RT (solid line) or 80 °C (dotted line), with the macrosurfactant being dissolved in the water phase and cyclohexane as solvent for P3HT.

Supplementary Information

Solubility behaviour of the polymeric macrosurfactant

The behaviour of the macrosurfactant in a solvent provides an indication of how it would behave in the emulsion. Therefore we dissolved both macrosurfactants (which distinguish in the type of the hydrophilic block and block length) in water, cyclohexane and chloroform, the same solvents as we used in the emulsions. In an organic solvent, the block copolymers form in general inverse micelles with the hydrophobic block (BuMA) forming the shell (stretched chains) and the hydrophilic block (PEGMA or DMAEMA) coiled in the core. The theoretical value of the inverse PEGMA₁₆-*b*-BuMA₄₂ micelles is 25.4 nm, for BuMA₅₉-*b*-DMAEMA₈₃ 46 nm. In chloroform and cyclohexane, we found an average feature size close to the theoretical values of inverse micelles for both macrosurfactants (see Fig. S1), i.e. they form inverse micelles in these solvents. In addition, there appears a peak at a few nm when dissolved in chloroform. These are coiled single molecules (theoretically PEGMA₁₆-*b*-BuMA₄₂: 2.84 nm, BuMA₅₉-*b*-DMAEMA₈₃: 4.44 nm) because all homopolymers of the block copolymers are well soluble in chloroform. The exception is PEGMA₁₆-*b*-BuMA₄₂ in chloroform where average size of the features is 100 nm.

In water, micelles are formed in theory but the features we found are much larger than expected (see Fig. S1). For BuMA₅₉-*b*-DMAEMA₈₃, the features are about the double of the theoretical value (57 nm). Most probably, micelles with not as collapsed chains in the core or small aggregates are formed. For PEGMA₁₆-*b*-BuMA₄₂, even bigger aggregates are formed.

The theoretical value of the inverse PEGMA₁₆-*b*-BuMA₄₂ micelles is 25.4 nm, for BuMA₅₉-*b*-DMAEMA₈₃ 46 nm. The theoretical value assumes that the polymer chains are fully extended and that the hydrophilic block is in the core of the micelle, while the hydrophobic block in the corona of the micelle (similar to Raduan et al²⁵).


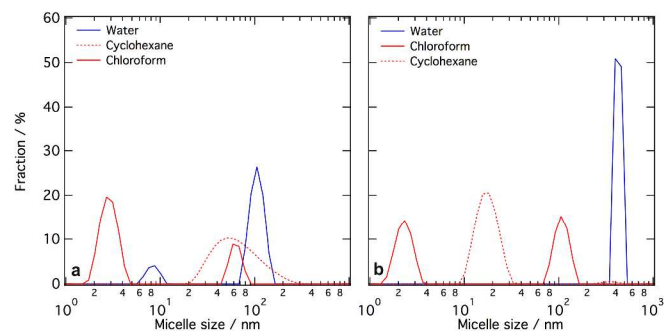


Fig. S1: Size distribution of a) BuMA₅₉-*b*-DMAEMA₈₃ and b) PEGMA₁₆-*b*-BuMA₄₂ micelles, respectively, in water, chloroform or cyclohexane.



Size distribution of a) BuMA59-b-DMAEMA83 and b) PEGMA16-b-BuMA42 micelles, respectively, in water, chloroform or cyclohexane.

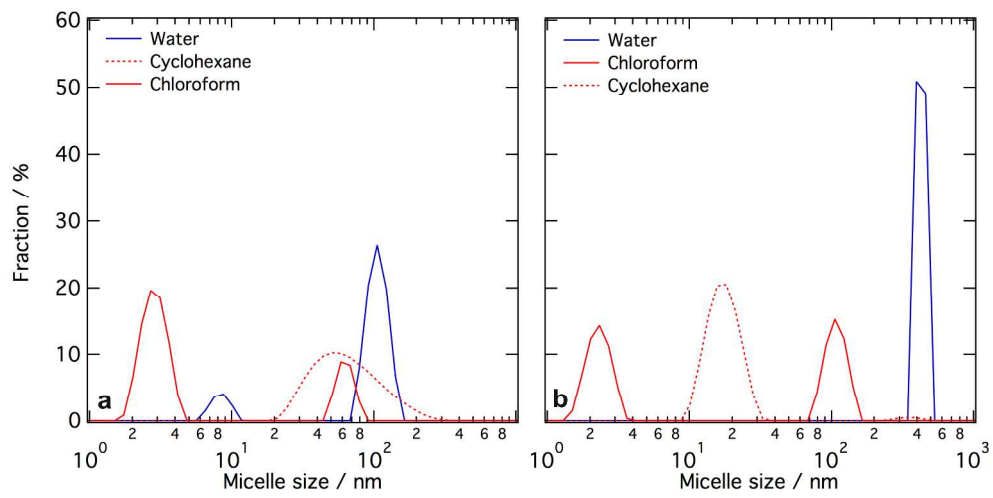