

1 Use of Monosaccharides in Metal-Catalyzed Coupling Reactions

2 Sara H. Kyne^{*,†} and Jason E. Camp^{*,‡}

3 [†]School of Chemistry, University of Lincoln, Lincoln LN6 7TS, United Kingdom

4 [‡]Department of Chemical Sciences, University of Huddersfield, Huddersfield HD1 3DH, United Kingdom

5 **ABSTRACT:** The addition of monosaccharides to metal-
6 catalyzed coupling reactions can be beneficial in terms of
7 decreasing the time required, chemical waste products and
8 overall cost of the process. Monosaccharides are used in a
9 number of different ways, including (a) acting as a ligand for
10 the metal, (b) providing the appropriate reduction potential
11 for a chemical process and (c) acting as a reducing agent for
12 the formation and stabilization of catalytically active metal
13 nanoparticles. Recently, there has been a significant amount of
14 research in this growing field and there is thus the potential for
15 the addition of monosaccharides to coupling reactions to have
16 a significant impact on the synthesis of the important small
17 molecules on which we have all come to rely. This Perspectives
18 Article will cover recent developments in the addition of monosaccharides to metal-catalyzed coupling reactions with an
19 emphasis on their utility and limitations in order to facilitate the further development of this exciting area of research.

20 **KEYWORDS:** Monosaccharide, Biorenewables, Metal catalysis, Green chemistry, Nanoparticle




21 ■ INTRODUCTION

22 Metal-catalyzed coupling processes are a ubiquitous part of the
23 modern chemists' toolkit for the synthesis of added-value small
24 molecules on which we have all come to rely. To make these
25 processes more efficient, in terms of time, expense and cost to
26 the environment, unmodified monosaccharides have been
27 added to metal-catalyzed reactions as part of research into
28 the use of biorenewables in catalytic/chemical reactions. The
29 addition of monosaccharides can serve many purposes in these
30 reactions, including (a) acting as a ligand for the metal, (b)
31 providing the reduction potential for a chemical process and (c)
32 acting as a reducing agent for the formation and stabilization of
33 catalytically active metal nanoparticles. The ability of
34 monosaccharides to reduce metals has been known for
35 decades,¹ for example Benedict's² or Fehling's tests,³ but their
36 use in cross-coupling reactions has flourished in recent years.
37 This review will focus on the latest uses of monosaccharides in
38 metal-catalyzed coupling reactions. Because of recent reviews
39 and full publications, the following areas will not be covered in
40 this review: polysaccharides,^{4–9} smaller sugar derived alde-
41 hydes/carboxylic acids (Leuckart–Wallach reaction)^{10–16} or
42 reactions in which sugars are used as starting materials or
43 incorporated into the molecule.^{17–24}

44 ■ MONOSACCHARIDES AS LIGANDS

45 One of the most common uses of monosaccharides in metal-
46 catalyzed reactions are as ligands for a catalytically active metal
47 species.²⁵ For example, Sekar and Thakur recently disclosed the
48 synthesis of phenols **2** from aryl halides **1** in a process that was
49 catalyzed by a copper/glucose system (Scheme 1).²⁶ Aryl
50 iodides and bromides **1** were reacted with excess potassium

Scheme 1. Synthesis of Phenols **2** from Aryl Halides **1**

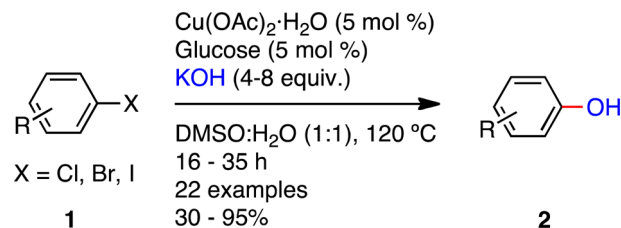


hydroxide (4–8 equiv) in the presence of copper(II) acetate (5
51 mol %) and D-glucose (5 mol %) to give good to excellent
52 yields of the corresponding phenols **2**. The reactivity of aryl
53 chlorides depended on the nature of the electron withdrawing
54 group with substrates containing a nitro group giving an
55 excellent yield of phenol **2**.²⁶

56 Recently, a number of carbon–nitrogen cross-coupling
57 reactions have been developed employing a catalytic system
58 formed *in situ* from copper(I) iodide and D-glucosamine in the
59 presence of base.²⁷ For example, anilines were formed from aryl
60 halides in the presence of excess aqueous ammonia (10 equiv)
61 or sodium azide (3 equiv).^{28,29} Zhang et al. reported the use of
62 similar conditions for the cross-coupling of aryl halides **3** with
63 nitrogen heterocycles **4** (1.2 equiv.; Scheme 2).³⁰ Most of the
64 examples used imidazole as the heterocycle **4**, and good yields
65 were observed for aryl iodides **3** bearing electron-withdrawing
66

Received: August 10, 2016

Revised: September 12, 2016


Scheme 2. Cross-Coupling of Aryl Halides **3** with Nitrogen Heterocycles **4**

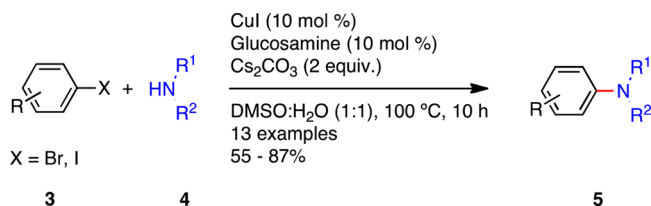

67 groups. Unfortunately, the reaction did not occur with aryl
68 chlorides.

69 Zhang et al. extended this methodology to carbon–sulfur
70 cross-coupling reactions. In this work, aryl iodides **6** were
71 reacted with diphenyl disulfide (**7**, 0.6 equiv) in the presence of
72 copper(I) iodide (10 mol %), D-glucosamine (10 mol %) and
73 cesium carbonate (2 equiv) to give the corresponding
74 unsymmetrical diaryl sulfide **8** (Scheme 3).³⁰ When aryl


Scheme 3. Carbon–Sulfur Cross-Coupling Reaction

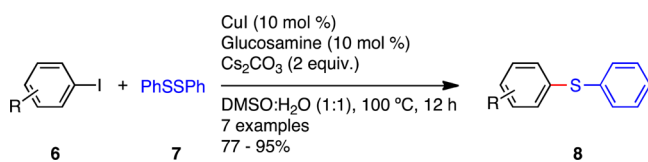

75 bromides were tested the reaction occurred, but required 24
76 h to go to completion. Similar methodology was used by the
77 same group to synthesize a variety of diaryl sulfones from aryl
78 halides and sodium benzenesulfonates.³¹

79 D-Glucosamine has also been successfully employed as a
80 ligand in iron-catalyzed Grignard cross-coupling reactions of
81 vinylic **10** and allylic bromides **11** (Scheme 4). Phenyl- or


Scheme 4. D-Glucosamine Successfully Employed as a Ligand in Iron-Catalyzed Grignard Cross-Coupling Reactions

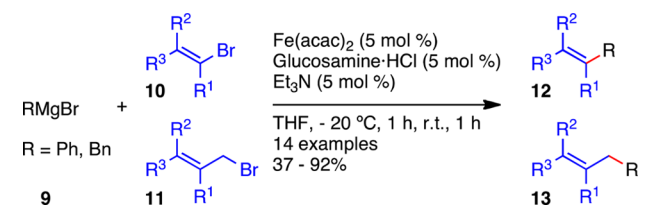

82 benzylmagnesium bromides **9** were reacted with bromides **10**
83 or **11** in the presence of iron(II) acetylacetonate (5 mol %) and
84 D-glucosamine hydrochloride (5 mol %). Triethylamine (5 mol
85 %) was added to deprotonate the ligand and thus increase its
86 solubility in THF.³² Moderate yields of substituted alkenes **12**
87 were obtained from allylic bromides **10**, and good yields of the
88 sp³-hybridized products **13** were obtained from alkenyl
89 bromides **11**.

90 D-Glucosamine was shown to improve the yield in palladium-
91 catalyzed Mizoroki–Heck reactions of aryl halides (Scheme
92 5).³³ Aryl halides **14** were reacted with activated alkenes **15**
93 (1.2 equiv) in the presence of palladium(II) acetate (0.5 mol
94 %), D-glucosamine (1 mol %) and potassium carbonate (2.0
95 equiv). Aryl iodides and bromides afforded good to excellent
96 conversion to stilbenes **16** with unsubstituted and *para*-
97 substituted electron withdrawing groups. Conversion was

Scheme 5. D-Glucosamine Shown To Improve Yield in Palladium-Catalyzed Mizoroki–Heck Reactions of Aryl Halides

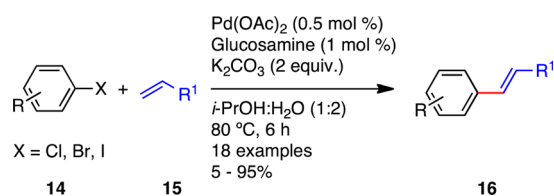


moderate when the arene was substituted at the *ortho* position. 98
Aryl chlorides **14** reacted, albeit with low conversion (5–25%). 99

MONOSACCHARIDES FOR NANOPARTICLE FORMATION

One of the most common uses of monosaccharides in organic
transformations are as reductants for the formation of metal
nanoparticles, in which the sugar serves to reduce the metal in
the presence of a template.^{34–45} Monosaccharides, glucose in
particular, have also been used as supports for metal
nanoparticles.^{46–49} In some cases, the monosaccharides act as
both the stabilizer for the metal nanoparticles as well as the
reducing agent.^{50–54} Alternatively, additional reducing agents
can be added to the mixture of sugar and metal if required. For
example, monodispersed colloidal carbon spheres have been
synthesized by a two-step hydrothermal approach under mild
conditions by Sun et al.⁵⁵ In this work, separating the
nucleation and growth steps allowed for a narrow size
distribution with diameters ranging from 160 to 400 nm.
Interestingly, the size distribution decreased with an increasing
concentration of glucose. D-Glucose has also been used as the
metal nanoparticle support. In this case, palladium(0) nano-
particles were synthesized by the reduction of H₂[PdCl₄] or
[Pd(NH₃)₄Cl₂]Cl₂ in the presence of excess hydroxylamine and
D-glucose under ambient, aqueous conditions.⁵⁶ Character-
ization of the palladium nanoparticles revealed magnetization
differences depending on the oxidation state of the palladium
precursor. TEM analysis revealed that when starting from the
Pd(II) complex, the nanoparticles were an average size of 6 nm
and polydispersed, whereas starting from the Pd(IV) complex
formed nanoparticles with an average size of 8 nm that were
mainly monodispersed. In 2004, Sun and Li reported the
synthesis of colloidal carbon spheres starting from glucose,
which underwent subsequent functionalization due to the
reactive surface present.⁵⁷ For example, the FTIR spectrum
revealed the existence of carbonyl and hydroxyl groups that
maintained the hydrophilicity of the carbon spheres. Colloidal
carbon spheres were prepared from aqueous glucose by
hydrothermal synthesis, undergoing aromatization and carbon-
ization to form 200 nm carbon spheres at 160 °C in 3.5 h, and
1500 nm at 180 °C in 10 h. Under reflux, palladium(0)
nanoparticles were loaded onto the surface, covering the carbon
spheres with a uniform shell of 10–20 nm palladium. In related
methodology, Zhang et al. described the preparation of highly
dispersed, narrow diameter palladium nanoparticles on carbon
spheres via *in situ* reduction.⁵⁸ Precise control of the dispersity
and size of the palladium(0) nanoparticles was possible by
careful adjustment of the reaction conditions (temperature,
time, pH and ratio of palladium(0) to carbon spheres).
Homogeneously distributed, small diameter (7.7 nm) palladium
crystals were prepared on carbon spheres at pH 7.0 in ethanol
at 70 °C.

149 The isolated metal nanoparticles have subsequently been
 150 used in a number of important catalytic processes. For example,
 151 Sen et al. recently reported a palladium(0) nanoparticle
 152 catalyzed domino Sonogashira-cyclization reaction to synthe-
 153 size various isoindolinones **20** and furoquinolines **21** in good
 154 yields (Scheme 6).⁵⁹ Palladium(0) nanoparticles were prepared

Scheme 6. Palladium(0) Nanoparticle Catalyzed Domino Sonogashira-Cyclization Reaction to Synthesize Various Isoindolinones **20 and Furoquinolines **21****

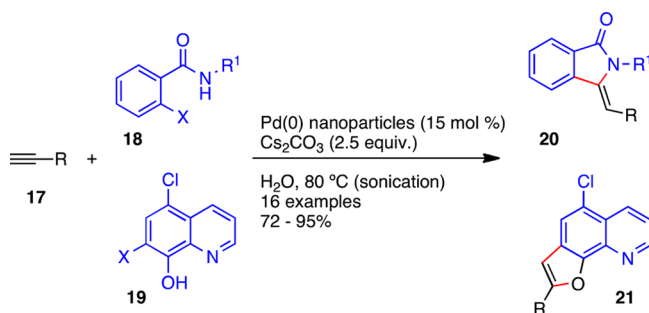


155 by the procedure of Sarkar et al. in which $H_2[PdCl_4]$ was
 156 reduced in the presence of hydroxylamine and D-glucose under
 157 aqueous conditions.⁵⁶ Following the reaction, the catalyst could
 158 be recovered in high yield and a recycling study showed only a
 159 gradual decrease in activity for up to five subsequent reactions
 160 before significant loss of yield was observed.

161 ■ MONOSACCHARIDES AS REDUCTANTS IN CHEMICAL PROCESSES

162 Monosaccharides can also be added to organic transformations
 163 to act as reductants for chemical process that occur in the
 164 absence of catalyst^{60,61} or to reduce a metal precatalyst to the
 165 necessary oxidation state *in situ* so that the reaction can
 166 proceed. This concept has been employed for a variety of
 167 reactions such as dehalogenations,⁶² reductions^{63–66} and
 168 coupling processes. Glucose can also be used for the *in situ*
 169 formation of the active metal catalyst. For example, Cuevas-
 170 Yañez et al. showed that addition of 25 mol % of glucose to the
 171 reaction mixture resulted in an increased yield of the desired
 172 triazoles **24** from alkynes **22** and azides **23** under copper-
 173 catalyzed click reaction conditions (Scheme 7).⁶⁷

Scheme 7. Increased Yield of the Desired Triazoles **24 from Alkynes **22** and Azides **23** under Copper-Catalyzed Click Reaction Conditions**

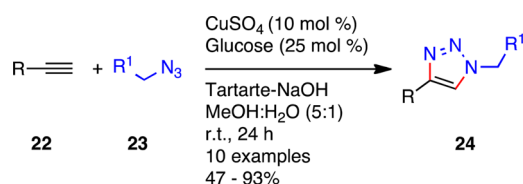

175 In related work, Singh et al. showed that it was beneficial to
 176 add glucose to copper-catalyzed click reactions⁶⁸ that were part
 177 of multicomponent coupling reactions under microwave
 178 conditions (Scheme 8). Thus, the three component reaction
 179 of phenylazides **25**, 4-(prop-2-yn-1-yloxy)benzaldehydes **26**,
 180 and 1,2-diaminobenzenes **27** afforded the triazole adducts **28** in
 181 good yields (Scheme 8a).⁶⁹ Additionally, a four component
 182 process resulted in the efficient formation of 3-phenyl-2-[4-((1-

phenyl-1H-1,2,3-triazol-4-yl)methoxy}phenyl]thiazolidin-4-
 ones **29** from readily available starting materials (Scheme 8b).⁷⁰
 In both cases, the glucose is purported to reduce the copper to
 the catalytically active species. Related work by Wan et al.
 demonstrated that copper–glucose systems catalyzed the three
 component reactions of phenols, acyl chlorides and Wittig
 reagents to form β -aryloxy acrylates.⁷¹ Furthermore, Guchhait
 et al. developed a novel A³-coupling methods for the synthesis
 of N-fused imidazoles using a copper(II) sulfate–glucose
 catalyst.⁷² This methodology was subsequently harnessed by
 Iyer et al. for the synthesis of luminescent imidazo[1,2-
 a]pyridines.⁷³


■ MONOSACCHARIDES FOR THE IN SITU FORMATION/STABILIZATION OF CATALYSTS

One of the most important advances in this area is the ability to
 form catalytically active metal nanoparticles *in situ* from
 unmodified reducing sugars and subsequently recycle the
 catalyst. Traditionally, bioderived metal catalysts need to be
 synthesized and isolated prior to reaction, and are frequently
 difficult to recycle following the reaction, which can increase
 the amount of time, chemical waste and expense of the overall
 process.^{74–81} Building upon the work in nanoparticle formation
 from reducing sugars, and the use of reducing sugars as
 reductants in catalytic processes, Nacci et al. recently disclosed
 an Ullman type homocoupling of aryl halides catalyzed by *in*
situ generated palladium(0) nanoparticles (Scheme 9).⁸² Thus,
 the homocoupling of bromo- and chloroarenes **30** in the
 presence of glucose (0.5 equiv), palladium(II) acetate (3 mol
 %) and tetrabutylammonium hydroxide (3.0 equiv) afforded
 the desired biaryls **31** in good yield. In this process, the glucose
 is postulated to both reduce the palladium(II) acetate to the
 catalytically active palladium(0) species, as well as stabilize the
in situ formed catalyst through the formation of nanoparticles.
 In contrast to other related reports (*vide infra*), exogenous
 capping agents were used in this study. TEM analysis was used
 to confirm the formation of nanoparticles, which had an
 average particle size around 15 nm, and XPS was used to show
 that the palladium in the isolated nanoparticles was in the zero
 oxidation state. A recycling study demonstrated that the
 catalytic solution was active for 3 cycles, but the yield decreased
 precipitously thereafter.


Nacci et al. also showed that an Ullman type homocoupling
 of haloarenes **32** to give the corresponding biaryls **33** could be
 facilitated by gold nanoparticles formed *in situ* from the
 reduction of gold(III) acetate (2 mol %) with a stoichiometric
 amount of glucose (Scheme 10).⁸³ This catalytic system was
 active for bromo- and iodo-substituted arenes **32**, as well as
 alkenes. The less reactive aryl chlorides were found to be
 unreactive under the reaction conditions. It was also found that
 the ionic liquid tetrabutylammonium acetate (TBAA) was a
 competent solvent and base for the reaction, which could
 substitute for water. Interestingly, the nanoparticles formed in
 the ionic liquid were much larger than those formed in water
 (ca. 2 nm vs. Twenty nm respectively) and in general resulted
 in a decreased yield compared to the aqueous conditions.
 Unfortunately, attempts at recycling these catalysts showed a
 similar poor performance to the palladium system discussed
 above (cf. Scheme 9).

Recently, we disclosed methods for the use of glucose
 derived palladium(0) nanoparticles as *in situ* formed catalysts
 for Suzuki–Miyaura cross-coupling reactions in the green
 solvent isopropyl alcohol (Scheme 11).⁸⁴ The cross-coupling of


Scheme 8. Four Component Process Resulted in the Efficient Formation of 3-Phenyl-2-[4-((1-phenyl-1H-1,2,3-triazol-4-yl)methoxy)phenyl]thiazolidin-4-ones 29

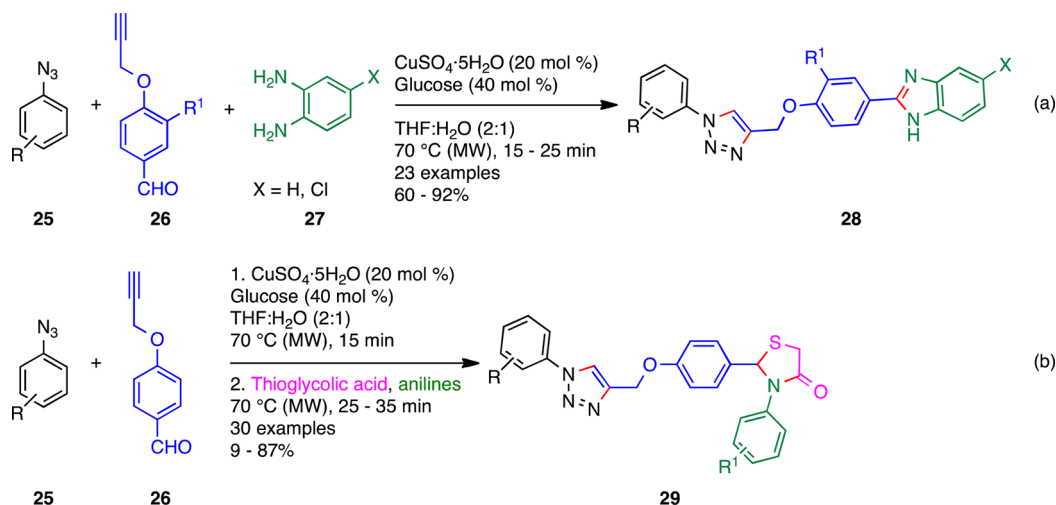


Scheme 9. Ullman Type Homocoupling of Aryl Halides Catalyzed by *in Situ* Generated Palladium(0) Nanoparticles

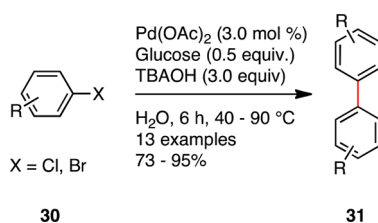

Scheme 10. Ullman Type Homocoupling of Haloarenes 32 To Give Corresponding Biaryls 33 Facilitated by Gold Nanoparticles Formed *in Situ* from Reduction of Gold(III) Acetate with Stoichiometric Amount of Glucose

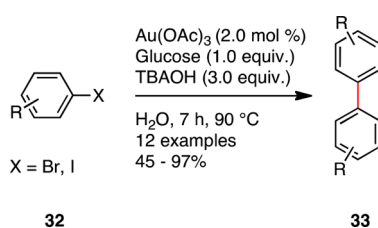

Scheme 11. Use of Glucose Derived Palladium(0) Nanoparticles as *in Situ* Formed Catalysts for Suzuki–Miyaura Cross-Coupling Reactions Green Solvent Isopropyl Alcohol

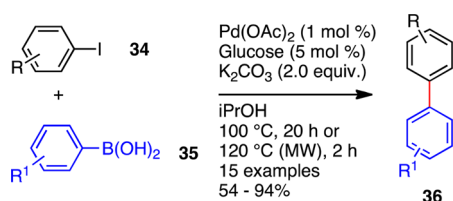


245 aryl iodides 34 and aryl boronic acids 35 in the presence of
246 palladium(II) acetate (1 mol %) and glucose (5 mol %) gave
247 the desired biaryls 36 in moderate to good yields under either
248 thermal or microwave heating conditions. In contrast to the
249 reports of Nacci et al., only a small amount of glucose was
250 required and no capping agents were employed. EF-TEM

analysis of the *in situ* formed nanoparticles showed that the
251 palladium was surrounded by a hydrophilic, hydroxylated shell.
252 The hydrophilic/polar nature of the nanoparticles allowed for
253 their facile removal from the cross-coupled product. ICP-MS
254 analysis showed a 65% decrease in the amount of metal
255 incorporated into the final compounds compared to reactions
256 that did not contain glucose. Interestingly, Jiang and Fossey et
257 al. have found that monosaccharides bind to boronic acid to
258 form the less reactive boronate ester. They used the retardation
259 of the Suzuki–Miyaura homocoupling reaction to develop
260 fluorescent sensors for glucose detection.^{85,86}

261
262 Subsequently, Jain et al. described the use of reducing sugars
263 in palladium mediated cross-coupling reactions, in which the
264 metal was catalyzing multiple, mechanistically distinct steps;
265 autotandem catalysis^{87,88} (Scheme 12).⁸⁹ After screening nine

Scheme 12. Use of Reducing Sugars in Palladium Mediated Cross-Coupling Reactions

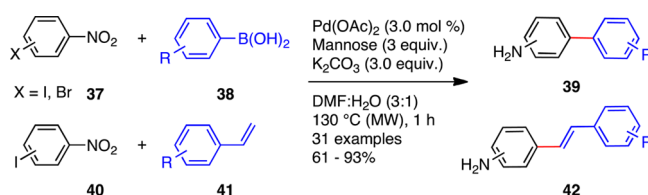


266 difference reducing sugars, they found that the addition of
267 mannose (3 equiv) gave the desired cross-coupled products of
268 Suzuki–Miyaura and Mizoroki–Heck reactions, while con-
269 currently reducing the nitro functionality to an aniline. For
270 example, reaction of halo-nitrobenzenes 37 with arylboronic
271 acids 38 in aqueous DMF at 130 °C (microwave) gave the
272 coupled biaryl anilines 39 in moderate to excellent yields.
273 Similarly, the reaction of iodo-nitrobenzenes 40 with styrenes
274 41 under the same reaction conditions afforded substituted
275 amino-stilbenes 42 in good to excellent yields. It is unclear from
276 the analysis conducted by the researchers whether the mannose
277 is simply acting as a ligand and source of hydrogen under the
278 reaction conditions, or if it is also stabilizing *in situ* formed
279 nanoparticles.

280 Building upon our work discussed above, we recently
281 reported the use of glucose derived nanoparticles for the

282 Mizoroki–Heck, Sonogashira and Suzuki–Miyaura cross-
283 coupling reactions in aqueous solvents (Scheme 13).⁹⁰ The

Scheme 13. Use of Glucose Derived Nanoparticles for the Mizoroki–Heck, Sonogashira and Suzuki–Miyaura Cross-Coupling Reactions in Aqueous Solvents

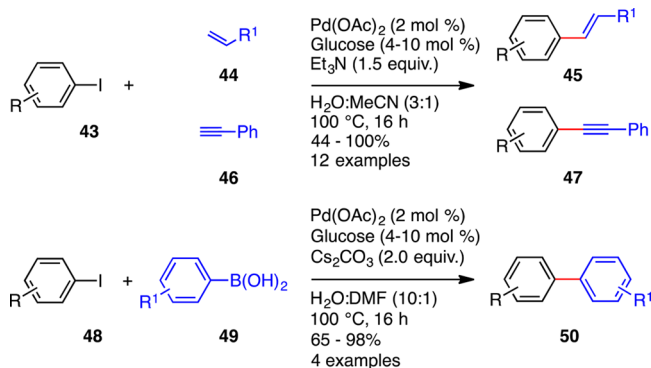

284 reaction of aryl halides 43 with alkenes 44 or alkynes 46
285 proceeded in moderate to excellent yields to afford stilbenes 45
286 or substituted alkynes 47, respectively. The palladium(0)
287 nanoparticle catalysts were formed *in situ* from palladium(II)
288 acetate (2 mol %) via the addition of glucose (4–10 mol %) to
289 the reaction. In addition, a Suzuki–Miyaura protocol for the
290 synthesis of biaryls 50 in aqueous DMF was developed using
291 the same *in situ* derived palladium(0) nanoparticles. Import-
292 tantly, this protocol was also viable for aryl bromides. In
293 contrast to the study by Jian et al.,⁷⁴ the nitro functionality was
294 not reduced in any of the three cross-coupling reactions that
295 were investigated. This is possibly due to the relatively small
296 amount of glucose that was added to the reaction (cf. Scheme
297 12). EF-TEM analysis of the *in situ* formed nanoparticles
298 confirmed that the palladium was surrounded by a hydrophilic,
299 hydroxylated shell. The nature of this shell allowed for the facile
300 partitioning of the catalyst between the aqueous and organic
301 phases, which enabled catalyst recycling for up to four cycles
302 without significant loss of activity.

303 CONCLUSION

304 The importance of the addition of monosaccharides to metal-
305 catalyzed processes in organic chemistry has expanded rapidly
306 in recent years. These biorenewable materials can be used for a
307 number of important processes including as ligands for a metal
308 catalyst, to provide the appropriate reduction potential for a
309 chemical process, and as a reducing agent for the formation and
310 stabilization of catalytically active metal nanoparticles. These
311 recent developments in the field will provide the basis for
312 further rapid advancements. Looking forward, catalytic
313 processes in which the reducing potential of renewable sugars
314 is harnessed for the generation, stabilization and turnover of
315 catalytically active metal nanoparticles, sugar-powered catalysis,
316 will be developed. These processes have the potential to make
317 existing protocols greener in terms of time, expense and cost to
318 the environment, as well as allowing for the development of
319 novel metal-catalyzed processes that are currently not possible.
320 Additionally, the inherent chirality of the monosaccharides will
321 be harnessed in order to develop catalytic access to
322 enantiomerically enriched products. In conclusion, the addition
323 of monosaccharides to metal-catalyzed processes has resulted in
324 a number of important new methods that allow access to the

small molecules on which we have all come to rely. It is
expected that innovative new applications will be developed
that build on this exciting research.

■ AUTHOR INFORMATION

Corresponding Authors

*S. H. Kyne. Email: skyne@lincoln.ac.uk. Tel: +44 (0)15 2283 7402.

*J. E. Camp. Email: j.e.Camp@hud.ac.uk. Tel: +44 (0)14 8447 3180.

Notes

The authors declare no competing financial interest.

Biographies



Sara H. Kyne obtained her Ph.D. from The University of Melbourne (Australia) under the supervision of Prof. Carl H. Schiesser in the area of physical–organic intramolecular radical chemistry. She then undertook a postdoctoral position with Prof. Jonathan M. Percy (University of Strathclyde, UK) and a Marie Curie Intra European Fellowship with Prof. Louis Fensterbank (Université Pierre et Marie Curie, France). She is currently a lecturer at the University of Lincoln working on the development of sustainable catalysis and radical methodology.



Jason E. Camp obtained his Ph.D. from The Pennsylvania State University under the supervision of Prof. Steven Weinreb working on the total synthesis of the chartellamide and chartelline family of marine natural products. He then was a postdoctoral fellow working with Prof. Donald Craig (Imperial College London) before obtaining lectureships at the University of Nottingham and Queen Mary University of London. He is currently a senior lecturer at the University of Huddersfield working on the development of novel autotandem catalysis methods as well as sugar-powered catalysis protocols.

355 ■ REFERENCES

- 356 (1) Mattson, A. M.; Jensen, C. O. Colorimetric determination of
357 reducing sugars with triphenyltetrazolium chloride. *Anal. Chem.* **1950**,
358 *22*, 182–185.
- 359 (2) Benedict, S. R. A reagent for the detection of reducing sugars. *J.*
360 *Biol. Chem.* **1908**, *5*, 485–487.
- 361 (3) Fehling, H. Die quantitative bestimmung von zucker und
362 stärke mittelst kupfervitriol. *Justus Liebigs Ann. Chem.* **1849**, *72*,
363 106–113.
- 364 (4) For a recent review, see: Molnár, Á.; Papp, A. The use of
365 polysaccharides and derivatives in palladium-catalyzed coupling
366 reactions. *Catal. Sci. Technol.* **2014**, *4*, 295–310.
- 367 (5) For a recent review, see: Kaushik, M.; Moores, A. Review:
368 nanocelluloses as versatile supports for metal nanoparticles and their
369 applications in catalysis. *Green Chem.* **2016**, *18*, 622–637.
- 370 (6) Rezayat, M.; Blundell, R. K.; Camp, J. E.; Walsh, D. A.;
371 Thielemans, W. Green, one step synthesis of catalytically active
372 palladium nanoparticles supported on cellulose nanocrystal. *ACS*
373 *Sustainable Chem. Eng.* **2014**, *2*, 1241–1250.
- 374 (7) Kaushik, M.; Basu, K.; Benoit, C.; Cirtiu, C. M.; Vali, H.; Moores,
375 A. Cellulose nanocrystals as chiral inducers: Enantioselective catalysis
376 and transmission electron microscopy 3D characterization. *J. Am.*
377 *Chem. Soc.* **2015**, *137*, 6124–6127.
- 378 (8) Yasukawa, T.; Miyamura, H.; Kobayashi, S. Cellulose-supported
379 chiral rhodium nanoparticles as sustainable heterogeneous catalysts for
380 asymmetric carbon-carbon bond-forming reaction. *Chem. Sci.* **2015**, *6*,
381 6224–6229.
- 382 (9) Ghaderi, A.; Gholinejad, M.; Firouzabadi, H. Palladium deposited
383 on naturally occurring supports as a powerful catalyst for carbon-carbon
384 bond formation reactions. *Curr. Org. Chem.* **2016**, *20*, 327–348.
- 385 (10) Leuckart, R. Ueber die einwirkung von phenylcyanat auf
386 phenole und phenoläther. *Ber. Dtsch. Chem. Ges.* **1885**, *18*, 2341–2344.
- 387 (11) Wallach, O. Zur kenntniss der terpene und der ätherischen oele.
388 ueber die ueberführung von ketonen und aldehyden in basen. *Justus*
389 *Liebigs Ann. Chem.* **1905**, *343*, 54–74.
- 390 (12) Webers, V. J.; Bruce, W. F. The Leuckart reaction: A study of
391 the mechanism. *J. Am. Chem. Soc.* **1948**, *70*, 1422–1424.
- 392 (13) Gibson, H. W. Chemistry of formic acid and its simple
393 derivatives. *Chem. Rev.* **1969**, *69*, 673–692.
- 394 (14) Ledoux, A.; Sandjong Kuigwa, L.; Framery, E.; Andrioletti, B. A
395 highly sustainable route to pyrrolidone derivatives – direct access to
396 biosourced solvents. *Green Chem.* **2015**, *17*, 3251–3254.
- 397 (15) Wei, Y.; Wang, C.; Jiang, X.; Xue, D.; Liu, Z.-T.; Xiao, J.
398 Catalyst-free transformation of levulinic acid into pyrrolidinones with
399 formic acid. *Green Chem.* **2014**, *16*, 1093–1096.
- 400 (16) Neochoritis, C. G.; Stotani, S.; Mishra, B.; Dömling, A. Efficient
401 isocyanide-less isocyanide-based multicomponent reactions. *Org. Lett.*
402 **2015**, *17*, 2002–2005.
- 403 (17) Plazl, I. P.; Leskovšek, S.; Koloini, T. Hydrolysis of sucrose by
404 conventional and microwave heating in stirred tank reactor. *Chem. Eng.*
405 *J.* **1995**, *59*, 253–257.
- 406 (18) Breuer, M.; Ditrich, K.; Habicher, T.; Hauer, B.; Keßler, M.;
407 Stürmer, R.; Zelinski, T. Industrial methods for the production of
408 optically active intermediates. *Angew. Chem., Int. Ed.* **2004**, *43*, 788–
409 824.
- 410 (19) For a recent example, see: Mensah, E.; Camasso, N.; Kaplan,
411 W.; Nagorny, P. Chiral phosphoric acid directed regioselective
412 acetalization of carbohydrate-derived 1,2-diols. *Angew. Chem., Int. Ed.*
413 **2013**, *52*, 12932–12936.
- 414 (20) For a recent example, see: Caratzoulas, S.; Davis, M. E.; Gorte,
415 R. J.; Gounder, R.; Lobo, R. F.; Nikolakis, V.; Sandler, S. I.; Snyder, M.
416 A.; Tsapatsis, M.; Vlachos, D. G. Challenges of and insights into acid-
417 catalyzed transformations of sugars. *J. Phys. Chem. C* **2014**, *118*,
418 22815–22833.
- 419 (21) For a recent example, see: Galbis, J. A.; de García García-Martín,
420 M.; de Paz, V.; Galbis, E. Synthetic polymers from sugar-based
421 monomers. *Chem. Rev.* **2016**, *116*, 1600–1636.
- (22) For a recent example, see: Saloranta, T.; Leino, R. Unprotected 422
carbohydrates as starting material in chemical synthesis: Not just a 423
challenge but an opportunity. *Synlett* **2015**, *26*, 421–425. 424
- (23) For a recent example, see: Lourenço, L. M. O.; Neves, M. G. P. 425
M. S.; Cavaleiro, J. A. S.; Tomé, J. P. C. Synthetic approaches to 426
glycophthalocyanines. *Tetrahedron* **2014**, *70*, 2681–2698. 427
- (24) For a recent example, see: Adhikary, N. D.; Kwon, S.; Chung, 428
W.-J.; Koo, S. One-pot conversion of carbohydrates into pyrrole-2- 429
carbaldehydes as sustainable platform chemicals. *J. Org. Chem.* **2015**, 430
80, 7693–7701. 431
- (25) Woodward, S.; Diéguez, M.; Pámies, O. Use of sugar-based 432
ligands in selective catalysis: Recent developments. *Coord. Chem. Rev.* 433
2010, *254*, 2007–2030. 434
- (26) Thakur, K. G.; Sekar, G. D-Glucose as green ligand for selective 435
copper-catalyzed phenol synthesis from aryl halides with an easy 436
catalyst removal. *Chem. Commun.* **2011**, *47*, 6692–6694. 437
- (27) Cheng, D.; Gan, F.; Qian, W.; Bao, W. D-Glucosamine – a 438
natural ligand for the N-arylation of imidazoles with aryl and 439
heteroaryl bromides catalyzed by CuI. *Green Chem.* **2008**, *10*, 171– 440
173. 441
- (28) Thakur, K. G.; Ganapathy, D.; Sekar, G. D-Glucosamine as a 442
green ligand for copper catalyzed synthesis of primary aryl amines 443
from aryl halides and ammonia. *Chem. Commun.* **2011**, *47*, 5076– 444
5078. 445
- (29) Thakur, K. G.; Srinivas, K. S.; Chiranjeevi, K.; Sekar, G. D- 446
Glucosamine as an efficient ligand for the copper-catalyzed selective 447
synthesis of anilines from aryl halides and NaN₃. *Green Chem.* **2011**, 448
13, 2326–2329. 449
- (30) Wen, M.; Shen, C.; Wang, L.; Zhang, P.; Jin, J. An efficient D- 450
glucosamine-based copper catalyst for C–X couplings and its 451
application in the synthesis of nilotinib intermediate. *RSC Adv.* 452
2015, *5*, 1522–1528. 453
- (31) Yang, M.; Shen, S.; Li, Y.; Shen, C.; Zhang, P. D-Glucosamine as 454
a green ligand for copper catalyzed synthesis of aryl sulfones from aryl 455
halides and sodium sulfonates. *RSC Adv.* **2014**, *4*, 26295–26300. 456
- (32) Sova, M.; Frlan, R.; Gobec, S.; Stavber, G.; Časar, Z. D- 457
Glucosamine in iron-catalysed cross-coupling reactions of Grignards 458
with allylic and vinylic bromides: application to the synthesis of a key 459
sitagliptin precursor. *Appl. Organomet. Chem.* **2015**, *29*, 528–535. 460
- (33) Amini, M.; Etemadi, H. D-Glucosamine as an efficient and green 461
additive for palladium-catalyzed Heck reaction. *Chem. Pap.* **2013**, *67*, 462
759–763. 463
- (34) For a comprehensive review, see: Dahl, J. A.; Maddux, B. L. S.; 464
Hutchison, J. E. Toward greener nanosynthesis. *Chem. Rev.* **2007**, *107*, 465
2228–2269. 466
- (35) For a recent review, see: Varma, R. S. Journey on greener 467
pathways: from the use of alternate energy inputs and benign reaction 468
media to sustainable applications of nano-catalysts in synthesis and 469
environmental remediation. *Green Chem.* **2014**, *16*, 2027–2041. 470
- (36) For a recent review, see: Gawande, M. B.; Shelke, S. N.; Zboril, 471
R.; Varma, R. S. Microwave-assisted chemistry: synthetic applications 472
for rapid assembly of nanomaterials and organics. *Acc. Chem. Res.* 473
2014, *47*, 1338–1348. 474
- (37) For a recent review, see: Virkutyte, J.; Varma, R. S. Green 475
synthesis of metal nanoparticles: Biodegradable polymers and enzymes 476
in stabilization and surface functionalization. *Chem. Sci.* **2011**, *2*, 837– 477
846. 478
- (38) For a recent review, see: Narayanan, R. Synthesis of green 479
nanocatalysts and industrially important green reactions. *Green Chem.* 480
Lett. Rev. **2012**, *5*, 707–725. 481
- (39) For a recent example, see: Shervani, Z.; Yamamoto, Y. 482
Carbohydrate-directed synthesis of silver and gold nanoparticles: 483
Effect of the structure of carbohydrates and reducing agents on the size 484
and morphology of the composites. *Carbohydr. Res.* **2011**, *346*, 651– 485
658. 486
- (40) For a recent example, see: Shervani, Z.; Yamamoto, Y. Size and 487
morphology controlled synthesis of gold nanoparticles in green 488
solvent: Effect of reducing agents. *Mater. Lett.* **2011**, *65*, 92–95. 489

- (41) For a recent example, see: Moukarzel, W.; Fitremann, J.; Marty, J.-D. Seed-less amino-sugar mediated synthesis of gold nanostars. *Nanoscale* **2011**, *3*, 3285–3290.
- (42) For a recent example, see: Fellingner, T.-P.; White, R. J.; Titirici, M.-M.; Antonietti, M. Borax-mediated formation of carbon aerogels from glucose. *Adv. Funct. Mater.* **2012**, *22*, 3254–3260.
- (43) For a recent example, see: Kahrilas, G. A.; Haggren, W.; Read, R. L.; Wally, L. M.; Fredrick, S. J.; Hiskey, M.; Prieto, A. L.; Owens, J. E. Investigation of antibacterial activity by silver nanoparticles prepared by microwave-assisted green syntheses with soluble starch, dextrose, and arabinose. *ACS Sustainable Chem. Eng.* **2014**, *2*, 590–598.
- (44) Gole, A.; Kumar, A.; Phadtare, S.; Mandale, A. B.; Sastry, M. Glucose induced *in-situ* reduction of chloroaurate ions entrapped in a fatty amine film: formation of gold nanoparticle–lipid composites. *PhysChemComm* **2001**, *4*, 92–95.
- (45) Xiong, L.; Tong, Z.-H.; Li, L.-L.; Yu, H.-Q. Morphology dependent antimicrobial activity of Cu/Cu_xO nanoparticles. *Ecotoxicology* **2015**, *24*, 2067–2072.
- (46) Jin, M.; He, G.; Zhang, H.; Zeng, J.; Xie, Z.; Xia, Y. *Angew. Chem., Int. Ed.* **2011**, *50*, 10560–10564.
- (47) Huang, X.; Li, Y.; Zhou, H.; Zhong, X.; Duan, X.; Huang, Y. Simplifying the creation of dumbbell-like Cu-Ag nanostructures and their enhanced catalytic activity. *Chem. - Eur. J.* **2012**, *18*, 9505–9510.
- (48) Stojanović, Z.; Otoničar, M.; Lee, J.; Stevanović, M. M.; Hwang, M. P.; Lee, K. H.; Choi, J.; Uskokovic, D. The solvothermal synthesis of magnetic iron oxide nanocrystals and the preparation of hybrid poly(l-lactide)–polyethyleneimine magnetic particles. *Colloids Surf., B* **2013**, *109*, 236–243.
- (49) Kumar, D. V. R.; Kim, I.; Zhong, Z.; Kim, K.; Lee, D.; Moon, J. Cu(II)–alkyl amine complex mediated hydrothermal synthesis of Cu nanowires: exploring the dual role of alkylamines. *Phys. Chem. Chem. Phys.* **2014**, *16*, 22107–22115.
- (50) Sun, X.; Li, Y. Colloidal carbon spheres and their core/shell structures with noble-metal nanoparticles. *Angew. Chem., Int. Ed.* **2004**, *43*, 597–601.
- (51) Chen, C.; Sun, X.; Jiang, X.; Niu, D.; Yu, A.; Liu, Z.; Li, J. G. A two-step hydrothermal synthesis approach to monodispersed colloidal carbon spheres. *Nanoscale Res. Lett.* **2009**, *4*, 971–976.
- (52) Kong, L.; Lu, X.; Bian, X.; Zhang, W.; Wang, C. Accurately tuning the dispersity and size of palladium particles on carbon spheres and using carbon spheres/palladium composite as support for polyaniline in H₂O₂ electrochemical sensing. *Langmuir* **2010**, *26*, 5985–5990.
- (53) For a recent example, see: Zhang, P.; Gong, Y.; Li, H.; Chen, Z.; Wang, Y. Solvent-free aerobic oxidation of hydrocarbons and alcohols with Pd@N-doped carbon from glucose. *Nat. Commun.* **2013**, *4*, 1593–1604.
- (54) Nie, T.; Wu, H.; Wong, K.-H.; Chen, T. Facile synthesis of highly uniform selenium nanoparticles using glucose as the reductant and surface decorator to induce cancer cell apoptosis. *J. Mater. Chem. B* **2016**, *4*, 2351–2358.
- (55) Chen, C.; Sun, X.; Jiang, X.; Niu, D.; Yu, A.; Liu, Z.; Li, J. G. A two-step hydrothermal synthesis approach to monodispersed colloidal carbon spheres. *Nanoscale Res. Lett.* **2009**, *4*, 971–976.
- (56) Nouh, E. S. A.; Roy, M.; Sarkar, S. Glucose stabilized magnetic palladium nanoparticles exhibiting enhanced magnetic properties under exposure to hydrogen. *Mater. Express* **2012**, *2*, 275–284.
- (57) Sun, X.; Li, Y. Colloidal carbon spheres and their core/shell structures with noble-metal nanoparticles. *Angew. Chem., Int. Ed.* **2004**, *43*, 597–601.
- (58) Kong, L.; Lu, X.; Bian, X.; Zhang, W.; Wang, C. Accurately tuning the dispersity and size of palladium particles on carbon spheres and using carbon spheres/palladium composite as support for polyaniline in H₂O₂ electrochemical sensing. *Langmuir* **2010**, *26*, 5985–5990.
- (59) Pal, R.; Chatterjee, N.; Roy, M.; Nouh, E. S. A.; Sarkar, S.; Jaisankar, P.; Sarkar, S.; Sen, A. K. *Tetrahedron Lett.* **2016**, *57*, 43–47.
- (60) Rostamizadeh, S.; Aryan, R.; Ghaieni, H. R. Aqueous 1 M glucose solution as a novel and fully green reaction medium and catalyst for the oxidant-free synthesis of 2-arylbenzimidazoles. *Synth. Commun.* **2011**, *41*, 1794–1804.
- (61) Aryan, R.; Beyzaei, H.; Sadeghi, F. Facile synthesis of some novel tetrasubstituted 2,4-diaminopyrimidine derivatives in aqueous glucose solution as a fully green medium and promoter. *J. Heterocyclic Chem.* **2015**, DOI: 10.1002/jhet.2514.
- (62) Weidlich, T.; Opršal, J.; Krejčová, A.; Jašúrek, B. Effect of glucose on lowering Al–Ni alloy consumption in dehalogenation of halogenoanilines. *Monatsh. Chem.* **2015**, *146*, 613–620.
- (63) Kumar, M.; Sharma, U.; Sharma, S.; Kumar, V.; Singh, B.; Kumar, N. Catalyst-free water mediated reduction of nitroarenes using glucose as a hydrogen source. *RSC Adv.* **2013**, *3*, 4894–4898.
- (64) For related nitroarene to aniline reductions using reducing sugars, see: Rajapakse, A.; Barnes, C. L.; Gates, K. S. Synthesis and crystal structure of the azoxydichinyl helicene, pyrido[3,2-*f*]quinolino[6,5-*c*]cinnoline 5-oxide monohydrate. *J. Chem. Crystallogr.* **2011**, *41*, 1712–1716.
- (65) For a related nitroarene to aniline reduction using reducing sugars, see: Soloniewicz, R.; Teodorczyk, M. Spectrophotometric determination of reducing sugars with aromatic nitro compounds. *Microchim. Acta* **1982**, *77*, 105–114.
- (66) For a related nitroarene to aniline reduction using reducing sugars, see: Galbraith, H. W.; Degering, E. F.; Hitch, E. F. The alkaline reduction of aromatic nitro compounds with glucose. *J. Am. Chem. Soc.* **1951**, *73*, 1323–1324.
- (67) García, M. A.; Ríos, Z. G.; González, J.; Pérez, V. M.; Lara, N.; Fuentes, A.; González, C.; Corona, D. Cuevas-Yañez, E. The use of glucose as alternative reducing agent in copper-catalyzed alkyne-azide cycloaddition. *Lett. Org. Chem.* **2011**, *8*, 701–706.
- (68) Kumar, Y.; Bahadur, V.; Singh, A. K.; Parmar, V. S.; Singh, B. K. Microwave-assisted copper azide alkyne cycloaddition (CuAAC) reaction using D-glucose as a better alternative reductant. *J. Indian Chem. Soc.* **2013**, *90*, 1893–1903.
- (69) Kumar, Y.; Bahadur, V.; Singh, A. K.; Parmar, V. S.; Van der Eycken, E.; Singh, B. K. Microwave-assisted Cu(I)-catalyzed, three-component synthesis of 2-(4-((1-phenyl-1H-1,2,3-triazol-4-yl)-methoxy)phenyl)-1H-benzo[*d*]imidazoles. *Beilstein J. Org. Chem.* **2014**, *10*, 1413–1420.
- (70) Kumar, Y.; Matta, A.; Kumar, P.; Parmar, V. S.; Van der Eycken, E.; Singh, B. K. Cu(I)-catalyzed microwave-assisted synthesis of 1,2,3-triazole linked with 4-thiazolidinones: a one-pot sequential approach. *RSC Adv.* **2015**, *5*, 1628–1639.
- (71) Zhang, Y.; Liu, Y.; Wan, J.-P. Copper-catalyzed three-component reactions of phenols, acyl chlorides and Wittig reagents for the synthesis of β -aryloxy acrylates. *New J. Chem.* **2015**, *39*, 1567–1569.
- (72) Guchhait, S. K.; Chandgude, A. L.; Priyadarshani, I. J. *Org. Chem.* **2012**, *77*, 4438–4444.
- (73) Balijapalli, U.; Iyer, S. K. CuO–CuAl₂O₄ and D-glucose catalyzed synthesis of a family of excited state intramolecular proton transfer imidazo[1,2-*a*]pyridine analogues and their optical properties. *Dyes Pigm.* **2015**, *121*, 88–98.
- (74) Shen, C.; Shen, H.; Yang, M.; Xia, C.; Zhang, P. A novel D-glucosamine-derived pyridyl-triazole@palladium catalyst for solvent-free Mizoroki–Heck reactions and its application in the synthesis of Axitinib. *Green Chem.* **2015**, *17*, 225–230.
- (75) Vaccaro, L.; Petrucci, C.; Strappaveccia, G.; Giacalone, F.; Gruttadauria, M.; Pizzo, F. An E-Factor Minimized Protocol for a Sustainable and Efficient Heck Reaction in Flow. *ACS Sustainable Chem. Eng.* **2014**, *2*, 2813–2819.
- (76) Khalafi-Nezhad, A.; Panahi, F. Size-controlled synthesis of palladium nanoparticles on a silica–cyclodextrin substrate: A novel palladium catalyst system for the heck reaction in water. *ACS Sustainable Chem. Eng.* **2014**, *2*, 1177–1186.
- (77) Gatard, S.; Salmon, L.; Deraedt, C.; Ruiz, J.; Astruc, D.; Bouquillon, S. Palladium nanoparticles stabilized by glycodendrimers 625

- 626 and their application in catalysis. *Eur. J. Inorg. Chem.* **2014**, *2014*,
627 4369–4375.
- 628 (78) Puthiaraj, P.; Ahn, W.-S. Highly active palladium nanoparticles
629 immobilized on NH₂-MIL-125 as efficient and recyclable catalysts for
630 Suzuki–Miyaura cross coupling reaction. *Catal. Commun.* **2015**, *65*,
631 91–95.
- 632 (79) Song, H.-Q.; Zhu, Q.; Zheng, X.-J.; Chen, X.-G. J. One-step
633 synthesis of three-dimensional graphene/multiwalled carbon nano-
634 tubes/Pd composite hydrogels: an efficient recyclable catalyst for
635 Suzuki coupling reactions. *J. Mater. Chem. A* **2015**, *3*, 10368–10377.
- 636 (80) Hardy, J. J. E.; Hubert, S.; Macquarrie, D. J.; Wilson, A. J.
637 Chitosan-based heterogeneous catalysts for Suzuki and Heck reactions.
638 *Green Chem.* **2004**, *6*, 53–56.
- 639 (81) Putta, C. B.; Ghosh, S. Palladium nanoparticles on amphiphilic
640 carbon spheres: A green catalyst for Suzuki–Miyaura reaction. *Adv.*
641 *Synth. Catal.* **2011**, *353*, 1889–1896.
- 642 (82) Monopoli, A.; Calò, V.; Ciminale, F.; Cotugno, P.; Angelici, C.;
643 Cioffi, N.; Nacci, A. Glucose as a clean and renewable reductant in the
644 Pd-nanoparticle-catalyzed reductive homocoupling of bromo- and
645 chloroarenes in water. *J. Org. Chem.* **2010**, *75*, 3908–3911.
- 646 (83) Monopoli, A.; Cotugno, P.; Palazzo, G.; Ditaranto, N.; Mariano,
647 B.; Cioffi, N.; Ciminale, F.; Nacci, A. Ullmann Homocoupling
648 catalysed by gold nanoparticles in water and ionic liquid. *Adv. Synth.*
649 *Catal.* **2012**, *354*, 2777–2788.
- 650 (84) Camp, J. E.; Dunsford, J. J.; Cannons, E. P.; Restorick, W. J.;
651 Gadzhieva, A.; Fay, M. W.; Smith, R. J. Glucose-derived palladium(0)
652 nanoparticles as *in situ*-formed catalysts for Suzuki–Miyaura cross-
653 coupling reactions in isopropanol. *ACS Sustainable Chem. Eng.* **2014**, *2*,
654 500–505.
- 655 (85) Xu, S.-Y.; Ruan, Y.-B.; Luo, X.-X.; Gao, Y.-F.; Zhao, J.-S.; Shen,
656 J.-S.; Jiang, Y.-B. Enhanced saccharide sensing based on simple
657 phenylboronic acid receptor by coupling to Suzuki homocoupling
658 reaction. *Chem. Commun.* **2010**, *46*, 5864–5866.
- 659 (86) Xu, S.-Y.; Wang, H.-C.; Flower, S. E.; Fossey, J. S.; Jiang, Y.-B.;
660 James, T. D. Suzuki homo-coupling reaction based fluorescent sensors
661 for monosaccharides. *RSC Adv.* **2014**, *4*, 35238–35241.
- 662 (87) For a recent review, see: Camp, J. E. Auto-Tandem Catalysis:
663 Activation of multiple, mechanistically distinct process by a single
664 catalyst. *Eur. J. Org. Chem.* **2016**, DOI: 10.1002/ejoc.201600803.
- 665 (88) For a recent example, see: Lester, R. P.; Dunsford, J. J.; Camp, J.
666 E. A Multifaceted Catalysis Approach to Nitrile Activation: Direct
667 synthesis of halogenated allyl amides from allylic alcohols. *Org. Biomol.*
668 *Chem.* **2013**, *11*, 7472–7476.
- 669 (89) Rohilla, S.; Pant, P.; Jain, N. Pd/mannose promoted tandem
670 cross coupling-nitro reduction: expedient synthesis of aminobiphenyls
671 and aminostilbenes. *RSC Adv.* **2015**, *5*, 31311–31317.
- 672 (90) Camp, J. E.; Dunsford, J. J.; Dacosta, O. S. G.; Blundell, R. K.;
673 Adams, J.; Britton, J.; Smith, R. J.; Bousfield, T. W.; Fay, M. W.
674 Recyclable glucose-derived palladium(0) nanoparticles as *in situ*-
675 formed catalysts for cross-coupling reactions in aqueous media. *RSC*
676 *Adv.* **2016**, *6*, 16115–16121.