

Engineering zonal cartilaginous tissue by modulating oxygen levels and mechanical cues through the depth of infrapatellar fat pad stem cell laden hydrogels.

Luo, L; O'Reilly, AR; Thorpe, SD; Buckley, CT; Kelly, DJ

Copyright © 2016 John Wiley & Sons, Ltd.

This is a pre-copyedited, author-produced PDF of an article accepted for publication in Journal of Tissue Engineering and Regenerative Medicine following peer review. The version of record is available <http://onlinelibrary.wiley.com/doi/10.1002/term.2162/full>

For additional information about this publication click this link.

<http://qmro.qmul.ac.uk/xmlui/handle/123456789/18194>

Information about this research object was correct at the time of download; we occasionally make corrections to records, please therefore check the published record when citing. For more information contact scholarlycommunications@qmul.ac.uk



Engineering zonal cartilaginous tissue by modulating oxygen levels and mechanical cues through the depth of infrapatellar fat pad stem cell laden hydrogels

Journal:	<i>Journal of Tissue Engineering and Regenerative Medicine</i>
Manuscript ID:	TERM-15-0358
Wiley - Manuscript type:	Research Article
Date Submitted by the Author:	29-Jul-2015
Complete List of Authors:	Luo, Lu; Trinity College Dublin, Trinity Center for Bioengineering; Trinity College Dublin, Department of Mechanical and Manufacturing Engineering O'Reilly, Adam; Trinity College Dublin, Trinity Center for Bioengineering; Trinity College Dublin, Department of Mechanical and Manufacturing Engineering Thorpe, Stephen; Queen Mary University of London, Institute of Bioengineering Buckley, Conor; Trinity College Dublin, Trinity Center for Bioengineering; Trinity College Dublin, Department of Mechanical and Manufacturing Engineering; Kelly, Daniel; Trinity College Dublin, Trinity Centre for Bioengineering; Trinity College Dublin, Department of Mechanical and Manufacturing Engineering; Royal College of Surgeons in Ireland, Department of Anatomy; Royal College of Surgeons in Ireland and Trinity College Dublin, Advanced Materials and Bioengineering Research Centre
Keywords:	Cartilage tissue engineering, Oxygen, Mechanical environment, Confinement, Dynamic compression, Proteoglycan 4

SCHOLARONE™
Manuscripts

1
2
3
4 **Engineering zonal cartilaginous tissue by modulating oxygen levels and**
5
6
7 **mechanical cues through the depth of infrapatellar fat pad stem cell**
8
9
10 **laden hydrogels**
11

12 Lu Luo ^{a,b}, Adam R. O'Reilly ^{a,b}, Stephen D. Thorpe ^c, Conor T. Buckley ^{a,b}, Daniel J.
13 Kelly ^{a,b,d,e*}
14
15

16
17
18 ^a Trinity Centre for Bioengineering, Trinity Biomedical Sciences Institute, Trinity
19 College Dublin, Dublin, Ireland.

20
21 ^b Department of Mechanical and Manufacturing Engineering, School of Engineering,
22 Trinity College Dublin, Dublin, Ireland.

23
24 ^c Institute of Bioengineering, School of Engineering and Materials Science, Queen Mary
25 University of London, London, UK.

26
27
28 ^d Department of Anatomy, Royal College of Surgeons in Ireland, Dublin 2, Ireland.

29
30 ^e Advanced Materials and Bioengineering Research Centre (AMBER), Royal College of
31 Surgeons in Ireland and Trinity College Dublin, Dublin, Ireland.
32

33
34
35 *Corresponding author

36 *E-mail address:* kellyd9@tcd.ie

37
38 *Address:* Department of Mechanical and Manufacturing Engineering

39 School of Engineering

40 Trinity College Dublin

41 Dublin 2

42 Ireland

43
44
45
46 *Telephone:* +353-1-896-3947

47
48 *Fax:* +353-1-679-5554
49
50
51
52
53
54
55
56
57
58
59
60

Abstract

Engineering tissues with a structure and spatial composition mimicking those of native articular cartilage (AC) remains a challenge. This study examined if infrapatellar fat pad derived stem cells (FPSCs) can be used to engineer cartilage grafts with a bulk composition and a spatial distribution of matrix similar to the native tissue. In an attempt to mimic the oxygen gradients and mechanical environment within AC, FPSC laden hydrogels (either 2mm or 4mm in height) were confined to half of their thickness and subjected to dynamic compression (DC). Confining hydrogels was predicted to lower the oxygen tension in the bottom of constructs, increasing both total glycosaminoglycan (GAG) and collagen synthesis in 2mm high tissues. When subjected to DC alone, both GAG and collagen accumulation increased within these constructs. Furthermore, the dynamic modulus of constructs increased from 0.96 MPa to 1.45 MPa. In contrast, there was no beneficial effect of either confinement or DC on tissue development of 4mm high constructs. Furthermore, there was no synergistic benefit of coupling confinement and DC on overall levels of matrix accumulation; however in all constructs, irrespective of their height, the combination of these boundary conditions lead to the development of engineered tissues that spatially best resembled native AC. The superficial region of these constructs mimicked that of native tissue, staining weakly for GAG, strongly for type II collagen, and in 4mm high tissues more intensely for proteoglycan 4 (lubricin). This study demonstrated that FPSCs respond to joint-like environmental conditions by producing cartilage tissues mimicking native AC.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Keywords:

Cartilage tissue engineering, Oxygen, Mechanical environment, Confinement, Dynamic compression, Proteoglycan 4.

For Peer Review

1. Introduction

Articular cartilage (AC) is a highly organised tissue with spatially-varying structure and composition, which is typically divided into three distinct zones: the superficial, middle and deep zone. The cellular morphology, collagen network structure, and extracellular matrix (ECM) composition all vary through the depth of the tissue (Klein *et al.*, 2009a, Klein *et al.*, 2009b, Mow and Guo, 2002). For example, in human adult AC, the collagen content (as a % of dry weight) is highest in the superficial zone and decreases with depth, whereas glycosaminoglycan (GAG) content (as a % of dry weight) is lowest in the superficial zone and increases with depth (Muir *et al.*, 1970). This unique depth dependent structure and composition is crucial to the mechanical functions of AC (Roth and Mow, 1980, Williamson *et al.*, 2003, Wilson *et al.*, 2007, Gannon *et al.*, 2012, Gannon *et al.*, 2015a, Gannon *et al.*, 2015b). The high collagen content and its densely packed parallel structure in the superficial zone imparts substantial tensile strength to the tissue (Roth and Mow, 1980, Williamson *et al.*, 2003). It may also contribute to the low permeability observed in the superficial zone of AC (Mansour and Mow, 1976, Maroudas *et al.*, 1968), with removal of this collagen rich region significantly impacting the dynamic properties of the tissue (Gannon *et al.*, 2012, Gannon *et al.*, 2015a). Furthermore, the higher GAG content within the deeper regions of the tissue is also believed to contribute to the increases in compressive modulus with depth through AC (Schinagl *et al.*, 1997, Wilson *et al.*, 2007, Klein *et al.*, 2007).

Despite the importance of this zonal structure and composition to the functionality of AC, to date few studies have attempted to engineer tissues with a depth dependent

1
2
3
4 structure and composition mimicking that of AC. Previous studies have explored
5
6 isolating chondrocytes from different zones of AC and incorporating them into specific
7
8 regions of a hydrogel in order to engineer zonal cartilage tissue (Kim *et al.*, 2003, Klein
9
10 *et al.*, 2003, Sharma *et al.*, 2007). While conceptually promising, difficulties
11
12 distinguishing the different zones of AC when isolating cells from a diseased joint and
13
14 the limited availability of zonal chondrocytes may limit the clinical translation of this
15
16 approach (Klein *et al.*, 2009a). Other zonal tissue engineering strategies include varying
17
18 the stiffness (Ng *et al.*, 2005, Ng *et al.*, 2006, Ng *et al.*, 2009) or composition (Nguyen *et*
19
20 *al.*, 2011b) through the depth of a scaffold or hydrogel in an attempt to engineer zone
21
22 specific environments. For example, Nguyen *et al.* demonstrated that unique
23
24 biomaterial compositions can direct bone marrow derived mesenchymal stem cells
25
26 (BMSCs) into specific chondrocytic phenotypes corresponding to the various zones of
27
28 AC (Nguyen *et al.*, 2011a), and by incorporating these different biomaterial
29
30 compositions into a tri-layered hydrogel that it was possible to engineer a tissue with
31
32 spatially-varying mechanical and biochemical properties similar to native AC (Nguyen
33
34 *et al.*, 2011b).

35
36
37
38
39
40
41
42 A potential limitation with such approaches is the development of engineered
43
44 constructs consisting of specific (and homogenous) regions with distinct boundaries, as
45
46 opposed to the creation of tissues with gradients in structure, composition and
47
48 biomechanics mimicking the native tissue. An alternative approach to engineering
49
50 zonal AC grafts is to recapitulate aspects of the tissue microenvironments which may
51
52 be responsible for the formation of the zonal structure and composition in AC during
53
54 tissue development and maturation (Thorpe *et al.*, 2013). In the case of articular
55
56
57
58
59
60

1
2
3
4 cartilage, low oxygen levels and mechanical stimulation are two joint specific
5
6 environmental factors known to regulate chondrogenesis and cartilage tissue
7
8 formation. Physiologically AC exists in a low oxygen environment, with the oxygen
9
10 tension decreasing with depth from the articular surface (Zhou *et al.*, 2004).
11
12 Furthermore, the tissue experiences various mechanical stimuli such as high
13
14 magnitude cyclic hydrostatic pressure and distortional strains during joint movement
15
16 (Mow and Guo, 2002). We have previously shown that it is possible to create AC-like
17
18 gradients in oxygen levels through the depth of BMSC laden hydrogels by radial
19
20 confinement of the developing constructs. When confinement was coupled with the
21
22 application of dynamic compression, which produced a gradient in mechanical cues
23
24 through the depth of these constructs, it was possible to engineer tissues with zonal
25
26 gradients in biochemical composition mimicking certain aspects of native AC (Thorpe
27
28 *et al.*, 2013). However the bulk tissue composition and mechanical properties of the
29
30 engineered grafts were still inferior to the native tissue.
31
32
33
34
35
36
37

38 We and others have demonstrated that joint tissue derived stem cells, such as synovial
39
40 membrane derived stem cells and infrapatellar fat pad derived stem cells (FPSCs), have
41
42 a unique capacity for chondrogenesis (De Bari *et al.*, 2001, English *et al.*, 2007, Buckley
43
44 *et al.*, 2010b, Vinardell *et al.*, 2012b, Vinardell *et al.*, 2012a, Carroll *et al.*, 2014), and
45
46 can be used to engineer cartilage grafts with a bulk composition and mechanical
47
48 properties approaching that of native tissue (Mesallati *et al.*, 2014). The hypothesis of
49
50 this study is that joint tissue derived stem cells will generate AC-like tissue, both in
51
52 terms of absolute levels of matrix accumulation and its spatial distribution, when
53
54 presented with an environment mimicking that found through the depth of AC. To test
55
56
57
58
59
60

1
2
3
4 this hypothesis, FPSC laden hydrogels either 2mm or 4mm in height (spanning the
5
6 cartilage thicknesses observed in large joints) were fabricated. Constructs were first
7
8 cultured in a chondrogenic medium in unconfined free swelling conditions for 3 weeks,
9
10 after which they were radially confined to half their thickness and subjected to
11
12 dynamic compression for another 3 weeks. Finite element models were developed to
13
14 predict the effects of these boundary conditions on nutrient availability (oxygen and
15
16 glucose) and the mechanical environment within the developing constructs. The
17
18 impact of these altered boundary conditions on the bulk and spatial development of
19
20 the engineered grafts was also assessed.
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

2. Materials and Methods

2.1. Cell Isolation and Expansion

Porcine FPSCs were isolated from the entire IFP of the knee joint of the animal (3-4 months old, ~50kg) using a previously described protocol (Buckley and Kelly, 2012). Cells were seeded at a density of 5×10^3 cell/cm² in high-glucose Dulbecco's modified Eagle's medium (hgDMEM) GlutaMAX™ supplemented with 10% fetal bovine serum and 1% penicillin (100 U/mL)-streptomycin (100 µg/mL) (all GIBCO, Biosciences, Dublin, Ireland) and expanded to passage 2 in a humidified atmosphere of 5% CO₂ at 37°C. Fibroblast-growth factor-2 (ProSpec-Tany TechnoGene Ltd, Israel) was added during the whole expansion period at a concentration of 5 ng/ml to promote the growth and chondrogenic potential of the FPSCs (Buckley and Kelly, 2012).

2.2. Hydrogel construct fabrication and culture

At the end of passage 2, cells were harvested and encapsulated in agarose (Type VII, Sigma-Aldrich) as previously described (Thorpe *et al.*, 2010) to obtain a final gel concentration of 2% and a cell density of 20×10^6 cells/ml. The agarose-gel suspension was then cast between stainless steel plates, one of which was overlaid with a patterned polydimethylsiloxane layer, allowed cool to room temperature (RT), and cored to produce cylindrical constructs with a diameter of 6mm and a height of either 2mm or 4mm. All constructs were patterned on one surface. Both types of constructs (2mm/4mm height) were maintained in a 58 cm² culture dish (6 constructs per dish;

1
2
3
4 Nunclon; Nunc, VWR, Dublin, Ireland) in either 6 ml (per 2mm height constructs) or 9
5
6 ml (per 4mm height constructs) of chondrogenic medium consisting of hgDMEM
7
8 GlutaMAX™ supplemented with penicillin (100 U/ml)-streptomycin (100 µg/ml), 100
9
10 µg/ml sodium pyruvate, 40 µg/ml L-proline, 4.7 µg/mL linoleic acid, 50 µg/ml L-
11
12 ascorbic acid-2-phosphate, 1.5 mg/ml bovine serum albumin, 1 × insulin–transferrin–
13
14 selenium, 100 nM dexamethasone (all from Sigma-Aldrich, Dublin, Ireland) and 10
15
16 ng/ml recombinant human transforming growth factor-β3 (TGF-β3; ProSpec-Tany
17
18 TechnoGene Ltd). Care was taken to ensure that the constructs remained patterned
19
20 surface up throughout the culture period and that they did not flip over to maintain
21
22 stable oxygen and glucose gradients within them. Media was exchanged twice weekly.
23
24
25
26
27
28 At each exchange media was sampled and stored at -85°C for biochemical analysis.
29
30
31
32
33

34 **2.3. Experimental design**

35
36
37 Both 2mm and 4mm high constructs were first maintained in unconfined free swelling
38
39 (UFS) conditions in a chondrogenic medium for 21 days to allow matrix establishment
40
41 (Haugh *et al.*, 2011). At this point, samples were radially confined to half of their height
42
43 using custom made polytetrafluoroethylene confinement chambers and subjected to
44
45 cyclic dynamic compression of 10% strain (1Hz, 2 hours/day, 5 days/week) for a further
46
47 21 days as previously described (Thorpe *et al.*, 2013) (see CDC group; Fig. 1), while
48
49 samples remained in UFS conditions were used as a control. The effect of these
50
51 boundary conditions was to lower the oxygen tension in the bottom of the construct
52
53 and increase the magnitude of strain in the top of the tissue to more closely
54
55
56
57
58
59
60

1
2
3
4 recapitulate the microenvironment within articular cartilage. Samples that were
5
6 confined but still in FS conditions (CFS) and samples that remained unconfined but
7
8 subjected to DC (UDC) were also maintained to study the effects of confinement alone
9
10 and dynamic compression alone on the development of the tissue (Fig. 1). Constructs
11
12 (n=6 per group) were assessed at day 0, 21 and 42.
13
14
15
16
17
18
19

20 **2.4. Computational modelling of oxygen and glucose transport**

21
22 The diffusion of oxygen and glucose was modelled using a mass balance relation
23
24 combined with Fick's law for diffusion (Sengers *et al.*, 2005, Thorpe *et al.*, 2013, Zhou
25
26 *et al.*, 2004). The reaction term in the equation followed Michaelis-Menten kinetics:
27
28
29

$$30 \quad \frac{\partial c}{\partial t} = D \nabla^2 c - n \frac{Q_m c}{K_m + c}$$

31
32 Here, c is the solute concentration [mol L^{-1}], D is the diffusion coefficient [$\text{cm}^2 \text{s}^{-1}$], n is
33
34 the cell density [cells L^{-1}], Q_m is the maximum consumption rate [mol h^{-1}] and K_m is the
35
36 concentration at half the maximum consumption rate [mol L^{-1}]. The values of the
37
38 parameters for each solute diffusion model were obtained from the literature. For the
39
40 oxygen model; $Q_m (\text{O}_2) = 38.88 \text{ fmol h}^{-1} \text{ cell}^{-1}$ (Buckley *et al.*, 2012) and $K_m (\text{O}_2) = 6 \times 10^{-6}$
41
42 mol m^{-3} (Sengers *et al.*, 2005). Similarly, for the glucose diffusion model; $Q_m (\text{glucose}) =$
43
44 $61.2 \text{ fmol h}^{-1} \text{ cell}^{-1}$ and $K_m (\text{glucose}) = 0.35 \times 10^{-3} \text{ mol m}^{-3}$ (Sengers *et al.*, 2005). For
45
46 both models the diffusion coefficient in 2 % agarose was calculated using the Mackie
47
48 and Meares relation:
49
50
51
52
53
54
55
56
57
58
59
60

$$\frac{D_{\text{agarose}}}{D_{\text{H}_2\text{O}}} = \frac{n_f^2}{(2 - n_f)}$$

Assuming that $n_f = 0.98$ for 2 % agarose. For the oxygen model, $D_{\text{H}_2\text{O}}(\text{O}_2) = 3.0 \times 10^{-5} \text{ cm}^2 \text{ s}^{-1}$, $D_{\text{agarose}}(\text{O}_2) = 2.77 \times 10^{-5} \text{ cm}^2 \text{ s}^{-1}$. Similarly, for the glucose model, $D_{\text{H}_2\text{O}}(\text{glucose}) = 0.92 \times 10^{-5} \text{ cm}^2 \text{ s}^{-1}$ and $D_{\text{agarose}}(\text{glucose}) = 0.85 \times 10^{-5} \text{ cm}^2 \text{ s}^{-1}$.

Using COMSOL, an axisymmetric model was constructed for both the confined and the unconfined case. In accordance with the experimental procedure, both groups were initially modelled as unconfined for the first 21 days, before being divided into their respective groups for the remaining 21 days. The initial value for glucose in the media was 25 mM, while for the oxygen model the initial value in the media was 208.5 μM ; a value which corresponded to an oxygen tension of 21%. For the oxygen model there was also an essential boundary condition of 208.5 μM at the free surface to account for the diffusion of oxygen into the media from the atmosphere. A media change was modelled every 3.5 days at which point the oxygen and glucose concentrations in the media were returned to their initial values.

2.5. Modelling of the mechanical environment within developing constructs

The peak fluid pressure and the strains in the engineered tissues were estimated during dynamic compression for both the confined and unconfined groups at day 21.

Using the finite element package FEBio, a pseudo axisymmetric model was developed for both construct geometries, each of which were compressed to 10 % strain over 0.5 seconds. In order to characterise the heterogeneous distribution of collagen and GAG

1
2
3
4 through the construct, an algorithm was developed that used histological sections of
5
6 the engineered tissues to estimate the material parameters in each element of the
7
8 model based on its pixel intensity relative to the total number of pixels in the image.
9
10 Briefly, alcian blue and picosirius red histology images were used to quantify the
11
12 spatial distribution of GAG and collagen, respectively, within the engineered tissues.
13
14 The algorithm involved dividing each image into elements corresponding to the mesh
15
16 of the finite element model. The relative pixel intensity was then used to determine
17
18 the percentage wet weight of the ECM component in each element of the image,
19
20 based on knowing the overall GAG and collagen content at that timepoint. The
21
22 mechanical properties of each element within the finite element model were then
23
24 updated with respect to the ECM concentration. The model parameters relating to
25
26 GAG levels were updated using a previously developed algorithm (Narmoneva *et al.*,
27
28 1999, Khoshgoftar *et al.*, 2012), while the material parameters related to the collagen
29
30 were changed using a simple linear approach outlined by Nagel *et al.* (Nagel and Kelly,
31
32 2012).
33
34
35
36
37
38
39

40 The governing stress equation in the model was similar to that used previously in the
41
42 literature (Nagel and Kelly, 2012), with the exception that fluid pressurization during
43
44 loading was also considered. Fluid pressure was accounted for as described previously
45
46 (Holmes and Mow, 1990). The total stress was thus given by:
47
48
49

$$\sigma_{total} = -\Delta\pi I + \sigma_{collagen} + \sigma_{agarose} - pI$$

50
51 Here $\Delta\pi$ was the Donnan osmotic pressure which was dependent on the concentration
52
53 of GAG in the element; σ_{fibres} was the stress in the collagen fibre network, this was
54
55
56
57
58
59
60

1
2
3
4 assumed to be isotropic and dependent on the concentration of collagen in the
5
6 element; σ_{agarose} was the stress in the agarose hydrogel which was constant and
7
8 isotropic; p represents the fluid pressure.
9

10
11
12 The method was validated by using it to predict the stress relaxation curve of the
13
14 unconfined compression tests conducted at day 21 on the 2mm and 4mm constructs
15
16 (see below). Both cases produced curves which matched the experimental data with
17
18 an $R^2 > 0.95$.
19
20
21
22
23
24

25 **2.6. Assessment of mechanical properties**

26
27

28 Construct mechanical properties were tested ($n=3/4$ per group) using a standard
29
30 materials testing machine with a 5N load cell (Zwick Roell Z005, Herefordshire, UK) as
31
32 previously described (Buckley *et al.*, 2009). Briefly, constructs were immersed in
33
34 phosphate buffered saline (PBS) bath and placed between two impermeable platens. A
35
36 preload of 0.01 N was used to ensure direct contact between construct and platen
37
38 surfaces. An unconfined stress-relaxation test was then performed, which consisted of
39
40 a ramp compression up to 10% strain of the sample thickness followed by a hold
41
42 period of 30 minutes until equilibrium was reached. The equilibrium compressive
43
44 modulus of the sample was calculated from the equilibrium force. A dynamic test
45
46 consisting of a cyclic strain amplitude of 1% at 1 Hz for 10 cycles was performed
47
48 directly after the equilibrium test to determine the dynamic modulus.
49
50
51
52
53
54
55
56
57
58
59
60

2.7. Quantitative biochemical analysis

After mechanical testing, constructs were maintained in PBS for 30 mins to allow them to recover to their initial thickness, after which constructs (n=3/4 per group) were transversely sliced into two halves for determination of the spatial distribution of matrix within the engineered tissue. The top and bottom halves of the samples were weighed (wet) and stored separately at -85 °C for subsequent analyses. Samples were digested with 125 µg/ml papain in 0.1 M sodium acetate, 5 mM L-cysteine HCl, 0.05 M EDTA, pH 6.0 (all Sigma-Aldrich) under constant rotation at 60 °C for 18 hours. The DNA content of the samples was measured using the Hoechst bisBenzimide H33258 dye assay with calf thymus DNA as a standard as previously described (Kim *et al.*, 1988). GAG content was quantified using the dimethylmethylene blue dye-binding assay (Blyscan, Biocolor Ltd., Northern Ireland), with a glycosaminoglycan standard. Collagen content was determined through measurement of the hydroxyproline content (Kafienah and Sims, 2004) and calculated using a hydroxyproline-to-collagen ratio of 1:7.69 (Ignat'eva *et al.*, 2007). GAG and collagen accumulation within constructs was normalized to construct wet weight and to DNA content. GAG and collagen release into the media during the whole culture period was also analysed using the methods described above. Total GAG and collagen synthesis was calculated as the sum of GAG and collagen accumulated within constructs and released into the media.

2.8. Histology and immunohistochemistry

1
2
3
4 Whole constructs (n=2 per group) were fixed with 4% paraformaldehyde (Sigma-
5 Aldrich), wax embedded and sectioned perpendicularly to the disk surface at a
6 thickness of 5 µm. Sections were stained histologically with 1% alcian blue 8GX in 0.1M
7 HCl for GAG distribution and with picro-sirius red for collagen distribution (all Sigma-
8 Aldrich). Sections were immunohistochemically stained for collagen type II using a
9 mouse monoclonal collagen type II antibody (1:100; 1 mg/mL; Abcam) as previously
10 described (Thorpe *et al.*, 2010). Constructs were also immunohistochemically stained
11 for proteoglycan 4 (PRG4) expression with a mouse monoclonal antibody (1:50; 0.5
12 mg/mL; Novus Biologicals, Littleton, USA) using a modified protocol. Briefly, Sections
13 were enzymatically treated with 1 mg/ml pronase (64072 PUK/g; Millipore Ireland,
14 Cork, Ireland) in a humidified environment at 37 °C for 12 mins. Slides were then
15 blocked with blocking buffers consisting of PBS containing 1% bovine serum albumin
16 and 10% goat serum (all Sigma-Aldrich) for 2 hours at RT and sections were incubated
17 with the primary antibody diluted in blocking buffer at 4 °C over night. After washing in
18 PBS/0.05% Tween20 (Sigma-Aldrich), sections were blocked for peroxidase activity
19 using hydrogen peroxide (Sigma-Aldrich), followed by an incubation for 1 hour in the
20 secondary antibody, anti-mouse IgG biotin antibody produced in goat (1:133; 2 mg/mL;
21 Sigma-Aldrich). Colour was developed using the Vectastain ABC kit followed by
22 exposure to peroxidase DAB substrate kit (both Vector Laboratories, Peterborough,
23 UK). Sections of porcine cartilage and ligament were used as positive and negative
24 controls for collagen type II staining respectively. For PRG4 staining, cartilage
25 (superficial zone) was used as positive control and cartilage without the addition of
26 primary antibody was used as negative control.
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

2.9. Statistical analysis

Statistics were performed using MINITAB 15.1 software (Minitab Ltd., Coventry, UK). A two-sample T-test was used for data sets containing only two groups. For data sets which contain more than two groups, a general lineal model for analysis of variance with Tukey's test for multiple comparisons was used. Significance was determined at $p < 0.05$ and a trend towards significance was defined as $p < 0.1$. All graphical results are presented as mean \pm standard deviation.

3. Results

3.1. *Construct height determines the spatial development of tissue engineered cartilage*

The availability of regulatory factors such as oxygen and glucose within engineered tissues will depend on the size of the cell seeded construct. Therefore we first sought to explore how the height of FPSC seeded agarose hydrogels would determine the availability of oxygen and glucose within the construct and hence the spatial development of the engineered tissue. Constructs either 2mm or 4mm in height were fabricated, and care was taken to ensure they did not flip over during the culture period to maintain a stable oxygen and glucose gradient within them. Finite element models predicted that a low oxygen microenvironment is created in the bottom core of 2mm hydrogels (~5% O₂, see red circle area), while even lower oxygen levels were predicted in the bottom of the 4mm gels, with an average oxygen tension of 1.2% across the bottom half (Fig. 2A). Models also predict sufficient and relatively homogeneously distributed glucose levels within both 2mm and 4mm samples, with no obvious difference observed between them (Fig. 2B). The 2mm constructs stained reasonably homogeneously for GAG and collagen, while a larger core region staining less intensely for GAG and collagen was observed in the 4mm gels (Fig. 2C and D).

To further explore the spatial development of the engineered tissues they were sliced half way along their height and the biochemical content of the 'top' and 'bottom' of the engineered tissue was measured (Fig. 3). At day 42, significant cell proliferation occurred in both the 2mm and 4mm gels, with higher DNA content measured

1
2
3
4 compared to day 0 (data now shown). The DNA content was higher in the top of both
5
6 2mm and 4mm tissues compared to the corresponding bottom region of each
7
8 construct ($p < 0.05$; Fig. 3A), indicating greater cell proliferation in this region of the
9
10 engineered tissue. There was a trend ($p < 0.1$) towards greater GAG accumulation (as a
11
12 % of wet weight) in the bottom of the 2mm constructs (Fig. 3B), which was significant
13
14 ($P < 0.01$) when GAG content was normalised to DNA content (Fig. 3D). Greater
15
16 ($P < 0.001$) collagen accumulation (as a % of wet weight) was observed in the top of the
17
18 4mm constructs (Fig. 3C), however no significant difference was observed if collagen
19
20 content was normalised to DNA content (Fig. 3E).
21
22
23
24
25
26
27
28

29
30 **3.2. Modulating spatial oxygen and glucose availability within FPSC seeded**
31
32 **hydrogels by partially confining the constructs alters matrix synthesis and the**
33
34 **spatial development of the engineered tissue**
35
36

37 As a low oxygen environment is known to enhance chondrogenesis of stem cells
38
39 (Buckley *et al.*, 2010a, Meyer *et al.*, 2010), we next sought to determine how reducing
40
41 oxygen availability to the bottom of FPSC seeded hydrogels, by radially confining the
42
43 bottom half of the engineered tissue, would influence matrix synthesis and distribution
44
45 throughout the construct. We have previously shown that this approach can be used
46
47 to increase GAG accumulation within the bottom of BMSC seeded hydrogels (Thorpe *et*
48
49 *al.*, 2013). Confining the hydrogels was predicted to lower the oxygen tension in the
50
51 bottom of the 2mm and 4mm gels (Fig. 4, see red circles). It was also predicted to
52
53 increase oxygen levels in the top of the engineered tissue (the confinement chamber
54
55
56
57
58
59
60

1
2
3
4 moved the construct higher in the culture media and hence nearer the oxygen source),
5
6 leading to the development of a steeper oxygen gradient through the depth of the
7
8 construct. A reduction in glucose availability throughout the hydrogels was also
9
10 predicted in both the 2mm and 4mm confined gels, nevertheless this reduced glucose
11
12 level (~18mM) is still predicted to be sufficient to maintain viable cells in culture (Fig.
13
14 4). Partial confinement of free swelling (CFS) hydrogels was found to increase both
15
16 total GAG and collagen synthesis (ECM accumulated in hydrogel and released into the
17
18 media) in the 2mm gels compared to unconfined free swelling (UFS) controls ($p<0.05$),
19
20 however no significant difference was observed when total GAG or collagen synthesis
21
22 was normalised to DNA content (Fig. 5A and B). In the 4mm gels, partial confinement
23
24 reduced total GAG synthesis and this was also significant when total GAG synthesis
25
26 was normalised to DNA content ($p<0.05$; Fig. 5A). Looking at the spatial development
27
28 of the engineered tissues, it was found that confinement increased the DNA and
29
30 collagen content within the top of both 2mm and 4mm gels ($p<0.05$; Fig. 5C and E).
31
32 This increase in collagen content was not significant when normalised to DNA content
33
34 (Supplementary Fig. 1A). Furthermore, confinement increased GAG accumulation
35
36 throughout the 2mm gels, but reduced GAG accumulation throughout the 4mm gels
37
38 ($p<0.05$; Fig. 5D). Histologically, it appeared that confinement increased GAG
39
40 accumulation around the bottom periphery of the gels (Supplementary Fig. 1B).
41
42
43
44
45
46
47
48
49
50
51
52

53 ***3.3. The development of tissue engineered cartilage subjected to dynamic***
54 ***compression depends on the height of the construct***
55
56
57
58
59
60

1
2
3
4 We and others have previously shown that the application of delayed dynamic
5
6 compression (either alone or combined with shear stress) can enhance the
7
8 development of cartilage grafts engineered using MSCs (Thorpe *et al.*, 2013, Huang *et*
9
10 *al.*, 2010, Bian *et al.*, 2012, Li *et al.*, 2010). Hence, we next sought to determine how
11
12 the application of delayed dynamic compression (DC) would influence the bulk and
13
14 spatial development of engineered tissues of differing heights. After 3 weeks in
15
16 unconfined free swelling (UFS) culture, 2mm and 4mm FPSC seeded hydrogels were
17
18 subjected to DC. Model predictions of the mechanical environment due to DC showed
19
20 a very low fluid pressure in both 2mm and 4mm unconfined dynamically compressed
21
22 (UDC) gels (~0.02 MPa; Fig. 6A). A relatively homogenous mechanical environment was
23
24 predicted through the depth of both 2mm and 4mm engineered tissues, with no
25
26 remarkable difference in strain levels predicted between 2mm and 4mm gels (Fig. 6A).
27
28 GAG and collagen accumulation within the construct increased in the 2mm UDC gels
29
30 compared to UFS controls ($p < 0.05$; Fig. 7A and B). In contrast, DC reduced GAG
31
32 ($p < 0.05$) and collagen ($p < 0.1$) accumulation within the 4mm gels (Fig. 7A and B). The
33
34 reduction in GAG accumulation in the 4mm gels could be partially explained by an
35
36 increase in GAG release to the media (Fig. 7A). When normalised to DNA content, total
37
38 (accumulated + released) GAG and collagen synthesis was not significantly affected by
39
40 the application of DC in either the 2mm or the 4mm gels (Fig. 7A and B).
41
42
43
44
45
46
47
48

49
50 DC was found to significantly increase the DNA and GAG content in both the top and
51
52 bottom of 2mm gels, and to significantly increase the collagen content in the top of the
53
54 same gels ($p < 0.05$; Fig. 7C, D and E). These differences were no longer significant when
55
56 matrix levels were normalised to DNA content (Supplementary Fig. 2A).
57
58
59
60

1
2
3
4 Immunohistochemistry revealed enhanced type II collagen deposition at the superficial
5 region of 2mm UDC gels (Supplementary Fig. 2B). The increased levels of matrix
6 accumulation due to the application of loading translated into improvements in the
7 mechanical properties of the engineered tissues. The equilibrium modulus of the 2mm
8 UDC gels was found to be 95.3kPa, compared to 43.3kPa for the UFS controls. The
9 dynamic modulus of the 2mm UDC gels was found to be 1452kPa, compared to 969kPa
10 for the UFS controls (data not shown). In contrast to the 2mm gels, DC reduced GAG
11 accumulation in both the top and bottom of the 4mm gels ($p < 0.05$; Fig. 7D and
12 Supplementary Fig. 2A). Histologically, 4mm UDC gels appeared similar to UFS controls,
13 albeit that alcian blue staining appeared slightly more homogenous within UDC gels
14 (Supplementary Fig. 2B).
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33

34 ***3.4. Coupling partial confinement and dynamic compression can lead to the***
35 ***development of engineered cartilage with zonal features mimicking certain***
36 ***aspects of the native tissue***
37
38
39
40

41 Separately confinement and DC have been shown to generally enhance the
42 development of 2mm gels, but were not necessarily beneficial to the development of
43 4mm gels. Therefore we were interested in exploring how the combination of both
44 factors would influence the development of the engineered tissues. Partially confining
45 the hydrogels was predicted to alter the mechanical environment in both 2mm and
46 4mm confined dynamically compressed (CDC) hydrogels, leading to a higher fluid
47 pressure inside the constructs and a dramatically increased strain magnitude across
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3
4 the top of the constructs (Fig. 6). Overall, there was no synergistic effect of coupling
5
6 confinement and DC on overall levels of matrix accumulation and mechanical
7
8 properties of the constructs compared to the application of confinement alone or DC
9
10 alone (data not shown). There was however some important differences in the zonal
11
12 development of CDC constructs compared to UFS controls and other previously
13
14 reported experimental groups. In both 2mm and 4mm gels, the combination of
15
16 confinement and DC was found to lead to the development of an engineered tissue
17
18 that spatially best resembled native articular cartilage. Collagen accumulation was
19
20 significantly greater in the top of 2mm CDC gels ($p<0.05$; Fig. 8C), which was not
21
22 observed in UFS controls (this was also not observed in UDC gels, see Fig. 7E, but was
23
24 found in CFS gels, see Fig. 5E). No significant difference was observed in GAG
25
26 accumulation between the top and bottom of 2mm CDC gels (Fig. 7B); however GAG
27
28 accumulation was higher in the top of 2mm CFS gels (see Fig. 5D), a non-native
29
30 gradient in matrix levels. When normalised to DNA levels, GAG synthesis was found to
31
32 be greater in the bottom of CDC gels compared to the top ($p<0.05$; Supplementary Fig.
33
34 3A).

35
36
37
38
39
40
41
42 A similar gradient in collagen and GAG accumulation was observed in the 4mm CDC
43
44 gels (Fig. 8B and C). In fact, while the combination of confinement and DC was not
45
46 beneficial to overall levels of matrix accumulation in the 4mm gels, it did lead to the
47
48 development of a tissue with a zonal composition perhaps best mimicking that of the
49
50 native tissue of all experimental groups. GAG/DNA trended higher ($p<0.1$) and
51
52 collagen/DNA was lower ($p<0.001$) in the bottom of the 4mm CDC constructs
53
54 compared to the top (supplementary Fig. 3), which was not observed in any other
55
56
57
58
59
60

1
2
3
4 group. Furthermore, the superficial region of both 2mm and 4mm CDC constructs best
5
6 mimicked that of the native tissue, staining weakly for GAG and strongly for type II
7
8 collagen (Fig. 9A and B). In addition, proteoglycan (PRG4) staining was stronger in the
9
10 superficial region of 4mm CDC constructs compared to UFS controls (Fig. 9C) and
11
12 indeed UDC constructs (data not shown).
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

For Peer Review

4. Discussion

Engineering tissues with a structure and spatial composition mimicking those of native articular cartilage remains a challenge. This study examined if FPSCs can be used to engineer cartilage grafts with a bulk biochemical composition and a spatial distribution similar to the native tissue. FPSCs were encapsulated in agarose hydrogels to make constructs of either 2mm or 4mm in height, and constructs were subjected to partial confinement and/or DC. Confinement alone was predicted to significantly lower oxygen levels in the bottom of both 2mm and 4mm gels, increasing GAG and collagen accumulation in 2mm gels, but lowering GAG accumulation in 4mm gels. The influence of DC alone on chondrogenesis of FPSCs was found to also depend on the height of the gels: DC increased GAG and collagen accumulation in 2mm gels, but decreased GAG accumulation in 4mm gels. When confinement was coupled with DC, an altered mechanical environment within constructs was predicted, with increased strain magnitude observed in the top of both 2mm and 4mm CDC constructs. This correlated with an increase in total collagen accumulation and collagen type II deposition within the top of both 2mm and 4mm CDC gels compared to UFS controls. Furthermore, the superficial region of 2mm and 4mm CDC constructs stained weakly for GAG and strongly for collagen type II, with enhanced staining for PRG4 further observed in 4mm CDC gels, thus mimicking certain aspects of the zonal composition in articular cartilage. Although the engineered tissue did not quite achieve native levels of matrix accumulation (approaching 3% GAG and 2% collagen as a percentage of wet weight) and biomechanical function (approaching 100kPa for the equilibrium modulus), they

1
2
3
4 are of a similar order of magnitude and may have attained the necessary function and
5
6 zonal composition to thrive within a load bearing defect (Nagel and Kelly, 2013).
7
8

9
10 A low oxygen microenvironment (~5%) was predicted to develop in the bottom core of
11
12 2mm FPSC seeded UFS hydrogels (Fig. 2A), which correlated with higher GAG synthesis
13
14 (as indicated by GAG/DNA levels) in the bottom of the engineered tissue (Fig. 3D).
15
16 However, no significant difference in collagen synthesis at per cell level (collagen/DNA)
17
18 was found between the top and bottom of the tissue (Fig. 3E). We have previously
19
20 demonstrated increased GAG/DNA but not collagen/DNA levels in FPSC seeded
21
22 hydrogels cultured in 5% oxygen compared to 20% oxygen (Buckley *et al.*, 2010a). An
23
24 even lower oxygen tension was predicted in the bottom of 4mm UFS gels, with an
25
26 average oxygen concentration of 1.2% across the bottom half. However, it didn't affect
27
28 either GAG or collagen synthesis at per cell level in the bottom of the tissue (Fig. 3D
29
30 and E). This suggested that while a low oxygen environment (~5% oxygen) can
31
32 promote the chondrogenesis of the stem cells (Buckley *et al.*, 2010a, Meyer *et al.*,
33
34 2010), very low oxygen levels may not necessarily be beneficial for the development of
35
36 the tissue. Previous studies have reported significant decreases in cell metabolism and
37
38 proteoglycan synthesis when freshly-excised articular cartilage explants were cultured
39
40 at an oxygen tension <2% (Lee and Urban, 1997). Furthermore, more recent studies
41
42 have demonstrated that severe hypoxia suppresses the capacity of MSCs to undergo
43
44 chondrogenesis (Cicione *et al.*, 2013). Significantly higher collagen accumulation was
45
46 observed in the top of the 4mm gels compared to the bottom (Fig. 3C), which may be
47
48 attributed to the higher cell proliferation in the top of these constructs (Fig. 3A). In
49
50 fact, greater cell proliferation was also observed in the top of all experimental groups
51
52
53
54
55
56
57
58
59
60

1
2
3
4 (2mm and 4mm CFS, UDC and CDC). This may be explained by the fact that the higher
5
6 oxygen tension environment generated in the top of the gels promoted a more
7
8 proliferative phenotype, as greater cell proliferation has been observed in adipose
9
10 derived stem cells cultured at 20% oxygen compared to 5% oxygen (Wang *et al.*, 2005).
11
12

13
14 Partial confinement was found to reduce GAG accumulation in the 4mm gels, but to
15
16 enhance GAG accumulation in the 2mm gels. This could be explained by the fact that
17
18 the confinement had a more critical impact on oxygen availability in the 4mm gels,
19
20 with the average oxygen tension predicted to decrease from 1.24% to 0.24% (anoxia)
21
22 in the bottom of these constructs. Previous studies have reported significantly
23
24 decreased matrix production of chondrocytes when they were cultured in anoxic
25
26 conditions (oxygen tension <0.1%) (Grimshaw and Mason, 2000), and as discussed
27
28 above, such low levels of oxygen availability may suppress MSC chondrogenesis (Cicione
29
30
31
32
33 *et al.*, 2013).
34
35

36
37 The development of tissue engineered cartilage subjected to DC was found to also
38
39 depend on the height of the construct. In 2mm gels the application of DC was found to
40
41 increase GAG and collagen accumulation and the mechanical functionality of the
42
43 engineered graft, with a 2-fold increase in the equilibrium modulus of engineered
44
45 tissues. It also led to increases in type II collagen deposition, particularly at the top
46
47 surface of the engineered tissue. This suggests that the unique combination of
48
49 mechanical cues and oxygen tension (Fig. 2A) in this region of the 2mm constructs
50
51 preferentially supports collagen type II deposition. In contrast to the 2mm gels, the
52
53 application of DC lead to a reduction in matrix accumulation in the 4mm gels (Fig. 7).
54
55
56
57
58
59
60

1
2
3
4 The reduction in GAG accumulation within the 4mm gels could be partially explained
5
6 by increased GAG release to the media in response to mechanical loading (Fig. 7A). The
7
8 fact that the radial surface area of the 4mm gels is twice that of the 2mm gels may
9
10 partially explain why such GAG loss is higher in the thicker gels. The increased levels of
11
12 matrix accumulation in the mechanically loaded 2mm gels appeared to be driven by
13
14 increased cell proliferation in these constructs. There is an obvious explanation for
15
16 why DC only enhanced cell proliferation in the thinner gels. The finite element model
17
18 suggests that this is unlikely due to differences in the mechanical environment alone,
19
20 as similar strain levels and very low fluid pressures (~ 0.02 MPa, physiological level is
21
22 ~ 10 MPa) are predicted in the 2mm and 4m gels (Fig. 6). This suggests a more complex
23
24 interplay between nutrient availability and mechanical cues is regulating FPSC fate in
25
26 the different gels.
27
28
29
30
31

32
33 Articular cartilage (AC) is characterised by its unique depth dependent composition.
34
35 The collagen content is highest at the superficial zone and decreases with depth, while
36
37 GAG content is lowest in the superficial zone and increases with depth (Muir *et al.*,
38
39 1970). This depth dependent composition together with the collagen network
40
41 organisation is crucial to the biomechanical properties of the tissue (Roth and Mow,
42
43 1980, Williamson *et al.*, 2003, Wilson *et al.*, 2007, Gannon *et al.*, 2012, Gannon *et al.*,
44
45 2015a, Gannon *et al.*, 2015b). Subjecting FPSC seeded hydrogels to both confinement
46
47 and DC appeared to lead to the development of an engineered tissue that best
48
49 mimicked the depth dependant composition of native AC. While confinement led to
50
51 greater collagen accumulation in the top of engineered tissues, mimicking the native
52
53 tissue, it also led to greater GAG accumulation in the top of the 2mm gels (Fig. 5D and
54
55
56
57
58
59
60

1
2
3
4 E). However, by coupling confinement and DC it was possible to engineer a tissue
5
6 where GAG levels were not higher in the top of the tissue but where collagen levels
7
8 were (Fig. 8B and C). Furthermore, the superficial region of CDC constructs best
9
10 resembled that of the native tissue (Fig. 9A and B). Of note was the finding that the
11
12 combination of partial confinement and DC lead to increased PRG4 deposition at the
13
14 top surface of the 4mm gels (Fig. 9C). PRG4 is a protein expressed by the cells in the
15
16 superficial zone of AC, which is important for the boundary lubrication of this tissue.
17
18 Mechanical loading has previously been shown to be a key stimulus for PRG4
19
20 deposition (Grad *et al.*, 2005, Nugent-Derfus *et al.*, 2007), with the results of this study
21
22 suggesting that the specific combination of oxygen availability and mechanical
23
24 stimulation within this region of the 4mm high constructs is enhancing production of
25
26 this superficial zone protein.
27
28
29
30
31

32
33 In conclusion, this study provided new insights into how environmental factors within
34
35 the joint, such as oxygen levels and mechanical loading, may contribute to the
36
37 development of the depth dependent changes in composition within AC. We
38
39 demonstrated that, by regulating the spatial environment through the depth of
40
41 developing constructs, it is possible to engineer cartilage tissues with zonal
42
43 compositions mimicking certain aspects of AC using FPSCs. The attained zonal
44
45 composition may better equip the engineered tissue to achieve a long-term stable
46
47 cartilage repair. Mimicking the complex collagen architecture of AC will be required to
48
49 engineered grafts that truly mimic the depth dependent properties of the native
50
51 tissue.
52
53
54
55
56
57
58
59
60

Acknowledgements

Funding was provided by the European Research Council Starter Grant (StemRepair – Project number 258463). The authors have no conflicts of interest.

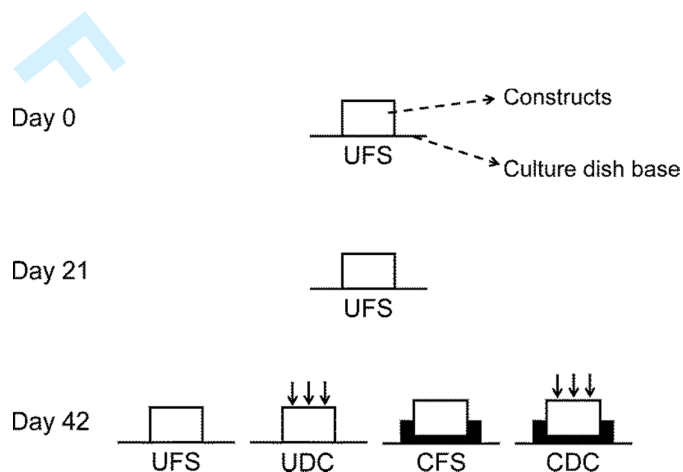


Figure 1. Experimental design. Constructs either 2mm or 4mm in height were first cultured in unconfined free swelling (UFS) conditions until day 21, and care was taken to ensure constructs did not flip over during the whole culture period to maintain a stable oxygen and glucose gradient within them. Samples were then confined to half of their height and subjected to dynamic compression (CDC) until day 42 while samples remained in UFS conditions were used as controls. Constructs that were confined but still in free swelling (CFS) conditions and constructs that remained unconfined but subjected to dynamic compression (UDC) were also maintained to study the effects of confinement alone and dynamic compression alone on the development of the tissue.

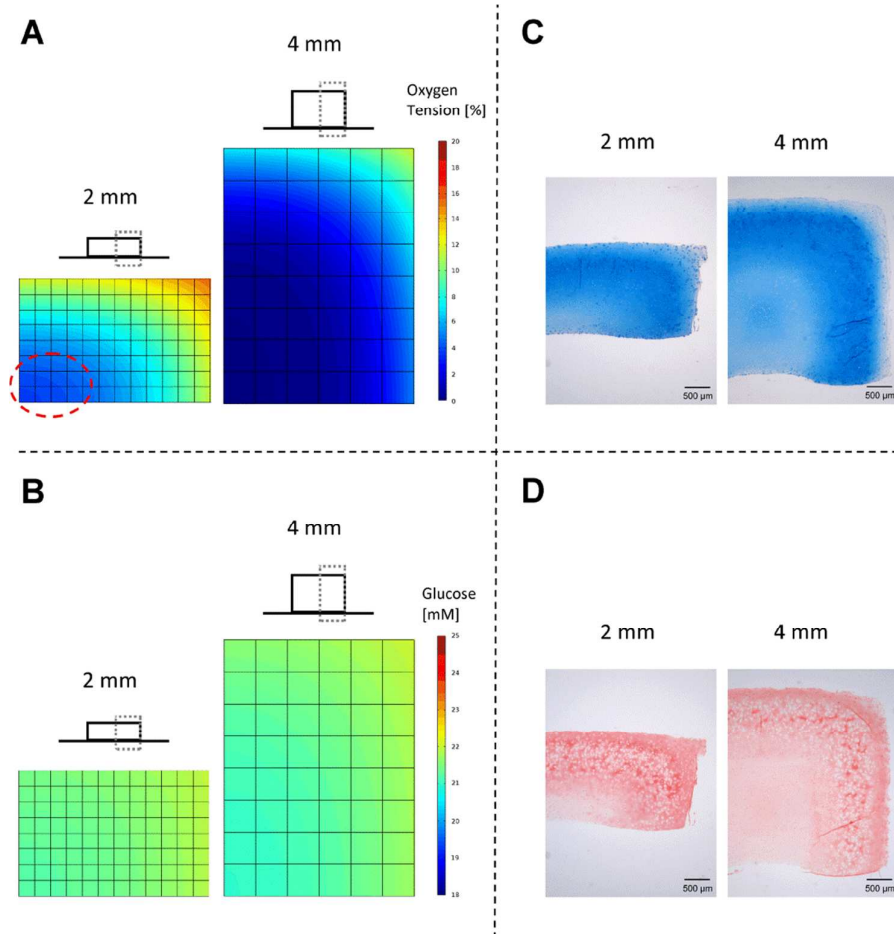


Figure 2. Oxygen and glucose environment and matrix distribution with 2mm and 4mm samples at day 42. (A) An axisymmetric computational model predicting oxygen environment and (B) an axisymmetric computational model predicting glucose environment within both 2mm and 4mm samples. The resulting oxygen/glucose concentration data was calculated from the regions within constructs which were indicated by grey boxes. (C) Alcian blue staining of GAG and (D) Picro-sirius red staining of collagen distribution within both samples at day 42. Histology images were taken at 2x magnification, and they represent approximately 2/3 of the whole sample.

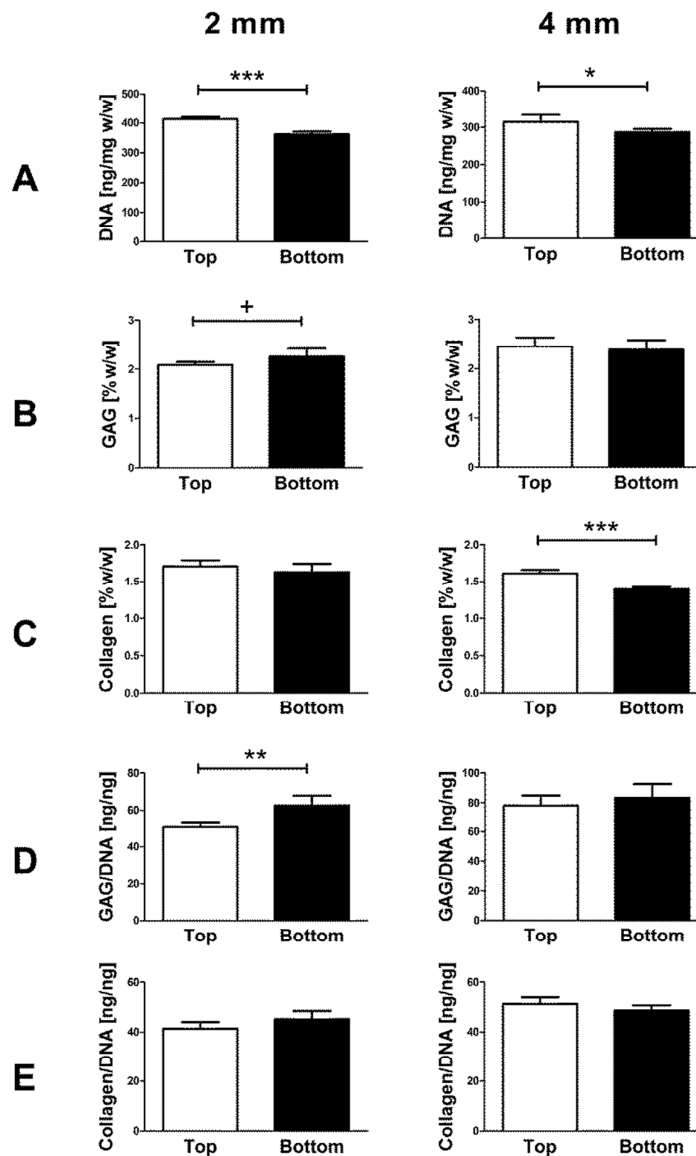


Figure 3. Biochemical content of the top and bottom halves of 2mm and 4mm unconfined free swelling (UFS) samples at day 42. (A) DNA content [ng/mg w/w]; (B) GAG content [% w/w]; (C) Collagen content [% w/w]; (D) GAG/DNA [ng/ng] and (E) Collagen/DNA [ng/ng]. +: trend, $p < 0.1$; *: $p < 0.05$; **: $p < 0.01$; ***: $p < 0.001$.

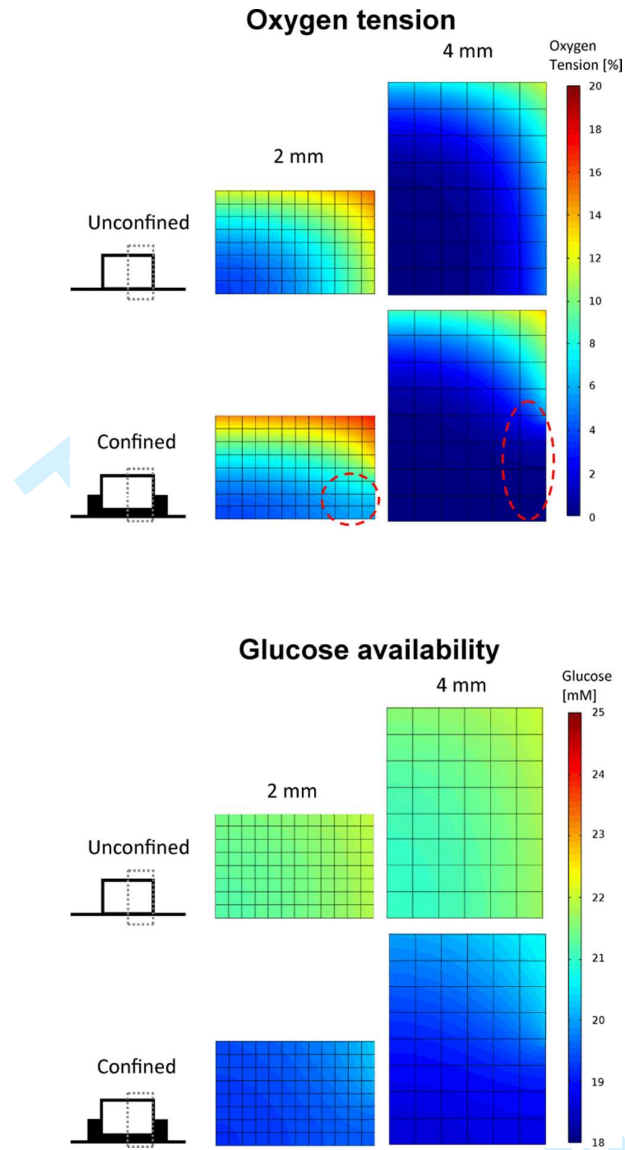


Figure 4. An axisymmetric computational model predicting oxygen and glucose environment within unconfined and confined free swelling 2mm and 4mm samples at day 42. The resulting oxygen/glucose data was calculated from regions within constructs which were indicated by grey boxes. Red circles highlight regions with lowered oxygen tension in the 2mm and 4mm confined samples.


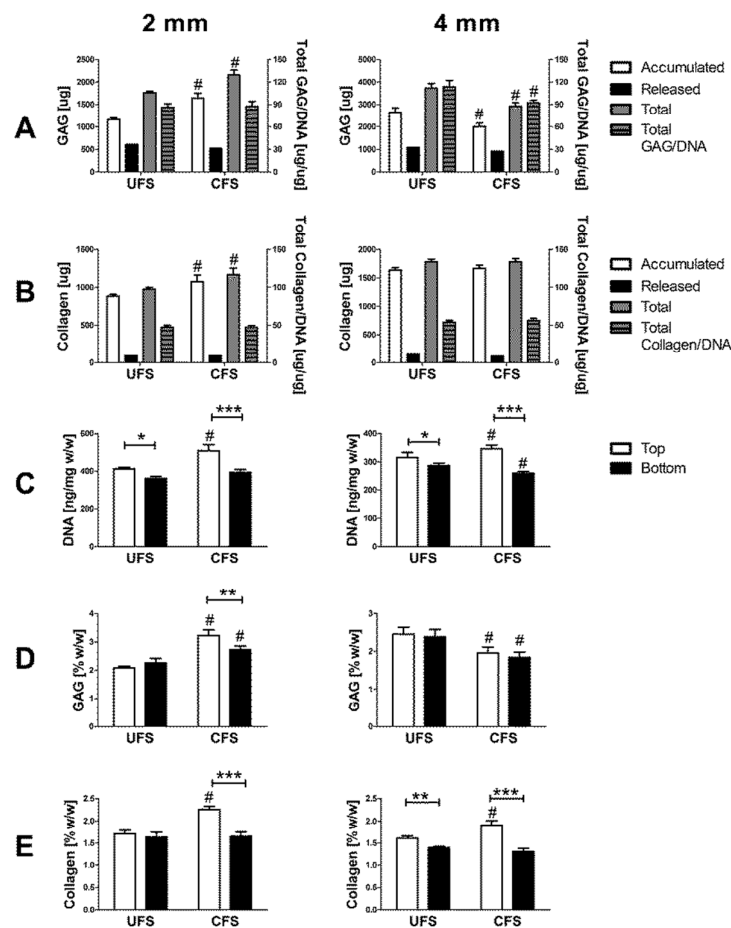


Figure 5. (A) GAG content [µg] and (B) collagen content [µg] accumulated within constructs, released into media and total synthesised (accumulated+released) in unconfined free swelling (UFS) and confined free swelling (CFS) 2mm and 4mm constructs at day 42. Total GAG/DNA [µg/µg] and total collagen/DNA [µg/µg] value were also plotted on the right Y axis within each graph. (C) DNA content [ng/mg w/w], (D) GAG content [%w/w] and (E) collagen content [%w/w] of the top and bottom halves of the UFS and CFS 2mm and 4mm samples at day 42. #: p<0.05 vs. UFS; *: p<0.05; **: p<0.01; ***: p<0.001.

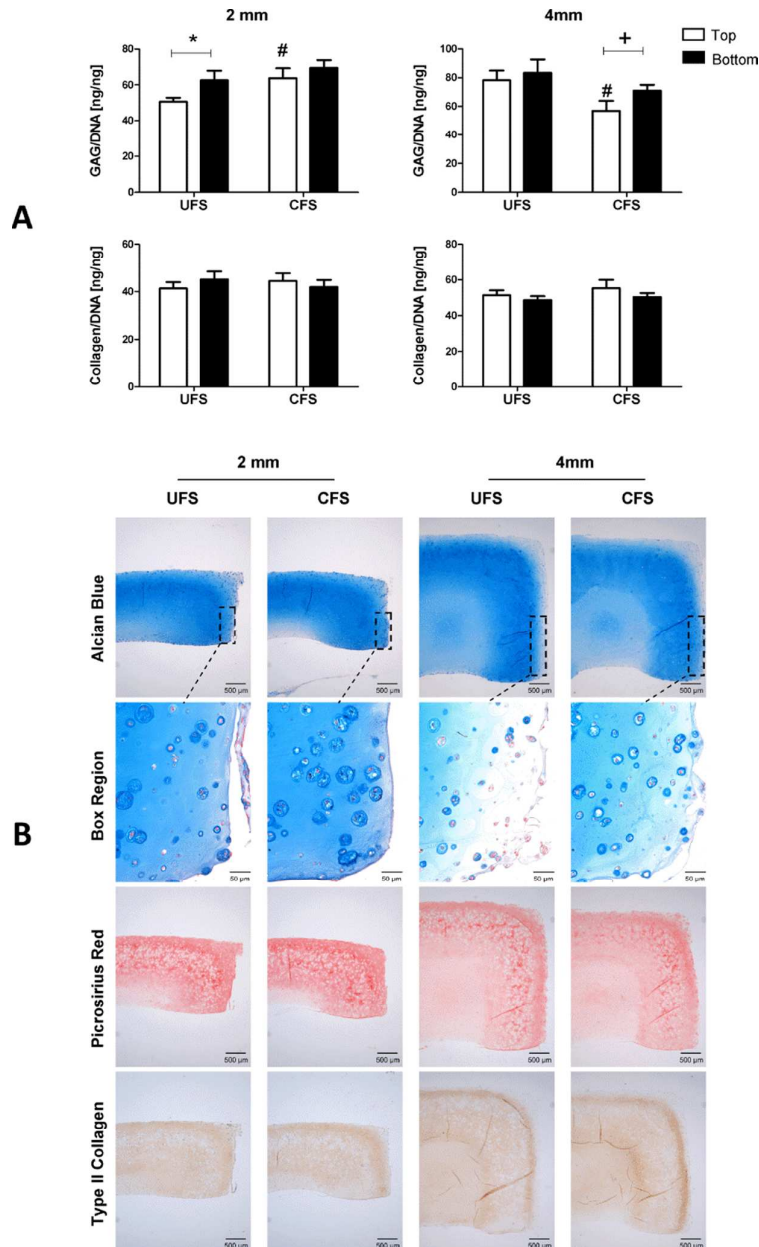

Supplementary figure 1. (A) GAG/DNA [ng/ng] and collagen/DNA [ng/ng] value of the top and bottom halves of UFS and CFS 2mm and 4mm constructs at day 42. #: $p < 0.05$ vs. UFS; +: trend, $p < 0.1$; *: $p < 0.05$. (B) Alcian blue, picrosirius red and collagen type II staining of UFS and CFS 2mm and 4mm constructs at day 42.

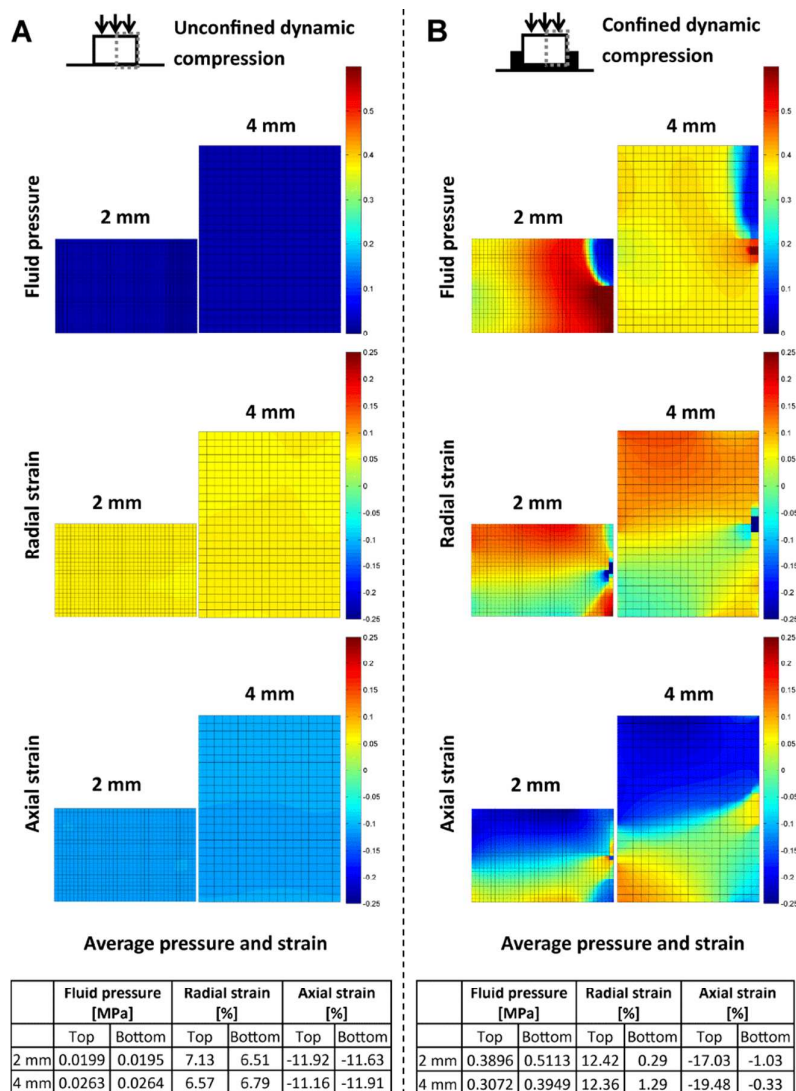


Figure 6. An axisymmetric computational model predicting the mechanical environment of fluid pressure [MPa], radial strain [%; positive] and axial strain [%; negative] within (A) unconfined dynamically compressed (UDC) and (B) confined dynamically compressed (CDC) 2mm and 4mm constructs at day 21. The mechanical environment data were calculated from regions within constructs, which were indicated by grey boxes.


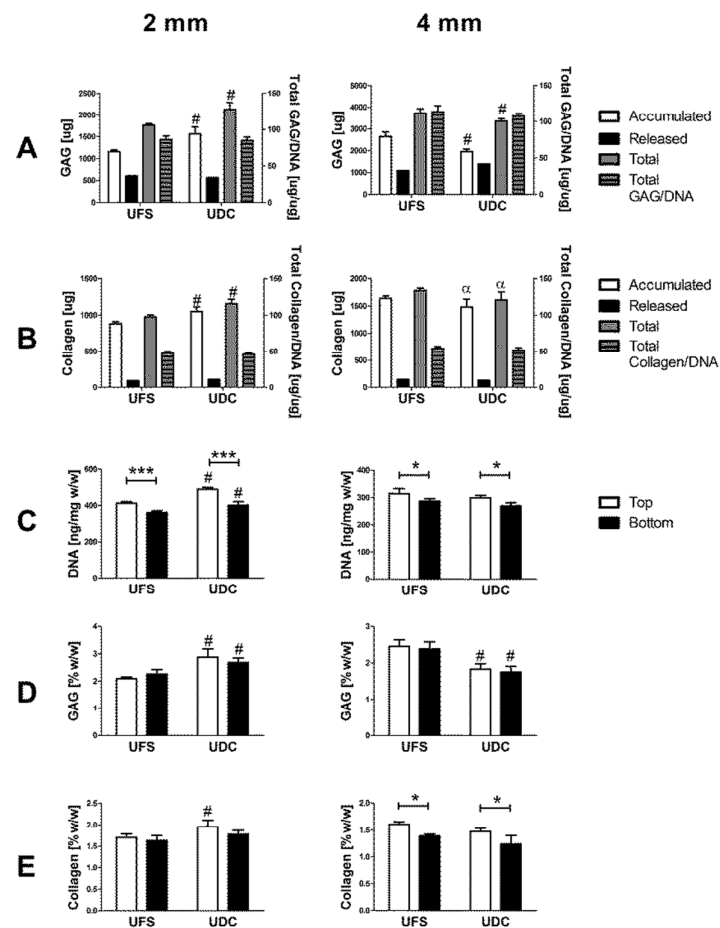


Figure 7. (A) GAG content [μg] and (B) collagen content [μg] accumulated within constructs, released into media and total synthesised (accumulated+released) in unconfined free swelling (UFS) and unconfined dynamically compressed (UDC) 2mm and 4mm constructs at day 42. Total GAG/DNA [μg/μg] and total collagen/DNA [μg/μg] value were also plotted on the right Y axis within each graph. (C) DNA content [ng/mg w/w], (D) GAG content [%w/w] and (E) collagen content [%w/w] of the top and bottom halves of the UFS and UDC 2mm and 4mm samples at day 42. α: trend, p<0.1 vs. UFS; #: p<0.05 vs. UFS; *: p<0.05; ***: p<0.001.

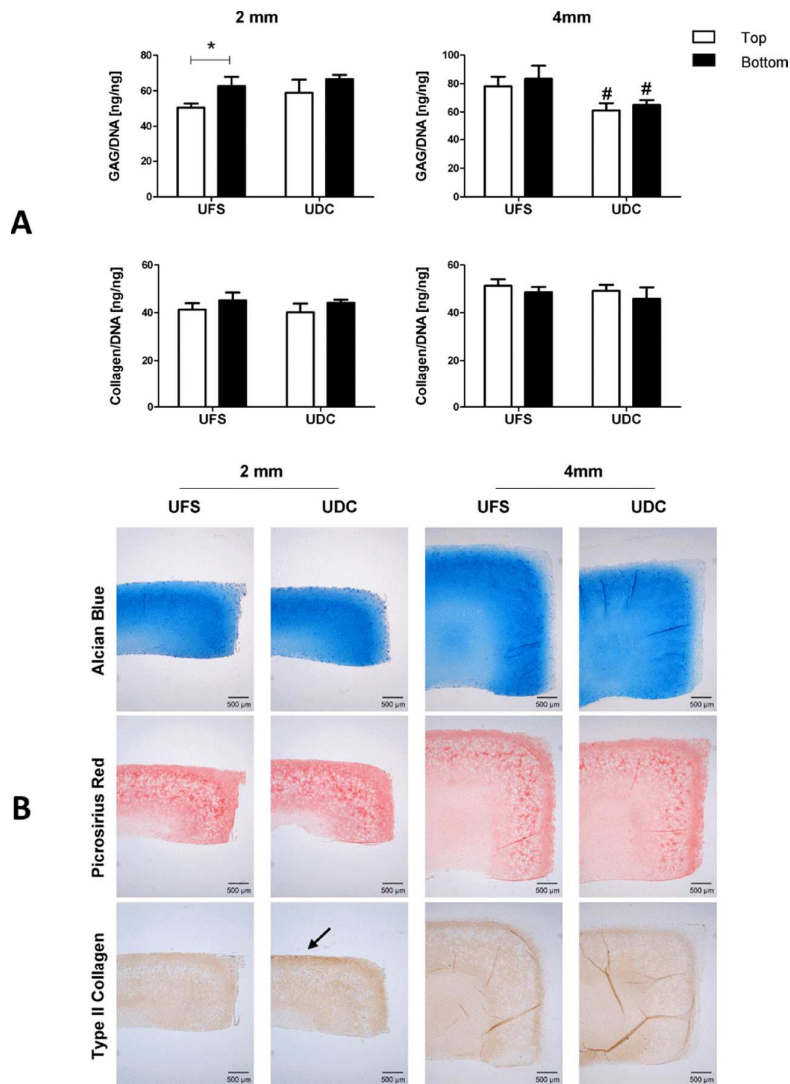

Supplementary figure 2. (A) GAG/DNA [ng/ng] and collagen/DNA [ng/ng] value of the top and bottom halves of UFS and UDC 2mm and 4mm constructs at day 42. #: $p < 0.05$ vs. UFS; *: $p < 0.05$. (B) Alcian blue, picrosirius red and collagen type II staining of UFS and UDC 2mm and 4mm constructs at day 42. Arrow indicates the enhanced collagen type II deposition in the superficial region of 2mm UDC constructs.


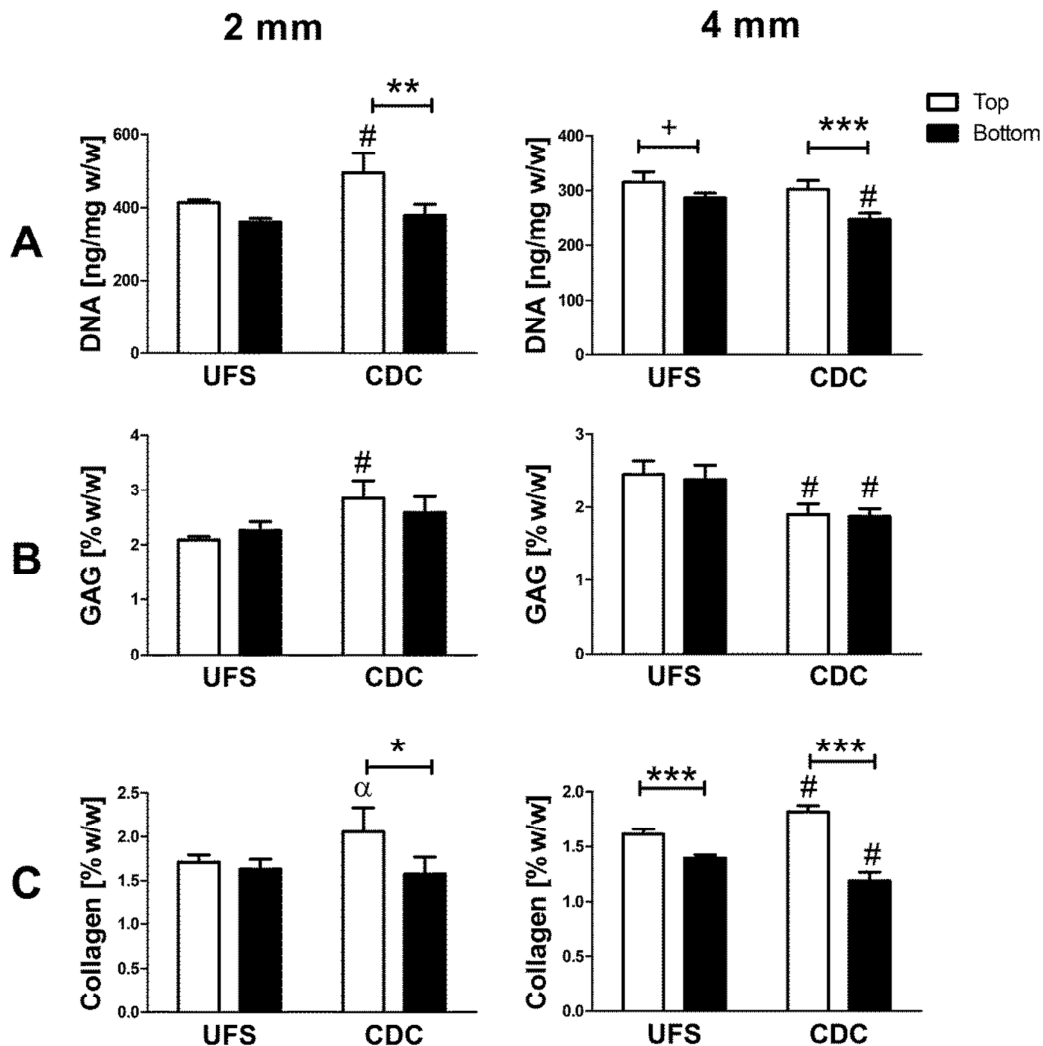


Figure 8. (A) DNA content [ng/mg w/w], (B) GAG content [%w/w] and (C) collagen content [%w/w] of the top and bottom halves of the unconfined free swelling (UFS) and confined dynamically compressed (CDC) 2mm and 4mm samples at day 42. α : trend, $p < 0.1$ vs. UFS; #: $p < 0.05$ vs. UFS; +: trend, $p < 0.1$; *: $p < 0.05$; **: $p < 0.01$; ***: $p < 0.001$.

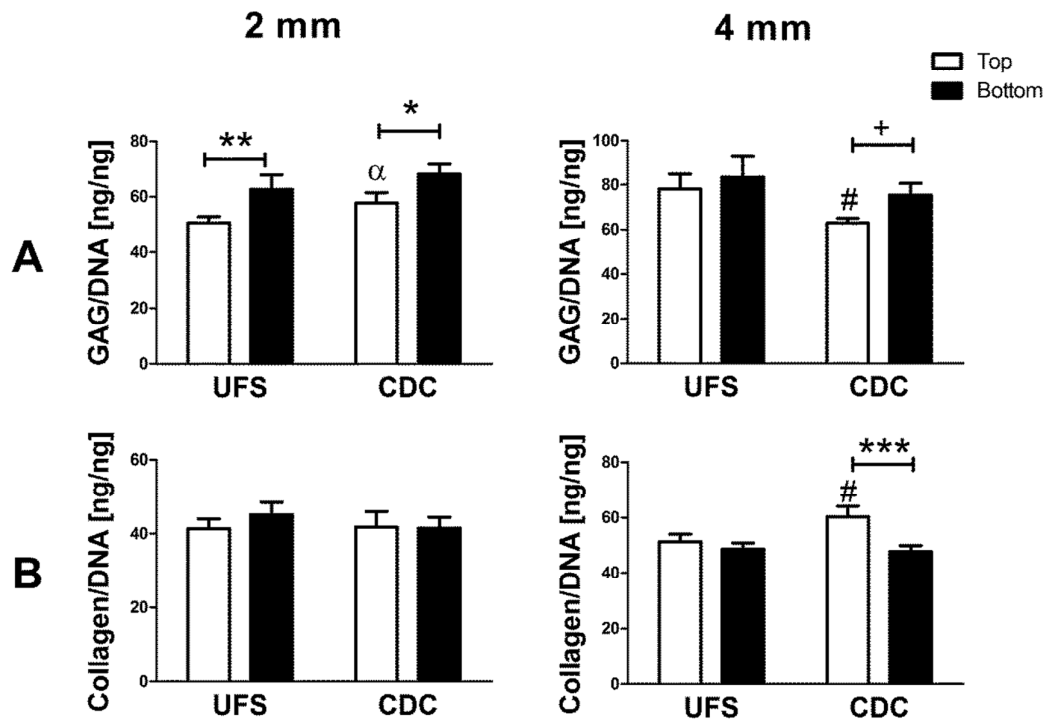

Supplementary figure 3. (A) GAG/DNA [ng/ng] and (B) collagen/DNA [ng/ng] value of the top and bottom halves of UFS and CDC 2mm and 4mm constructs at day 42. α : trend, $p < 0.1$ vs. UFS; #: $p < 0.05$ vs. UFS; +: trend, $p < 0.1$; *: $p < 0.05$; **: $p < 0.01$; ***: $p < 0.001$.

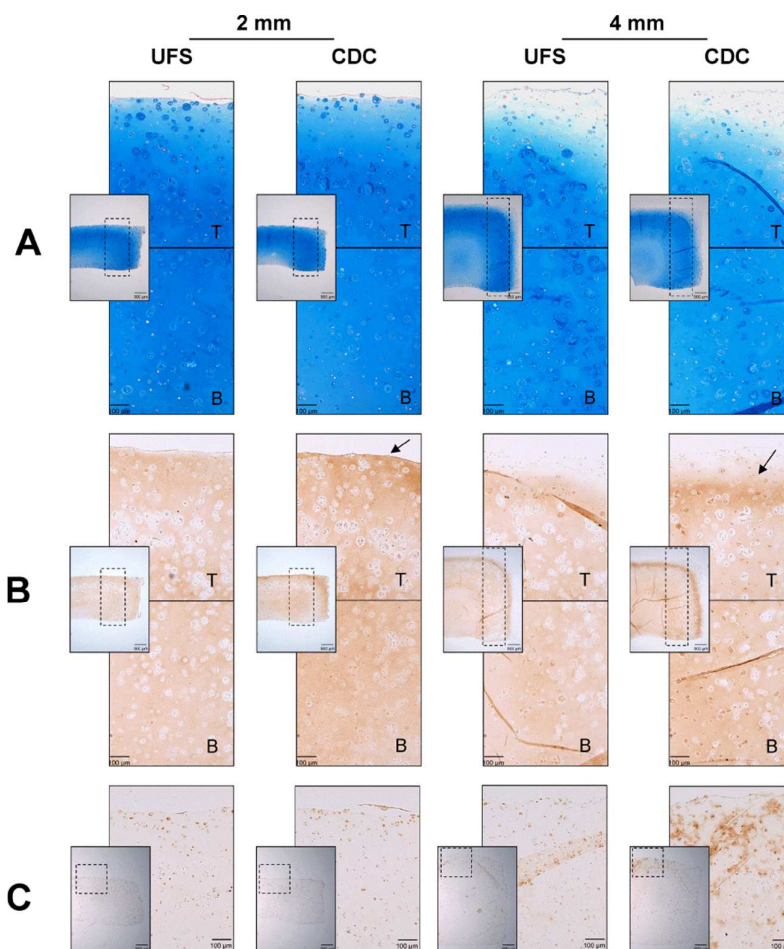


Figure 9. (A) Alcian blue staining for GAG distribution and (B) Immunohistochemical staining for collagen type II distribution through the depth of UFS and CDC 2mm and 4mm constructs at day 42. T: top; B: bottom. Inserted images were taken at 2x magnification to show staining at bulk construct level, with box regions indicating areas where high magnification images were taken. Arrows indicate the enhanced collagen type II deposition in the superficial region of both 2mm and 4mm CDC constructs. (C) Immunohistochemical staining for PRG4 expression at the superficial region of UFS and CDC 2mm and 4mm constructs at day 42.

Reference

- 1
2
3
4
5
6
7
8
9 Bian L, Zhai DY, Zhang EC *et al.* 2012, Dynamic compressive loading enhances cartilage
10 matrix synthesis and distribution and suppresses hypertrophy in hmsc-laden
11 hyaluronic acid hydrogels, *Tissue Eng Part A*, 18: 715-724.
12
13
14
15
16 Buckley CT, Kelly DJ. 2012, Expansion in the presence of fgf-2 enhances the functional
17 development of cartilaginous tissues engineered using infrapatellar fat pad
18 derived mscs, *J Mech Behav Biomed Mater*, 11: 102-111.
19
20
21
22
23 Buckley CT, Meyer EG, Kelly DJ. 2012, The influence of construct scale on the
24 composition and functional properties of cartilaginous tissues engineered using
25 bone marrow-derived mesenchymal stem cells, *Tissue Eng Part A*, 18: 382-396.
26
27
28
29
30 Buckley CT, Thorpe SD, O'brien FJ *et al.* 2009, The effect of concentration, thermal
31 history and cell seeding density on the initial mechanical properties of agarose
32 hydrogels, *J Mech Behav Biomed Mater*, 2: 512-521.
33
34
35
36
37 Buckley CT, Vinardell T, Kelly DJ. 2010a, Oxygen tension differentially regulates the
38 functional properties of cartilaginous tissues engineered from infrapatellar fat
39 pad derived mscs and articular chondrocytes, *Osteoarthritis Cartilage*, 18:
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
- Carroll SF, Buckley CT, Kelly DJ. 2014, Cyclic hydrostatic pressure promotes a stable
cartilage phenotype and enhances the functional development of cartilaginous

1
2
3
4 grafts engineered using multipotent stromal cells isolated from bone marrow
5
6 and infrapatellar fat pad, *J Biomech*, 47: 2115-2121.
7

8
9 Cicione C, Muinos-Lopez E, Hermida-Gomez T *et al.* 2013, Effects of severe hypoxia on
10
11 bone marrow mesenchymal stem cells differentiation potential, *Stem Cells Int*,
12
13 2013: 232896.
14

15
16 De Bari C, Dell'accio F, Tylzanowski P *et al.* 2001, Multipotent mesenchymal stem cells
17
18 from adult human synovial membrane, *Arthritis Rheum*, 44: 1928-1942.
19

20
21 English A, Jones EA, Corscadden D *et al.* 2007, A comparative assessment of cartilage
22
23 and joint fat pad as a potential source of cells for autologous therapy
24
25 development in knee osteoarthritis, *Rheumatology (Oxford)*, 46: 1676-1683.
26

27
28 Gannon AR, Nagel T, Bell AP *et al.* 2015a, The changing role of the superficial region in
29
30 determining the dynamic compressive properties of articular cartilage during
31
32 postnatal development, *Osteoarthritis and Cartilage*, 23: 975-984.
33

34
35 Gannon AR, Nagel T, Bell AP *et al.* 2015b, Postnatal changes to the mechanical
36
37 properties of articular cartilage are driven by the evolution of its collagen
38
39 network, *European Cells and Materials*, 29: 105-123.
40

41
42 Gannon AR, Nagel T, Kelly DJ. 2012, The role of the superficial region in determining
43
44 the dynamic properties of articular cartilage, *Osteoarthritis Cartilage*, 20: 1417-
45
46 1425.
47

48
49 Grad S, Lee CR, Gorna K *et al.* 2005, Surface motion upregulates superficial zone
50
51 protein and hyaluronan production in chondrocyte-seeded three-dimensional
52
53 scaffolds, *Tissue Eng*, 11: 249-256.
54
55
56
57
58
59
60

- 1
2
3
4 Grimshaw MJ, Mason RM. 2000, Bovine articular chondrocyte function in vitro
5
6 depends upon oxygen tension, *Osteoarthritis Cartilage*, 8: 386-392.
7
8
9 Haugh MG, Meyer EG, Thorpe SD *et al.* 2011, Temporal and spatial changes in
10
11 cartilage-matrix-specific gene expression in mesenchymal stem cells in
12
13 response to dynamic compression, *Tissue Eng Part A*, 17: 3085-3093.
14
15
16 Holmes MH, Mow VC. 1990, The nonlinear characteristics of soft gels and hydrated
17
18 connective tissues in ultrafiltration, *J Biomech*, 23: 1145-1156.
19
20
21 Huang AH, Farrell MJ, Kim M *et al.* 2010, Long-term dynamic loading improves the
22
23 mechanical properties of chondrogenic mesenchymal stem cell-laden hydrogel,
24
25 *Eur Cell Mater*, 19: 72-85.
26
27
28 Ignat'eva NY, Danilov NA, Averkiev SV *et al.* 2007, Determination of hydroxyproline in
29
30 tissues and the evaluation of the collagen content of the tissues, *Journal of*
31
32 *Analytical Chemistry*, 62: 51-57.
33
34
35 Kafienah W, Sims TJ. 2004, Biochemical methods for the analysis of tissue-engineered
36
37 cartilage, *Methods Mol Biol*, 238: 217-230.
38
39
40 Khoshgoftar M, Wilson W, Ito K *et al.* 2012, Influence of tissue- and cell-scale
41
42 extracellular matrix distribution on the mechanical properties of tissue-
43
44 engineered cartilage, *Biomech Model Mechanobiol.*
45
46
47 Kim TK, Sharma B, Williams CG *et al.* 2003, Experimental model for cartilage tissue
48
49 engineering to regenerate the zonal organization of articular cartilage,
50
51 *Osteoarthritis and Cartilage*, 11: 653-664.
52
53
54 Kim YJ, Sah RL, Doong JY *et al.* 1988, Fluorometric assay of DNA in cartilage explants
55
56 using hoechst 33258, *Anal Biochem*, 174: 168-176.
57
58
59
60

- 1
2
3
4 Klein TJ, Chaudhry M, Bae WC *et al.* 2007, Depth-dependent biomechanical and
5
6 biochemical properties of fetal, newborn, and tissue-engineered articular
7
8 cartilage, *J Biomech*, 40: 182-190.
9
10
11 Klein TJ, Malda J, Sah RL *et al.* 2009a, Tissue engineering of articular cartilage with
12
13 biomimetic zones, *Tissue Eng Part B Rev*, 15: 143-157.
14
15
16 Klein TJ, Rizzi SC, Reichert JC *et al.* 2009b, Strategies for zonal cartilage repair using
17
18 hydrogels, *Macromol Biosci*, 9: 1049-1058.
19
20
21 Klein TJ, Schumacher BL, Schmidt TA *et al.* 2003, Tissue engineering of stratified
22
23 articular cartilage from chondrocyte subpopulations, *Osteoarthritis and*
24
25 *Cartilage*, 11: 595-602.
26
27
28 Lee RB, Urban JP. 1997, Evidence for a negative pasteur effect in articular cartilage,
29
30 *Biochem J*, 321 (Pt 1): 95-102.
31
32
33 Li Z, Yao SJ, Alini M *et al.* 2010, Chondrogenesis of human bone marrow mesenchymal
34
35 stem cells in fibrin-polyurethane composites is modulated by frequency and
36
37 amplitude of dynamic compression and shear stress, *Tissue Eng Part A*, 16: 575-
38
39 584.
40
41
42 Mansour JM, Mow VC. 1976, The permeability of articular cartilage under compressive
43
44 strain and at high pressures, *J Bone Joint Surg Am*, 58: 509-516.
45
46
47 Maroudas A, Bullough P, Swanson S *et al.* 1968, The permeability of articular cartilage,
48
49 *Journal of Bone & Joint Surgery, British Volume*, 50: 166-177.
50
51
52 Mesallati T, Buckley CT, Kelly DJ. 2014, Engineering articular cartilage-like grafts by self-
53
54 assembly of infrapatellar fat pad-derived stem cells, *Biotechnol Bioeng*, 111:
55
56 1686-1698.
57
58
59
60

- 1
2
3
4 Meyer EG, Buckley CT, Thorpe SD *et al.* 2010, Low oxygen tension is a more potent
5
6 promoter of chondrogenic differentiation than dynamic compression, *J*
7
8 *Biomech*, 43: 2516-2523.
9
10
11 Mow VC, Guo XE. 2002, Mechano-electrochemical properties of articular cartilage:
12
13 Their inhomogeneities and anisotropies, *Annu Rev Biomed Eng*, 4: 175-209.
14
15
16 Muir H, Bullough P, Maroudas A. 1970, The distribution of collagen in human articular
17
18 cartilage with some of its physiological implications, *J Bone Joint Surg Br*, 52:
19
20 554-563.
21
22
23 Nagel T, Kelly DJ. 2012, Apparent behaviour of charged and neutral materials with
24
25 ellipsoidal fibre distributions and cross-validation of finite element
26
27 implementations, *Journal of the mechanical behavior of biomedical materials*,
28
29 9: 122-129.
30
31
32 Nagel T, Kelly DJ. 2013, The composition of engineered cartilage at the time of
33
34 implantation determines the likelihood of regenerating tissue with a normal
35
36 collagen architecture, *Tissue Eng Part A*, 19: 824-833.
37
38
39 Narmoneva D, Wang J, Setton L. 1999, Nonuniform swelling-induced residual strains in
40
41 articular cartilage, *Journal of biomechanics*, 32: 401-408.
42
43
44 Ng KW, Ateshian GA, Hung CT. 2009, Zonal chondrocytes seeded in a layered agarose
45
46 hydrogel create engineered cartilage with depth-dependent cellular and
47
48 mechanical inhomogeneity, *Tissue Eng Part A*, 15: 2315-2324.
49
50
51 Ng KW, Mauck RL, Statman LY *et al.* 2006, Dynamic deformational loading results in
52
53 selective application of mechanical stimulation in a layered, tissue-engineered
54
55 cartilage construct, *Biorheology*, 43: 497-507.
56
57
58
59
60

1
2
3
4 Ng KW, Wang CC, Mauck RL *et al.* 2005, A layered agarose approach to fabricate
5
6 depth-dependent inhomogeneity in chondrocyte-seeded constructs, *J Orthop*
7
8 *Res*, 23: 134-141.

9
10
11 Nguyen LH, Kudva AK, Guckert NL *et al.* 2011a, Unique biomaterial compositions direct
12
13 bone marrow stem cells into specific chondrocytic phenotypes corresponding
14
15 to the various zones of articular cartilage, *Biomaterials*, 32: 1327-1338.

16
17
18 Nguyen LH, Kudva AK, Saxena NS *et al.* 2011b, Engineering articular cartilage with
19
20 spatially-varying matrix composition and mechanical properties from a single
21
22 stem cell population using a multi-layered hydrogel, *Biomaterials*, 32: 6946-
23
24 6952.

25
26
27 Nugent-Derfus G, Takara T, O'Neill J *et al.* 2007, Continuous passive motion applied to
28
29 whole joints stimulates chondrocyte biosynthesis of prg4, *Osteoarthritis and*
30
31 *cartilage*, 15: 566-574.

32
33
34 Roth V, Mow VC. 1980, The intrinsic tensile behavior of the matrix of bovine articular
35
36 cartilage and its variation with age, *J Bone Joint Surg Am*, 62: 1102-1117.

37
38
39 Schinagl RM, Gurskis D, Chen AC *et al.* 1997, Depth-dependent confined compression
40
41 modulus of full-thickness bovine articular cartilage, *J Orthop Res*, 15: 499-506.

42
43
44 Sengers BG, Van Donkelaar CC, Oomens CW *et al.* 2005, Computational study of
45
46 culture conditions and nutrient supply in cartilage tissue engineering,
47
48 *Biotechnol Prog*, 21: 1252-1261.

49
50
51 Sharma B, Williams CG, Kim TK *et al.* 2007, Designing zonal organization into tissue-
52
53 engineered cartilage, *Tissue Eng*, 13: 405-414.

- 1
2
3
4 Thorpe SD, Buckley CT, Vinardell T *et al.* 2010, The response of bone marrow-derived
5
6 mesenchymal stem cells to dynamic compression following tgf-beta3 induced
7
8 chondrogenic differentiation, *Ann Biomed Eng*, 38: 2896-2909.
9
10
11 Thorpe SD, Nagel T, Carroll SF *et al.* 2013, Modulating gradients in regulatory signals
12
13 within mesenchymal stem cell seeded hydrogels: A novel strategy to engineer
14
15 zonal articular cartilage, *PLoS One*, 8: e60764.
16
17
18 Vinardell T, Rolfe RA, Buckley CT *et al.* 2012a, Hydrostatic pressure acts to stabilise a
19
20 chondrogenic phenotype in porcine joint tissue derived stem cells, *Eur Cell*
21
22 *Mater*, 23: 121-132; discussion 133-124.
23
24
25 Vinardell T, Sheehy EJ, Buckley CT *et al.* 2012b, A comparison of the functionality and
26
27 in vivo phenotypic stability of cartilaginous tissues engineered from different
28
29 stem cell sources, *Tissue Eng Part A*, 18: 1161-1170.
30
31
32 Wang DW, Fermor B, Gimble JM *et al.* 2005, Influence of oxygen on the proliferation
33
34 and metabolism of adipose derived adult stem cells, *J Cell Physiol*, 204: 184-
35
36 191.
37
38
39 Williamson AK, Chen AC, Masuda K *et al.* 2003, Tensile mechanical properties of bovine
40
41 articular cartilage: Variations with growth and relationships to collagen
42
43 network components, *J Orthop Res*, 21: 872-880.
44
45
46 Wilson W, Huyghe JM, Van Donkelaar CC. 2007, Depth-dependent compressive
47
48 equilibrium properties of articular cartilage explained by its composition,
49
50 *Biomech Model Mechanobiol*, 6: 43-53.
51
52
53
54
55
56
57
58
59
60

1
2
3
4 Zhou S, Cui Z, Urban JP. 2004, Factors influencing the oxygen concentration gradient
5
6 from the synovial surface of articular cartilage to the cartilage-bone interface: A
7
8 modeling study, *Arthritis Rheum*, 50: 3915-3924.
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

For Peer Review