



OPEN

SUBJECT AREAS:
ELECTRONIC PROPERTIES
AND DEVICES
ELECTROCHEMISTRYReceived
3 October 2014Accepted
22 December 2014Published
30 January 2015Correspondence and
requests for materials
should be addressed to
B.H.K. (kbh37@
incheon.ac.kr) or Y.J.
(yjun@konkuk.ac.kr)* These authors
contributed equally to
this work.

One-step hydrothermal synthesis of graphene decorated V_2O_5 nanobelts for enhanced electrochemical energy storage

Minoh Lee^{1*}, Suresh Kannan Balasingam^{2*}, Hu Young Jeong³, Won G. Hong⁴, Han-Bo-Ram Lee⁵,
Byung Hoon Kim⁶ & Yongseok Jun⁷

¹Department of Chemical Engineering, Ulsan National Institute of Science and Technology (UNIST), Ulsan 689-798, Republic of Korea, ²Department of Chemistry, Ulsan National Institute of Science and Technology (UNIST), Ulsan 689-798, Republic of Korea, ³School of Materials Science and Engineering, Ulsan National Institute of Science and Technology (UNIST), Ulsan 689-798, Republic of Korea, ⁴Division of Materials Science, Korea Basic Science Institute, Daejeon 305-333, Republic of Korea, ⁵Department of Materials Science and Engineering, Incheon National University, Incheon 406-772, Republic of Korea, ⁶Department of Physics, Incheon National University, Incheon 406-772, Republic of Korea, ⁷Department of Materials Chemistry & Engineering, Konkuk University, Seoul 143-701, Republic of Korea.

Graphene-decorated V_2O_5 nanobelts (GVNBs) were synthesized via a low-temperature hydrothermal method in a single step. V_2O_5 nanobelts (VNBs) were formed in the presence of graphene oxide, a mild oxidant, which also enhanced the conductivity of GVNBs. From the electron energy loss spectroscopy analysis, the reduced graphene oxide (rGO) are inserted into the layered crystal structure of V_2O_5 nanobelts, which further confirmed the enhanced conductivity of the nanobelts. The electrochemical energy-storage capacity of GVNBs was investigated for supercapacitor applications. The specific capacitance of GVNBs was evaluated using cyclic voltammetry (CV) and charge/discharge (CD) studies. The GVNBs having V_2O_5 -rich composite, namely, V_3G_1 (VO/GO = 3 : 1), showed superior specific capacitance in comparison to the other composites (V_1G_1 and V_1G_3) and the pure materials. Moreover, the V_3G_1 composite showed excellent cyclic stability and the capacitance retention of about 82% was observed even after 5000 cycles.

Ensuring the availability of energy is a serious concern faced worldwide, and therefore, alternative energy-conversion systems based on renewable energy sources have been in the focus of research. The transportation of that kind of sustainable energy from the point of generation to the end user is yet another challenging task that involves power grids for large-distance and high-capacity energy-storage devices for small-scale and mobile applications¹. For small-scale applications, batteries have been developed with high energy density that, however, are limited by a low power density. Traditional capacitors are best known for their high power density, but have a fundamental flaw in their low energy density. By combining the figure of merit of these two systems, supercapacitors (also known as ultracapacitors or electrochemical double-layer capacitors, EDLCs) are being developed, resulting in higher power density and energy density than conventional batteries and traditional capacitors, respectively². Basically, carbon materials are best known for their double layer capacitance behaviour, which provides the high power density to the capacitors. To enhance the energy density of supercapacitors, suitable pseudocapacitance materials have been combined with the carbon-based materials. Various carbon materials, such as activated carbon, graphite, carbon nanotubes, or graphene have been used. Among these, graphene, a new class of carbon material has attracted great interest due to its high surface area and excellent electrical, mechanical, chemical, and thermal properties^{3,4}. In case of pseudocapacitance materials, conducting polymers and transition-metal oxides are primarily used in order to enhance the energy density of supercapacitors⁵. Among the various transition-metal oxides, V_2O_5 (VO) has widely been investigated as a high-potential candidate material because of the following merits: low cost, abundant resources, layered structure, high energy density, and wide potential window arising from its multivalent oxidation states^{6,7}. Although VO-based materials have achieved remarkable benchmark properties in various fields, such as in lithium-ion batteries, field-effect transistors, gas sensors, and supercapacitors, their poor electronic conductivity and bulk material properties



prevent enhanced device performance^{8–12}. In this regard, a large number of VO nanostructures, such as nanowires, nanotubes, and nanobelts have recently been fabricated in order to obtain a high surface area^{13,14}. Moreover, the combination of commercially available carbon allotropes and their derivatives with metal-oxide materials enhances the electronic conductivity of the composites and also prevents agglomeration of metal-oxide nanoparticles during cycling tests^{15–17}. Enhanced electrochemical energy storage using nanostructured VO/graphene composites have been reported recently^{18–21}. However, the preparation of nanostructures of VO/graphene composites commonly followed two-step processes in which reduced graphene oxide (rGO) was usually prepared either by chemical reduction or by a thermal treatment in order to obtain higher conductivity^{22–25}. Further, very recently, our group synthesized graphene decorated nanostructured VO by simple mixing of VO particles and graphene oxide (GO) in DI water. However, this process takes a long time (approximately eight weeks) to fabricate nanostructure²⁶. In this paper, we have reported a facile low-temperature hydrothermal process for the rapid synthesis of graphene-decorated VO nanobelts (GVNBs) without any harmful oxidizing or reducing chemical agents and surfactants. During the synthesis of GVNBs, VO particles were converted into uniformly distributed nanobelts with simultaneous reduction of GO into rGO, even at low temperature. GO played a vital role in this study. Initially, GO might act as a mild oxidizing agent to synthesize V_2O_5 nanobelts in DI water under hydrothermal conditions, in which GO is converted into rGO (generally, oxidizing agents reduce themselves while chemical reaction occurs). Once the GVNBs are synthesized, the highly conducting reduced GO provides double layer capacitance (in turn high power density) to the supercapacitors. Overall, the nanostructured VO involves in the faradaic reaction (pseudocapacitance), which provides high energy density and the highly conducting rGO having large surface area implicates double layer capacitance, which delivers high power density to the supercapacitors. The as prepared GVNBs having vanadium rich composition showed the enhanced specific capacitance of 288 F g^{-1} due to the combination of pseudocapacitance and double-layer capacitance behaviour.

Results and Discussion

Figure 1 illustrates the role of the different precursors on the synthesis of GVNBs by the low-temperature hydrothermal process. The

mixing of VO suspension and rGO precursors did not induce the formation of nanobelts (Scheme a). However, the mixing of GO precursors with the VO dispersion under the same experimental conditions (scheme c) leads to the formation of GVNBs. In order to confirm the role of GO on the nanobelts formation, only VO dispersion was subjected to the low-temperature hydrothermal process at identical experimental conditions (scheme b), but no noticeable morphological change could be observed. Figure 2 presents the field-emission scanning electron microscopy (FE-SEM) images of pristine VO, VO after the hydrothermal treatment, the composite of VO with rGO, and GVNBs synthesized via the low-temperature hydrothermal process with different ratios of VO and GO (V_3G_1 , V_1G_1 , and V_1G_3 , here V_3G_1 indicates the ratio of VO/GO = 3:1). On the basis of FE-SEM images, the transformation into nanobelts have been observed only in case GO was added into the VO suspension, whereas the absence of GO or the use of rGO at the same conditions did not induce the formation of GVNBs. The structure of pristine VO, GVNBs, and rGO have been investigated by X-ray diffraction (XRD), as shown in Figure 3. The peaks of pristine VO well matched the corresponding standard pattern (JCPDS Card No. 89-0612). The XRD patterns of different composites (V_3G_1 , V_1G_1 , and V_1G_3) of GVNBs contain peaks of GO, rGO, and VO nanobelts (VNBs). The peaks at 6.32° , 25.9° , 28.5° , 32.7° , and 41.7° correspond to the (001), (110), (111), (004), and (005) planes of VNBs, respectively^{27,28}. The interlayer distance of GVNBs at the (001) reflection is calculated to be 1.40 nm, which is larger than the interlayer distance of pure V_2O_5 nanowires (1.15 nm) reported previously for the same (001) planes^{29,30}. The peaks at 17.2° , 24.6° are assigned to partially reduced GO and rGO respectively³¹. Usually, GO is reduced to rGO via a high-temperature heat treatment or by strong reducing agents. In this experiment, partially reduced GO (prGO) was synthesized using the hydrothermal method under identical conditions for all samples to enable a quantitative comparison of the performance^{32–34}. GO shows (001) reflection at the peak position of 10.72° (8.25 \AA)³⁵. When GO is reduced by external factors like a heat treatment or reducing chemical agents, etc., the peak position of the GO sheet shifts toward higher scattering angles, according to the degree of reduction. prGO synthesized by the hydrothermal method shows the (002) reflection at the peak position of 16° (5.54 \AA). The new peak appeared the (002) plane at 24° (3.71 \AA) is the characteristic of rGO. Most interestingly, the GVNBs show a very sharp characteristic

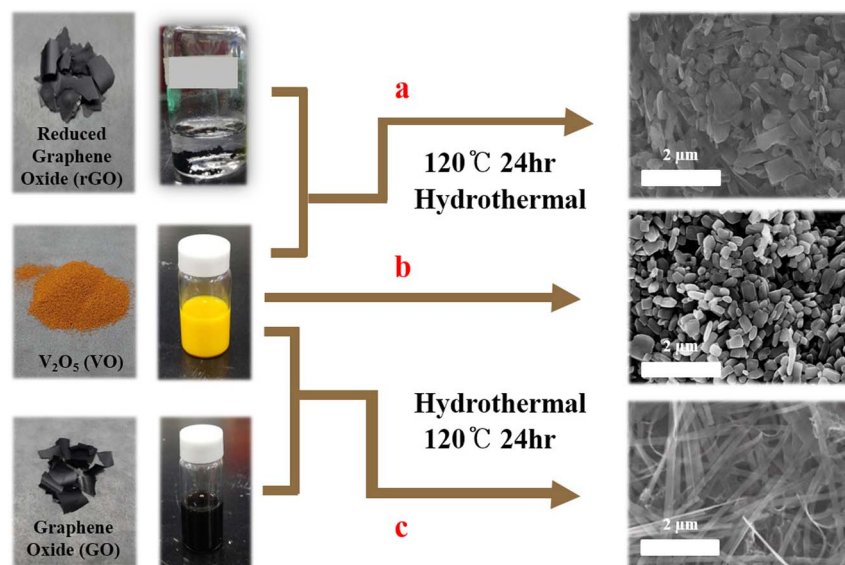


Figure 1 | Schemes a and b represent the absence of nanobelts formation in case of rGO addition and without carbon material, respectively, via low-temperature hydrothermal synthesis. Scheme c represents the formation of GVNBs by mixing of GO into VO dispersion under the same hydrothermal conditions.

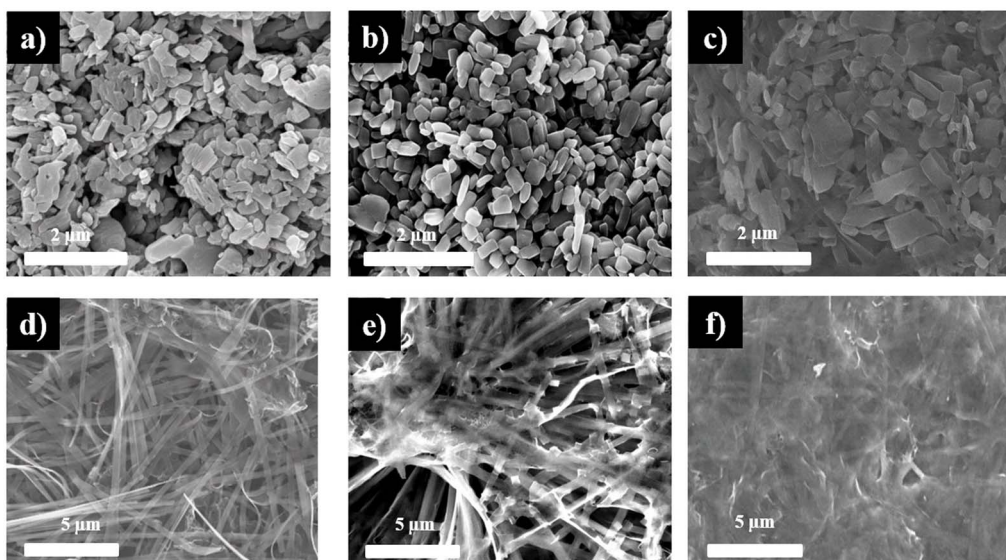


Figure 2 | SEM images of (a) pristine VO particles, (b) VO after the hydrothermal treatment, (c) VO with rGO after the hydrothermal treatment, and calcined GNVBs with the following ratios of VO and GO: (d) 3:1 (e), 1:1 (f) 1:3.

rGO peak of the (002) plane at 24° (3.71 \AA) and, simultaneously, the (002) reflection of prGO at the peak position of 17.5° (5.07 \AA), which confirms that the mixing of V_2O_5 with GO under the identical hydrothermal conditions leads to the pronounced reduction of GO to rGO (shift of the (002) peak from 16 to 17.5°)^{31,36,37} Figure 4a shows a bright-field transmission electron microscopy (BF-TEM) image of a GNVB with a width of $\sim 200 \text{ nm}$ and the corresponding selective area electron diffraction (SAED) pattern. Orthorhombic crystal structure with a lattice parameter of $a = 12.30 \text{ \AA}$, $b = 3.81 \text{ \AA}$, $c = 13.98 \text{ \AA}$ is confirmed by the indexing of diffraction spots, which are larger than the pure VNBs lattice parameter values ($a = 11.722 \text{ \AA}$, $b = 3.570 \text{ \AA}$, $c = 11.520 \text{ \AA}$)³⁸. The GNVB preferentially grows along the [010] direction. In order to identify the existence of carbon element inside the GNVBs, we employed scanning transmission electron microscopy (STEM) and electron energy loss spectroscopy (EELS) technique. As shown in EELS, elemental mapping of figure 4c and d, carbon is detected at the whole GNVB region, but the distribution is uneven. Moreover, the point EELS spectrum (see Figure 4e) clearly shows the strong carbon signal at the marked region of figure 4d. The bright contrast of STEM image, strong carbon signal, and increased lattice parameter may be due to the

distribution of nano-sized rGO sheets between the V_2O_5 layers. Figure S1 (a) shows the Raman spectrum of V_3G_1 , which reflects the interaction of VO and GO. The peak at 990 cm^{-1} corresponds to the stretching mode related to the vanadium-oxygen bond $\text{V}=\text{O}$ ³⁹. The peaks at 519 cm^{-1} and 688 cm^{-1} are assigned to the bending vibrations of $\text{V}_3\text{-O}$ (trily coordinated oxygen) and $\text{V}_2\text{-O}$ (doubly coordinated oxygen) bonds, respectively⁴⁰. The peaks centered at 283 cm^{-1} and 403 cm^{-1} are attributed to the modes originating from y - and x -displacements of O1 atoms, respectively⁴¹. High-frequency Raman peaks at 1352 cm^{-1} and 1590 cm^{-1} matched the D and G band of GO, respectively. The G band of GNVBs shows a little shift of up to 10 cm^{-1} compared to that of rGO, which may be due to the interaction between the GO and VO interfaces (Figure S1 (b))^{42,43}. As evident from the V2p X-ray photoelectron spectroscopy (XPS) spectrum shown in Figure S2, the peaks located at 515.8 eV and 517.5 eV correspond to the +4 and +5 oxidation states of vanadium ions, respectively. The ratio of the two V2p peaks represents the quantitative information of two different vanadium ions (+4 and +5) in the composites. If VO and GO are mixed in DI water, after 1 day, a significant amount of V^{4+} ions is oxidized and the seeding is initiated in a direction, which is confirmed by the reduction in the ratio of $\text{V}^{4+}/\text{V}^{5+}$ from 0.096 to 0.055. Following the hydrothermal reaction, the increase in the ratio of $\text{V}^{4+}/\text{V}^{5+}$ (from 0.055 to 0.2524) was observed, which could be ascribed to the metastable state of vanadium oxide. The higher value of $\text{V}^{4+}/\text{V}^{5+}$ (0.2524) compared to the previous report (0.153)²⁶ might be due to the effect of external forces such as high pressure and temperature during the hydrothermal reaction. Therefore, the mechanism of the nanobelts formation can be assumed as follows: The oxygen-containing functional groups present at the GO surface interact with the vanadium pentoxide surface. GO acts like an oxidizing agent, which oxidizes the vanadium ions from the partially existing V^{4+} to the V^{5+} soluble state during the reaction with GO. This intermediate compound is unstable and turns back into the stable +4 oxidation state (formation of VO seeds by trapping electrons from water molecules), and forms nanobelts^{26,44}. As suggested by Li et al., seeded V_2O_5 pieces gather together in the existence of rGO, gradually grows in a direction to form a nanobelt composite^{45–49}. Figure S3 presents C1s XPS spectra of GO before and after the hydrothermal treatment, and mixture of GO and V_2O_5 (V_3G_1) after the hydrothermal treatment. Compared to pristine GO (GO before the hydrothermal treatment, Figure S3 (a)), a lower amount of oxygen-containing functional groups at the

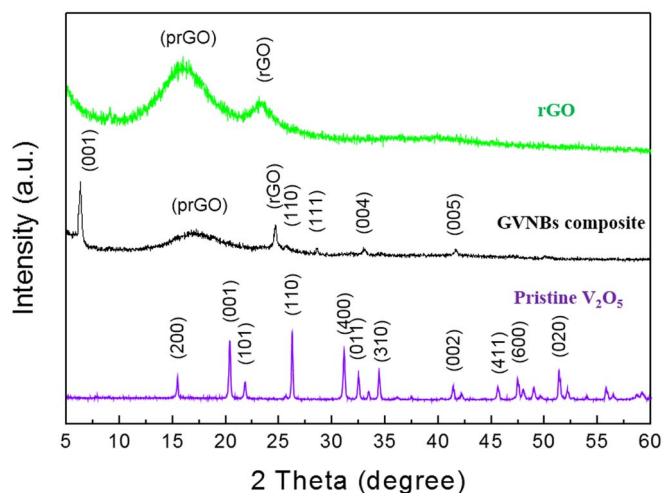


Figure 3 | XRD spectra of pristine V_2O_5 , composite GNVBs, and rGO measured in the 2θ range of 5° to 60° .


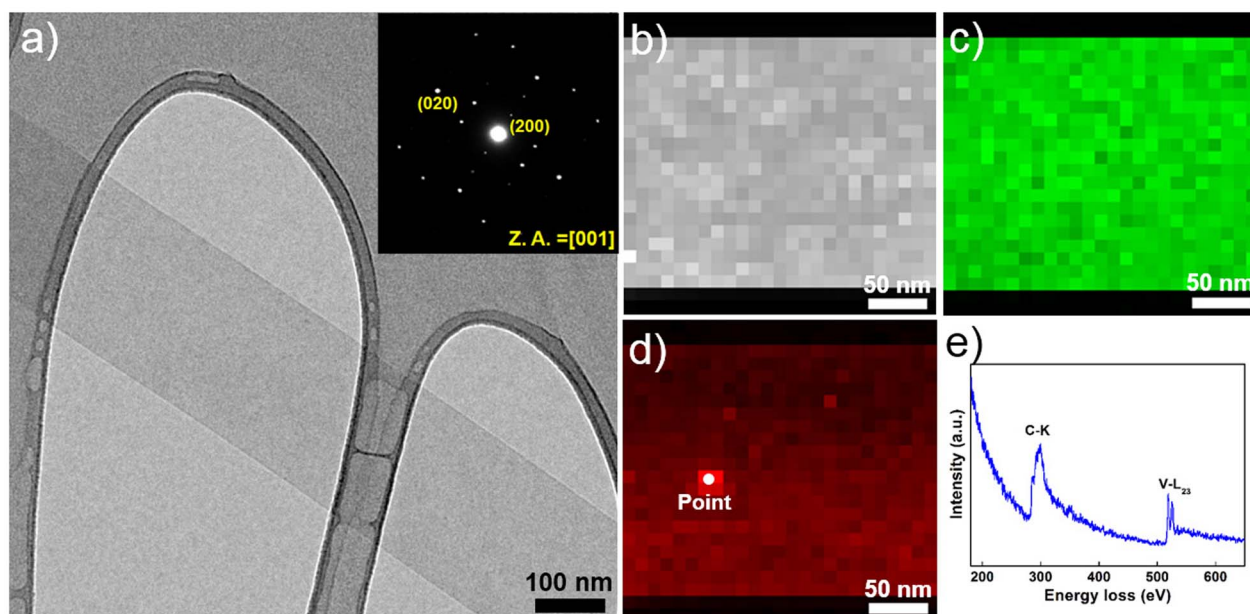


Figure 4 | (a) BF-TEM image of a GVNB and corresponding SAED (The inset). (b) HAADF-STEM image of a GVNB and corresponding EELS elemental mapping (c) vanadium and (d) carbon. (e) EELS spectrum acquired at the point of figure (d).

surface of GO and a higher portion of C-C bonding is observed in Figures S3 (b) and (c), which shows that even the low-temperature hydrothermal treatment leads to the partial reduction of GO to rGO. Interestingly, a higher portion of C-C bonding (284.6 eV) is observed in Figure S3 (c), which may originate from the interaction of V_2O_5 with GO, in addition to the hydrothermal treatment^{32,36,37,44,50}. The width and thickness of a single nanobelt has been measured using atomic force microscopy (AFM), the measured values are 330 ± 20 nm and 25 ± 5 nm, respectively (Figure S4).

The electrochemical performance of VO, rGO and GVNBs was measured in 1 M Na_2SO_4 electrolyte and the specific capacitance C_s (in $F g^{-1}$) of the electro-active materials was calculated using CV, as well as galvanostatic charge/discharge curves. CV of the electro-active materials was carried out at a scan rate of $10 mV s^{-1}$ in the potential window of 0.0 to 0.8 V (Figure 5 (a)). All curves retain their quasi-rectangular shape, which confirms ideal EDLC of the materials. The vanadium-rich composite (V_3G_1) shows a broad redox peak with retention of quasi-rectangular shape. The calculated C_s value of the electro-active materials V_3G_1 , V_1G_1 , V_1G_3 , rGO, and VO are 288, 244, 135, 28.8, and $24.8 F g^{-1}$ respectively. As expected, the three different composites of V_xG_y material (V_3G_1 , V_1G_1 , and V_1G_3) possess higher C_s values than rGO and VO. The enhanced capacitance of the V_xG_y materials is attributed to the combination of non-faradaic (EDLC) and faradaic (redox) electrochemical processes. The intercalated rGO sheets provide high electrical conductivity and the addition of rGO with VO provides larger surface area, which further enhances the EDLC (non-faradaic process) of the V_xG_y materials. Moreover, the V_2O_5 nanobelts have high surface area, layered crystal structure, and multivalent oxidation states of vanadium ions. These properties facilitate the insertion and extraction of alkali-metal ions (Li^+ , Na^+ , K^+ etc.) near the surface of the electro-active material. The electrochemical sodium-ion insertion process can be expressed as follows⁵¹:



From Equation (1), the charge/discharge processes involve the reversible intercalation of sodium ions into the layered V_2O_5 crystal structure with simultaneous electron transfer. This redox reaction leads to the partial reduction of V^{+5} to V^{+4} (and vice versa during oxidation)

and thus provides the pseudocapacitance to the V_xG_y composites. Among the V_xG_y group of electro-active materials, the vanadium-rich composite V_3G_1 showed the highest C_s value of around $288 F g^{-1}$ (at the scan rate of $10 mV s^{-1}$), which is higher than the previously reported capacitances in the works of Fu et al¹⁹. (graphene/vanadium-oxide nanotubes, $225 F g^{-1}$ @ $10 mV s^{-1}$ in 1 M Na_2SO_4 solution), and Bonso et al⁵². (composite of exfoliated graphite nanoplatelets and V_2O_5 nanotubes, $35 F g^{-1}$ @ $10 mV s^{-1}$ in 2 M KCl, $226 F g^{-1}$ @ $10 mV s^{-1}$ in LiTFSI electrolyte). The rGO-dominated composite V_1G_3 has a low content of excess rGO and also the porosity is limited by the existence of excess rGO (see SEM image Figure 2 (f)). Noticeably, the presently investigated rGO has a lower capacitance than the values reported in the literature^{19,53,54}. The lower C_s value of rGO is ascribed to the low conductivity, which arises from the partial reduction of GO to rGO. Since the low-temperature hydrothermal synthesis was adopted and furthermore, no reducing chemical reagents are added in this work, the degree of reduction of GO to rGO is less compared to other methods^{19,51,55,56}. From the XRD analysis, the intensity of the rGO peak is smaller than that of the GO peak, which confirms the partial reduction of GO to rGO. In general, GO has lower conductivity than rGO due to the presence of oxygen-containing functional groups in the sp^3 -hybridized orbital^{31,33}. The lower C_s value of pristine V_2O_5 particles may arise from the smaller surface area and lower conductivity in comparison to V_2O_5 nanostructures^{19,57}. If the V_xG_y materials are synthesized hydrothermally at low temperature, the interaction between oxygen-containing functional groups (present in GO) and the V_2O_5 crystallites is significant, which leads to the pronounced conversion of GO to rGO (refer also to the XRD section and the mechanism for nanobelt formation). Therefore, all V_xG_y composites possess higher conductivity and capacitance than the individual components. Moreover, the presence of V_2O_5 nanobelts between the graphene sheets prohibits the re-stacking of graphene sheets, which further enhances the conductivity of graphene³⁴. To further understand the electrochemical reversibility of the V_3G_1 composite, additional CV studies were performed at different scan rates (5, 10, 25, 50, 75, 100, and $125 mV s^{-1}$) in 1 M Na_2SO_4 electrolyte solution. All CV curves retain their ideal quasi-rectangular shape even at higher scan rates (Figure 5 (b)), which is an indication of ideal capacitive behavior with excellent reversibility of this electrode material⁵¹. Figure 5 (c) shows the relationship between the

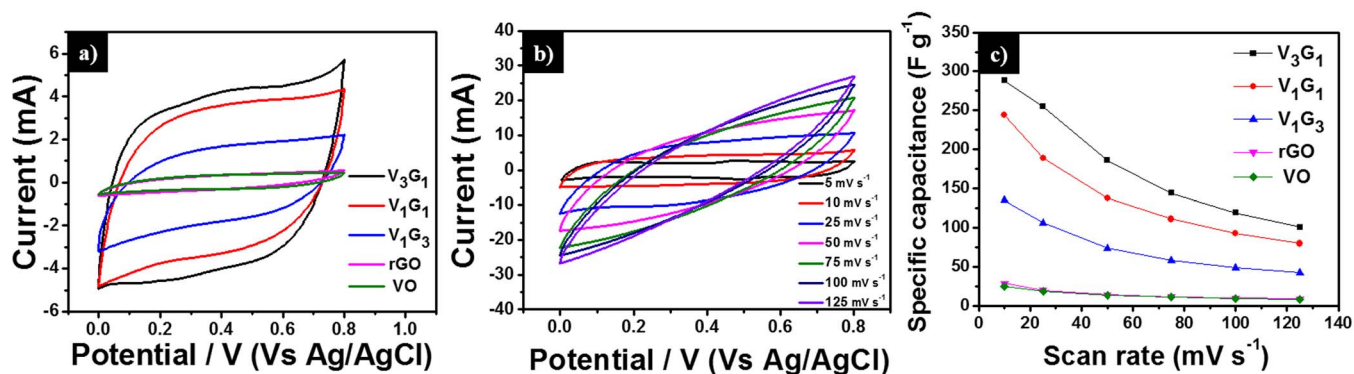


Figure 5 | (a) CV curves of rGO, pristine VO particles, V_1G_3 , V_1G_1 , and V_3G_1 electro-active materials measured at a scan rate of 10 mV s^{-1} in $1 \text{ M Na}_2\text{SO}_4$ solution. (b) CV curves of the V_3G_1 electrode measured at different scan rates ranging from 5 to 125 mV s^{-1} . (c) Specific capacitance calculated from the CV curves of Figure 1(b) of the V_3G_1 electrode at various scan rates.

specific capacitance of the electrode materials and the scan rate. By increasing the scan rate, the C_s value drops, which is a common phenomenon arising from the mass-transport limitation of sodium ions at high scan rates⁵⁸. In detail, the interior (bulk part) of the electrode cannot sustain the redox transition due to the diffusion limitation of ions within the electrode. Therefore, the part of the electrode surface is inaccessible for electrochemical reaction at higher scan rates, which leads to a lower capacitance. Figure 6 (a) shows the galvanostatic charge-discharge (CD) curves of rGO, pristine VO particles, and the three different V_xG_y composites obtained using $1 \text{ M Na}_2\text{SO}_4$ solution at a current density of 0.5 A g^{-1} . The C_s values of the electro-active materials V_3G_1 , V_1G_1 , V_1G_3 , rGO, and VO are 128.8, 111.9, 117.5, 8.2, and 6.3 F g^{-1} respectively. Consistent with the CV curves, the discharge time and the specific capacitance of the V_xG_y materials are higher than those of pristine V_2O_5 particles and rGO sheets. The CD profiles of the V_3G_1 and V_1G_1 composites are symmetric and resemble an equilateral triangle, which is an indication of a high rate capability during the CD process. The CD curve of the V_1G_3 composite deviates from the ideal linear relationship due to the poor conductivity of this material, which further limits its pseudocapacitance¹⁹. Figure 6 (b) presents the CD profiles of the V_3G_1 composite at various CD rates. All CD curves exhibit a nearly linear CD rate from low to high current densities, which is an indication of balanced faradaic and non-faradaic processes. At very low discharge current density of 0.25 A g^{-1} , the pseudocapacitance behavior is clearly visible, reflected in the non-linear shape of the CD curve, and the specific capacitance of 134 F g^{-1} was observed. For higher current densities such as 0.5, 0.75 and 1 A g^{-1} , the respective specific capacitance values are calculated as 128.8, 108 and 103.9 F g^{-1} .

Further the calculated specific capacitance values of V_1G_1 at various current densities (0.25, 0.5, 0.75 and 1 A g^{-1}) are as follows: 128, 111.9, 105 and 97.5 F g^{-1} . The graphene rich composition V_1G_3 has specific capacitance values of 121, 117.5, 88.1 and 55 F g^{-1} at the same descending order of current density values. Electrochemical impedance spectroscopy (EIS) is an ideal tool to analyze the internal resistance and capacitance of electrode materials. EIS experiments were carried out in the frequency range of 0.01 Hz to 100 KHz in aqueous $1 \text{ M Na}_2\text{SO}_4$ solution. Figure 6 (c) represents the Nyquist plots of rGO, pristine V_2O_5 particles, and three different composites of V_xG_y electro-active materials. Each Nyquist plot shows a semicircle at high-to-medium frequencies and an inclined line at low frequency, which represent the charge-transfer and diffusion resistance, respectively. In the high-frequency region, the first intersection point with the real axis represents the total impedance of the bulk solution (R_s), electrodes (R_e), and the contact resistance (R_c) between electrode and current collector. At medium frequencies, the second intersection point of the semicircle with the real axis indicates the combination of the double-layer capacitance (C_{dl}) in parallel with the charge-transfer resistance (R_{ct}). The inclined line in the low-frequency region represents the Warburg impedance (W_s) corresponding to the diffusive resistance of the electrolyte in the interior part of the electrode surface. The R_{ct} values of VO, rGO, V_1G_3 , V_1G_1 , and V_3G_1 are 27.5, 20.2, 13.6, 9.2, and 5.7Ω respectively. The charge-transfer resistance of the V_xG_y materials is lower than in case of VO and rGO. The lower R_{ct} value of the V_xG_y materials leads to improved charge transfer and enhanced capacitance due to the following reasons: (i) V_2O_5 nanobelts having high surface area enhances the pseudocapacitance of the electrode material, (ii) V_xG_y materials possess highly conducting rGO

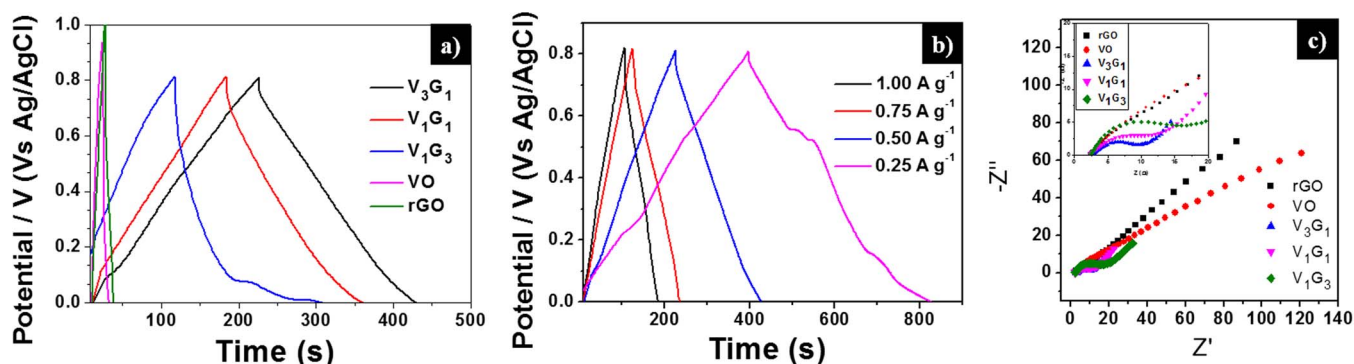


Figure 6 | (a) Galvanostatic charge-discharge curves of rGO, pristine VO particles, V_1G_3 , V_1G_1 , and V_3G_1 electro-active materials measured at a constant current density of 0.5 A g^{-1} in $1 \text{ M Na}_2\text{SO}_4$ solution. (b) Galvanostatic charge-discharge curves of V_3G_1 electrode material measured at various current densities. (c) Electrochemical impedance spectra of rGO, pristine V_2O_5 particles, V_1G_3 , V_1G_1 , and V_3G_1 electro-active materials measured in $1 \text{ M Na}_2\text{SO}_4$ solution. The inset shows an enhanced view of the high-to-medium frequency region.



sheets with high surface area improved the electronic conductivity of the GNVB composite and also enhance the electrochemical double-layer capacitance of the working electrode and (iii) the incorporation of V_2O_5 nanobelts between the graphene sheets prevents the agglomeration of graphene sheets which also enhances the conductivity. Electrochemical cycling stability is one of the key factors that determines the applicability of this material to commercial supercapacitors. The cyclic stability of the V_3G_1 composite was measured by CV in the potential window of 0 to 0.8 V at a high scan rate of 200 mV s^{-1} for 5000 cycles. According to previous reports, the capacitance retention of pure vanadium oxide in aqueous electrolyte is very poor due to the structural damage caused by the insertion and desorption of electrolyte ions^{19,59}. In the present case, the V_3G_1 material retains 93% of its initial capacitance value after 1000 cycles and, further, 82% capacitance retention is observed even after 5000 cycles which demonstrates excellent stability of the material with superior reversibility during the cycling test (Figure 7 (a)). This capacitance retention is much higher than that previously reported by Fu et al¹⁹. (48% retention after 5000 cycles @ 100 mV s^{-1} scan rate) and the best among vanadium oxide-based composite materials^{51,52}. EIS was measured after 5000 cycles for the post analysis of the electrode material. The shape of the EIS spectrum was similar to the initial spectrum, which comprises a semicircular arc in the high-frequency region and an inclined line in the low-frequency region. The R_{ct} value increased from 2.3 to 6.32Ω after 5000 cycles (see Figure 7 (b)). This might be induced by the adhesion loss between the electro-active material and the current collector or due to the dissolution of a small amount of V_2O_5 in aqueous medium at a high scan rate (the change in color of the solution from white to yellow is an indication)^{53,60,61}. From the electrochemical performance described above, we conclude that GNVBs could be a potential candidate for practical supercapacitor applications. Moreover, the electrical conductance affects the intrinsic performance of GNVBs, hence we measured the current-voltage (I - V) characteristics of a single GNVB synthesized by hydrothermal method as shown in Fig. S5, the values are much higher than a single GNVB grown by spontaneous method and V_2O_5 nanowire (VON) synthesized by sol-gel method²⁶. The superior current was observed in the I - V curve of GNVB synthesized by hydrothermal method which may be the reason for the enhancement of the specific capacitance.

In summary, we have reported a facile method for the synthesis of GNVBs using a low-temperature hydrothermal process. GO played a vital role as a mild oxidizing agent for the formation of nanowires, as well as enhanced the conductivity of GNVBs. The insertion of rGO

into the layered V_2O_5 crystal structure is confirmed by EELS analysis. The high surface area and pseudocapacitive nature of VNBs along with the enhanced conductivity of GNVBs upon addition of graphene resulted in an improved specific capacitance. Among various GNVBs, the V_2O_5 -rich composition, V_3G_1 showed the highest capacitance and long-term cycle life with the capacitance retention of 82% even after 5000 cycles.

Methods

Preparation of GO and rGO. GO was prepared from natural graphite powder according to the modified Hummer's method⁶². 12 g of graphite powder (SP-1, Bay carbon), 10 g of $K_2S_2O_8$ (Sigma Aldrich, $\geq 99.0\%$), and 10 g of P_2O_5 (Sigma Aldrich, 99.99%) were added to 50 mL of concentrated H_2SO_4 solution and heated to 80°C . The resultant mixture was kept overnight with 2 L of DI water. The mixture was then filtered and washed with DI water several times. The suspension was dried in vacuum under ambient conditions. This pretreated flake-like graphite was mixed with 460 mL of H_2SO_4 at 0°C , and then 60 g of $KMnO_4$ (Sigma Aldrich, $\geq 99.0\%$) was added slowly for further oxidation. The mixture was stirred for 2 h at 35°C and, subsequently, 920 mL of DI water was added. Shortly afterwards, 2.8 L of DI water and 50 mL of 30% H_2O_2 (SAMCHUN pure chemical) were added into the concentrated H_2SO_4 solution. The GO suspension was centrifuged and washed with 5 L of 10% HCl (SAMCHUN pure chemical) solution and, repeatedly, with 5 L of DI water, followed by filtering of the graphite-oxide solution through dialysis (dialysis membrane: Spectrum Laboratories, MWCO-12-14,000) for 2 weeks. Finally, GO sheets were prepared through drying the resulting suspension at 50°C for 3 days. In this work, two kinds of rGO were separately prepared by different methods. The first type of rGO was prepared by pyrolysis of GO in a quartz tube furnace at 1100°C for 2 h under Ar flow⁶³ for comparison purpose with GO used for the synthesis of GNVBs. The other type of rGO was obtained via the hydrothermal route³² and annealed in a vacuum furnace to investigate the characteristics of supercapacitors under the same conditions like those of GNVBs.

Synthesis of graphene decorated V_2O_5 nanobelts composites (GVNBs). Different ratios (3 : 1, 1 : 1, 1 : 3) of pristine V_2O_5 (VO) particles (Aldrich) and of as-synthesized GO were dispersed in 30 mL of DI water and then stirred vigorously for 2 h at room temperature. The obtained yellow/brownish slurry was transferred into a 50 mL Teflon-lined stainless-steel autoclave and maintained at 120°C for 24 h in a muffle furnace. Then, the autoclave was cooled naturally to room temperature inside the muffle furnace. The resulting material was freeze-dried for 72 h to obtain GNVBs with high surface area. The final product was transferred into a vacuum furnace and annealed at 400°C for 2 h under Ar gas in order to improve the crystallinity of the GNVBs.

Materials Characterization. The crystalline structure of the as-prepared samples was characterized using XRD (Bruker D8 Advance with $\text{Cu K}\alpha$ radiation, $\lambda = 1.54178 \text{ \AA}$). The morphologies of the samples were observed by FE-SEM (Nano230, FEI co.). XPS (Thermo Fisher, UK) measurements were performed with monochromatic Al $\text{K}\alpha$ radiation as X-ray source for the investigation of the surface states. To gain further insight into the structure of the products, they were additionally investigated by Raman spectroscopy (Alpha 300S, WITec) using a He-Ne laser with 532 nm in wavelength. The thickness of a single GNVB on SiO_2 substrate was measured using AFM (Multimode V, Veeco). BF-TEM, electron diffraction pattern, and EELS were

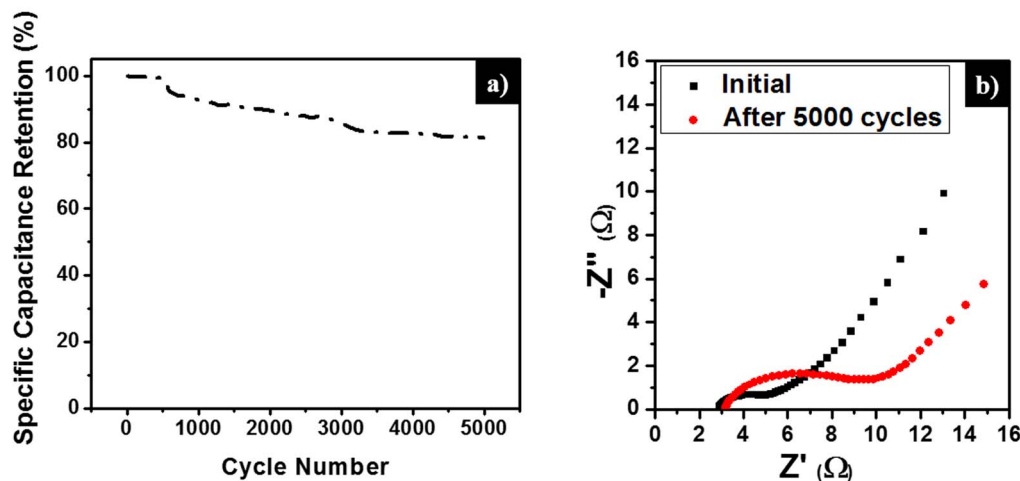


Figure 7 | (a) Specific capacitance retention of the V_3G_1 electrode as a function of cycle number, measured by CV at a scan rate of 200 mV s^{-1} in 1 M Na_2SO_4 solution. (b) EIS analysis of the V_3G_1 electrode at the initial stage and after 5000 cycles.



performed with an image-side aberration-corrected TEM (Titan3 G2 60-300, FEI) which was operated at 80 kV. High-angle annular dark field (HAADF) scanning transmission electron microscopy (STEM) was carried out using a probe-side aberration-corrected TEM (JEOL 2100F, JEOL) operated at 200 kV.

Electrochemical Characterization. Electrochemical experiments were carried out in the typical three-electrode-cell setup using a potentiostat/galvanostat (Biologic/VSP) at room temperature. The working-electrode paste was prepared by mixing the corresponding electro-active materials (rGO , V_2O_5 , V_1G_3 , V_1G_1 , and V_3G_1), conducting acetylene black, and a polymeric binder (polyvinylidene difluoride) in the mass ratio of 80:10:10 and ground in a mortar using an N-methyl pyrrolidone (NMP) solvent. The paste was then coated on nickel-foam substrate (mass loading ~ 3.5 mg/cm²) using the spatula and then dried at 120 °C for 12 h in a vacuum oven. A large surface area platinum mesh was used as counter electrode, Ag/AgCl (std. KCl) was used as reference electrode, and 1 M Na₂SO₄ solution was used as electrolyte. Cyclic voltammograms (CV) were obtained at various scan rates (5, 10, 25, 50, 75, 100, 125 mV s⁻¹) in the potential window of 0 to 0.8 V (Vs Ag/AgCl [std. KCl]). Electrochemical impedance spectroscopy (EIS) measurements were carried out over the frequency range of 0.1 Hz to 100 kHz with the AC amplitude of 10 mV. Galvanostatic charge/discharge curves were recorded at different current densities (0.25, 0.5, 0.75, 1 A g⁻¹) in the potential window of 0 to 0.8 V (Vs Ag/AgCl [std. KCl]).

- Wang, H. & Dai, H. Strongly coupled inorganic-nano-carbon hybrid materials for energy storage. *Chem. Soc. Rev.* **42**, 3088–3113 (2013).
- Ellis, B. L., Knauth, P. & Djenizian, T. Three-dimensional self-supported metal oxides for advanced energy storage. *Adv. Mater.* **26**, 3368–3397 (2014).
- Geim, A. K. Graphene: Status and prospects. *Science* **324**, 1530–1534 (2009).
- Geim, A. K. & Novoselov, K. S. The rise of graphene. *Nat. Mater.* **6**, 183–191 (2007).
- Yan, J., Wang, Q., Wei, T. & Fan, Z. Recent advances in design and fabrication of electrochemical supercapacitors with high energy densities. *Adv. Energy Mater.* **4** (2014).
- Wang, W. Y., Takahashi, K., Lee, K. & Cao, G. Nanostructured vanadium oxide electrodes for enhanced lithium-ion intercalation. *Adv. Funct. Mater.* **16**, 1133–1144 (2006).
- Wang, Y. & Cao, G. Developments in nanostructured cathode materials for high-performance lithium-ion batteries. *Adv. Mater.* **20**, 2251–2269 (2008).
- Cao, A. M., Hu, J. S., Liang, H. P. & Wan, L. J. Self-assembled vanadium pentoxide (V₂O₅) hollow microspheres from nanorods and their application in lithium-ion batteries. *Angew. Chem. Int. Ed.* **44**, 4391–4395 (2005).
- Liu, J., Xia, H., Xue, D. & Lu, L. Double-shelled nanocapsules of V₂O₅-based composites as high-performance anode and cathode materials for Li ion batteries. *J. Am. Chem. Soc.* **131**, 12086–12087 (2009).
- Dexmer, J. et al. Vanadium oxide-PANI nanocomposite-based macroscopic fibers: 1D alcohol sensors bearing enhanced toughness. *Chem. Mater.* **20**, 5541–5549 (2008).
- Kim, G. T. et al. Field-effect transistor made of individual V₂O₅ nanofibers. *Appl. Phys. Lett.* **76**, 1875–1877 (2000).
- Wee, G., Soh, H. Z., Cheah, Y. L., Mhaisalkar, S. G. & Srinivasan, M. Synthesis and electrochemical properties of electrospun V₂O₅ nanofibers as supercapacitor electrodes. *J. Mater. Chem.* **20**, 6720–6725 (2010).
- Aricò, A. S., Bruce, P., Scrosati, B., Tarascon, J. M. & Van Schalkwijk, W. Nanostructured materials for advanced energy conversion and storage devices. *Nat. Mater.* **4**, 366–377 (2005).
- Bruce, P. G., Scrosati, B. & Tarascon, J. M. Nanomaterials for rechargeable lithium batteries. *Angew. Chem. Int. Ed.* **47**, 2930–2946 (2008).
- Lee, J. W. et al. Extremely stable cycling of ultra-thin V₂O₅ nanowire-graphene electrodes for lithium rechargeable battery cathodes. *Energy Environ. Sci.* **5**, 9889–9894 (2012).
- Sathiyaraj, M., Prakash, A. S., Ramesha, K., Tarascon, J. M. & Shukla, A. K. V₂O₅-anchored carbon nanotubes for enhanced electrochemical energy storage. *J. Am. Chem. Soc.* **133**, 16291–16299 (2011).
- Perera, S. D. et al. Vanadium oxide nanowire-carbon nanotube binder-free flexible electrodes for supercapacitors. *Adv. Energy Mater.* **1**, 936–945 (2011).
- Wang, Y. & Cao, G. Synthesis and enhanced intercalation properties of nanostructured vanadium oxides. *Chem. Mater.* **18**, 2787–2804 (2006).
- Fu, M. et al. Graphene/vanadium oxide nanotubes composite as electrode material for electrochemical capacitors. *Physica B* **421**, 77–82 (2013).
- Zhao, H., Pan, L., Xing, S., Luo, J. & Xu, J. Vanadium oxides/reduced graphene oxide composite for lithium-ion batteries and supercapacitors with improved electrochemical performance. *J. Power Sources* **222**, 21–31 (2013).
- Perera, S. D. et al. Vanadium oxide nanowire-Graphene binder free nanocomposite paper electrodes for supercapacitors: A facile green approach. *J. Power Sources* **230**, 130–137 (2013).
- Stankovich, S. et al. Synthesis of graphene-based nanosheets via chemical reduction of exfoliated graphite oxide. *Carbon* **45**, 1558–1565 (2007).
- Li, D., Müller, M. B., Gilje, S., Kaner, R. B. & Wallace, G. G. Processable aqueous dispersions of graphene nanosheets. *Nat. Nanotechnol.* **3**, 101–105 (2008).
- Shin, H. J. et al. Efficient reduction of graphite oxide by sodium borohydride and its effect on electrical conductance. *Adv. Funct. Mater.* **19**, 1987–1992 (2009).
- Becerril, H. A. et al. Evaluation of solution-processed reduced graphene oxide films as transparent conductors. *ACS Nano* **2**, 463–470 (2008).
- Lee, M. et al. Graphene oxide assisted spontaneous growth of V₂O₅ nanowires at room temperature. *Nanoscale* **6**, 11066–11071 (2014).
- Yu, J., Yu, J. C., Ho, W., Wu, L. & Wang, X. A Simple and General Method for the Synthesis of Multicomponent Na₂V₆O₁₆·3H₂O Single-Crystal Nanobelts. *J. Am. Chem. Soc.* **126**, 3422–3423 (2004).
- Avansi Jr, W., Ribeiro, C., Leite, E. R. & Mastelaro, V. R. Vanadium pentoxide nanostructures: An effective control of morphology and crystal structure in hydrothermal conditions. *Cryst. Growth Des.* **9**, 3626–3631 (2009).
- Xiong, C., Aliev, A. E., Gnade, B. & Balkus Jr, K. J. Fabrication of silver vanadium oxide and V₂O₅ nanowires for electrochromics. *ACS Nano* **2**, 293–301 (2008).
- Kim, B. H. et al. Hydrogen spillover in Pd-doped V₂O₅ nanowires at room temperature. *Chem. Asian J.* **7**, 684–687 (2012).
- Kim, B. H. et al. Investigation on the existence of optimum interlayer distance for H₂ uptake using pillared-graphene oxide. *Int. J. Hydrogen Energy* **37**, 14217–14222 (2012).
- Zhou, Y., Bao, Q., Tang, L. A. L., Zhong, Y. & Loh, K. P. Hydrothermal dehydration for the “green” reduction of exfoliated graphene oxide to graphene and demonstration of tunable optical limiting properties. *Chem. Mater.* **21**, 2950–2956 (2009).
- Dreyer, D. R., Park, S., Bielawski, C. W. & Ruoff, R. S. The chemistry of graphene oxide. *Chem. Soc. Rev.* **39**, 228–240 (2010).
- Nethravathi, C. & Rajamathi, M. Chemically modified graphene sheets produced by the solvothermal reduction of colloidal dispersions of graphite oxide. *Carbon* **46**, 1994–1998 (2008).
- Hong, W. G. et al. Agent-free synthesis of graphene oxide/transition metal oxide composites and its application for hydrogen storage. *Int. J. Hydrogen Energy* **37**, 7594–7599 (2012).
- Rout, C. S. et al. Synthesis and characterization of patronite form of vanadium sulfide on graphitic layer. *J. Am. Chem. Soc.* **135**, 8720–8725 (2013).
- Nam, I., Kim, N. D., Kim, G. P., Park, J. & Yi, J. One step preparation of Mn₃O₄/graphene composites for use as an anode in Li ion batteries. *J. Power Sources* **244**, 56–62 (2013).
- Petkov, V. et al. Structure of V₂O₅·nH₂O xerogel solved by the atomic pair distribution function technique. *J. Am. Chem. Soc.* **124**, 10157–10162 (2002).
- Fang, W. C. Synthesis and electrochemical characterization of vanadium oxide/carbon nanotube composites for supercapacitors. *J. Phys. Chem. C* **112**, 11552–11555 (2008).
- Yan, B. et al. Single-crystalline v₂O₅ ultralong nanoribbon waveguides. *Adv. Mater.* **21**, 2436–2440 (2009).
- Baddour-Hadjean, R., Pereira-Ramos, J. P., Navone, C. & Smirnov, M. Raman microspectrometry study of electrochemical lithium intercalation into sputtered crystalline v₂O₅ thin films. *Chem. Mater.* **20**, 1916–1923 (2008).
- Tsukamoto, T., Yamazaki, K., Komurasaki, H. & Ogino, T. Effects of surface chemistry of substrates on Raman spectra in graphene. *J. Phys. Chem. C* **116**, 4732–4737 (2012).
- Das, A., Chakraborty, B. & Sood, A. K. Raman spectroscopy of graphene on different substrates and influence of defects. *Bull. of Mater. Sci.* **31**, 579–584 (2008).
- Liu, H. & Yang, W. Ultralong single crystalline V₂O₅ nanowire/graphene composite fabricated by a facile green approach and its lithium storage behavior. *Energy Environ. Sci.* **4**, 4000–4008 (2011).
- Ren, X., Jiang, Y., Zhang, P., Liu, J. & Zhang, Q. Preparation and electrochemical properties of V₂O₅ submicron-belts synthesized by a sol-gel H₂O₂ route. *J. Sol-Gel Sci. Technol.* **51**, 133–138 (2009).
- Zhou, F., Zhao, X., Yuan, C., Li, L. & Xu, H. Low-temperature hydrothermal synthesis of orthorhombic vanadium pentoxide nanowires. *Chem. Lett.* **36**, 310–311 (2007).
- Zhou, F., Zhao, X., Liu, Y., Yuan, C. & Li, L. Synthesis of millimeter-range orthorhombic V₂O₅ nanowires and impact of thermodynamic and kinetic properties of the oxidant on the synthetic process. *Eur. J. Inorg. Chem.* **16**, 2506–2509 (2008).
- Livage, J. Vanadium pentoxide gels. *Chem. Mater.* **3**, 578–593 (1991).
- Li, M., Kong, F., Wang, H. & Li, G. Synthesis of vanadium pentoxide (V₂O₅) ultralong nanobelts via an oriented attachment growth mechanism. *CrystEngComm* **13**, 5317–5320 (2011).
- Xu, L. et al. Spontaneous redox synthesis of Prussian blue/graphene nanocomposite as a non-precious metal catalyst for efficient four-electron oxygen reduction in acidic medium. *J. Power Sources* **240**, 101–108 (2013).
- Perera, S. D. et al. Vanadium oxide nanowire – Graphene binder free nanocomposite paper electrodes for supercapacitors: A facile green approach. *J. Power Sources* **230**, 130–137 (2013).
- Bonso, J. S. et al. Exfoliated graphite nanoplatelets–V₂O₅ nanotube composite electrodes for supercapacitors. *J. Power Sources* **203**, 227–232 (2012).
- Ramadoss, A. & Kim, S. J. Improved activity of a graphene–TiO₂ hybrid electrode in an electrochemical supercapacitor. *Carbon* **63**, 434–445 (2013).
- Ramadoss, A., Kim, G.-S. & Kim, S. J. Fabrication of reduced graphene oxide/TiO₂ nanorod/reduced graphene oxide hybrid nanostructures as electrode materials for supercapacitor applications. *CrystEngComm* **15**, 10222–10229 (2013).



55. Yang, S. *et al.* Bottom-up Approach toward Single-Crystalline VO₂-Graphene Ribbons as Cathodes for Ultrafast Lithium Storage. *Nano Lett.* **13**, 1596–1601 (2013).
56. Zhao, H., Pan, L., Xing, S., Luo, J. & Xu, J. Vanadium oxides–reduced graphene oxide composite for lithium-ion batteries and supercapacitors with improved electrochemical performance. *J. Power Sources* **222**, 21–31 (2013).
57. Qu, Q., Zhu, Y., Gao, X. & Wu, Y. Core–Shell Structure of Polypyrrole Grown on V₂O₅ Nanoribbon as High Performance Anode Material for Supercapacitors. *Adv. Energy Mater.* **2**, 950–955 (2012).
58. Liu, W.-w., Yan, X.-b. & Xue, Q.-j. Multilayer hybrid films consisting of alternating graphene and titanium dioxide for high-performance supercapacitors. *J. Mater. Chem. C* **1**, 1413–1422 (2013).
59. Reddy, R. N. & Reddy, R. G. Porous structured vanadium oxide electrode material for electrochemical capacitors. *J. Power Sources* **156**, 700–704 (2006).
60. Yan, J. *et al.* Rapid microwave-assisted synthesis of graphene nanosheet/Co₃O₄ composite for supercapacitors. *Electrochim. Acta* **55**, 6973–6978 (2010).
61. Yan, J. *et al.* Fast and reversible surface redox reaction of graphene–MnO₂ composites as supercapacitor electrodes. *Carbon* **48**, 3825–3833 (2010).
62. Tung, V. C., Allen, M. J., Yang, Y. & Kaner, R. B. High-throughput solution processing of large-scale graphene. *Nat. Nanotechnol.* **4**, 25–29 (2009).
63. Wang, X., Zhi, L. & Müllen, K. Transparent, conductive graphene electrodes for dye-sensitized solar cells. *Nano Lett.* **8**, 323–327 (2008).

Acknowledgments

This research was supported by the National Research Foundation of Korea (NRF) funded by the Korean government, MSIP (2013R1A1A2059244). B.H.K. and H.-B.-R. L. were supported by the Incheon National University Research Grant in 20141308. We would like

to thank Mr. R. Ananthakumar, Jeju National University, Republic of Korea for the assistance of specific capacitance calculations.

Author contributions

M.L. and S.K.B. designed the study, performed experiments, collected and analysed data, and wrote the paper. H.Y.J. performed and analysed the TEM study. W.G.H. provided graphene oxide and analysed the data. H.-B.-R.L. performed electrical measurement and analysed data. B.H.K. and Y.J. supervised the study and wrote the paper. All authors discussed the results and commented on the manuscript.

Additional information

Supplementary information accompanies this paper at <http://www.nature.com/scientificreports>

Competing financial interests: The authors declare no competing financial interests.

How to cite this article: Lee, M. *et al.* One-step hydrothermal synthesis of graphene decorated V₂O₅ nanobelts for enhanced electrochemical energy storage. *Sci. Rep.* **5**, 8151; DOI:10.1038/srep08151 (2015).



This work is licensed under a Creative Commons Attribution-NonCommercial-ShareAlike 4.0 International License. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in the credit line; if the material is not included under the Creative Commons license, users will need to obtain permission from the license holder in order to reproduce the material. To view a copy of this license, visit <http://creativecommons.org/licenses/by-nc-sa/4.0/>