



International Congress of Science and Technology of Metallurgy and Materials, SAM - CONAMET 2013

## Combustion syntheses of $\text{Co}_3\text{O}_4$ powders using different fuels

María Celeste Gardey Merino<sup>a\*</sup>, Leonardo D. Tornello Nasisi<sup>a</sup>, William M. Montoya<sup>a</sup>,  
Jesús N. Urrutia Aguilera<sup>a</sup>, M. Emilia Fernandez de Rapp<sup>b</sup>, Gustavo E. Lascalea<sup>d</sup> and  
Patricia G. Vázquez<sup>e</sup>

<sup>a</sup> Grupo CLIOPE, Universidad Tecnológica Nacional - Facultad Regional Mendoza, Rodríguez 273, Mendoza-5500, Argentina.

<sup>b</sup> Centro de Investigaciones en Sólidos (CINSO) CITEDEF – CONICET, J.B. de La Salle 4397, Villa Martelli, Prov. de Buenos Aires (B1603ALO), Argentina.

<sup>c</sup> Laboratorio de Investigaciones y Servicios Ambientales Mendoza (LISAMEN) - CCT CONICET– Mendoza, Av. Ruíz Leal s/n. Parque General San Martín, Mendoza-5500, Argentina.

<sup>d</sup> Centro de Investigación y Desarrollo en Ciencias Aplicadas "Dr. Jorge J. Ronco" (CINDECA) CCT CONICET – La Plata, Universidad Nacional de La Plata, Calle 47 N° 257 La Plata-1900, Buenos Aires, Correo Electrónico (autor de contacto): [mccgardey@frm.utn.edu.ar](mailto:mccgardey@frm.utn.edu.ar)

---

### Abstract

$\text{Co}_3\text{O}_4$  powders are used as pigment in solar selective paints. In this work, two new gel-combustion processes for the synthesis of  $\text{Co}_3\text{O}_4$  nanopowders with lysine (Lys) or ethylenediaminetetraacetic acid (Edta) as fuel are presented. The first route is a conventional, stoichiometric process, while the second one is a non-stoichiometric, pH-controlled process. The samples were calcined in air at 500 °C. They were characterized by X-ray diffraction (XRD), scanning electron microscopy (SEM), transmission electron microscopy (TEM), Fourier transform infrared spectrum (FTIR), Thermogravimetric analysis (TGA) and differential scanning calorimetry (DSC) and the optical properties of the pigments were assessed with a spectrophotometer. In all cases, powders exhibited the  $\text{Co}_3\text{O}_4$  crystalline structure. A minimum crystallite average size of 19 nm for powders obtained by the “stoichiometric/Lys” combustion route was observed, meanwhile, a maximum value of 47 nm was stated for powders obtained by the “non-stoichiometric/Edta” combustion process. The average particle size ranged between 50 and 100 nm. The powders obtained by the stoichiometric nitrate–lysine route were selected to study its optical properties, their solar absorption was 88%, compared with the references, evidencing their aptitude to be used in solar absorbent paints.

**Keywords:** combustion synthesis,  $\text{Co}_3\text{O}_4$ , selective painting, pigments.

---

\* Corresponding author. Tel.: +54-261-524-3001; fax: +54-261-524-4531  
E-mail address: [mccgardey@frm.utn.edu.ar](mailto:mccgardey@frm.utn.edu.ar)

## 1. Introduction

The oxides of transition metals (Co, Mn, Fe, Cr), for example  $\text{Co}_3\text{O}_4$ , present a high absorption in the solar spectrum by the existence of numerous, allowed, electronic transitions between their “d” orbitals partially full (Vince et al., 2000). The cobalt pigments are of paramount importance in ceramic industry due their spectacular variety of colours, high tinting strength and remarkable stability under chemical, thermal and reducing conditions (Mimani and Ghosh, 2000). Thus, cobalt oxides are used in absorbent paints to solar collector between other applications like gas-sensing, catalysis and anode material in Li-ion rechargeable batteries (Yang et al., 2010).  $\text{Co}_3\text{O}_4$  has been obtained by different methods as, precipitation (Pal and Chauhan, 2010), sol-gel (Luisetto et al., 2008), spray-pyrolysis (Avila et al., 2004), hydrothermal synthesis (Gui et al., 2012). Other methods like, reflux (Ozkaya et al., 2009), macanochemical (Yang et al., 2004), ultrasound assisted (Askarinejad and Morsali, 2009), on biotemplates (Yang et al., 2010) and chemical vapor deposition (CVD) (Barreca et al., 2011) using organic complexes (Thangavelu et al., 2011) and by gel-combustion synthesis (Venkateswara and Sunandana, 2008- Toniolo et al., 2010) were also viable.

In particular, in gel-combustion synthesis of  $\text{Co}_3\text{O}_4$ , it has been studied the influence of fuel-oxidant ratio and fuel types on powders properties. For example in studies of combustion syntheses using urea as fuel, it was achieved an optimized fuel-oxidant ratio which allowed a smallest average crystallite size of 6 nm (Venkateswara and Sunandana, 2008). On the other hand, both the influences of type of fuels and fuel-oxidant ratio were studied in  $\text{Co}_3\text{O}_4$  powders obtained by combustion syntheses using urea and glycine as fuels, in these studies the smaller average size of crystallite was 23 nm and the largest specific surface area was  $36\text{m}^2/\text{g}$  using glycine as fuel.

In this work, two new gel-combustion routes for the synthesis of  $\text{Co}_3\text{O}_4$  nanopowders with lysine (Lys) or ethylenediaminetetraacetic acid (Edta) as fuels are presented. The first route is a conventional stoichiometric process, while the second one is a non-stoichiometric, pH-controlled process. The samples were calcined in air at  $500\text{ }^\circ\text{C}$ . They were characterized by X-ray diffraction (XRD), scanning electron microscopy (SEM), transmission electron microscopy (TEM), Fourier transform infrared spectrum (FTIR), Thermogravimetric analysis (TGA) and differential scanning calorimetry (DSC), and the optical properties of the pigments were assessed with a spectrophotometer.

The objective of this work is to establish the influence of the type of fuel and the synthesis route on the final properties of obtained powders like crystalline structure, average crystallite size and shape and size of particle, and to verify the aptitude of powders to be used for solar selective paints.

## 2. Experimental Procedure

$\text{Co}_3\text{O}_4$  nanopowders were obtained by gel-combustion process for the synthesis using Lys ( $\text{C}_6\text{H}_{14}\text{N}_2\text{O}_2$ ) or Edta ( $\text{C}_{10}\text{H}_{16}\text{N}_2\text{O}_8$ ) as fuels. The first one is a conventional stoichiometric process, while the second one is a non-stoichiometric, pH-controlled process. All the chemical routes were performed using reagents of analytical grade. The final calcination temperatures were at  $500\text{ }^\circ\text{C}$  during 2 h.

### 2.1. Stoichiometric processes

#### Stoichiometric nitrate–lysine route

5g of  $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  (Aldrich) and 0.83g of Lys ( $\text{C}_6\text{H}_{14}\text{N}_2\text{O}_2$ , Aldrich) were dissolved in distilled water to obtain a homogeneous solution, with a total volume of 250 ml (pH 3). The Lys/Co molar ratio chosen was 9/34 (0.26) as calculated on the basis of the following stoichiometric reaction of combustion:



This precursor solution was concentrated on a hot plate at  $250\text{ }^\circ\text{C}$  until a viscous gel was obtained. Soon after, it ignited and the combustion process proceeded without flame. These powders were named  $\text{Co}_3\text{O}_4\text{-S-Lys}$ .

#### Stoichiometric nitrate–Edta route:

The same procedure was used, starting from the same mass of 5g of  $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ , but in this case the stoichiometric reaction requires an Edta/Co molar ratio of 9/40 (0.22), based on the following, stoichiometric reaction of combustion:



These powders were named  $\text{Co}_3\text{O}_4$ -S-Edta.

## 2.2. Non-stoichiometric, pH-controlled process

### Non-stoichiometric pH-controlled nitrate–lysine route

A first solution was prepared from 5g of  $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$  (Aldrich), 10 ml of  $\text{HNO}_3$  (concentrated) and an amount of distilled water sufficient to reach a volume of 100 mL. This solution was concentrated until a small volume in a hot plate to reduce the amount of nitrates, and then distilled water was added again to obtain 100 mL of solution. A second solution was prepared by dissolving 4.15 g of Lys in distilled water. Then, both solutions were carefully mixed, resulting the homogeneous mixture with a Lys/Co molar ratio of 1.32. This ratio was chosen based on the “oxidative valence criterion”, taking into account previous studies of similar processes, where the optimum ratio for a pH controlled nitrate–glycine route to synthesize  $\text{ZrO}_2$ – $\text{CeO}_2$  solid solutions was found to be 5 (Jain et al., 1981–Lascalea 2004). Then,  $\text{NH}_4\text{OH}$  (diluted 1:1, Merck) was added to obtain a precursor solution with pH 8. This solution was then concentrated on a hot plate at 250 °C until it turned into a viscous gel, which finally burned with flames due to the desired, exothermic reaction of combustion. These powders were named  $\text{Co}_3\text{O}_4$ -NS-Lys.

### Non-stoichiometric pH-controlled nitrate–Edta route:

The same procedure was used, starting from the same mass of 5g of  $\text{Co}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ , but in this case also based on of above-mentioned criterion, the Edta /Co molar ratio resulted of 1.12. These powders were named  $\text{Co}_3\text{O}_4$ -NS-Edta.

## 2.3. Materials characterization

The phases present in the as-synthesized  $\text{Co}_3\text{O}_4$  nanopowders (obtained after calcination) were identified by X-ray diffraction (XRD) using a Philips PW 3710 diffractometer operated with  $\text{Cu-K}\alpha$  radiation. Our data were compared with those reported in the Inorganic Crystal Structure Database (ICSD). The average crystallite size was determined from the broadening of Bragg peaks using the Scherrer equation (Klug and L. Alexander, 1974).

The morphology of the powders was analyzed by scanning electron microscopy (SEM, Philips 505 microscope) and transmission electron microscopy (TEM, JEOL 100 CX II microscope). The operation voltage was 100kV. In both cases, the preparation of samples was performed following conventional procedures.

Fourier transform infrared spectrum (FTIR) of powders was obtained with a Bruker IFS 66 equipment. TGA (Thermogravimetric Analysis) was carried out with a detector SHIMADZU TGA-51 type at a rate of 20°C/min, between environmental temperature and 600 °C, in air, with a platinum cell. DSC (Differential Scanning Calorimetry) was carried out with a detector SHIMADZU DSC-50 type at a rate of 20°C/min, between environmental temperature and 600°C in air, with an aluminium cell.

The optical characteristics, transmission and reflection of samples in the solar spectrum, were studied with a spectrophotometer of double beam SHIMADZU, model UV-3101PC with integration sphere model 3100. From this measures it was calculated the solar absorptance ( $\alpha_s$ ). The studied pigments were placed in a basin of quartz.

### 3. Results and discussion

In agreement with the XRD pattern of Fig. 1, a spinel crystal structure of  $\text{Co}_3\text{O}_4$  corresponding to database ICSD N° 36256, was obtained in all obtained powders. The average crystallite sizes calculated by Scherrer's equation are informed in Table 1, evidencing that a minimum crystallite average size of 19 nm was observed for powders obtained by the “stoichiometric/Lys” combustion route, meanwhile, a maximum value of 47 nm was stated for powders obtained by the “non-stoichiometric /Edta” combustion process. Additionally powders, obtained by stoichiometric routes, had lower average crystallite sizes than those obtained by non-stoichiometric processes, since similar tendencies are observed in  $\text{Co}_3\text{O}_4$  powders synthesized by combustion syntheses using glycine and urea as fuels (Toniolo et al., 2010) and in  $\text{Ce}_{0.9}\text{Zr}_{0.1}\text{O}_2$  powders obtained by gel-combustion methods using different fuels (M.G. Zimicz et al., 2011). The influence of the type of fuel is, then, evident over the observed crystallite average size, being lowest these powders obtained by Lys routes.

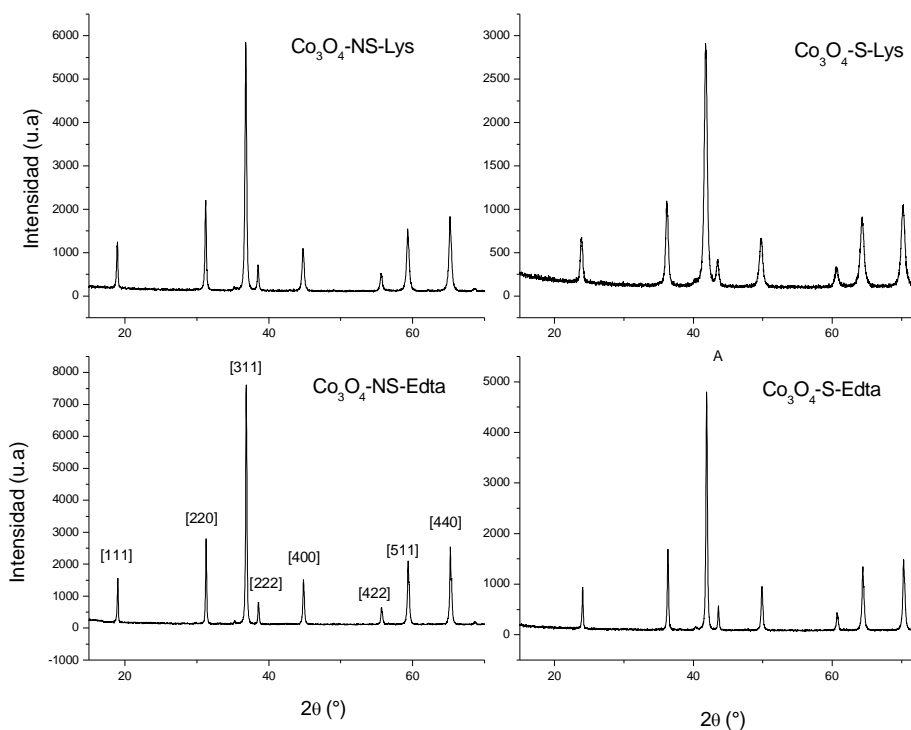



Fig. 1. XRD patterns of  $\text{Co}_3\text{O}_4$  obtained nanopowders.

Specific surface areas of obtained  $\text{Co}_3\text{O}_4$  powders are exhibit in Table 1, the higher area corresponding to  $\text{Co}_3\text{O}_4$ -NS-Edta powders. Additionally the specific surface area of powders obtained using Edta as a fuel is higher than the observed from powders obtained with the same route employing lysine as fuel.

Table 1. Average crystallite sizes and BET specific surface areas of obtained  $\text{Co}_3\text{O}_4$  nanopowders.

Route	Average crystallite size (nm)	BET specific surface area ( $\text{m}^2/\text{g}$ )
$\text{Co}_3\text{O}_4$ -S-Lys	19	13
$\text{Co}_3\text{O}_4$ -NS-Lys	38	8
$\text{Co}_3\text{O}_4$ -S-Edta	43	23
$\text{Co}_3\text{O}_4$ -NS-Edta	47	29

By SEM, it was observed that all samples exhibited a high degree of agglomeration, as is shown in Fig. 2. In particular, for powders obtained by non-stoichiometric routes, structures more compact are observed. A similar agglomeration is evidenced in  $\text{Co}_3\text{O}_4$  powders synthesized by combustion synthesis using glycine and urea as fuels (Venkateswara and Sunandana, 2008).

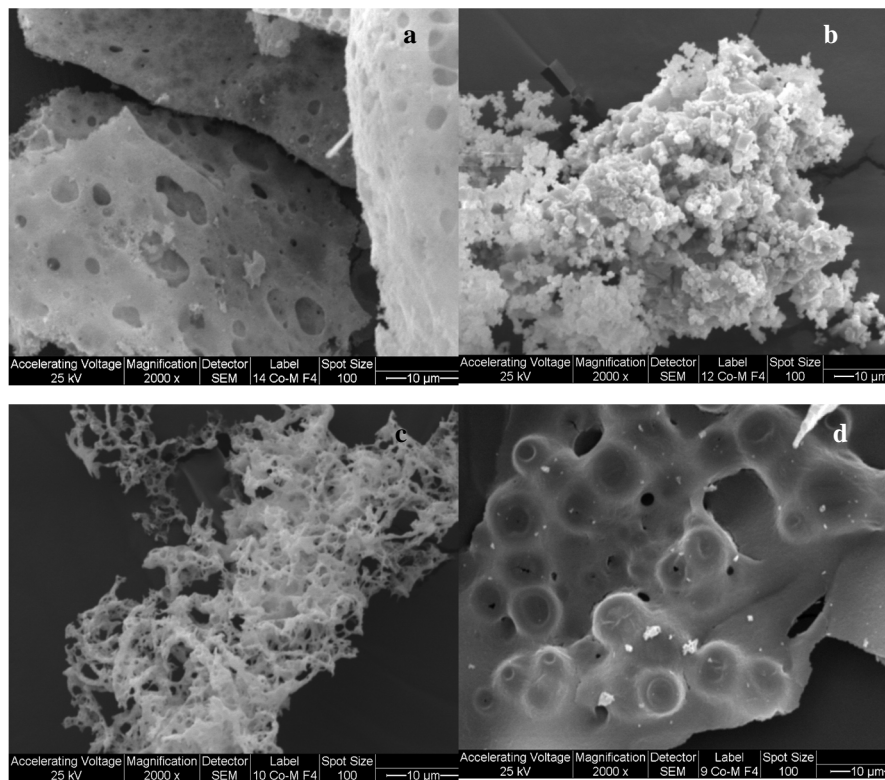Fig 2. SEM micrographs of: a)  $\text{Co}_3\text{O}_4$ -S-Lys, b)  $\text{Co}_3\text{O}_4$ -NS-Lys, c)  $\text{Co}_3\text{O}_4$ -S-Edta and d)  $\text{Co}_3\text{O}_4$ -NS-Edta.

As can be estimated through TEM observations, the agglomerated particle size ranges between 50 and 100 nm, as shown in Fig. 3, where are displayed TEM micrographs of all obtained powders. A polyhedral shape of crystallites is evidenced as well, with an octahedral shape more frequently observed. The same shape was observed in  $\text{Co}_3\text{O}_4$  particles obtained by precipitation methods too (Tang and Hao, 2008).

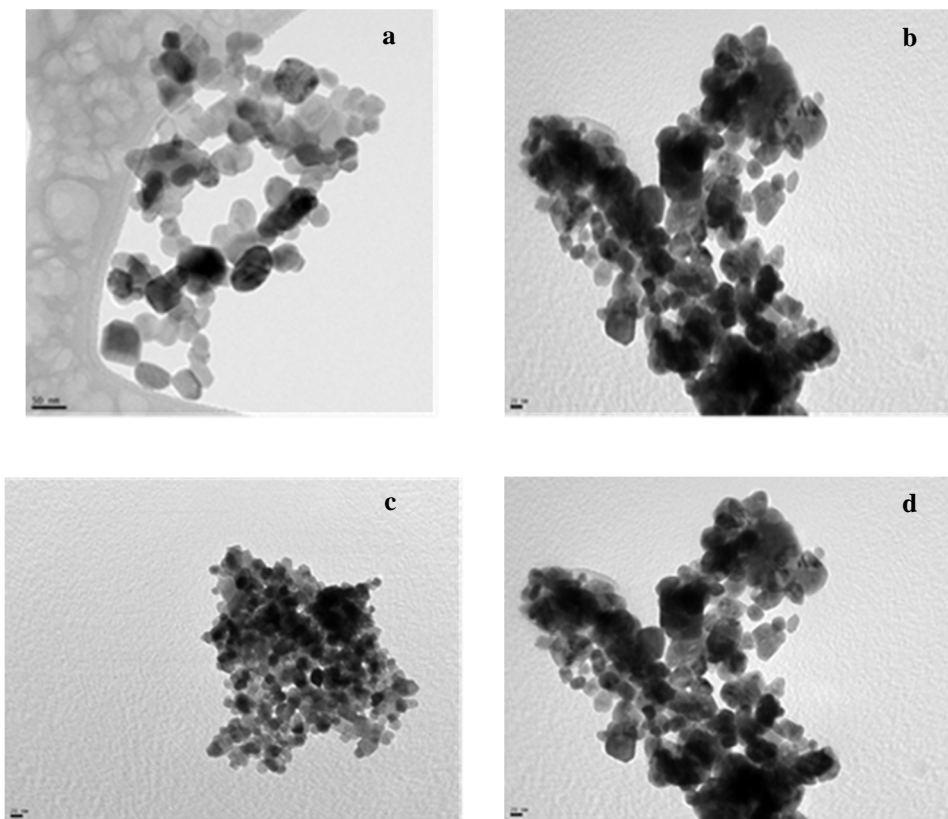
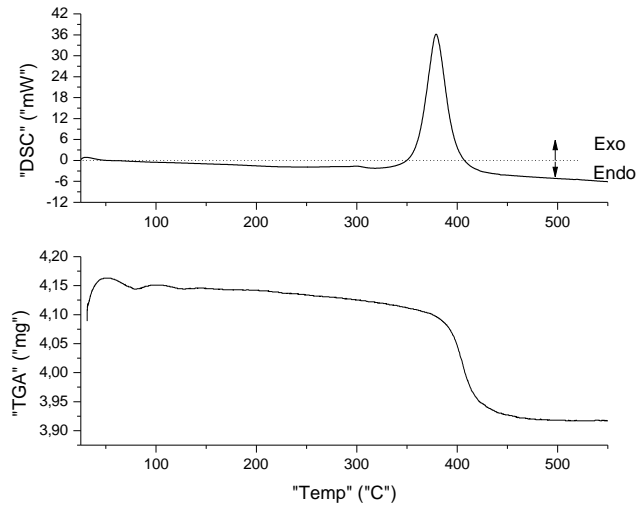
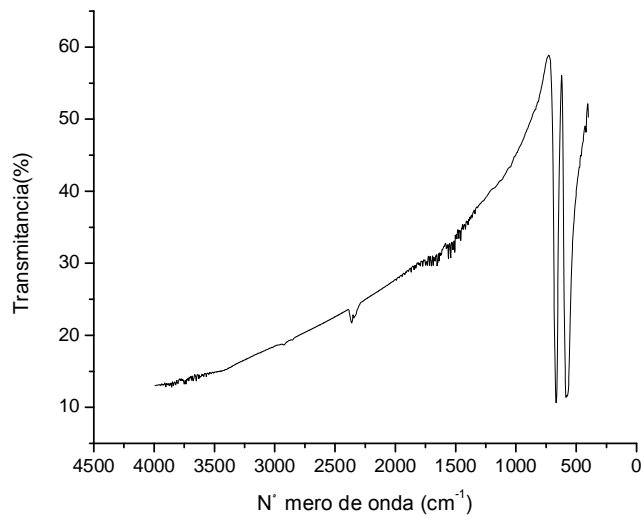


Fig 3. TEM micrographs of: a)  $\text{Co}_3\text{O}_4\text{-S-Lys}$ , b)  $\text{Co}_3\text{O}_4\text{-NS-Lys}$ , c)  $\text{Co}_3\text{O}_4\text{-S-Edta}$  and d)  $\text{Co}_3\text{O}_4\text{-NS-Edta}$ .

DSC and TGA plots corresponding to  $\text{Co}_3\text{O}_4\text{-NS-Edta}$  can be observed in Fig. 4. At  $400^\circ\text{C}$  an exothermic transformation with a release of energy of 36 mW was observed. Additionally a loose of weight of 0.05 mg was produced at the same temperature. Both changes could be related with a phase change from the CoO phase to  $\text{Co}_3\text{O}_4$  phase according to the phases found by Toniolo et al. (2010), like Co, CoO and  $\text{Co}_3\text{O}_4$ , in ashes collected after a combustion synthesis of cobalt oxides.

FT-IR were carried out on samples of all the obtained powders, all resulting spectra were identical to the one plotted in Fig. 5. The IR spectra evidenced two distinct and sharp bands at  $622(\nu_1)$  and  $727(\nu_2)$   $\text{cm}^{-1}$ , which originate from the stretching vibrational modes of the metal–oxygen bond and confirming the formation of a  $\text{Co}_3\text{O}_4$  spinel oxide. The  $\nu_1$  band is characteristic of  $\text{Co}^{3+}$  vibration in octahedral sites of the spinel, and  $\nu_2$  band is attributable to  $\text{Co}^{2+}$  vibration in tetrahedral ones (Gui et al., 2012). Similar bands corresponding to  $\nu_1$  y  $\nu_2$  are observed in cobalt oxides synthetized by microwave methods (Al-Tuwirqi, 2011).

Fig 4. DSC y TGA plots of  $\text{Co}_3\text{O}_4\text{-EC-Edta}$ .Fig. 5. FT-IR Spectrum of  $\text{Co}_3\text{O}_4\text{-NS-Lys}$ .

Among the four nanopowders obtained, the  $\text{Co}_3\text{O}_4\text{-S-Lys}$  ones were selected to study their optical properties with a spectrophotometer, because the observed efficiency of their synthesis was the best, stated in terms of the mass of produced pigment. The objective of this study was to verify their optical properties before the fabrication of the solar paints. The resulting solar absorption was 88 %. These results evidence their aptitude to be used in solar absorbent paints because the absorption is just in the range of 88-94%, usually acceptable for generic solar selective paints made with pigments of  $\text{Co}_3\text{O}_4$  (Van Buskirk, 1982).

## 4. Conclusion

In this work, two new gel-combustion processes for the synthesis of  $\text{Co}_3\text{O}_4$  nanopowders, with lysine (Lys) or ethylenediaminetetraacetic acid (Edta) as fuel are presented. The first type of route is a conventional, stoichiometric process, while the second one is a non-stoichiometric, pH-controlled process. A spinel crystal structure of  $\text{Co}_3\text{O}_4$  was observed in all obtained powders. A minimum crystallite average size of 19 nm for powders obtained by the “stoichiometric/Lys” combustion route was observed, meanwhile, a maximum value of 47 nm was stated for powders obtained by the “non-stoichiometric /Edta” combustion process. Additionally, that powders obtained by stoichiometric routes yield lower average crystallite sizes than the obtained by non-stoichiometric processes was confirmed as a rule in this material. The influence of the type of fuel is evidenced on crystallite average size, being the lowest values observed on powders obtained by means of the Lys routes. By TEM the size particle of agglomerates was evaluated ranging 50-100 nm, being the crystallites polyhedrically shaped as observed. The nanopowders obtained by stoichiometric nitrate–lysine (the process with the best yield) were selected to study optical properties. Their solar absorption was 88% evidencing their aptitude to be used in solar absorbent paints, as compared with other related pigments described in literature.

## Acknowledgements

The authors wish to thank Eng. Edgardo Soto and Lic. María E. Canafoglia for their experimental contribution in the measurements of adsorption-desorption of  $\text{N}_2$  and SEM, respectively. Additionally, we thank Dr. J. M. Martín Martínez from the Adhesions and Adhesives Laboratory, University of Alicante, Spain for their accurate TEM's micrographs. Finally the authors thank to UTN, FRM for research founding.

## References

- Vince, J., Šurca Vuk, A., Opara Krašovec, U., Orel, B., Köhl, M., Heck, M. 2003. Absorber coatings based on  $\text{CoCuMnO}$ , spinels prepared via the sol-gel process: structural and optical properties. *Solar Energy Materials & Solar Cells* 79, 313-330.
- Mimani, T., Ghosh, S., 2000. Combustion synthesis of cobalt pigments: blue and pink. *Current Science*, 78, 892–896.
- Yang, L., Guan W., Bai B., Xu Q., Xiang Y. 2010. Synthesis of yeast-assisted  $\text{Co}_3\text{O}_4$  hollow microspheres - A novel biotemplating technique. *Journal of Alloys and Compounds* 504, L10 - L13.
- Pal, J., Chauhan, P. 2010. Study of physical properties of cobalt oxide ( $\text{Co}_3\text{O}_4$ ) nanocrystals. *Materials Characterization* 6, 575-579.
- Luisetto I., Pepe F., Bemporad E., 2008. Preparation and characterization of nano cobalt oxide. *Journal of Nanoparticle Research* 10, 59–67.
- Avila G., A., Barrera C, E., Huerta A., L., Muhl, S., 2004. Cobalt oxide films for solar selective surfaces, obtained by spray-pyrolysis. *Solar Energy Materials & Solar Cells*, 82, 269–278.
- Gui, Z., Zhu, J., Hu, Y., 2012. A simple preparative method for porous hollow-ware stacked cobalt oxides and their catalytic properties. *Materials Chemistry and Physics* 124, 243–247.
- Ozkaya, T., Baykal, A., Toprak, M. S., Koseoğlu, Y., Durmuş, Z., 2009. Reflux synthesis of  $\text{Co}_3\text{O}_4$  nanoparticles and its magnetic characterization. *Journal of Magnetism and Magnetic Materials*, 321, 2145–2149.
- Yang, H., Yuehua, H., Xiangchao, Z., Guanzhou, Q., 2004. Mechanochemical synthesis of cobalt oxide nanoparticles. *Materials Letters* 58, 387–389.
- Askarinejad, A., Morsali, A., 2009. Direct ultrasonic-assisted synthesis of sphere-like nanocrystals of spinel  $\text{Co}_3\text{O}_4$  and  $\text{Mn}_3\text{O}_4$ . *Ultrasonics Sonochemistry* 16, 124–131.
- Barreca, D., Bekermann, D., Comini, E., Devi, A., Fischer, R. A., Gasparotto, A., Gavagnin, M., Maccato C., Sada, C., Sberveglieri, G., Tondello, E., 2011. Plasma enhanced-CVD of undoped and fluorine-doped  $\text{Co}_3\text{O}_4$  nanosystems for novel gas sensors. *Sensors and Actuators B* 160 , 79–86.
- Thangavelu, K., Parameswari, K., Kuppusamy, K., Haldorai, Y., 2011. A simple and facile method to synthesize  $\text{Co}_3\text{O}_4$  nanoparticles from metal benzoate dihydrazinate complex as a precursor. *Materials Letters* 65, 1482–1484.
- Venkateswara Rao, K., Sunandana, C., 2008.  $\text{Co}_3\text{O}_4$  nanoparticles by chemical combustion: Effect of fuel to oxidizer ratio on structure, microstructure and EPR. *Solid State Communications* 148, 32–37.
- Toniolo, J., Takimi, A., Bergmann, C., 2010. Nanostructured cobalt oxides ( $\text{Co}_3\text{O}_4$  and  $\text{CoO}$ ) and metallic Co powders synthesized by the solution combustion method. *Materials Research Bulletin* 45, 672–676.
- Jain, S. R., Adiga, K. C., Pai Verneker, V. R., 1981. A new approach to thermochemical calculations of condensed fuel-oxidizer mixtures. *Combustion and flame* 40, 71-79.
- Lascalea, G. E., 2004. Obtención y propiedades de polvos nanocristalinos y materiales cerámicos de grano submicrométrico basados en circonia. Tesis para optar al título de Doctor en Ciencia y Tecnología, Mención Materiales. Instituto Sabato/Universidad Nacional de San Martín, Buenos Aires, Argentina.



- Klug, H., Alexander, L., 1974. X-ray Diffraction Procedures for Polycrystalline and Amorphous Materials. In: second ed., John Wiley and Sons, New York.
- Zimicz, M. G., Fábregas, I. O., Lamas, D. G., Larrondo, S. A., 2011. Effect of synthesis conditions on the nanopowder properties of  $Ce_{0.9}Zr_{0.1}O_2$ . Materials Research Bulletin 46, 850–857.
- Tang, X., Li, J., Hao J., 2008. Synthesis and characterization of spinel  $Co_3O_4$  octahedra enclosed by the {1 1 1} facets”, Materials Research Bulletin 43, 2912-2918.
- Al-Tuwirqi, R., Al-Ghamdi, A. A., Aal, N. A., Umar A., Mahmoud, W. E., 2011. Facile synthesis and optical properties of  $Co_3O_4$  nanostructures by the microwave route. Superlattices and Microstructures 49, 416–421.
- Van Buskirk, O. R., 1982. Solar selective surfaces. US 4310596, Jan 12.