



Kuna, Kranthi and Airey, Gordon and Thom, Nick (2016)
Development of a tool to assess in-situ curing of
Foamed Bitumen Mixtures. *Construction and Building
Materials*, 124 . pp. 55-68. ISSN 0950-0618

Access from the University of Nottingham repository:

<http://eprints.nottingham.ac.uk/41348/1/Kuna%20et%20al%20In%20situ%20curing%20CBM%20Vol%20124%202016.pdf>

Copyright and reuse:

The Nottingham ePrints service makes this work by researchers of the University of Nottingham available open access under the following conditions.

This article is made available under the Creative Commons Attribution Non-commercial No Derivatives licence and may be reused according to the conditions of the licence. For more details see: <http://creativecommons.org/licenses/by-nc-nd/2.5/>

A note on versions:

The version presented here may differ from the published version or from the version of record. If you wish to cite this item you are advised to consult the publisher's version. Please see the repository url above for details on accessing the published version and note that access may require a subscription.

For more information, please contact eprints@nottingham.ac.uk

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32

Development of a Tool to Assess In-Situ Curing of Foamed Bitumen Mixtures

Kranthi Kuna¹, Gordon Airey², Nick Thom³

(^aResearcher, University of Nottingham, the United Kingdom, k.kranthi13@gmail.com)

(^b Professor, University of Nottingham, the United Kingdom,
gordon.airey@nottingham.ac.uk)

(^cAssistant Professor, University of Nottingham, the United Kingdom,
nicholas.thom@nottingham.ac.uk)

ABSTRACT

This paper discusses the simplest yet crucial mix design consideration of Foamed Bitumen Mixtures (FBMs); curing. The objective of the present study is to attain better understanding of the curing mechanism of FBMs and lessen the gap between laboratory curing and field evolution of these mixtures. This was achieved by carrying out a laboratory curing study in two phases. The first phase aimed to understand the curing mechanism and to interpret the level of impact of factors such as temperature and time on the curing of FBMs. The effect of these factors on curing was evaluated with reference to stiffness gain and water loss of FBM specimens. The second phase was intended to develop a tool to assess in-situ curing of FBMs. With a view to assessing in-situ strength (or stiffness) the applicability of the maturity method, which is commonly used to estimate in-situ compressive strength of concrete before removal of formwork, to FBMs was evaluated. A strong correlation was found between maturity and the stiffness values obtained from the laboratory tests which resulted in development of maturity-stiffness relationships. The application of the method to assess the in-situ stiffness was presented using three hypothetical pavement sections. The results illustrate the influence of ambient temperature and the importance of cement addition to FBMs.

Keywords: Foamed bitumen mixes, curing, mechanical properties, maturity, in-situ stiffness

2 1 INTRODUCTION

3 Curing is the process by which FBMs gain strength or stiffness with expulsion
4 of water. Despite the fact that a wide range of studies have been undertaken on curing,
5 significant issues still need to be addressed. This is because of the complexity that
6 water brings to these mixtures. Water plays different roles during different stages of
7 mix design. Its existence aids the mixing and compaction phases, but negatively
8 affects the early strength. In addition to the climatic parameters like temperature,
9 humidity and wind, other factors such as aggregate gradation and properties, layer
10 thickness, initial water, binder, cement (or) additive content, layers applied on top,
11 drainage condition, and finally traffic load influence the curing process [1].

12 Assessing the in-situ curing of FBM is essential to decide when the next layer
13 of the pavement is to be applied. It also helps to obtain in-situ stiffness modulus of the
14 pavement layers which is the most important input parameter in pavement design and
15 evaluation. However, this assessment is not practical using non-destructive testing
16 equipment such as falling weight deflectometers (FWDs) and light weight
17 deflectometers (LWDs) particularly during the construction (early stages of curing).
18 Moreover, obtaining cores from the FBM layer is also difficult especially in the initial
19 phase of the curing [2]. Hence, Lee [3] highlighted the importance of specifying curing
20 condition in terms of amount of water present in the mixture. Since then different
21 agencies have specified maximum water content in the mixtures as a requirement of a
22 cold recycled layer (both foamed bitumen and emulsion treated). The departments of
23 transportation of Arizona, Iowa, South Dakota, Vermont and Washington allow a
24 maximum water content of 1.5% before a layer is laid over an FBM layer [4]. In
25 Europe the usual range for residual water content to determine the ideal time for
26 placing a bituminous layer over FBM layer is 1-1.5% [5]. To evaluate this in the field,
27 a link is necessary between laboratory curing and in-situ curing. To achieve this it is
28 important to understand the curing mechanism and factors that affect curing such as
29 temperature, time and material content (RAP, cement, etc.) and the level of the extent
30 to which these factors affect the curing mechanism.

31 The present work has tried to address some of the above discussed concerns by
32 identifying important parameters that affect curing and establishing a necessary link
33 between laboratory and in-situ curing. In order to assess in-situ strength (or stiffness)
34 the applicability of the maturity method, which is commonly used to estimate in-situ
35 compressive strength of concrete before removal of formwork, was applied and
36 evaluated with regard to FBMs.

37 2 METHODOLOGY ADOPTED

38 To achieve the above mentioned objectives a curing study was conducted in two
39 phases. In the first phase (Phase 1) an experimental study was carried out to interpret
40 the level of impact that temperature and time have on the curing of FBMs. The effect
41 of these factors on curing has been evaluated with reference to stiffness gain and water
42 loss of specimens made from these mixtures. The second phase (Phase 2) deals with
43 the applicability of the maturity method as a tool to assess the in-situ characteristics
44 of FBMs. Along with validating the maturity method, practical implications of the
45 maturity method were also evaluated in Phase 2.

46 In the present study, the terms 'early stage curing' (less than 7 days after
47 compaction); 'intermediate stage curing' (between 8 days and 35 days) and 'long term

1 curing' (between 35 days and 300 days) were used for convenience. In Phase 1 FBMs
 2 were cured up to 30 – 35 days at different curing temperatures and the curing trends
 3 were developed by monitoring water loss and stiffness gain in FBMs over this period
 4 of time. In Phase 2 the specimens were cured long term i.e. up to 180 to 300 days and
 5 maturity – stiffness models were developed. Table 1 presents the mixtures considered
 6 in the study. As can be seen from the table a total of four mixture types were considered
 7 in the study; two with 50% Reclaimed Asphalt Pavement (RAP) aggregate and two
 8 without any RAP content. One from each category contained 1% cement as can be
 9 seen in the table. The table also presents the mix design parameters that were adopted
 10 in the study. These are the parameters that were obtained from the mix design study
 11 carried out on these mixtures without cement [6]. It was assumed that the addition of
 12 cement doesn't influence the optimum mixing water content (MWC), foamed bitumen
 13 content (FBC) and design number of gyrations (N_{design}) in the gyratory compactor.
 14 Therefore, the same parameters that were obtained in the study for the mixtures
 15 without cement were used for the mixtures with cement (1% cement content). The
 16 cement used in the study is Ordinary Portland Cement (OPC). For brevity the physical
 17 properties of the materials used in the study are not presented in the paper. The details
 18 can be found elsewhere [6]. Although the original curing study includes all the
 19 mixtures in Table 1, only results of mixtures with 100% virgin aggregate (100% VA)
 20 are discussed in the curing parametric study (Phase 1) of the present paper.

21
 22

Table 1 Mix design parameters adopted in the study

	MWC (%)	FBC (%)	N_{design}
50%RAP+1%Cement	4.8	3.25	110
50%RAP	4.8	3.25	110
100%VA+1%Cement	5.2	4	140
100%VA	5.2	4	140

23 Notes: RAP: Reclaimed Asphalt Pavement; VA: Virgin Aggregate; MWC: Mixing Water Content;
 24 FBC: Foamed Bitumen Content; N_{design} : design number of gyrations

25 **3 CURING MECHANISM (PARAMETRIC) STUDY**

26 As discussed previously, since most of the agencies require a limit on the amount
 27 of water present in the FBM layer before laying a binder course and (or) surface, a
 28 link is necessary between laboratory curing and field water content requirements.
 29 Therefore, the present study aimed at developing curing trends in terms of water loss
 30 and stiffness gain for different temperatures and over a period of time to understand
 31 the curing mechanism which also helps in establishing a link between laboratory
 32 curing and field curing. These trends also help in understanding the acceleration of
 33 curing at elevated temperatures and to predict the properties of the FBM layers in the
 34 pavement for different climatic conditions. The water evolution trends obtained by
 35 monitoring the curing process give knowledge on the time it takes for various materials
 36 to reach equilibrium water content [1]. The results are also expected to be valuable
 37 inputs to formulate the necessary relation between laboratory properties and field
 38 trends, which gives valuable guidance for structural design of pavements.

39

40 **3.1 Selection of conditioning temperatures**

41 A detailed literature review revealed that conditioning temperatures of 60°C,
 42 40°C and 20°C have been popular, although other conditioning temperatures can also

1 be found in the literature. Curing temperatures above the softening point are usually
2 recommended to be avoided as they may cause bitumen to flow and change its
3 dispersion within the mixture which may change mixture properties in addition to
4 inducing unrepresentative ageing of the bitumen. Therefore, to keep the specimens
5 below the softening point of the bitumen used in the mixture, which is 45°C for the
6 70/100 grade bitumen used in this study, curing temperatures of 40°C, 30°C, 20°C and
7 5°C were adopted. Though curing at 20°C and 5°C are not always to be considered as
8 accelerated curing, these temperatures were included in the study to understand the
9 effect of these temperatures on curing.

10 **3.2 Monitoring curing**

11 The curing trends were developed by monitoring water loss and stiffness gain in
12 FBMs over a period of time. The specimens were gyratory compacted cylindrical
13 specimens of 100mm diameter and about 62mm high. The extracted specimens were
14 placed in temperature controlled cabinets at the curing temperature. The non-
15 destructive stiffness test, Indirect Tensile Stiffness Modulus (ITSM), was selected for
16 assessing curing of the FBM specimen over a period of 30 days. This test was preferred
17 over ultrasonic testing because of its more realistic level of applied stress. It was
18 carried out in accordance with DD 213: 1993. ITSM was chosen in order to carry out
19 the test on the same set of specimens to nullify variability in the mixtures and to derive
20 reliable trends for curing evaluation. These tests were carried out at a temperature of
21 20°C.


22 It was identified from preliminary studies [7] that the mechanical properties of
23 sealed specimens (likely to be most representative of in-situ conditions) were always
24 found to be 50-70% of those of unsealed specimens. So it was assumed that the sealed
25 condition can be interpreted using unsealed data and therefore only the unsealed curing
26 condition was considered in the present study.

27 **3.3 Effect of time and temperature on curing trends**


28 The water content in the 100% VA-FBM specimens which was monitored over
29 time is plotted in Figure 1. Trend lines which are power curves are also included in
30 the figure. The initial water content in the mixture during compaction was 5.2%. The
31 plots showed that water content in the specimen reached about a quarter
32 (approximately 1.3%) of the initial amount after 24 hours of curing at both 30°C and
33 40°C. Similarly, water content reached about half (2.6%) of the initial amount when
34 specimens were cured at 20°C and 5°C. The trends suggest that the rate of water loss
35 is approximately proportional to the amount of water present in the mixture. In other
36 words, the rate of water loss decreased with time. It is clear from the plots that the
37 water loss is dependent on the curing temperature. The higher the curing temperature
38 the faster was the water loss. However, all curves, except the 5°C curve, seem to reach
39 a steady state after which the loss is negligible.

40 The stiffness (ITSM) values that were measured over time on the 100% VA-
41 FBM specimens cured at different temperatures are plotted in Figure 2. The plot shows
42 stiffness monitored for a period of 30 days at curing temperatures of 40°C, 30°C, 20°C
43 and 5°C. Trend lines which are logarithmic with positive tangential slope are also
44 included in the plot. As can be seen from the figure, for all conditions stiffness
45 increased with time of curing. However, this gain was more rapid for specimens cured
46 at higher temperatures. This could be attributed to rapid water loss that takes place at
47 higher temperature which yields higher stiffness values with time. Moreover, in a
48 similar way to water loss, the rate of stiffness gain is decreasing with time which
49 implies that the stiffness gain is very much related to water loss from the specimen.


1 This curing phenomenon can be seen in Figure 3 in which water loss and stiffness gain
 2 of 100% VA-FBM specimens cured at 20°C is presented. The figure illustrates the
 3 curing mechanism in which these FBMs gain stiffness with water loss during curing.
 4

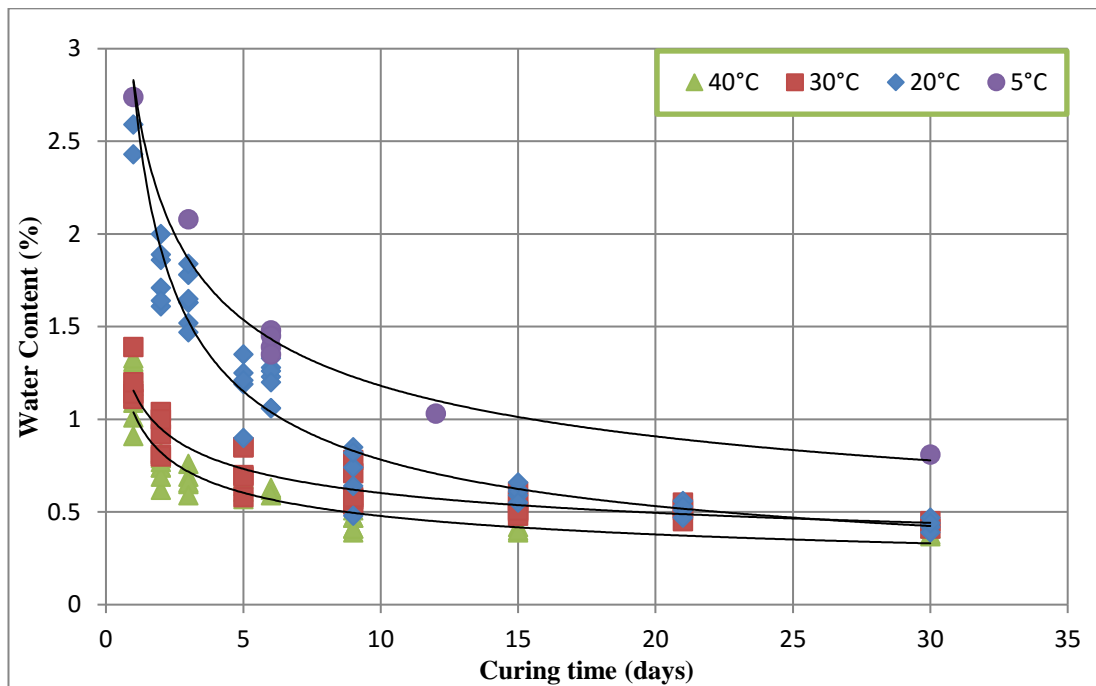

5
 6 **Figure 1 Effect of time and temperature on water loss in 100% VA-FBM**
 7 **specimens**

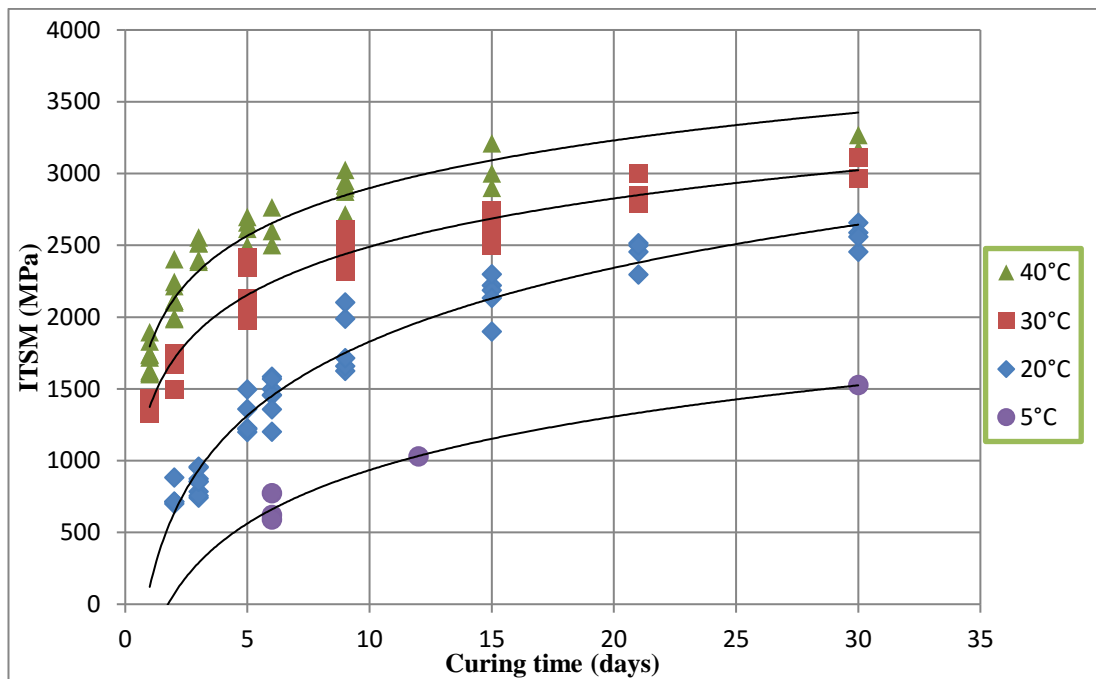

8
 9 **Figure 2 Effect of time and temperature on stiffness gain in 100% VA-FBM specimens**

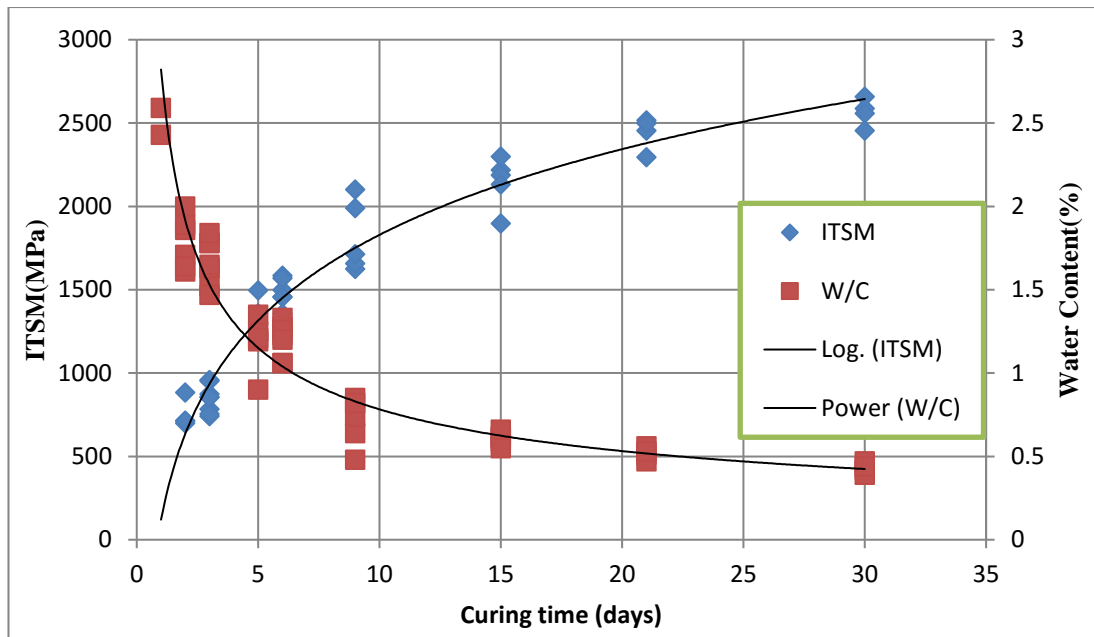

1
2 **Figure 3 Effect of time on curing (water loss and stiffness gain) in 100% VA-FBM**
3 **cured at 20°C**

4
5 **3.4 Effect of water content on stiffness**


6 Figure 4 shows a plot of stiffness (ITSM) versus water content for the 100%
7 VA-FBM specimens that were cured at different temperatures. As a general trend,
8 with decrease in the water content the stiffness increased. However, as can be seen
9 from the figure when individual temperatures are considered it is found that the
10 temperature has a significant additional impact on the stiffness of the mixture. For
11 example, the specimens which were cured at 40°C having water content around 1%
12 showed far higher stiffness (ITSM) than the specimens cured at lower temperatures at
13 the same water content.

14 To study the effect of temperature on bitumen properties, bitumen was extracted
15 in accordance with BS 598-102 from the 100% VA-FBM specimens that were cured
16 for 30 days. Frequency sweep tests were carried out on the extracted bitumen and
17 complex modulus (G^*) master curves are plotted in Figure 5 to understand the effect
18 of the curing temperature on the bitumen properties. The figure presents the complex
19 modulus (G^*) master curves at a reference temperature of 20°C for the extracted
20 bitumen from 100% VA-FBM specimens cured at 20°C and 40°C for 30 days. It has
21 to be noted that the change in bitumen complex modulus before foaming and after
22 extraction is not only because of the curing but also because of oxidation that occurs
23 during bitumen foaming. As can be seen from the plots, the difference in complex
24 modulus for the extracted bitumen is significant, particularly at the ITSM testing
25 frequency which is approximately 5Hz which indicates that the difference in bitumen
26 ageing between 20°C and 40°C curing is considerable. Hence, from the results it is
27 evident that water loss is not the only mechanism involved in the curing. High
28 temperature is clearly responsible for additional stiffness gain, possibly by facilitating
29 binder adhesion and more importantly because of the increase in binder stiffness
30 during the curing process.

31 The practical implication of these observations is that specifying a water content
32 limit for FBM layers before allowing traffic or allowing layers (binder courses) to be


1 placed over the FBM layer is not appropriate. For example if an agency specified a
2 1% water content limit, the 100% VA mixture takes approximately 2 days, 7 days and
3 15 days respectively if the average temperature is 40°C, 20°C and 5°C (Figure 1).
4 However, it reaches different levels of stiffness. In this example it reaches 1850MPa
5 at 40°C, 1450MPa at 20°C and 1150MPa at 5°C (Figure 4). The stiffness achieved by
6 the mixture at 40°C is about 60% higher than that achieved at 5°C for the same water
7 content. This issue can be addressed by developing a tool to assess the stiffness of
8 these mixtures based on the temperature history of the compacted FBM layer. The
9 following section discusses the development of such a tool.

10

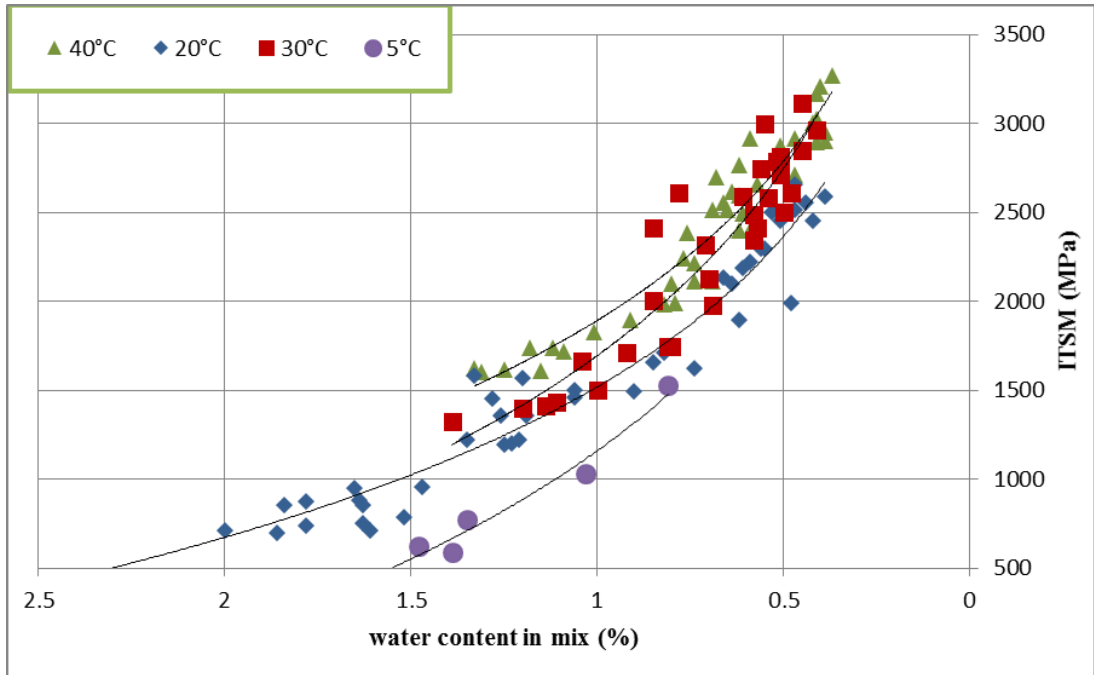

11

12 **Figure 4 Effect of water content and temperature on stiffness in 100%VA-FBM**

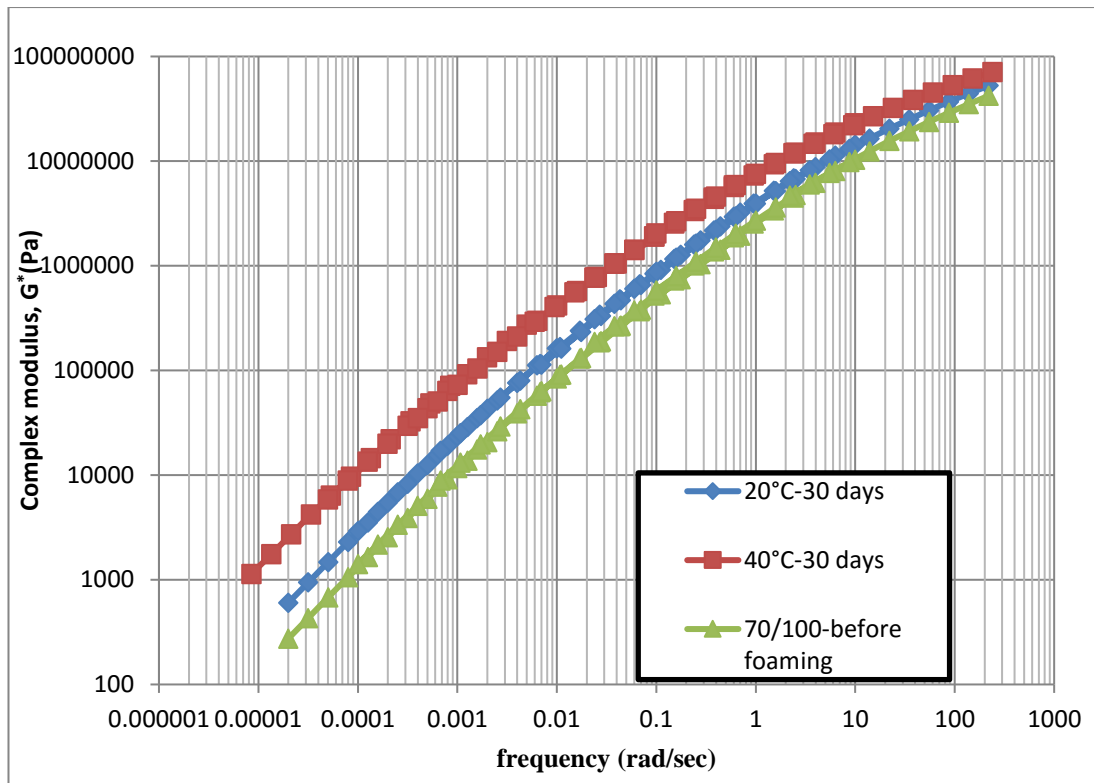

1
2 **Figure 5 Effect of curing temperature on bitumen properties in terms of**
3 **complex modulus master curves for extracted and pure bitumen at a reference**
4 **temperature of 20°C**

5 **4 ASSESSMENT OF IN-SITU CURING**

6 Simulating in-situ condition in the laboratory is the most difficult step in mix
7 design of cold recycled mixtures (FBMs and emulsion treated mixtures) [8]. Hence, a
8 significant amount of research has been carried out on the development of a laboratory
9 curing protocol for these mixes. However, there is a considerable variation in
10 equivalent in-situ condition proposed by different researchers [9]. Nevertheless, as a
11 general trend, with increase in conditioning time and temperature equivalent in-situ
12 conditioning time is increased. In addition to that, the temperature was found to be a
13 more influential parameter than water content on the mechanical properties. This
14 observation suggests the use of the maturity method, which is used for estimating in-
15 place strength of concrete based on its temperature history. The maturity method could
16 help as a tool to estimate in-situ stiffness in view of the fact that the in-situ water
17 content specification could result in different stiffness values for different temperature
18 histories.

19 For concrete, the maturity method allows an estimation of in-situ compressive
20 strength as the concrete design criterion in most cases is compressive strength.
21 However as the objective of the present study is to propose a tool to estimate in-situ
22 stiffness, which is an important input parameter for pavement structural design,
23 stiffness (ITSM) was used to generate maturity – stiffness relationships.

24 **4.1 Maturity methods**

25 The maturity method is a technique commonly used in the concrete industry to
26 account for the combined effects of time and temperature on the strength gain [10].
27 This technique allows in-place concrete strength to be estimated using time and

1 temperature history of concrete in the field [11]. Maturity functions are used to convert
 2 the actual temperature to an equivalent temperature. This concept of a time -
 3 temperature factor (maturity) can also be used to quantify the strength development of
 4 FBMs [12]. For instance, if FBM is cured say either at 40°C or 60°C, the maturity can
 5 be calculated and the strength of the FBM can be estimated. If curing temperature is
 6 low (say 40°C) the time to reach the required maturity will be longer than if the curing
 7 temperature is high (say 60°C). As long as the same maturity is reached for both curing
 8 conditions, their strength should be the same.

9 **4.1.1 Selection of Maturity function**

10 The time-temperature functions (TTF) or maturity functions are used to convert
 11 time and temperature history of in-place concrete to a factor which is related to its
 12 strength. The two TTFs that are being used in in-place strength determination of
 13 concrete are the Nurse-Saul function and Arrhenius function.

14 As Malhotra and Carino (2003) [13] observed, in 1951 Saul defined maturity as
 15 the product of time and temperature based on his study on steam curing of concrete.
 16 Thus, maturity can be computed from the temperature history using the following
 17 equation called the Nurse-Saul equation (Eq. 1)).

$$18 \quad M = \sum_0^t (T - T_0) \Delta t \quad \text{Equation 1}$$

19 Where, M = maturity at age t, T = average temperature of the concrete during
 20 the time interval Δt , T_0 = datum temperature

21 The Nurse-Saul function can be used to convert a given temperature time curing
 22 history to an equivalent age of curing at a reference temperature as follows:

$$23 \quad t_e = \frac{\sum (T - T_0) \Delta t}{(T_r - T_0)} \quad \text{Equation 2}$$

24 Where, t_e = equivalent age at the reference temperature, T_r = reference
 25 temperature

26 In this case equivalent age represents the duration of the curing period at the
 27 reference temperature that would result in the same maturity as the curing period at
 28 the actual temperature. The above equation can be re-written as follows:

$$29 \quad t_e = \sum_0^t \alpha \Delta t \quad \text{Equation 3}$$

30 Where, α = age conversion factor.

31 The age conversion factor converts a curing interval Δt to the equivalent curing
 32 interval at a standard reference temperature. For example if we assume a datum
 33 temperature of 0°C and reference temperature of 20°C, then the age conversion factor
 34 for a specimen cured at 40°C for 3 days according to Eq. 2 & 3 is 3 ((40-0)/(20-0))
 35 and the equivalent age, t_e is 6 days.

36 It has to be noted that Eq. 1 assumes a linear relationship between rate of strength
 37 gain and curing temperature. However this was not true in most cases [10]. Therefore
 38 later in 1977, [14], Hansen and Pedersen proposed a new time temperature function
 39 based on the Arrhenius equation. The new function allowed the computation of the
 40 equivalent age of concrete as follows:

$$41 \quad t_e = \sum_0^t e^{\frac{-E[\frac{1}{T} - \frac{1}{T_r}]}{R}} \Delta t \quad \text{Equation 4}$$

42 Where, t_e = the equivalent age at the reference temperature, E = apparent
 43 activation energy, J/mol, R = universal gas constant, 8.314 J/mol-K, T = average
 44 absolute temperature of the concrete during interval Δt in Kelvin, and T_r = absolute
 45 reference temperature in Kelvin.

46 Carino (2001) [10], suggested that obtaining accurate values for activation
 47 energy is not practical and proposed a simplified equation (Eq. 5). It was also shown
 48 that both the equations (Eq. 4 and Eq. 5) give the same strength values from maturity

1 – strength models. Moreover it was also stated that the sensitivity factor in Eq. 5 has
 2 a more physical significance compared to activation energy. In the present study Eq.
 3 5 is used for its simplicity.


$$4 \quad t_e = \sum_0^t e^{B(T-T_r)} * \Delta t \quad \text{Equation 5}$$

5 Then the expression for the age conversion factor becomes the following:

$$6 \quad \alpha = e^{B(T-T_r)} \quad \text{Equation 6}$$

7 Where, B = temperature sensitivity factor, $1/^\circ\text{C}$

8 Figure 6 illustrates the importance of equivalent age and the summation involved in
 9 in Eq. 5. The figure describes a situation in which the FBM curing condition was
 10 changed to 20°C after curing for 40 days at 5°C . As discussed earlier (Figure 2), the
 11 rate of stiffness gain is dependent on the stiffness achieved by the mixture. Therefore
 12 the equivalent age term considers this effect and adjusts the stiffness increase to the
 13 rate associated with the new conditioning temperature and the current stiffness. To
 14 explain graphically, when the curing condition changed from 5°C to 20°C on the 40th
 15 day, the stiffness gain rate was taken from a horizontally transferred 20°C curve rather
 16 than the rate of the actual 20°C curing curve on the 40th day.
 17

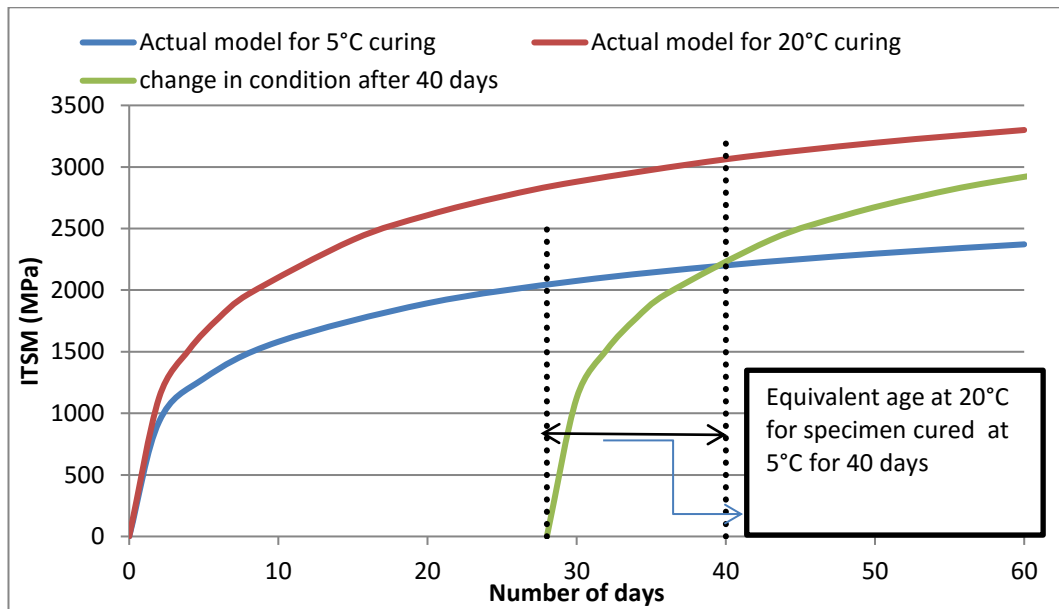

18
 19 **Figure 6 Illustration of equivalent age (Curing temperature was changed from**
 20 **5°C to 20°C at 40 days)**

21
 22
 23
 24
 25
 26
 27
 28
 29
 30
 31
 32
 33

4.1.2 Formulating the effect of temperature on strength (stiffness) gain

As rate of strength or stiffness gain is dependent on the curing temperature it is important to formulate temperature dependency in maturity – strength models. This can be done by a temperature dependent factor called the rate constant (k), which is the initial slope of the strength (or stiffness) versus time of the curing curve at a specific constant temperature. Carino et al., (1992) [15] examined the following relationship for describing the rate constant k(T) as a function of temperature.

$$k(T) = Ae^{BT} \quad \text{Equation 7}$$

Where, A = the value of the rate constant at 0 °C

4.1.3 Strength – Maturity Relationships

Many equations have been proposed to model the strength gain of concrete, but three are often used. These three functions are the exponential, hyperbolic and logarithmic functions, which are defined as follows [13]:

Exponential:

$$S = S_u e^{-\left[\frac{\tau}{M}\right]^\beta} \quad \text{Equation 8}$$

Where, S = compressive strength (MPa), S_u = limiting compressive strength (MPa), M = maturity index (hours), τ = characteristic time constant (hours), and β = shape parameter.

Hyperbolic:

$$S = S_u \frac{k(M-M_0)}{1+k(M-M_0)} \quad \text{Equation 9}$$

$$S = S_u \frac{\sqrt{k(M-M_0)}}{1+\sqrt{k(M-M_0)}} \quad \text{Equation 10}$$

Where, M_0 = maturity when strength development is assumed to begin ($^{\circ}\text{C} \cdot \text{hours}$ or hours), and k = rate constant ($1/[^{\circ}\text{C} \cdot \text{hours}]$ or 1/hours).

The differences between Eq. 9 and Eq. 10 as stated by Carino (2001) [10] are in terms of the hydration kinetics of individual cement particles. Eq. 9 is derived based on linear kinetics, which means that the degree of hydration of an individual cement particle is a linear function of the product of time and the rate constant. Eq. 6-10 is based on parabolic kinetics. Thus Eqs. 9 & 10 are termed as the linear hyperbolic and parabolic hyperbolic models.

Logarithmic:


$$S = \frac{a}{S_0} + \frac{b}{S_0} \log M \quad \text{Equation 11}$$

Where, S_0 is strength when strength development is assumed to begin. The constants a and b are related to the water – cement ratio of the concrete and the type of cement.

4.2 Applicability of Maturity method to FBMs

As discussed, the maturity method is a technique commonly used in the concrete industry to account for the combined effects of time and temperature on the strength gain. The notion of applying the maturity method arises from the fact that the stiffness of a given FBM is dependent on age and temperature history as seen in the previous sections. Moreover, similar to concrete, at early age temperature has a predominant effect on stiffness gain in FBMs. On account of this temperature dependency it is not straightforward to estimate the in-situ properties based on the laboratory test data obtained under standard laboratory conditions [13]. A function of time and temperature was considered an appropriate approach to describe the behaviour of these materials [12]. Moreover, Doyle et al. [9] also identified that in-situ properties of cold bituminous emulsion mixes can be estimated by the maturity approach. Therefore applicability of the maturity method to FBM stiffness gain will be explored and modifications are proposed for predicting stiffness as accurately as possible.

Modifications to the maturity or time-temperature functions were needed as the mechanism by which FBMs gain strength is different from that of concrete. The primary difference is in the definition of curing in the concrete industry and for FBMs. With regard to concrete, curing is a process in which the concrete is protected from loss of water and the concrete strength development occurs during the curing period when water is available for cement hydration. In contrast to that, for FBMs curing is a process in which the compacted material discharges water through evaporation and gains stiffness or tensile strength by formation of continuous bituminous mastic film [16]. The other characteristic of concrete is its 'crossover behaviour', where concrete cured at higher temperature initially has higher strength but later has lower strength than concrete cured at lower temperature. The crossover behaviour of concrete is illustrated in Figure 7. This crossover is because a higher initial temperature results in more than a proportional increase in the initial rate of hydration resulting in reacted products not having time to uniformly distribute within the pores of the hardening paste [10]. However, this crossover effect is not seen in the FBM curing process, as seen in Figure 2. Similar results have also been found in other research investigations [12, 17]. It has to be noted that the results from these figures were for a curing period of around 30 days whereas crossover relates to the long-term strength of concrete. Nonetheless, analogous results were found for much longer curing periods which will be shown in subsequent sections.

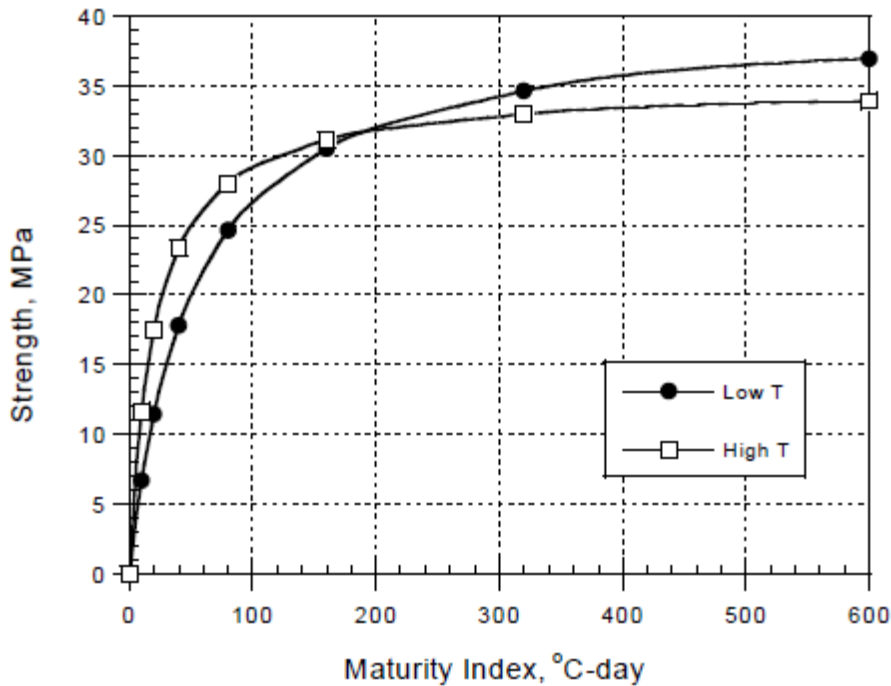

1
2 **Figure 7 The crossover effect in concrete [10]**

3 In the present discussion, maturity refers to the function of temperature and
4 equivalent age computed using a time-temperature function. This is a slightly different
5 interpretation from the definition given by Malhotra and Carino [13] in which maturity
6 was referred to either a temperature – time factor computed using the Nurse-Saul
7 function (Eq. 1) or equivalent age computed using any of the maturity functions (Eq.
8 2, Eq. 4 and Eq. 5). The general steps followed in developing the maturity - stiffness
9 model for each mixture considered are presented below

- 10
- The FBM specimens were cured at different curing temperatures (5°C, 20°C,
11 and 40°C).
 - ITSM (stiffness) tests were performed at different intervals of time. The values
12 of rate constant (k) at each temperature were determined by fitting stiffness
13 data to stiffness – age relationships for isothermal conditions.
 - Temperature sensitivity factor (B) was determined by fitting the Arrhenius
14 equation (Eq. 7) to rate constant (k) versus temperature data.
 - Age conversion factor (α) was calculated (Eq. 6) for each time period over
15 which the ITSM test was conducted.
 - Equivalent age (t_e) was obtained for each time period using Eq. 5.
 - Maturity was calculated for all test data and plotted against stiffness.
16
 - A best fit maturity – stiffness relationship was obtained by fitting maturity
17 versus stiffness data.
18
19
20
21
22

23 The methodology adopted for the maturity – strength relationship will be
24 explained with reference to the 50%RAP + 1% cement mixture.
25

4.2.1 Stiffness-age relationships

It was identified in the previous section that a logarithmic fit best describes the stiffness increase of FBMs over time (Figure 2). This is because the logarithmic function provided a good prediction of the high initial rate of stiffness gain which is a characteristic of FBMs. However, the logarithmic function overestimated the stiffness of these mixtures over a long period of time. This can be seen in Figure 8 to Figure 10. These figures present the average ITSM test results for the FBM (50%RAP + 1% Cement) cured and monitored over a long period (296 days). The short term curing data (up to 30 days) is equivalent to that presented in Figure 2. The specimens cured at 30°C were not cured long term and were used for validation of the approach. Because of the overestimation of the logarithmic function in the long term, a hyperbolic equation is used to fit the stiffness data over time. Hyperbolic equations for strength gain under isothermal curing for concrete are as shown in Eq. 12 and Eq. 13. Theoretical analysis of the expressions (hyperbolic equations) to describe the strength development of concrete can be found in Carino (1984)[18]. In the analysis it was also shown that under isothermal conditions the strength gain of the concrete can be described by a hyperbolic curve (Eq. 12 and Eq. 13). The maturity term (M) was replaced with time term (t) from Eq. 8 and Eq. 9.

$$S = S_u \frac{k(t-t_0)}{1+k(t-t_0)} \quad \text{Equation 12}$$

$$S = S_u \frac{\sqrt{k(t-t_0)}}{1+\sqrt{k(t-t_0)}} \quad \text{Equation 13}$$

Where, S is strength at age t; S_u is the asymptotic value of the strength for the hyperbolic function that fits the data; k is the rate constant which is related to the rate of strength gain at a constant temperature; t_0 is age at the start of strength development. It was also shown by Carino (1984) that these parameters are temperature dependent and can be obtained by conducting a regression analysis on strength data obtained at different curing temperatures.

In the present study as the material property considered is stiffness (ITSM), strength (S) is replaced by stiffness (E) in Eq. 12 and Eq. 13. It is assumed that the stiffness development starts at age t_0 as per these models. However, in the present study it was assumed that stiffness development starts immediately after compaction ($t_0 = 0$). Thus the two equations (Eq. 12 and Eq. 13) can be re-written as follows.


$$E = E_u \frac{kt}{1+kt} \quad \text{Equation 14}$$

$$E = E_u \frac{\sqrt{kt}}{1+\sqrt{kt}} \quad \text{Equation 15}$$


The stiffness – time data for the three curing temperatures (5°C, 20°C and 40°C) was fitted by the hyperbolic relationships given by Eq. 14 and Eq. 15. There are several approaches to determine the parameters limiting stiffness (E_u) and k. The simplest approach is to conduct regression analysis using the least squares curve fitting technique. The data in Figure 8 to Figure 10 were subjected to regression analysis and the best fit curves for logarithmic and the two hyperbolic curves can be seen in the figures. As can be seen, the parabolic hyperbolic equation (Eq. 15) best described the trend. The coefficient of determination, R^2 , found from regression analysis for the test data confirmed that the parabolic hyperbolic equation is the best fit to the stiffness over time. The minimum R^2 was found to be 0.78, 0.9, 0.96 respectively for logarithmic, linear hyperbolic and parabolic hyperbolic models.

The limiting stiffness, E_u and the rate constant, k obtained from the regression analysis for each curing temperature are summarised in Table 2.


1 Long term curing data fitted to the hyperbolic parabolic model for 50%RAP+1%
 2 Cement – FBM for all curing temperatures is presented in Figure 11. It is evident from the
 3 figure that the limiting stiffness (E_u) is directly dependent on curing temperature.
 4 The higher the curing temperature, the higher was the limiting stiffness which means
 5 that there was no crossover effect found in FBMs. Moreover, the temperature
 6 dependency of the limiting stiffness was nearly linear.
 7

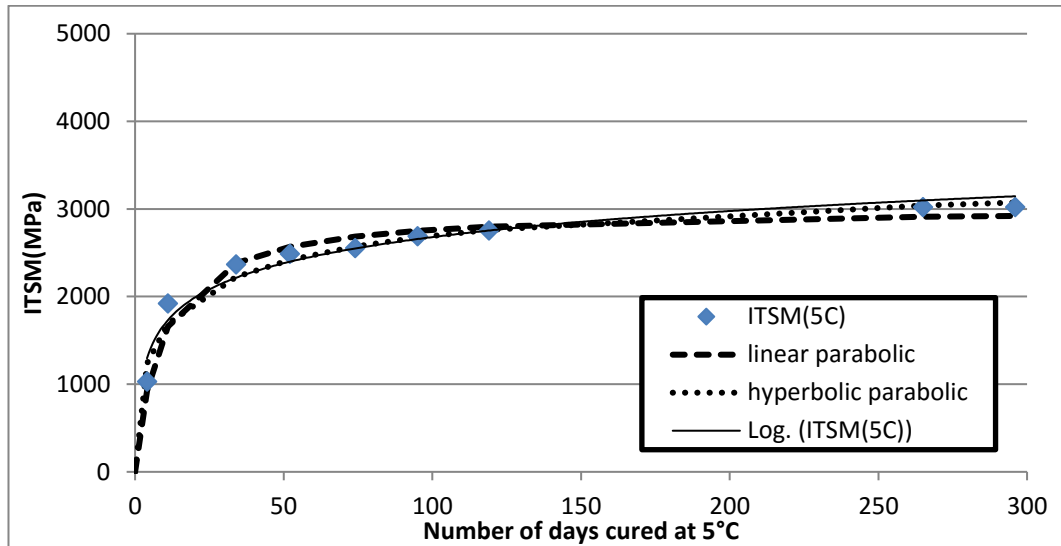

8
 9 **Figure 8 Stiffness development relationships for 50%RAP + 1%Cement- FBM**
 10 **cured at 5°C**

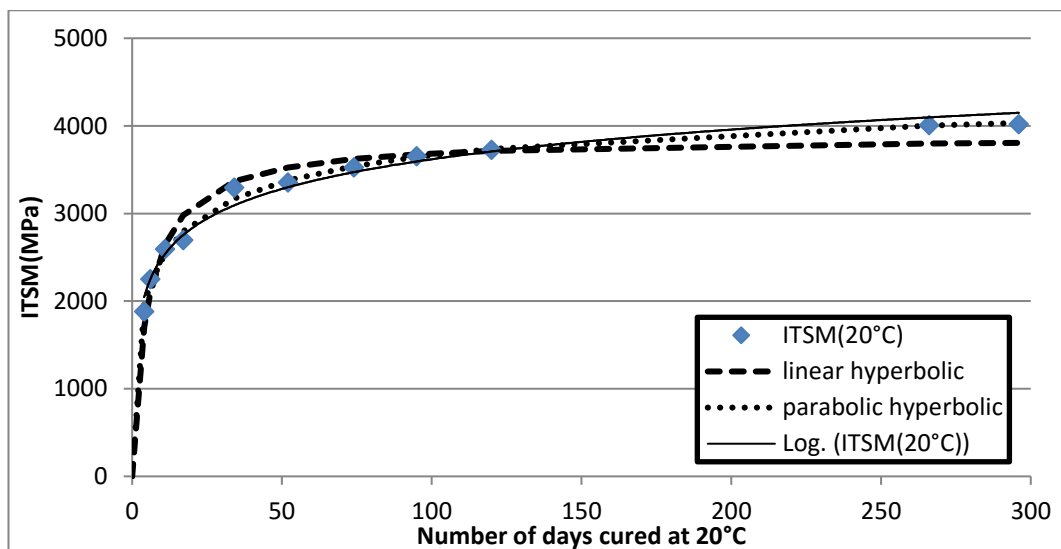

11
 12 **Figure 9 Stiffness development relationships for 50%RAP + 1%Cement- FBM**
 13 **cured at 20°C**

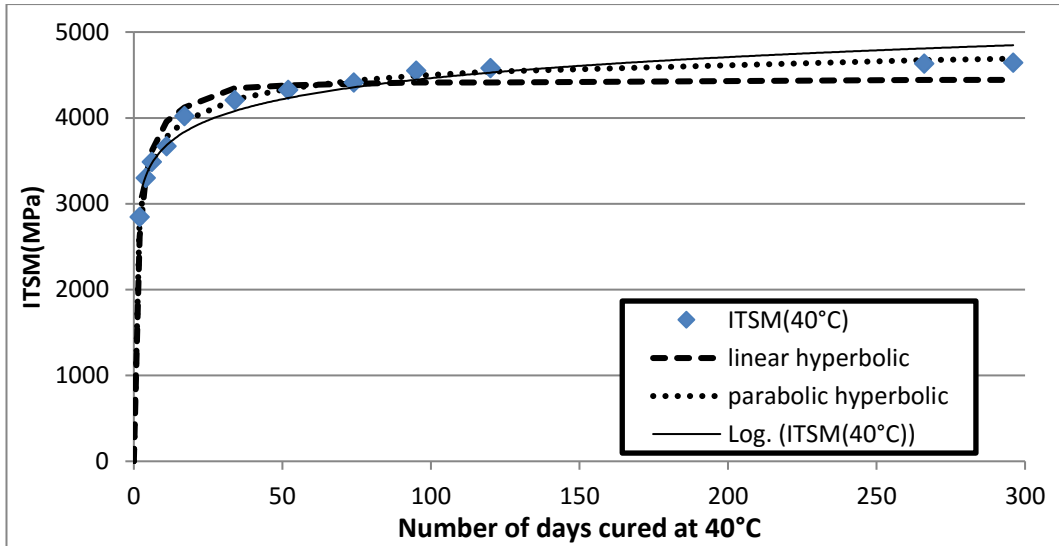


1
2 **Figure 10 Stiffness development relationships for 50%RAP + 1% Cement- FBM**
3 **cured at 40°C**

4

5 **Table 2 Summary of parameters obtained by fitting age versus stiffness data**

Temperature	5°C		20°C		40°C	
	k(1/day)	E_u (MPa)	k(1/day)	E_u (MPa)	k(1/day)	E_u (MPa)
50%RAP+1%Cement	0.06	3622	0.13	4687	0.9	4977
50%RAP	0.01	2842	0.08	3377	0.72	3489
100%VA+1%Cement	0.07	3199	0.28	4253	2.16	4556
100%VA	0.02	2620	0.05	3834	0.58	3895

6

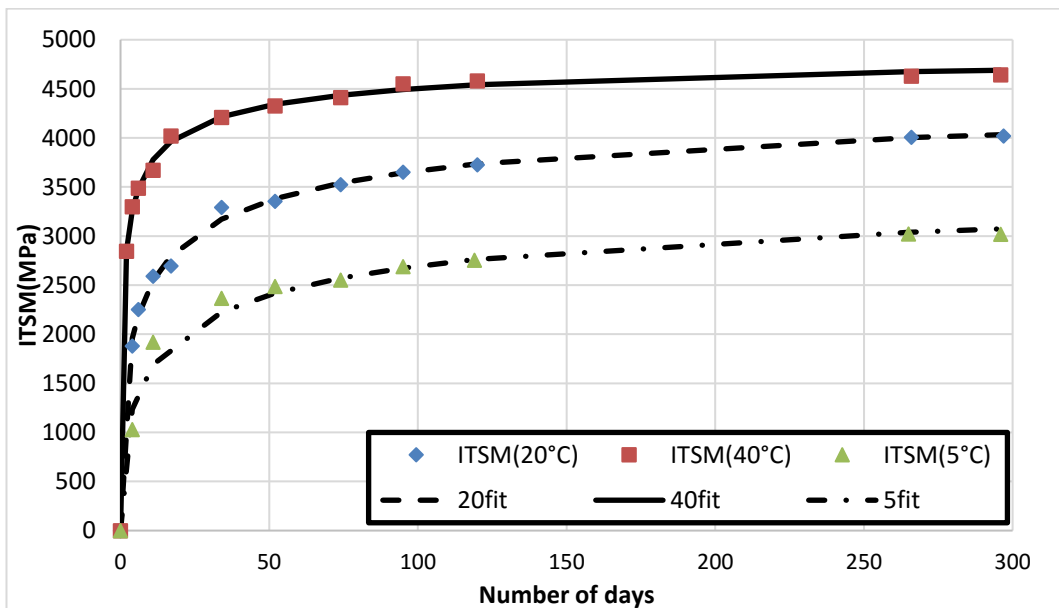

7

8 **Figure 11 Long term curing data fitted to hyperbolic parabolic model for**
9 **50%RAP+1% Cement - FBM**

4.2.2 Temperature sensitivity factor

This section examines the variation of the value of the rate constant (k) with curing temperature in order to obtain the temperature sensitivity factor (B). As was discussed, the rate constant (k) is related to the rate of stiffness gain at a constant temperature, and it was obtained from an appropriate equation of stiffness gain versus age. In order to describe stiffness development under variable curing temperatures it is necessary to determine how the rate constant is affected by curing temperature. For this the k values in Table 2 are plotted against curing temperature as can be seen in Figure 12. The best fit Arrhenius equation (Eq. 7) was determined. The parameters that were obtained in the analysis are tabulated in Table 3. A is the value of the rate constant at 0°C and B is the temperature sensitivity factor.

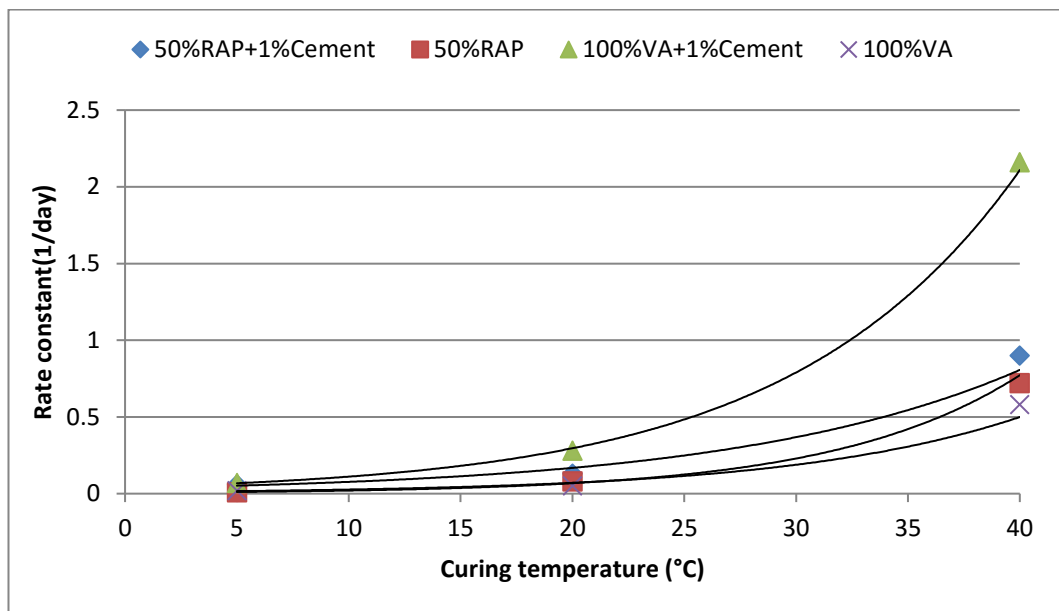


Figure 12 Variation of rate constant (k) with temperature

Table 3 Summary of parameters obtained by fitting age versus stiffness data

Mixture type	A	B(1/°C)	R-squared
50%RAP+1%Cement	0.035	0.078	0.97
50%RAP	0.006	0.121	0.99
0%RAP+1%Cement	0.041	0.098	0.99
0%RAP	0.01	0.097	0.96

4.2.3 Age conversion factor and equivalent age

The age conversion factors for different temperatures were calculated using Eq. 6. The equation utilised the temperature sensitivity factors from Table 3. The reference temperature to which age was converted was assumed as 20°C . The age conversion factor (α) obtained for different mixtures is presented in Figure 13. The age conversion factor (α) at 20°C is 1 as the reference temperature considered in the study is 20°C . The equivalent age is the duration of time that a specimen would need to be cured at a specified reference temperature (in the present case 20°C) to equal the maturity of the specimen cured at various temperatures. The equation for equivalent age used in the present study is as given in Eq. 5. For developing the maturity – stiffness

relationships, the specimens are cured at isothermal conditions. Therefore, for isothermal condition in Eq. 5, Δt can be replaced with t ($\Sigma \Delta t$) and summation is not needed. Thus Eq. 5 can be re-written as Eq. 16 in which t is the elapsed time of test since compaction, B is temperature sensitivity factor (Table 3), T is curing temperature and T_r is the reference temperature (in the present case T_r was considered as 20°C).

$$t_e = e^{B(T-T_r)} * t \quad \text{Equation 16}$$

It has to be noted that for calculating in-situ maturity where variable temperature exists Eq. 5 has to be used as it is. The equivalent age obtained using Eq. 16 for a reference temperature of 20°C is plotted against stiffness in Figure 14 for the 50%RAP + 1% cement FBM mixture. The equivalent age – stiffness data for 20°C condition remains the same as in Figure 9 as the reference temperature considered was 20°C .

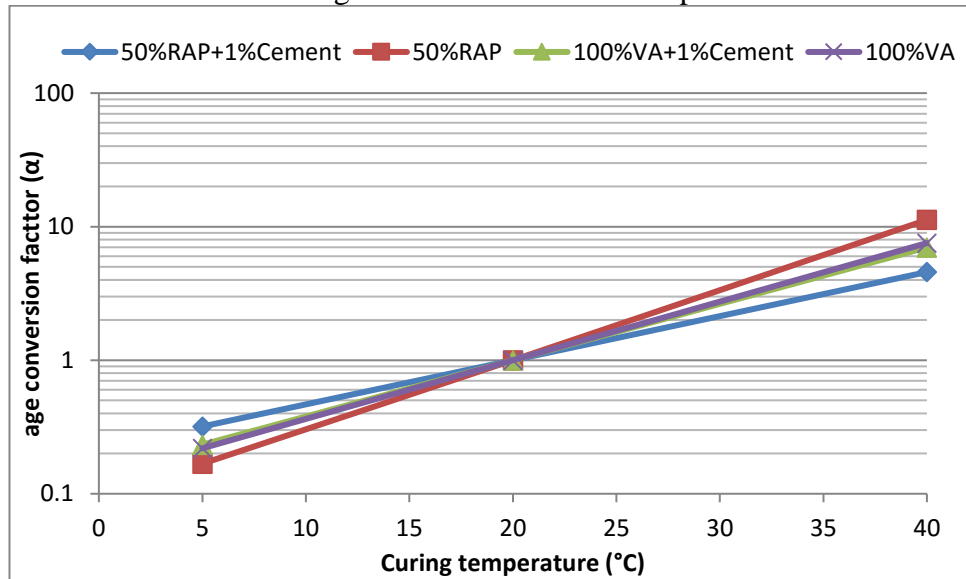


Figure 13 Age conversion factor for reference temperature of 20°C

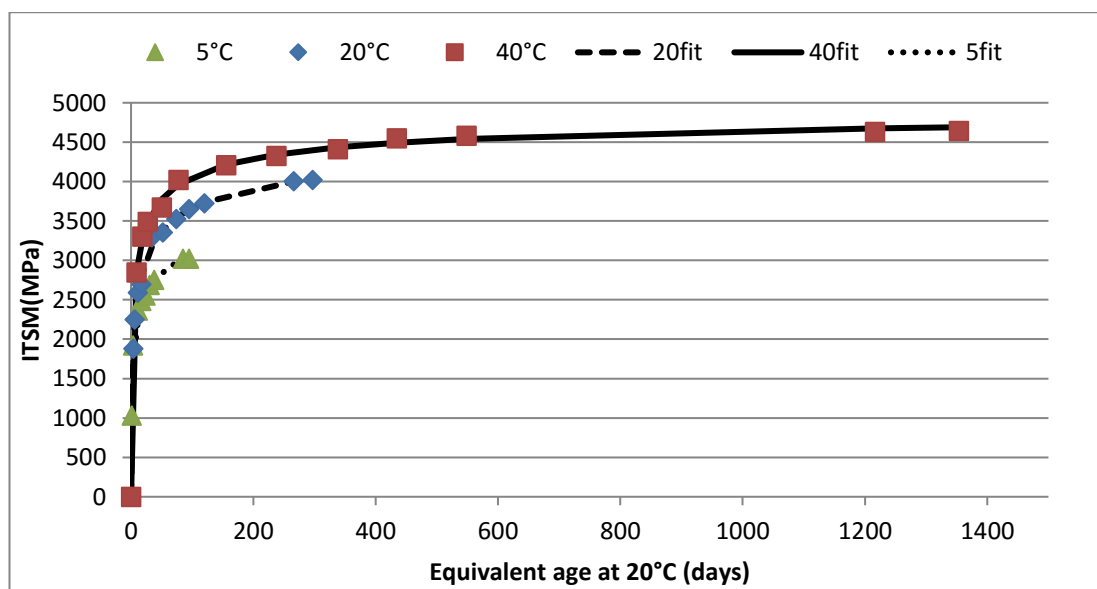


Figure 14 Equivalent age at 20°C for 50%RAP + 1% Cement - FBM

4.2.4 Maturity - stiffness relationship

According to the standard definition of maturity, samples of the same FBM should have equal stiffness if they have equal maturities irrespective of their curing

1 histories. As the present study is dealing with the equivalent age approach the term
 2 maturity refers to equivalent age. Figure 14 clearly shows that the equivalent age
 3 doesn't have a unique relationship with stiffness. The traditional maturity rule is
 4 therefore an approximation in the present case as it assumes that the limiting stiffness
 5 or strength of the mixture subjected to continuous curing is not affected by early age
 6 temperature history. However, as was shown in Figure 7 and Figure 11, this was not
 7 the case in either FBMs or concrete. In both cases it is clear that the curing temperature
 8 not only affects the initial rate of stiffness but also the limiting values. Therefore the
 9 traditional maturity rule results in inaccurate results.

10 To resolve the nature of the above problem, Carino (1984) introduced a model
 11 for concrete called a rate constant model which states that there exists a unique
 12 relationship between relative strength (S/Su) and equivalent age. The relative strength
 13 can be obtained by dividing strength by the limiting strength obtained for the curing
 14 temperature that the specimen experienced. Figure 15 is a plot of the relative stiffness
 15 versus equivalent age obtained for the 50%RAP + 1% Cement mixture. The data
 16 points very much group around a single curve and therefore it can be interpreted that
 17 there exists a relationship between relative strength and equivalent age. However, in
 18 FBMs unlike concrete there is no crossover effect as was shown in Figure 11.
 19 Moreover, the limiting stiffness (Table 2) was found to have a nearly linear
 20 relationship with temperature. Therefore a temperature term is introduced into the
 21 equivalent age function (Eq. 16). The resulting function is Eq. 17. This equation is
 22 valid for isothermal curing. However, for variable temperature conditions, the
 23 equation becomes as shown in Eq. 18. This equation is analogous to the Nurse-Saul
 24 maturity function (Eq. 1) in which the time term (Δt) is replaced with equivalent time
 25 (Δt_e) and the datum temperature is 0°C.


$$26 \quad M = t_e * T = e^{B(T-T_r)} * t * T \quad \text{Equation 17}$$

$$27 \quad M = \sum_0^t \Delta t_e * T \quad \text{Equation 18}$$

28 Maturity using Eq. 17 was calculated and plotted against stiffness in Figure 16.
 29 The datum temperature (T_0) was assumed as 0°C as there is direct influence of water
 30 evaporation on the mixture stiffness gain. The figure clearly shows that the data points
 31 are grouped around a single curve whose equation is as in Eq. 19 which is the same
 32 equation as Eq. 10 except that the datum temperature was assumed as 0°C. The
 33 stiffness values were fitted to maturity values with Eq. 19 using the least squares curve
 34 fitting technique and the parameters E, E_u and k were obtained. The parameters
 35 obtained for all the mixtures considered in the present study are tabulated in Table 4.
 36

$$37 \quad E = E_u \frac{\sqrt{kM}}{1+\sqrt{kM}} \quad \text{Equation 19}$$

1

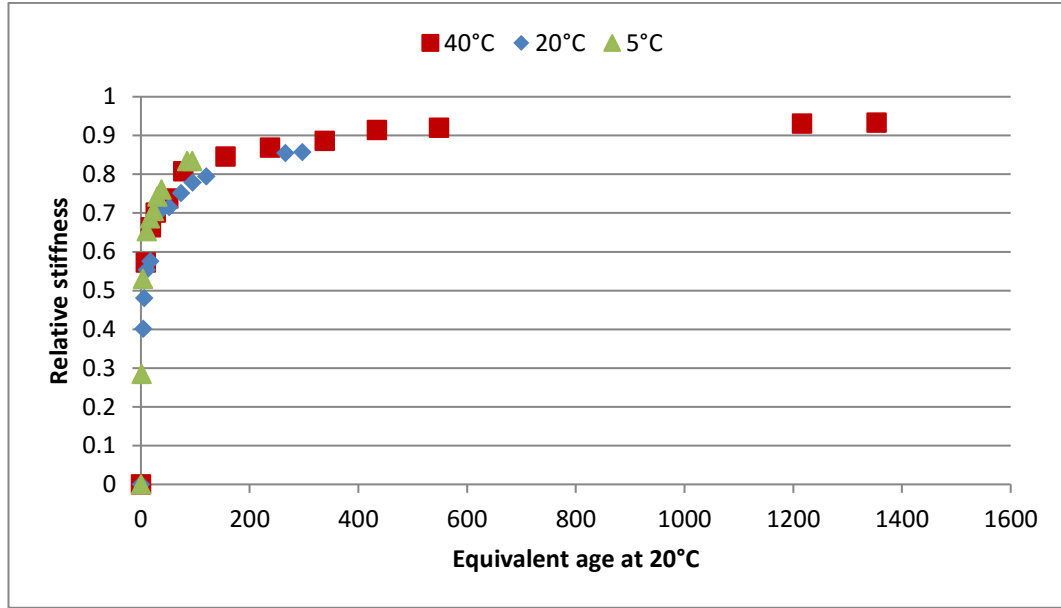


2

3

Figure 15 Relative stiffness versus equivalent age at 20°C for 50%RAP + 1% Cement – FBM

4

5

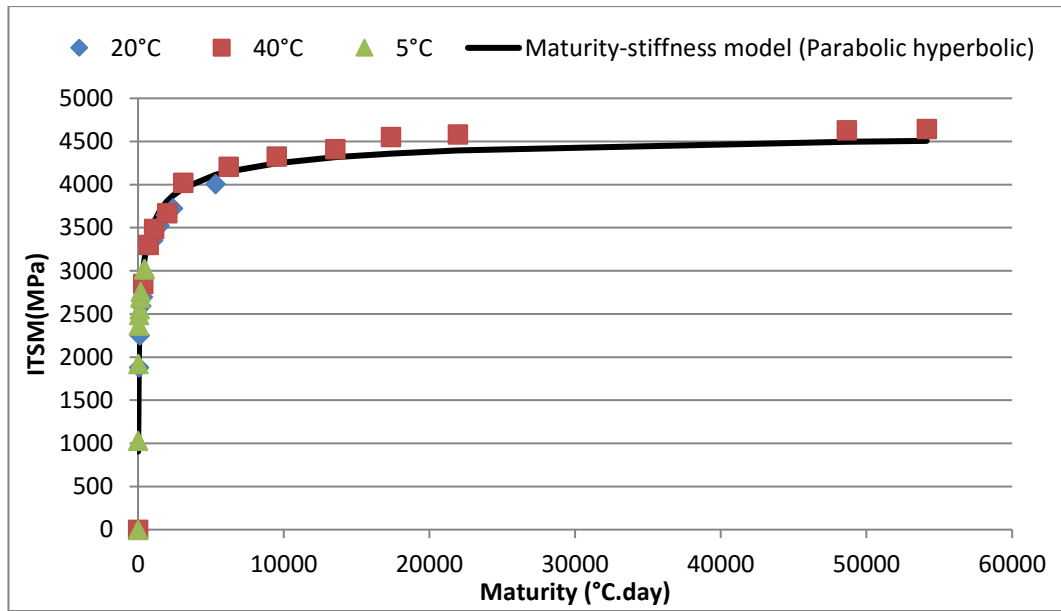

6

7

Figure 16 Maturity and stiffness relationship for 50%RAP + 1% Cement- FBM

8

Table 4 Parameters obtained for Maturity – Stiffness model


FBM - Type	E_u (MPa)	k (1/day)
50%RAP+1%Cement	4712	0.008
50%RAP	3187	0.011
0%RAP+1%Cement	4384	0.013
0%RAP	3764	0.002

1 **4.3 Validation of the method**

2 The experimental study also included validating the applicability of the maturity
3 – stiffness models to other temperatures (isothermal) that were not included while
4 developing the models. The study also tried to verify how well the model can account
5 for the effect of variations in temperature on FBM curing. For this, three conditions
6 namely short term (less than 10 days), intermediate (between 10 days and 35 days)
7 and long term (between 35 days and 300 days) were considered.
8


9 **4.3.1 Isothermal curing temperature**

10
11 For verifying isothermal condition, the ITSM test data that was obtained for the
12 curing mechanism study at 30°C was used. The stiffness (ITSM) data measured on the
13 specimens cured at 30°C obtained for short term and intermediate term was plotted
14 against the stiffness values obtained from the maturity-stiffness model that had been
15 developed (Figure 17 to Figure 20). From these figures, values corresponding to
16 ‘30°C-30°C’ are results for isothermal curing which indicate specimens were
17 conditioned at 30°C during the early stage (less than 7 days after compaction) and as
18 well as during the intermediate stage (between 10 days and 35 days). These figures
19 indicate that the maturity-stiffness model estimates the stiffness reasonably well in all
20 cases except for 50%RAP-FBM in which the model has overestimated slightly.
21

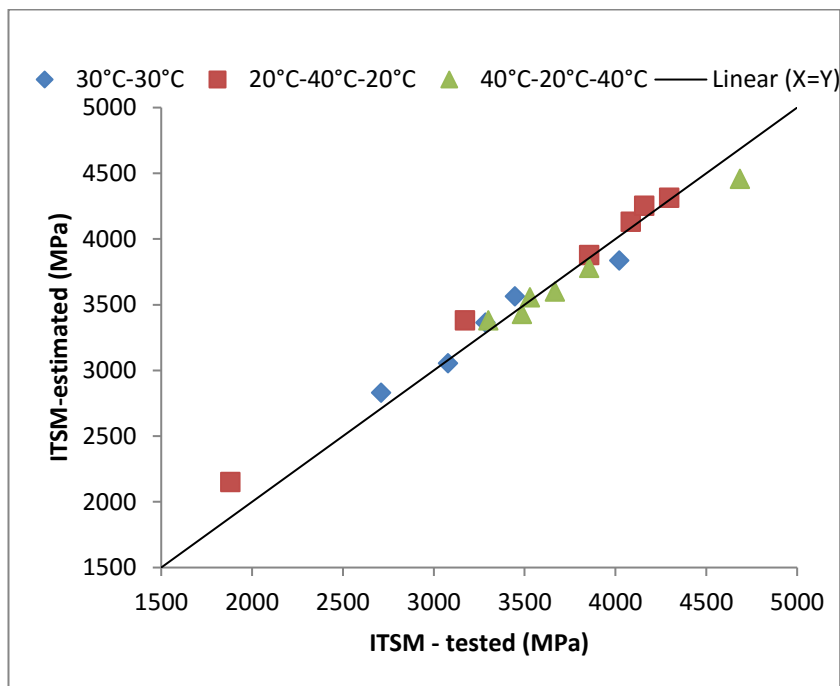


22
23 **Figure 17 Verification of Maturity - Stiffness model for 50%RAP + 1%Cement - FBM**

24

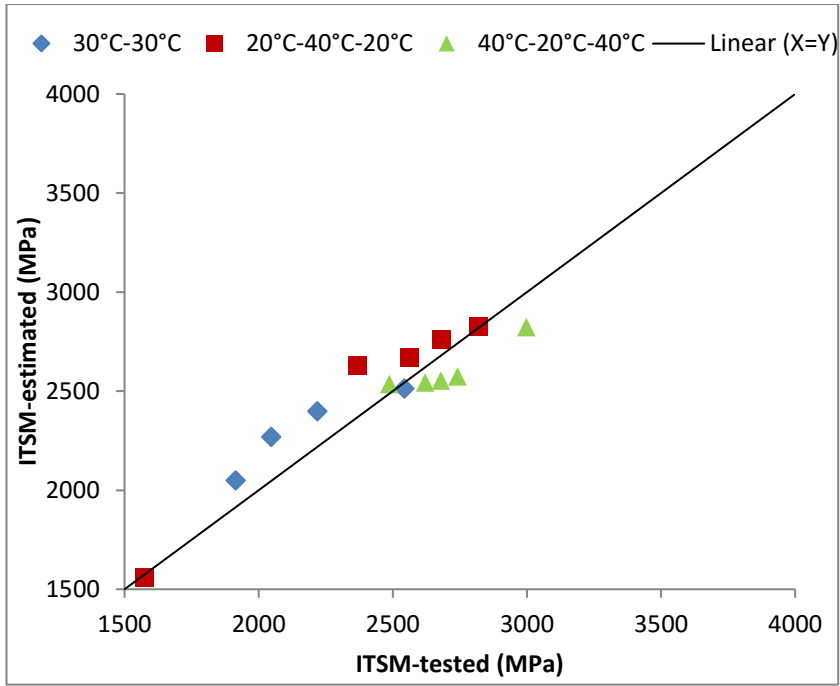


1
2 **Figure 18 Verification of Maturity - Stiffness model for 50%RAP – FBM**

3

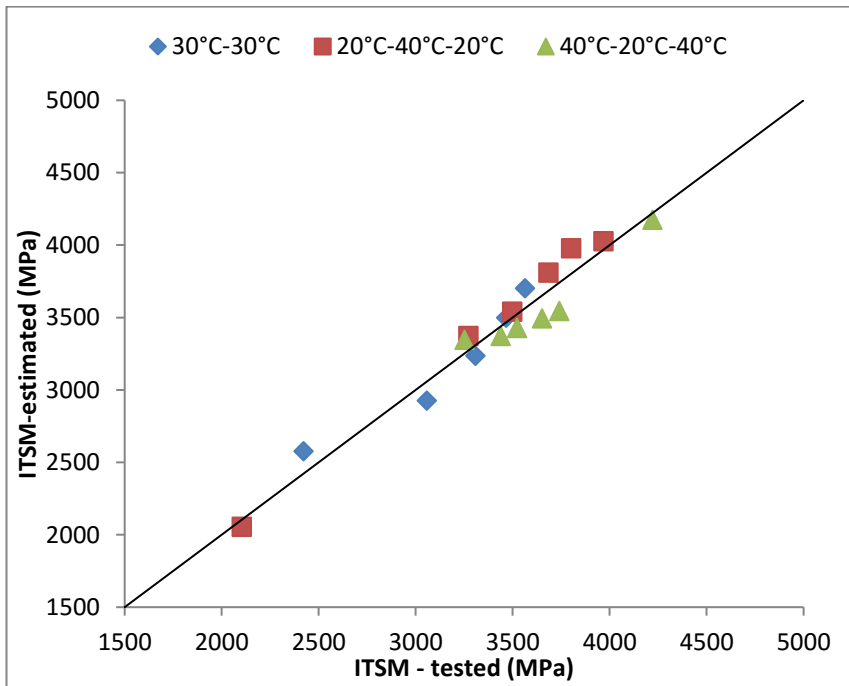

4
5 **Figure 19 Verification of Maturity - Stiffness model for 100%VA+1%Cement - FBM**

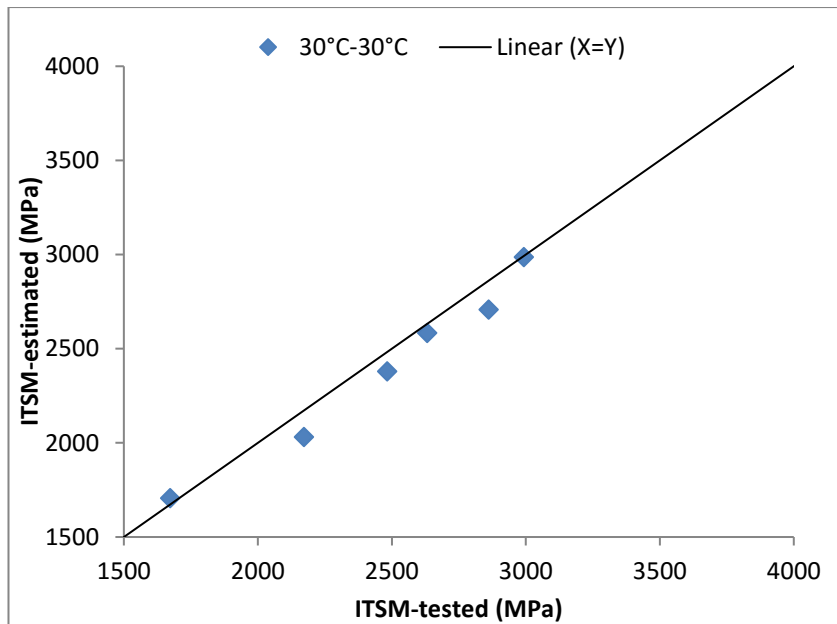

1
2 **Figure 20 Verification of Maturity - Stiffness model for 100% VA - FBM**

3 **4.3.2 Variable curing temperatures**

4
5 To verify how well the maturity-stiffness model addresses varying temperatures,
6 specimens were cured with two variable temperature conditioning sequences. The first
7 case is conditioning the specimens at 20°C during the early stage curing (up to 7 days
8 after compaction) and then changing to a 40°C cabinet to cure during the intermediate
9 stage (7 days to 35 days) and finally the specimen was transferred back to the 20°C
10 conditioning cabinet for long term curing. This conditioning sequence is termed as
11 '20°C-40°C-20°C'. Similarly the second sequence studied was 40°C-20°C-40°C. The
12 specimens were tested for ITSM at different intervals of time.

13 Table 5 presents the curing sequence for 20°C-40°C-20°C for
14 50% RAP+1% Cement-FBM. It also shows the calculations for maturity and from it the
15 stiffness values that were predicted. Maturity was calculated using Eq. 16 and Eq. 18.
16 Stiffness (ITSM) was estimated using Eq. 19 using corresponding values from Table
17 4 and maturity values. The first three values calculated in Table 5 are presented in
18 Figure 21 for comparison. The figure illustrates graphically the estimation of stiffness
19 comprising the tested value and estimated value for stiffness from the maturity-
20 stiffness model. As can be seen in the figure, the conditioning changed from 20°C
21 initially to 40°C at 4 days. The dotted lines in the figure demonstrate the actual path
22 of the stiffness increase for this particular sequence of curing. The figure suggests that
23 though the stiffness values obtained from the maturity-stiffness model were
24 marginally higher than the tested values, the model predicted the stiffness adequately
25 in the particular case of 50% RAP + 1% Cement FBM as can be seen in Figure 17.
26 Figure 18 and Figure 19 show how well the model predicted stiffness gain for variable
27 temperature conditions for 50% RAP and 100% VA + 1% Cement FBMs.


28 It is worth noting that the model slightly underestimated the stiffness of the
29 samples which were cured initially at 40°C and marginally overestimated specimens
30 that were cured at 20°C. Underestimation for the 40°C-20°C-40°C sequence could be
31 attributed to the slightly conservative nature of the model (Figure 16). The reason for
32 overestimation could probably be the failure of the mixture to gain stiffness at the rate
33 the model estimated after changing the conditioning temperature. This shortcoming

1 can also be seen in Figure 21. From the above discussion it can be stated that though
 2 estimated stiffness from the developed model marginally differs from the test results,
 3 they are close enough to state that the maturity approach provides a satisfactory basis
 4 for estimating the stiffness of FBMs. Furthermore, the model also quantifies the
 5 stiffness gain extremely well for varying temperature conditions.
 6

7 **Table 5 Maturity calculations for 20°C-40°C-20°C sequence of curing for**
 8 **50%RAP+1% Cement-FBM**

Curing sequence-20°C-40°C-20°C						
ITSM test (MPa)	Time (days)	Δt (days)	T (°C)	Δt_e (days)	Maturity (°C.day)	ITSM-Predicted (MPa)
1880	4	4	20	4	80	2152
3171	8	4	40	18	732	3382
3856	21	13	40	59	2458	3880
4084	39	18	40	82	5750	4133
4159	61	22	40	101	9773	4255
4295	242	181	20	181	13393	4316

9

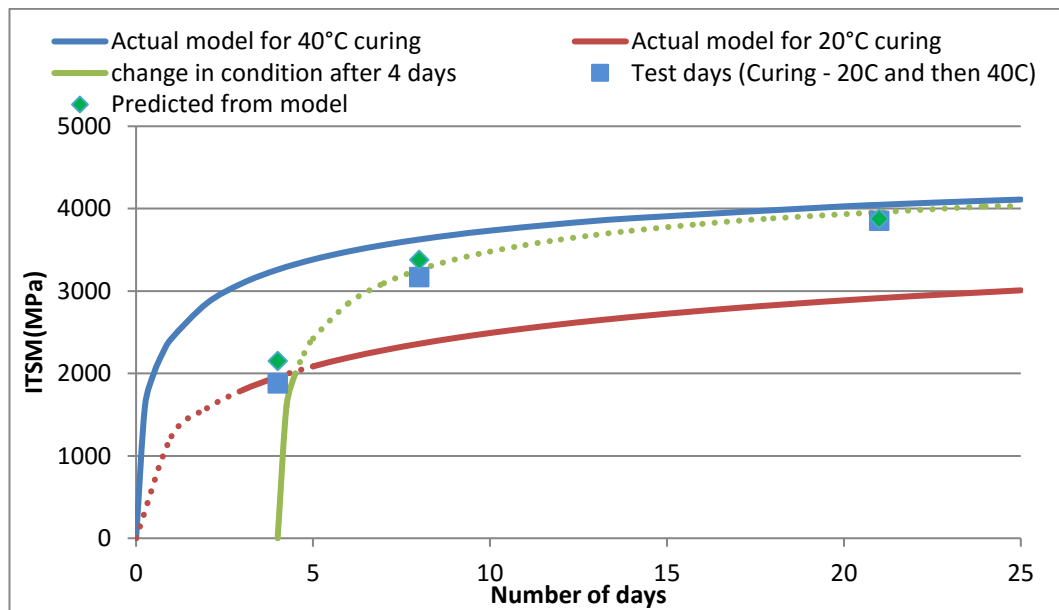

10


11 **Figure 21 Effect of temperature variation on stiffness (50%RAP + 1% Cement)**

12 **4.4 Practical implications**

13 As seen in the previous section the maturity method was found to be capable of
 14 estimating the stiffness under varying temperature conditions and it provides a tool to
 15 estimate in-situ stiffness after compaction of FBM layers. This method is particularly
 16 helpful to assess when the FBM layer can be covered with overlying layers if the in-
 17 situ temperature data is available. To explain the applicability of the maturity method
 18 three hypothetical pavement sections were considered. The locations were selected so
 19 that each represented moderate to cold temperature so as to evaluate the effect of
 20 ambient temperature on the stiffness gain of FBM. The temperature data was obtained
 21 from the National Climatic Data Centre (NCDC) website (www.ncdc.noaa.gov).
 22 Figure 22 presents the mean daily air temperatures for April, 2014 in the locations
 23 selected. It was assumed that the construction (compaction) of the FBM layer was


1 carried out on 1st of April and the mixture started gaining stiffness from the first day.
 2 The stiffness values for each day were calculated using the cumulative maturity
 3 approach as discussed in the previous section, assuming the temperature of the FBM
 4 to be the same as the air temperature.

5 The stiffness results estimated using the maturity method are presented in Figure
 6 23. For simplicity, the layer temperature was assumed to be same as the air
 7 temperature. However, for engineering purposes it is envisaged that pavement
 8 temperature models such as BELLS model could be used as an alternative. As
 9 expected the higher ambient temperatures resulted in higher stiffness values. The
 10 results show the stiffness trend for mixtures with 50%RAP, one with 1% Cement and
 11 the other without any cement, to explain the benefit of cement addition. These trends
 12 help in taking decisions regarding when the overlying layer can be placed on the FBM
 13 layer or when the traffic can be allowed on the pavement layer. For example if an
 14 agency requirement is to place the binder course or surface course over the FBM layer
 15 only if it reaches a stiffness of 1000MPa, in such circumstances these trends can be
 16 very helpful. Table 6 shows the effect of location and presence of cement on the
 17 number of days required to reach a stiffness of 1000MPa. As can be seen from the
 18 table both location and presence of cement significantly influence the stiffness trend
 19 and thus decisions such as trafficking and layer placements. For moderately warmer
 20 (Nottingham) and colder (Stockholm) conditions, the difference in days to reach
 21 1000MPa was found to be 7 days and 9 days respectively for mixtures with cement
 22 and without cement. The influence of the cement on the early stage of curing was
 23 significant as the difference between mixtures with cement and without cement for the
 24 colder condition (Stockholm) considered in the present study was as high as 13 days.
 25

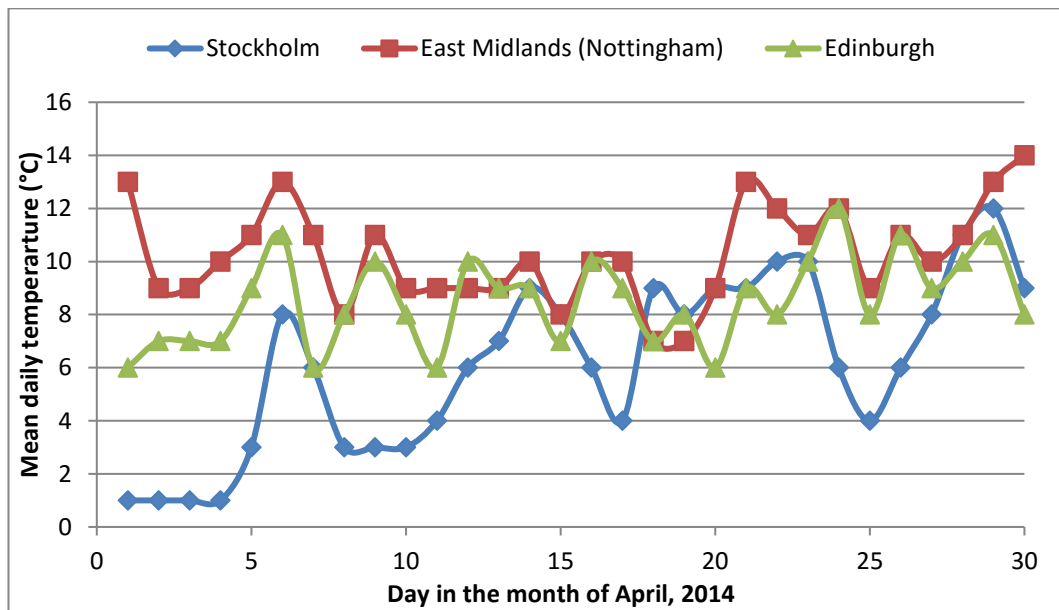

26
 27 **Figure 22 Mean daily temperatures for month of April, 2014 in locations considered in**
 28 **the study**

29
 30

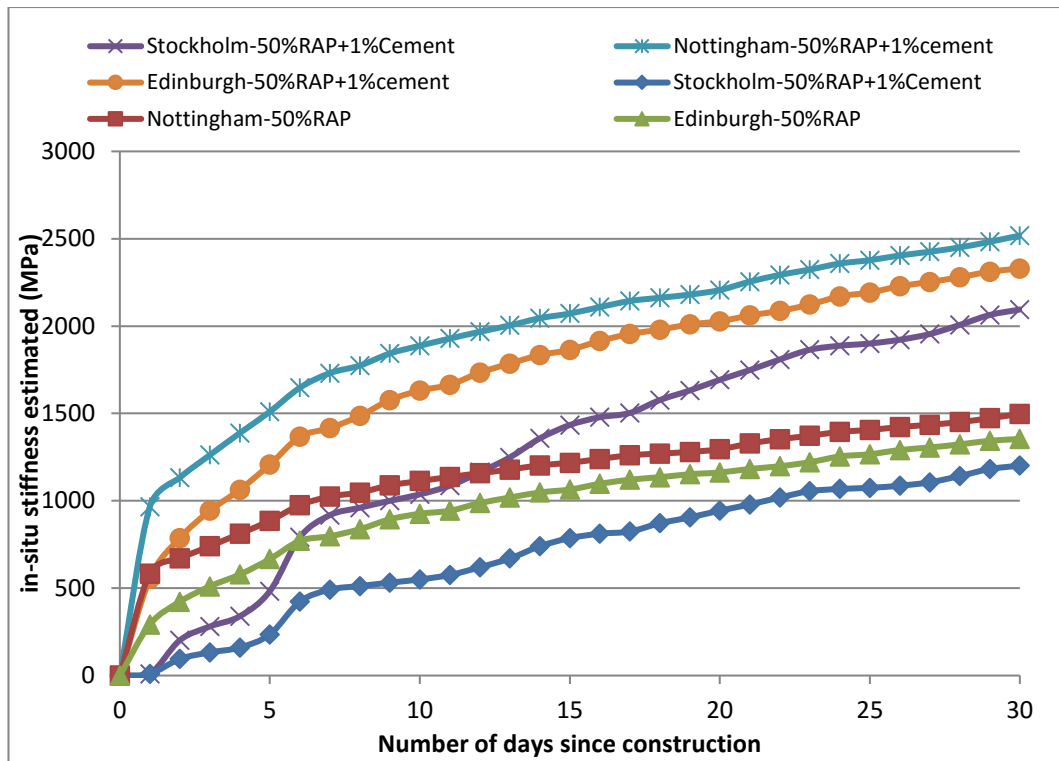

1
2 **Figure 23 Effect of location and cement on stiffness gain (hypothetical sections)**

3
4 **Table 6 Practical implication of maturity method**

Number of days to reach stiffness of 1000 MPa			
	Stockholm	Edinburgh	Nottingham
50%RAP + 1%Cement	9	4	2
50%RAP	22	13	7

5
6 It has been shown in the present paper that the maturity model which describes the
7 combined effect of time and temperature on curing can be used as an alternative to in-
8 situ water content specification to decide when a FBM layer can be overlaid with
9 subsequent pavement layers. However, in addition to time and temperature, relative
10 humidity and amount of rainfall are also important parameters that influence in-situ
11 curing. Therefore, it is advised that decisions should be made in conjunction with
12 relative humidity and precipitation data. It is also important to note that integrating the
13 effect of traffic load on the stiffness evolution into the maturity model was not in the
14 scope of the present paper. Clearly early-life trafficking has the potential to cause
15 irreversible damage and this should therefore ideally be incorporated into any
16 decision-making approach.

1

2 5 CONCLUSIONS

3 This study was intended to improve understanding of the curing mechanism of FBMs
4 and to lessen the gap between laboratory curing and field evolution of these mixtures. In
5 achieving this, a link was established between laboratory mix design and field performance by
6 evaluating applicability of the maturity method.

7 The study also aimed to understand the curing mechanism and to interpret the level of
8 impact that factors such as temperature and time have on the curing of FBMs. The effect of
9 these factors on curing was evaluated with reference to stiffness gain and water loss of
10 specimens made from these mixtures. The following observations were made:

- 11 • The temperature is as important a parameter as time, as temperature has a greater
12 influence on curing rate and also on bitumen properties.
- 13 • Higher curing temperatures resulted in higher rate of stiffness gain. This trend is not
14 only because of rapid water loss but also due to an increase in binder stiffness at
15 higher curing temperatures.

16 The study also evaluated the applicability of the maturity method as a tool to assess the in-
17 situ characteristics of FBM layers in the pavement. It was found that replacing the time term
18 with an equivalent age term in the maturity function aided in estimating stiffness rather than
19 relative stiffness. This was possible because of the characteristic curing of FBMs in which the
20 limiting stiffness that these mixtures reach strongly depends on the curing temperature at least
21 for the length of curing stages considered in the present study. A strong correlation was found
22 between maturity and the stiffness values obtained from the laboratory tests which resulted in
23 development of maturity-stiffness relationships. The application of the method to assess the in-
24 situ stiffness was presented using three hypothetical pavement sections. The results showed the
25 influence of ambient temperature and the importance of cement addition to FBMs.

26 REFERENCES

27

- 28 1. Jenkins, K.J., & Moloto, P. K. , *Technical memorandum: Updating bituminous stabilized*
29 *materials guidelines: Mix design report (Phase II Task 8: Curing Protocol: Validation)*. 2008,
30 Asphalt Academy: Pretoria.
- 31 2. Batista, F.A., De Lurdes Antunes, M., Mollenhauer, K., & McNally, C.. and I. *Building blocks*
32 *for a best practice guide on cold in place recycling*. in *5th Eurasphalt & Eurobitume Congress*.
33 2012. stanbul, Turkey.
- 34 3. Lee, D.Y. *Treating marginal aggregates and soil with foamed asphalt*. in *Association of*
35 *Asphalt Paving Technologists*. 1981.
- 36 4. Kim, Y., S. Im, and H.D. Lee, *Impacts of Curing Time and Moisture Content on Engineering*
37 *Properties of Cold In-Place Recycling Mixtures Using Foamed or Emulsified Asphalt*. *Journal*
38 *of Materials in Civil Engineering*, 2011. 23(5).
- 39 5. Tebaldi, G., et al., *Synthesis of standards and procedures for specimen preparation and in-field*
40 *evaluation of cold-recycled asphalt mixtures*. *Road Materials and Pavement Design*, 2014.
41 15(2): p. 272-299.
- 42 6. Kuna, K., G. Airey, and N. Thom, *Laboratory Mix Design Procedure for Foamed Bitumen*
43 *Mixtures*. 2014: Transportation Research Record: Journal of the Transportation Research
44 Board. p. 1–10.

1 7. Ojum, C., et al., *An Investigation into the Effects of Accelerated Curing on Cold Recycled*
2 *Bituminous Mixtures*, in *International Symposium of Asphalt Pavements*. 2014: Raleigh, North
3 Carolina. p. 1177-1188.

4 8. Leech, D., *Cold mix bituminous materials for use in structural layers of roads*. Crowthorne
5 (Berkshire, UK): ;, in *Transport Research Laboratory (TRL)*. 1994.

6 9. Doyle, T.A., et al., *Developing maturity methods for the assessment of cold-mix bituminous*
7 *materials*. *Construction and Building Materials*, 2013. 38(0): p. 524-529.

8 10. Carino, N.J. and H.S. Lew, *The Maturity Method: From Theory to Application*. 2001, Building
9 and Fire Research Laboratory National Institute of Standards and Technology:
10 Gaithersburg, USA.

11 11. Nixon, J.M., et al., *Evaluation of the Maturity Method to Estimate Concrete Strength in Field*
12 *Applications*, in *ALDOT Research Project 930-590*. 2008, Highway Research Center and
13 Department of Civil Engineering at Auburn University.

14 12. Thomas A. Doyle, C.M., Amanda Gibney, Amir Tabakovic, *Developing maturity methods for*
15 *the assessment of cold-mix bituminous materials*. *Construction and Building Materials*, 2013.
16 Volume 38: p. 524–529.

17 13. Malhotra, V.M. and N.J. Carino, *Handbook on Nondestructive Testing of Concrete Second*
18 *Edition*. 2003: CRC Press; 2 edition.

19 14. Hansen, P.F. and E.J. Pedersen, *Maturity Computer for Controlled Curing and Hardening of*
20 *Concrete*. 1977, Swedish National Road and Transport Research Institute (VTI). p. 21-25.

21 15. Carino, N.J., L.I. Knab, and J.R. Clifton, *Applicability of the Maturity Method to High-*
22 *Performance Concrete*, in *NISTIR-4819*. 1992, National Institute of Standards and Technology
23 (US): Springfield, VA.

24 16. Academy, A., *A Guideline for the Design and Construction of Bitumen Emulsion and Foamed*
25 *Bitumen Stabilised Materials*. 2009.

26 17. J. -P. Serfass, J.-E.P., J. -P. Henrat, X. Carbonneau, *Influence of curing on cold mix mechanical*
27 *performance*. *Materials and Structures*, 2004. 37(5): p. 365-368.

28 18. Carino, N., *The Maturity Method: Theory and Application*. *ASTM Journal of Cement, Concrete*
29 *and Aggregates*, 1984. 6(2).

30