



Redetermination of the crystal structure of β -zinc molybdate from single-crystal X-ray diffraction data

Olfa Mtioui-Sghaier,^a Rafael Mendoza-Meroño,^a Lilia Ktari,^b Mohamed Dammak^b and Santiago García-Granda^{a*}

^aDepartamento de Química Física y Analítica, Facultad de Química, Universidad de Oviedo-CINN, C/ Julián Clavería, 8, 33006 Oviedo, Spain, and ^bLaboratoire de Chimie Inorganique, Faculté des Sciences de Sfax, Route de Soukra, 3000 Sfax, Tunisia. *Correspondence e-mail: sgg@uniovi.es

Received 8 May 2015; accepted 21 June 2015

Edited by M. Weil, Vienna University of Technology, Austria

The crystal structure of the β -polymorph of ZnMoO_4 was redetermined on the basis of single-crystal X-ray diffraction data. In comparison with previous powder X-ray diffraction studies [Katikaneani & Arunachalam (2005). *Eur. J. Inorg. Chem.* pp. 3080–3087; Cavalcante *et al.* (2013). *Polyhedron*, **54**, 13–25], all atoms were refined with anisotropic displacement parameters, leading to a higher precision with respect to bond lengths and angles. β - ZnMoO_4 adopts the wolframite structure type and is composed of distorted ZnO_6 and MoO_6 octahedra, both with point group symmetry 2. The distortion of the octahedra is reflected by variation of bond lengths and angles from 2.002 (3)–2.274 (4) Å, 80.63 (11)–108.8 (2)° for equatorial and 158.4 (2)–162.81 (14)° for axial angles (ZnO_6), and of 1.769 (3)–2.171 (3) Å, 73.39 (16)–104.7 (2), 150.8 (2)–164.89 (15)° (MoO_6), respectively. In the crystal structure, the same type of MO_6 octahedra share edges to built up zigzag chains extending parallel to [001]. The two types of chains are condensed by common vertices into a framework structure. The crystal structure can alternatively be described as derived from a distorted hexagonally closed packed arrangement of the O atoms, with Zn and Mo in half of the octahedral voids.

Keywords: crystal structure; redetermination; β - ZnMoO_4 ; hydrothermal synthesis; wolframite structure type.

CCDC reference: 1408028

1. Related literature

Most molybdates of divalent cations crystallize either in the scheelite-type or in the wolframite-type (Macavei & Schulz,

1993). Zinc molybdate (ZnMoO_4) is an inorganic semiconductor. It adopts the wolframite-type of structure (Keeling, 1957) and is dimorphic. The two phases, referred to as α - (triclinic symmetry) and β - (monoclinic symmetry), can be selectively obtained by controlling the synthetic conditions (Abrahams *et al.*, 1967; Zhang *et al.*, 2010). Previous crystal structure refinements of β - ZnMoO_4 , based on X-ray powder diffraction data, were reported by Cavalcante *et al.* (2013) and Katikaneani & Arunachalam (2005). For structure refinement of ZnWO_4 , isotypic with the title compound, see: Trots *et al.* (2009).

2. Experimental

2.1. Crystal data

ZnMoO_4	$V = 131.98 (2) \text{ \AA}^3$
$M_r = 225.31$	$Z = 2$
Monoclinic, $P2_1/c$	Mo $K\alpha$ radiation
$a = 4.6980 (3) \text{ \AA}$	$\mu = 13.62 \text{ mm}^{-1}$
$b = 5.7380 (4) \text{ \AA}$	$T = 293 \text{ K}$
$c = 4.8960 (4) \text{ \AA}$	$0.08 \times 0.06 \times 0.03 \text{ mm}$
$\beta = 90.311 (7)^\circ$	

2.2. Data collection

Oxford Diffraction Xcalibur CCD diffractometer	1207 measured reflections
Absorption correction: multi-scan (<i>CrysAlis PRO</i> ; Oxford Diffraction, 2014)	405 independent reflections
$T_{\min} = 0.905$, $T_{\max} = 1.000$	358 reflections with $I > 2\sigma(I)$
	$R_{\text{int}} = 0.036$

2.3. Refinement

$R[F^2 > 2\sigma(F^2)] = 0.028$	29 parameters
$wR(F^2) = 0.068$	$\Delta\rho_{\text{max}} = 1.20 \text{ e \AA}^{-3}$
$S = 1.10$	$\Delta\rho_{\text{min}} = -1.17 \text{ e \AA}^{-3}$
405 reflections	

Data collection: *CrysAlis CCD* (Oxford Diffraction, 2014); cell refinement: *CrysAlis RED* (Oxford Diffraction, 2014); data reduction: *CrysAlis RED*; program(s) used to solve structure: *SIR2011* (Burla *et al.*, 2012); program(s) used to refine structure: *SHELXL2014* (Sheldrick, 2015); molecular graphics: *DIAMOND* (Brandenburg & Putz, 1999); software used to prepare material for publication: *WinGX* (Farrugia, 2012), *pubCIF* (Westrip, 2010) and *PARST* (Nardelli, 1995).

Acknowledgements

We acknowledge financial support from the Spanish Ministerio de Economía y Competitividad (MAT2013–40950-R), Gobierno del Principado de Asturias (GRUPIN14–060) and ERDF.

Supporting information for this paper is available from the IUCr electronic archives (Reference: WM5159).

References

- Abrahams, S. C. (1967). *J. Chem. Phys.* **46**, 2052–2063.
- Brandenburg, K. & Putz, H. (1999). *DIAMOND*. Crystal Impact GbR, Bonn, Allemagne.
- Burla, M. C., Caliandro, R., Camalli, M., Carrozzini, B., Cascarano, G. L., Giacovazzo, C., Mallamo, M., Mazzone, A., Polidori, G. & Spagna, R. (2012). *J. Appl. Cryst.* **45**, 357–361.
- Cavalcante, L. S., Moraes, E., Almeida, M. A. P., Dalmascio, C. J., Batista, N. C., Varela, J. A., Longo, E., Siu Li, M., Andrés, J. & Beltrán, A. (2013). *Polyhedron*, **54**, 13–25.
- Farrugia, L. J. (2012). *J. Appl. Cryst.* **45**, 849–854.
- Katikaneani, P. & Arunachalam, R. (2005). *Eur. J. Inorg. Chem.* pp. 3080–3087.
- Keeling, R. O. (1957). *Acta Cryst.* **10**, 209–213.
- Macavei, J. & Schulz, H. (1993). *Z. Kristallogr.* **207**, 193–208.
- Nardelli, M. (1995). *J. Appl. Cryst.* **28**, 659.
- Oxford Diffraction (2014). *CrysAlis PRO*, *CrysAlis CCD* and *CrysAlis RED*. Oxford Diffraction Ltd., Abingdon, England.
- Sheldrick, G. M. (2015). *Acta Cryst.* **C71**, 3–8.
- Trots, D. M., Senyshyn, A., Vasylechko, L., Niewa, R., Vad, T., Mikhailik, V. B. & Kraus, H. (2009). *J. Phys. Condens. Matter*, **21**, 325402.
- Westrip, S. P. (2010). *J. Appl. Cryst.* **43**, 920–925.
- Zhang, G., Yu, S., Yang, Y., Jiang, W., Zhang, S. & Huang, B. (2010). *J. Cryst. Growth*, **312**, 1866–1874.

supporting information

Acta Cryst. (2015). E71, i6–i7 [doi:10.1107/S205698901501186X]

Redetermination of the crystal structure of β -zinc molybdate from single-crystal X-ray diffraction data

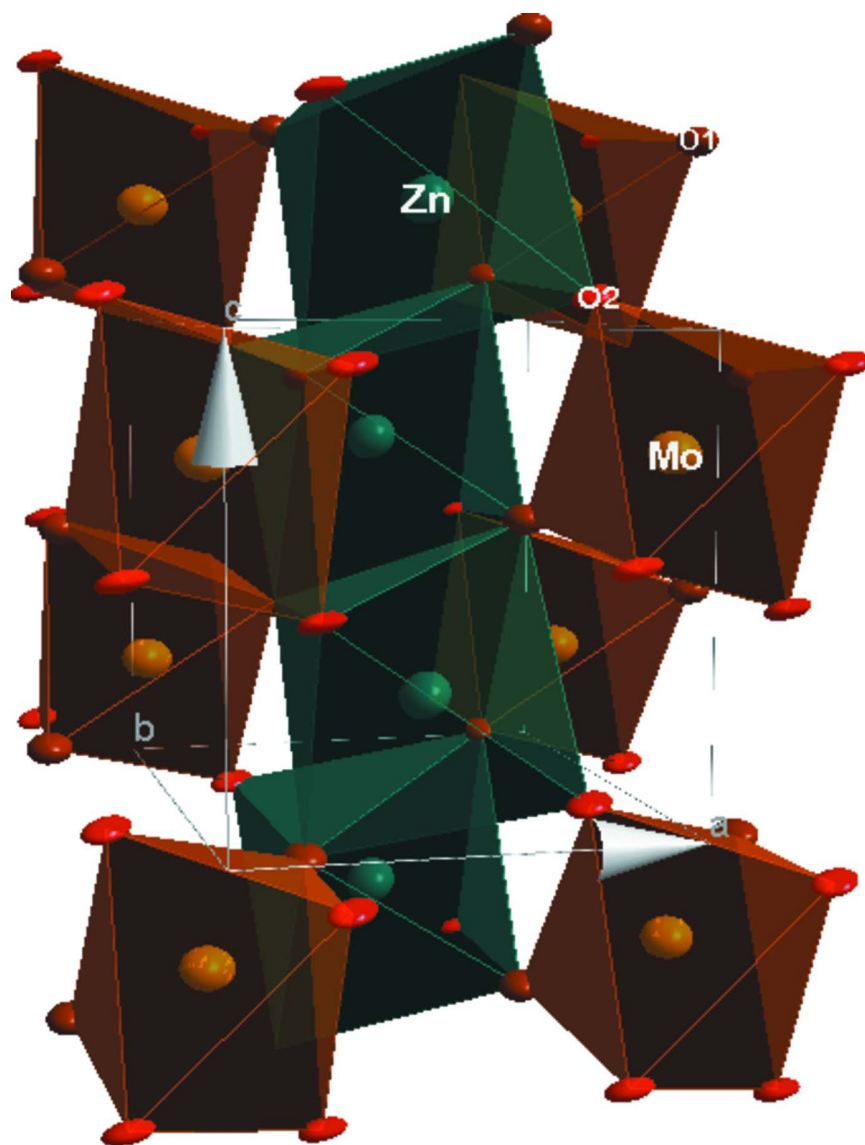
Olfa Mtioui-Sghaier, Rafael Mendoza-Meroño, Lilia Ktari, Mohamed Dammak and Santiago García-Granda

S1. Synthesis and crystallization

Reagents were used as commercial sources with no further purification. An aqueous solution was prepared by a mixture of 0.047 g 2,2'-bipyridine, 0.015 g of molybdenum trioxide and 0.043 g of zinc acetate in 10 ml water. The reaction mixture was stirred at room temperature to homogeneity, then transferred into a teflon-lined stainless steel vessel (40 ml) and heated to 453 K for 48 h under autogenous pressure and after-wards cooled slowly to room temperature. The resulting material was obtained as colorless single-crystals without side products. The solid was filtered off, washed thoroughly with distilled water, and finally air-dried at room temperature.

S2. Refinement

The remaining maximum and minimum electron densities were found 0.77 Å and 0.90 Å, respectively, from the O1 atom. O1 is located on the center of a tree-metal triangle, bridging one Mo and two Zn atoms.

**Figure 1**

A view of the crystal structure of β -ZnMoO₄. Anisotropic displacement parameters are drawn at the 50% probability level.

β -Zinc molybdate

Crystal data

MoO₄Zn

$M_r = 225.31$

Monoclinic, $P2_1/c$

$a = 4.6980$ (3) Å

$b = 5.7380$ (4) Å

$c = 4.8960$ (4) Å

$\beta = 90.311$ (7)°

$V = 131.98$ (2) Å³

$Z = 2$

$F(000) = 208$

$D_x = 5.670$ Mg m⁻³

Mo $K\alpha$ radiation, $\lambda = 0.71073$ Å

Cell parameters from 570 reflections

$\theta = 3.6$ – 31.1 °

$\mu = 13.62$ mm⁻¹

$T = 293$ K

Prism, colourless

$0.08 \times 0.06 \times 0.03$ mm

Data collection

Oxford Diffraction Xcalibur CCD diffractometer	1207 measured reflections
Radiation source: Enhance (Mo) X-ray Source	405 independent reflections
Detector resolution: 10.2673 pixels mm ⁻¹	358 reflections with $I > 2\sigma(I)$
ω - and φ -scans	$R_{\text{int}} = 0.036$
Absorption correction: multi-scan (<i>CrysAlis PRO</i> ; Oxford Diffraction, 2014)	$\theta_{\text{max}} = 31.3^\circ$, $\theta_{\text{min}} = 3.6^\circ$
$T_{\text{min}} = 0.905$, $T_{\text{max}} = 1.000$	$h = -6 \rightarrow 6$
	$k = -8 \rightarrow 8$
	$l = -6 \rightarrow 6$

Refinement

Refinement on F^2	0 restraints
Least-squares matrix: full	$w = 1/[\sigma^2(F_o^2) + (0.0209P)^2 + 0.5403P]$
$R[F^2 > 2\sigma(F^2)] = 0.028$	where $P = (F_o^2 + 2F_c^2)/3$
$wR(F^2) = 0.068$	$(\Delta/\sigma)_{\text{max}} < 0.001$
$S = 1.10$	$\Delta\rho_{\text{max}} = 1.20 \text{ e } \text{\AA}^{-3}$
405 reflections	$\Delta\rho_{\text{min}} = -1.17 \text{ e } \text{\AA}^{-3}$
29 parameters	

Special details

Geometry. All e.s.d.'s (except the e.s.d. in the dihedral angle between two l.s. planes) are estimated using the full covariance matrix. The cell e.s.d.'s are taken into account individually in the estimation of e.s.d.'s in distances, angles and torsion angles; correlations between e.s.d.'s in cell parameters are only used when they are defined by crystal symmetry. An approximate (isotropic) treatment of cell e.s.d.'s is used for estimating e.s.d.'s involving l.s. planes.

Fractional atomic coordinates and isotropic or equivalent isotropic displacement parameters (\AA^2)

	<i>x</i>	<i>y</i>	<i>z</i>	$U_{\text{iso}}^*/U_{\text{eq}}$
Mo1	1.0000	0.81190 (10)	0.2500	0.00507 (18)
Zn1	1.5000	0.69182 (15)	0.7500	0.0092 (2)
O1	1.2538 (7)	0.6236 (6)	0.4014 (7)	0.0080 (7)
O2	0.7835 (7)	0.8950 (6)	0.5603 (7)	0.0058 (7)

Atomic displacement parameters (\AA^2)

	U^{11}	U^{22}	U^{33}	U^{12}	U^{13}	U^{23}
Mo1	0.0065 (3)	0.0045 (3)	0.0041 (3)	0.000	-0.0002 (2)	0.000
Zn1	0.0087 (4)	0.0116 (4)	0.0073 (4)	0.000	0.0009 (3)	0.000
O1	0.0089 (17)	0.0110 (16)	0.0041 (17)	0.0006 (14)	0.0003 (13)	-0.0004 (14)
O2	0.0088 (16)	0.0064 (14)	0.0021 (16)	-0.0005 (13)	0.0016 (12)	-0.0010 (13)

Geometric parameters (\AA , $^\circ$)

Mo1—O1 ⁱ	1.769 (3)	Zn1—O2 ^{iv}	2.002 (3)
Mo1—O1	1.769 (3)	Zn1—O2 ^v	2.002 (3)
Mo1—O2	1.894 (3)	Zn1—O1 ^{vi}	2.094 (3)
Mo1—O2 ⁱ	1.894 (3)	Zn1—O1	2.094 (3)
Mo1—O2 ⁱⁱ	2.171 (3)	Zn1—O1 ^{vii}	2.274 (4)
Mo1—O2 ⁱⁱⁱ	2.171 (3)	Zn1—O1 ^{viii}	2.274 (4)
O1 ⁱ —Mo1—O1	104.7 (2)	O2 ^{iv} —Zn1—O1	95.54 (14)

O1 ⁱ —Mo1—O2	97.25 (15)	O2 ^v —Zn1—O1	96.96 (14)
O1—Mo1—O2	100.46 (15)	O1 ^{vi} —Zn1—O1	158.4 (2)
O1 ⁱ —Mo1—O2 ⁱ	100.46 (15)	O2 ^{iv} —Zn1—O1 ^{vii}	162.81 (14)
O1—Mo1—O2 ⁱ	97.25 (15)	O2 ^v —Zn1—O1 ^{vii}	88.37 (13)
O2—Mo1—O2 ⁱ	150.8 (2)	O1 ^{vi} —Zn1—O1 ^{vii}	82.25 (14)
O1 ⁱ —Mo1—O2 ⁱⁱ	164.89 (14)	O1—Zn1—O1 ^{vii}	80.63 (11)
O1—Mo1—O2 ⁱⁱ	88.90 (14)	O2 ^{iv} —Zn1—O1 ^{viii}	88.37 (13)
O2—Mo1—O2 ⁱⁱ	73.39 (16)	O2 ^v —Zn1—O1 ^{viii}	162.81 (14)
O2 ⁱ —Mo1—O2 ⁱⁱ	84.01 (11)	O1 ^{vi} —Zn1—O1 ^{viii}	80.63 (11)
O1 ⁱ —Mo1—O2 ⁱⁱⁱ	88.90 (14)	O1—Zn1—O1 ^{viii}	82.24 (14)
O1—Mo1—O2 ⁱⁱⁱ	164.89 (15)	O1 ^{vii} —Zn1—O1 ^{viii}	74.53 (18)
O2—Mo1—O2 ⁱⁱⁱ	84.01 (11)	Mo1—O1—Zn1	126.54 (19)
O2 ⁱ —Mo1—O2 ⁱⁱⁱ	73.39 (16)	Mo1—O1—Zn1 ^{viii}	133.83 (18)
O2 ⁱⁱ —Mo1—O2 ⁱⁱⁱ	78.49 (18)	Zn1—O1—Zn1 ^{viii}	97.75 (14)
O2 ^{iv} —Zn1—O2 ^v	108.8 (2)	Mo1—O2—Zn1 ^{ix}	125.93 (18)
O2 ^{iv} —Zn1—O1 ^{vi}	96.96 (14)	Mo1—O2—Mo1 ⁱⁱ	106.61 (16)
O2 ^v —Zn1—O1 ^{vi}	95.54 (14)	Zn1 ^{ix} —O2—Mo1 ⁱⁱ	124.32 (17)

Symmetry codes: (i) $-x+2, y, -z+1/2$; (ii) $-x+2, -y+2, -z+1$; (iii) $x, -y+2, z-1/2$; (iv) $x+1, y, z$; (v) $-x+2, y, -z+3/2$; (vi) $-x+3, y, -z+3/2$; (vii) $x, -y+1, z+1/2$; (viii) $-x+3, -y+1, -z+1$; (ix) $x-1, y, z$.