



UNIVERSITY  
OF WOLLONGONG  
AUSTRALIA

University of Wollongong  
Research Online

---

Australian Institute for Innovative Materials - Papers

Australian Institute for Innovative Materials

---

2016

# Seed mediated one-pot growth of versatile heterogeneous upconversion nanocrystals for multimodal bioimaging

Shihui Wen

*University of Technology, Sydney*

Du Li

*Macquarie University, Donghua University, University of Technology, Sydney*

Deming Liu

*University of Technology Sydney, Macquarie University*

Xiaoxue Xu

*Macquarie University, University of Technology Sydney*

Yi Du

*University of Wollongong, ydu@uow.edu.au*

*See next page for additional authors*

---

## Publication Details

Wen, S., Li, D., Liu, D., Xu, X., Du, Y., Mitchell, D. R. G., Shi, B., Shi, X. & Jin, D. (2016). Seed mediated one-pot growth of versatile heterogeneous upconversion nanocrystals for multimodal bioimaging. SPIE - International Society for Optical Engineering. Proceedings, 10013 1001315-1-1001315-7.

Research Online is the open access institutional repository for the University of Wollongong. For further information contact the UOW Library: [research-pubs@uow.edu.au](mailto:research-pubs@uow.edu.au)

---

# Seed mediated one-pot growth of versatile heterogeneous upconversion nanocrystals for multimodal bioimaging

## Abstract

The rapid development of a variety of molecular contrast agents makes the multimodality bioimaging highly attractive towards higher resolution, more sensitive, informative diagnosis. The key lies in the development of facile material synthesis that allows the integration of multiple contrast agents, ideally in a way that each of the components should be logically assembled to maximize their performances. Here, we report the one-pot programmable growth of multifunctional heterogeneous nanocrystal with tunable size, shape, composition, and properties. We demonstrated a facile one-pot hot-injection method to enable the highly selectively controlled growth of different sodium lanthanide fluoride nanomaterials in either longitudinal or transversal directions with atomic scale precision. This technique allows the upconversion luminescence signal, MRI signal and x-ray signal logically integrated and optimized within one single versatile nanoplatform for multimode bioimaging. These findings suggest that the facile strategy developed here have the promising to get the desired heterogeneous nanocrystals as an all-in-one contrast agent for integrated and self-correlative multimodal bioimaging.

## Keywords

upconversion, one-pot, nanocrystals, seed, growth, versatile, mediated, heterogeneous, bioimaging, multimodal

## Disciplines

Engineering | Physical Sciences and Mathematics

## Publication Details

Wen, S., Li, D., Liu, D., Xu, X., Du, Y., Mitchell, D. R. G., Shi, B., Shi, X. & Jin, D. (2016). Seed mediated one-pot growth of versatile heterogeneous upconversion nanocrystals for multimodal bioimaging. SPIE - International Society for Optical Engineering. Proceedings, 10013 1001315-1-1001315-7.

## Authors

Shihui Wen, Du Li, Deming Liu, Xiaoxue Xu, Yi Du, David R. G Mitchell, Bingyang Shi, Xiangyang Shi, and Dayong Jin

# Seed Mediated One-pot Growth of Versatile Heterogeneous Upconversion Nanocrystals for Multimodal Bioimaging

Shihui Wen<sup>1,3</sup>, Du Li<sup>1,2,3,4</sup>, Deming Liu<sup>1,2,3</sup>, Xiaoxue Xu<sup>1,2,3</sup>, Yi Du<sup>5</sup>, David R. G. Mitchell<sup>6</sup>, Bingyang Shi<sup>3,7</sup>, Xiangyang Shi<sup>4</sup>, Dayong Jin<sup>1,2,3\*</sup>

<sup>1</sup>Institute for Biomedical Materials and Devices, Faculty of Science, University of Technology Sydney, NSW, 2007, Australia; <sup>2</sup>ARC Research Hub for Integrated Device for End-user Analysis at Low-levels (IDEAL), Faculty of Science, University of Technology, Sydney, New South Wales 2007, Australia; <sup>3</sup>Advanced Cytometry Labs, ARC Centre of Excellence for Nanoscale BioPhotonics, Macquarie University, Sydney, NSW, 2109, Australia; <sup>4</sup>State Key Laboratory for Modification of Chemical Fibers and Polymer Materials, College of Materials Science and Engineering, Donghua University, Shanghai 201620, People's Republic of China; <sup>5</sup>Institute for Superconducting and Electronic Materials, Innovation Campus, University of Wollongong, NSW, 2522, Australia; <sup>6</sup>Australian Institute for Innovative Materials (AIIM), Innovation Campus, University of Wollongong, North Wollongong, NSW, 2522, Australia; <sup>7</sup>Faculty of Medicine & Health Sciences, Macquarie University, Sydney, NSW, 2109, Australia

\*Corresponding author: dayong.jin@uts.edu.au (D. Jin)

## ABSTRACT:

The rapid development of a variety of molecular contrast agents makes the multimodality bioimaging highly attractive towards higher resolution, more sensitive, informative diagnosis. The key lies in the development of facile material synthesis that allows the integration of multiple contrast agents, ideally in a way that each of the components should be logically assembled to maximize their performances. Here, we report the one-pot programmable growth of multifunctional heterogeneous nanocrystal with tunable size, shape, composition, and properties. We demonstrated a facile one-pot hot-injection method to enable the highly selectively controlled growth of different sodium lanthanide fluoride nanomaterials in either longitudinal or transversal directions with atomic scale precision. This technique allows the upconversion luminescence signal, MRI signal and x-ray signal logically integrated and optimized within one single versatile nanoplatform for multimode bioimaging. These findings suggest that the facile strategy developed here have the promising to get the desired heterogeneous nanocrystals as an all-in-one contrast agent for integrated and self-correlative multimodal bioimaging.

## KEYWORDS:

Upconversion nanocrystals, one-pot synthesis, heterogeneous growth, partitioned doping, multimode imaging

## 1. INTRODUCTION

The rapid development of the molecular imaging technology makes the multimodality imaging is possible to circumvent the limitations of single imaging modes and provide more sensitive and accurate diagnosis.<sup>1,2</sup> For example, multimodality single-photon emission computed tomography (SPECT)/X-ray computed tomography (CT) imaging technology was introduced in 1977 and widely used in clinical diagnosis. However, the performance of the multimode imaging is strongly determined by the usage of the contrast agent, apart from the improvement in the instrument and methodology.<sup>3-5</sup> Therefore, the development of flexible multimodal platform which allows selection of the imaging modality to be used has evoked considerable interest.<sup>1,6-9</sup>

For multimodal contrast agents design, lanthanide doped upconverting nanoparticles (UCNPs) have created tremendous excitement due to their incomparable advantages such as improved deep tissue penetration and zero auto-fluorescence.<sup>9-16</sup> Apart from these excellent optical imaging applications, UCNPs could also be used as magnetic resonance (MR) and CT contrast agent due to the high attenuation and magnetic properties of some lanthanide ions. In particular, for MR imaging, NaGdF<sub>4</sub>- or KMnF<sub>3</sub>-based  $T_1$  MR contrast agents and NaDyF<sub>4</sub>-based  $T_2$  MR contrast agents have been designed for imaging applications.<sup>17, 18</sup> For CT imaging applications, all the lanthanide elements have the higher attenuation than the clinical used Iodine-based CT contrast agents. Therefore, most of multifunctional UCNPs were successfully formed for dual/triplet bioimaging, which makes it possible to get complementary in vivo information from different imaging modalities with a single administration. Even much effort has been dedicated, most of the formed agents are just the “mixture” of the different imaging agent for multimodal imaging.<sup>9</sup> To fulfill the advantage of the different imaging modals, it is essential to design and fabricate the integrated agent with different agent sitting in their advantage placement with atomic scale precision. For instance, NaGdF<sub>4</sub> should be put on the surface of the final particles due to its surface Gd ions are the major contributors to the relaxivity enhancement, while NaYF<sub>4</sub>, Yb,Er should be in the central of the particle to enhance the luminescence. Also, Dy should be away from the Yb or Er due to its quench effect, for CT imaging Lu has the highest attenuation and could be put in any place. However, the development of a programmable diversity of nanomaterials with the desired functionalities and performance has always been the challenge for chemists and material scientists.

In this present study, we developed a synthesis strategy capable of engineering the architecture of heterogeneous UCNPs through rational and independent programming of every architecture-determining element. The shape, size and the element spatial arrangement could be well controlled. Through facile one-pot hot-injection method, programmable heterogeneous nanocrystals (including nanorod, nanodumbbell, and nanoring-coated-dumbbell) were formed via controlled selective growth of different sodium lanthanide fluoride nanocrystals in site and direction. The formed partitioned heterogeneous nanocrystals afford their uses as nanoplatform for multimode CT/MR/UCL imaging to fulfill their advantages in biomedicine.

## 2. EXPERIMENTAL SECTION

UCNPs had been synthesized according to our previously reported method.<sup>11, 19</sup> The longitudinal growth of NaREF<sub>4</sub> onto the core of NaYF<sub>4</sub>:Yb,Er NCs was conducted via a successive layer-by-layer hot-injection protocol. Firstly, shell precursors were prepared. 1.0 mmol YCl<sub>3</sub>·6H<sub>2</sub>O were added to a 50 mL flask containing oleic acid (OA, 6.5 mL) and 1-octadecene (ODE, 15 mL). The mixture was heated to 170 °C under argon for 30 min to obtain a clear solution and then cooled down to about 50 °C, followed by the addition of 5 mL methanol solution of NH<sub>4</sub>F (4.0 mmol) and NaOH (2.5 mmol) and 3 mL methanol solution of KOH (2.0 mmol). After stirring for 30 min, the solution was heated to 80 °C under argon for 20 min to remove methanol, and then the solution was further heated to 150 °C for another 30 min. Finally, the reaction solution was cooled down to room temperature and labeled as NaYF<sub>4</sub> shell precursors. Similarly, the NaGdF<sub>4</sub> and NaDyF<sub>4</sub> shell precursors were synthesized using 1.0 mmol GdCl<sub>3</sub>·6H<sub>2</sub>O and 1.0 mmol DyCl<sub>3</sub>·6H<sub>2</sub>O, instead of YCl<sub>3</sub>·6H<sub>2</sub>O. For the longitudinal growth of NaYF<sub>4</sub>, 0.2 mmol NaYF<sub>4</sub>:Yb,Er core particles were added to a 50 mL flask containing 3 mL OA, 7 mL ODE, 69 mg NaOH, and 77 mg KOH. The mixture was heated to 170 °C under argon for 30 min, and then the solution was further heated to 310 °C. After that, 0.5 mL of NaYF<sub>4</sub> shell precursors were immediately injected into the reaction mixture and ripened at 310 °C for 5 min followed by the same injection and ripening cycles for 20 times. Finally, the reaction solution was cooled down to room temperature and the formed nanorods were purified according to the procedures used for the purification of NaYF<sub>4</sub>:Yb,Er core particles.

For the nanodumbbell synthesis, the NaYF<sub>4</sub>:Yb,Er@NaLuF<sub>4</sub>@NaDyF<sub>4</sub> rods were first formed according to method 2.3. Then 0.15 mmol GdCl<sub>3</sub> were added to a 50 mL flask with 6 mL OA and 6 mL ODE. The mixture was heated to 170 °C under argon for 30 min to obtain a clear solution and cooled down to about 50 °C, followed by the addition of 4 mL methanol solution of NH<sub>4</sub>F (0.6 mmol), NaOH (0.15 mmol) and KOH (0.12 mmol). After stirring for 30 min, the formed NaYF<sub>4</sub>:Yb,Er@NaLuF<sub>4</sub>@NaDyF<sub>4</sub> rods (0.05 mmol in cyclohexane) were added and the solution was heated to 80 °C under argon for 20 min to remove methanol and cyclohexane, and then the solution was further heated to 310 °C for another 90 min. Finally, the reaction solution was cooled down to room temperature and the formed nanoplate were purified according to the procedures used for the purification of NaYF<sub>4</sub>:Yb,Er core particles. In terms of the nanoring-coated-nanodumbbell synthesis, the methods were similar with the nanodumbbell synthesis, except the 0.1875 mmol of NaOH was used and without the addition of KOH.

### 3. RESULTS AND DISCUSSION

The UCNPs nanostructure design for multimodal imaging is depicted in Figure 1. A bamboo structure nanoparticle platform was employed to host upconverting luminescence, T2-based MR imaging, T1-based MR imaging as well as CT imaging contrast agents at different parts. A facile seed-mediated one-pot hot-inject method was used to synthesis our versatile heterogeneous materials through controlled longitudinal heterogeneous growth of appropriate lanthanide ions. As a result, incompatible optical, MR, and CT imaging agents can be programmable engineered for flexible and efficient multimodal imaging applications.

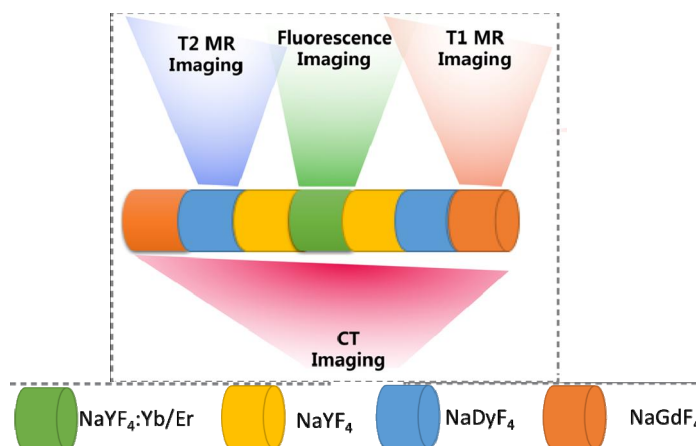


Figure 1. Schematic structure of the designed UCNPs through longitudinal epitaxial growth for multimode imaging

As a proof-of-concept experiment, we employed a seven-section  $\text{NaYF}_4, \text{Yb, Er-NaYF}_4\text{-NaDyF}_4\text{-NaGdF}_4$  nanocrystals in a bamboo shape by longitudinal controlled growth.  $\text{NaYF}_4, \text{Yb, Er}$  in the core site was employed for luminescence imaging  $\text{Yb}^{3+}$  and  $\text{Er}^{3+}$  harvest the NIR excitations. Then, a section of  $\text{NaYF}_4$  was chosen to separate  $\text{Yb}^{3+}/\text{Er}^{3+}$  with  $\text{Dy}^{3+}$  (T2-based MR imaging) to avoid the quenching by cross-relaxation. Finally,  $\text{NaGdF}_4$  was chosen as the outer parts for better T1-based MR contrast effect due to its the surface  $\text{Gd}^{3+}$  are the major contributors to the imaging enhancement.

The seed nanoparticle ( $\text{NaYF}_4:20\%\text{Yb}, 2\%\text{Er}$ ) with the diameter around 25 nm (Figure 2a) had been first synthesized for the further controlled growth. Transmission electron microscopy (TEM) micrographs (Figure 1b-d) confirmed that the epitaxial growth of shells in the longitudinal direction of the core. After the  $\text{NaYF}_4$  controlled growth, apparent rod-like shape structures with the length of 42 nm were obtained, different from the core with the quasi-sphere morphology. Further, the length of nanorods increased to 57 and 70 nm after the further growth of  $\text{NaDyF}_4$  and  $\text{NaGdF}_4$ , respectively. It is notable that the width of the nanocrystals did not show any apparent changes and remained at around 25 nm for the whole reaction process. The elemental mapping analysis shows the elemental distribution of Gd, Dy, Y, Yb, Na, and F of the formed nanorods (Figure 2e), which are very consistent with the our designed structure.

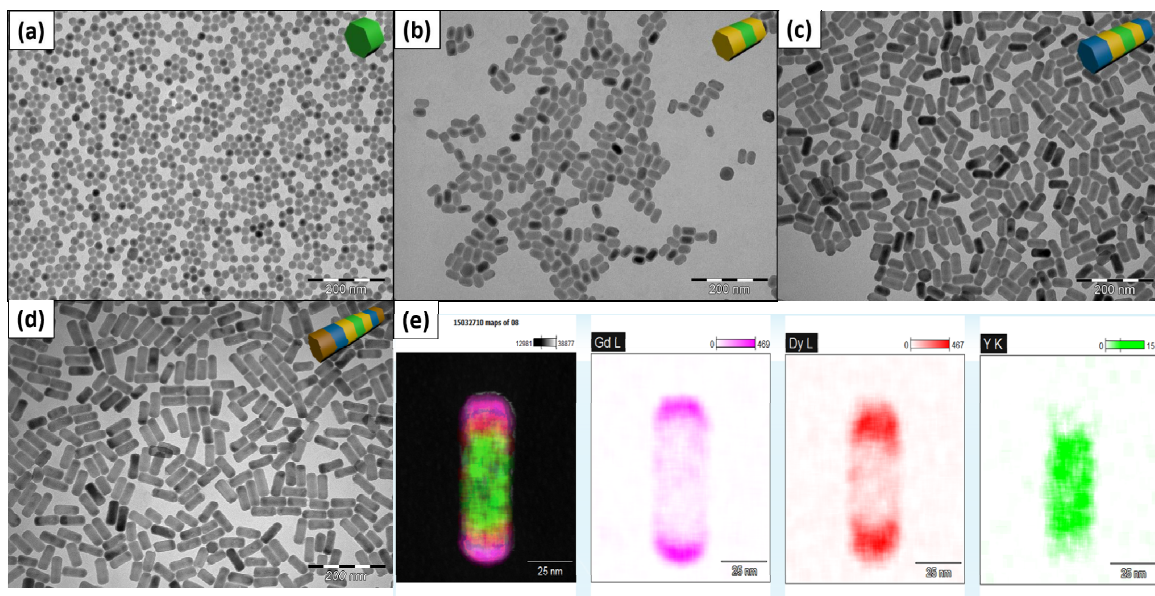


Figure 2. TEM images of the UCNPs nanospheres (a) and nanorods (b-d) with different aspect ratio and different materials through longitudinal epitaxial growth. (a) UCNPs core nanospheres  $\text{NaYF}_4:\text{Yb,Er}$ ; (b) three-section  $\text{NaYF}_4:\text{Yb,Er-NaYF}_4$  nanorods by growth of  $\text{NaYF}_4$ ; (c) five-section  $\text{NaYF}_4:\text{Yb,Er-NaYF}_4\text{-NaDyF}_4$  nanorods by growth of  $\text{NaDyF}_4$ ; (d) seven-section  $\text{NaYF}_4:\text{Yb,Er-NaYF}_4\text{-NaDyF}_4\text{-NaGdF}_4$  nanorods by growth of  $\text{NaGdF}_4$ ; (e) HAADF-STEM image with elemental mapping of the seven-section  $\text{NaYF}_4:\text{Yb,Er-NaYF}_4\text{-NaDyF}_4\text{-NaGdF}_4$  nanorod.

To confirm the feasibility of the developed methods, we also synthesized seven-section  $\text{NaYF}_4:\text{Yb,Er-NaYF}_4\text{-NaGdF}_4\text{-NaDyF}_4$  nanorods using same methods just change the addition order of  $\text{NaDyF}_4$  and  $\text{NaGdF}_4$ . The results show that the growth behavior of  $\text{NaYF}_4:\text{Yb,Er-NaYF}_4\text{-NaGdF}_4\text{-NaDyF}_4$  nanorods is similar with that of  $\text{NaYF}_4:\text{Yb,Er-NaYF}_4\text{-NaDyF}_4\text{-NaGdF}_4$  nanorods, which means the order of the element could be optional change depend on our design. Moreover, the nanodumbbell (Figure 3d) and nanoring-coated-dumbbell (Figure 3e) nanocrystals could be synthesized through changing the amount of the  $\text{NaOH}$  and  $\text{KOH}$  in the reaction system. These results means the mono-disperse nanorods with high aspect ratio or different element doping can be facile synthesized by the seed-mediated epitaxial growth in a high concentration of oleate ions and the aid of  $\text{KOH}$ . This is due to the aid of high concentration of  $\text{NaOH}$  or  $\text{KOH}$  in the reaction oleate ions can passivate effectively the side surfaces (100) (010) of nanorods and so grow very long homogeneous or heterogamous nanocrystals with the control.



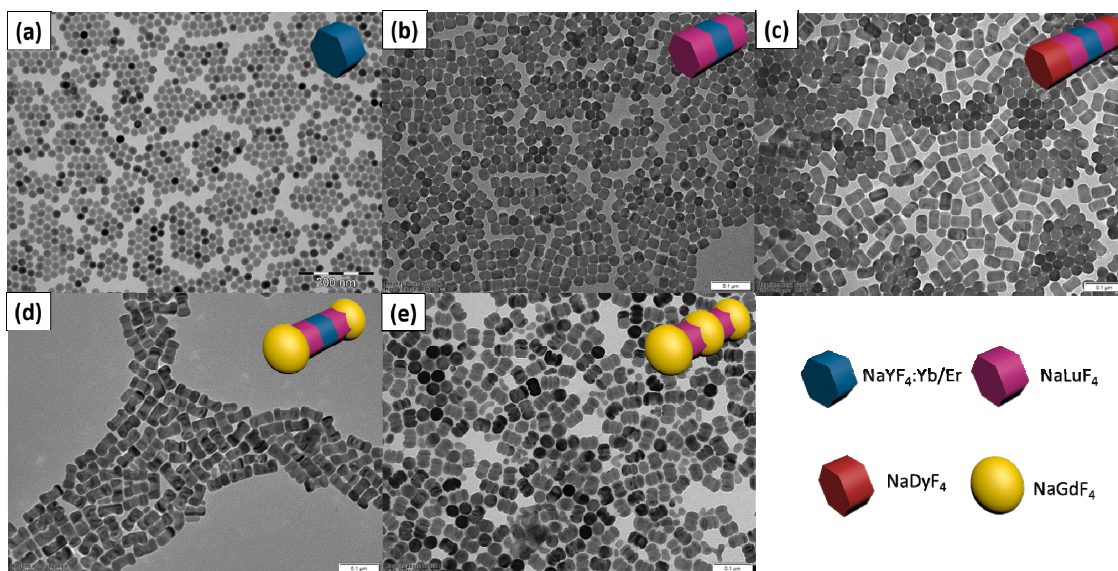


Figure 3. TEM images of the UCNPs nanospheres (a), nanorods (b, c), nanodumbbell (d) and nanoring-coated-dumbbells (e) with different aspect ratio and different materials through longitudinal and transversal epitaxial growth.

Before the multimode imaging application of the developed nanoring-coated-dumbbells, their cytotoxicity was first evaluated by the standard MTT viability assay. As shown in figure 4a, no significant cytotoxicity of the nanoring-coated-dumbbells is discovered even at the concentration of the particles as high as  $80 \mu\text{g}/\text{mL}^{-1}$ , when compared to the cells treated with PBS. The good cytocompatibility of the nanocrystals is crucial for their further bioimaging applications. To confirm the multimode imaging ability of the formed nanoring-coated-dumbbells, we did the in vivo MR/CT/UCL imaging of a xenografted tumor model. As shown in figure 4b, the tumor region shows a high contrast signal to the background in all the four imaging modes after intratumoral injection compared with that before the injection. These results suggest that the acquired nanoring-coated-dumbbells have a promising capability for in vivo multimode bioimaging.

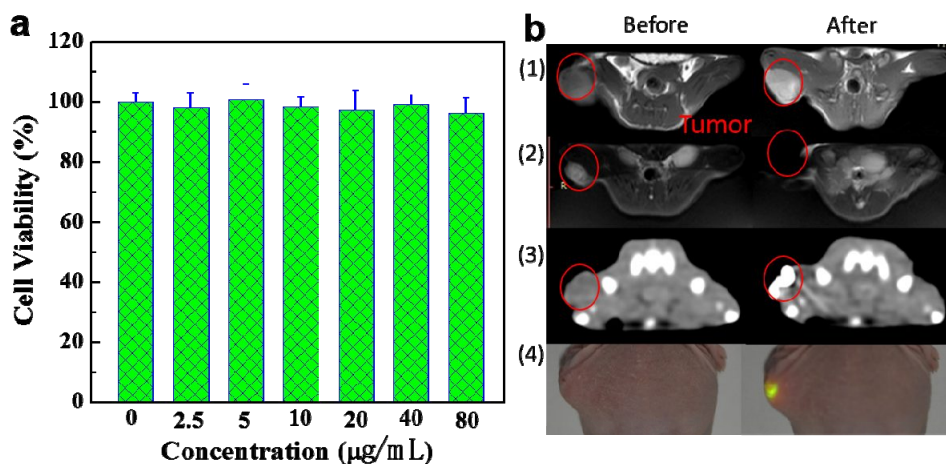


Figure 4. Cell viability study and in vivo bioimaging. (a) MTT assay of the viability of SKOV-3 cells after treatment with nanoring-coated-dumbbells at different concentrations for 24 h; (b) In vivo MR T1 (1), MR T2 (2), CT (3), and UCL (4) images of the xenografts SKOV-3 tumor model before and after injection of the multifunctional UCNPs.

## 4. CONCLUSIONS

To conclude, we develop a facile seed mediated one-pot hot-injection method to build the multifunctional heterogeneous nanocrystal for multimode bioimaging. The method enables the highly selectively controlled growth of different sodium lanthanide fluoride in either longitudinal or transversal directions. Through optimizing different imaging element within one versatile nanoplatform, the formed multifunctional nanoring-coated-dumbbells shows the excellent MR/CT/UCL imaging ability. Due to the easy surface functionalization of the nanocrystals, it is expected that multifunctional nanoring-coated-dumbbells may be developed as a versatile platform for targeted imaging as well as the drug delivery.

## REFERENCES

- [1] Louie, A. Y. "Multimodality Imaging Probes: Design and Challenges," *Chem. Rev. Papers* 110(5), 3146-3195 (2010).
- [2] Lee, D.-E., Koo, H., Sun, I.-C., Ryu, J. H., Kim, K., and Kwon, I. C. "Multifunctional nanoparticles for multimodal imaging and theragnosis," *Chem. Soc. Rev. Papers* 41(7), 2656-2672 (2012).
- [3] Zarschler, K., Rocks, L., Licciardello, N., Boselli, L., Polo, E., Garcia, K. P., De Cola, L., Stephan, H., and Dawson, K. A. "Ultrasmlal inorganic nanoparticles: State-of-the-art and perspectives for biomedical applications," *Nanomedicine: Nanotechnology, Biology and Medicine. Papers* 12(6), 1663-1701 (2016).
- [4] Wen, S., Li, K., Cai, H., Chen, Q., Shen, M., Huang, Y., Peng, C., Hou, W., Zhu, M., Zhang, G., and Shi, X. "Multifunctional dendrimer-entrapped gold nanoparticles for dual mode CT/MR imaging applications," *Biomaterials. Papers* 34(5), 1570-1580 (2013).
- [5] Chen, Q., Li, K., Wen, S., Liu, H., Peng, C., Cai, H., Shen, M., Zhang, G., and Shi, X. "Targeted CT/MR dual mode imaging of tumors using multifunctional dendrimer-entrapped gold nanoparticles," *Biomaterials. Papers* 34(21), 5200-5209 (2013).
- [6] Weissleder, R. "Molecular imaging in cancer," *Science. Papers* 312(5777), 1168-1171 (2006).
- [7] Alric, C., Taleb, J., Le Duc, G., Mandon, C., Billotey, C., Le Meur-Herland, A., Brochard, T., Vocanson, F., Janier, M., Perriat, P., Roux, S., and Tillement, O. "Gadolinium chelate coated gold nanoparticles as contrast agents for both X-ray computed tomography and magnetic resonance imaging," *J. Am. Chem. Soc. Papers* 130(18), 5908-5915 (2008).
- [8] Baptista, P., Pereira, E., Eaton, P., Doria, G., Miranda, A., Gomes, I., Quaresma, P., and Franco, R. "Gold nanoparticles for the development of clinical diagnosis methods," *Anal. Bioanal. Chem. Papers* 391(3), 943-950 (2008).
- [9] Li, X., Zhang, F., and Zhao, D. "Lab on upconversion nanoparticles: optical properties and applications engineering via designed nanostructure," *Chemical Society Reviews. Papers* 44(6), 1346-1378 (2015).
- [10] Gai, S., Li, C., Yang, P., and Lin, J. "Recent Progress in Rare Earth Micro/Nanocrystals: Soft Chemical Synthesis, Luminescent Properties, and Biomedical Applications," *Chemical Reviews. Papers* 114(4), 2343-2389 (2014).
- [11] Zhao, J., Lu, Z., Yin, Y., McRae, C., Piper, J. A., Dawes, J. M., Jin, D., and Goldys, E. M. "Upconversion luminescence with tunable lifetime in NaYF<sub>4</sub>:Yb,Er nanocrystals: role of nanocrystal size," *Nanoscale. Papers* 5(3), 944-952 (2013).
- [12] Zhang, Y., Zhang, L., Deng, R., Tian, J., Zong, Y., Jin, D., and Liu, X. "Multicolor Barcoding in a Single Upconversion Crystal," *Journal of the American Chemical Society. Papers* 136(13), 4893-4896 (2014).



- [13] Zhou, B., Shi, B., Jin, D., and Liu, X. "Controlling upconversion nanocrystals for emerging applications," *Nat Nano. Papers* 10(11), 924-936 (2015).
- [14] Lu, Y., Lu, J., Zhao, J., Cusido, J., Raymo, F. M., Yuan, J., Yang, S., Leif, R. C., Huo, Y., Piper, J. A., Paul Robinson, J., Goldys, E. M., and Jin, D. "On-the-fly decoding luminescence lifetimes in the microsecond region for lanthanide-encoded suspension arrays," *Nature Communications. Papers* 5(3741) (2014).
- [15] Lu, Y., Zhao, J., Zhang, R., Liu, Y., Liu, D., Goldys, E. M., Yang, X., Xi, P., Sunna, A., Lu, J., Shi, Y., Leif, R. C., Huo, Y., Shen, J., Piper, J. A., Robinson, J. P., and Jin, D. "Tunable lifetime multiplexing using luminescent nanocrystals," *Nat Photon. Papers* 8(1), 32-36 (2014).
- [16] Zhao, J., Jin, D., Schartner, E. P., Lu, Y., Liu, Y., Zvyagin, A. V., Zhang, L., Dawes, J. M., Xi, P., Piper, J. A., Goldys, E. M., and Monro, T. M. "Single-nanocrystal sensitivity achieved by enhanced upconversion luminescence," *Nat Nano. Papers* 8(10), 729-734 (2013).
- [17] Johnson, N. J. J., Oakden, W., Stanisiz, G. J., Scott Prosser, R., and van Veggel, F. C. J. M. "Size-Tunable, Ultrasmall NaGdF<sub>4</sub> Nanoparticles: Insights into Their T<sub>1</sub> MRI Contrast Enhancement," *Chemistry of Materials. Papers* 23(16), 3714-3722 (2011).
- [18] Das, G. K., Johnson, N. J. J., Cramen, J., Blasiak, B., Latta, P., Tomanek, B., and van Veggel, F. C. J. M. "NaDyF<sub>4</sub> Nanoparticles as T<sub>2</sub> Contrast Agents for Ultrahigh Field Magnetic Resonance Imaging," *The Journal of Physical Chemistry Letters. Papers* 3(4), 524-529 (2012).
- [19] Liu, D., Xu, X., Du, Y., Qin, X., Zhang, Y., Ma, C., Wen, S., Ren, W., Goldys, E. M., Piper, J. A., Dou, S., Liu, X., and Jin, D. "Three-dimensional controlled growth of monodisperse sub-50 nm heterogeneous nanocrystals," *Nature Communications. Papers* 7(10254) (2016).