

Original citation:

Zhang, Binjia, Xie, Fengwei, Shamshina, Julia L., Rogers, Robin D., McNally, Tony, Wang, David K., Halley, Peter J, Truss, Rowan W, Zhao, Si-ming and Chen, Ling. (2017) Facile preparation of starch-based electroconductive films with ionic liquid. ACS Sustainable Chemistry & Engineering.

Permanent WRAP URL:

<http://wrap.warwick.ac.uk/88417>

Copyright and reuse:

The Warwick Research Archive Portal (WRAP) makes this work by researchers of the University of Warwick available open access under the following conditions. Copyright © and all moral rights to the version of the paper presented here belong to the individual author(s) and/or other copyright owners. To the extent reasonable and practicable the material made available in WRAP has been checked for eligibility before being made available.

Copies of full items can be used for personal research or study, educational, or not-for profit purposes without prior permission or charge. Provided that the authors, title and full bibliographic details are credited, a hyperlink and/or URL is given for the original metadata page and the content is not changed in any way.

Publisher's statement:

"This document is the Accepted Manuscript version of a Published Work that appeared in final form in ACS Sustainable Chemistry & Engineering copyright © American Chemical Society after peer review and technical editing by the publisher.

To access the final edited and published work

<http://pubs.acs.org/page/policy/articlesonrequest/index.html> ."

A note on versions:

The version presented here may differ from the published version or, version of record, if you wish to cite this item you are advised to consult the publisher's version. Please see the 'permanent WRAP URL above for details on accessing the published version and note that access may require a subscription.

For more information, please contact the WRAP Team at: wrap@warwick.ac.uk

Facile preparation of starch-based electroconductive films with ionic liquid

Binjia Zhang^{a,b,c}, *Fengwei Xie*^{*,c}, *Julia L. Shamshina*^{d,e}, *Robin D. Rogers*^e, *Tony McNally*^f,
David K. Wang^g, *Peter J. Halley*^c, *Rowan W. Truss*^c, *Siming Zhao*^b, *Ling Chen*^{**,a}

^a Guangdong Province Key Laboratory for Green Processing of Natural Products and Product Safety, South China University of Technology, 381 Wushan Road, Guangzhou, Guangdong 510640, China

^b Key Laboratory of Environment Correlative Dietology (Ministry of Education), College of Food Science and Technology, Huazhong Agricultural University, 1 Shizishan Street, Wuhan, Hubei 430070, China

^c School of Chemical Engineering, The University of Queensland, Brisbane, Queensland 4072, Australia

^d 525 Solutions, Inc., 720 2nd Street, Tuscaloosa, Alabama 35401, United States

^e Department of Chemistry, McGill University, 801 Sherbrooke Street West, Montreal, Quebec H3A 0B8, Canada

^f International Institute for Nanocomposites Manufacturing (IINM), WMG, University of Warwick, Coventry CV4 7AL, United Kingdom

^g School of Chemical and Biomolecular Engineering, The University of Sydney, Darlington, NSW 2006, Australia

* *Corresponding Author. Email: f.xie@uq.edu.au, fwhsieh@gmail.com (F. Xie)*

** *Corresponding Author. Email: felchen@scut.edu.cn (L. Chen)*

KEYWORDS: *Starch-based materials; Ionic liquid; 1-Ethyl-3-methylimidazolium acetate; Plasticizer; Energy-saving processing; Electroconductive films*

1
2
3 **ABSTRACT:** Here, we discovered that starch could be straightforwardly processed into
4 optically-transparent electroconductive films, by compression molding at a relatively mild
5 temperature (55 °C or 65 °C), much lower than those commonly used in biopolymer melt
6 processing (typically over 150 °C). Such significantly-reduced processing temperature was
7 achieved with the use of an ionic liquid plasticizer, 1-ethyl-3-methylimidazolium acetate
8 ([C₂mim][OAc]). A higher [C₂mim][OAc] content, lower processing temperature (55 °C), and/or
9 higher relative humidity (RH) (75%) during the sample post-processing conditioning, suppressed
10 the crystallinity of the processed material. The original A-type crystalline structure of starch was
11 eliminated, although small amounts of B-type and V-type crystals were formed subsequently.
12 The starch crystallinity could be linked to the mechanical properties of the films. Moreover, the
13 processing destroyed the original lamellar structure of starch, and the amorphous starch
14 processed with [C₂mim][OAc]/water could aggregate on the nanoscale. The films displayed
15 excellent electrical conductivity ($> 10^{-3}$ S/cm), which was higher with a lower processing
16 temperature (55 °C) and a higher conditioning RH (75%). The incorporation of [C₂mim][OAc]
17 reduced the thermal decomposition temperature of starch by 30 °K, while the formulation and
18 processing conditions did not affect the film thermal stability.
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

INTRODUCTION

Nowadays, bio- or “green” materials from renewable resources are increasingly selected for reasons of environmental sustainability and carbon impact.¹ Biopolymers can be referred to as polymers directly from biomass, a natural, abundant and underutilized source of renewable feedstocks, which principally are cellulose, hemicellulose, chitin, starch, and lignin. Biopolymers are not only widely available and sustainable, but also can be biodegradable and biocompatible, and thus have several economic and environmental advantages. Moreover, the societal recognition and expectation for environmentally-friendly products create a demand for technically advantageous materials that can replace petroleum-derived plastics.

The application of biopolymers heavily relies on their processability into usable forms. However, the processing of biopolymers is somewhat challenging due to the strong intermolecular hydrogen bonding in their native forms,² and the processing conditions usually depend on the identity of the biopolymer. Traditionally, for the film formation, biopolymers have been mostly processed by solution methods (casting), based on a film-forming solution (more rare, dispersion) where biopolymers are first solubilized into a liquid phase. Organic solvent systems, capable of disruption of hydrogen bonding (*e.g.*, DMF, DMAc), are utilized, which, after casting of the film, are removed (usually by drying at a higher temperature).³ However, these methods are much less efficient and less suitable for industrial-scale production due to significant use of corrosive solvent systems. In another method of film casting, ionic liquids (ILs, salts that melt below 100 °C) are used in place of VOCs, to solubilize biopolymers. Thus, we have recently shown that reproducible, strong, and versatile cellulose⁴⁻⁵ or chitin films,⁶ made from either

1
2
3 biopolymer alone or combined with other polymer(s), can be prepared through the
4 dissolution of biopolymer in 1-ethyl-3-methylimidazolium ([C₂mim][OAc]) ionic liquid
5 (IL) followed by the casting of films and washing out the solvent. Films prepared using
6 this methodology can be prepared with the controlled composition, thickness, surface
7 properties, flexibility, and transparency.
8
9

10
11
12
13
14
15 While the melt processing of biopolymers has also been practiced,⁷⁻⁹ high processing
16 temperature, high viscosity, and easy thermal decomposition during processing remains to
17 be challenges.^{3, 10-11} With chemical modification, biopolymers can be converted into
18 soluble forms (*e.g.*, cellulose acetate) or derivatives that are more processable (*e.g.*,
19 hydroxypropyl starch). Nevertheless, such conversion not only increases the costs but also
20 modifies the inherent properties of the biopolymers. Besides, for promoting
21 environmental sustainability and reducing carbon impact, people have put more emphasis
22 on material production technologies requiring less energy input.
23
24
25
26
27
28
29
30
31
32
33

34 To this end, plasticizers that are effective in disrupting the native hydrogen-bonding
35 network of biopolymers could provide solutions for the easier and “greener” treatment of
36 biopolymers. Starch, a polysaccharide found in plants such as maize (corn), potato,
37 cassava, wheat, and rice, represents a typical model with a naturally complex structure
38 involving strong intermolecular hydrogen bonding. In the native form of granules
39 (<1 μm~100 μm), starch has a multi-level hierarchical structure, which is based on two
40 major biomacromolecules, amylose (mainly linear) and amylopectin (hyper-branched)
41 (~nm). Nevertheless, between the granule and molecular levels, there are alternating
42 amorphous and semicrystalline shells (growth rings) (100~400 nm), with the latter shell
43 being stacked crystalline and amorphous lamellae (periodicity) (9~10 nm).¹²⁻¹⁵ Therefore,
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

1
2
3 it is important to understand how the complex structure of starch can be altered to achieve
4
5 the desired plasticized forms.
6

7
8 With a plasticizer and elevated temperature, a process known as “gelatinization” (with
9
10 abundant plasticizer content) or “melting” (with limited plasticizer content) occurs,
11
12 resulting in a disruption of the 3D structure of native starch. If preferential conditions are
13
14 reached, this process can lead to a homogeneous amorphous material known as
15
16 “thermoplastic starch (TPS)” or “plasticized starch,” which is essential in the production
17
18 of some starch-based materials.^{3, 10-11, 16} For the dissolution of starch, in particular, water
19
20 is the most commonly-used solvent, although the process does not take place at room
21
22 temperature resulting only in starch swelling, and high temperatures are needed for its
23
24 complete dissolution;¹⁷⁻¹⁸ yet, phase separation often occurs. Such phase separation (*i.e.*,
25
26 heterogeneous conditions) makes aqueous systems to be unfavorable for starch
27
28 processing. Substances such as polyols (*e.g.*, glycerol, glycol, sorbitol), compounds
29
30 containing nitrogen (*e.g.*, urea, ammonium derived, amines), and citric acid have been
31
32 reported to be effective for the plasticization of starch,^{3, 10} but not for its dissolution.
33
34 Other well-known solvents for starch is dimethyl sulfoxide (DMSO),¹⁹ often with the
35
36 addition of salts such as calcium chloride (CaCl₂),²⁰ urea/alkali (NaOH) aqueous
37
38 solution,²¹ concentrated mineral and organic acids,²² ethylene diamine,²³ pyridine,²⁴ or
39
40 *N,N*-dimethylacetamide (DMAc)/lithium chloride (LiCl) system.²⁵⁻²⁶ These solvents are
41
42 corrosive, toxic, often hydrolyze polymer decreasing its molecular weight (MW), many
43
44 are unsuitable for biomedical applications, often volatile, and usually difficult to recycle.
45
46
47
48
49
50
51

52
53 A plasticizer for starch should preferably be thermally-stable and non-volatile both
54
55 during thermal processing and in post-processing stages, be ineffective in enhancing
56
57
58
59
60

1
2
3 starch macromolecular degradation, be non-toxic to humans and the environment, and be
4 able to promote starch-based materials with enhanced performance and new capabilities.
5
6 Unfortunately, commonly used plasticizers do not yet have all the desired attributes and
7
8 thus finding alternative and better plasticizers for starch is of interest. By avoiding many
9
10 of the reactive chemicals and facilitating a physical dissolution process, ionic liquids (ILs)
11
12 overcome the disadvantages of “conventional” dissolution/plasticization practices.²⁷
13
14
15

16
17 ILs that contain a strongly basic, hydrogen bond accepting anion (*e.g.*, carboxylates or
18
19 halides) have the ability to wholly or partially disrupt the intermolecular hydrogen
20
21 bonding present in biopolymeric networks. As a result, ILs are demonstrated to either
22
23 fully dissolve or plasticize many biopolymers such as starch,²⁸⁻³² cellulose,³³⁻³⁴
24
25 chitin/chitosan,³⁵⁻³⁷ silk fibroin,³⁸⁻⁴⁰ lignin,⁴¹ zein protein,²⁸ and wool keratin.⁴² As such,
26
27 these ILs can be used as excellent media for polysaccharide plasticization and
28
29 modification resulting in the development of advanced biomaterials, such as ionically
30
31 conducting polymers or solid polymer electrolytes.⁴³⁻⁵⁰ For example, 1-ethyl-3-
32
33 methylimidazolium acetate ([C₂mim][OAc]) has desirable properties, *e.g.*, low toxicity
34
35 (LD₅₀ > 2000 mg·kg⁻¹), low corrosiveness, low melting point (< -20 °C), low viscosity
36
37 (10 mPa·s at 80 °C), and favorable biodegradability.⁵¹
38
39
40
41
42

43
44 For the processing of polysaccharides with ILs, solution methods were predominantly
45
46 involved in previous studies. Sankri *et al.*⁵² and Leroy *et al.*⁵³ have done pioneering work
47
48 using an IL 1-butyl-3-methylimidazolium chloride ([C₄mim][Cl]) as a new plasticizer for
49
50 melt processing of starch-based materials, which demonstrated improved plasticization,
51
52 electrical conductivity, and hydrophobicity. Our previous work⁵⁴ has shown that
53
54 [C₂mim][OAc] has a significant plasticization effect on starch, including high-amylose
55
56
57
58
59
60

1
2
3 starch, prepared via a thermal compression molding process, and can reduce the
4
5 crystallinity and make the amorphous phase more mobile leading to desirable properties
6
7 for some specific applications (*e.g.*, electrically-conductive materials). However, in these
8
9 past efforts, a high temperature (up to 160 °C) and/or multiple processing steps were
10
11 required to fabricate starch-based films. Such high-temperature conditions make it
12
13 difficult to incorporate thermally-sensitive ingredients (such as bioactive ingredients and
14
15 enzymes) into starch-based materials.
16
17
18
19

20 In contrast to the previous work, this paper reports a facile and energy-saving process
21
22 to create starch-based electrically-conductive films. In this research, the one-step
23
24 compression molding process required only a mild temperature (55 °C or 65 °C) to
25
26 transform native starch into a transparent material with electrical conductivity.
27
28 Furthermore, we revealed that the structure and properties of the resultant material could
29
30 be easily tailored by the formulation and processing conditions.
31
32
33
34
35

36 **EXPERIMENTAL SECTION**

37 **Materials**

38
39 A chemically-unmodified regular maize starch (RMS) was supplied by New Zealand
40
41 Starch Ltd. (Onehunga, Auckland, New Zealand) with the product name “Avon Maize
42
43 Starch”. This starch has an amylose content of 24.4%.⁵⁵ The original moisture content
44
45 (MC) of this starch was 13.6 wt.% as measured by a Satorius Moisture Analyser (Model
46
47 MA30, Sartorius Weighing Technology GmbH, Weender Landstraße 94-108, 37075,
48
49 Goettingen, Germany). Milli-Q water was used in all instances. [C₂mim][OAc] of
50
51 ≥ 95 wt% purity (with *ca.* 1200 ppm water content), produced by IoLiTec Ionic Liquids
52
53
54
55
56
57
58
59
60

1
2
3 Technologies GmbH (Salzstraße 184, D-74076 Heilbronn, Germany) was also supplied
4
5 by Chem-Supply Pty Ltd.
6

7
8 [C₂mim][OAc]-aqueous solutions: [C₂mim][OAc] is a liquid completely miscible with
9
10 water at room temperature.⁵⁶ In this work, 0.15:1 mol/mol [C₂mim][OAc]:water solution
11
12 was prepared, where this mole ratio accounted for the MC of starch and the purity and
13
14 MC of the IL.
15

16 17 18 **Film preparation** 19

20
21 Two formulations were used for the film preparation (see Table S1 and S2 in Support
22
23 Information (SI)). 0.15:1 mol/mol [C₂mim][OAc]:water solution was added drop-wise to
24
25 the starch, accompanied by careful blending using a mortar and pestle to ensure an even
26
27 distribution of the liquid mixture in the starch. Then, the blended samples were
28
29 hermetically sealed and stored in Ziploc[®] bags under ambient conditions (*ca.* 28 °C) for at
30
31 least 4 h, before thermal compression molding. The storage allowed time for further
32
33 equilibration of the samples. The blended sample was carefully and uniformly spread over
34
35 the molding area with poly(tetrafluoroethylene) glass fabrics (Dotmar EPP Pty Ltd,
36
37 Acacia Ridge, Qld, Australia) located between the starch and the mould. Then,
38
39 compression molding was undertaken at a specific temperature (55 °C or 65 °C) under
40
41 pressure (8 MPa) for 30 min. After opening the mold, an optically transparent sample
42
43 (9 cm × 6 cm, thickness *ca.* 1.2 mm) could be retrieved. The films were conditioned at
44
45 two different relative humidities (RH), 33% (over-saturated magnesium chloride solution)
46
47 and 75% (over-saturated sodium chloride solution),⁵⁷ at room temperature in desiccators
48
49 for 7 days before material characterizations. From the sample preparation to conditioning,
50
51 no observation indicated that [C₂mim][OAc] phased out of the starch films. This
52
53
54
55
56
57
58
59
60

suggested a strong binding between [C₂mim][OAc] and the starch. The MCs in the samples were subject to change during conditioning. After the conditioning, the thickness of all films was *ca.* 1 mm. Table 1 shows the compositions in mass and mole ratios after conditioning. The MCs were determined by weighing the samples before and after vacuum-oven drying at 100 °C for 48 h to remove all the moisture.

Table 1. Mass and mole ratios of different starch-[C₂mim][OAc] films

Sample	Mass ratio			Mole ratio of IL and water content relative to hydroxyl groups (–OH) in starch		
	Starch (dry basis)	[C ₂ mim][OAc]	water	Starch hydroxyl	[C ₂ mim][OAc]	water
IL18-T55-H33	99.36 ± 0.00	60 ± 0	28.59 ± 0.20	1 ± 0	0.18 ± 0.00	0.86 ± 0.01
IL18-T55-H75	99.36 ± 0.00	60 ± 0	55.06 ± 0.99	1 ± 0	0.18 ± 0.00	1.66 ± 0.03
IL18-T65-H33	99.36 ± 0.00	60 ± 0	28.54 ± 0.58	1 ± 0	0.18 ± 0.00	0.86 ± 0.02
IL18-T65-H75	99.36 ± 0.00	60 ± 0	54.78 ± 0.40	1 ± 0	0.18 ± 0.00	1.65 ± 0.01
IL21-T55-H33	86.40 ± 0.00	60 ± 0	29.44 ± 0.49	1 ± 0	0.21 ± 0.00	1.02 ± 0.02
IL21-T55-H75	86.40 ± 0.00	60 ± 0	53.72 ± 0.56	1 ± 0	0.21 ± 0.00	1.87 ± 0.02
IL21-T65-H33	86.40 ± 0.00	60 ± 0	30.11 ± 0.19	1 ± 0	0.21 ± 0.00	1.05 ± 0.01
IL21-T65-H75	86.40 ± 0.00	60 ± 0	53.95 ± 0.41	1 ± 0	0.21 ± 0.00	1.87 ± 0.01

In the following text, the plasticized starch samples are coded in the format of “IL18-T55-H33”, where “IL18” denotes the IL content (0.18) in a mole ratio relative to starch hydroxyls (see SI Table S2), “T55” shows the temperature used for compression molding, and “H33” indicates the relative humidity (RH) for conditioning.

Characterization

1
2
3 **Sample compositions.** The MCs were determined gravimetrically. Namely, the
4 samples were placed in a vacuum oven at 100 °C for 48 h, which allowed the removal of
5 all the moisture. The samples were weighed before and after the oven drying to estimate
6 the MCs. At least three replicates were used for determining the MC of each sample.
7

8
9
10 **Scanning electron microscopy (SEM).** The starch samples were cryo-ground in liquid
11 nitrogen. The fractures were put on circular metal stubs previously covered with double-
12 sided adhesive before platinum coating at 5 nm thickness using an Eiko Sputter Coater,
13 under vacuum (7×10^{-3} bar). The morphology of the starch samples was examined using
14 a scanning electron microscope (SEM, JEOL JSM-6460LA, Tokyo, Japan). An
15 accelerating voltage of 5 kV and a spot size of 6 nm were used. A magnification of 1000×
16 was used for all the images.
17

18
19 **Powder X-ray diffraction (pXRD).** The starch film samples (size *ca.* 2 cm × 2 cm)
20 were placed in the sample holder of a X-ray powder diffractometer (D8 Advance, Bruker
21 AXS Inc., Madison, WI, USA) equipped with a graphite monochromator, a copper target,
22 and a scintillation counter detector. pXRD patterns were recorded for an angular range
23 (2θ) of 4–40°, with a step size of 0.02° and a step rate of 0.5 s per step, and thus the scan
24 time lasted for approximately 15 min. The radiation parameters were set at 40 kV and
25 30 mA, with a slit of 2 mm. Traces were processed using the Diffrac Plus Evaluation
26 Package (Version 11.0, Bruker AXS Inc., Madison, WI, USA) to determine the X-ray
27 diffractograms of the samples. The degree of crystallinity was calculated with the PeakFit
28 software (Version 4.12, Systat Software, Inc., San Jose, CA, USA) following the method
29 by Lopez-Rubio, et al.⁵⁸ Eq. (1):
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

$$X_c = \frac{\sum_{i=1}^n A_{ci}}{A_t} \quad (1)$$

where A_{ci} is the area under each crystalline peak with index i , and A_t is the total area (both amorphous background and crystalline peaks) under the diffractogram.

The V-type crystallinity (single-helical amylose structure) was quantitatively estimated based on the total crystalline peak areas at 7.5° , 13° , and 20° following the method provided in reference.⁵⁹

Attenuated total reflectance Fourier-transform infrared (ATR-FTIR) spectroscopy. The ATR-FTIR spectra of different starch samples were recorded using a Nicolet 5700 FTIR spectrometer (Thermo Electron Corporation, Madison, WI, USA) equipped with a Nicolet Smart Orbit attenuated total reflectance (ATR) accessory incorporating a diamond internal reflection element. For each spectrum, 64 scans were recorded over the range of $4000\text{--}600\text{ cm}^{-1}$ at RT (about $22\text{ }^\circ\text{C}$) at a resolution of 4 cm^{-1} , co-added and Fourier-transformed. The background spectrum was recorded on air and subtracted from the sample spectrum. ATR-FTIR spectra were baseline-corrected and deconvoluted using PeakFit (v4.12). The ratio of band intensities at 995 cm^{-1} and 1022 cm^{-1} was used for analyzing the film molecular rearrangement.

Synchrotron small-angle X-ray scattering (SAXS). SAXS analysis was carried out on the SAXS/WAXS beamline (flux, 10^{13} photons/s) at the Australian Synchrotron (Clayton, Vic., Australia), at a wavelength $\lambda = 1.47\text{ \AA}$. The 2D scattering patterns were collected using a Pilatus 1M camera (active area $169 \times 179\text{ mm}$; and pixel size $172 \times$

172 μm). The scatterBrain software was used to acquire the one-dimensional (1D) data from the 2D scattering pattern; and the data in the angular range of $0.0015 < q < 0.15 \text{ \AA}^{-1}$ was used as the SAXS pattern, in which $q = 4\pi\sin\theta/\lambda$ (where 2θ is the scattering angle and λ is the wavelength of the X-ray source).⁶⁰⁻⁶¹ All data were background subtracted and normalized. The starch-based films were placed on a multi-well stage provided by the Australian Synchrotron, and then the SAXS data recorded for an acquisition time of 1 s.

For the SAXS patterns, the inflection data centered at around 0.007 \AA^{-1} were fitted using a unified model Eq. (2):⁶²

$$I(q) = G \exp\left(-\frac{R_g^2 q^2}{3}\right) + C \left(\frac{\left(\operatorname{erf}\left(\frac{qR_g}{\sqrt{6}}\right)\right)^3}{q} \right)^\alpha \quad (2)$$

In this equation, G is the pre-factor of the Guinier function corresponding to a radius R_g ; and C and α are the pre-factor and the exponent of the power-law function, respectively.

Tensile testing. Tensile tests were performed with an Instron[®] 5543 universal testing machine (Instron Pty Ltd, Bayswater, Vic., Australia) with a 500N load cell on dumbbell-shaped specimens cut from the sheets with a constant deformation rate of 10 mm/min at room temperature. The specimens corresponded to Type 4 of the Australian Standard AS 1683:11 (ISO 37:1994), and the testing section of each specimen was 12 mm in length and 2 mm in width. Young's modulus (E), tensile strength (σ_t), and elongation at break (ε_b) were determined by the Instron[®] software, from at least 7 specimens for each of the plasticized starch samples.

1
2
3 **Thermogravimetric analysis (TGA).** A Mettler Toledo TGA/DSC1 machine
4 (Mettler-Toledo Ltd., Port Melbourne, Vic., Australia) was used with 40 μL aluminum
5 crucibles with a cap with a pinhole for thermogravimetric analysis (TGA) under nitrogen.
6
7
8 This equipment was calibrated using the melting points of Au, Zn and In standards
9 (1064 $^{\circ}\text{C}$, 419.5 $^{\circ}\text{C}$, and 155.6 $^{\circ}\text{C}$, respectively). A sample mass of about 5 mg was used
10 for each run. The samples were heated from 25 $^{\circ}\text{C}$ to 550 $^{\circ}\text{C}$ and measured in the
11 dynamic heating regime, using a constant heating ramp of 3 K/min.
12
13
14
15
16
17
18

19 **Electrical conductivity.** An alternating current (AC) impedance spectroscopy method
20 was used to measure the proton conductivity of each film in a conductivity cell. The
21 resistance of the films was probed by a frequency response analyzer (FRA, CompactStat,
22 Ivium Technologies B. V., The Netherlands) with an oscillating voltage of 20 mV over a
23 frequency range of 1 MHz – 1 Hz. The conductivity of starch films was tested at room
24 temperature (*ca.* 26 $^{\circ}\text{C}$) at a RH of 33% or 75% using a Model 740 Membrane Testing
25 System (MTS, Scribner Associates, Inc., Southern Pines, NC, USA). A 15 min
26 equilibration time was used at each RH before the measurement. The conductivity (σ ,
27 S/cm) of the film samples was calculated using Eq. (3):
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49

$$\sigma = \frac{l}{A \times R} \quad (3)$$

50 where l (cm) is the film thickness, A (cm^2) the film area, and R (Ω) the film resistance.
51
52
53

54 RESULTS AND DISCUSSION

56 Sample compositions

57
58
59
60

1
2
3 Table 1 shows the composition (in mass ratios and mole ratios) of different
4 [C₂mim][OAc]-plasticized starch-based films. The MC of the film was adjusted using
5
6 conditioning at a certain RH in a humidity chamber (see Experimental). At the same RH,
7
8 a higher MC could result from a higher [C₂mim][OAc] content in the film (see SI Table
9
10 S1 and S2 for the original formulations for sample preparation). These phenomena could
11
12 be ascribed to the strong hydrophilicity of [C₂mim][OAc], which had a stronger affinity
13
14 to water than to starch hydroxyls, and played the major role in the moisture absorption of
15
16 the films from the environment.⁶³ As the electrical conductivity of starch-[C₂mim][OAc]
17
18 films is mainly related to the moisture and IL contents in the films, RH can potentially
19
20 tailor the electrical conductivity of starch-[C₂mim][OAc] films.⁶⁴
21
22
23
24
25
26


27 **Visual appearance**

28
29
30 Immediately after compression molding and before conditioning, different
31
32 [C₂mim][OAc]-plasticized starch-based films were placed on top of a paper sheet printed
33
34 with The University of Queensland (UQ) logos to indicate their optical transparency. All
35
36 starch-[C₂mim][OAc] films displayed high transparency, showing the proper
37
38 plasticization of starch by [C₂mim][OAc]. IL21-T65 was observed having the highest
39
40 transparency, while IL18-T55 was least transparent. These results were as expected as a
41
42 higher [C₂mim][OAc] (lower starch content) and/or a higher processing temperature
43
44 could facilitate interactions between [C₂mim][OAc] and starch molecules, *i.e.*, a stronger
45
46 plasticization effect. Abundant plasticization could disrupt the sophisticated granule
47
48 structure of native starch, leading to the higher transparency of the film.
49
50
51
52
53

54 **Surface morphology**

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Figure 1 collects the SEM images of the normal and fracture surfaces of starch-[C₂mim][OAc] films under either 33% or 75% RHs. IL18-T55-H33/75 were observed still containing the apparent starch granule shapes that were not destroyed during processing. With a reduced starch content in the formulation, IL21-T55-H33/75 also displayed such granule shapes on its surfaces. It has been reported that even after gelatinization in abundant water, there are still some granule shells that are not destroyed. These granule shells could be similar to “ghosts”,⁶⁵ which are formed due to the physical crosslinking of polysaccharide chains within swollen granules.⁶⁶

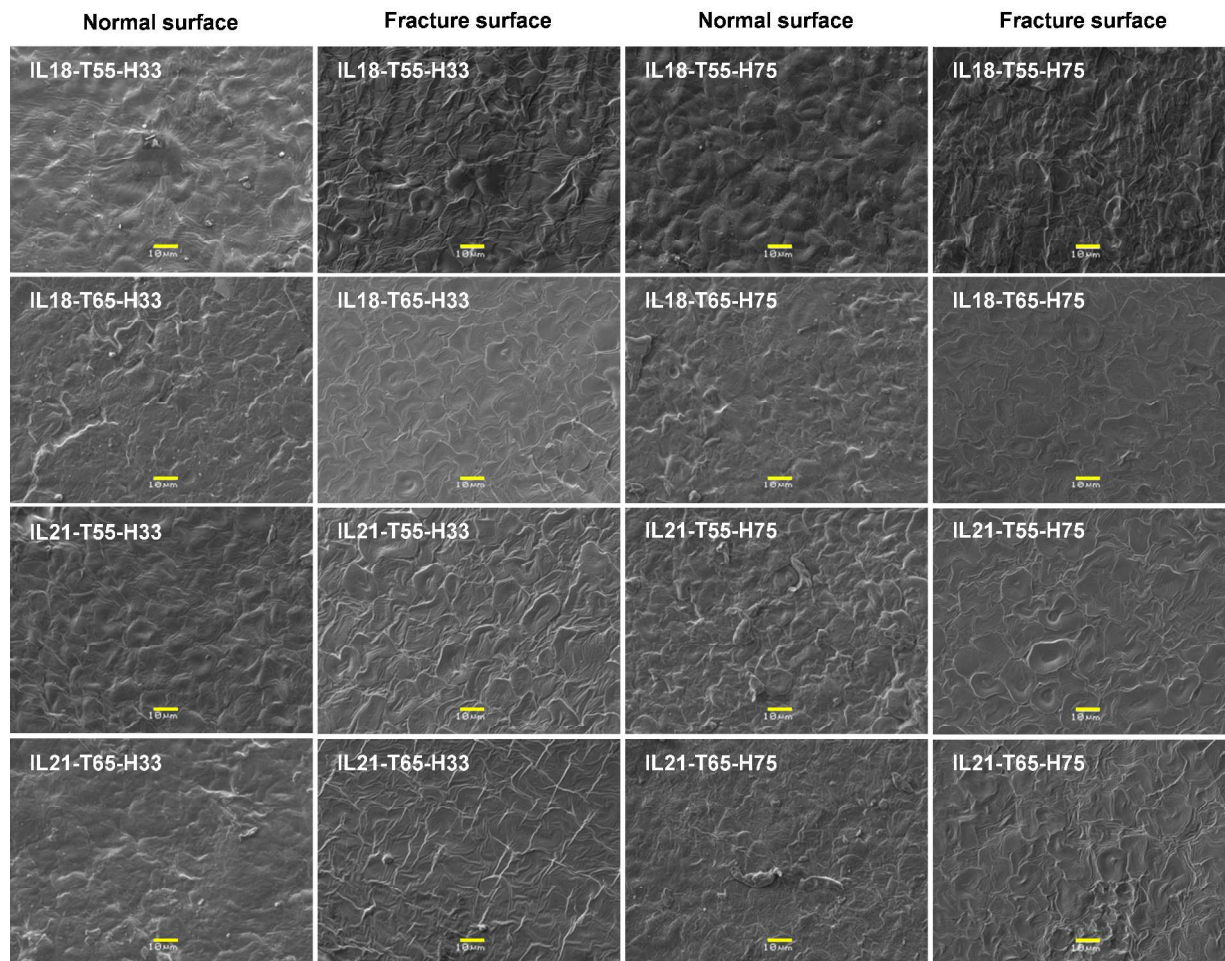

36
37
38
39
40
41
42
43
44

Figure 1. SEM images of normal and fracture surfaces of starch-[C₂mim][OAc] films. The spot size was 6 nm. The scale bar (yellow) indicates 10 μm.

45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

With a higher processing temperature (IL18-T65-H33/75 and IL21-T65-H33/75), these remaining granules became much less apparent, and the surface morphologies became more homogeneous and smooth. These results suggested that at a higher temperature, the aqueous IL was more effective in the disruption of the native starch structure and the disentanglement of starch molecules. Nonetheless, the two starch contents used did not result in any significant difference in morphology.

Crystalline structure

Powder X-ray diffraction (pXRD) provides an elucidation of the long-range molecular order in the polymer. There are three polymorphic crystalline structures of starch, termed A, B or V-type, and the types of crystallinity can be unambiguously distinguished by inspecting the characteristic X-ray diffraction patterns.^{14, 67} This is important as each type of the starch crystalline structures interacts differently with water molecules. Normally, in the crystalline structure of native starch, A-type and B-type polymorphs are found; both are left-handed, six-fold structures. However, the A-type polymorph is arranged as H-bonded parallel-stranded double helices (one double helix at the corner and another at the center of the unit cell) packed in a B2-monoclinic space group;⁶⁷ such close-packed arrangement allows for capture of only four water molecules in the unit cell. Water thus cannot be removed from A-type starch without a complete destruction of its crystalline structure. The double helices of B-polymorph are packed into a hexagonal unit cell, P6₁ space group,⁶⁷ and thus the arrangement is more open allowing for a presence of larger number of water molecules, located in a central channel surrounded by six double helices. Here as many as thirty-six water molecules are located in the unit cell between the six double helices,⁶⁸ creating a “column” of water surrounded by the hexagonal network. Finally, V-type polymorph is arranged into a single, left-handed helix, where the hydroxyl groups of the glucose units all lie nearly in the plane of the ring, resulting in a larger hydrophobic central cavity.

Figure 2 shows the pXRD pattern for the native starch and different starch-[C₂mim][OAc] films. Native RMS showed the typical A-type pattern, with strong reflections at 2θ of about 15° and 23° and an unresolved doublet at 2θ of 17° and 18°,

1
2
3 with a few weak peaks at 2θ of about 26° , 30° , and 33° .^{55, 69} For the plasticized samples,
4
5 the doublet at 2θ of 17° and 18° disappeared, suggesting a complete loss of the A-type
6
7 pattern. Besides, the plasticized samples displayed the weak V_H -type pattern as shown by
8
9 sharp peaks at 2θ of 7° , 13° , and 20° ,⁵⁹ and the modest B-type pattern as indicated by
10
11 strong reflections at 2θ of 5° , 17° , 22° and 24° .^{55, 69} The V_H -type crystalline structure is
12
13 commonly observed in processed starch, which is caused by the rapid recrystallization of
14
15 single-helical structures of amylose during cooling after processing.⁵⁹ While the
16
17 plasticized RMS had both (newly-formed) V_H -type and B-type crystalline structures, the
18
19 crystallinity was low as indicated by the reduced XRD intensities. In particular, IL21-
20
21 T55-H75 and IL21-T65-H75 were predominantly amorphous. Based on these results, the
22
23 combination of high $[C_2mim][OAc]$ and moisture contents could make the starch chains
24
25 too mobile to arrange into crystals during the processing and conditioning.
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

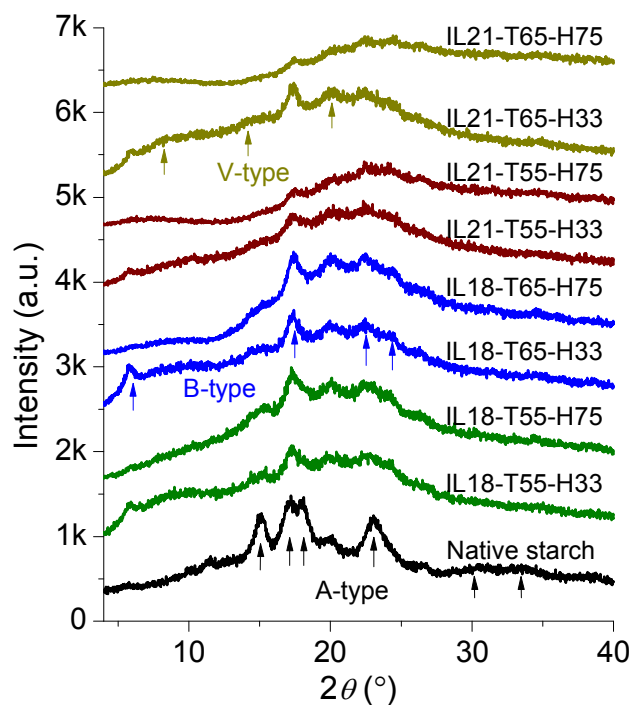


Figure 2. pXRD patterns for native starch and starch-[C₂mim][OAc] films.

Table 2 lists the XRD parameters for the changes in crystalline structure. The total crystallinity (X_c) of the native starch was 38.62%, including 37.53% for the A-type crystalline structure and the rest 1.09% for V-type. IL21-T55-H33 had reduced X_c of just 4.66% (containing 3.99% for B-type and 0.68% for V-type). With a higher processing temperature, IL21-T65-H33 had higher total X_c and higher X_c for both the B- and V-type crystalline structures. These results suggested a higher temperature could allow stronger interactions between starch and [C₂mim][OAc], which facilitated the rearrangements of starch molecules to form new crystals. However, at 75% RH, these rearrangements might be restricted to some degree, as seen from IL21-55-75 and IL21-65-75 with reduced X_c values. With both high [C₂mim][OAc] and MCs, the interactions of these liquids with

starch hydroxyls could dominate, and thus the interactions between starch molecules were inhibited.

Table 2. Parameters for crystalline structure of native starch and starch-[C₂mim][OAc] films.

Sample	X_c (%) measured by XRD ^a				ATR-FTIR band
	Total	A-type	B-type	V-type	intensity ratio $R_{995/1022}$
Native starch	38.62	37.53	–	1.09	–
IL18-T55-H33	6.63	–	6.01	0.61	2.297 ± 0.026
IL18-T55-H75	6.23	–	5.64	0.59	2.066 ± 0.018
IL18-T65-H33	7.07	–	6.24	0.83	2.282 ± 0.020
IL18-T65-H75	6.53	–	5.77	0.76	2.054 ± 0.022
IL21-T55-H33	4.66	–	3.99	0.68	1.940 ± 0.015
IL21-T55-H75	4.04	–	3.49	0.55	1.829 ± 0.023
IL21-T65-H33	5.27	–	4.24	1.03	2.002 ± 0.028
IL21-T65-H75	4.60	–	3.79	0.81	1.876 ± 0.019

^a XRD values are within ± 1%

ATR-FTIR results can also reflect the change in starch orders. Specifically, the absorption band intensity at 1022 cm⁻¹ relates to the amorphous parts, while that at 995 cm⁻¹ corresponds to the hydrogen bonding and the regularity resulting from molecular rearrangements. Therefore, the band intensity between 995 cm⁻¹ and 1022 cm⁻¹ ($R_{995/1022}$) can be used to study the recrystallization of starch-based materials.⁷⁰ Figure 3 shows the ATR-FTIR spectra for the native starch and starch-[C₂mim][OAc] films, with

the $R_{995/1022}$ values shown in Table 2. It can be seen that $R_{995/1022}$ was increased with processing temperature and starch content, suggesting a higher degree of molecular rearrangements. A higher RH reduced $R_{995/1022}$ ratio, which meant a higher MC did not favor the molecular rearrangements. All these results were consistent with the XRD analysis.


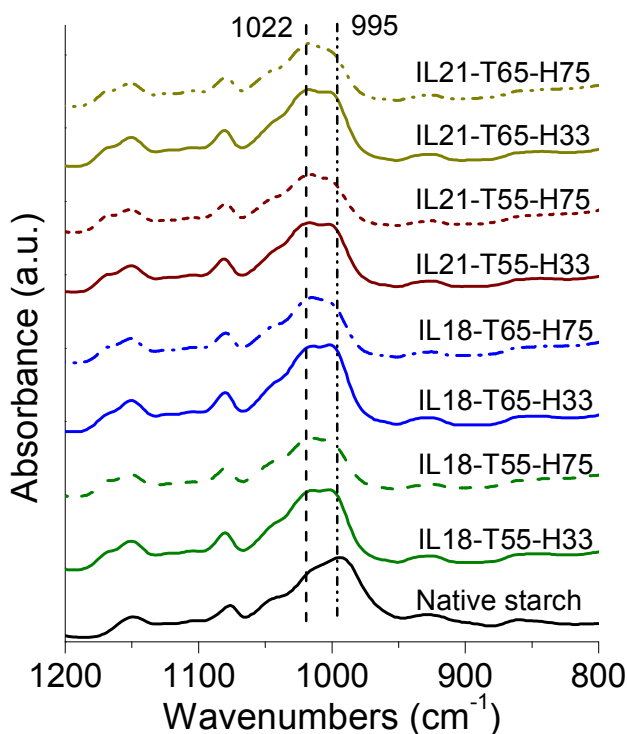


Figure 3. FTIR spectra for native starch and starch-[C₂mim][OAc] films.

Nano-structural features

Figure 4 presents the synchrotron-SAXS patterns for the native starch and starch-[C₂mim][OAc] films. As expected, the native starch had a characteristic SAXS peak at

1
2
3 *ca.* 0.06 \AA^{-1} , ascribed to its native semicrystalline lamellae.⁷¹ IL18-T55-H33 displayed a
4 weaker lamellar peak than the native starch, and a new inflection at *ca.* 0.007 \AA^{-1} . This
5 inflection could be correlated to the Guinier scattering behavior, *i.e.*, a structure with a
6 certain radius of gyration, R_g .⁷² Here, this inflection could be attributed to the aggregates
7 of starch chains (mainly amorphous) with $[\text{C}_2\text{mim}][\text{OAc}]$ -water molecules on the
8 nanoscale (R_g : *ca.* 60 nm) (see Table 3).
9
10
11
12
13
14
15
16
17
18
19

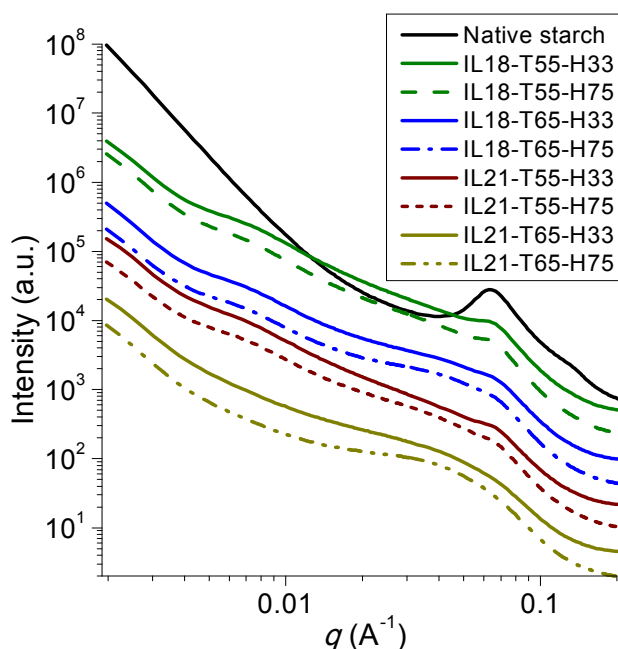

20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43 **Figure 4.** SAXS patterns for native starch and starch- $[\text{C}_2\text{mim}][\text{OAc}]$ films.
44
45
46
47
48

49 Also can be seen in Figure 4 that a lower starch content and/or a higher processing
50 temperature reduced the visibility of the lamellar peak. The other two inflections could be
51 seen at q values lower than the lamellae peak position (*ca.* 0.007 \AA^{-1} and 0.04 \AA^{-1}).
52 Regarding this, the increased $[\text{C}_2\text{mim}][\text{OAc}]$ content and processing temperature
53
54
55
56
57
58
59
60

1
2
3 facilitated the disruption of starch semi-crystalline lamellae, from which the out-phasing
4
5 of starch molecules was enhanced. These starch molecules aggregated into not only the
6
7 aggregates with increased R_g but also new starch aggregates of a smaller size (R_g : *ca.*
8
9 10 nm). At a higher RH, the inflection at *ca.* 0.04 \AA^{-1} became more apparent, indicating
11
12 the stronger feature of starch aggregates, presumably due to the increased content of
13
14 amorphous starch (indicated by the XRD results).
15
16
17
18
19
20
21

22 **Table 3.** Nanostructural parameters for native starch and starch-[C₂mim][OAc] films.
23
24

Sample	$q \text{ (\AA}^{-1}\text{)}$	$d_{\text{Bragg}} \text{ (nm)}$	$R_g \text{ (nm)}$	α
Native starch	0.0629 ± 0.0000	9.99 ± 0.00	–	–
IL18-T55-H33	0.0610 ± 0.0000	10.30 ± 0.00	59.11 ± 1.17	1.97 ± 0.02
IL18-T55-T75	0.0610 ± 0.0000	10.30 ± 0.00	62.80 ± 1.47	1.96 ± 0.02
IL18-T65-T33	0.0610 ± 0.0000	10.30 ± 0.00	68.76 ± 2.33	1.75 ± 0.02
IL18-T65-T75	0.0610 ± 0.0000	10.30 ± 0.00	71.89 ± 3.02	1.69 ± 0.02
IL21-T55-H33	0.0616 ± 0.0008	10.20 ± 0.14	67.45 ± 1.53	1.86 ± 0.01
IL21-T55-H75	0.0610 ± 0.0000	10.30 ± 0.00	69.54 ± 2.07	1.77 ± 0.02
IL21-T65-H33	–	–	8.64 ± 0.08	2.60 ± 0.03
IL21-T65-T75	–	–	8.86 ± 0.05	2.78 ± 0.03

25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48 For IL21-T65-H33/75, no lamellar peak was observed as that for the native starch.
49
50 Instead, at that q range, a “shoulder” peak appeared at *ca.* 0.06 \AA^{-1} . This shoulder
51
52 indicated a molecular organization (both amorphous and ordered starch) on the
53
54 nanoscale.⁷³ In other words, a concomitant reduction in starch content and an increase in
55
56
57
58
59
60

1
2
3 processing temperature prominently enhanced the plasticization of starch by
4 [C₂mim][OAc] acting as flexible spacers (typically between the amylopectin branching
5 points) in starch-based films.⁷⁴⁻⁷⁵ This plasticization effect led to the alignment of
6 amorphous starch and crystallites in a certain distribution range on the nanoscale. Again,
7 the inflection at *ca.* 0.007 Å⁻¹ (*i.e.*, the starch aggregates) disappeared, indicating an
8 increase in the homogeneity of starch-[C₂mim][OAc] films (IL21-T65-H33/75).
9
10
11
12
13
14
15
16
17

18 **Mechanical properties**

19
20 Figure 5 shows the tensile properties of different starch-based films, tensile strength
21 (σ_t), Young's modulus (E), and elongation at break (ϵ_b). All three factors, composition,
22 temperature and relative humidity affected the mechanical properties. Generally, a larger
23 amount of starch resulted in higher tensile strength of the films, *i.e.*, tensile for IL18 was
24 greater than for IL21 films. Contrarily, but expectedly, elongation at break (also known as
25 fracture strain) that represents the capability of a material to resist changes of shape
26 without crack formation was greater with a higher amount of plasticizer ([C₂mim][OAc]-
27 water). The composition affected Young's modulus to somewhat greater extent than it did
28 for tensile and elongation at break, thus films with greater starch content a great increase
29 in Young's modulus. Relative humidity had a larger effect on tensile strength and
30 elongation at break than on Young's modulus, which was independent of humidity but
31 affected by the amount of polymer in films. Both tensile strength and elongation were
32 greater at a lower humidity. Finally, the samples processed at a higher temperature had
33 greater tensile strength and elongation; again humidity was much stronger dependent on
34 composition than on processing and conditioning conditions.
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

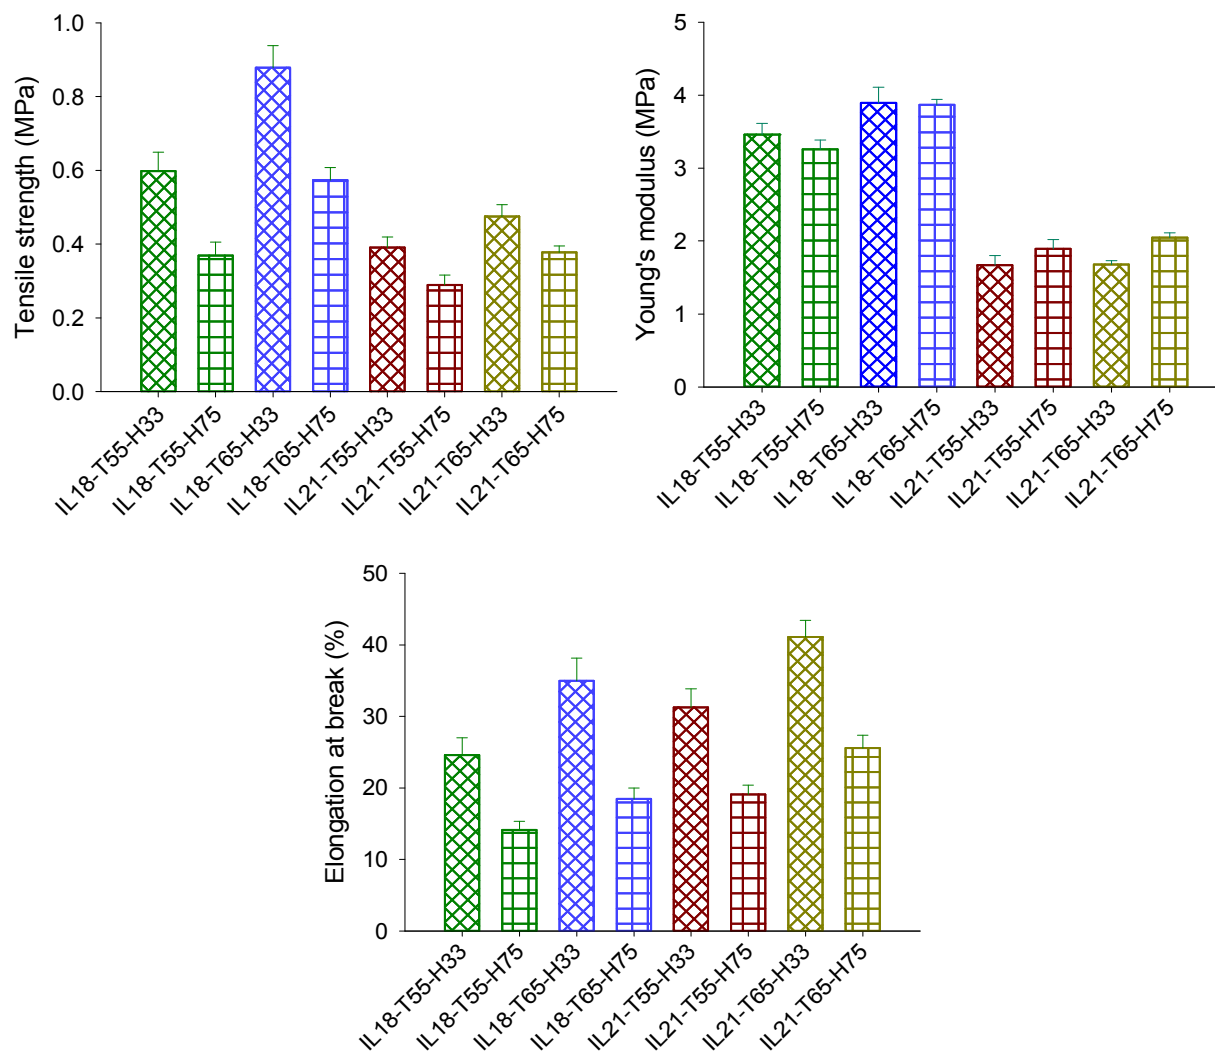


Figure 5. Tensile strength (σ_t), Young's modulus (E), and elongation at break (ϵ_b) of starch- $[\text{C}_2\text{mim}][\text{OAc}]$ films.

A higher processing temperature facilitated plasticization by disrupting the original hydrogen bonding in the native starch allowing the formation of new crystals and molecular entanglements as indicated by the pXRD and SAXS results. These new structures could mechanically reinforce the materials.

1
2
3 Except for IL18-T55-H75 (whose crystallinity X_c was determined to be 6.23 %), the
4 rest of the films follows the clearly pronounced trend: the higher crystallinity, the higher
5 tensile strength. On the other hand, a higher starch content (lower [C₂mim][OAc] content)
6 contributed to higher σ_t and E and lower ε_b (except for the effect of RH on IL21-T55 and
7 IL21-T65). These results were expected considering the plasticization effect of
8 plasticizers ([C₂mim][OAc] and water). Both [C₂mim][OAc] and water could result in a
9 partial disruption of hydrogen bonding between starch molecules, forming hydrogen
10 bonds with –OH sites of starch. Besides, [C₂mim][OAc] and water could effectively
11 increase the free volume of starch macromolecules, resulting in reduced strength and
12 stiffness. Moreover, the plasticizers prevented macromolecular entanglement, resulting in
13 less “connections” between the polymer chains, as demonstrated by higher ε_b . Regarding
14 the opposite trend for IL21-T55-H33/75 and IL21-T65-H33/75 as affected by RH, it was
15 proposed when the samples were well saturated by [C₂mim][OAc] and/or water, both the
16 polymer elasticity and the structural effect of the plasticizers could contribute to lower E .
17 Perhaps the strong interactions between [C₂mim][OAc] and water⁶³ might also influence
18 E .

19
20
21 Also, compared with IL/glycerol-plasticized starch films prepared by a high
22 temperature (e.g. 160 °C) melt processing,⁷⁶⁻⁷⁸ the starch-[C₂mim][OAc] films here
23 developed at mild temperatures had lower σ_t and E , but higher or comparative ε_b . This
24 phenomenon could be mainly attributed to the lower starch content (higher IL-water
25 content) in this work, which contributed to the reduced strength and stiffness and the
26 weakened “connections” between the starch chains for the starch-IL films as discussed
27 above.

Thermal stability

Figure 6 shows the TGA results for the pure IL, the native starch, and different starch-
[C₂mim][OAc] films. It can be seen that pure [C₂mim][OAc] had a big derivative weight
loss peak between about 160 °C and 275 °C, showing its thermal decomposition. This
temperature range of TGA decomposition is exactly in agreement with a previous study
which documented the lower thermal stability of acetate IL's than IL's containing other
anions like [Cl⁻].⁷⁹ Also, starting from about 75 °C, there was a slight weight loss
immediately before the decomposition, which might be ascribed to the evaporation of
impurities present in the starting materials (< 5%, mainly acetic acid, methylimidazole,
and water).

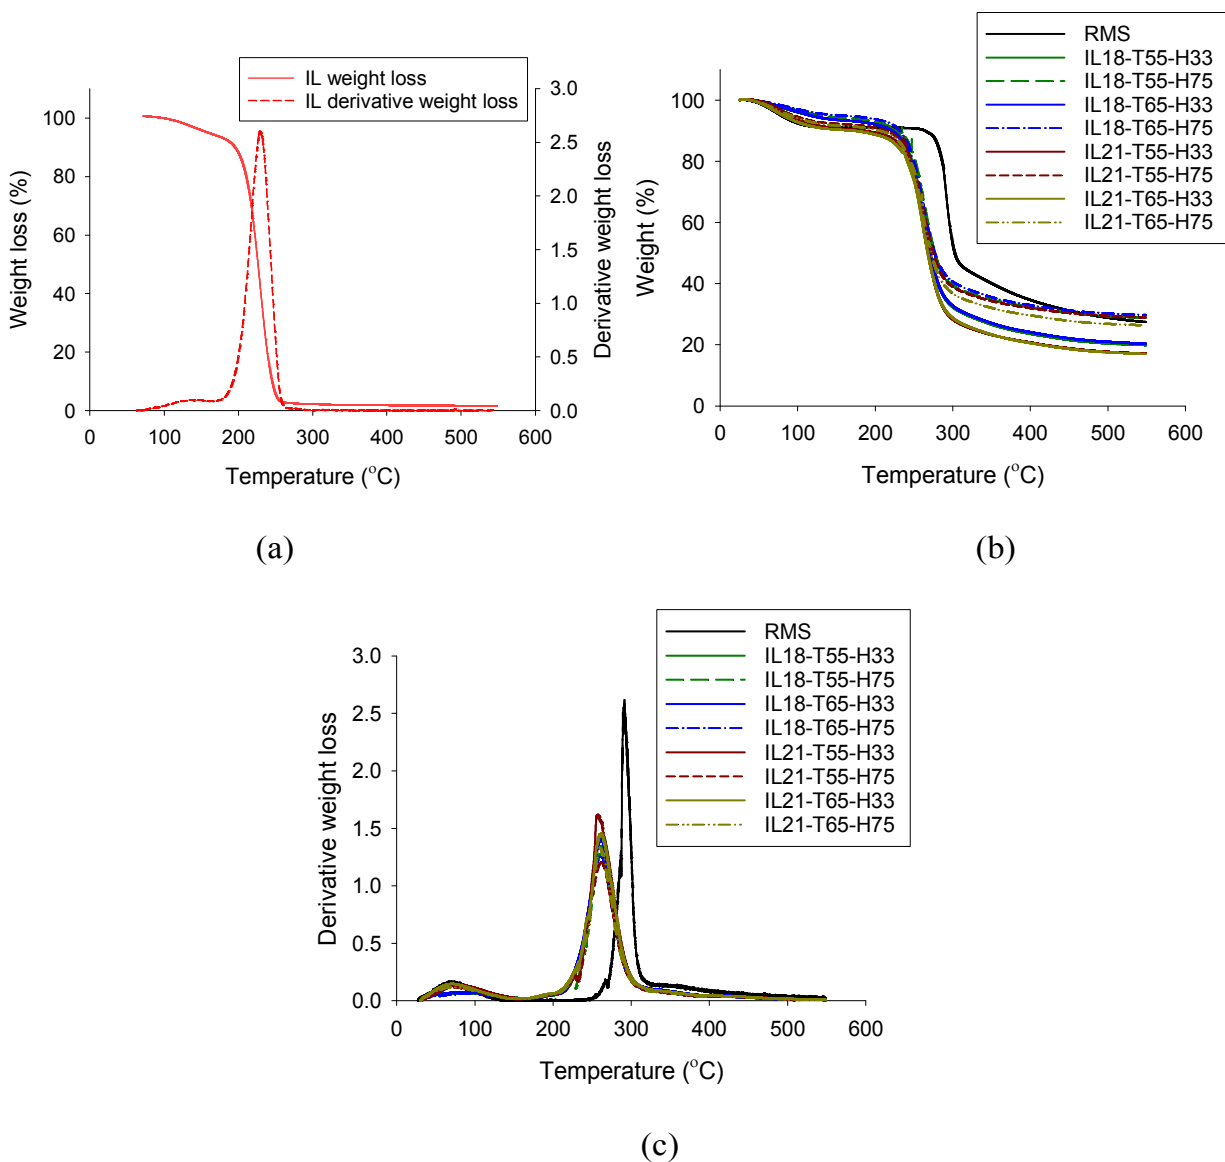


Figure 6. TGA results of the pure IL (a), and different starch-[C₂mim][OAc] films (b, weight loss; c, derivative weight loss).

For the native starch, there was a weight loss between *ca.* 40 °C and 140 °C, due to the evaporation of moisture in the starch. After that, the thermal decomposition of starch occurred between *ca.* 240 °C and 330 °C, which was in agreement with previous

1
2
3 studies.⁸⁰⁻⁸¹ This main peak could be specifically associated with the breakage of long
4
5 chains of starch as well as the thermal oxidation of the glucose rings.⁸⁰
6
7

8 All the processed starch-based films displayed a very similar thermal decomposition
9
10 profile. The main decomposition spanned from 185 °C to 330 °C. As previous studies
11
12 have shown that the thermal decomposition temperature of pure [C₂mim][OAc] was from
13
14 *ca.* 160 °C to 275 °C,⁷⁸ the peak for [C₂mim][OAc] would be overlapped by the thermal
15
16 decomposition peak of the native starch. The main decomposition (the maximum rate of
17
18 weight loss, or derivative peak, at *ca.* 260 °C) occurred much earlier for the processed
19
20 samples than for the native starch (derivative peak at *ca.* 290 °C). Thus, all starch-
21
22 [C₂mim][OAc] films had reduced thermal stability, which was in agreement with the
23
24 previous studies.^{54, 64, 78} No difference was observed for the different starch-based films,
25
26 irrespective of [C₂mim][OAc] or water content and RH. Water/[C₂mim][OAc] should
27
28 have already had reached the maximum interactions with the starch. Hence no effect
29
30 could be seen regarding the thermal stability of the films.
31
32
33
34
35
36

37 **Electrical conductivity**

38
39
40 Electrical conductivity is an important characteristic of [C₂mim][OAc]-plasticized
41
42 polymer films. Wang *et al.*⁴⁴ prepared starch-based films plasticized by 30 wt.% 1-allyl-
43
44 3-methylimidazolium chloride ([Amim][Cl]), which had an electrical conductivity as high
45
46 as 10^{-1.6} S/cm at 14.5 wt.% water content. Sankri *et al.*⁵² showed that starch-based films
47
48 plasticized by 30 wt.% 1-butyl-3-methylimidazolium chloride ([C₄mim][Cl]) had an
49
50 electrical conductivity of 10^{-4.6} S/cm at 13 wt.% water content. Sankri *et al.*⁵² proposed
51
52 that the high electrical conductivity obtained by Wang *et al.*⁴⁴ may be explained by
53
54 increased ion mobility due to the ion pair dissociation mechanism described by Zhang *et*
55
56
57
58
59
60

1
2
3 *al.*³³. This ion pair dissociation might not be apparent for [Amim][Cl] resulting in more
4 localized ions in the case of [Amim][Cl]-plasticized starch. Also, as the ion diffusivity
5 and mobility mainly control the conductivity, the anion should be small with delocalized
6 charge.
7
8
9
10
11

12 Figure 7 shows the electrical conductivity results for the different samples in this work.
13 All the samples had good electrical conductivity ($>10^{-3}$ S/cm). In particular, IL21-T55-
14 H33 and IL21-T55-H75 showed the highest electrical conductivity of 0.0055 and
15 0.0118 S/cm, respectively. Also, for the samples with the same starch content and
16 conditioned at the same RH, a lower processing temperature (55 °C instead of 65 °C)
17 could lead to a higher electrical conductivity. In these results, a higher processing
18 temperature allowed [C₂mim][OAc] and water molecules to strongly interact with the
19 starch, which might have reduced the extent of ion pair dissociation.
20
21
22
23
24
25
26
27
28
29
30

31 From Figure 7, a general trend could be identified that either an increase in RH or
32 [C₂mim][OAc] content could increase the electrical conductivity, with the effect of RH
33 being more significant. Wang, et al.⁴⁴ have indicated that increasing ion concentration by
34 increasing the IL content could improve the conductance of plasticized starch films
35 effectively, and similarly, a high water content can promote a better transference of the
36 anions and cations in the films.
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

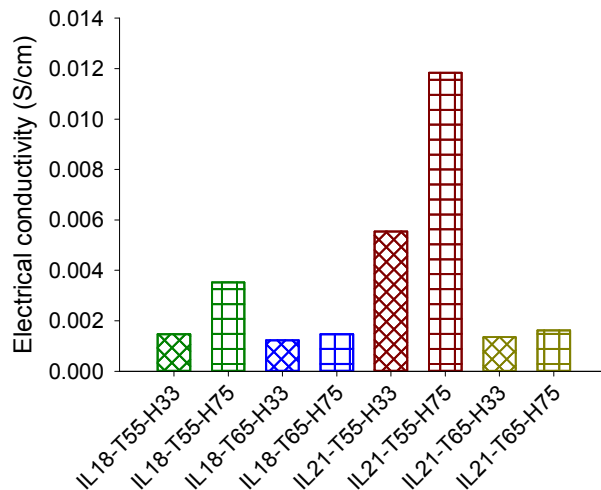


Figure 7. Electrical conductivity of starch-[C₂mim][OAc] films.

CONCLUSION

In this work, we demonstrate that starch can be processed into optically transparent films easily and rapidly by compression molding at mild temperatures (55 °C or 65 °C), which are much lower than the temperatures commonly used in the thermal melt processing of biopolymer (typically over 150 °C). This process was achieved with the use of an ionic liquid, [C₂mim][OAc], which was assisted by a high processing pressure (8 MPa) to disrupt the sophisticated and resistant granule structure of native starch. Moreover, the structure and properties of the resultant films could be tailored by starch content, compression molding temperature, and/or RH used for the sample post-processing conditioning.

With the pXRD analysis, it was found that the simple processing eliminated the original A-type crystalline structure of starch and the processed materials contained newly

1
2
3 formed crystals (predominantly B-type and some V-type). These new structures could
4 contribute to enhanced mechanical properties (σ_t , E , and ε_b). Nonetheless, a higher
5 [C₂mim][OAc] content, lower processing temperature (55 °C), and/or higher RH (75%)
6 during conditioning reduced the crystallinity and even resulted in an amorphous material.
7 Also, SAXS revealed that the processing could destroy the original lamellar structure of
8 starch, and the plasticized starch tended to form a gel-like structure on the nanoscale in a
9 coordinated fashion, which could be favored by increased processing temperature and
10 conditioning RH. The starch-[C₂mim][OAc] films displayed excellent electrical
11 conductivity ($>10^{-3}$ S/cm), which was higher with a lower processing temperature (55 °C)
12 and a higher conditioning RH (75%). With the use of [C₂mim][OAc], the thermal stability
13 of starch-based films was reduced by 30 °K but was independent of the formulation and
14 processing conditions.
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30

31
32 Our findings here could not only benefit the development of advanced biopolymer-
33 based materials with tailored structure and properties such as electrical conductivity but
34 also guide the evolution of material processing techniques for reducing energy
35 consumption as well as enhancing processing versatility to incorporate heat-sensitive
36 ingredients.
37
38
39
40
41
42
43
44

45 ASSOCIATED CONTENT

46
47
48 **Supporting Information (SI)** is available free of charge on the ACS Publications website at
49

50 DOI: xxx. See SI for supplementary Tables and Figure.
51
52

53 AUTHOR INFORMATION

54 55 56 57 **Corresponding Author** 58 59 60

1
2
3 * Fengwei Xie. Email: f.xie@uq.edu.au, fwhsieh@gmail.com
4

5 * Ling Chen. Email: felchen@scut.edu.cn
6
7

8 **Author Contributions**

9
10
11 The manuscript was written through contributions of all authors. All authors have given approval
12
13 to the final version of the manuscript.
14
15

16 **Notes**

17
18 The authors declare no competing financial interest.
19
20
21

22 **ACKNOWLEDGMENT**

23
24 The research leading to these results has received funding from the Australian Research Council
25
26 (ARC) under the Discovery Project No. 120100344. D. K. Wang thanks the awards given by
27
28 ARC Discovery Early Career Researcher Award (No. DE150101687). This work has also been
29
30 supported by the Hubei Provincial Natural Science Foundation of China (No. 2016CFB142), the
31
32 Fundamental Research Funds for the Central Universities (No. 2662016QD008), and the Open
33
34 Project Program of Provincial Key Laboratory of Green Processing Technology and Product
35
36 Safety of Natural Products (No. 201602). The SAXS/WAXS measurements were performed at
37
38 the Australian Synchrotron, Victoria, Australia. This research was undertaken, in part, thanks to
39
40 funding from the Canada Excellence Research Chairs Program.
41
42
43
44
45
46

47 **ABBREVIATIONS**

48
49 IL, ionic liquid; [C₂mim][OAc], 1-ethyl-3-methylimidazolium acetate; SEM, scanning electron
50
51 microscope; XRD, X-ray diffraction; ATR-FTIR, attenuated total reflectance-Fourier transform
52
53 infrared; SAXS, small-angle X-ray scattering; TGA, thermogravimetric analysis.
54
55
56
57
58
59
60

REFERENCES

1. Laurent, A.; Olsen, S. I.; Hauschild, M. Z., Limitations of carbon footprint as indicator of environmental sustainability. *Environ. Sci. Technol.* **2012**, *46* (7), 4100-4108, DOI 10.1021/es204163f.
2. Mekonnen, T.; Mussone, P.; Khalil, H.; Bressler, D., Progress in bio-based plastics and plasticizing modifications. *J. Mater. Chem. A* **2013**, *1* (43), 13379-13398, DOI 10.1039/C3TA12555F.
3. Liu, H.; Xie, F.; Yu, L.; Chen, L.; Li, L., Thermal processing of starch-based polymers. *Prog. Polym. Sci.* **2009**, *34* (12), 1348-1368, DOI 10.1016/j.progpolymsci.2009.07.001.
4. Turner, M. B.; Spear, S. K.; Holbrey, J. D.; Rogers, R. D., Production of bioactive cellulose films reconstituted from ionic liquids. *Biomacromolecules* **2004**, *5* (4), 1379-1384, DOI 10.1021/bm049748q.
5. Turner, M. B.; Spear, S. K.; Holbrey, J. D.; Daly, D. T.; Rogers, R. D., Ionic liquid-reconstituted cellulose composites as solid support matrices for biocatalyst immobilization. *Biomacromolecules* **2005**, *6* (5), 2497-2502, DOI 10.1021/bm050199d.
6. King, C.; Shamshina, J. L.; Gurau, G.; Berton, P.; Khan, N. F. A. F.; Rogers, R. D., A platform for more sustainable chitin films from an ionic liquid process. *Green Chem.* **2017**, *19* (1), 117-126, DOI 10.1039/C6GC02201D.
7. Matet, M.; Heuzey, M.-C.; Pollet, E.; Ajji, A.; Avérous, L., Innovative thermoplastic chitosan obtained by thermo-mechanical mixing with polyol plasticizers. *Carbohydr. Polym.* **2013**, *95* (1), 241-251, DOI 10.1016/j.carbpol.2013.02.052.
8. Xie, D. F.; Martino, V. P.; Sangwan, P.; Way, C.; Cash, G. A.; Pollet, E.; Dean, K. M.; Halley, P. J.; Avérous, L., Elaboration and properties of plasticised chitosan-based exfoliated nano-biocomposites. *Polymer* **2013**, *54* (14), 3654-3662, DOI 10.1016/j.polymer.2013.05.017.
9. Li, M.; Liu, P.; Zou, W.; Yu, L.; Xie, F.; Pu, H.; Liu, H.; Chen, L., Extrusion processing and characterization of edible starch films with different amylose contents. *J. Food Eng.* **2011**, *106* (1), 95-101, DOI 10.1016/j.jfoodeng.2011.04.021.
10. Xie, F.; Halley, P. J.; Avérous, L., Rheology to understand and optimize processibility, structures and properties of starch polymeric materials. *Prog. Polym. Sci.* **2012**, *37* (4), 595-623, DOI

1
2
3 10.1016/j.progpolymsci.2011.07.002.
4

5 11. Xie, F.; Pollet, E.; Halley, P. J.; Avérous, L., Starch-based nano-biocomposites. *Prog. Polym. Sci.*
6 **2013**, *38* (10-11), 1590-1628, DOI 10.1016/j.progpolymsci.2013.05.002.
7

8 12. Pérez, S.; Baldwin, P. M.; Gallant, D. J., Structural features of starch granules I. In *Starch (Third*
9 *Edition)*, James, B.; Roy, W., Eds. Academic Press: San Diego, 2009; pp 149-192, DOI 10.1016/B978-0-
10 12-746275-2.00005-7.
11

12 13. Jane, J.-I., Structural features of starch granules II. In *Starch (Third Edition)*, James, B.; Roy, W.,
13 Eds. Academic Press: San Diego, 2009; pp 193-236, DOI 10.1016/B978-0-12-746275-2.00006-9.
14

15 14. Pérez, S.; Bertoft, E., The molecular structures of starch components and their contribution to the
16 architecture of starch granules: a comprehensive review. *Starch/Stärke* **2010**, *62* (8), 389-420, DOI
17 10.1002/star.201000013.
18

19 15. Fu, Z.-q.; Wang, L.-j.; Li, D.; Wei, Q.; Adhikari, B., Effects of high-pressure homogenization on
20 the properties of starch-plasticizer dispersions and their films. *Carbohydr. Polym.* **2011**, *86* (1), 202-207,
21 DOI 10.1016/j.carbpol.2011.04.032.
22

23 16. Avérous, L., Biodegradable multiphase systems based on plasticized starch: a review. *Polym. Rev.*
24 **2004**, *44* (3), 231-274, DOI 10.1081/MC-200029326.
25

26 17. Campbell, M. R.; Yeager, H.; Abdubek, N.; Pollak, L. M.; Glover, D. V., Comparison of methods
27 for amylose screening among amylose-extender (*ae*) maize starches from exotic backgrounds. *Cereal*
28 *Chem.* **2002**, *79* (2), 317-321, DOI 10.1094/CCHEM.2002.79.2.317.
29

30 18. Moran, J. I.; Cyras, V. P.; Giudicessi, S. L.; Erra-Balsells, R.; Vazquez, A., Influence of the
31 Glycerol Content and Temperature on the Rheology of Native and Acetylated Starches During and After
32 Gelatinization. *J. Appl. Polym. Sci.* **2011**, *120* (6), 3410-3420, DOI 10.1002/app.33347.
33

34 19. Kurtzman, R. H.; Jones, F. T.; Bailey, G. F., Dissolution of starches in dimethylsulfoxide and
35 variations in starches of several species, varieties, and maturities. *Cereal Chem.* **1973**, *50* (312), 312-322.
36

37 20. Knutson, C. A.; Grove, M. J., Rapid method for estimation of amylose in maize starches. *Cereal*
38 *Chem.* **1994**, *7* (5), 469-471.
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
21. Hu, J. B.; Cheng, F.; Lin, Y.; Zhao, K.; Zhu, P. X., Dissolution of starch in urea/NaOH aqueous solutions. *J. Appl. Polym. Sci.* **2016**, *133* (19), DOI 10.1002/app.43390.
 22. Jordan, T.; Schmidt, S.; Liebert, T.; Heinze, T., Molten imidazole - a starch solvent. *Green Chem.* **2014**, *16* (4), 1967-1973, DOI 10.1039/c3gc41818a.
 23. Cowie, J. M. G., Studies on amylose and its derivatives. Part I. Molecular size and configuration of amylose molecules in various solvents. *Die Makromolekulare Chemie* **1960**, *42* (1), 230-247, DOI 10.1002/macp.1960.020420123.
 24. Aburto, J.; Alric, I.; Thiebaud, S.; Borredon, E.; Bikiaris, D.; Prinos, J.; Panayiotou, C., Synthesis, characterization, and biodegradability of fatty-acid esters of amylose and starch. *J. Appl. Polym. Sci.* **1999**, *74* (6), 1440-1451, DOI 10.1002/(SICI)1097-4628(19991107)74:6<1440::AID-APP17>3.0.CO;2-V.
 25. Fang, J. M.; Fowler, P. A.; Tomkinson, J.; Hill, C. A. S., The preparation and characterisation of a series of chemically modified potato starches. *Carbohydr. Polym.* **2002**, *47* (3), 245-252, DOI 10.1016/S0144-8617(01)00187-4.
 26. Heinze, T.; Talaba, P.; Heinze, U., Starch derivatives of high degree of functionalization. 1. Effective, homogeneous synthesis of p-toluenesulfonyl (tosyl) starch with a new functionalization pattern. *Carbohydr. Polym.* **2000**, *42* (4), 411-420, DOI 10.1016/S0144-8617(99)00182-4.
 27. Scott, M. P.; Brazel, C. S.; Benton, M. G.; Mays, J. W.; Holbrey, J. D.; Rogers, R. D., Application of ionic liquids as plasticizers for poly(methyl methacrylate). *Chem. Commun.* **2002**, (13), 1370-1371, DOI 10.1039/b204316p.
 28. Biswas, A.; Shogren, R. L.; Stevenson, D. G.; Willett, J. L.; Bhowmik, P. K., Ionic liquids as solvents for biopolymers: Acylation of starch and zein protein. *Carbohydr. Polym.* **2006**, *66* (4), 546-550, DOI 10.1016/j.carbpol.2006.04.005.
 29. Zhu, S.; Wu, Y.; Chen, Q.; Yu, Z.; Wang, C.; Jin, S.; Ding, Y.; Wu, G., Dissolution of cellulose with ionic liquids and its application: A mini-review. *Green Chem.* **2006**, *8* (4), 325-327, DOI 10.1039/B601395C.
 30. El Seoud, O. A.; Koschella, A.; Fidale, L. C.; Dorn, S.; Heinze, T., Applications of ionic liquids

1
2
3 in carbohydrate chemistry: A window of opportunities. *Biomacromolecules* **2007**, *8* (9), 2629-2647, DOI
4 10.1021/bm070062i.
5

6
7 31. Zakrzewska, M. E.; Bogel-Lukasik, E.; Bogel-Lukasik, R., Solubility of carbohydrates in ionic
8 liquids. *Energy Fuels* **2010**, *24* (2), 737-745, DOI 10.1021/ef901215m.
9

10
11 32. Wilpiszewska, K.; Spychaj, T., Ionic liquids: Media for starch dissolution, plasticization and
12 modification. *Carbohydr. Polym.* **2011**, *86* (2), 424-428, DOI 10.1016/j.carbpol.2011.06.001.
13

14
15 33. Zhang, H.; Wu, J.; Zhang, J.; He, J., 1-Allyl-3-methylimidazolium chloride room temperature
16 ionic liquid: A new and powerful nonderivatizing solvent for cellulose. *Macromolecules* **2005**, *38* (20),
17 8272-8277, DOI 10.1021/ma0505676.
18

19
20 34. Heinze, T.; Schwikal, K.; Barthel, S., Ionic liquids as reaction medium in cellulose
21 functionalization. *Macromol. Biosci.* **2005**, *5* (6), 520-525, DOI 10.1002/mabi.200500039.
22

23
24 35. Qin, Y.; Lu, X.; Sun, N.; Rogers, R. D., Dissolution or extraction of crustacean shells using ionic
25 liquids to obtain high molecular weight purified chitin and direct production of chitin films and fibers.
26 *Green Chem.* **2010**, *12* (6), 968-971, DOI 10.1039/C003583A.
27

28
29 36. Wu, Y.; Sasaki, T.; Irie, S.; Sakurai, K., A novel biomass-ionic liquid platform for the utilization
30 of native chitin. *Polymer* **2008**, *49* (9), 2321-2327, DOI 10.1016/j.polymer.2008.03.027.
31

32
33 37. Xie, H.; Zhang, S.; Li, S., Chitin and chitosan dissolved in ionic liquids as reversible sorbents of
34 CO₂. *Green Chem.* **2006**, *8* (7), 630-633, DOI 10.1039/B517297G.
35

36
37 38. Phillips, D. M.; Drummy, L. F.; Conrady, D. G.; Fox, D. M.; Naik, R. R.; Stone, M. O.; Trulove,
38 P. C.; De Long, H. C.; Mantz, R. A., Dissolution and regeneration of bombyx mori silk fibroin using ionic
39 liquids. *J. Am. Chem. Soc.* **2004**, *126* (44), 14350-14351, DOI 10.1021/ja046079f.
40

41
42 39. Wang, Q.; Chen, Q.; Yang, Y.; Shao, Z., Effect of various dissolution systems on the molecular
43 weight of regenerated silk fibroin. *Biomacromolecules* **2013**, *14* (1), 285-289, DOI 10.1021/bm301741q.
44

45
46 40. Wang, Q.; Yang, Y.; Chen, X.; Shao, Z., Investigation of rheological properties and conformation
47 of silk fibroin in the solution of AmimCl. *Biomacromolecules* **2012**, *13* (6), 1875-1881, DOI
48 10.1021/bm300387z.
49
50
51
52
53
54
55
56
57
58
59
60

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
41. Pu, Y.; Jiang, N.; Ragauskas, A. J., Ionic liquid as a green solvent for lignin. *J. Wood Chem. Technol.* **2007**, *27* (1), 23-33, DOI 10.1080/02773810701282330.
42. Xie, H.; Li, S.; Zhang, S., Ionic liquids as novel solvents for the dissolution and blending of wool keratin fibers. *Green Chem.* **2005**, *7* (8), 606-608, DOI 10.1039/B502547H.
43. Wang, N.; Zhang, X.; Wang, X.; Liu, H., Ionic liquids modified montmorillonite/thermoplastic starch nanocomposites as ionic conducting biopolymer. *Macromol. Res.* **2009**, *17* (5), 285-288, DOI 10.1007/BF03218863.
44. Wang, N.; Zhang, X.; Liu, H.; He, B., 1-Allyl-3-methylimidazolium chloride plasticized-corn starch as solid biopolymer electrolytes. *Carbohydr. Polym.* **2009**, *76* (3), 482-484, DOI 10.1016/j.carbpol.2008.11.005.
45. Wang, N.; Zhang, X.; Liu, H.; Han, N., Ionically conducting polymers based on ionic liquid-plasticized starch containing lithium chloride. *Polym. Polym. Compos.* **2010**, *18* (1), 53-58.
46. Ramesh, S.; Liew, C.-W.; Arof, A. K., Ion conducting corn starch biopolymer electrolytes doped with ionic liquid 1-butyl-3-methylimidazolium hexafluorophosphate. *J. Non-Cryst. Solids* **2011**, *357* (21), 3654-3660, DOI 10.1016/j.jnoncrysol.2011.06.030.
47. Ramesh, S.; Shanti, R.; Morris, E.; Durairaj, R., Utilisation of corn starch in production of 'green' polymer electrolytes. *Mater. Res. Innovations* **2011**, *15* (1), s8, DOI 10.1179/143307511x13031890747291.
48. Ramesh, S.; Shanti, R.; Morris, E., Studies on the thermal behavior of CS:LiTFSI:[Amim] Cl polymer electrolytes exerted by different [Amim] Cl content. *Solid State Sci.* **2012**, *14* (1), 182-186, DOI 10.1016/j.solidstatesciences.2011.11.022.
49. Liew, C.-W.; Ramesh, S., Electrical, structural, thermal and electrochemical properties of corn starch-based biopolymer electrolytes. *Carbohydr. Polym.* **2015**, *124* (0), 222-228, DOI 10.1016/j.carbpol.2015.02.024.
50. Liew, C.-W.; Ramesh, S.; Ramesh, K.; Arof, A. K., Preparation and characterization of lithium ion conducting ionic liquid-based biodegradable corn starch polymer electrolytes. *J. Solid State*

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Electrochem. **2012**, *16* (5), 1869-1875, DOI 10.1007/s10008-012-1651-5.

51. Wang, H.; Gurau, G.; Rogers, R. D., Ionic liquid processing of cellulose. *Chem. Soc. Rev.* **2012**, *41* (4), 1519-1537, DOI 10.1039/C2CS15311D.

52. Sankri, A.; Arhaliass, A.; Dez, I.; Gaumont, A. C.; Grohens, Y.; Lourdin, D.; Pillin, I.; Rolland-Sabaté, A.; Leroy, E., Thermoplastic starch plasticized by an ionic liquid. *Carbohydr. Polym.* **2010**, *82* (2), 256-263, DOI DOI: 10.1016/j.carbpol.2010.04.032.

53. Leroy, E.; Jacquet, P.; Coativy, G.; Reguerre, A. I.; Lourdin, D., Compatibilization of starch–zein melt processed blends by an ionic liquid used as plasticizer. *Carbohydr. Polym.* **2012**, *89* (3), 955-963, DOI 10.1016/j.carbpol.2012.04.044.

54. Xie, F.; Flanagan, B. M.; Li, M.; Sangwan, P.; Truss, R. W.; Halley, P. J.; Strounina, E. V.; Whittaker, A. K.; Gidley, M. J.; Dean, K. M.; Shamshina, J. L.; Rogers, R. D.; McNally, T., Characteristics of starch-based films plasticised by glycerol and by the ionic liquid 1-ethyl-3-methylimidazolium acetate: a comparative study. *Carbohydr. Polym.* **2014**, *111*, 841-848, DOI 10.1016/j.carbpol.2014.05.058.

55. Tan, I.; Flanagan, B. M.; Halley, P. J.; Whittaker, A. K.; Gidley, M. J., A method for estimating the nature and relative proportions of amorphous, single, and double-helical components in starch granules by ¹³C CP/MAS NMR. *Biomacromolecules* **2007**, *8* (3), 885-891, DOI 10.1021/bm060988a.

56. Mateyawa, S.; Xie, D. F.; Truss, R. W.; Halley, P. J.; Nicholson, T. M.; Shamshina, J. L.; Rogers, R. D.; Boehm, M. W.; McNally, T., Effect of the ionic liquid 1-ethyl-3-methylimidazolium acetate on the phase transition of starch: Dissolution or gelatinization? *Carbohydr. Polym.* **2013**, *94* (1), 520-530, DOI 10.1016/j.carbpol.2013.01.024.

57. Young, J. F., Humidity control in the laboratory using salt solutions—a review. *Journal of Applied Chemistry* **1967**, *17* (9), 241-245, DOI 10.1002/jctb.5010170901.

58. Lopez-Rubio, A.; Flanagan, B. M.; Gilbert, E. P.; Gidley, M. J., A novel approach for calculating starch crystallinity and its correlation with double helix content: A combined XRD and NMR study. *Biopolymers* **2008**, *89* (9), 761-768, DOI 10.1002/bip.21005.

- 1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60
59. van Soest, J. J. G.; Hulleman, S. H. D.; de Wit, D.; Vliegthart, J. F. G., Crystallinity in starch bioplastics. *Ind. Crops Prod.* **1996**, *5* (1), 11-22, DOI 10.1016/0926-6690(95)00048-8.
60. Zhang, B.; Chen, L.; Li, X.; Li, L.; Zhang, H., Understanding the multi-scale structure and functional properties of starch modulated by glow-plasma: A structure-functionality relationship. *Food Hydrocolloids* **2015**, *50*, 228-236, DOI 10.1016/j.foodhyd.2015.05.002.
61. Zhang, B.; Zhao, Y.; Li, X.; Li, L.; Xie, F.; Chen, L., Supramolecular structural changes of waxy and high-amylose cornstarches heated in abundant water. *Food Hydrocolloids* **2014**, *35*, 700-709, DOI 10.1016/j.foodhyd.2013.08.028.
62. Zhang, B.; Chen, L.; Xie, F.; Li, X.; Truss, R. W.; Halley, P. J.; Shamshina, J. L.; Rogers, R. D.; McNally, T., Understanding the structural disorganization of starch in water-ionic liquid solutions. *Phys. Chem. Chem. Phys.* **2015**, *17*, 13860-13871, DOI 10.1039/c5cp01176k.
63. Shi, W.; Damodaran, K.; Nulwala, H. B.; Luebke, D. R., Theoretical and experimental studies of water interaction in acetate based ionic liquids. *Phys. Chem. Chem. Phys.* **2012**, *14* (45), 15897-15908, DOI 10.1039/C2CP42975F.
64. Xie, F.; Flanagan, B. M.; Li, M.; Truss, R. W.; Halley, P. J.; Gidley, M. J.; McNally, T.; Shamshina, J. L.; Rogers, R. D., Characteristics of starch-based films with different amylose contents plasticised by 1-ethyl-3-methylimidazolium acetate. *Carbohydr. Polym.* **2015**, *122*, 160-168, DOI 10.1016/j.carbpol.2014.12.072.
65. Derek, R.; Prentice, M.; Stark, J. R.; Gidley, M. J., Granule residues and “ghosts” remaining after heating A-type barley-starch granules in water. *Carbohydr. Res.* **1992**, *227*, 121-130, DOI 10.1016/0008-6215(92)85065-8.
66. Debet, M. R.; Gidley, M. J., Why do gelatinized starch granules not dissolve completely? Roles for amylose, protein, and lipid in granule “ghost” integrity. *J. Agric. Food Chem.* **2007**, *55* (12), 4752-4760, DOI 10.1021/jf070004o.
67. Buléon, A.; Colonna, P.; Planchot, V.; Ball, S., Starch granules: structure and biosynthesis. *Int. J. Biol. Macromol.* **1998**, *23* (2), 85-112, DOI 10.1016/S0141-8130(98)00040-3.

- 1
2
3 68. Zhang, B.; Zhao, Y.; Li, X.; Zhang, P.; Li, L.; Xie, F.; Chen, L., Effects of amylose and
4 phosphate monoester on aggregation structures of heat-moisture treated potato starches. *Carbohydr.*
5 *Polym.* **2014**, *103*, 228-233, DOI 10.1016/j.carbpol.2013.12.055.
6
7
8
9
10 69. Cheetham, N. W. H.; Tao, L., Variation in crystalline type with amylose content in maize starch
11 granules: an X-ray powder diffraction study. *Carbohydr. Polym.* **1998**, *36* (4), 277-284, DOI Doi:
12 10.1016/s0144-8617(98)00007-1.
13
14
15
16 70. Lopez-Rubio, A.; Flanagan, B. M.; Shrestha, A. K.; Gidley, M. J.; Gilbert, E. P., Molecular
17 rearrangement of starch during in vitro digestion: toward a better understanding of enzyme resistant starch
18 formation in processed starches. *Biomacromolecules* **2008**, *9* (7), 1951-8, DOI 10.1021/bm800213h.
19
20
21
22 71. Zhang, B.; Chen, L.; Xie, F.; Li, X.; Truss, R. W.; Halley, P. J.; Shamshina, J. L.; Rogers, R. D.;
23 McNally, T., Understanding the structural disorganization of starch in water-ionic liquid solutions. *Phys.*
24 *Chem. Chem. Phys.* **2015**, *17* (21), 13860-13871, DOI 10.1039/C5CP01176K.
25
26
27
28 72. Beaucage, G., Determination of branch fraction and minimum dimension of mass-fractal
29 aggregates. *Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys.* **2004**, *70* (3), 031401, DOI
30 10.1103/PhysRevE.70.031401.
31
32
33
34 73. Lopez-Rubio, A.; Htoon, A.; Gilbert, E. P., Influence of extrusion and digestion on the
35 nanostructure of high-amylose maize starch. *Biomacromolecules* **2007**, *8* (5), 1564-1572, DOI
36 10.1021/bm061124s.
37
38
39
40 74. Daniels, D. R.; Donald, A. M., Soft material characterization of the lamellar properties of starch:
41 Smectic side-chain liquid-crystalline polymeric approach. *Macromolecules* **2004**, *37* (4), 1312-1318, DOI
42 10.1021/ma030360h.
43
44
45
46 75. Vermeulen, R.; Derycke, V.; Delcour, J. A.; Goderis, B.; Reynaers, H.; Koch, M. H. J.,
47 Gelatinization of starch in excess water: Beyond the melting of lamellar crystallites. A combined wide-
48 and small-angle X-ray scattering study. *Biomacromolecules* **2006**, *7* (9), 2624-2630, DOI
49 10.1021/bm060252d.
50
51
52
53 76. Li, M.; Xie, F.; Hasjim, J.; Witt, T.; Halley, P. J.; Gilbert, R. G., Establishing whether the
54
55
56
57
58
59
60

1
2
3 structural feature controlling the mechanical properties of starch films is molecular or crystalline.
4
5 *Carbohydr. Polym.* **2015**, *117*, 262-270, DOI 10.1016/j.carbpol.2014.09.036.
6

7
8 77. Xie, F.; Flanagan, B. M.; Li, M.; Truss, R. W.; Halley, P. J.; Gidley, M. J.; McNally, T.;
9
10 Shamshina, J. L.; Rogers, R. D., Characteristics of starch-based films with different amylose plasticised
11
12 by 1-ethyl-3-methylimidazolium acetate contents. *Carbohydr. Polym.* **2015**, *122*, 160-168, DOI
13
14 10.1016/j.carbpol.2014.12.072.
15

16
17 78. Zhang, B.; Xie, F.; Zhang, T.; Chen, L.; Li, X.; Truss, R. W.; Halley, P. J.; Shamshina, J. L.;
18
19 McNally, T.; Rogers, R. D., Different characteristic effects of ageing on starch-based films plasticised by
20
21 1-ethyl-3-methylimidazolium acetate and by glycerol. *Carbohydr. Polym.* **2016**, *146*, 67-79, DOI
22
23 10.1016/j.carbpol.2016.03.056.
24

25
26 79. Wendler, F.; Todi, L.-N.; Meister, F., Thermostability of imidazolium ionic liquids as direct
27
28 solvents for cellulose. *Thermochim. Acta* **2012**, *528* (0), 76-84, DOI 10.1016/j.tca.2011.11.015.
29


30
31 80. Liu, X.; Yu, L.; Liu, H.; Chen, L.; Li, L., Thermal decomposition of corn starch with different
32
33 amylose/amylopectin ratios in open and sealed systems. *Cereal Chem.* **2009**, *86* (4), 383-385, DOI
34
35 doi:10.1094/CCHEM-86-4-0383.

36
37 81. Liu, X.; Yu, L.; Xie, F.; Li, M.; Chen, L.; Li, X., Kinetics and mechanism of thermal
38
39 decomposition of cornstarches with different amylose/amylopectin ratios. *Starch/Stärke* **2010**, *62* (3-4),
40
41 139-146, DOI 10.1002/star.200900202.
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

- Table of Contents -

Facile preparation of starch-based electroconductive films with ionic liquid

*Binjia Zhang^{a,b,c}, Fengwei Xie^{*c}, Julia L. Shamshina^{d,e}, Robin D. Rogers^e, Tony McNally^f,
David K. Wang^g, Peter J. Halley^c, Rowan W. Truss^c, Siming Zhao^b, Ling Chen^{*a}*

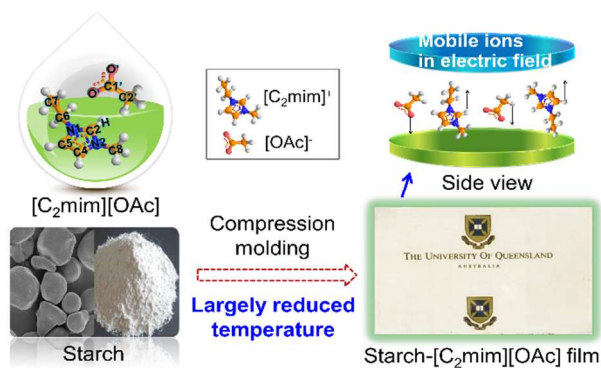

With an ionic liquid (1-ethyl-3-methylimidazolium acetate, [C₂mim][OAc]), starch was facilely processed into optically-transparent electroconductive films at greatly reduced temperature, relative to that commonly used in biopolymer melt processing.