



## Physical Chemistry Chemical Physics

## ARTICLE

## Inorganically Coated Colloidal Quantum Dots in Polar Solvents by Microemulsion-Assisted Method

Received 00th January 20xx,  
Accepted 00th January 20xx

DOI: 10.1039/x0xx00000x

[www.rsc.org/](http://www.rsc.org/)María Acebrón<sup>a,b</sup>, Facundo C. Herrera<sup>c</sup>, Martín Mizrahi<sup>c</sup>, Cristina Navío<sup>b</sup>, Ramón Bernardo-Gavito<sup>b,†</sup>, Daniel Granados<sup>b</sup>, Félix G. Requejo<sup>c\*</sup>, Beatriz H. Juárez<sup>a,b\*</sup>

The dielectric nature of organic ligands capping semiconductor colloidal nanocrystals (NCs) makes them incompatible with optoelectronic applications. For this reason, these ligands are regularly substituted through ligand-exchange processes by shorter (even atomic), or inorganic ones. In this work, an alternative path is proposed to obtain inorganically coated NCs. Differently to a regular ligand exchange processes, the here reported method produces core-shell NCs simultaneously to the removal of the original organic shell. This procedure leads to connected NCs resembling 1D worm-like networks with increased optical properties and polar solubility, in comparison with the initial CdSe NCs. The nature of the inorganic shell has been elucidated by X-ray Absorption Near Edge Structure (XANES), Extended X-ray Absorption Fine Structure (EXAFS) and X-ray Photoelectron Spectroscopy (XPS). The 1D morphology along with the lack of long insulating organic ligands and the higher solubility in polar media turns these structures very attractive for their further integration into optoelectronic devices.

## Introduction

Current technology demands very efficient, robust and versatile emitting systems for their integration as active layers into optoelectronic devices. To this aim, colloidal semiconductor nanocrystals (NCs) are promising candidates due to their tunable electronic and optical properties.<sup>[1,2]</sup> Although fine control over size, size-distribution, shape, and composition of colloidal NCs has been achieved, further control over the surface chemistry turns essential for their integration into devices, where radiative and non-radiative paths, electronic coupling and carrier mobilities govern their conductivity, and eventually, their performance.<sup>[3,4]</sup>

Since 1993, the hot-injection<sup>[5]</sup> method has proved its versatility and superior potential to control size, shape, composition and crystallinity, as the NCs are produced in high boiling point solvents. This method enables the obtaining of highly efficient systems such as

core, core-shell or core-shell-shell structures and also permits the choice of different materials for the core and the shell. By choosing these materials the confinement regime can be defined modulating the electron and hole wave-functions.<sup>[4]</sup> One example of strongly confined system is the CdSe/ZnS core-shell NCs in which the wide band gap of ZnS compare to CdSe leads in high quantum efficiencies and photo-stability. However, the use of non-polar solvents and organic surfactants regularly yields hydrophobic NCs with a long insulating capping shell that limits their use in optoelectronic devices. Since interparticle connection and electronic coupling governs their efficiency, the regular organic insulating capping shell is exchanged by conductive, shorter or even atomic ligands, such as halides.<sup>[6]</sup>

During the last years, the so-called inorganic ligands have attracted special attention because they provide polar soluble NCs and reduce the insulating electrical barrier of organic ligand shells favoring electrical conductivity in 2D quantum-dot monolayers. Among the inorganic ligands, chalcogenides, hydrochalcogenides, mixed chalcogenides, halometallate ligands as well as hydroxy or amino functional groups have been used to replace the initial insulating shells. This replacement yields increased carrier mobilities, for both electrons and holes, and yields better conductivity.<sup>[3, 7-9]</sup> As drawbacks, in many cases, the use of efficient NCs as starting material requires multiple steps reactions and post-treatment procedures are needed to obtain the ligand exchanged NCs. Also, the use of smelly or toxic reactants and the need of a strict oxygen-free working environment may limit their usage.

In this work we report on an alternative approach to grow inorganic shells on CdSe NCs, which implies the removal of the original long insulating ligands to a large extent simultaneously to the fabrication of core-shell structures in friendly working conditions (Room temperature and ambient atmosphere). The here reported

<sup>a</sup> Applied Physical Chemistry Department. Universidad Autónoma de Madrid, Cantoblanco, 28049. Madrid

<sup>b</sup> IMDEA Nanoscience, Faraday 9, Cantoblanco, 28049, Madrid

<sup>c</sup> Instituto de Investigaciones Físicoquímicas Teóricas y Aplicadas (INIFTA), CONICET and FCE, UNLP, CC/16, suc 4, 1900 La Plata, Argentina

<sup>†</sup> Present address: Physics Department, Lancaster University, United Kingdom LA1 4YB

Electronic Supplementary Information (ESI) available: TEM images of NCs networks (Figure S1), CdSe core characterization by X-ray Absorption Spectroscopy (Figure S2 and Table S1). EDX analyses (Table S2 and S6). Size histograms of initial NCs, and treated NCs (Figure S3). Small Angle X-ray Scattering results of samples in microemulsion (Figures S4, S5 and Tables S3, S4 and S5). Photoluminescence response after one month (Figure S6). XPS results in the S2P region (Figure S7) and fitted values to Zn K-edge EXAFS oscillations (Table S7).

## ARTICLE

procedure yields coated colloidal NCs with better optical properties than the initial ones and increased solubility in polar solvents such as ethanol, isopropanol or formamide. The employed treatment combines the Successive Ionic Layer Adsorption Reaction (SILAR) and the use of Water-in-Oil (W/O) microemulsions as reaction media to grow controlled monolayers on CdSe seeds previously produced by hot-injection. In these W/O microemulsions the small drops of water act as nanoreactors in which the shells growth takes place.

The use of microemulsions for NCs synthesis dates from the 80's, when Brus and coworkers were able to produce CdSe NCs with tunable ligand spheres.<sup>[10]</sup> During the following decade a great effort was made to improve this methodology to synthesize CdS, CdSe, and Cd<sub>1-x</sub>Zn<sub>x</sub>S NCs with different morphologies,<sup>[11]</sup> CdS superlattices,<sup>[12]</sup> and CdS@SiO<sub>2</sub> nanocomposites.<sup>[13]</sup> There are certain benefits derived from the use of microemulsions as nanoreactors, such as the performance of lower rate reactions and ligand exchange procedures without precipitation at room temperature (RT) (for a given composition), in well suspended NCs dispersions. Examples of concomitant ligand removal and shell formation have been previously reported in the coverage of oleic acid, dodecylamine and octadecylamine capped-NCs with SiO<sub>2</sub>,<sup>[14]</sup> which renders the final encapsulated nanocomposites soluble in solvents of higher polarity.

The combination of these methodologies, namely, hot injection, SILAR, and microemulsions involves the removal of the initial ligand shell to a high extent and triggers the connection between NCs. In contrast to regular ligand exchange processes, where the NCs are regularly synthesized by multiple-steps reactions and the insulating ligands are replaced to provide NCs compatibility, the here proposed procedure benefits from the lack of organic ligands and, at the same time, allows the synthesis of type I or quasi-type II core-shell structures. These new NCs form 1D networks with increased solubility in polar media and improved optical properties. We believe these features can be very promising to obtain NCs for further progress in the formation of NCs solids with expected high carrier mobilities or active layers in optoelectronic devices.

## Experimental

**Chemicals.** Cadmium oxide Puratonic (CdO, 99.998 %) and octadecylphosphonic acid (ODPA, 97 %) were purchased from Alfa Aesar. Trioctylphosphine (TOP, 90 %), Igepal CO-520 (poly(5)oxyethylene-4-nonylphenylether), thioacetamide (TA, ≥ 99.0 %), thiocarbamide (TC, ≥ 99.0 %), zinc acetate dihydrated (ZnAc, ≥ 98.0 %), octadecene (ODE, 90 %) and Coumarin 6 (98 %) were purchased from Sigma Aldrich. Trioctylphosphine oxide (TOPO, 98 %) was purchased from Merck. Absolute ethanol (99.8 %), cyclohexane (99.5 %), formamide (≥ 99.5 %), isopropanol (≥ 99.8 %) and chloroform (99.6 %) were purchased from Sharlau. ZnS, hydrated ZnSO<sub>4</sub>, CdSO<sub>4</sub> and ZnO were used as references for X-ray Absorption Near Edge Structure (XANES) spectroscopy. All chemicals were used directly without further purification.

**CdSe NCs Synthesis.** The CdSe NCs were synthesized according to a previously reported hot-injection method with some modifications.<sup>[15]</sup> For the reaction, 0.06 g of CdO, 3g of TOPO and 0.280 g of ODPA were placed in a three neck round flask under inert atmosphere and the temperature was set at 150 °C. At this temperature a red solution was obtained and degassed for one hour under vacuum. Later, the temperature was increased to 340 °C for the Cd (ODPA) complex formation, leading to a colorless solution. Once the complex is formed, the temperature was decreased to 300 °C and 1.8 ml of TOP were added. Further, the temperature was

increased to 320 °C and 0.43 ml of a Se@TOP solution (0.058 g of Se dissolved in 0.360g of TOP) was injected. Afterwards, the heating mantle was removed and the solution was left to recover room temperature (RT). Once the NCs are formed the solution was filtered through a 0.45 μm PTFE filter to remove the unreacted organic products and the sample was washed by four cycles of centrifugation and re-dispersion using hexane as solvent and methanol as non-solvent.

**Shells Synthesis in Microemulsion.** Once the ODPA capped NCs were synthesized, they were transferred to a W/O microemulsion containing 0.62 g of Igepal CO-520 as surfactant, 100 μl of water and 12 ml of cyclohexane. For each microemulsion the ratio water/igePAL/cyclohexane was set to 4.9/0.8/94.3 (v/v). The S and Zn precursors were added also as microemulsions with similar composition where the salts were previously dissolved in the water used for the microemulsion preparation. For the preparation of these precursor microemulsions the maximum amount of salts soluble in 100 μl of water were dissolved and the necessary quantity of surfactant and cyclohexane needed to maintain the ratio water/igePAL/cyclohexane were added to these salts solutions.

The concentration and particle size of the initial NCs are estimated from both TEM and UV-Vis spectra,<sup>[16]</sup> and the necessary amount of S and Zn precursor for the formation of one monolayer of ZnS was calculated according to the SILAR method<sup>[17]</sup>. The necessary amount of S microemulsion was calculated taking into the account the S precursor concentrations and was added to the NCs microemulsion under stirring (500 RPM) and the mixture was stirred for 48 hours at RT. Later, the calculated amount of Zn microemulsion was added and stirred for further 48 hours. Once the NCs are produced, they are washed by centrifugation and re-dispersion cycles (5 cycles) with chloroform and ethanol. Finally, they were dissolved in polar solvents (formamide, ethanol and isopropanol). The main disadvantage of using microemulsions is the exhaustive cleaning, necessary to isolate the NCs from the microemulsion medium. This is usually overcome by the use of high volumes of solvent/non-solvent during the washing procedure.

## Characterization

**Steady-State Spectroscopy.** Optical absorption measurements were carried out using a Varian Spectrophotometer (Cary 50). Photoluminescence (PL) spectra were recorded in a spectrofluorometer (Horiba JobinYvon Fluoromax-4) using an excitation wavelength of 420 nm and acquiring corrected spectra. The samples were placed in a quartz cuvette and the concentration was maintained constant for comparison of the initial and treated NCs.

**Quantum Yield Measurements.** The relative Quantum Yield (QY) was measured by comparison with an emitting standard (Coumarin 6).<sup>[18]</sup> The QYs were calculated in different media and the solvents refractive indexes were estimated using a hand refractometer model 330. The concentrations were fixed below 0.1 of optical density to avoid reabsorption effects.

**Time Resolved Spectroscopy.** The decay rates were acquired employing a time correlated single photon counting card (PicoQuant, TimeHarp 260 PICO Single) with 25 ps base resolution. The samples in solution were placed in a quartz cuvette and pumped with a tunable supercontinuum laser (Fianium SC400+ superchrome) delivering 10 ps long pulses with λ = 450 nm and a repetition rate of 40 MHz (25 ns). The emission is collected with a multi-core optical fiber and passed through a 0.5 m spectrometer (Andor Shamrock)

with a 300 l/mm grating. The filtered emission was detected by an avalanche photo diode (TAU-SPAD-250) with <250 dark counts per second, timing resolution of 300 ps and a detection efficiency of 50 % at 550 nm. The measured instrument response function is 600 ps at 550 nm.

**Transmission Electron Microscopy (TEM).** Low Resolution Transmission Electron Microscopy (TEM) images were obtained using a JEOL JEM 1010 microscope operating at 100 kV. High Resolution Electron Transmission Microscopy (HRTEM) images and Energy Dispersive X-Ray (EDX) analysis were obtained in a JEOL 2100F microscope operating at 200 kV and equipped with an EDX detector INCA x-sight from Oxford Instruments. Size histograms were obtained from HRTEM images. HRTEM images at low acceleration voltages were obtained at Centro Nacional de Microscopía Electrónica at Universidad Complutense de Madrid with a JEOL JEM ARM200cF microscope operating at 80 kV working in Transmission and Scanning-Transmission (HRSTEM) mode in bright and dark fields and using the High-Angle Annular Dark-Field (HAADF) detector to acquire the elemental mappings. The elemental distribution was performed by Electron Energy Loss Spectroscopy (EELS).

**X-ray Photoelectron Spectroscopy (XPS).** XPS measurements were performed under Ultra High Vacuum (UHV) conditions (with a base pressure of  $7 \times 10^{-10}$  mbar) using a monochromatic Al K-alpha line as exciting photon source ( $h\nu = 1486.7$  eV), a hemispherical energy analyzer (SPHERA-U7, analyzer pass energy was set to 20 eV for the XPS measurements to have a resolution of 0.6 eV) and to compensate the built up charge on the sample surface during the measurements it was necessary the use of a Flood Gun (FG-500, Specs) with low energy electrons of 3 eV and 40  $\mu$ A.

**Small Angle X-ray Scattering (SAXS).** SAXS experiments were performed at INIFTA (La Plata, Argentina) facilities using a XEUS 1.0 equipment from XENOCs with a K $\alpha$ -Copper radiation microsource. A PILATUS-100K detector was used with 513 mm sample detector distance. One-dimensional curves were obtained by integration of the 2D data using the Foxtrot program. The scattering intensity distributions as a function of the scattering vector ( $q$ ) were obtained in the  $q$  range between 0.028 and 0.65  $\text{\AA}^{-1}$ . The samples were placed in borosilicate glass capillary tubes of 1.5 of diameter and 10  $\mu$ m of wall thickness.


**X-ray Absorption (XAS).** XAS experiments were measured at the SXS (S and Cd edges) and XAFS2 (Zn and Se edges) beamlines at the LNLS (Laboratório Nacional de Luz Síncrotron), Campinas, Brazil. X-ray Absorption Near Edge Structure (XANES) spectroscopy measurements at the S K (2472 eV) and Cd L3 (3538 eV) edges were carried out using a double-crystal monochromator equipped with InSb(111) crystals giving an energy resolution of 2 eV at the S K-edge, and 1 eV at the Cd L3-edge. Experiments were performed in a vacuum of  $10^{-9}$  mbar at RT. The incident beam intensity ( $I_0$ ) was measured using a thin foil of Al located before the main chamber. Samples were dropped on carbon tape to be measured in Total Electron Yield (TEY) and fluorescence modes, collecting the emitted current for each incident photon-energy with an electrometer connected to the sample. To avoid self-absorption effects<sup>[19]</sup> only results on TEY mode are presented and analyzed in this work. The photon energies were calibrated using a Mo or Ag metallic foil and setting the first inflection point to the energy of the Mo L3 absorption edge (2520 eV) for S, and to the Ag L2 absorption edge (3524 eV) for Cd measurements. The final XANES spectra were obtained after background subtraction and normalization to the postedge intensity. Extended X-ray Absorption Fine Structure (EXAFS) experiments at the Zn K edge (9659 eV) spectra were measured at room temperature

using a Si(111) single channel-cut crystal monochromator in fluorescence mode. An ionization chamber was used to detect the incident flux and a 15-element germanium solid-state detector was used to sense the fluorescence signal from the sample. ZnSO<sub>4</sub>, ZnS and ZnAc reference samples were measured in transmission mode with two ion chambers as detectors. The EXAFS data was extracted from the measured absorption spectra by standard methods using the ATHENA software which is part of the IFFEFIT package.<sup>[20]</sup> The Fourier transforms were calculated using the Hanning filtering function. EXAFS modeling was carried out using the ARTEMIS program (IFFEFIT package). Structural parameters (coordination numbers, bond lengths and their Debye–Waller factor) were obtained by a nonlinear least-squares fit of the theoretical EXAFS signal to the data in R space by Fourier Transforming both the experimental and calculated data. Theoretical scattering path amplitudes and phase shifts for all paths used in the fits were calculated using the FEFF code.<sup>[21]</sup> The passive reduction factor S02 was restrained to the value of 0.86. This value was obtained fitting the EXAFS spectrum of metallic Zn foil constraining the coordination number of the first coordination shell to 12.

**Fourier Transform Infrared Spectroscopy (FTIR).** FTIR spectra were acquired using a FT-IR Spectrum 100 PerkinElmer spectrometer equipped with an Attenuated Total Reflectance (ATR) module. The samples were prepared by drop-casting and dried with an air flow. OPDA powders and cyclohexane were measured directly.

## Results and discussion

Figure 1 shows the followed procedure where ODPA-capped CdSe NCs, synthesized according to a previously reported hot-injection method with some modifications,<sup>[15]</sup> are dispersed in a W/O microemulsion by addition of Igepal, water and cyclohexane to the CdSe NCs dispersion (from (a) to (b)). The shells formation by SILAR is triggered by the controlled addition of S precursor first (c) and, secondly, the Zn precursor (d). The precursor solutions are equally prepared in W/O microemulsions (see Experimental Section for details). The coating reaction and ligand removal will take place in these water drops while after washing and redispersion in polar solvents (e) the particle connection occurs. Further details about experimental procedure can be found in Figure S1, SI.

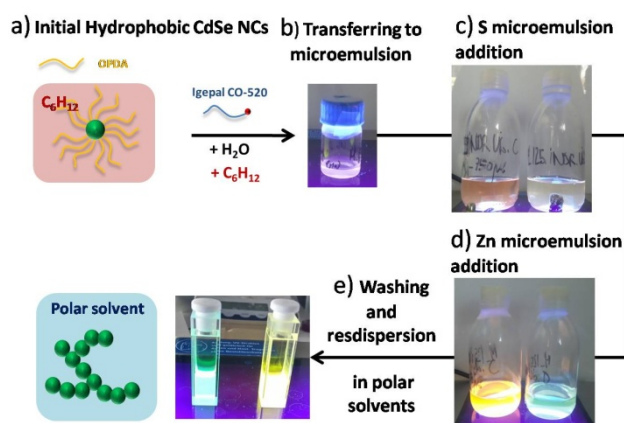

**Fig. 1.** Sketch of the methodology that combines SILAR with water-in-oil microemulsions. CdSe NCs produced by hot injection (a) are included in a microemulsion (b), where different S (c) and Zn precursors (d) are added. Later the samples were washed and redispersed in polar solvents (e).



## ARTICLE


In this work, two different sulfur precursors were used, namely: thioacetamide (TA) and thiocarbamide (TC) which, despite of their structural similarities, yield NCs with different optical properties and thickness coverages. For the Zn-containing microemulsion medium zinc acetate (ZnAc) was chosen based on its previously reported reactivity with  $S^{2-}$  to obtain ZnS-coated NCs.<sup>[22]</sup> These precursors, with mild reactivity, have been widely used to grow CdS and ZnS thin films by chemical bath deposition and CdS NCs.<sup>[23]</sup>

Figure 2 shows TEM, STEM and HRTEM images of initial and treated NCs. After the treatment in microemulsion, the initial CdSe NCs (Figure 2a) yield connected NCs in worm-like 1D structures (Figures 2b and 2c). These networks are obtained regardless the use of TA+ZnAc or TC+ZnAc (more images can be found in Figures S2, S1). As evidenced by the HRTEM images (Figures 2c and S3), the NCs are not fused following the same crystallization orientation (no evidences of oriented attachment are observed),<sup>[24]</sup> but organized in a randomly oriented network. We ascertained that these 1D structures are formed during washing, as no aggregation is visible by SAXS experiments performed with NCs in microemulsion (Figures S4-S5 and Tables S1-S3, S1). In the here reported case, the formation of these 1D structures is mainly promoted by the lack of initial ODPA ligands which are removed to a high extent after TA or TC treatments, although interparticle dipole-dipole interactions may also contribute.<sup>[15, 25]</sup> Indeed, the connected network points to a lack of organic ligands between NCs. This ligand removal is ascertained by EDX (table S4, S1), showing that the initial P content (from phosphonic species) decreases 70 % after the coverage treatments. Also, the differences observed in FTIR spectra of initial and treated NCs support the removal of phosphonic species (Figure S6, S1).

The CdSe NCs size distribution obtained from HRTEM images (Figure S7, S1) is  $2.6 \pm 0.2$  nm according to statistics obtained from at least 300 NCs, and in good agreement with the 2.5 nm diameter estimated from the UV-Vis spectrum<sup>[16]</sup> and data extracted by XANES spectroscopy and EXAFS experiments at Se K-edge (Figure S8 and Table S5, S1). The average diameters of the NCs networks upon treatment obtained by HRTEM are  $3.7 \pm 0.4$  nm for TA+ZnAc NCs and  $2.7 \pm 0.3$  nm for TC+ZnAc ones, evidencing a thicker shell for TA+ZnAc treatment. Size histograms of initial and treated NCs can be found in Figure S9, S1. Indeed, the formation of a thicker shell for TA+ZnAc treated NCs is also evidenced by SAXS, where the data were fitted to a core@shell model of homogeneous and rigid spheres (Figure S4 and Tables S1-S2, S1). We attribute the thicker film formation to the higher decomposition rate of TA compared to TC for  $S^{2-}$  production, as previously reported.<sup>[26]</sup> Elemental distribution profiles for TA+ZnAc treated samples were obtained by EELS (Figures 2d-g) working in STEM mode and using the HAADF detector. The maps and STEM images are recorded at 80 KV in order to preserve the stability of the samples under the irradiation beam. The elemental maps in Figure 2e and 2f, corresponding to the area selected in Figure 2d, show a layer of S and Zn around the underneath NCs. Filtering the cores, an homogenous Zn and S layer through the whole network is evidenced in Figure 2g.

Figure 3 shows the optical properties of initial CdSe NCs (Figure 3a), TA+ZnAc (Figure 3b) or TC+ZnAc treated NCs (Figure 3c). For TA treated NCs (Figure 3b), a redshift in the optical properties compared to the initial cores is apparent during the first addition of TA (red line) and a further slight shift upon the Zn precursor addition (brown line). The observed total redshift of the absorption edge is  $44 \pm 10$  nm. This shift can be explained assuming a well-known type-I or quasi type-II core-shell NCs,<sup>[1]</sup> where a concomitant increase in the photoluminescence (PL) response is also recorded. In contrast, in the


case of TC+ZnAc treated NCs (Figure 2e), a blue-shifted absorption edge ( $-13 \pm 5$  nm) and only initial moderate PL increments (slightly red-shifted respect to the initial cores) are observed. The shifts of the absorption edges shown correspond to the means calculated for at least 10 different samples.

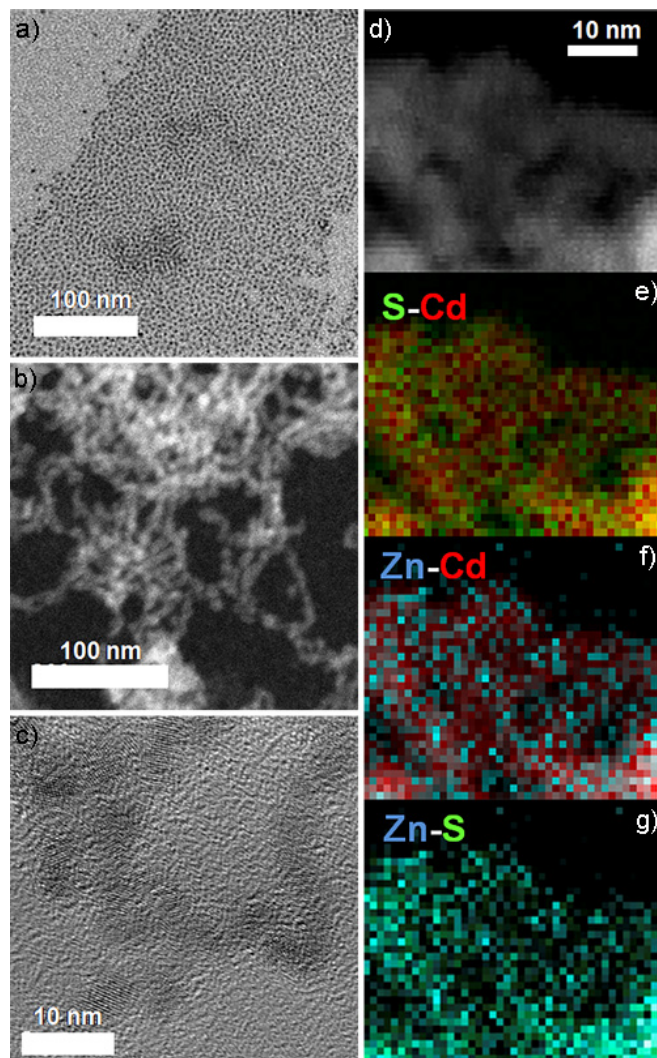

**Fig. 2.** (a) TEM image of initial CdSe NCs. (b) and (c) correspond to a STEM and HRTEM images, respectively of the 1D networks obtained after the coating process. Lack of original ligands is inferred in the NCs networks, where the well-defined distances between NCs in the original colloidal dispersions are removed. (e-g) show EELS elemental analysis maps of TA+ZnAc treated NCs acquired at 80 KV of the region shown in (d) (Scale bar 10 nm) evidencing the presence of Zn and S as coating.

As evidenced by EDX (Table S6, S1), for TA and TA+ZnAc treated samples the S content is higher than for TC and TC+ZnAc treated ones (for comparable reaction times), which would explain the previously mentioned formation of a thicker shell and a more red-shifted optical response, as reported in Figure 3b compared to Figure 3c.

On the other hand, the blueshifted absorption edge for TC treated samples could be explained by a partial surface oxidation and

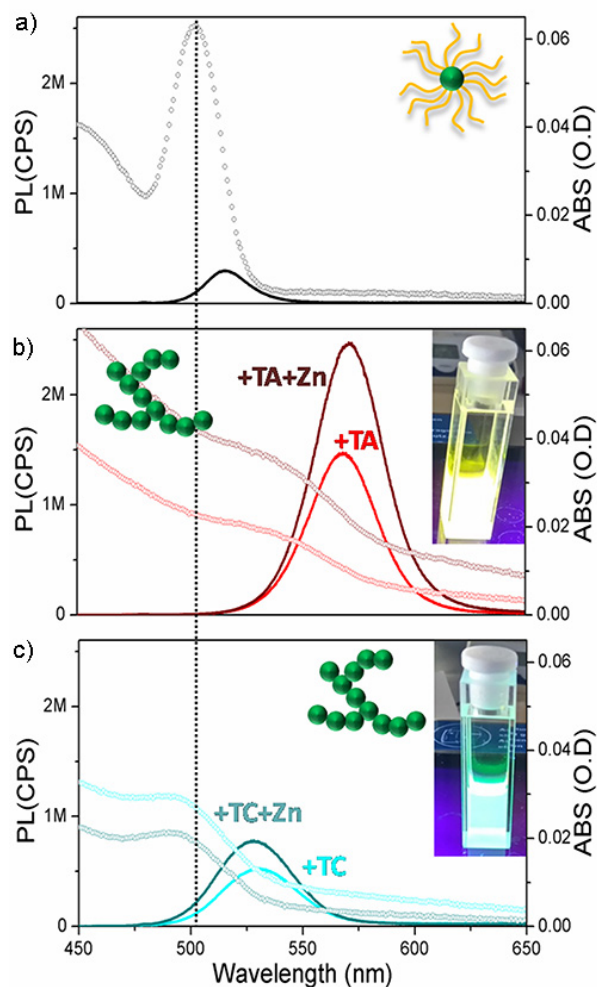

**Fig. 3.** Absorption (open circles) and emission spectra (full lines) of initial NCs (a), NCs treated with TA and TC+ZnAc (b) and NCs treated with TC and TA+ZnAc (c). All spectra were acquired in the microemulsion medium. Insets show networks dispersions in isopropanol.

concomitant mean effective size reduction of the cores.<sup>[27, 28]</sup> However, since no evidences of oxidized Cd species are detected by XANES (further discussed in Figure 6), the degradation of the CdSe cores can be discarded. Likewise, since the blue shifted absorption edge is evident before Zn addition,  $Zn_xCd_{1-x}Se$  alloyed structures can also be discarded.<sup>[27, 29]</sup> Other factors affecting the absorption edge include the substitution of long aliphatic ligands by shorter and more electronegative ones,<sup>[30]</sup> and/or a slight reduction of the particle size produced by a feasible moderate etching of the CdSe cores by TC. In addition, the treated samples show improved stability in polar solvents, as it is observed in the optical images shown as insets in Figures 3b and 3c corresponding to treated samples in isopropanol.

In order to characterize in more detail the effects of the coverage in the optical properties of the CdSe cores, the decay dynamics of initial and treated NCs were analyzed and summarized in Figure 4 and Table 1. Figure 4a and Table 1 show the decay dynamics of initial CdSe NCs (1), NCs treated with TA (2) and TA+ZnAc in microemulsion (3), and in ethanol (4). The same data for NCs treated with TC (5), and TC+ZnAc (6 and 7) can be found in Figure 4b and Table 1. The decay rates of both initial and treated NCs fit quite well with a double exponential function suggesting that multiple processes are involved in the decays. From these fittings two different decay rates can be calculated:  $\tau_1$ , corresponding to a very fast decay which has been

previously related to non-radiative processes involving surface defects, and  $\tau_2$ , which has been ascribed to the excitonic recombination.<sup>[31]</sup> While the faster decay rate slightly increases for both treated samples respect to the initial CdSe NCs in microemulsion, it slightly decreases in ethanol pointing to a possible passivation effect of the surfactant (IGEPAL), or TA or TC leading to TA-Cd(Zn) and TC-Cd(Zn) complexes anchored to the formed shell which could be also suggested from FTIR spectra analysis (Figure S6, SI).<sup>[32]</sup> Although visual inspection of figure 4 could suggest that the treated NCs in microemulsion decay faster than the initial ones we have to clarify that this is because of a mayor contribution of  $\tau_1$  to the decay curves of the treated samples. In fact, the slower decay rate,  $\tau_2$ , remains practically constant for any treatment in microemulsion and only decreases in ethanol, which can be the result of either, the already mentioned removal of the ligands or complexes during the washing procedure, or the interparticle connection triggering electronic coupling in the 1D structures, as previously observed for chalcogenide NCs,<sup>[9]</sup> or even both of them.


Figure 5 shows the temporal evolution of the QYs as the precursors are added for both types of samples in microemulsion, and the final QYs measured in isopropanol as polar medium. Maximum QYs values of 10 % and 20 % in alcohol are obtained for samples treated with TC+ZnAc (Figure 5a) and TA+ZnAc (Figure 5b), respectively. This means that using an experimentally comfortable method (RT and ambient conditions) we are able to produce polar soluble NCs free of insulating ligands to a large extent presenting, at least, 4 times higher QYs than the original hydrophobic ones. The QY values for TA+ZnAc treated CdSe cores in isopropanol are comparable to QYs obtained for NCs coated with inorganic ligands.<sup>[8]</sup> Interestingly, while the QY values in microemulsion are initially larger for TA treated samples, the opposite tendency is observed for TC treated ones.

These last samples show increased PL response for longer reaction times (after 1 month), indicating a possible surface reconstruction with time according to the slower decomposition rate of TC (Figure S10, SI).<sup>[26]</sup>


In order to understand the nature of the grown shells and the NCs composition synchrotron X-ray Absorption Spectroscopy (XAS) measurements were performed. XANES results can be seen in Figure 6 where Figure 6a includes the S-K edge measurements for the samples treated with TA+ZnAc and TC+ZnAc. Spectra of hydrated  $ZnSO_4$  and  $CdSO_4$  are also included for comparison. As it can be seen in both samples, two main peaks at 2474 and 2483 eV can be observed. The former peak is present as major contribution in sulfide compounds, and the latter is present in the sulfate salts.<sup>[19, 33]</sup> Thus, according to the S-K edge spectra a combination of sulfides and sulfates seems feasible, although out of these spectra,

**Table 1.** Life time values and fitting parameters of initial and treated NCs measured in microemulsion and ethanol.

Sample	$\tau_1$ (ns)	$\tau_2$ (ns)	R
(1) Initial NCs (microemulsion)	1.5	11.3	0.99718
(2) NCs + TA (microemulsion)	1.9	9.9	0.99892
(3) NCs+ TA + ZnAc (microemulsion)	2.2	11.3	0.99877
(4) NCs + TA + ZnAc (EtOH)	1.0	4.8	0.99908
(5) NCs + TC (microemulsion)	1.8	11.3	0.99838
(6) NCs+ TC + ZnAc (microemulsion)	2.0	12.1	0.99834
(7) NCs + TC + ZnAc (EtOH)	1.2	7.1	0.99793

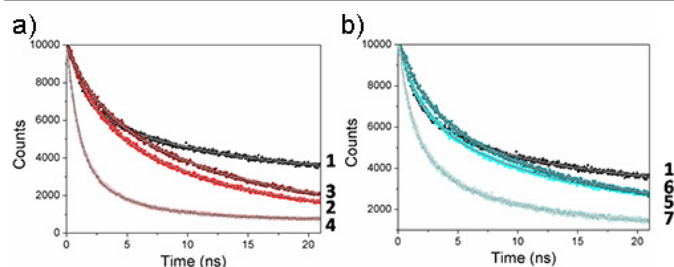

**Fig. 4.** (a) Decay dynamics (dotted lines) and double exponential fittings (solid lines) of Initial NCs (black (1)), TA treated NCs (red (2)), TA+ZnAc treated NCs (wine (3)) and washed TA+ZnAc treated NCs redispersed in ethanol (empty wine dots (4)) (b) Decay dynamics of initial NCs (black (1)), TC treated NCs (cyan(5)), TC+ZnAc treated NCs (dark cyan (6)) and washed TC+ZnAc treated NCs redispersed in ethanol (empty dark cyan dots (7)).

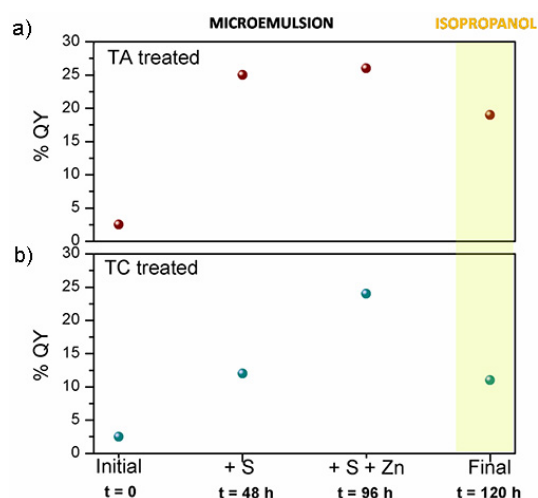

**Fig. 5.** QYs of TA and TA+ZnAc treated NCs (a) and TC and TC+ZnAc treated NCs (b) in microemulsion. Final QYs after treatment and washing procedure measured in isopropanol.

clear identification to ZnS and/or CdS cannot be ascribed univocally and the contribution of Cd or Zn sulfides and sulfates cannot be distinguishable from these results. The presence of sulfides and sulfates in both samples is also ascertained by XPS (Figure S11, SI) where signals close to 162 eV are assigned to sulfides and the more oxidized signals close to 170 eV could be associated to sulfates. The additional Cd L-XANES (Figure 6b) and Zn K-XANES (Figure 6c) results allow a direct interpretation about sulfides and sulfates species. Cd XANES spectra of TA+ZnAc and TC+ZnAc samples drastically differ from CdSO<sub>4</sub> (figure 6b), whose Cd L-XANES spectrum shows a pre-peak at 3538 eV. Moreover, both Cd XANES spectra corresponding to our samples are very close to the already reported for CdS.<sup>[34]</sup>


However, as reported in Table S6, SI, the initial Se content decreases for both TA and TC treated samples concomitantly to the increase of S content, which is probably related to the formation of a CdSe<sub>1-x</sub>S<sub>x</sub> layer. In both treated samples the S+Se/Cd ratio remains constant after sulfur addition, suggesting that an intermediate CdSe<sub>1-x</sub>S<sub>x</sub> shell is also rather feasible. In this sense, our Cd L-XANES characterization is also compatible with the presence of CdSe<sub>1-x</sub>S<sub>x</sub>, already reported elsewhere.<sup>[35]</sup>

Additionally, from Zn K-XANES (Figure 6c) and Zn K-edge EXAFS (Figure 6d) results, the chemical state of Zn in our samples respect to several reference compounds can be compared. In both cases the observations are conclusive in respect to the presence of sulfides and sulfates species. According to the energy edge position (see vertical

reference line in Figure 6c) and general feature of the spectra, the chemical state of Zn in both NCs cannot be associated with ZnS and is closer to oxidized Zn-species, in particular close to ZnSO<sub>4</sub>, which is in principle reasonable since this is the outer element in the NCs. This is confirmed by EXAFS results just by the only inspection of the first coordination shell from the Fourier Transform of EXAFS oscillations for each sample and reference compounds (Figure 6d and Table S7, SI). It is important to note that XANES and EXAFS experiments at the Zn K-edge were performed in microemulsion and samples were not exposed to air. This means that any change at the chemical state of Zn is only due the chemistry of the synthesis. On the contrary, XANES experiments at Cd L-edge were performed in vacuum after dropping of the liquid sample on carbon tape. Since the chemical Cd-state is not oxidized this implies the good stability of the core of the NCs.

Gathering the whole picture, the closest description of the final NCs composition is compatible with a CdSe core with a CdSe<sub>1-x</sub>S<sub>x</sub> and/or CdS intermediate shell, which is responsible for the optical behavior of the samples according to type I or quasi type II structures and a more external oxidized shell of Zn-species, as suggested by the sketches depicted in Figure 7.

The treatments yield 1D NCs with improved optical properties relative to the initial CdSe cores. All samples show improved stability in formamide, isopropanol and ethanol respect to non-polar solvents such as toluene or cyclohexane. While the solvent coordination to metal surface atoms and solvent density may help to stabilize the worm-like NCs, the presence of the more oxidized external shell of undefined Zn species could be responsible for the increased stability in polar media.

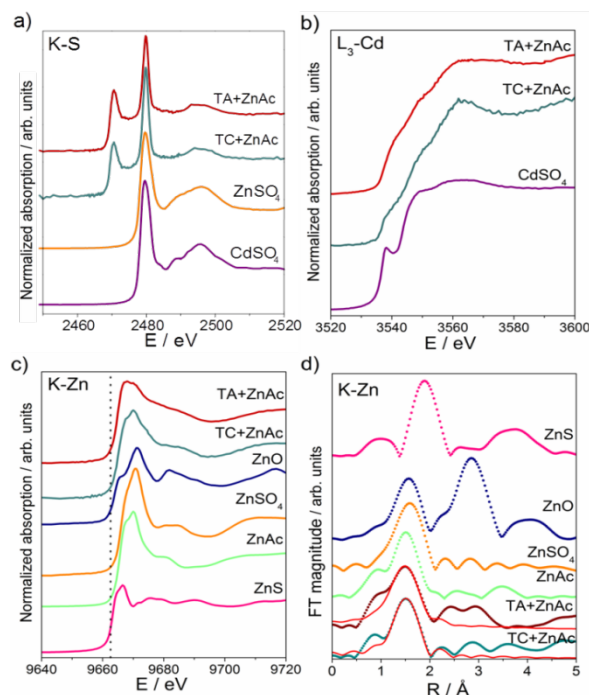

**Fig. 6.** XANES characterization of TA+ZnAc and TC+ZnAc treated samples along with reference compounds at K S-edge (a), L<sub>3</sub> Cd-edge and Zn K-edge (b), K Zn-edge (c). Vertical dotted line in (c) indicates the energy position for Zn K-edge. Fourier transform of Zn K-edge EXAFS oscillations of the samples and reference Zn-compounds (d). Red full lines correspond to fitted functions (see Table S7, SI).



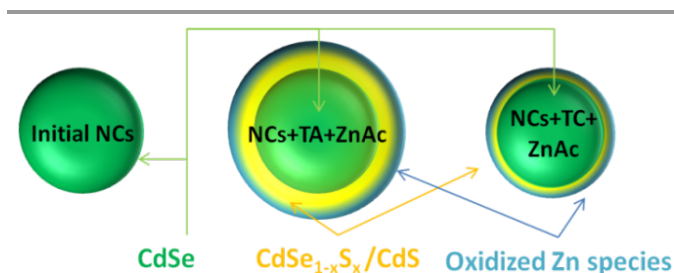


Fig. 7. Suggested morphology for initial NCs and NCs treated with TA+ZnAc and TC+ZnAc, respectively.

## Conclusions

In summary, a combined methodology including the Successive Ionic Layer Adsorption Reaction (SILAR) and water-in-oil (W/O) microemulsions is applied to control the growth of inorganic layers on previously produced CdSe seeds. The procedure involves almost the complete elimination of the original phosphonate ligand shell simultaneously to the synthesis of core-shell structures, and yields 1D worm-like NCs structures. The obtained NCs are composed of several species, including sulfides and more oxidized ones, as confirmed by X-ray Absorption Near Edge Structure, Extended X-ray Absorption Fine Structure and X-ray Photoelectron Spectroscopy. The developed procedure improves the optical properties of the initial NCs according to type-I or quasi type-II core-shell structures, reduces their solubility in non-polar media and increases the sample stability in polar media such as isopropanol, ethanol, and formamide. This networks showing higher solubility in polar media can be advantageous to produce active layers for optoelectronic applications.

## Acknowledgements

BHJ and MA thank for funding in the frame of the following projects: S2013/MIT-2740 from Comunidad de Madrid, MAT2013-47395-C4-3-R and FIS2015-67367-C2-1-P from the Spanish Ministry of Economy and Competitiveness. BHJ, FCH, MM and FGR thank CEAL-AL/2015-15 from UAM-Banco Santander FCH, MM and FGR also acknowledge to CONICET (Project PIP 1035). XAFS experiments were partially supported by Project XAFS2-20150061 (LNLS, Campinas, Brazil). The authors acknowledge to Dr. L. Giovanetti and Dr. C. Huck-Iriart for SAXS experiments, which were performed at INIFTA thanks to project "Nanopymes" (EropeAid/132184/D/ SUP/AR-Contract-896). DG acknowledges RYC-2012-09864, MAD2D-CM Program (S2013/MIT-3007) and SUPER-MNAN (ESP2015-65597-C4-3-R) for financial support.

## References

[1] C. d. M. Donega, *Chemical Society Reviews* 2011, **40**, 1512.  
 [2] A. Rogach, *Semiconductor Nanocrystal Quantum Dots. Synthesis, Assembly, Spectroscopy and Applications*, Springer-Verlag Wien, 2008.  
 [3] M. V. Kovalenko, L. Manna, A. Cabot, Z. Hens, D. V. Talapin, C. R. Kagan, V. I. Klimov, A. L. Rogach, P. Reiss, D. J. Milliron, P. Guyot-Sionnest, G. Konstantatos, W. J. Parak, T. Hyeon, B. A. Korgel, C. B. Murray, W. Heiss, *ACS Nano* 2015, **9**, 1012.

[4] D. V. Talapin, J.-S. Lee, M. V. Kovalenko, E. V. Shevchenko, *Chemical Reviews* 2010, **110**, 389.  
 [5] C. B. Murray, D. J. Norris, M. G. Bawendi, *Journal of the American Chemical Society* 1993, **115**, 8706.  
 [6] J. Tang, K. W. Kemp, S. Hoogland, K. S. Jeong, H. Liu, L. Levina, M. Furukawa, X. Wang, R. Debnath, D. Cha, K. W. Chou, A. Fischer, A. Amassian, J. B. Asbury, E. H. Sargent, *Nature Materials* 2011, **10**, 765; Z. Ning, Y. Ren, S. Hoogland, O. Voznyy, L. Levina, P. Stadler, X. Lan, D. Zhitomirsky, E. H. Sargent, *Advanced Materials* 2012, **24**, 6295; A. H. Ip, S. M. Thon, S. Hoogland, O. Voznyy, D. Zhitomirsky, R. Debnath, L. Levina, L. R. Rollny, G. H. Carey, A. Fischer, K. W. Kemp, I. J. Kramer, Z. Ning, A. J. Labelle, K. W. Chou, A. Amassian, E. H. Sargent, *Nature Nanotechnology* 2012, **7**, 577.  
 [7] M. V. Kovalenko, M. Scheele, D. V. Talapin, *Science* 2009, **324**, 1417; M. V. Kovalenko, M. I. Bodnarchuk, J. Zaumseil, J.-S. Lee, D. V. Talapin, *Journal of the American Chemical Society* 2010, **132**, 10085; M. A. Boles, D. V. Talapin, *Science* 2014, **344**, 1340; F. Liu, J. Zhu, J. Wei, Y. Li, L. Hu, Y. Huang, O. Takuya, Q. Shen, T. Toyoda, B. Zhang, J. Yao, S. Dai, *The Journal of Physical Chemistry C* 2014, **118**, 214; K. J. Schnitzenbaumer, G. Dukovic, *The Journal of Physical Chemistry C* 2014, **118**, 28170; H. Zhang, J. Jang, W. Liu, D. V. Talapin, *ACS Nano* 2014, **8**, 7359; K. J. Schnitzenbaumer, T. Labrador, G. Dukovic, *The Journal of Physical Chemistry C* 2015, **119**, 13314.  
 [8] A. Nag, M. V. Kovalenko, J.-S. Lee, W. Liu, B. Spokoyny, D. V. Talapin, *Journal of the American Chemical Society* 2011, **133**, 10612.  
 [9] H. Zhang, B. Hu, L. Sun, R. Hovden, F. W. Wise, D. A. Muller, R. D. Robinson, *Nano Letters* 2011, **11**, 5356.  
 [10] M. L. Steigerwald, A. P. Alivisatos, J. M. Gibson, T. D. Harris, R. Kortan, A. J. Muller, A. M. Thayer, T. M. Duncan, D. C. Douglass, L. E. Brus, *Journal of the American Chemical Society* 1988, **110**, 3046.  
 [11] J. Cizeron, M. P. Pileni, *The Journal of Physical Chemistry* 1995, **99**, 17410; C.-C. Chen, C.-Y. Chao, Z.-H. Lang, *Chemistry of Materials* 2000, **12**, 1516; N. Pinna, K. Weiss, H. Sack-Kongehl, W. Vogel, J. Urban, M. P. Pileni, *Langmuir* 2001, **17**, 7982; N. Pinna, K. Weiss, J. Urban, M. P. Pileni, *Advanced Materials* 2001, **13**, 261; Y.-w. Jun, S.-M. Lee, N.-J. Kang, J. Cheon, *Journal of the American Chemical Society* 2001, **123**, 5150; B. A. Simmons, S. Li, V. T. John, G. L. McPherson, A. Bose, W. Zhou, J. He, *Nano Letters* 2002, **2**, 263; S. Libert, D. V. Goia, E. Matijević, *Langmuir* 2003, **19**, 10673.  
 [12] W. Xu, D. L. Akins, *Materials Letters* 2004, **58**, 2623.  
 [13] S.-Y. Chang, L. Liu, S. A. Asher, *Journal of the American Chemical Society* 1994, **116**, 6739.  
 [14] R. Koole, M. M. van Schooneveld, J. Hilhorst, C. de Mello Donegá, D. C. Hart, A. van Blaaderen, D. Vanmaekelbergh, A. Meijerink, *Chemistry of Materials* 2008, **20**, 2503.  
 [15] L. Carbone, C. Nobile, M. De Giorgi, F. D. Sala, G. Morello, P. Pompa, M. Hytch, E. Snoeck, A. Fiore, I. R. Franchini, M. Nadasan, A. F. Silvestre, L. Chiodo, S. Kudera, R. Cingolani, R. Krahne, L. Manna, *Nano Letters* 2007, **7**, 2942.  
 [16] W. W. Yu, L. Qu, W. Guo, X. Peng, *Chemistry of Materials* 2003, **15**, 2854; J. Jasieniak, L. Smith, J. v. Embden, P. Mulvaney, M. Califano, *The Journal of Physical Chemistry C* 2009, **113**, 19468.  
 [17] R. Xie, U. Kolb, J. Li, T. Basché, A. Mews, *Journal of the American Chemical Society* 2005, **127**, 7480; J. J. Li, Y. A. Wang, W. Guo, J. C. Keay, T. D. Mishima, M. B. Johnson, X. Peng, *Journal of the American Chemical Society* 2003, **125**, 12567; M. Ristov, G. Sinadinovski, I. Grozdanov, M. Mitreski, *Thin solid films* 1989, **173**, 53.  
 [18] M. Grabolle, M. Spieles, V. Lesnyak, N. Gaponik, A. Eychmüller, U. Resch-Genger, *Analytical Chemistry* 2009, **81**, 6285.  
 [19] F. Jalilievand, *Chemical Society Reviews* 2006, **35**, 1256.

## ARTICLE

- [20] B. Ravel, M. Newville, ATHENA, ARTEMIS, HEPHAESTUS: data analysis for X-ray absorption spectroscopy using IFFEFIT 2005, **12**, 537.
- [21] S. I. Zabinsky, J. J. Rehr, A. Ankudinov, R. C. Albers, M. J. Eller, *Physical Review B* 1995, **52**, 2995.
- [22] W. L.-D. Li Wen-Zhe, GAO Rui, DONG Hao-Peng, NIU Guang-Da, GUO, Q. Y. Xu-Dong, [*J. Acta Phys. -Chim. Sin* 2013, **29**, 2345.
- [23] R. M. Souto, S. González, A. Arévalo, *Journal of Electroanalytical Chemistry and Interfacial Electrochemistry* 1987, **216**, 273; M. Krunks, J. Madarász, T. Leskelä, A. Mere, L. Niinistö, G. Pokol, *Journal of Thermal Analysis and Calorimetry* 2003, **72**, 497; Q. Yu, C.-Y. Liu, *The Journal of Physical Chemistry C* 2009, **113**, 12766; S. Jana, B. B. Srivastava, N. Pradhan, *The Journal of Physical Chemistry C* 2013, **117**, 1183.
- [24] C. Schliehe, B. H. Juárez, M. Pelletier, S. Jander, D. Greshnykh, M. Nagel, A. Meyer, S. Foerster, A. Kornowski, C. Klinke, H. Weller, *Science* 2010, **329**, 550.
- [25] R. L. Penn, *The Journal of Physical Chemistry B* 2004, **108**, 12707.
- [26] G. T. Patterson, *Metals Speciation, Separation, and Recovery*, Vol. 2, CRC Press, 1990.
- [27] K. Židek, M. Abdellah, K. Zheng, T. Pullerits, *Scientific Reports* 2014, **4**, 7244.
- [28] W. Lee, H. Kim, D.-R. Jung, J. Kim, C. Nahm, J. Lee, S. Kang, B. Lee, B. Park, *Nanoscale Research Letters* 2012, **7**, 1.
- [29] X. Zhong, M. Han, Z. Dong, T. J. White, W. Knoll, *Journal of the American Chemical Society* 2003, **125**, 8589.
- [30] J. R. McBride, A. D. Dukes, M. A. Schreuder, S. J. Rosenthal, *Chemical Physics Letters* 2010, **498**, 1; M. A. Schreuder, J. R. McBride, A. D. Dukes, J. A. Sammons, S. J. Rosenthal, *The Journal of Physical Chemistry C* 2009, **113**, 8169.
- [31] C. de Mello Donegá, M. Bode, A. Meijerink, *Physical Review B* 2006, **74**, 085320; M. Cirillo, T. Aubert, R. Gomes, R. Van Deun, P. Emplit, A. Biermann, H. Lange, C. Thomsen, E. Brainis, Z. Hens, *Chemistry of Materials* 2014, **26**, 1154; W. Nan, Y. Niu, H. Qin, F. Cui, Y. Yang, R. Lai, W. Lin, X. Peng, *Journal of the American Chemical Society* 2012, **134**, 19685.
- [32] F. Jalilehvand, Z. Amini, K. Parmar, *Inorganic Chemistry* 2012, **51**, 10619; M. Ranjbar, M. Yousefi, R. Nozari, S. Sheshmani, *Int. J. Photoenergy* 2013, **9**, 203.
- [33] R. Alonso Mori, E. Paris, G. Giuli, S. G. Eeckhout, M. Kavčič, M. Žitnik, K. Bučar, L. G. M. Pettersson, P. Glatzel, *Analytical Chemistry* 2009, **81**, 6516.
- [34] G. Van der Snickt, J. Dik, M. Cotte, K. Janssens, J. Jaroszewicz, W. De Nolf, J. Groenewegen, L. Van der Loeff, *Analytical Chemistry* 2009, **81**, 2600.
- [35] M. W. M. Y. M. Yiu, L. Liu, Y. Hu, and T.K. Sham, AIP Conference Proceedings 2014, **1590**, 26-31.