



Tran, Lam Thi Ngoc and Meneghetti, Marcello and Zur, Lidia and Tran, Van Thi Thanh and Lukowiak, Anna and Zonta, Daniele and Righini, Giancarlo C. and Ferrari, Maurizio (2016) SnO₂ based glasses : A viable photonic system. In: 18th Italian National Conference on Photonic Technologies (Fotonica 2016). IET, Stevenage. ISBN 9781785612688 , <http://dx.doi.org/10.1049/cp.2016.0895>

This version is available at <https://strathprints.strath.ac.uk/60983/>

Strathprints is designed to allow users to access the research output of the University of Strathclyde. Unless otherwise explicitly stated on the manuscript, Copyright © and Moral Rights for the papers on this site are retained by the individual authors and/or other copyright owners. Please check the manuscript for details of any other licences that may have been applied. You may not engage in further distribution of the material for any profitmaking activities or any commercial gain. You may freely distribute both the url (<https://strathprints.strath.ac.uk/>) and the content of this paper for research or private study, educational, or not-for-profit purposes without prior permission or charge.

Any correspondence concerning this service should be sent to the Strathprints administrator: strathprints@strath.ac.uk

SnO₂ BASED GLASSES: A VIABLE PHOTONIC SYSTEM

Thi Ngoc Lam Tran^{1,2,3}, *Marcello Meneghetti*^{4,2}, *Lidia Zur*^{5,2}, *Thi Thanh Van Tran*⁶, *Anna Lukowiak*⁷,
Daniele Zonta^{1,2,8}, *Giancarlo C. Righini*^{5,9}, *Maurizio Ferrari*^{2,5}

1 Department of Civil, Environmental and Mechanical Engineering, University of Trento, Via Mesiano, 77, 38123 Trento, Italy

2 IFN-CNR CSMFO Lab., and FBK Photonics Unit via alla Cascata 56/C Povo, 38123 Trento, Italy

3 Ho Chi Minh City University of Technical Education, 1 Vo Van Ngan Street, Linh Chieu Ward, Thu Duc District, Ho Chi Minh City, Vietnam

4 Department of Physics, Via Sommarive 14, Povo, 38123 Trento, Italy

5 Centro di Studi e Ricerche "Enrico Fermi", Piazza del Viminale 1, 00184 Roma, Italy

6 University of Science, Vietnam National University, 227 Nguyen Van Cu Street, Ward 4, District 5, Ho Chi Minh City, Vietnam

7 Institute of Low Temperature and Structure Research PAS, Okolna St. 2, 50-422 Wroclaw, Poland

8 Department of Civil and Environmental Engineering, University of Strathclyde, 75 Montrose Street, Glasgow, G11XJ, UK

9 IFAC - CNR, MiPLab., 50019 Sesto Fiorentino, Italy

**thingoclam.tran@unitn.it*

Keywords: transparent glass-ceramics, SnO₂-SiO₂, rare-earths, luminescence, energy transfer.

Abstract

The present work focuses on sol-gel derived SnO₂-based thin glass-ceramic films doped with Er³⁺ ions, fabricated by dip-coating technique. Our goal is to find a viable fabrication protocol to obtain them. Thin films with a variety of composition were synthesized and their structural, optical and spectroscopic properties were investigated. The FTIR spectra and X-ray diffraction patterns were used to characterize the structure of the thin films. The transparency of the thin film was tested by UV-Vis transmittance measurements. The energy transfer dynamic was investigated by time-resolved spectroscopy and photoluminescence measurements.

1. Introduction

Silica-based materials doped with rare earth ions are widely employed in photonics. However, in pure silica, doping ions easily form clusters which lead to quenching effect due to the ion-ion energy transfer. As a result, the concentration of these active ions is limited. A possible strategy to reduce this problem is to use transparent glass-ceramics. The incorporation of rare earth ions in nanocrystals prevents the aggregation of these ions and allows nanocrystal-ion energy transfer [1]. This phenomenon increases the luminescence quantum yield because SnO₂ has a higher absorption cross section than that one of rare earth ions. Moreover, these glass-ceramic materials merge the unique optical properties of both crystals and glasses [2]. Among the various materials that could be used as nanocrystals embedded in silica matrix, tin dioxide presents some interesting characteristics. SnO₂ is a wide-band gap semiconductor (E_g = 3.6 eV at 300 K) with very low cut-off phonon energy of 630 cm⁻¹ [3]. Increasing as much as possible the concentration of SnO₂ nanocrystals in amorphous SiO₂ is one of the crucial problems. In [4], un-

doped thin films were fabricated with different molar percentages of SnO₂: from 12 mol% to 60 mol% in order to focus on the compositional effects. In this case, the limit of SnO₂ concentration embedded in host material reached 30 mol% instead of 25 mol% like in earlier approaches [5][6]. Van et al [7] recently suggested that Er³⁺ inhibits the growth of SnO₂ crystals on the surface of SiO₂-SnO₂ films, so the effect of rare earth on the SnO₂ crystallization deserves careful investigation.

In this study we synthesize glass-ceramics xSnO₂-(100-x)SiO₂ thin films doped with Er³⁺ ions. Optical, spectroscopic and structural assessment of the samples has been investigated by several characterization techniques.

2. Experimental procedure

2.1. Fabrication of xSnO₂-(100-x)SiO₂ doped with Er³⁺ thin films

The xSnO₂-(100-x)SiO₂ (x = 10, 20 and 30 mol%) glass-ceramic thin films doped with different concentrations of Er³⁺ (1, 2 and 3 mol%) were fabricated by sol-gel route and dip-coating technique. Precursors SnCl₂·2H₂O and Er(NO₃)₃·5H₂O were dissolved into ethanol before being added to the starting solution that had been prepared by mixing tetraethyl orthosilicate (TEOS), ethanol, de-ionized water, and hydrochloric acid as a catalyst. The final mixture was stirred for 16 hours. Then, thin films activated by Er³⁺ were deposited on the high purity silica and silicon substrates by dip-coating technique with the dipping rate of 8 cm/min. After each dip-coating step the film was annealed in air at 150°C for 3 min. After three steps, final thin films were transparent and crack-free after heat-treatment for 1 hour in air at various temperatures ranging from 600°C to 1200°C. Figure 1 shows the diagram illustrating whole fabrication procedure of thin films.

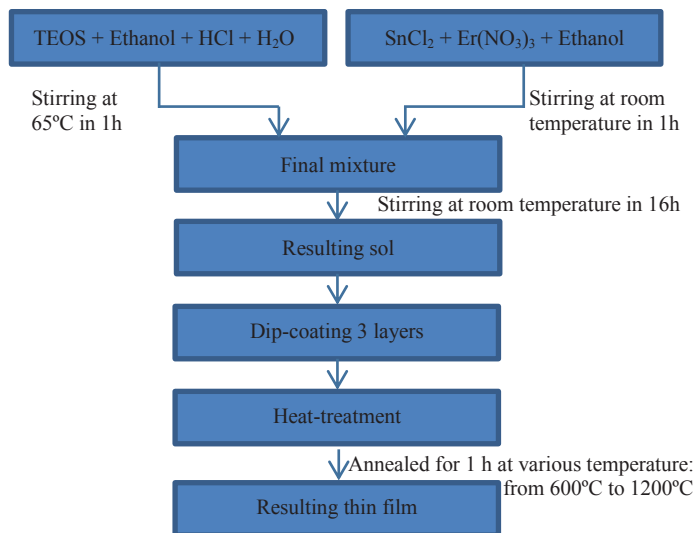


Fig. 1 Flowchart of the fabrication protocol of sol-gel derived $\text{SnO}_2\text{-SiO}_2\text{-Er}^{3+}$ glass-ceramic thin films.

2.2. Characterization of resulting thin films

As mentioned before, the structure, transparency and photoluminescence features of all resulting thin films were characterized. FTIR transmission measurements were performed to get information about structure and residual water and solvent content. The crystallization of tin-dioxide component was studied with X-ray diffraction. In addition, the transparency of the thin films was investigated by UV-Vis transmittance spectra. The photoluminescence of the Er^{3+} ions in the surrounding glass-ceramics environment was employed to investigate the role of SnO_2 nanocrystals as sensitizer of Er^{3+} ions.

3. Results and discussion

3.1. Structure

3.1.1 FTIR

The infrared absorption spectra of the $30\text{SnO}_2\text{-70SiO}_2$ thin film doped with 1 mol% Er^{3+} heat-treated in air at temperature ranging from 600°C to 1200°C for 1 hour is shown in Figure 2. The modes at 1626 cm^{-1} and 3404 cm^{-1} are assigned to the OH group vibrations. These modes are still present in the samples heat-treated at 600°C . With higher annealing temperature, starting from 800°C , they disappear because of the elimination of water from inside the thin films [8].

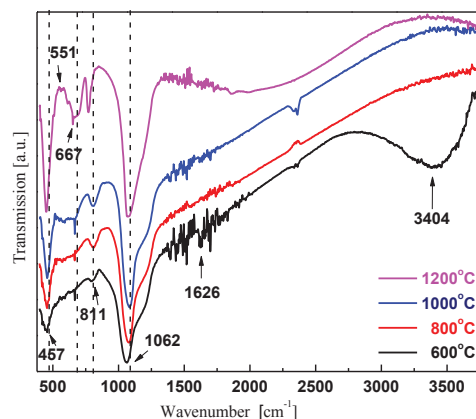


Fig. 2 Infrared spectra of the $30\text{SnO}_2\text{-70SiO}_2$ thin film doped with 1% Er^{3+} heat-treated in air at different temperature for 1 hour.

The broad absorption band at 1062 cm^{-1} is assigned to asymmetric stretching vibration of $\equiv\text{Si-O-Si}\equiv$ linking bonds. There are also other absorption bands concerning Si-O-Si bonding: 811 cm^{-1} and 457 cm^{-1} assigned to the symmetric stretching and to the δ vibrational mode, respectively. The weak band at about 667 cm^{-1} is due to the vibration absorption band of $\delta(\text{O-Sn-O})$ bonding, which indicates the growth of SnO_2 nanocrystals [4]. The FTIR feature indicates that after heat treatment at 1200°C a fully densified film is obtained.

3.1.2 XRD

The X-Ray diffraction patterns of $30\text{SnO}_2\text{-70SiO}_2$ thin film doped with 1% Er^{3+} (Figure 3), heat-treated in air at temperature ranging from 800°C to 1200°C for 1 hour, show that SnO_2 nanocrystals only appear in sample annealed at temperature higher than 1000°C .

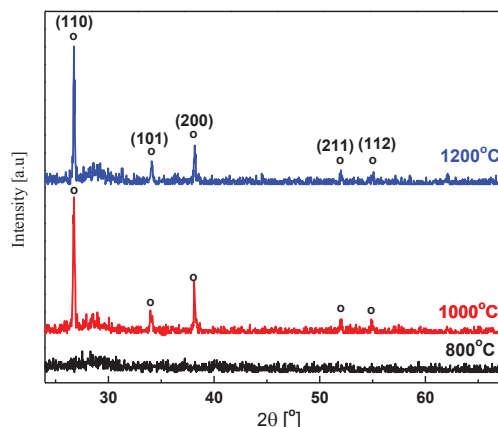


Fig. 3 X-Ray diffraction patterns of $30\text{SnO}_2\text{-70SiO}_2$ thin film doped with 1 mol% Er^{3+} , heat-treated in air at different temperature for 1 hour.

Figure 4 shows XRD spectra of $x\text{SnO}_2-(100-x)\text{SiO}_2$ ($x = 10, 20$ and 30 mol%) thin films, doped with 1% Er^{3+} and annealed at 1200°C for 1 hour. The diffraction peaks at $2\theta = 26.9^\circ, 34.1^\circ, 38.2^\circ$ and 52.0° correspond to the network side (110), (101), (200), (211) and (112) of SnO_2 rutile crystal phase (JCPDS 41-1445).

As expected, the higher concentration of SnO_2 is, the larger number of SnO_2 nanocrystals are formed.

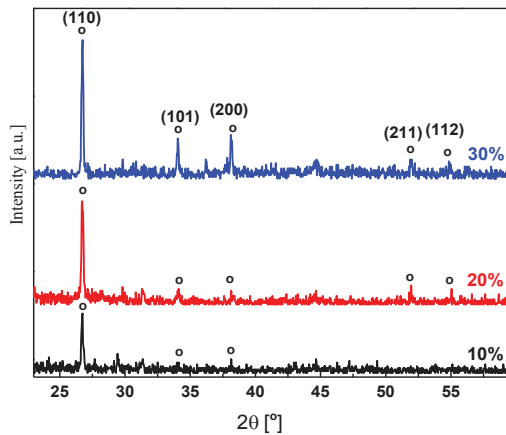


Fig. 4 X-Ray diffraction patterns of $x\text{SnO}_2-(100-x)\text{SiO}_2$ ($x = 10, 20$ and 30 mol%) glass-ceramic thin films doped with 1% Er^{3+} .

3.2. Transparency

The UV-Vis transmittance spectra of the thin films deposited on the high purity silica with different concentration of SnO_2 , ranging from 10 to 20 mol% activated by 1 mol% of Er^{3+} and annealed at 500°C are shown in Figure 5. It can be seen that the transmittance of these samples remains around 90% over the $400\text{ nm} - 1.1\ \mu\text{m}$ region.

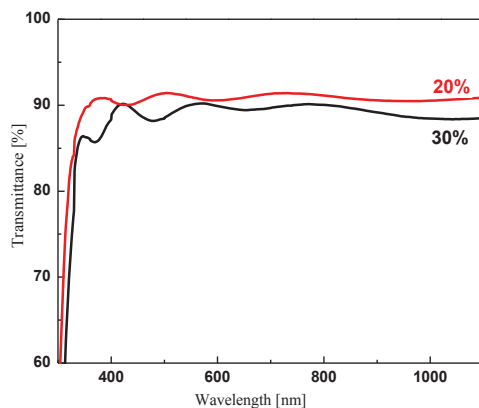


Fig. 5 UV-Vis transmittance spectra of $x\text{SnO}_2-(100-x)\text{SiO}_2$ ($x = 20$ and 30 mol%) doped with 1 mol% Er^{3+} thin films, annealed at 500°C .

3.3. Photoluminescence

Figure 6 shows the $1.5\ \mu\text{m}$ photoluminescence spectra of $30\text{SnO}_2-70\text{SiO}_2$ glass-ceramic thin films doped with different concentration of Er^{3+} ranging from 1 up to 3 mol% upon excitation at 300 nm . The luminescence spectra indicates an efficient energy transfer from the SnO_2 nanocrystals to the rare earth ions [5]. Moreover, the narrowing of the emission peaks, associated to the Stark multiplets, evidences that the rare earth ions are embedded in the SnO_2 nanocrystals. It is well known that, increasing the concentration of rare earth ions, the luminescence quenching is observed due to clustering effect and ions-ions interaction. Although SnO_2 nanocrystals helps in dispersing Er^{3+} ions, the emission intensity decreases slightly when the concentration of Er^{3+} reaches the percentage of 2 mol% and it shows a strong quenching for the 3 mol% sample.

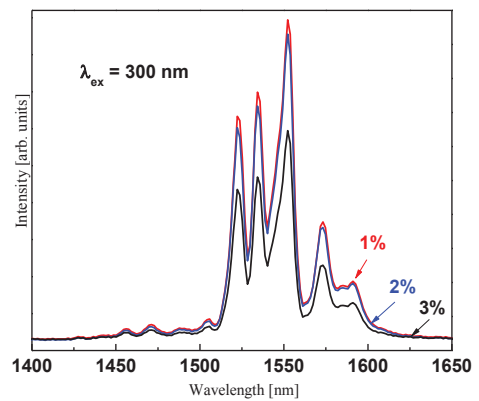


Fig. 6 Photoluminescence spectra of $30\text{SnO}_2-70\text{SiO}_2$ thin films doped with different concentration of Er^{3+} heat-treated at 1200°C .

4. Conclusion

We have figured out the fabrication protocol to obtain fully densified thin film with the highest concentrations of SnO_2 and Er^{3+} : 30 mol% and 2 mol%, respectively. The viability of SnO_2 based glasses in form of thin films was investigated. The films are crack-free and exhibit a transmittance of around 90% over the $400\text{ nm} - 1.1\ \mu\text{m}$ region. The role of SnO_2 nanocrystals as Er^{3+} luminescence sensitizers was experimentally confirmed.

Acknowledgements

The research was performed in the framework of the CNR-PAS joint Project (2014–2016), Cost Action MP1401 and Centro Fermi PLANS project. Thi Ngoc Lam Tran acknowledges the scholarship of the Ministry of Education and Training, Vietnam International Education Development.

References

- [1] J. Del-Castillo, V. D. Rodríguez, A. C. Yanes, and J. Ramos, 'Energy transfer from the host to Er^{3+} dopants in semiconductor SnO_2 nanocrystals segregated in sol – gel silica glasses', *J. Nanoparticle Res.*, 2008, 10, pp. 499–506.
- [2] M. Ferrari, E. F. Centre, G. C. Righini, and E. F. Centre, 'Glass-Ceramic Materials for Guided-Wave Optics', *Int. J. Appl. Glas. Sci.*, 2015, 6, (3), pp. 240–248.
- [3] R. S. Katiyar, P. Dawson, M. M. Hargreave, and G. R. Wilkinson, 'Dynamics of the rutile structure III. Lattice dynamics, infrared and Raman spectra of SnO_2 ', *J. Phys. C Solid State Phys.*, 1971, 4, pp. 2421–2431.
- [4] T. Van Tran, S. Turrell, M. Eddafi, B. Capoen, M. Bouazaoui, P. Roussel, S. Berneschi, G. Righini, M. Ferrari, S. N. B. Bhaktha, O. Cristini, and C. Kinowski, 'Investigations of the effects of the growth of SnO_2 nanoparticles on the structural properties of glass-ceramic planar waveguides using Raman and FTIR spectroscopies', *J. Mol. Struct.*, 2010, 976, (1–3), pp. 314–319.
- [5] S. N. B. Bhaktha, F. Beclin, M. Bouazaoui, B. Capoen, A. Chiasera, M. Ferrari, C. Kinowski, G. C. Righini, O. Robbe, and S. Turrell, 'Enhanced fluorescence from Eu^{3+} in low-loss silica glass-ceramic waveguides with high SnO_2 content', *Appl. Phys. Lett.*, 2008, 93, (21), pp. 193–195.
- [6] B. N. S. Bhaktha, C. Kinowski, M. Bouazaoui, B. Capoen, O. Robbe-cristini, F. Beclin, P. Roussel, M. Ferrari, and S. Turrell, 'Controlled Growth of SnO_2 Nanocrystals in Eu^{3+} - Doped SiO_2 - SnO_2 Planar Waveguides: A Spectroscopic Investigation', *J. Phys. Chem. C*, 2009, 113, pp. 21555–21559.
- [7] T. T. T. Van, S. Turrell, B. Capoen, L. Q. Vinh, O. Cristini-Robbe, M. Bouazaoui, F. d'Acapito, M. Ferrari, D. Ristic, a. Lukowiak, R. Almeida, L. Santos, and C. Kinowski, 'Erbium-Doped Tin-Silicate Sol–Gel-Derived Glass-Ceramic Thin Films: Effect of Environment Segregation on the Er^{3+} emission', *Sci. Adv. Mater.*, 2015, 7, (2), pp. 301–308.
- [8] C. Duverger, M. Montagna, R. Rolli, S. Ronchin, L. Zampedri, M. Fossi, S. Pelli, G. G. Righini, A. Monteil, C. Armellini, and M. Ferrari, 'Erbium-activated silica xerogels: Spectroscopic and optical properties', *J. Non. Cryst. Solids*, 2001, 280, (1–3), pp. 261–268.