

GERMANIA AND ALUMINA DOPANT DIFFUSION AND VISCOUS FLOW EFFECTS AT PREPARATION OF DOPED OPTICAL FIBERS

Jens KOBELKE, Kay SCHUSTER, Joerg BIERLICH, Sonja UNGER, Anka SCHWUCHOW, Tino ELSMAN, Jan DELLITH, Claudia AICHELE, Ron FATOBENE ANDO, Hartmut BARTELT

Leibniz Institute of Photonic Technology, Albert-Einstein-Strasse 9, 07745 Jena, Germany

jens.kobelke@leibniz-ipht.de, kay.schuster@leibniz-ipht.de, joerg.bierlich@leibniz-ipht.de, sonja.unger@leibniz-ipht.de, anka.schwuchow@leibniz-ipht.de, tino.elsmann@leibniz-ipht.de, jan.dellith@leibniz-ipht.de, claudia.aichele@leibniz-ipht.de, ron.spittel@leibniz-ipht.de, hartmut.bartelt@leibniz-ipht.de

DOI: 10.15598/aeec.v15i1.2009

Abstract. We report on germania and alumina dopant profile shift effects at preparation of compact optical fibers using packaging methods (Stack-and-Draw method, Rod-in-Tube (RiT) technique). The sintering of package hollow volume by viscous flow results in a shift of the core-pitch ratio in all-solid microstructured fibers. The ratio is increased by about 5 % in the case of a hexagonal package. The shift by diffusion effects of both dopants is simulated for typical slow speed drawing parameters. Thermodynamic approximations of surface dissociation of germania doped silica suggest the need of an adequate undoped silica barrier layer to prevent an undesired bubble formation at fiber drawing. In contrast, alumina doping does not estimate critical dissociation effects with vaporous aluminium oxide components. We report guide values of diffusion length of germania and alumina for the drawing process by kinetic approximation. The germania diffusion involves a small core enlargement, typically in the sub-micrometer scale. Though, the alumina diffusion enlarges it by a few micrometers. A drawn pure alumina preform core rod transforms to an amorphous aluminosilicate core with a molar alumina concentration of only about 50 % and a non-gaussian concentration profile.

Keywords

Alumina, diffusion, doped silica, germania, optical fiber, sensor fiber.

1. Introduction

For about two decades, fibers with extreme refractive index contrast, for instance holey and all-solid microstructured fibers, have been intensively investigated due to their unique optical properties, e.g. unusual dispersion, endlessly single mode transmission, photonic band gap propagation, etc. [1], [2] and [3]. Such fibers are suitable for various sensor applications, e.g. in chemical analytics by absorption, Raman or Brillouin spectroscopy. Fibers with extreme material contrast between core and cladding are also interesting for different applications, e.g. nonlinear devices [4], or sensors for temperature, strain or pressure monitoring with core-inscribed Bragg gratings [5].

The typical fabrication approach for both fiber types follows packaging procedures. The Rod-in-Tube process combines a core glass rod with a different cladding glass hollow cylinder, whereas the Stack-and-Draw method arranges different doped rods or hollow cylinders surrounded by a jacketing tube. The interstitial volume between the mostly hexagonal packaged circular elements is removed at least in the final drawing procedure by evacuation. Alternatively, by drawing at atmospheric pressure the interspace collapse can also be affected by surface tension. The profiles of the doped fibers are smoothed by diffusion, compared to the preform. On the diffusion of GeO₂ in silica matrix by doped layer annealing is reported in [6]. Diffusion and dissociation effects of germania at all-solid fiber fabrication are shown in [7], about the alumina diffusion with low Al₂O₃ concentration reports [8].

2. Simulation of Dopant Dissociation and Diffusion

The germania dissociation is the cause for the development of the central dip in typical gradient and step index fibers. The dissociation can be described by the following simplified reaction:




Figure 1 shows an exemplary equilibrium partial pressure of the gaseous reaction product GeO starting with a glass composition 10 mol% GeO₂ - 90 mol% SiO₂. The chemical equilibrium was calculated with the program HSC [9]. It demonstrates the high evaporation tendency at fiber drawing temperature of about 1900 °C. The partial pressure of GeO is about 6 % of atmospheric pressure at this temperature. In contrast, for alumina doping no significant vaporous components at this temperature were found. All considered gaseous species, e.g. AlO(g), AlO₂(g), Al₂O(g), Al₂O₂(g), Al₂O₃(g) [10], show an equilibrium partial pressure $p \ll 10^{-6}$ Pa in the simulation.

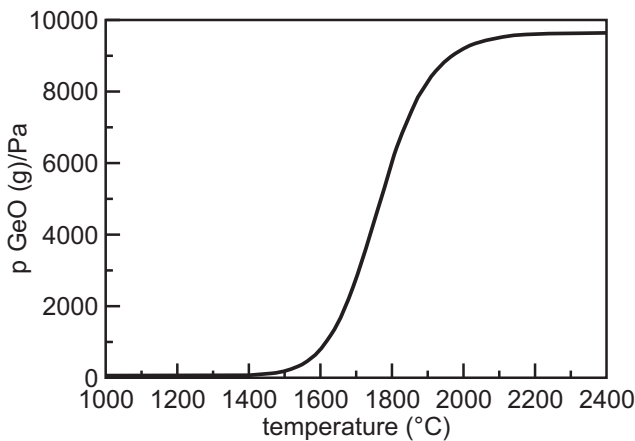


Fig. 1: Calculation of partial pressure vs. temperature for evaporation reaction of germania-silica glass (10 mol% GeO₂), total pressure: 1 bar.

However, in variation to chemical equilibrium consideration the experimental dopant distribution is limited by diffusion effects, depending on temperature and dopant concentration. Figure 2 shows the expected diffusion coefficients at drawing temperature dependent on the dopant concentration. The variation of germania concentration from 1 mol% to 20 mol% at 1900 °C increases the diffusion coefficient by a factor of about 3, from $10^{-10.5}$ cm²·s⁻¹ to 10^{-10} cm²·s⁻¹ [6].

The investigation of annealed aluminosilicate layers by [8] indicates a significantly higher diffusion coefficient with a strong nonlinearity compared to germania doping. In the drawing temperature range (1900–2200 °C) it is expected to be from about

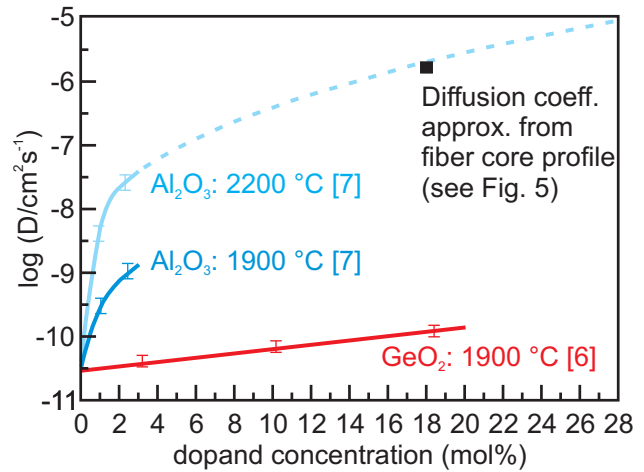


Fig. 2: Approximated concentration dependence of diffusion coefficients for germania (corr. to [6]) and alumina (corr. to [8]) in a silica preform at 1900 °C and 2200 °C, respectively.

10^{-8} cm²·s⁻¹ up to 10^{-9} cm²·s⁻¹ even for low alumina concentration. Though the investigated maximum Al₂O₃ concentration was about 3 mol% in [8].

The effective diffusion time τ_{DF} during fiber drawing was calculated from the axial diffusion zone length z_D and the fiber drawing speed v_F :

$$\tau_{DF} = \frac{z_D}{v_F}. \quad (2)$$

The axial diffusion zone length was approximated from the axial temperature profile, measured along the central axis of the drawing furnace. Based on the equivalent temperature T_{eq} (K), the diffusion zone length z_D can be approximated from the temperature profile (see Fig. 3).

T_{eq} is associated with the activation energy of diffusion E_a given by Eq. (3):

$$\frac{1}{T_{eq}} = \frac{1}{T_{max}} + \frac{R}{E_a}, \quad (3)$$

where T_{max} (K) is the maximum temperature of the axial temperature profile and R is the universal gas constant. E_a is given in [6] and [8] presuming an Arrhenius dependence of the diffusion coefficient.

Figure 3 shows the graphically determined diffusion zone lengths with $T_{max} = 1900$ °C for germania doped fiber drawing and $T_{max} = 2200$ °C for aluminosilicate fiber drawing. The value of z_D is about 38 mm for a germania doping level between 1 mol% and 20 mol% [7]. For alumina diffusion z_D is approximated to be 52 mm for an Al₂O₃ concentration of 2 mol% and extrapolated to be 60 mm for 20 mol% Al₂O₃.

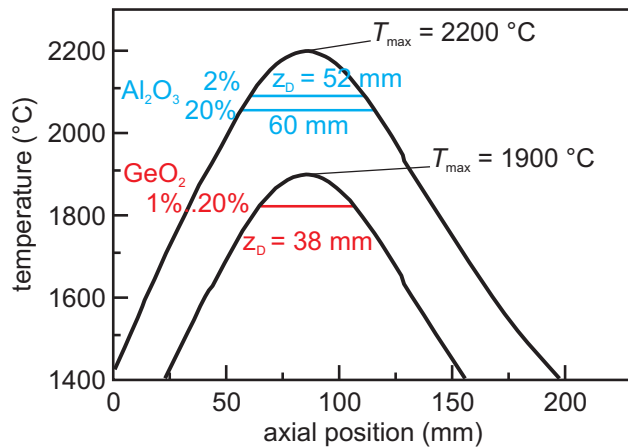


Fig. 3: Approximated effective diffusion zone lengths for alumina and germania doped silica preforms in the drawing furnace.

3. Drawing Experiments

An all-solid microstructured fiber with 19 germanium doped cores (core diameter: $d = 5.0 \mu\text{m}$, pitch: $\Lambda = 10.0 \mu\text{m}$) was manufactured by stack-and-draw technique for a setup in a Coherent Antiresonant Raman Spectroscopic Probe [11]. The preform package arrangement and the drawn fiber are shown in Fig. 4.

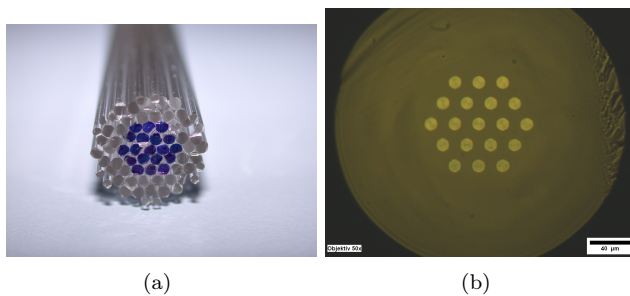


Fig. 4: (a) preform package arrangement of the 19 core fiber. The germania doped rods are marked blue. (b) micrograph of the fiber after drawing.

The shift of the ratio d/Λ was found to be about 5 %. It is caused by the evacuation of the interstitial volume during drawing. The core diameter of the GeO_2 doped preform rods was $504 \mu\text{m}$, the outer diameter of $1000 \mu\text{m}$, which corresponds to the pitch of the preform arrangement. The GeO_2 concentration was 6 mol%. The core was deposited by Modified Chemical Vapor Deposition (MCVD) with 25 doped layers. After the drawing the core-pitch-ratio has changed from 0.504 (preform) to ratio d/Λ : 0.532–0.533 in the fiber. This corresponds to the expectation by sintering of the interspace volume. The diameter varies over all core elements 5.31 – $5.57 \mu\text{m}$, the pitch: 9.98 – $10.45 \mu\text{m}$, respectively. Due to the relatively low diffusivity of germanium, no significant additional broadening of the core

diameter is experimentally observed. The pure silica cladding layer thickness of about $2.35 \mu\text{m}$ is sufficient for avoidance of bubble formation according Eq. (1).

An aluminosilicate core fiber with extreme high alumina concentration was prepared by RiT technique. A crystalline alumina rod (sapphire) with 2.8 mm diameter was inserted in a silica tube (Heraeus F300) with outer diameter $OD = 30 \text{ mm}$ and central hole diameter $ID = 3 \text{ mm}$. The preform was drawn with a drawing speed of $v_F = 40 \text{ m}\cdot\text{min}^{-1}$ to an UV-acrylate coated fiber with an outer diameter of $125 \mu\text{m}$. The drawing furnace temperature, measured with an IR-thermometer, was $2200 \text{ }^\circ\text{C}$. The drawing force F was between 0.1 N and 0.17 N . The effective drawing temperature was calculated from the effective drawing viscosity given by Eq. (4) proposed in [12]:

$$\eta(T) = \frac{4F\Delta z_b}{3v_P(OD^2 - ID^2) \ln\left(\frac{v_F}{v_P}\right)}, \quad (4)$$

where Δz_b is the axial width of the heating zone for viscous flow in the neck down region of the preform. It is about 35 mm for the used drawing furnace. The approximated viscosity was calculated as about $\log(\eta/\text{Pas}) \approx 3$. This corresponds to the measured temperature of the IR-thermometer. It is supposed, that the melting temperature of sapphire (ca. $2050 \text{ }^\circ\text{C}$) was exceeded.

4. Results

The dopant concentration profile of the drawn fiber was investigated by SEM analysis. Figure 5 shows the shift of the radial alumina concentration profile from the preform to the fiber. The relative positioning is normalized to the outer diameter of the preform and the fiber, respectively.

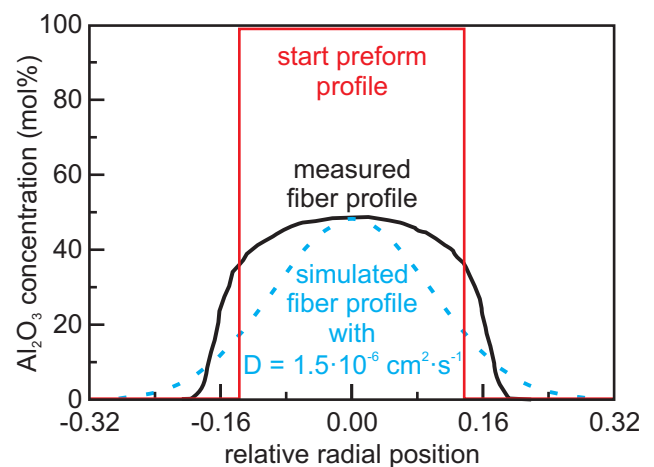


Fig. 5: Alumina concentration profile of the drawn fiber compared to the starting profile of the preform.

The composition of the core changes from pure alumina in the preform to an aluminosilicate glass composition of 50.6 % SiO_2 and 49.4 % Al_2O_3 in the center of the fiber core. The mean diffusion coefficient calculates to be $1.5 \cdot 10^{-6} \text{ cm}^2 \cdot \text{s}^{-1}$ by Fick's law. The approximation is based on an axial diffusion zone length of 60 mm in the drawing furnace and a drawing speed of $40 \text{ m} \cdot \text{min}^{-1}$. By extrapolating the specified concentration dependence in [8], the found diffusivity corresponds to an aluminosilicate glass with a mean concentration of 18 mol% Al_2O_3 (see Fig. 2). Nevertheless, the experimentally found alumina concentration profile in the fiber cannot be explained only by a simple thermal activated alumina dopant concentration flow balance.

We found structural crystalline changes in the thermal induced transition region from preform core to the fiber core. The investigation of the preform neck-down region by X-ray diffraction analysis shows beside a strong amorphous phase intense peaks of mullite (see Fig. 6). Similar recrystallization effects were also described in [13]. Obviously, the formation of mullite is caused by the long dwell time (approx. 50 min) during passing the neck-down region. After removing the preform out of the drawing furnace it was quenched with natural air convection. The cooling rate is here strong limited by the low surface-volume ratio of the upper neck-down region of the preform. Compared to this low cooling rate under static air quenching conditions, the drawn fiber suffers an extremely high cooling rate by a drawing speed of $40 \text{ m} \cdot \text{min}^{-1}$. The duration for passing a length of the neck-down region in this case is only 0.05 s.

The investigation of the fiber core (shown in Fig. 7) by electron backscattering shows an amorphous core cross section.

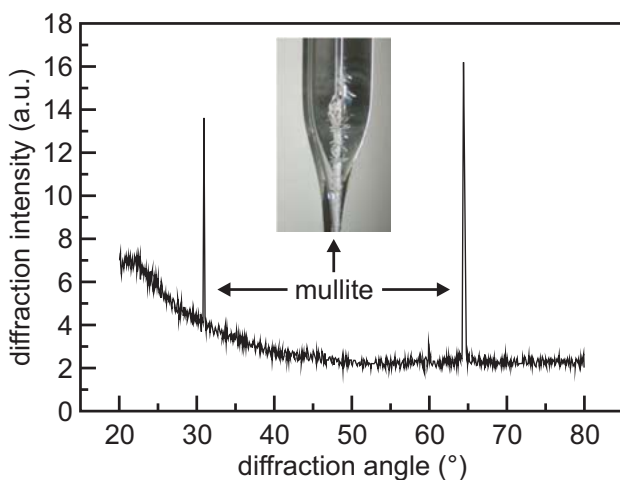


Fig. 6: X-ray diffraction pattern of the core material in the preform neck-down region (inset: photograph of the preform neck-down region, arrowhead shows to the measuring point).

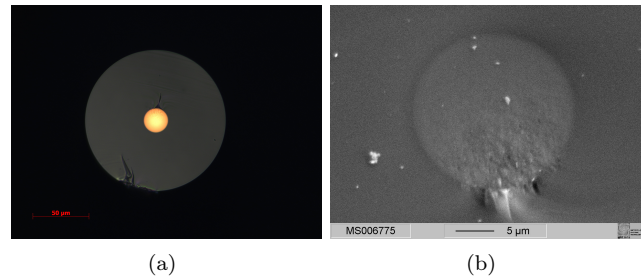


Fig. 7: (a) white light micrograph of the fiber end face, (b) SEM picture of the fiber core.

We have not found the appearance of any separate crystalline phase in the fiber core. This corresponds with the high transmission and low scattering level of the aluminosilicate core. Figure 7(a) shows the micrograph of the cleaved fiber with white light transmission illumination. The brightness contrast between core and cladding is caused by the high refractive index difference. The SEM picture in Fig. 7(b) demonstrates the excellent homogeneity of the core region. No separate crystals or heterophase separations were observed. The fracture surface at the core cladding interface is caused by the strong tension mismatch between the silica clad and the aluminosilicate core, which has a much higher thermal expansion than silica.

Figure 8 shows the spectral loss of the multimode fiber with a core diameter of $21 \mu\text{m}$ and a numerical aperture of $\text{NA} = 0.54$.

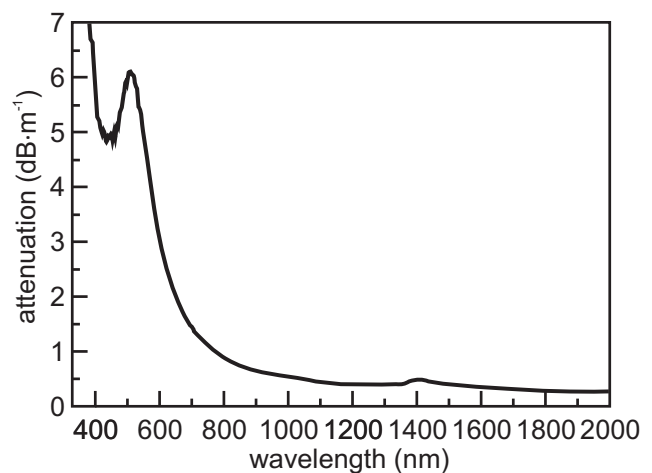


Fig. 8: Attenuation spectrum of the aluminosilicate core fiber.

The minimum loss was found at a wavelength of 1850 nm with $0.27 \text{ dB} \cdot \text{m}^{-1}$. For a typical application, like Bragg grating inscription at a wavelength of 1550 nm [5], the loss is $0.37 \text{ dB} \cdot \text{m}^{-1}$. The peak at 550 nm is attributed to impurities of the sapphire starting material.

5. Conclusion

Dopant diffusion combined with thermal induced dissociation can cause variations and disturbances in dopant profiles of all-solid microstructured fibers. For germania doping, a sufficient silica barrier avoids the undesired bubble formation by thermal dissociation. The shift of the core-pitch-ratio by evacuation of the interspace of hexagonal preform packages has to be considered for the design of the final compact fiber. The drawing of a sapphire core in silica cladding does not result in a fiber with a pure alumina core. We found a maximum alumina concentration of about 50 mol% in the fiber core. Obviously, the sufficient softening of the complete preform at fiber drawing presumes the melting of the sapphire rod. The necessarily applied high drawing temperature $T > 2050$ °C causes an intense reciprocal diffusion of alumina and silica. We found an intermediate recrystallization to mullite in the neck-down region of the preform. The drawn fiber shows an aluminosilicate core with a non-gaussian alumina concentration profile and a maximum Al_2O_3 concentration of about 50 mol%. The diameter of the core is enlarged about by factor 2 compared to the preform cross section. Although the high alumina glasses show devitrification tendency, we found no crystalline phase in the final fiber core. Obviously, the large cooling rate during fiberization of the preform allows overcome the high recrystallization tendency. The fiber core shows a low spectral loss minimum < 1 dB·m⁻¹ due to its low scattering and good axial homogeneity. Future applications of this fiber type are to be seen in high temperature sensing and complex all-solid fiber devices, which require a high numerical aperture.

Acknowledgment

This work was supported by the Ministry of Economy, Technology and Work of the Federal State Thuringia and the European Social Fond (ESF).

References

- [1] KNIGHT, J. C., T. A. BIRKS, P. S. RUSSEL and D. M. ATKIN. All-silica single-mode optical fiber with photonic crystal cladding. *Optics Letters*. 1996, vol. 21, iss. 19, pp. 1547–1549. ISSN 0146-9592.
- [2] RUSSELL, P. Photonic crystal fibers. *Science*. 2003, vol. 299, iss. 5605, pp. 358–362. ISSN 1095-9203. DOI: 10.1126/science.1079280.
- [3] LÆGSGAARD, J. and A. BJARKLEV. Microstructured Optical Fibers—Fundamentals and Applications. *Journal of the American Ceramic Society*. 2006, vol. 89, iss. 1, pp. 2–12. ISSN 1551-2916. DOI: 10.1111/j.1551-2916.2005.00798.x.
- [4] KARRAS, C., W. PAA, D. LITZKENDORF, S. GRIMM, K. SCHUSTER and H. STAFAST. SiO_2 - Al_2O_3 - La_2O_3 glass - a superior medium for optical Kerr gating at moderate pump intensity. *Optical Material Express*. 2016, vol. 6, iss. 1, pp. 125–130. ISSN 2159-3930. DOI: 10.1364/OME.6.000125.
- [5] ELSMANN, T., A. LORENZ, N. S. YAZD, T. HABISREUTHER, J. DELLITH, A. SCHWUCHOW, J. BIERLICH, K. SCHUSTER, M. ROTHHARDT, L. KIDO and H. BARTELT. High temperature sensing with fiber Bragg gratings in sapphire-derived all-glass optical fibers. *Optics Express*. 2014, vol. 22, iss. 22, pp. 26831–26839. ISSN 1094-4087. DOI: 10.1364/OE.22.026825.
- [6] KIRCHHOF, J., S. UNGER, B. KNAPPE and J. DELLITH. Diffusion in binary GeO_2 - SiO_2 glasses. *Physics and Chemistry of Glasses: European Journal of Glass Science Technology part B*. 2007, vol. 48, iss. 3, pp. 129–133. ISSN 1753-3562.
- [7] KOBELKE, J., J. BIERLICH, K. WONDRACZEK, C. AICHELE, Z. PAN, S. UNGER, K. SCHUSTER and H. BARTELT. Diffusion and Interface Effects during Preparation of All-Solid Microstructured Fibers. *Materials*. 2014, vol. 7, iss. 9, pp. 6879–6892. ISSN 1996-1944. DOI: 10.3390/ma7096879.
- [8] UNGER, S., J. DELLITH, A. SCHEFFEL and J. KIRCHHOF. Diffusion in Yb_2O_3 - Al_2O_3 - SiO_2 glass. *Physics and Chemistry of Glasses: European Journal of Glass Science Technology part B*. 2011, vol. 52, iss. 2, pp. 41–46. ISSN 1753-3562.
- [9] HSC Chemistry, version 6.12, 2007 Outotec Research Oy, HSC Chemistry 6.0. *User's Guide Volume 1/2: Chemical Reaction and Equilibrium Software with Extensive Thermochemical Database and Flowsheet Simulation*.
- [10] CHASE, M. W. *NIST-JANAF thermochemical tables*. 4th ed. New York: American Institute of Physics for the National Institute of Standards and Technology, 1998. ISBN 1563968207.
- [11] DOCHOW, S., I. LATKA, M. BECKER, R. SPITTEL, J. KOBELKE, K. SCHUSTER, A. GRAF, S. BRUECKNER, S. UNGER, M. ROTHHARDT, B. DIETZEK, C. KRAFFT and J. POPP. Multicore fiber with integrated fiber Bragg gratings for background-free Raman sensing. *Optics Express*. 2012, vol. 20,

iss. 18, pp. 20156–20169. ISSN 1094-4087.
DOI: 10.1364/OE.20.020156.

- [12] KIRCHHOF, J., K. GERTH, J. KOBELKE and K. SCHUSTER. Photonic Crystal Fibers - Viscous Behaviour of Silica Tubes During Collapsing and Hollow Fiber Drawing Poc. In: *6th ESG Conference*. Montpellier: Glass Odyssey, 2002, pp. 196–201.
- [13] PAN, Z. *Consolidation of high melting SiO₂-Al₂O₃-La₂O₃ glass powders with gas pressure vacuum viscous sintering technology*. Jena, 2016. Dissertation thesis. Friedrich-Schiller-Universitaet Jena.

About Authors

Jens KOBELKE was born 1959 in Merseburg, Germany. He studied chemistry received his Ph.D. from Technische Hochschule Merseburg in 1986. Since this time he works at Institute of Photonic Technology (IPHT) Jena on the development and preparation of special optical fibers.

Kay SCHUSTER was born 1965 in Beetzendorf, Germany. He studied chemistry at Martin-Luther-University Halle and received his Ph.D. 1995 from the University Karlsruhe. Since 1996 he is with the IPHT Jena. He is the leader of the fiber technological group at IPHT and engaged in research on optical speciality fibers.

Joerg BIERLICH was born 1973 in Jena, Germany. He studied medical engineering at University of Applied Science Jena and received his Ph.D. 2008 from the Bergakademie Freiberg. Since 2001 he works at IPHT Jena on preparation of specialty optical fibers.

Sonja UNGER was born 1951 in Rathen, Germany. She received the Ph.D. degree in inorganic chemistry from the College of Education, Erfurt, Germany, in 1977. She works at the IPHT in the Optical Fiber Technology Group as a research collaborator in the field of MCVD technology. She is engaged on research in the development of materials and high silica speciality optical fibers (active fibers for laser

and amplifier, photosensitive and nonlinear fibers).

Anka SCHWUCHOW was born in 1970 in Jena, Germany. From 1988 to 1991 she studied microelectronics at Technical University of Sofia (VMEI) in Sofia (Bulgaria) and from 1991 telecommunications at Technische Universitaet Dresden. There she obtained her first german degree. Since 1994 she has been a member of IPHT Jena and has specialized in characterisation of optical fibers and preforms and rare earths in glasses.

Tino ELSMANN was born 1986 in Zeulenroda, Germany. He studied physics at University Jena and received the diploma degree 2010. Actually he is a Ph.D. student at the IPHT Jena. He is interested in fiber optical devices, e.g. fiber Bragg gratings for special applications.

Jan DELLITH was born 1973 in Jena, Germany. He studied material engineering at University of Applied Science Jena and received his Ph.D. 2008 from the Bergakademie Freiberg. Since 2000 he works at IPHT Jena in particular in the field of solid state analytics.

Claudia AICHELE was born 1969 in Jena, Germany. She studied material science at the Bergakademie Freiberg. There she received the diploma engineer degree in 1993. Since 1995 she is with the IPHT Jena. Her interests are material investigation and preparation by MCVD method and thermodynamical simulation.

Ron FATOBENE ANDO was born 1981 in Jena, Germany. He studied physics at the Friedrich Schiller University Jena and received his Ph.D. in 2016. His interests comprise the design and simulations of specialty optical fibers.

Hartmut BARTELT was born 1951. He studied physics at University of Karlsruhe and Nuernberg-Erlangen. After receiving Ph.D. degree 1980 and habilitation 1985 he worked at Siemens AG Erlangen. Since 1994 he is Professor at the University of Jena and head of the Fiber Optics Division of the IPHT. His interests are in theory and application of fiber optics.