

Physical and chemical induced spin crossover

This content has been downloaded from IOPscience. Please scroll down to see the full text.

2010 J. Phys.: Conf. Ser. 217 012022

(<http://iopscience.iop.org/1742-6596/217/1/012022>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 194.95.157.184

This content was downloaded on 28/04/2017 at 10:20

Please note that [terms and conditions apply](#).

You may also be interested in:

[Mössbauer Spectroscopy: Elegance and versatility in chemical diagnostics](#)

Philipp Gütlich and Yann Garcia

[Molecular switching in iron complexes bridged via tin-cyanides observed by Mössbauer and ESR spectroscopy](#)

S Jung, F Renz, M Klein et al.

[Room temperature hysteretic spin transition in 1D iron\(II\) coordination polymers](#)

Marinela M Dîrtu, Anil D Naik, Jacqueline Marchand-Brynaert et al.

[Pressure effect studies in molecular magnetism](#)

Philipp Gütlich, Ana B Gaspar, Vadim Ksenofontov et al.

[Mössbauer spectroscopy, Raman- and IR- microscopy studies of hysteretic behaviour in spin-crossover systems](#)

A Ahrens-Botzong, K Muffler, S M Stuppy et al.

[Influence of a thermochromic anion on the spin crossover of iron\(II\) trinuclear complexes probed by Mössbauer spectroscopy](#)

François Robert, Anil D Naik and Yann Garcia

[Mössbauer thermal scan study of a spin crossover system](#)

P Mendoza Zélis, G A Pasquevich, F H Sánchez et al.

[Analysis of phase transitions in spin-crossover compounds by using atom – phonon coupling model](#)

A Gîndulescu, A Rotaru, J Linares et al.

Physical and chemical induced spin crossover

F Renz¹

Leibniz University Hannover, Institute of Inorganic Chemistry, Callinstr. 9,
D-30167 Hannover, Germany

E-mail: Franz.Renz@acd.uni-hannover.de

Abstract. Physical spin crossover (spin transition), one of the most fascinating dynamic electronic structure phenomena occurring in coordination compounds of third row transition metal ions, mostly of iron(II), iron(III) and cobalt(II), has attracted increasing attention by many research groups. Some examples for physical and chemical induced spin crossover are discussed. Among the physical is the temperature and pressure induced switching. Novel effects observed by irradiation and magnetic and electric field will be discussed. Some chemical induced switching effects caused by solvation, ligand exchange, ligand isomerisation and bond breaking will be briefly outlined.

1. Introduction

Molecular switching is one of the major targets in various disciplines, such as technology, biology and medicine. One approach is to develop chemically and physically induced transitions between electronic states. In some transition metal complexes such a switching has been discovered and labelled spin crossover (SC) or spin transition phenomenon [13, 14] (see Figure 1). The phenomenon of thermal spin crossover, though already well known in inorganic chemistry for more than seven decades, has developed in recent years to one of the most actively studied subjects in coordination chemistry [8, 14, 10, 12, 11, 15].

2. Physical Induced

2.1. Thermal Induced SC (TISC)

The thermal spin crossover was first observed in an Fe(III) complexes by Cambi, et al. in 1931. After 60 years the first Fe(II)-spin crossover complex, the [Fe(II)(phen)₂(NCS)₂], was found by Baker, et al. in 1963. The Mössbauer effect was very important for the understanding of the nature of this switching phenomenon. The essential condition for TISC is that the zero-point-energy gap, the difference in zero-point vibrational energy between high-spin and low-spin state, is at the order of thermal energy kT [13, 14].

¹ To whom any correspondence should be addressed.

2.2. Pressure Induced SC (PISC)

The application of pressure leads to a first order approximation to an increased zero-point-energy gap. This shifts the transition temperature in the TISC to higher values [16]. In case of structural changes due to the application of pressure the opposite may be the case [16].

2.3. Light Induced SC

2.3.1. Batch Light Induced SC

2.3.1.1. *Light Induced Excited Spin-State Trapping (LIESST)*: The phenomena of LIESST (Light-Induced Excited Spin State Trapping) and reverse LIESST are well reviewed in the literature [14, 15]. For LIESST: green light irradiation on the Fe(II)-low-spin (S=0) state leads to an excited singlet state and decays via triplet states (S=1) to a trapped meta-stable quintet state, the Fe(II)-high-spin state (S=2) [14].

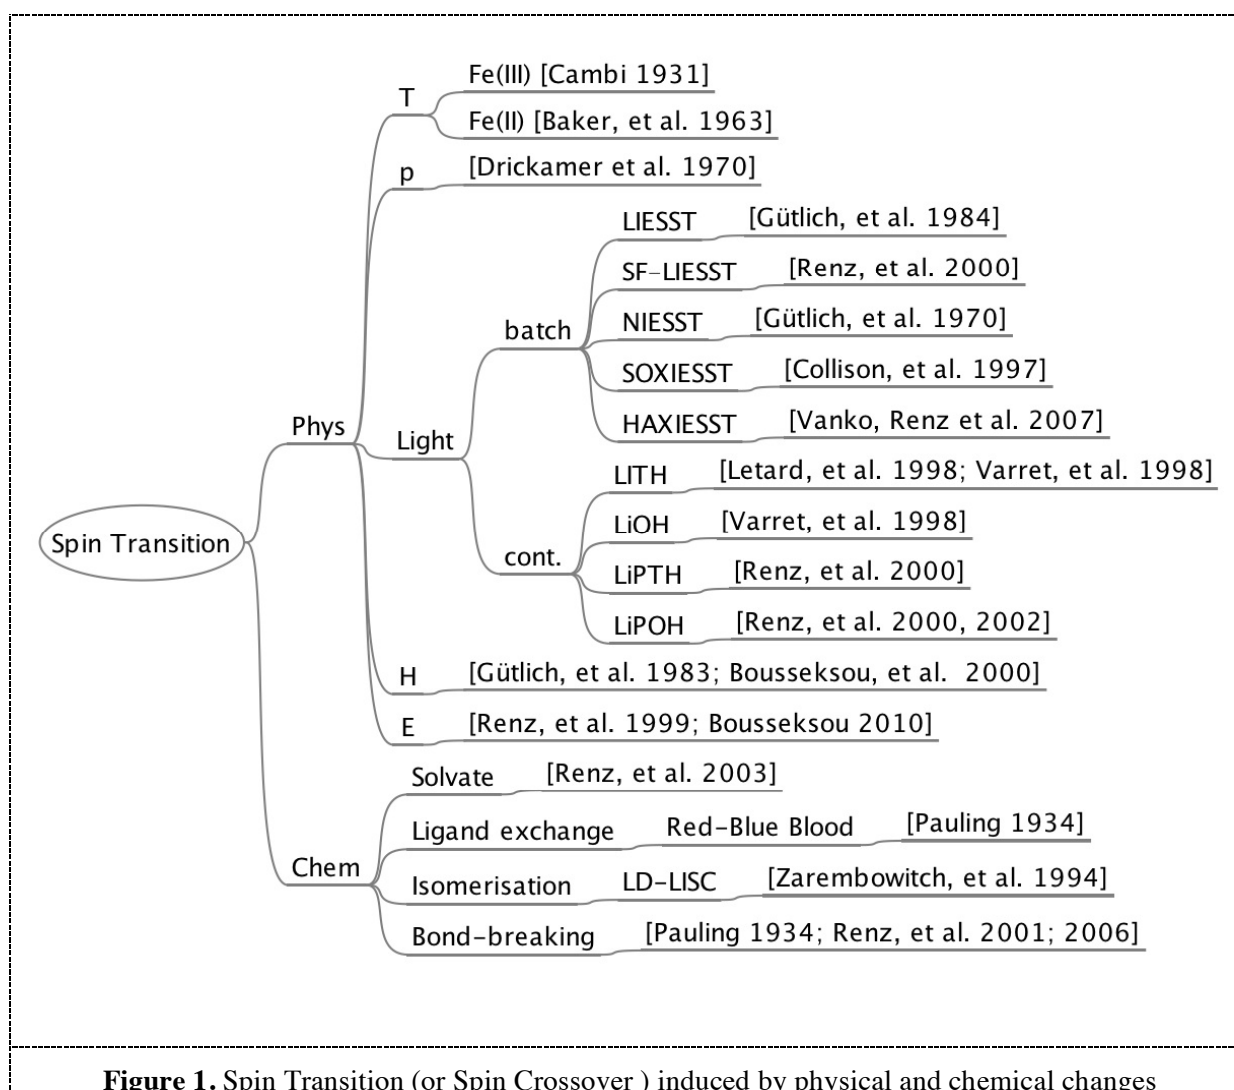


Figure 1. Spin Transition (or Spin Crossover) induced by physical and chemical changes

2.3.1.2. *Strong-Field- Light Induced Excited Spin-State Trapping (SF-LIESST)*[26]: Unexpected long life-time (mega-seconds) of the light-induced meta-stable state are observed for the strong-field

complexes $[\text{Fe(II)}_x\text{Mn(II)}_{1-x}(\text{terpy})_2](\text{ClO}_4)_2$, ($x < 0.1$). In opposite the non-diluted ($x = 1$) compound follows the expected LIESST mechanism at a life-time of sub-nanoseconds. The SF-LIESST effect seems to correlate with the tri-dentate inherent structure motive performing a double mode transition [22]. In comparison to that, usual mono-dentate perform single mode transitions. In such compounds the LIESST effect was first observed, e.g. $[\text{Fe(II)}(\text{ptz})_6]^{2+}$.

2.3.1.3. Nuclear Induced Excited Spin-State Trapping (NIESST)[14]: The nuclear decay of radioactive atoms embedded in a compound is known to lead to various chemical and physical "after effects" such as bond rupture, redox processes, formation of metastable states and others. One ways of investigating such effects is the "Mössbauer Emission Spectroscopy" (MES). Using this technique some metastable HS states of $^{57}\text{Fe(II)}$ in strong and intermediate ligand fields are observed. Many examples are described in a recent review article [9]. In analogy to the LIESST effect (generating and trapping of metastable HS states by irradiation with an external light source) the mechanism of the "Nuclear Decay Induced Excited Spin State Trapping (NIESST)" with its nuclear decay process $^{57}\text{Co(EC)}^{57}\text{Fe}$ may be regarded as an "internal" molecular excitation source.

2.3.1.4. Soft-X-ray Induced Excited Spin-State Trapping (SOXIESST)[5]: The soft X-ray electronic L-shell excitation in iron(II) coordination complexes leads to trapped metastable HS states. This is similar to the LIESST effect. Unfortunately further "after" effects such as bond rupture are also observed. This limits the application of this effect.

2.3.1.5. Hard-X-ray Induced Excited Spin-State Trapping (HAXIESST)[30]: The hard X-ray electronic K-shell excitation in iron(II) coordination complexes leads to trapped metastable HS states. This is similar to NIESST, SOXIESST and LIESST effect. In comparison to the SOXIESST and NIESST the HAXIESST has a much smaller probability for irreversible bond breaking. While L-shell experiments are performed under vacuum a K-shell measurement is done at ambient pressure under atmospheric conditions. A further advantage of the HAXIESST is its ability of single molecule addressing and switching, due to the atomistic spatial resolution of the short wavelength. In opposite the LIESST effects has a resolution of around 500 nm.

2.3.2. Continuous Light Induced SC

2.3.2.1. Light Induced Thermal Hysteresis (LITH)[17, 7]: Monitoring the HS fraction under constant-intensity continuous irradiation and variable temperature allows to observe a light induced thermal hysteresis. The LITH indicates a measure for cooperativity among the switching centers. If the cooperativity between the switching centers vanishes the thermal hysteresis width collapses to zero, so that the heating and cooling curve become identical.

2.3.2.2. Light Induced Optical Hysteresis (LIOH)[7]: Monitoring the HS fraction under variable-intensity continuous irradiation and constant temperature allows to observe a light induced optical hysteresis. LITH and LIOH can be interpreted in mean approximation with a master equation including a non-linear relaxation term[7].

2.3.2.3. Light Perturbed Thermal Hysteresis (LiPTH)[27]: Monitoring the HS fraction under constant-intensity continuous irradiation and variable temperature within a thermal hysteresis

allows to Light-perturb the thermal hysteresis (LiPTH). LiPTH allows to switch even at room temperature and in batch irradiations[28]. So far the maximum shift of a hysteresis was found to be around 50 K.

2.3.2.4. Light Perturbed Optical Hysteresis (LiPOH)[28, 27]: Monitoring the HS fraction under variable-intensity continuous irradiation and constant temperature within a thermal hysteresis allows to Light-perturb the thermal hysteresis seen as an optical hysteresis (LiPOH). LiPOH allows to switch even at room temperature and in batch irradiations[28].

2.4. Magnetic Field Induced SC (H)[4]

The effect of the magnetic field on the spin crossover transition temperature was weak and yielded a shift of ca. 2 K with a field of 5 Tesla as seen by Gütlich, et al. [21]. Almost two decades later Bousseksou, et al. used pulsed high-fields of up to 32 Tesla [3]. This turned out to be very effective[4].

2.5. Electric Field Induced SC (E)

The effect of the electric field on the spin crossover was seen on stretching a polar polymer matrix [25]. The matrix-incorporated spin crossover compound was exposed and affected by the electrostatic field of the polymer. More recent examples show the effect of the electrostatic field affects the bistability [6, 1, 19].

3. Chemical Induced

3.1. Solvate Induced SC

In solution the cooperativity is lowered and exhibit a Boltzmann-like behaviour. In opposite, non-coordinated solvates or adsorbats induce molecular switching (AIMS)[24] with potential room for applications.

3.2. Ligand Exchange Induced SC

Many compounds change their spin state on ligand exchange. E.g. hemoglobine reversibly coordinates oxygen. This causes the blue and red blood-color. Along with that a spin state change was observed by Pauling and Corvell [20].

3.3. Ligand Isomerisation Induced SC[29]

Roux et al. [29] have reported a method to obtain ligand-driven light-induced spin changes (LD-LISC) in transition metal compounds. Photo-sensitive ligands, such as cis-trans photo-isomerizable ligands, can alter the ligand field strength on irradiation and induce a spin state conversion at the metal center. LD-LISC was first observed in $[\text{Fe(II)}\text{L}_4(\text{NCS})_2]$ with L = cis, trans 4-styrylpyridine. For further examples see[2].

3.4. Bond-Breaking Induced SC

A non-reversible spin state change after a coordination bond-breaking is quite normal for many such chemical reactions. However, reversibility of such a phenomena is rare. One example is a rod-type structure consisting of $[\text{Fe(II)}(\text{acetate})_2]$ bridged by terpy-R-terpy (spacer R). Such systems switches pressure/digest and light-reversible [18, 23].

4. Outlook

This paper is a short compromise on some representative examples in an egocentric attempt to cover the vast development in the field and is far from complete. The intended compromise is to give a broad overview on selected effects and is not focused to systematically cover all the beautiful new compounds. Several very recent appealing new effects have not been included due to space restrictions.

Acknowledgments

Author wishes to acknowledge the assistance of his working group and his collaborators. This work was partly funded by the Leibniz University of Hanover (LUH), the ZFM/LUH, the LNQE/LUH, and the “Deutsche Forschungsgemeinschaft” (Priority Program SPP 1136 “Molecular Magnetism”; Re 1627/1-3), the “Fonds der chemischen Industrie”.

References

- [1] Baadji N, Piacenza M, Tugsuz T, Sala F D, Maruccio G and Sanvito S 2009 Electrostatic spin crossover effect in polar magnetic molecules *nature materials* **8** 813-7
- [2] Boillot M-L, Zarembowitch J and Sour A 2004 *Spin Crossover in Transition Metal Compounds II*, ed P Gülich and H Goodwin (Heidelberg: Springer) pp 261-76
- [3] Bousseksou A, Negre N, Goiran M, Salmon L, Tuchagues J P, Boillot M L, Boukheddaden K and Varret F 2000 Dynamic triggering of a spin-transition by a pulsed magnetic field *Eur. Phys. J. B* **13** 451-6
- [4] Bousseksou A, Varret F, Goiran M, Boukheddaden K and Tuchagues J P 2004 *Spin Crossover in Transition Metal Compounds III*, ed P Gülich and H Goodwin (Heidelberg: Springer) pp 65-84
- [5] Collison D, Garner C D, McGrath C M, Mosselmans J F W, Roper M D, Seddon J M W, Sinn E and Young N A 1997 Soft X-ray induced excited spin state trapping and soft X-ray photochemistry at the iron L_{2,3} edge in [Fe(phen)₂(NCS)₂] and [Fe(phen)₂(NCSe)₂] (phen = 1,10-phenanthroline) *J. Chem. Soc. Dalton Trans.* 4371-6
- [6] D’Avino G, Grisanti L, Guasch J, Ratera I, Veciana J and Painelli A 2008 Bistability in Fc-PTM Crystals: The Role of Intermolecular Electrostatic Interactions *J. Am. Chem. Soc.* **130** 12064-72
- [7] Desaix A, Roubeau O, Jeftic J, Haasnoot J G, Boukheddaden K, Coddjovi E, Linares J, Nogues M and Varret F 1998 Light-induced bistability in spin transition solids leading to thermal and optical hysteresis *Eur. Phys. J. B* **6** 183-93
- [8] Gülich P 1981 Spin crossover in iron(II)-complexes *Struct Bonding* **44** 83-192
- [9] Gülich P 2004 *Spin Crossover in Transition Metal Compounds II*, ed P Gülich and H Goodwin (Heidelberg: Springer) pp 231-60
- [10] Gülich P, Garcia Y and Goodwin H A 2000 Spin crossover phenomena in Fe(II) complexes *Chem. Soc. Rev.* **29** 419-27
- [11] Gülich P, Garcia Y and Spiering H 2002 *Magnetism: Molecules to Materials IV*, ed J S Miller and M Drillon (Weinheim: Wiley-VCH) pp 271-344
- [12] Gülich P, Garcia Y and Woike T 2001 Photoswitchable coordination compounds *Coordination Chemistry Reviews* **219** 839-79
- [13] Gülich P and Goodwin H A 2004 *Spin Crossover in Transition Metal Compounds I*, ed P Gülich and H Goodwin (Heidelberg: Springer) pp 1-48

- [14] Gütlich P, Hauser A and Spiering H 1994 Thermal and optical switching of iron(II) complexes *Angewandte Chemie - International Edition in English* **33** 2024-54
- [15] Gütlich P, van Koningsbruggen P J and Renz F 2004 Recent advances of spin crossover research *Optical Spectra and Chemical Bonding in Transition Metal Complexes* **107** 27-75
- [16] Ksenofontov V, Gaspar A B and Gütlich P 2004 *Spin Crossover in Transition Metal Compounds III*, ed P Gütlich and H Goodwin (Heidelberg: Springer) pp 23-64
- [17] Letard J F, Guionneau P, Rabardel L, Howard J A K, Goeta A E, Chasseau D and Kahn O 1998 Structural, magnetic, and photomagnetic studies of a mononuclear iron(II) derivative exhibiting an exceptionally abrupt spin transition. Light-induced thermal hysteresis phenomenon *Inorg. Chem.* **37** 4432-41
- [18] Lindner A, Menzel M, Renz F, Kurth D G and Thünemann A F 2006 Metallosupramolecular coordination polyelectrolytes investigated by Mössbauer spectroscopy *Hyperfine Interact.* **166** 465-8
- [19] Mahfoud T, Molnar G, Bonhommeau S, Cobo S, Salmon L, Demont P, Tokoro H, Ohkoshi S-I, Boukhedden K and Bousseksou A 2009 Electric-Field-Induced Charge-Transfer Phase Transition: A Promising Approach Toward Electrically Switchable Devices *J. Am. Chem. Soc.* **131** 15049-54
- [20] Pauling L and Corvell C D 1936 The Magnetic Properties and Structure of the Hemochromogens and related Substances *PNAS* **22** 159-63
- [21] Qi Y, Müller E W, Spiering H and Gütlich P 1983 The effect of a magnetic field on the high-spin α low-spin transition in bis(1,10-phenanthroline)iron thiocyanate ($[\text{Fe}(\text{phen})_2(\text{NCS})_2]$) *Chem. Phys. Lett.* **101** 503-5
- [22] Renz F 1995 *Diploma Thesis*, (Vienna: Vienna University of Technology)
- [23] Renz F 2001 Light Induced Excited States in Mono and Polynuclear Strong-Field Fe(II) Complex with Terpyridine-Derivatives *Molecular Photomagnetism Meeting*
- [24] Renz F, De Souza P A, Klingelhofer G and Goodwin H A 2002 Molecular sensors for moisture detection by Mossbauer spectroscopy *Hyperfine Interact.* **139** 699-704
- [25] Renz F, Hasegawa M, Hoshi T, El-Ayaan U, Linert W and Fukuda Y 1999 Anisotropic Effect after Stretching of the Spin-Crossover Compound $[\text{Fe}(\text{II})(2,6\text{-bis}(\text{benzimidazol-2}'\text{-yl)pyridine}(2))] (\text{ClO}_4)(2)$ in Polyvinylalcohol Polymer Matrix *Mol. Cryst. Liq. Cryst. Sci. Technol. Sect. A-Mol. Cryst. Liq. Cryst.* **335** 1243-52
- [26] Renz F, Oshio H, Ksenofontov V, Waldeck M, Spiering H and Gutlich P 2000 Strong field iron(II) complex converted by light into a long-lived high-spin state *Angew. Chem.-Int. Edit.* **39** 3699-700
- [27] Renz F, Spiering H, Goodwin H A and Gütlich P 2000 Light-perturbed hysteresis in an iron(II) spin-crossover compound observed by the Mossbauer effect *Hyperfine Interact.* **126** 155-8
- [28] Renz F, Spiering H, Gütlich P, Sugiyarto K H and Goodwin H 2002 Light Perturbed Thermal Hysteresis (LiPTH) in $[\text{Fe}(\text{bpp})_2][\text{Fe}(\text{CN})_5\text{NO}]$. In: *TOSS-Meeting*, (Seeheim, Germany)
- [29] Roux C, Zarembowitch J, Gallois B, Granier T and Claude R 1994 Toward Ligand-Driven Light-Induced Spin Change - Influence of the Configuration of 4-Styrylpyridine (Stpy) on the Magnetic- Properties of $\text{Fe}(\text{II})(\text{Stpy})_4(\text{Ncs})_2$ Complexes - Crystal-Structures of the Spin-Crossover Species $\text{Fe}(\text{Trans-Stpy})_4(\text{Ncs})_2$ and of the High-Spin Species $\text{Fe}(\text{Cis-Stpy})_4(\text{Ncs})_2$ *Inorg. Chem.* **33** 2273-9
- [30] Vanko G, Renz F, Molnar G, Neisius T and Karpati S 2007 Hard-X-ray-induced excited-spin-state trapping *Angew. Chem.-Int. Edit.* **46** 5306-9