

Article

A Study of the Conformers of the (Nonafluorobutanesulfonyl)imide Ion by Means of Infrared Spectroscopy and Density Functional Theory (DFT) Calculations

Oriole Palumbo ¹, Francesco Trequatrini ^{1,2,*}, Giovanni Battista Appetecchi ³ and Annalisa Paolone ¹

¹ Consiglio Nazionale delle Ricerche, Istituto dei Sistemi Complessi, U.O.S. La Sapienza, Piazzale A. Moro 5, 00185 Roma, Italy; oriele.palumbo@roma1.infn.it (O.P.); annalisa.paolone@roma1.infn.it (A.P.)

² Physics Department, Sapienza University of Rome, Piazzale A. Moro 5, 00185 Rome, Italy

³ Materials and Physicochemical Processes Laboratory (SSPT-PROMAS-MATPRO), ENEA (Italian National Agency for New Technologies, Energy and Sustainable Economic Development), Via Anguillarese 301, 00123 Rome, Italy; gianni.appetecchi@enea.it

* Correspondence: francesco.trequatrini@roma1.infn.it; Tel.: +39-06-4991-4526

Academic Editor: Palmiro Poltronieri

Received: 30 January 2017; Accepted: 20 February 2017; Published: 22 February 2017

Abstract: Pyrrolidinium-based ionic liquids with anions of the per(fluoroalkylsulfonyl)imide family are particularly interesting for their use as electrolytes in lithium batteries. These ions have several geometric isomers and the presence of different ion conformers and their distribution affects the ILs (Ionic liquids) physical and chemical properties. In the present work, we report the temperature dependence of the infrared spectra of the *N*-butyl-*N*-methyl-pyrrolidinium(trifluoromethanesulfonyl) (nonafluorobutanesulfonyl)imide (PYR₁₄-IM₁₄) ionic liquid; DFT (Density Functional Theory) calculations performed with different models provides indications about the IM₁₄ conformers and their vibrational spectra. Moreover the temperature dependence of the intensity of the lines identified as markers of different conformers provide indications about the conformers' distribution and the difference of their enthalpy in the liquid phase.

Keywords: infrared spectra; ionic liquids; DFT calculations

1. Introduction

Ionic liquids (ILs) are salts with melting point below 100 °C, which have been largely studied in recent years due to their peculiar properties [1–3], such as a wide liquidus range associated with a low melting point, negligible vapor pressure, chemical and electrochemical stabilities up to high temperatures, and high ionic conductivity, which make them attractive not only for catalytic reactions and synthesis but also for energy applications [1–5].

They are typically formed by organic cations, like imidazolium, pyrrolidinium, ammonium or alkyl phosphonium, and organic/inorganic anions, like hexafluorophosphate, tetrafluoroborate, triflate, dicyanamide, tetracyanamethanide, or bis(trifluoromethanesulfonyl)imide (TFSI) [1–4]. The physical and chemical properties of these compounds are influenced by the nature of the ions and by their structure. Indeed, all of the properties of ILs are the consequence of competitive microscopic interaction forces, the balance of which can generate an extremely rich scenario. In particular, these interactions can be finely tuned by assembling different combinations of cations and anions or by changing the length and the type of the side chains of the composing ions [4]. Many of the ions composing the ILs have geometric isomers, which can coexist in the liquid state according to the Boltzmann distribution.

For some ions, conformers can be identified by means of spectroscopic techniques, such as Raman and infrared spectroscopy, combined to ab initio or DFT (Density Functional Theory) calculations of the vibration frequencies [6–20].

In previous works [6,10,11,15–19] we investigated, by means of vibrational spectroscopies, the conformers of several ions largely used in the design of applicative ILs, since using ab initio calculations of the infrared-active intramolecular vibrations, it was possible to assign the experimental lines to the various ions composing the liquid, and even to their different conformers. Moreover, we reported the temperature and pressure dependence of the infrared absorption spectra of these ILs both in the liquid and in the solid phase in order to ascertain the changes of the intramolecular structure, and in particular of the conformer distribution induced by the crystallization/melting process. We focused on cations belonging to the pyrrolidinium and ammonium families and on imide anions such as bis(fluorosulfonyl)imide (FSI) and bis(trifluoromethanesulfonyl)imide (TFSI).

The TFSI anion is a flexible molecule that can adopt two energetically inequivalent conformations, the transoid and the cisoid forms, differing in energy by only 2.2 kJ/mol [7,9,13,16]. This ion has been widely studied by vibrational spectroscopies since it possesses very well detectable bands: in particular in the infrared spectra trans-TFSI displays a strong absorption around 628 cm^{-1} , while cis-TFSI shows two bands centered at 602 and 650 cm^{-1} [7,10]. Moreover, the temperature dependence of the intensities of the peaks attributed to different conformers can provide information about the energy separation of the various conformers [12] and their concentration, which affects the IL's physical and chemical properties in both the liquid and solid phases. Indeed, the molecular configurations of anions and cations is a key point to understand the dependence of the macroscopic properties of the ILs on their ionic composition. Regarding TFSI, the transoid conformer with a C2 symmetry is more stable than the cisoid one, which has a C1 symmetry [7,10,12], however, due to the low energy separation both conformers are present in the liquid state. Instead, the relative concentration of the TFSI conformers in the different phases of the ILs strongly depends on the cation, as we showed by comparing the temperature dependence of the infrared spectra of two ammonium-based ILs sharing the same TFSI anion, and having different cations: *N*-trimethyl-*N*-propylammonium TFSI and *N*-trimethyl-*N*-hexylammonium TFSI. As expected, the liquid phases of the two liquids are all characterized by the presence of both TFSI conformers. However, the solid phase shows different behavior for the two compounds: in solid TMPA-TFSI, the relative concentration of the conformers is strongly shifted toward a predominance of the transoid conformer; on the contrary, the solid TMHA-TFSI retains only the cis-TFSI, even if this rotamer is less thermodynamically stable. We also showed that the study of the relative concentration of the two anion conformers as a function of temperature and pressure provides information about the phase diagram [6,11,16,18,19].


Also the bis(fluorosulfonyl)imide (FSI) ion has two conformers: one with C2 (*trans*) [15,21,22] and the other with C1 (*cis*) symmetry [15,21–23]. The former is more stable, while the latter has a higher energy by about 4.5 kJ/mol; moreover they both give rise to well detectable bands in the IR spectrum that can be used as a marker of their presence [15].

Concerning cations, conformational analyses are more complex as many ions have an alkyl chain which considerably increases the number of single bonds around which one can have rotations. Some conformational analysis exists for selected cations of the families of pyrrolidinium [14,17,24], imidazolium [25,26] and ammonium [10,11]. Pyrrolidinium based ILs have been largely investigated for their potential application in electrochemistry; and, in particular, extensive investigations of the *N*-butyl-*N*-methyl-pyrrolidinium (PYR₁₄) cation conformers was performed [14,27,28]. Our recent calculations [28] showed that the PYR₁₄ ion possesses 33 conformers. The most stable is called equatorial-envelope, and it has a planar configuration of the four carbon atoms of the C₄N ring (envelope) and the butyl group at the equatorial position against these four atoms. At an energy only 1.8 kJ/mol higher, one finds the axial-envelope configurations, with the butyl group at an axial position against the four carbon atoms of the pyrrolidinium ring. About 3 kJ/mol higher than the most stable one, we find the twist-axial conformer, in which two atoms of the C₄N ring are located above and

below the plane constructed by the other three atoms. Higher energy conformer were found to span the entire energy range between 3 and 25 kJ/mol. The envelope and twist conformers can easily convert one into the other by means of pseudorotations, and, since the reported difference in energy between the different conformers is low [14,28], it has been suggested that these two conformers are both present in equilibrium in PYR₁₄-TFSI [14].

Indeed, the *N*-alkyl-*N*-methylpyrrolidiniumbis(trifluoromethanesulfonyl)imide ILs have been largely studied due to their potential use as electrolytes in lithium batteries, for which it is important to widen the liquidus range by shifting the melting temperature to lower temperatures. To achieve this goal several combinations of cations belonging to the pyrrolidinium family and appropriate anions of the per(fluoroalkylsulfonyl)imide family have been studied [5,29–32]. In particular calorimetric measurements [5,30,32] showed that an increase in the difference between the cation and the anion sizes induces a lowering of the melting transition temperature that ends in a very difficult crystallization, as observed in ILs containing (trifluoromethanesulfonyl)(nonafluorobutanesulfonyl)imide (such as PYR₁₄-IM₁₄ or PYR₁₃-IM₁₄), for which only a glass transition is detected around 190 K despite the repeated thermal cycles carried out at low rates and at low temperatures. A similar behavior has been reported also for PYR₁₄ (nonafluorobutanesulfonyl)(toluenesulfonyl)imide (PYR₁₄-IM_{T4}) [5], indicating that the unfavorable packing of strongly asymmetric anions such as IM₁₄ or IM_{T4} remarkably lowers the cation-anion lattice energy and hinders the crystallization of the ionic liquid materials [30].

To our knowledge, except for the previously reported TSFI and FSI anion, a systematic conformational analysis of various anions of the per(fluoroalkylsulfonyl)imide family and their vibrational spectra is still lacking. To fill this gap, in this work, we present an experimental and computational study of the IM₁₄ anion. In particular we report the temperature dependence of the infrared spectra of the PYR₁₄-IM₁₄ (structural formula in Scheme 1); DFT calculations performed with different models provides indications about the IM₁₄ conformers and their vibrational spectra. Indeed, only a conformational search by DFT was reported for IM₁₄ [32]. The comparison of the computational results with the experimental vibrational lines allows the detection of lines which can be used as good markers of the occurrence of the two lower energy anion conformers. Moreover, the temperature dependence of the intensity of those lines provides indications about the difference of the enthalpy of different conformers of the liquid phase.

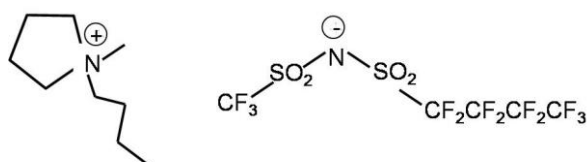

Scheme 1. Structural formula of PYR₁₄. IM₁₄: left, PYR₁₄⁺ cation; right, IM₁₄[−] anion.

2. Results and Discussion

The infrared spectra of the PYR₁₄-IM₁₄ ionic liquid measured in the frequency range between 400 and 1500 cm^{−1} at two different temperatures (e.g., around room temperature and at 180 K) are reported in Figure 1. It must be noticed that the spectrum was measured up to 3600 cm^{−1} (see Figure S1 in the supplementary Materials) and the absence of absorptions lines in the range between 1600 and 1700 cm^{−1} (O-H bending modes) and between 3200 and 3600 cm^{−1} (O-H stretching modes) ruled out the presence of water in the sample. In order to ascribe single vibration lines to the conformers of the composing ions we performed calculations of their vibrational frequencies and intensity.

For the PYR₁₄ cation, we considered only the lowest energy conformer which corresponds to the equatorial-envelope (eq-env) geometry [27,28] and we reported in Figure 1c the theoretical absorption spectrum obtained with the vibration frequencies and infrared intensities of the lines previously calculated by us by means of density functional theory at the level of the B3LYP (Becke, 3-parameter, Lee-Yang-Parr) approximation [27]. This approach has been already used to study the infrared spectrum

of the PYR_{14} -TFSI and its modifications induced by the interaction with a membrane [27]. It must be noticed that, in Figure 1, the calculated spectrum of the cation conformer is plotted multiplied by a factor of five for a better comparison, since the intensity obtained for its vibrational lines is very weak in this frequency range, compared to those obtained for the anion conformers, as we show in the following:

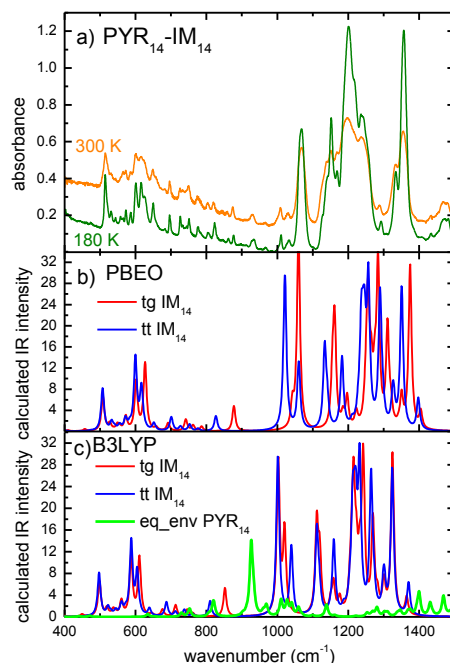


Figure 1. Comparison between the experimental absorbance of the PYR_{14} - IM_{14} measured at two different temperatures (a) and the calculated absorptions of the two IM_{14} conformers (results from PBE0 (Perdew-Burke-Ernzerhof) model in (b) and from B3LYP model in panel (c) and of the eq-env PYR_{14} conformer (B3LYP (Becke, 3-parameter, Lee-Yang-Parr) model in (c), in the frequency range between 400 and 1500 cm^{-1} . For a better comparison the calculated intensity of the PYR_{14} conformer is multiplied by a factor of five.

Indeed, for the IM_{14} anion, the conformational analysis performed by means of Spartan software (Wavefunction Inc., Irvine, CA, USA) indicates that this ion possesses 74 conformers, but calculations pointed out the occurrence of two low energy configurations, in agreement with previous partial DFT calculations [32]. The most stable configuration is called all-trans (*tt*), while at an energy 1.8 kJ/mol higher we found the trans-gauche (*tg*) conformer. The geometry of these two lowest energy conformers is reported in Figure 2, while their atomic positions are reported in the supporting info, Tables S1 and S2, respectively.

The higher energy conformers span the entire energy range up to ~19 kJ/mol.

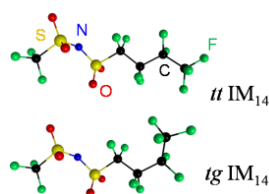


Figure 2. Equilibrium geometry of the two lowest energy IM_{14} conformers, *tt* IM_{14} and *tg* IM_{14} , as obtained by DFT calculations.

The vibration frequencies and their intensity were calculated for both IM_{14} conformers by means of two models: the B3LYP is commonly used for calculations on ions composing ionic liquids [6,10,13–15]; the PBE0 model, that has been reported to give better agreement with the experimental vibration frequencies than the B3LYP model in the bis(trifluoromethanesulfonyl)imide ion [15]. The unscaled calculated frequency values obtained by both methods are reported in the supporting materials, in Table S3, while the absorption spectra generated from these values between 400 and 1500 cm^{-1} with no scaling factor are reported in Figure 1b,c.

The comparison of the experimental absorbance with the calculated vibration lines provides evidence that the liquid shows the presence of the two anion conformers at both temperatures. In fact the lines below 700 cm^{-1} and between 1000 and 1500 cm^{-1} in the spectrum can be due either to the *tg* or the *tt* conformer or their superposition, so that the absence of one of them could not be excluded, whereas the contribution of the cation conformer in this frequency range is negligible, except for the line at 950 cm^{-1} . Moreover, the cation lines calculated with the PBE0 model coincide very well with the experimental lines. The frequencies obtained by the B3LYP model are, instead, underestimated and a scaling factor of 1.02 would be necessary to obtain a good agreement with the data. This better coincidence indicates a better performance of the PBE0 model, as already reported for the FSI anion, and it is worth noting that this model is much less time consuming than B3LYP.

As reported in Figure 1, between 1000 and 1400 cm^{-1} there are several intense absorption lines due to the two anion conformers, but they result quite superimposed in the experimental spectrum and therefore they are difficult to be used as markers of the two configurations. Instead, as better displayed in Figure 3, around 600 cm^{-1} , there are two clearly distinguishable lines, at 616 and 626 cm^{-1} , which can be assigned to the S-N-S in plane bending mode respectively of the *tt* and of *tg* IM_{14} conformers and, therefore, could be used as markers of presence of the two conformers. Indeed, absorbance spectra collected at various temperatures between 300 and 180 K (Figure 3) show that these two lines are present in the whole measured temperature range, even if their relative intensities change with temperature. It has been already reported that this PYR_{14} - IM_{14} undergoes a glass transition around 190 K [5,29–32]; therefore, the present measurements indicate that the two conformers are present both in the liquid and in the glassy state.

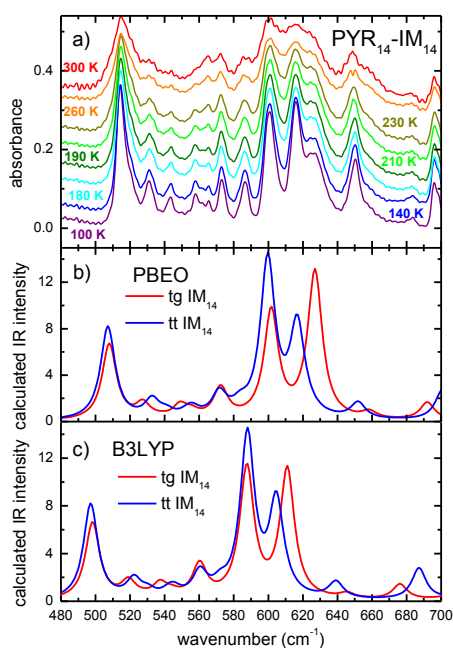


Figure 3. Comparison between the experimental temperature dependence of the absorbance of the PYR_{14} - IM_{14} (a) and the calculated absorptions of the two IM_{14} conformers (results from PBE0 model in (b) and from the B3LYP model in (c) in the frequency range between 550 and 700 cm^{-1}).

The temperature dependence of the absorbance spectrum allows the study of the temperature evolution of the concentration of the two conformers of IM₁₄. The ratio of the conformers' concentration, r , in a liquid is proportional to the ratio of the intensities of the spectral bands attributable to specific conformers [12]. In the present case, we can distinguish a band at 616 cm⁻¹ due to the low energy tt IM₁₄ and a band at 626 cm⁻¹ which is attributable to the higher energy tg IM₁₄ conformer.

Therefore, we define the ratio of the two conformer concentration, C_x , as:

$$r = \frac{[C_{tg}]}{[C_{tt}]} = \frac{I_{tg}}{I_{tt}} \quad (1)$$

where I_x designates the integrated IR (Infrared) intensity of the band centered at wavenumber x [12]. The following equation holds for the equilibrium constant, K , between conformers. In the liquid state:

$$-RT \ln K = \Delta H - T\Delta S \quad (2)$$

where R is the gas constant, T is the temperature and ΔH and ΔS are the enthalpy and entropy differences between the conformers. Considering that the ratio between the conformer concentrations is proportional to the equilibrium constant $K \propto r$, one obtains:

$$\ln(r) = -\frac{1}{T} \frac{\Delta H}{R} + \frac{\Delta S}{R} + c \quad (3)$$

where c is a constant [12].

In the present case we considered $I_{tg} = I_{626}$ and $I_{tt} = I_{616}$.

Figure 4 shows the plot of $\ln(r)$ vs. $1/T$, which verifies the Arrhenius dependence of the concentration from temperature, since there is a straight linear dependence of $\ln(r)$ on $1/T$ for our liquid. This linear dependence in the temperature range above 190 K allows the calculation of ΔH , which is found to be positive and equal to 0.98 ± 0.3 kJ/mol, further confirming that the tt IM₁₄ conformer is the more energetically favored.

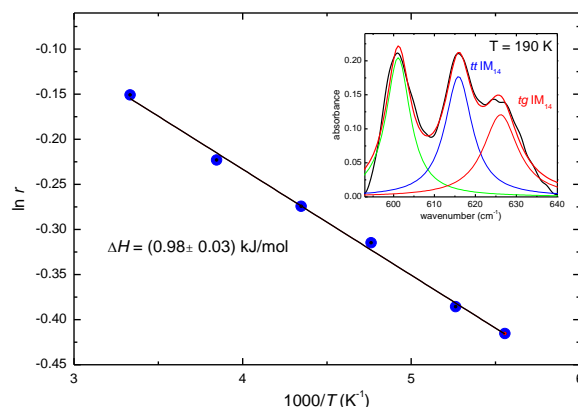


Figure 4. Temperature dependence of the logarithm of the ratio of the intensities of the bands due to the two IM₁₄ conformers and best fit line. In the inset an example of the fit of the absorbance spectrum and deconvolution into the contributions of the conformers is reported.

The presently reported study provides evidence that a careful comparison of computational results and experimental data is able to identify the lowest energy conformers also of complex systems, such as the presently investigated, in which a total number of 74 conformers is expected.

3. Materials and Methods

3.1. Experimental

The liquid *N*-butyl-*N*-methylpyrrolidinium (trifluoromethanesulfonyl)(nonafluorobutanesulfonyl) imide (Pyr₁₄-IM₁₄) was synthesized by a procedure developed at ENEA and described in detail elsewhere [29,30].

Infrared spectroscopy measurements were performed by means of a Bruker IFS 125 HR spectrometer (Bruker Corporation, Billerica, MA, USA) at the AILES beamline of the SOLEIL Synchrotron [33,34]. The spectra were recorded in the mid infrared range (400–6000 cm⁻¹) at a resolution of 0.5 cm⁻¹, by combining a potassium bromide beamsplitter and a wide-band bolometer detector from Infrared Laboratories. A thin layer of the IL was placed between the diamond windows of a vacuum tight cell. All measurements were performed in high vacuum ($p < 10^{-4}$ mbar), in order to avoid contaminations and absorption bands due to H₂O and CO₂. The transmission was calculated using the spectrum of the bare optical windows as a reference. Transmission measurements were converted to absorbance data. The samples were cooled down to 100 K by means of a Cryomec cryopump with a temperature rate of 5 K/min, and data were collected on heating at the same rate between this minimum temperature and 300 K.

3.2. Computational

Spartan software [35,36] was employed to find preliminary geometries of the conformers of the (trifluoromethanesulfonyl)(nonafluorobutanesulfonyl)imides ion by means of force field models, which were afterwards optimized by means of the Firefly package [37,38] performing DFT calculations with the 6-31G**basis set by means of two different theories: B3LYP or PBE0. The combination B3LYP theory and 6-31G**basis set has been largely used in the literature in order to investigate the vibrational properties of ionic liquids. However, in the case of the bis(trifluoromethanesulfonyl)imide and the bis(fluorosulfonyl)imide ion [15,16] it has been shown that the PBE0 functional gives better agreement with the experimental vibrational spectra. Therefore, here we compare the two models for the trifluoromethanesulfonyl)(nonafluorobutanesulfonyl)imides ion.

After the geometry optimization, the vibrational frequencies and the IR intensities were calculated. The wxMacMolPlt software (NCSA, Urbana, IL, USA) was used to visualize the molecular geometries and vibrations [39]. The IR spectrum of each conformer was simulated by summing Lorentzian curves centered at each calculated IR vibration frequency with a fixed 10 cm⁻¹ peak width.

4. Conclusions

In the present work we report the infrared spectrum of the PYR₁₄-IM₁₄ ionic liquid and its temperature dependence. DFT calculations performed with different models provides indications about the IM₁₄ conformers and their vibrational spectra. In particular the markers of the occurrence of the two low-energy conformers (the all-trans (*tt*) and the trans-gauche (*tg*) conformer), were identified in the spectrum. An analysis of the temperature dependence of these lines shows that these two conformers are both present in the glassy and in the liquid phase, and the difference of their enthalpy in the liquid phase is calculated.

Supplementary Materials: The following are available online at www.mdpi.com/2078-1547/8/1/7/S1, Table S1: Atomic positions of conformer *tg* IM₁₄ of the trifluoromethanesulfonyl)(nonafluorobutanesulfonyl)imides ion (the three coordinates are reported in Å), Table S2: Atomic positions of conformer *tg* IM₁₄ of the trifluoromethanesulfonyl)(nonafluorobutanesulfonyl)imides ion (the three coordinates are reported in Å), Table S3: Unscaled calculated frequency and intensity of the vibrations of the two conformers of the trifluoromethanesulfonyl)(nonafluorobutanesulfonyl)imides ion, with the two theories: PBE0 and B3LYP, Figure S1: Absorbance of the PYR₁₄-IM₁₄ measured at 300 K in the frequency range between 1300 and 1700 cm⁻¹ (panel a) and between 2700 and 3600 cm⁻¹ (panel b). Lines due to C-H bending and stretching modes are indicated, while the absence of absorptions lines in the range between 1600 and 1700 cm⁻¹ (O-H bending modes) and between 3200 and 3600 cm⁻¹ (O-H stretching modes) rules out the presence of water.

Acknowledgments: We wish to thank Pascale Roy and Jean-Blaise Brubach for assistance at the AILES beamline of the Synchrotron Soleil. This study was performed beamtime # 20160058 at the Soleil Synchrotron.

Author Contributions: Giovanni Battista Appetecchi synthesized the materials; Annalisa Paolone performed the experiments and the DFT calculations; Oriele Palumbo and Francesco Trequattrini analyzed the data; Oriele Palumbo wrote the paper.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Welton, T. Ionic liquids in catalysis. *Coord. Chem. Rev.* **2004**, *248*, 2459–2477. [[CrossRef](#)]
2. Navarra, M.A. Ionic liquids as safe electrolyte components for Li-metal and Li-ion batteries. *Mat. Res. Soc. Bull.* **2013**, *38*, 548–553. [[CrossRef](#)]
3. Armand, M.; Endres, F.; MacFarlane, D.R.; Ohno, H.; Scrosati, B. Ionic-liquid materials for the electrochemical challenges of the future. *Nat. Mater.* **2009**, *8*, 621–629. [[CrossRef](#)] [[PubMed](#)]
4. Matic, A.; Scrosati, B. Ionic liquids for energy applications. *MRS Bull.* **2013**, *38*, 533–537. [[CrossRef](#)]
5. Kunze, M.; Jeong, S.; Paillard, E.; Winter, M.; Passerini, S. Melting behavior of pyrrolidinium-based ionic liquids and their binary mixtures. *J. Phys. Chem.* **2010**, *114*, 12364–12369. [[CrossRef](#)]
6. Palumbo, O.; Vitucci, F.M.; Trequattrini, F.; Paolone, A. A study of the conformers of the *N,N*-diethyl-*N*-methyl-*N*-propylammonium ion by means of infrared spectroscopy and DFT calculations. *Vib. Spec.* **2015**, *80*, 11–16. [[CrossRef](#)]
7. Herstedt, M.; Smirnov, M.; Johansson, P.; Chami, M.; Grondin, J.; Servant, L.; Lassègues, J.C. Spectroscopic characterization of the conformational states of the bis(trifluoromethanesulfonyl)imide anion (TFSI⁻). *J. Raman Spectrosc.* **2005**, *36*, 762–770. [[CrossRef](#)]
8. Fujii, K.; Takamuku, T.; Kanzaki, R.; Umebayashi, Y.; Ishiguro, S.-I. Conformational equilibrium of bis(trifluoromethanesulfonyl)imide anion of a room-temperature ionic liquid: Raman spectroscopic study and DFT calculations. *J. Phys. Chem.* **2006**, *110*, 8179–8183. [[CrossRef](#)] [[PubMed](#)]
9. Canongia Lopes, J.N.; Shimizu, K.; Pádua, A.A.H.; Umebayashi, Y.; Fukuda, S.; Fujii, K.; Ishiguro, S.-I. A tale of two ions: The conformational landscapes of bis(trifluoromethanesulfonyl) amide and *N,N*-dialkylpyrrolidinium. *J. Phys. Chem. B* **2008**, *112*, 1465–1472. [[CrossRef](#)] [[PubMed](#)]
10. Vitucci, F.M.; Trequattrini, F.; Palumbo, O.; Brubach, J.-B.; Roy, P.; Paolone, A. Infrared spectra of bis(trifluoromethanesulfonyl)imide based ionic liquids: Experiments and DFT simulations. *Vib. Spec.* **2014**, *74*, 81–87. [[CrossRef](#)]
11. Vitucci, F.M.; Trequattrini, F.; Palumbo, O.; Brubach, J.-B.; Roy, P.; Navarra, M.A.; Panero, S.; Paolone, A. Stabilization of different conformers of bis(trifluoromethanesulfonyl)imide anion in ammonium based ionic liquids at low temperatures. *J. Phys. Chem.* **2014**, *118*, 8758–8764. [[CrossRef](#)] [[PubMed](#)]
12. Martinelli, A.; Matic, A.; Johansson, P.; Jacobsson, P.; Börjesson, L.; Fericola, A.; Panero, S.; Scrosati, B.; Ohno, H. Conformational evolution of TFSI⁻ in protic and aprotic ionic liquids. *J. Raman Spectrosc.* **2011**, *42*, 522–528. [[CrossRef](#)]
13. Fujii, K.; Seki, S.; Fukuda, S.; Kanzaki, R.; Takamuku, T.; Umebayashi, Y.; Ichiguro, S.-I. Anion conformation of low-viscosity room temperature ionic liquid 1-ethyl-3-methylimidazolium bis(fluorosulfonyl)imide. *J. Phys. Chem.* **2007**, *111*, 12829–12833. [[CrossRef](#)] [[PubMed](#)]
14. Fujimori, T.; Fujii, K.; Kanzaki, R.; Chiba, K.; Yamamoto, H.; Umebayashi, Y.; Ishiguro, S.-I. Conformational structure of room temperature ionic liquid *N*-butyl-*N*-methyl-pyrrolidiniumbis(trifluoromethanesulfonyl)imide—Raman spectroscopic study and DFT calculations. *J. Mol. Liquids* **2007**, *131–132*, 216–224. [[CrossRef](#)]
15. Gatto, S.; Palumbo, O.; Caramazza, S.; Trequattrini, F.; Postorino, P.; Appetecchi, G.B.; Paolone, A. The infrared spectrum of bis(fluorosulfonyl)imide revisited: attractive performances of the PBE0/6–31G** model. *Vib. Spec.* **2016**, *82*, 16–21. [[CrossRef](#)]
16. Palumbo, O.; Trequattrini, F.; Vitucci, F.M.; Navarra, M.A.; Panero, S.; Paolone, A. An infrared spectroscopy study of the conformational evolution of the bis(trifluoromethanesulfonyl)imide ion in the liquid and in the glass state. *Adv. Condens. Matter Phys.* **2015**, *2015*, 176067. [[CrossRef](#)]
17. Trequattrini, F.; Palumbo, O.; Gatto, S.; Appetecchi, G.B.; Paolone, A. A computational and experimental study of the conformers of pyrrolidinium ionic liquid cations containing an ethoxy group in the alkyl side chain. *Adv. Chem.* **2016**, *2016*, 1–9. [[CrossRef](#)]

18. Capitani, F.; Gatto, S.; Postorino, P.; Palumbo, O.; Trequattrini, F.; Deutsch, M.; Brubach, J.-B.; Roy, P.; Paolone, A. The complex dance of the two conformers of bis(trifluoromethanesulfonyl)imide as a function of pressure and temperature. *J. Phys. Chem.* **2016**, *120*, 1312–1318. [[CrossRef](#)] [[PubMed](#)]
19. Capitani, F.; Trequattrini, F.; Palumbo, O.; Paolone, A.; Postorino, P. Phase transitions of PYR₁₄-TFSI as a function of pressure and temperature: The competition between smaller volume and lower energy conformer. *J. Phys. Chem.* **2016**, *120*, 2921–2928. [[CrossRef](#)] [[PubMed](#)]
20. Sobczyk, L.; Chudoba, D.; Tolstoy, P.M.; Filarowski, A. Some brief notes on theoretical and experimental investigations of intramolecular hydrogen bonding. *Molecules* **2016**, *21*, 1657–1676. [[CrossRef](#)] [[PubMed](#)]
21. Farrugia, L.J.; Holfter, H.; Klapötke, T.M. Preparation and X-ray crystal structure of caesiumimidodisulphuryl fluoride Cs[N(SO₂F)₂]. *J. Fluor. Chem.* **1996**, *78*, 51–53. [[CrossRef](#)]
22. Matsumoto, K.; Oka, T.; Nohira, T.; Hagiwara, R. Polymorphism of alkali bis(fluorosulfonyl)amides (M[N(SO₂F)₂], M = Na, K, and Cs). *Inorg. Chem.* **2013**, *52*, 568–576. [[CrossRef](#)] [[PubMed](#)]
23. Beran, M.; Příhoda, J.; Žák, Z.; Cerník, M. A new route to the syntheses of alkali metal bis(fluorosulfonyl)imides: Crystal structure of LiN(SO₂F)₂. *Polyhedron* **2006**, *25*, 1292–1298. [[CrossRef](#)]
24. Ishida, H. Conformations of pyrrolidinium ion studied by molecular orbital calculations. *Z. Naturforsch.* **2000**, *55a*, 665–666.
25. Lassègues, J.C.; Grondin, J.; Holomb, R.; Johansson, P. Raman and AB initio study of the conformational isomerism in the 1-ethyl-3-methyl-imidazolium bis(trifluoromethanesulfonyl)imide ionic liquid. *J. Raman Spectrosc.* **2007**, *3*, 551–558. [[CrossRef](#)]
26. Ribeiro, M.C. High viscosity of imidazolium ionic liquids with the hydrogen sulfate anion: A raman spectroscopy study. *J. Phys. Chem.* **2012**, *116*, 7281–7290. [[CrossRef](#)] [[PubMed](#)]
27. Vitucci, F.M.; Palumbo, O.; Trequattrini, F.; Brubach, J.-B.; Roy, P.; Meschini, I.; Croce, F.; Paolone, A. Interaction of 1-butyl-1-methylpyrrolidinium bis(trifluoromethanesulfonyl)imide with an electrospun PVdF membrane: Temperature dependence of the concentration of the anion conformers. *J. Chem. Phys.* **2015**, *143*, 143. [[CrossRef](#)] [[PubMed](#)]
28. Palumbo, O.; Trequattrini, F.; Vitucci, F.M.; Paolone, A. Relaxation dynamics and phase transitions in ionic liquids: viscoelastic properties from the liquid to the solid state. *J. Phys. Chem.* **2015**, *119*, 12905–12911. [[CrossRef](#)]
29. Montanino, M.; Alessandrini, F.; Passerini, S.; Appetecchi, G.B. Water-based synthesis of hydrophobic ionic liquids for high-energy electrochemical devices. *Electrochim. Acta* **2013**, *96*, 124–133. [[CrossRef](#)]
30. Jeremias, S.; Carewska, M.; Conte, L.; Passerini, S.; Appetecchi, G.B. Asymmetry effect of novel per(fluoroalkylsulfonyl)imide anions in pyrrolidinium ionic liquids. *RSC Adv.* **2013**, *3*, 17755–17761. [[CrossRef](#)]
31. Castiglione, F.; Raos, G.; Appetecchi, G.B.; Montanino, M.; Passerini, S.; Moreno, M.; Famulari, A.; Mele, A. Blending ionic liquids: How physico-chemical properties change. *Phys. Chem. Chem. Phys.* **2010**, *12*, 1784–1792. [[CrossRef](#)] [[PubMed](#)]
32. Russina, O.; Lo Celso, F.; Di Michiele, M.; Passerini, S.; Appetecchi, G.B.; Castiglione, F.; Mele, A.; Caminiti, R.; Triolo, A. Mesoscopic structural organization in triphilic room temperature ionic liquids. *Faraday Discuss.* **2013**, *167*, 499–513. [[CrossRef](#)] [[PubMed](#)]
33. Roy, P.; GuidiCestelli, M.; Nucara, A.; Marcouille, O.; Calvani, P.; Giura, P.; Paolone, A.; Mathis, Y.-L.; Gerschel, A. Spectral distribution of infrared synchrotron radiation by an insertion device and its edges: A comparison between experimental and simulated spectra. *Phys. Rev. Lett.* **2000**, *84*, 483–486. [[CrossRef](#)] [[PubMed](#)]
34. Roy, P.; Brubach, J.-B.; Calvani, P.; De Marzi, G.; Filabozzi, A.; Gerschel, A.; Giura, P.; Lupi, S.; Marcouille, O.; Mermat, A.; et al. Infrared synchrotron radiation: From the production to the spectroscopic and microscopic applications. *Nucl. Instrum. Methods Phys. Res. Sect.* **2001**, *426*, 467–468. [[CrossRef](#)]
35. Shao, Y.; Molnar, L.F.; Jung, Y.; Kussmann, J.; Ochsenfeld, C.; Brown, S.T.; Gilbert, A.T.B.; Slipchenko, L.V.; Levchenko, S.V.; O'Neill, D.P.; et al. Advances in methods and algorithms in a modern quantum chemistry program package. *Phys. Chem. Chem. Phys.* **2006**, *8*, 3172–3191. [[CrossRef](#)] [[PubMed](#)]
36. Hehre, W.J. *A Guide to Molecular Mechanics and Quantum Chemical Calculations*; Wavefunction, Inc.: Irvine, CA, USA, 2003.
37. Granovsky, A.A. Firefly version 8.0. Available online: <http://classic.chem.msu.su/gran/firefly/index.html> (accessed on 21 February 2017).

38. Schmidt, M.W.; Baldrige, K.K.; Boatz, J.A.; Elbert, S.T.; Gordon, M.S.; Jensen, J.H.; Koseki, S.; Matsunaga, N.; Nguyen, K.A.; Su, S.; et al. General atomic and molecular electronic structure system. *J. Comput. Chem.* **1993**, *14*, 1347–1363. [[CrossRef](#)]
39. Bode, B.M.; Gordon, M.S. MacMolPlt: A graphical user interface for GAMESS. *J. Mol. Graph. Model.* **1999**, *16*, 133–138. [[CrossRef](#)]



© 2017 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).