



# Scalable and template-free production of mesoporous calcium carbonate and its potential to formaldehyde adsorbent

著者	YAMANAKA Shinya, OISO Takahiro, KURAHASHI Yuya, ABE Hiroya, HARA Kenji, FUJIMOTO Toshiyuki, KUGA Yoshikazu
journal or publication title	Journal of Nanoparticle Research
volume	16
number	2
page range	2266
year	2014-01-22
URL	<a href="http://hdl.handle.net/10258/00009469">http://hdl.handle.net/10258/00009469</a>

doi: [info:doi/10.1007/s11051-014-2266-9](https://doi.org/10.1007/s11051-014-2266-9)

**Scalable and template-free production of mesoporous calcium carbonate and its  
potential to formaldehyde adsorbent**

Shinya Yamanaka\*<sup>1</sup>, Takahiro Oiso <sup>2</sup>, Yuya Kurahashi <sup>2</sup>, Hiroya Abe<sup>3</sup>, Kenji Hara<sup>4</sup>,  
Toshiyuki Fujimoto <sup>1</sup> and Yoshikazu Kuga <sup>1</sup>

<sup>1</sup> College of Environmental Technology, Muroran Institute of Technology, Mizumoto-cho  
27-1, Muroran 050-8585, Japan

<sup>2</sup> Division of Applied Sciences, Muroran Institute of Technology, Mizumoto-cho 27-1,  
Muroran 050-8585, Japan

<sup>3</sup> Joining and Welding Research Institute, Osaka University, 11-1 Mihogaoka, Ibaraki,  
Osaka 567-0047, Japan

<sup>4</sup> Catalysis Research Center, Hokkaido University, Kita 21 Nishi 10, Kita-ku, Sapporo,  
Hokkaido 001-0021, Japan

\* Corresponding author. Tel.: +81 143 46 5747; fax: +81 143 46 5701.

*E-mail address:* syama@mmm.muroran-it.ac.jp (S. Yamanaka).

1 **Abstract:** Here we report a scalable and template-free production strategy in the synthesis  
2 of a mesoporous calcium carbonate, which undergoes self-assembled nanostructure  
3 formation through a temperature-induced aggregation and polymorphic transformation of  
4 the colloids. The specific surface area and pore size distribution of resulting mesoporous  
5 calcium carbonate are clearly different depending on the aging temperature. The specific  
6 surface area and average pore size for aging temperature of 293 K are  $207.3 \pm 9.8 \text{ m}^2/\text{g}$  and  
7  $8.8 \pm 0.6 \text{ nm}$ , respectively, and  $65.1 \pm 10.1 \text{ m}^2/\text{g}$  and  $19.9 \pm 2.6 \text{ nm}$  at 473 K. Additionally, we  
8 apply the mesoporous calcium carbonate powder to formaldehyde vapor adsorbent. We  
9 measure the adsorbed amount of gaseous formaldehyde and find that the vaterite-rich  
10 powder has larger adsorption per unit area than the calcite-rich one.

11

12 **Keywords:** Mesoporous calcium carbonate, vaterite, colloid processing, self-assembled  
13 nanostructure, formaldehyde adsorbent

14

15

16

17

18

19

20

21

## 1 **1. Introduction**

2 Calcium carbonate is one of the most abundant minerals and is widely used in industry  
3 as a raw material for cement, paper coating, and medicines, among others. The organization  
4 of its primary building units into hollow and porous superstructures is of considerable  
5 interest due to their promising applications in controllable release and encapsulation of  
6 drugs [Sukhorukov et al. 2004; Wei et al. 2008; Fujiwara et al. 2010], catalyst support  
7 [García-Mota et al. 2011], gas adsorbent [Zhao et al. 2011], as well as biomimetics [Addadi  
8 et al. 2003; Faatz et al. 2004; Xu et al. 2007]. Thus far, there have been two main processes  
9 capable of producing ordered superstructures of calcium carbonate. One is surface  
10 crystallization on templates [Walsh and Mann 1995; Tomioka et al. 2011], and the other is  
11 non-classical crystallization via colloidal intermediates [Cölfen and Mann 2003].  
12 Nevertheless, large-scale production involving porous superstructure formation of calcium  
13 carbonate remains challenging. Organized assemblies or soft templates have been  
14 commonly used for polymorph-controlled synthesis of calcium carbonate crystals [Qi et al.  
15 2002; Yang et al. 2003]. Besides conventional crystallizations, ordered superstructures (i.e.  
16 mesocrystals) can be assembled from nanoscopic building units, in what is known as  
17 “non-classical” crystallization [Jongen et al. 2000; Cölfen and Mann 2003; Wang et al.  
18 2005]. In this case, a soluble additive with well-defined concentration mediates the  
19 mesoscale transformation. These researches have not only offered important contributions  
20 to an understanding of biomineralization, also opened up the promising applications.

21 Various porous materials with huge specific surface areas such as activated carbon  
22 [Rong et al. 2003; Lee et al. 2010; Carter et al. 2011; Wen et al. 2011], silica [Srisuda and  
23 Virote. 2008], and hydroxyapatite [Kawai et al. 2006] have received much attention as

1 highly effective adsorbents for formaldehyde vapor. Formaldehyde, which is one of the  
2 most representative volatile organic compound, is highly toxic to humans. In our previous  
3 work [Yamanaka et al. 2013], we reported effective uses for discarded scallop shells as a  
4 formaldehyde adsorbent. We found that the specific surface area of the shell particles was  
5 positively correlated with the adsorbed amount of formaldehyde vapor.

6 We now demonstrate how mesoporous calcium carbonate powder applies to  
7 formaldehyde vapor adsorbent. We present a scalable production system of mesoporous  
8 calcium carbonate by means of an industrial carbonation process. In this process,  
9 self-assembled nanostructure formation takes place via Brownian aggregation of nanoscale  
10 building units in a colloidal intermediate dispersion. We then investigate the effect of  
11 thermal energy on the self-assembled pore structure and crystal polymorphs.

12

## 13 **2. Experimental procedure**

### 14 *2.1 Materials and synthesis of porous calcium carbonate*

15 Calcium hydroxide was purchased from Nacalai Tesque Inc., and ethylene glycol and  
16 ethanol were purchased from Kanto Chemical Co., Inc. Calcium carbonate was prepared by  
17 carbonation of calcium hydroxide in ethylene glycol–ethanol organic solvent mixture  
18 [Yasue et al. 1985]. Calcium hydroxide (25.0 g) was mixed with the mixture of ethylene  
19 glycol and ethanol (3:7 by weight to yield a total weight of 475.0 g) in the crystallizer.  
20 Calcium hydroxide reacted with CO<sub>2</sub> introduced from the bottom of the crystallizer, in  
21 which the stirring was conducted at the rate of 400 rpm. CO<sub>2</sub> was blended with N<sub>2</sub> at the  
22 concentration of 30 vol%, and the flow rate of CO<sub>2</sub> was 0.3 l/min. The carbonation reaction  
23 temperature was controlled at 293 K using a water bath. After the carbonation, the

1 suspension was centrifuged at 3,500 rpm for 30 min. The transparent supernatant was aged  
2 at a predetermined temperature. The subsequent treatment deals with the unnecessary  
3 organic solvent. The cloudy suspension was washed twice with ethanol to eliminate the  
4 excess ethylene glycol. The suspension was then centrifuged at 3,500 rpm for 20 min. The  
5 supernatant was then discarded, and the residue was dried in vacuum for 12 h. The resulting  
6 dry powder was used in the measurements.

7

## 8 *2.2 Characterization*

9 The specific surface area of the resulting samples was determined by nitrogen gas  
10 adsorption based on the multi-point BET method. Pore size distribution was determined by  
11 the BJH method. Both analyses were conducted on Autosorb-1-c/MK2 (Qantachrome,  
12 USA). In the BET and pore size distribution measurements, the samples were degassed for  
13 2 h at 473 K under a vacuum to remove adsorbed solvent molecules. To determine the  
14 crystal structure, X-ray diffraction (XRD, MultiFlex, Rigaku, Japan) powder patterns of the  
15 samples were obtained with Cu K $\alpha$  radiation (40 kV, 40 mA). SEM studies were performed  
16 using a JEOL JSM-6380A. The TEM image and selected area electron diffractions  
17 (SAEDs) were taken on a JEM-2100F operated at 200 kV after the sample powder was  
18 transferred onto a carbon-coated TEM grid.

19

## 20 *2.3 Formaldehyde adsorption*

21 The amount of adsorbed formaldehyde was measured by the constant volume method  
22 at 293 K, using a home-built vacuum line system. The procedure for the adsorption test is  
23 described in detail elsewhere [Yamanaka et al. 2013]. Briefly, the samples (0.2 g) were

1 precisely weighed in a bag made of non-woven fabric. Samples were placed into a  
2 cross-shaped cell and dried in vacuum overnight. Formaldehyde vapor (1866 Pa of total  
3 pressure) was introduced into the cell connected to the vacuum line. After the total pressure  
4 was reduced to 1600 Pa for adsorbing the vapor, we increased the total pressure to 1866 Pa,  
5 and this sequence was repeated until the system achieved equilibrium. The pressure  
6 difference before and after adsorption was then measured. Mole fraction of formaldehyde  
7 in the vapor phase is not equal that in the liquid phase because formaldehyde is a polar  
8 organic compound. Then, the amount of substance per unit sample **weight** was calculated  
9 from the equation of state for an ideal gas with an added correction factor of 0.27  
10 [Yamanaka et al. 2013], **and the amount of substance per unit sample area was obtained**  
11 **from its specific surface area.**

12

### 13 **3. Results and discussion**

14 In an industrial production system, calcium carbonate is produced on a large scale by  
15 carbonation of calcium hydroxide in water. We believe that our synthesis method is easily  
16 applied to an industrial system because we just switch the solvent from water to the organic  
17 solvent mixture. A schematic description of production of porous calcium carbonates is  
18 given in **Fig. 1**. We prepared a transparent dispersion of calcium carbonate nanoparticles  
19 (Fig. 1a), the starting liquid material for porous calcium carbonate particles, by carbonation  
20 of calcium hydroxide in ethylene glycol–ethanol organic solvent mixture (see section 2.1).  
21 Prepared liquid is a colloidal dispersion because it is transparent but exhibits the Tyndall  
22 effect. The solid fraction of the dispersion was calculated from the weight loss at 773 K  
23 using thermogravimetric-differential thermal analysis (TG-DTA; Seiko Instruments Exstar

1 6200N, 50 ml/min nitrogen flow, 10 K/min ramp). The solid fraction was  $5.5\pm 0.2$  mass%,  
2 with a yield of about 80%. The dispersion was then aged for a predetermined time to  
3 provide a thermal energy that leads to Brownian aggregation of the calcium carbonate  
4 nanoparticles via a gel (Fig. 1b). The organized pore structure of the calcium carbonate  
5 particles was controlled by aging temperature, because the Brownian aggregation rate and  
6 structural phase transition depend on temperature. During the aging process, the time for a  
7 transparent dispersion to become cloudy sol was 1 hour at 353 K, and 2 days at 293 K, for  
8 example.

9 We present first the characterization results for the porous calcium carbonate particles.  
10 The particle properties are summarized in **Table 1**. **The specific surface area and pore size**  
11 **distribution highly differed according to the aging temperature.** The specific surface area  
12 and average pore size for aging temperature of 293 K were  $207.3\pm 9.8$  m<sup>2</sup>/g and  $8.8\pm 0.6$  nm,  
13 respectively, and  $65.1\pm 10.1$  m<sup>2</sup>/g and  $19.9\pm 2.6$  nm at 473 K (**Fig. 2a, e**, and see Table 1).  
14 Figure 1c shows typical SEM images of the porous calcium carbonate particles obtained for  
15 aging temperatures of 293 K and 473 K. At low aging temperature, the particles form  
16 ellipsoidal structure, and dumbbell or rod-like structure at higher temperature. The major  
17 and minor axis size for the ellipsoidal shape of calcium carbonate were  $0.63\pm 0.07$  and  
18  $0.33\pm 0.04$   $\mu$ m, respectively, and  $1.45\pm 0.36$  and  $0.40\pm 0.07$   $\mu$ m for the dumbbell-like shape  
19 (see Table 1).

20 The peak positions of XRD profiles agree with those of the calcite (ICDD#05-0586)  
21 and/or vaterite (ICDD#33-0268) crystal for all samples (the corresponding results of the  
22 XRD profiles are shown in **Fig. 3**). The intensities of the calcite diffraction peaks decrease  
23 with increasing aging temperature, as the vaterite peaks rose up. **The ratio of vaterite to**



1 calcite crystal ( $f_v$ ) calculated from Rao's equation below [Rao 1973].

$$f_v = \frac{I_{100V} + I_{112V} + I_{114V}}{I_{100V} + I_{112V} + I_{114V} + I_{104C}}$$

2  
3  
4  
5 The subscript V and C indicate vaterite and calcite, respectively. The ratio of vaterite ( $f_v$ )  
6 increased with temperature (see Table 1). TEM observation revealed that the ellipsoidal  
7 structure was composed of minute calcite particles (Fig. 2b–d), whereas dumbbell-like  
8 structure had hierarchical vaterite framework (Fig. 2f–h).

9 Generally, three types of crystalline calcium carbonate (calcite, aragonite, and  
10 vaterite) are crystallized from amorphous calcium carbonate (ACC) [Addadi et al. 2003;  
11 Cölfen and Mann 2003; Faatz et al. 2004]. In the carbonation reaction, the initially formed  
12 ACC is immediately transformed into vaterite and calcite [Wei et al. 2003; Han et al. 2005].  
13 Recently, Rodriguez-Blanco et al. reported the kinetics and mechanism of ACC  
14 crystallization and found that the calcite was formed via dissolution of vaterite and  
15 subsequent reprecipitation [Rodriguez-Blanco et al. 2011]. Thus the solubility of calcium  
16 carbonate is crucial for the transformation [Hadiko et al. 2005]. Naka et al. successfully  
17 prepared stable vaterite particles by a delayed addition of polyacrylic acid (PAA) after the  
18 crystallization of calcium carbonate in the aqueous solution [Naka et al. 2006]. They  
19 concluded the vaterite particles were stable in consequence of binding PAA with calcium  
20 ions, which prevented phase transformation into calcite. Additionally, the solubility of  
21 calcium carbonate decreased in the mixture of ethylene glycol and water [Flatena et al.  
22 2010] compared with pure water. Because the carbonation process in this study contains  
23 little water, the dissolution of vaterite, i.e. transformation into calcite should not occur. The

1 above discussion and the observation results indicate that there are two transformation  
2 routes: one is transformation from amorphous to calcite, the other is into vaterite. Figures  
3 1d–f schematically illustrate the effect of aging temperature on the formation of porous  
4 calcium carbonate. As previously mentioned, the primary size of nanoparticles in the  
5 colloidal dispersion aggregated together was associated with the weak repulsive force (Fig.  
6 1d), because electrostatic interactions are negligible in such a relatively low dielectric  
7 constant medium [Israelachvili 1992]. At the same time, phase transition from unstable  
8 amorphous to stable calcite or metastable vaterite was also taking place (Fig. 1e). The  
9 colloidal particles undergo more preferable self-assembly to form ellipsoidal or  
10 dumbbell-shape aggregated structures, resulting from the reduction of the surface free  
11 energy [Guo et al. 2010]. When the system temperature is high, the metastable vaterite  
12 particles are formed, which drives them into forming layered stacking structures (Fig. 1f).  
13 In another one of our experiments, where the aging temperature was set to 293, 313, 333,  
14 353, and 473 K, the vaterite-rich particles increased with the aging temperature as shown in  
15 **Fig. 4a.**

16 In our previous work using scallop shells (calcite) [Yamanaka et al. 2013], we  
17 demonstrated formaldehyde adsorption for nanosized shell particles that were prepared by  
18 planetary ball milling and subsequent water addition. The largest specific surface area for  
19 the ground shell was 54.4 m<sup>2</sup>/g, and the maximum adsorbed amount of formaldehyde vapor  
20 was 1.1 mg/g. This value was a significant improvement in the adsorption amount  
21 compared to the feed shell particles (0.1 mg/g). We then reported that the specific surface  
22 area of the scallop shell particles was positively correlated with the adsorbed amount of  
23 formaldehyde vapor per unit weight of the shell particle.

1 In this work, we have successfully prepared mesoporous calcium carbonate with a  
2 large specific surface area of 207.3 m<sup>2</sup>/g (the ratio of vaterite crystal,  $f_V$ , was 0.11). The  
3 adsorbed amount of formaldehyde per unit weight was 8.2 mg/g, indicating specific surface  
4 area had a large influence on the formaldehyde adsorption, as expected. While using the  
5 vaterite-rich calcium carbonate ( $f_V$  was 0.88, and specific surface area was 65.1±10.1 m<sup>2</sup>/g),  
6 the adsorbed amount was 6.7 mg/g, which was approximately 6 times higher per unit  
7 weight, although its specific surface area was approximately equal to that of above ground  
8 scallop shell particles. We now focus on the adsorbed amount of formaldehyde per unit area  
9 (see section 2.3). As shown in **Fig. 4b**, the adsorbed amount per unit area increased with  
10 increasing ratio of vaterite crystal. The vaterite-rich sample ( $f_V=0.88$ , 0.11 mg/m<sup>2</sup>) had ca. 4  
11 times higher adsorption capacity per unit area than the calcite-rich one ( $f_V=0.11$ , 0.03  
12 mg/m<sup>2</sup>). It should be noted that the vaterite has a structure that enables it to adsorb  
13 formaldehyde easily. We measured FTIR spectra for calcite-rich and vaterite-rich calcium  
14 carbonate before and after formaldehyde adsorption (data not shown). We did not detect  
15 any differences other than the different polymorphs of calcium carbonate. This observation  
16 makes it difficult to explain the contributions of surface structure on the adsorption capacity.  
17 The modeled surface energies of vaterite are in the range 0.62–1.58 J/m<sup>2</sup> for the anhydrous  
18 surface, which is higher than that of calcite (104) surface (0.59 J/m<sup>2</sup>) [de Leeuw and Parker  
19 1998]. The favorable structure for gas adsorption reflects the surface energy and the  
20 thermodynamic stability of the polymorphs. We believe that the porous calcium carbonate  
21 presented here may also be a promising drug carrier material or template, due to its  
22 characteristic superstructure and very high specific surface area.

23

1 **4. Conclusion**

2 We have demonstrated a scalable production method for mesoporous calcium  
3 carbonate of which maximum specific surface area was 207.3 m<sup>2</sup>/g. We have also assessed  
4 its potential use as a formaldehyde vapor adsorbent. The vaterite was an appropriate  
5 polymorph of calcium carbonate in formaldehyde vapor adsorption compared to the calcite.

6  
7 **Acknowledgment**

8 We thank Prof. Jusuke Hidaka at Doshisha University for technical comment and  
9 assistance. This work was supported by a Grant-in-Aid for Young Scientists (B) (No.  
10 24710074) and a Grant-in-Aid for Scientific Research (C) (No. 22560812) of the Japan  
11 Society for the Promotion of Science, by the Cooperative Research Program of Catalysis  
12 Research Center, Hokkaido University, and performed under the Cooperative Research  
13 Program of Institute for Joining and Welding Research Institute, Osaka University.

14

15

16

17

18

19

20

21

22

23

## References

Addadi L, Raz S, Weiner S (2003) Taking advantage of disorder: Amorphous calcium carbonate and its roles in biomineralization. *Adv Mater* 15: 959-970.

Carter EM, Katz LE, Speitel Jr GE, Ramirez D (2011) Gas-phase formaldehyde adsorption isotherm studies on activated carbon: correlations of adsorption capacity to surface functional group density. *Environ Sci Technol* 45: 6498–6503.

Cölfen H, Mann S (2003) Higher-order organization by mesoscale self-assembly and transformation of hybrid nanostructures. *Angew Chem Int Ed* 42: 2350-2365.

de Leeuw NH, Parker SC (1998) Surface structure and morphology of calcium carbonate polymorphs calcite, aragonite, and vaterite: An atomistic approach. *J Phys Chem B* 102: 2914-2922.

Faatz M, Grohn F, Wegner G (2004) Amorphous calcium carbonate: Synthesis and potential intermediate in biomineralization. *Adv Mater* 16: 996-1000.

Flatena EM, Seierstenb M, Andreassen JP (2010) Induction time studies of calcium carbonate in ethylene glycol and water. *Chem Eng Res Des* 88: 1659-1668.

Fujiwara M, Shiokawa K, Araki M, Ashitaka N, Morigaki K, Kubota T, Nakahara Y (2010) Encapsulation of proteins into CaCO<sub>3</sub> by phase transition from vaterite to calcite. *Cryst Growth Des* 10: 4030-4037.

García-Mota M, Gómez-Díaz J, Novell-Leruth G, Vargas-Fuentes C, Bellarosa L, Bridier B, Pérez-Ramírez J, López N (2011) A density functional theory study of the ‘mythic’ Lindlar hydrogenation catalyst. *Theor Chem Acc* 128: 663-673.

Guo XH, Deng YH, Tu B, Zhao DY (2010) Facile synthesis of hierarchically mesoporous silica particles with controllable cavity in their surfaces. *Langmuir* 26: 702-708.

Hadiko G, Han YS, Fuji M, Takahashi M (2005) Synthesis of hollow calcium carbonate particles by the bubble templating method. *Mater Lett* 59: 2519-2522.

Han YS, Hadiko G, Fuji M, Takahashi M (2005) Effect of flow rate and CO<sub>2</sub> content on the phase and morphology of CaCO<sub>3</sub> prepared by bubbling method. *J Crystal Growth* 276: 541-548.

Israelachvili JN (1992) *Intermolecular and surfaces forces*, 2nd edn. Academic Press, London, U.K.

Jongen N, Bowen P, Lemaître J, Valmalette J, Hofmann H (2000) Precipitation of self-organized copper oxalate polycrystalline particles in the presence of hydroxypropylmethylcellulose (HPMC): Control of morphology. *J Colloid Interface Sci* 226: 189-198.

Kawai T, Ohtsuki C, Kamitakahara M, Miyazaki T, Sakaguchi Y, Konagaya S (2006) Removal of formaldehyde by hydroxyapatite layer biomimetically deposited on polyamide film. *Environ Sci Technol* 40: 4281-4285.

Lee KJ, Shiratori N, Lee GH, Miyawaki J, Mochida I, Yoon SH, Jang J (2010) Activated carbon nanofiber produced from electrospun polyacrylonitrile nanofiber as a highly efficient formaldehyde adsorbent. *Carbon* 48: 4248-4255.

Mullin JW (2001) *Crystallization*, 4th edn. Butterworths-Heinemann, Oxford, U.K.

Naka K, Huang SC, Chujo Y (2006) Formation of stable vaterite with poly(acrylic acid) by the delayed addition method. *Langmuir* 22: 7760-7767.

Qi L, Li J, Ma J (2002) Biomimetic morphogenesis of calcium carbonate in mixed solutions of surfactants and double-hydrophilic block copolymers. *Adv Mater* 14: 300-303.

Rao MS (1973) Kinetics and mechanism of the transformation of vaterite to calcite. Bull Chem Soc Jpn 46: 1414-1417.

Rodriguez-Blanco JD, Shaw S, Benning LG (2011) The kinetics and mechanisms of amorphous calcium carbonate (ACC) crystallization to calcite, via vaterite. Nanoscale 3: 265-271.

Rong HQ, Ryu ZY, Zheng JT, Zhang YL (2003) Influence of heat treatment of rayon-based activated carbon fibers on the adsorption of formaldehyde. J Colloid Interface Sci 261: 207-212.

Srisuda S, Virote B (2008) Adsorption of formaldehyde vapor by amine-functionalized mesoporous silica materials. J Environ Sci 20:379–384

Sukhorukov GB, Volodkin DV, Günther AM, Petrov AI, Shenoy DB, Mohwald H (2004) Porous calcium carbonate microparticles as templates for encapsulation of bioactive compounds. J Mater Chem 14: 2073-2081.

Tomioka T, Fuji M, Takahashi M, Takai C, Utsuno M (2011) Hollow structure formation mechanism of calcium carbonate particles synthesized by the CO<sub>2</sub> bubbling method. Cryst Growth Des 12: 771-776.

Walsh D, Mann S (1995) Fabrication of hollow porous shells of calcium carbonate from self-organizing media. Nature 377: 320-323.

Wang T, Cölfen H, Antonietti M (2005) Nonclassical crystallization: Mesocrystals and morphology change of CaCO<sub>3</sub> crystals in the presence of a polyelectrolyte additive. J Am Chem Soc 127: 3246-3247.

Wei H, Shen Q, Zhao Y, Wang DJ, Xu DF (2003) Influence of polyvinylpyrrolidone on the precipitation of calcium carbonate and on the transformation of vaterite to calcite. J Crystal

Growth 250: 516-524.

Wei W, Ma GH, Hu G, Yu D, Mcleish T, Su ZG, Shen ZY (2008), Preparation of hierarchical hollow CaCO<sub>3</sub> particles and the application as anticancer drug carrier. *J Am Chem Soc* 130: 15808-15810.

Wen Q, Li C, Cai Z, Zhang W, Gao H, Chen L, Zeng G, Shu X, Zhao Y (2011) Study on activated carbon derived from sewage sludge for adsorption of gaseous formaldehyde. *Bioresour Technol* 102: 942-947.

Xu AW, Ma Y, Cölfen H (2007) Biomimetic mineralization. *J Mater Chem* 17: 415-449.

Yamanaka S, Suzuma T, Fujimoto T, Kuga Y (2013) Production of scallop shell nanoparticles by mechanical grinding as a formaldehyde adsorbent. *J Nanoparticle Res* 15, 1573.1-8.

Yang D, Qi L, Ma J (2003) Well-defined star-shaped calcite crystals formed in agarose gels. *Chem Commun* 21: 1180-1181.

Yasue T, Mamiya A, Fukushima T, Arai Y (1985) Synthesis and characteristics of amorphous calcium carbonate in ethanol. *Gypsum & Lime* 198: 245-252.

Zhao Z, Zhang L, Dai H, Du Y, Meng X, Zhang R, Liu Y, Deng J (2011) Surfactant-assisted solvo- or hydrothermal fabrication and characterization of high-surface-area. Microporous Mesoporous Mater 138: 191-199.



## Figure captions

**Fig. 1** (a) Starting liquid material for porous calcium carbonate particles. (b) After the dispersion was aged for a predetermined amount of time, it became cloudy via a gelling state. (c) Typical SEM images of the porous calcium carbonate particles obtained by aging at 293 K and 473 K. The scale bar is 1  $\mu\text{m}$ . (d, e, and f) Schematic illustration of the effect of aging temperature on the formation process of porous calcium carbonate. (d) Primary size of nanoparticles in the colloidal dispersion. (e) Primary particles are aggregated together due to the weak repulsive force; while phase transition from unstable amorphous to stable calcite or metastable vaterite occurs. (f) Finally, the colloidal particles undergo a more preferable self-assembly to form ellipsoidal or dumbbell-shape aggregated structures.


**Fig. 2** Some features of the samples obtained by aging at 293 K (a–d), and 473 K (e–h). (a) BJH pore size distributions measured from nitrogen isotherm plots, (b) TEM image, (c) magnified image, and (d) SAED patterns obtained by electron diffraction study. (e) BJH pore size distributions, (f) TEM image, (g) magnified image, and (h) SAED patterns of the particle.

**Fig. 3** Typical XRD patterns of the prepared particles. The upper one is a sample obtained at 473 K, and the lower one at 293 K aging temperature. The crystallite size was 15 nm for (104) calcite, and 14 nm for (112) vaterite. The values almost coincide with the primary particle size from each TEM image (see Fig. 2c and g). The crystallite size was calculated from the full width at half maximum (FWHM) of the corrected diffraction profile. A Pseudo-Voigt fitting was conducted to obtain the FWHM for the (104) calcite and (112)

vaterite diffraction.

**Fig. 4** (a) The effect of the aging temperature on the crystal structure of porous calcium carbonate. The ratio of vaterite crystal was calculated from Rao's equation [Rao 1973]. (b) Relation between the ratio of vaterite phase and adsorbed amount of formaldehyde per unit area for formaldehyde concentration of  $1560 \text{ mg/m}^3$ .

**Fig. 1**

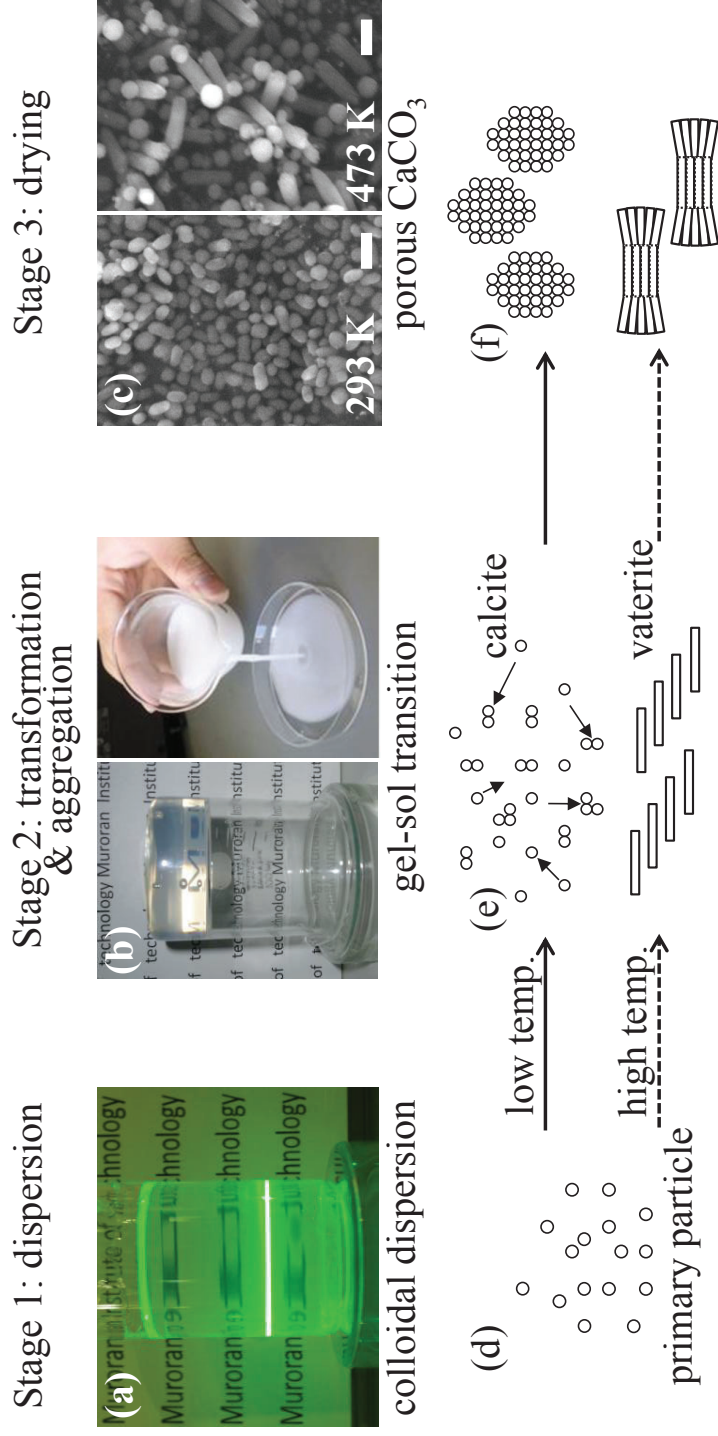

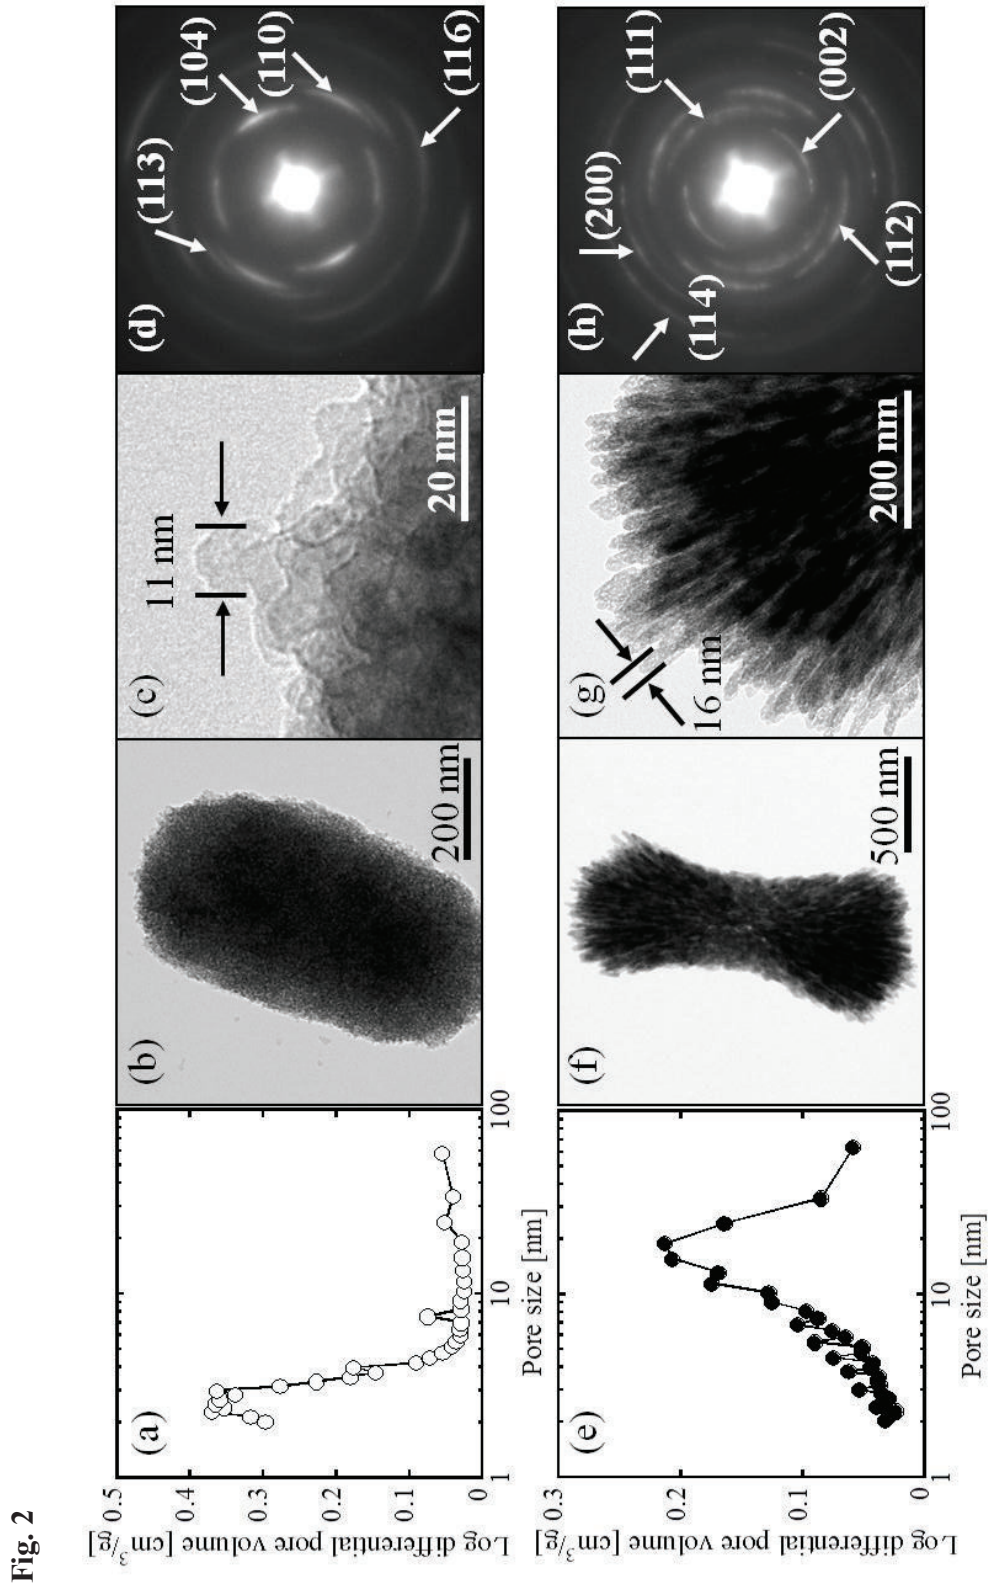


Fig. 2

Fig. 3


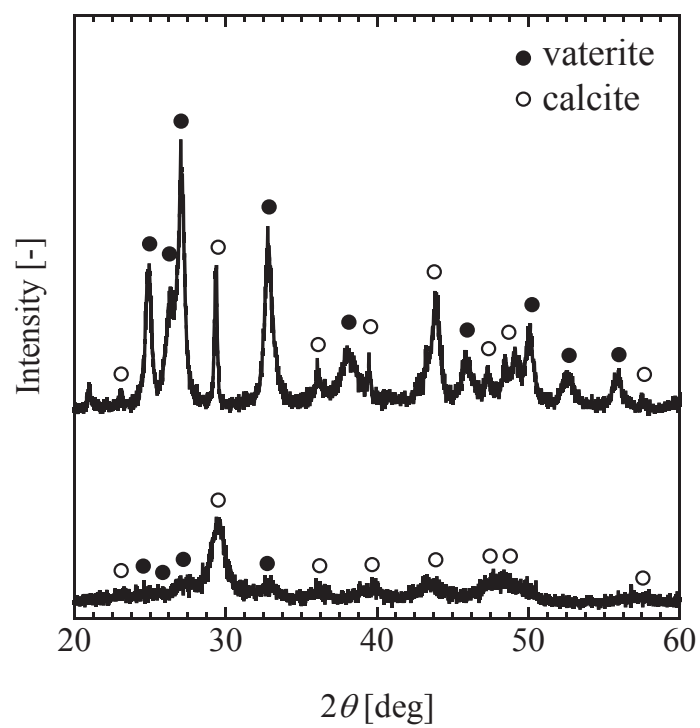


Fig. 4

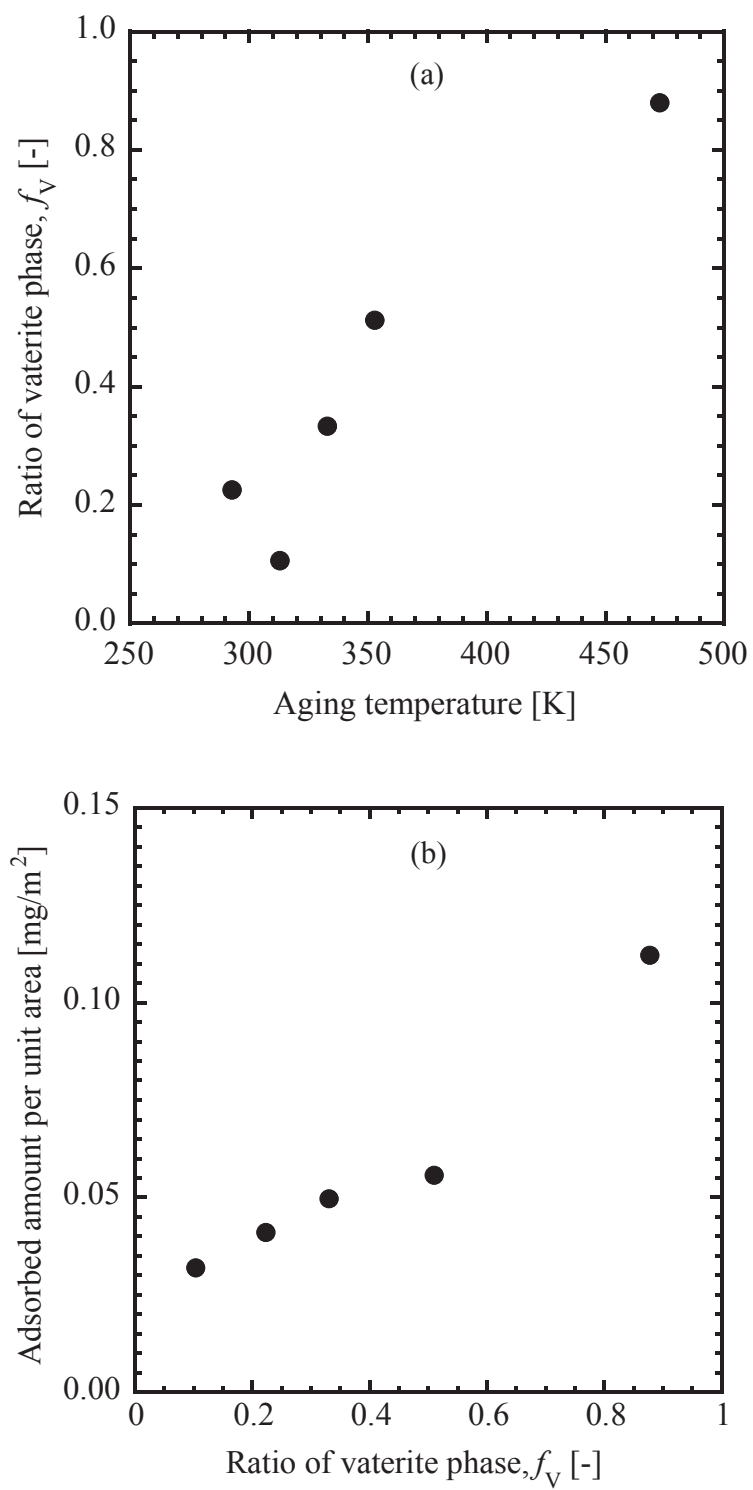

*Table*

**Table 1** Characterization results of porous calcium carbonate

Aging temperature [K]	$f_V^1$ [-]	Particle size <sup>2</sup> [ $\mu\text{m}$ ]	BET specific surface area [ $\text{m}^2/\text{g}$ ]	Total pore volume [ $\text{cm}^3/\text{g}$ ]	Mean pore size [nm]
293	0.22	major axis: $0.63 \pm 0.07$ minor axis: $0.33 \pm 0.04$	$207.3 \pm 9.8$	$0.454 \pm 0.034$	$8.8 \pm 0.6$
473	0.88	major axis: $1.45 \pm 0.36$ minor axis: $0.40 \pm 0.07$	$65.1 \pm 10.1$	$0.317 \pm 0.020$	$19.9 \pm 2.6$

<sup>1</sup> $f_V$  denotes the ratio of vaterite to calcite calculated from XRD intensity.

<sup>2</sup>Measured 100 particles from each SEM image.