



UNIVERSITÀ  
DEGLI STUDI  
DI PADOVA

*Università degli Studi di Padova*

*Padua Research Archive - Institutional Repository*

Photoswitchable catalysis by a nanozyme mediated by a lightsensitive cofactor

*Original Citation:*

*Availability:*

This version is available at: 11577/3227841 since: 2017-05-16T08:57:47Z

*Publisher:*

American Chemical Society

*Published version:*

DOI: 10.1021/jacs.6b12932

*Terms of use:*

Open Access

This article is made available under terms and conditions applicable to Open Access Guidelines, as described at <http://www.unipd.it/download/file/fid/55401> (Italian only)

(Article begins on next page)

# Photoswitchable catalysis by a nanozyme mediated by a light-sensitive cofactor

Simona Neri, Sergio Garcia Martin, Cristian Pezzato,<sup>†</sup> Leonard J. Prins<sup>\*</sup>

Department of Chemical Sciences, University of Padova, Padova, Italy


Supporting Information Available

## ABSTRACT:

The activity of a gold nanoparticle-based catalyst can be reversibly up- and down-regulated by light. Light is used to switch a small molecule between *cis*- and *trans*-isomers, which **inhibit** the catalytic activity of the nanoparticles to different  **extents**. The system is functional in aqueous buffer, which paves the way for integrating the system in biological networks.


The visual phototransduction process is a beautiful example of the functional power of complex chemical networks.<sup>1</sup> The process is initiated by the photon-triggered *cis-trans* isomerization of the co-factor retinal, which activates a cascade of catalytic events eventually leading to an electrical output signal for processing by the nervous system. In the quest towards responsive synthetic chemical systems of increasing complexity the availability of catalysts that can be regulated using an external trigger is an essential prerequisite.<sup>2,3</sup> The use of light is particularly attractive because it can be delivered very efficiently and with high temporal and spatial precision.<sup>4</sup> Although most attention has been focused on molecular catalysts equipped with light-sensitive molecular switches,<sup>5-10</sup> there is an increasing number of examples of catalytic systems of higher complexity that can be regulated with light.<sup>11,12</sup> In particular, nanoparticles functionalized with azobenzene-moieties have turned out to be very effective, which is mainly caused by the possibility to install innovative regulatory mechanism (*e.g.* light-induced aggregation-dissociation) that **are** hard to achieve with molecular catalysts.<sup>13-15</sup> It has been shown recently that nanoparticle aggregation can also be controlled using an external light-sensitive molecule, which liberates a proton upon light-induced isomerization and in that way affects the aggregation state of the nanoparticles.<sup>16,17</sup> Here, we apply a different strategy to control the activity of catalytic nanoparticles relying on the use of a small light-sensitive co-factor which inhibits catalytic activity because it competes with the substrate for binding to the catalytic monolayer (Figure 1). This mechanism, together with the fact that the system functions in water, makes for a close analogy with the visual phototransduction process and opens the way to light-regulated hybrid networks composed of nanoparticles and enzymes.

Au NP **1** are gold nanoparticles ( $d = 1.6 \pm 0.4$  nm) passivated with a monolayer of C<sub>9</sub>-thiols **terminating** with a 1,4,7-triazacyclononane (TACN):Zn<sup>2+</sup> head group (Figure 1).<sup>18</sup> Previously, we have shown that Au NP **1** and analogues catalyze very efficiently the transphosphorylation of 2-hydroxypropyl-4-nitrophenylphosphate (HPNPP), which is a model substrate for

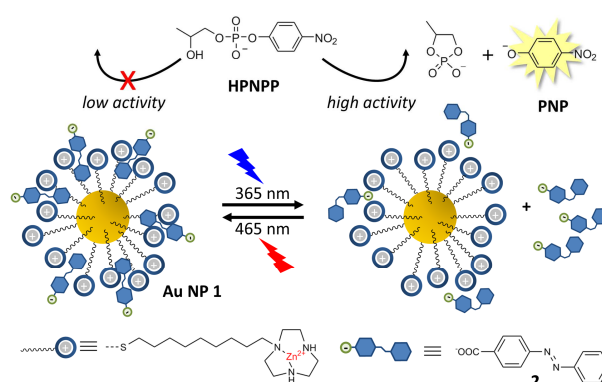

**Figure 1.** Light-induced *cis-trans* isomerization of **2** changes its affinity for Au NP **1**, which affects the transphosphorylation rate of HPNPP.

RNA-hydrolysis.<sup>19,20</sup> The system has been referred to as a nanozyme, because of its many analogies to enzymes: cooperativity between TACN·Zn<sup>2+</sup>-complexes, Michaelis-Menten reaction kinetics, and down-regulation of catalysis by inhibitors that compete with the substrate for binding to Au NP **1**.<sup>21-24</sup> In particular, this latter aspect stimulated us to exploit the reversible interaction between a competitor and Au NP **1** as a tool to regulate catalytic activity in a similar way **as** what happens in the visual phototransduction process. This would require the use of a small light-sensitive molecule that would change the affinity for Au NP **1** upon photoisomerization. Our attention was drawn to commercially available 4-(phenylazo)benzoic acid (**2**), because it combines a photoresponsive azobenzene and a carboxylic acid group, which is negatively charged at pH 7.0. UV-vis spectroscopy confirmed that also in the presence of Au NP **1** ([TACN·Zn<sup>2+</sup>] = 20 μM, [HEPES] = 10 mM, pH = 7.0) **2** can be reversibly switched between two photostationary states (*trans:cis* = 35:65 after λ = 365 nm for 50 minutes, *trans:cis* = 77:23 after λ = 465 nm for 10 minutes) (Supporting Information). Throughout the manuscript, *cis-2* and *trans-2* refer to the photostationary states enriched in *cis-2* (65%) and *trans-2* (77%), respectively. Next, the relative affinities of both *cis*- and *trans-2* for Au NP **1** were determined by means of a competition experiment with the fluorescent probe 6,8-dihydroxy-1,3-pyrenedisulfonic acid (**3**) (Figure 2a). In these experiments, *cis-2* and *trans-2* were titrated separately to a buffered aqueous solution of Au NP **1** ([TACN·Zn<sup>2+</sup>] = 20 μM) and **3** (8 μM). At this concentration nearly all **3** was bound to Au NP **1** resulting in a nearly complete quenching of its fluorescence by the gold core.<sup>25</sup> The addition of increasing amounts of **2** resulted in the displacement of **3** from the monolayer surface which could be

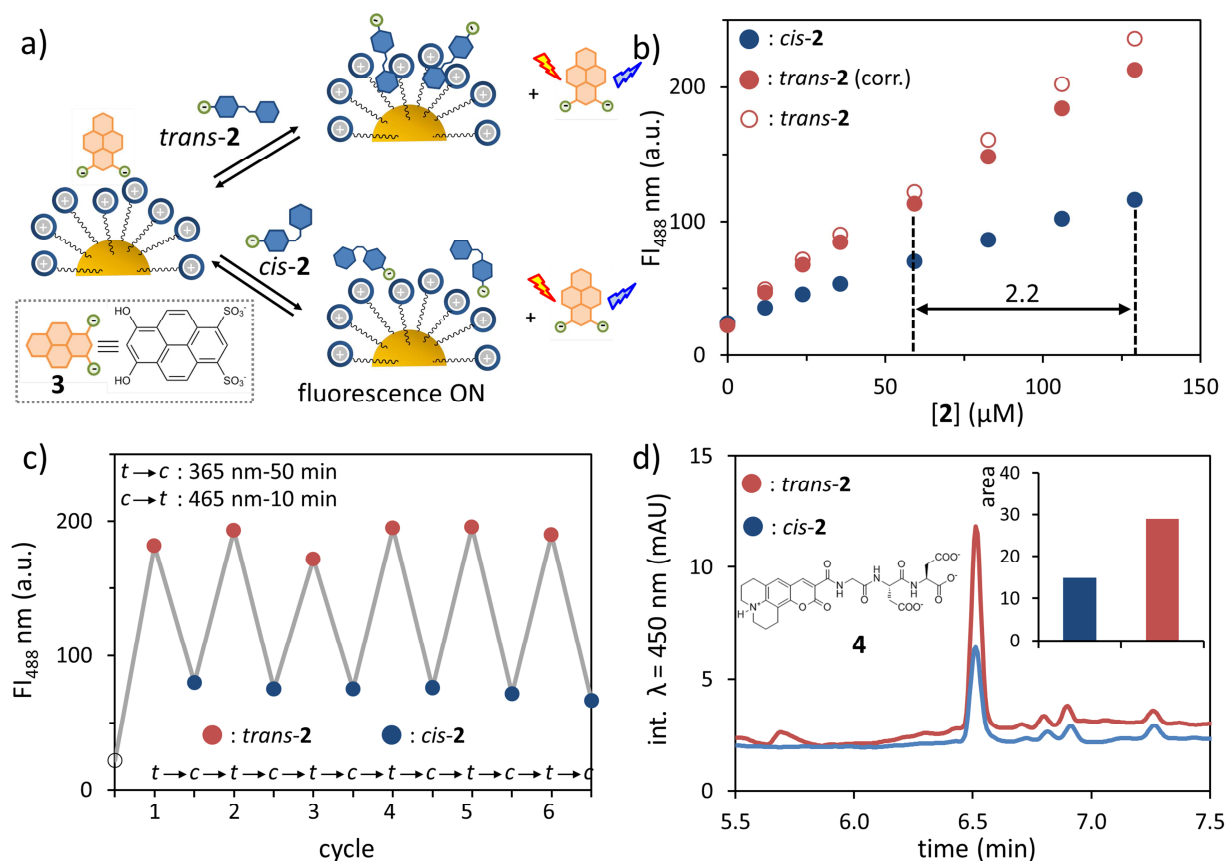


**Figure 2.** a) Schematic representation of the competition experiments between fluorophore **3** and *cis*- and *trans*-**2** for binding to Au NP **1**. b) Increase in fluorescence intensity as a function of the concentration of **2**. To permit comparison, the fluorescence intensity of *trans*-**2** was corrected for the intrinsic difference in fluorescence intensity of **3** in the presence of *trans*- and *cis*-**2**. c) Fluorescence intensity after repetitive irradiations (365 nm for 50 minutes, 465 nm for 10 minutes) of a solution containing Au NP **1**, **2** and **3**. The intensity is corrected for bleaching of probe **3** (see Supporting Information). d) Peak area of probe **4** (see Supporting Information) in the chromatograms of the dialysate after ultrafiltration of a solution containing Au NP **1**, probe **4**, and either *trans*- and *cis*-**2**. All experimental conditions are given in the Supporting Information.

detected by an increase in fluorescence intensity. The resulting displacement curves clearly showed that *trans*-**2** has a higher affinity (~2.2 times) for Au NP **1** compared to *cis*-**2**, which is a fundamental prerequisite for the use of **2** as a photoresponsive cofactor (Figure 2b).<sup>26</sup> The lower affinity of *cis*-**2** is ascribed to the increase in polarity of azobenzene upon *trans-cis* isomerization, which reduces favorable hydrophobic interactions with the apolar part of the monolayer.<sup>13,27</sup> Importantly, the complete reversibility of the interaction was demonstrated by measuring the fluorescence intensity after repetitive *trans-cis* and *cis-trans* isomerizations (Figure 2c). It is noted that the quantitative interpretation of these measurements required a correction for the photobleaching of probe **3** upon irradiation at 465 nm (Supporting Information). Additional direct evidence that the *cis*- and *trans*-isomers of **2** displace a surface-bound molecule to a different extent was obtained from ultrafiltration experiments followed by LC-MS measurements.<sup>28</sup> In these experiments equal amounts of either *cis*- or *trans*-**2** (100 μM) were added to a solution of Au NP **1** saturated with probe **4** (4.8 μM, Figure 2d) after which ultrafiltration using a 10 kDa MW cutoff PES-membrane was used to separate free from surface-bound molecules. LC-MS measurements of the filtrate showed a 2 times higher concentration of **4** in the sample to which *trans*-**2** was added compared to the *cis*-**2** sample, which is in agreement with the data obtained from fluorescence measurements (inset of Figure 2d).

At this stage we also verified through a series of analysis that Au NP **1** was not subject to structural alterations as a result of extensive irradiation. <sup>1</sup>H NMR and Cu<sup>2+</sup>-titrations confirmed that 5 irradiation cycles did not affect the structural and functional properties of the organic monolayer, whereas TEM, DLS and UV-vis measurements confirmed the integrity of the inorganic core (Supporting Information).

We then proceeded with a study of the inhibitory effect of the *cis*- and *trans*-isomers of **2** on the catalytic activity of Au NP **1** in the transphosphorylation of HPNPP (Figure 1). The reaction can be conveniently followed by UV-vis spectroscopy by measuring the increase in absorbance at 390 nm (which corresponds to the isosbestic point of *cis*- and *trans*-**2**) originating from the liberated *p*-nitrophenolate anion. It is noted that the Au nanoparticle metal component itself is not involved in the reaction. During the course of numerous studies using Au NP **1** or analogues, the reduction of *p*-nitrophenol to *p*-nitroaniline, which is known to be catalyzed by Au metal nanoparticles,<sup>29</sup> has never been observed.<sup>19,20</sup> Inhibition studies were performed by measuring the initial reaction rate at different concentrations of either *cis*- or *trans*-**2**. Comparison of the inhibition curves showed an enhanced inhibitory capacity of *trans*-**2** compared to *cis*-**2**, which is in line with the results of the displacement experiments (Figure 3a).

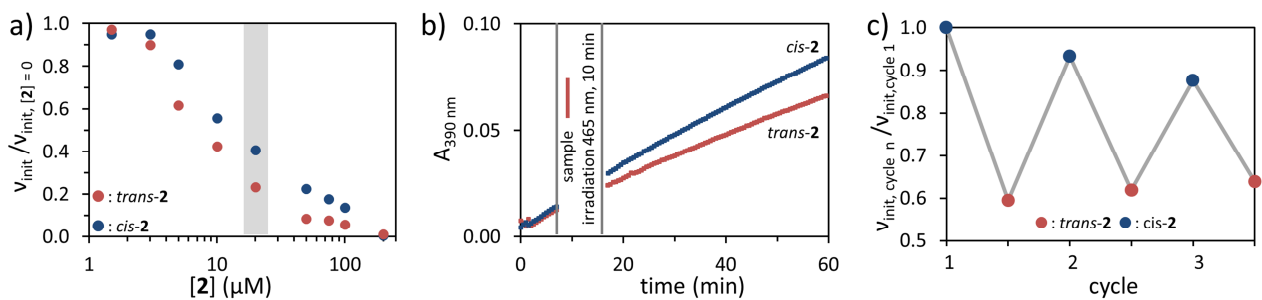

**Figure 3.** a) Plot of the initial rate (normalized on the rate for  $[2] = 0 \mu\text{M}$ ) of the transphosphorylation of HPNPP as a function of the concentrations of *cis*- and *trans*-2. b) Increase in absorbance as a function of time for samples that were (blue) and were not (red) irradiated at 465 nm for 10 minutes after 7 minutes of reaction. c) Plot of the initial rates (normalized on the initial rate of the first kinetics) for several irradiation cycles. Protocols and experimental conditions are given in the Supporting Information.

In particular between 5 and 20  $\mu\text{M}$  of **2** a significant difference was observed. From within this range, a 20  $\mu\text{M}$  concentration of **2** was chosen, because the lower reaction rates at higher inhibitor concentrations would increase the available time frame for detecting changes in activity upon irradiation. In an initial experiment we followed the course of the reaction after adding HPNPP to a buffered solution containing Au NP **1** and *cis*-2. After 7 minutes, the cuvette was irradiated for 10 minutes at 465 nm after which the measurement was continued together with a sample that was non irradiated. Whereas prior to irradiation both rates were obviously the same, after irradiation a clear difference was observed with a lower activity for the irradiated sample. This indicated that the *cis*-*trans* isomerization of **2** resulted in a down-regulation of Au NP **1** (Figure 3b). Objectively, the observed difference in rate is not large, but it is in line with what can be expected based on the relative affinities of *cis*- and *trans*-2 for Au NP **1**. It is worth reminding that **2** itself has a relatively low affinity for Au NP **1** and, also importantly, that the photostationary states are not very well resolved. The fact that the system is any way able to respond to the isomerization of **2** illustrates the sensitivity of this approach to regulate the catalytic activity of Au NP **1** with light. The same experiment performed in the absence of the inhibitor **2** obviously resulted in higher rates, but, importantly, irradiation of the sample had in this case no effect on the reaction rate (Supporting Information). Yet, although promising, this procedure proved not very suitable for multiple up- and down-regulation cycles. This was mainly caused by the accumulation of the cleavage product *p*-nitrophenolate in the system, which strongly absorbs in the same region as azobenzene **2**. As a result, we observed a strong reduction in the switching efficiency of **2** as the reaction proceeded. For this reason, we performed the experiments in a different way by adding the substrate HPNPP each time after isomerization of **2**. Thus, a large stock solution of Au NP **1** (20  $\mu\text{M}$ ) and **2** (20  $\mu\text{M}$ ) in HEPES (10 mM, pH = 7.0) was prepared and subjected to irradiation cycles to induce isomerization. After each irradiation a sample was transferred to a cuvette, HPNPP (100  $\mu\text{M}$ ) was added and the increase in absorbance at 390 nm was measured. This had also a second advantage that the initial rates could be quantitatively compared between different cycles. In total, 3 cycles were performed and the relative initial rates clearly demonstrated that the catalytic activity of the system can be reversibly up- and down-regulated using light (Figure 3c). Isomerization to the *trans*-isomer in all cases resulted in an (expected) decrease in activity, which was restored upon isomerization to the *cis*-isomer. In the absence of **2** reversible up- and down-regulation was never observed (Supporting Information). The slight decrease in performance over multiple cycles is a side effect originating from a degradation of the HEPES-buffer upon irradiation (Supporting Infor-

mation).<sup>30,31</sup> With that respect, we want to stress that this is one of the few examples of a light-modulated Au NP system that is functional in aqueous buffer<sup>17</sup> and thus marks a significant step forward towards the integration of such systems in biological networks.

In conclusion, we have shown that a small light-sensitive molecule can act as a co-factor to reversibly regulate the catalytic activity of a nanosystem. Similar to what happens in the visual phototransduction process, light irradiation causes a structural change in the cofactor which affects the affinity for the catalytic site. Evidently, the efficiency of the presented system is still less compared to natural systems and also compared to previously reported nanoparticle-based catalysts that operate in organic solvents. However, the fact that the light-sensitive molecule interacts with the nanoparticle through noncovalent interactions in water represents a significant step forward. The use of small, easily accessible molecule significantly facilitates optimization compared to related systems in the literature in which the light-sensitive unit is covalently attached to the monolayer. In addition, we have shown that light can be used to displace surface bound molecules, which is of interest for the development of innovative delivery systems and materials.

## ASSOCIATED CONTENT

### Supporting Information

Materials and instrumentation, experimental protocols, control experiments as mentioned in the manuscript. The Supporting Information is available free of charge on the ACS Publications website.

## AUTHOR INFORMATION

### Corresponding Author

leonard.prins@unipd.it

### Notes

The authors declare no competing financial interests.

### Present Address

† Department of Chemistry, Northwestern University, 2145 Sheridan Road, Evanston, Illinois 60208-3113, USA

## ACKNOWLEDGMENT

Financial support from Marie Curie ITN READ (289723) and COST Action CM1304 is acknowledged.

## REFERENCES

- (1) Ebrey, T.; Koutalos, Y., *Prog. Retin. Eye Res.* **2001**, *20*, 49-94.
- (2) Blanco, V.; Leigh, D.A.; Marco, V. *Chem. Soc.Rev.* **2015**, *44*, 5341-5370.
- (3) a) Wiester, M. J.; Ulmann, P. A.; Mirkin, C. A., *Angew. Chem. Int. Ed.* **2011**, *50*, 114-137. b) Raynal, M.; Ballester, P.; Vidal-Ferran, A.; van Leeuwen, P., *Chem. Soc. Rev.* **2014**, *43*, 1734-1787.
- (4) Stoll, R. S.; Hecht, S., *Angew. Chem. Int. Ed.* **2010**, *49*, 5054-5075.
- (5) Ueno, A.; Takahashi, K.; Osa, T., *J. Chem. Soc., Chem. Commun.* **1980**, 837-838.
- (6) Wurthner, F.; Rebek, J., *Angew. Chem. Int. Ed.* **1995**, *34*, 446-448.
- (7) Sugimoto, H.; Kimura, T.; Inoue, S., *J. Am. Chem. Soc.* **1999**, *121*, 2325-2326.
- (8) Sud, D.; Norsten, T. B.; Branda, N. R., *Angew. Chem. Int. Ed.* **2005**, *44*, 2019-2021.
- (9) Peters, M. V.; Stoll, R. S.; Kuhn, A.; Hecht, S., *Angew. Chem. Int. Ed.* **2008**, *47*, 5968-5972.
- (10) Stoll, R. S.; Peters, M. V.; Kuhn, A.; Heiles, S.; Goddard, R.; Buhl, M.; Thiele, C. M.; Hecht, S., *J. Am. Chem. Soc.* **2009**, *131*, 357-367.
- (11) Niazov, T.; Shlyahovsky, B.; Willner, I., *J. Am. Chem. Soc.* **2007**, *129*, 6374-6375.
- (12) Klajn, R.; Stoddart, J. F.; Grzybowski, B. A., *Chem. Soc. Rev.* **2010**, *39*, 2203-2237.
- (13) Klajn, R.; Bishop, K. J. M.; Grzybowski, B. A., *Proc. Natl. Acad. Sci.* **2007**, *104*, 10305-10309.
- (14) Wei, Y. H.; Han, S. B.; Kim, J.; Soh, S. L.; Grzybowski, B. A., *J. Am. Chem. Soc.* **2010**, *132*, 11018-11020.
- (15) Zhao, H.; Sen, S.; Udayabhaskararao, T.; Sawczyk, M.; Kucanda, K.; Manna, D.; Kundu, P. K.; Lee, J. W.; Kral, P.; Klajn, R., *Nat. Nanotechnol.* **2016**, *11*, 82-88.
- (16) Kundu, P. K.; Samanta, D.; Leizrowice, R.; Margulis, B.; Zhao, H.; Borner, M.; Udayabhaskararao, T.; Manna, D.; Klajn, R., *Nat. Chem.* **2015**, *7*, 646-652.
- (17) Samanta, D.; Klajn, R., *Adv. Opt. Mater.* **2016**, *4*, 1373-1377.
- (18) Pieters, G.; Cazzolaro, A.; Bonomi, R.; Prins, L. J., *Chem. Commun.* **2012**, *48*, 1916-1918.
- (19) Manea, F.; Houillon, F. B.; Pasquato, L.; Scrimin, P., *Angew. Chem. Int. Ed.* **2004**, *43*, 6165-6169.
- (20) Zaupa, G.; Mora, C.; Bonomi, R.; Prins, L. J.; Scrimin, P., *Chem. Eur. J.* **2011**, *17*, 4879-4889.
- (21) Prins, L. J., *Acc. Chem. Res.* **2015**, *48*, 1920-1928.
- (22) Wei, H.; Wang, E. K., *Chem. Soc. Rev.* **2013**, *42*, 6060-6093.
- (23) Wang, X.; Guo, W.; Hu, Y.; Wu, J.; Wei, H. Nanozymes: Next Wave of Artificial Enzymes. **2016**, Springer-Verlag GmbH Berlin Heidelberg.
- (24) Lin, Y. H.; Ren, J. S.; Qu, X. G., *Acc. Chem. Res.* **2014**, *47*, 1097-1105.
- (25) Sapsford, K. E.; Berti, L.; Medintz, I. L., *Angew. Chem. Int. Ed.* **2006**, *45*, 4562-4588.
- (26) The difference in affinity is reflected by the 2.2-fold higher concentration of *cis-2* (compared to *trans-2*) required to displace the same amount of **3**.
- (27) Pieters, G.; Pezzato, C.; Prins, L. J., *Langmuir* **2013**, *29*, 7180-7185.
- (28) Maiti, S.; Pezzato, C.; Martin, S. G.; Prins, L. J., *J. Am. Chem. Soc.* **2014**, *136*, 11288-11291.
- (29) Haratu, M., *Cattech*, **2002**, *6*, 102-115.
- (30) Zigler, J. S.; Lepezuniga, J. L.; Vistica, B.; Gery, I., *In Vitro Cell. Dev. Biol.* **1985**, *21*, 282-287.
- (31) Regrettably, the catalytic activity of Au NP **1** is completely inhibited by phosphate buffers such as PBS.

---

Authors are required to submit a graphic entry for the Table of Contents (TOC) that, in conjunction with the manuscript title, should give the reader a representative idea of one of the following: A key structure, reaction, equation, concept, or theorem, etc., that is discussed in the manuscript. Consult the journal's Instructions for Authors for TOC graphic specifications.

Insert Table of Contents artwork here

