

Fibers and Polymers

July 2017, Volume 18, Issue 7, pp 1255–1262

<https://doi.org/10.1007/s12221-017-6862-z>

<https://link.springer.com/article/10.1007/s12221-017-6862-z>

Characterization of the surface properties of cellulosic fibres in fibrous and ground forms by IGC and contact angle measurements

Erika Fekete^{1,2*} and Emília Csiszár²

¹Institute of Materials and Environmental Chemistry, Research Centre for Natural Sciences, Hungarian Academy of Sciences, H-1525 Budapest, P.O. Box 17, Hungary
e-mail: ebodine@mail.bme.hu

²Department of Physical Chemistry and Materials Science, Budapest University of Technology and Economics, H-1521 Budapest, P.O. Box 91, Hungary;
e-mail: ecsiszar@mail.bme.hu

*Corresponding author: Phone: +36-1-463-4335, Fax: +36-1-463-3474, address: Department of Physical Chemistry and Materials Science, Budapest University of Technology and Economics, H-1521 Budapest, P.O. Box 91, Hungary, [Email: ebodine@mail.bme.hu](mailto:ebodine@mail.bme.hu)

ABSTRACT

Surface properties of fibrous and ground cotton and linen were investigated by inverse gas chromatography (IGC) and the contact angle with different liquids was also measured on fabrics of both fibres. Results proved that dispersion component of surface tension (γ_s^d) determined by IGC depends not only on the surface energy, but also on several factors influencing the adsorbability of probe molecules on the cellulosic substrates. For cotton samples, the trapping of n-alkanes among waxy molecules in the outer layer of fibres can be presumed. This effect results in larger γ_s^d for cotton fibres than for linen in spite of the higher wettability of the linen fabrics. Besides the surface energy and trapping effects, the grinding also influences the γ_s^d values. Specific enthalpy of adsorption (ΔH_A^{ab}) of polar probes could be determined on all linen samples, but only on the ground cotton sample. Lewis acid-base character calculated for linen and ground cotton samples depends on the same effects as the γ_s^d does. The similar ΔH_A^{ab} values of chloroform (acidic) and THF (basic) measured on each of the samples support the conclusion that the surface character is amphoteric, which is also proved by the high ΔH_A^{ab} values of the amphoteric ethyl acetate and acetone probes.

Keywords:

- Inverse gas chromatography
- Dispersion component of surface tension
- Cotton
- Linen
- Contact angle measurement

1. INTRODUCTION

Cellulose based materials such as wood, cotton, linen and hemp have been used for thousands of years in the field of forest products, paper, textiles, etc. Recently, they are widely used for cellulose-reinforced composites with synthetic or biopolymer matrices, because they are biodegradable with low environmental and human health risks [1]. Since their application has broadened continuously, characterization of the surface properties is becoming increasingly important. In the last decades, inverse gas chromatography (IGC) especially at infinite dilution is considered to be a versatile, powerful, sensitive and relatively fast technique for characterization of the physicochemical properties of solid materials. Several papers have been published on surface properties of cellulosic materials and the information collected in this field is increasing significantly [2-19].

Notwithstanding that a series of papers appeared addressing the determination of dispersion component of surface tension and acid-base parameters by IGC, difficulties still exist, since calculation techniques applied for example in determination of the acid-base parameters are not always unambiguous, and sometimes the authors do not define even the units of the reported acid-base parameters. Furthermore, chemical composition, crystallinity and surface morphology of the cellulose based materials are other factors that influence the reported IGC results [2, 16]. Therefore it is not surprising that somewhat different results for similar materials can be found in the scientific literature.

Recently, we have investigated differently pretreated cotton and linen samples in order to determine and compare the surface energy and acid-base character of the fibres. In the first experiment, fibres from alkaline and enzyme treated cotton fabrics were tested by IGC [20]. The applied treatments i.e. alkaline scouring and bioscouring (i.e. pectinase treatment) are widely used for removing almost totally or partially, respectively, the waxy materials from the outer layer of

the cotton fibres. Although the measured dispersion component of surface tension (γ_s^d) was in a good agreement with the experimental results of other measurements and revealed that the alkaline treated cotton is more hydrophilic than the enzyme treated, surprisingly, the difference in γ_s^d as a result of the applied treatments was small (3-4 mJ/m²). In the light of the fact that the difference in presumable surface energy between the cellulose and the waxy coverage is significant, we expected much higher difference for the alkaline treated and enzyme treated cotton samples. Furthermore, the polar probes were not retained at all on the raw (untreated) cotton, and only a low retention and exclusively at low temperatures could be detected for the treated samples that revealed a basic character.

Assuming that the reason of the weak polar probe retention is the small accessible internal surface of the samples, in the second experiment the IGC measurements was carried out on ground cotton and the study was extended to fibrous and ground linen as well. In spite of the results obtained from numerous classical analytical and high performance methods proved that the new surfaces created by grinding were rich in oxygen, lower values of the dispersion component of surface tension were measured for the ground cotton and linen samples than for the fibres. Furthermore, higher γ_s^d were calculated for cotton than for linen [21]. Based on the X-ray diffraction analysis of fibres and their ground powders it was assumed that the reason of unreal surface energies can be the less effective adsorption of probes on the less perfect crystalline surface of ground samples. Results of the next comprehensive study on ground flax of different size confirmed our statement that the multicellular and multicomponent flax is very susceptible to grinding and undergoes complex chemical and physical changes [22]. All the applied methods revealed differences in properties of the fibrous and ground flax, and the results showed that dispersion components of surface tensions measured by IGC depends on several parameters (not only on surface energy) which influence the adsorption of probe molecules on the surface of

investigated samples. The grinding has also been reported to affect the surface properties assessed by IGC of other materials [23].

In the light of the results and observations discussed above, an important question is still open: why was so high γ_s^d measured for the raw cotton by IGC? In this paper we report the results on an investigation of this question using cotton and linen in fibrous and ground forms and characterizing the dispersion components of surface tensions and acid-base character by IGC. Additionally, results from contact angle measurements on the fabrics of both fibres also contribute to answer the question.

2. MATERIALS AND METHODS

2.1. Materials

Raw cotton and linen fibres in fibrous and ground form were used for the IGC test. The fibres were obtained from the respective raw fabrics (cotton: 155 g/m², plain weave; linen: 250 g/m², plain weave) kindly provided by Pannon-Flax Linen Weaving Co. Győr, Hungary. The fibres were cut into lengths of 1-3 mm and ground in a Mixer Mill MM400 (Retsch GmbH, Germany) at a frequency of 30 1/s, for 2.5 min. The ground fraction studied in this work was composed of particles with diameters enclosed between 200 and 315 µm, collected by sieving. Swatches of raw fabrics were used in contact angle measurement. The analytical grade chemicals for contact angle measurement and the chromatography grade probes used for IGC were purchased from Sigma-Aldrich Chemicals. The parameters of solvents used as probes in IGC are listed in Table 1.

Table 1.

2.2. Inverse Gas Chromatography

The fibrous and ground cellulosic fibres (approximately 1.5 g) were packed into a stainless steel column having an inner diameter of 5 mm and a length of 50 cm, and conditioned at 105 °C

for 16 h under a constant flow of nitrogen. For fibrous samples, the packing was performed directly from the yarn by pulling it through the column with the help of a steel wire. IGC measurement was carried out using a Perkin-Elmer Autosystem XL apparatus in the temperature range between 30 and 70 °C with increments of 10 °C. Vapour samples of 5-20 µl were injected into the column and retention peaks were recorded by a FID detector. High purity nitrogen was used as carrier gas, and its flow rate changed between 5 and 20 mL/min depending on measurement temperature and on the type of adsorbent. A new column was prepared for each set of experiments. Each reported value is the result of at least three parallel measurements.

2.3. Contact angle measurements

Contact angle measurements were carried out at 23 °C and 55 % relative humidity using a Ramé-Hart Contact angle goniometer (USA) with a drop image standard software of DT-Acquire and a camera. Liquid drops of 20 µl were deposited on each fabric sample and the image of the drops deposited onto the fabric surface was captured immediately by the camera. The value reported is the average of at least 5 readings for each of the samples.

3. BACKGROUND OF IGC AT INFINITE DILUTION

The IGC technique using infinite dilutions is a fast, accurate and relatively simple method for the study of the energetics of solid surfaces. According to the principle of the method, the column is packed with the solid to be characterized and probe molecules with known thermodynamic characteristics are made adsorbed on its surface. Surface characteristics can be derived from retention times or volumes. With this technique the dispersion component of the surface tension of the adsorbent can be determined in two ways. Both approaches are based on the fact that the free energy of adsorption (ΔG_A) is related to the net retention volume (V_N) [24], i.e.

$$\Delta G_A = -RT \ln V_N + C \quad (1)$$

where C is a constant depending on the reference state selected, R is the universal gas constant and T the temperature of the column. The relationship between the free energy (ΔG_A) and the reversible work of adhesion (W_A) is given by Eq. 2

$$-\Delta G_A = N a_{LV} W_A \quad (2)$$

where N is Avogadro's number and a_{LV} is the molecular surface area of the adsorbate. The free energy and reversible work of adhesion can be divided into two parts: a dispersion term (ΔG_A^d , W_A^d) and the one characterizing the electron donor-acceptor interaction (ΔG_A^{ab} , W_A^{ab}) of the components

$$W_A = W_A^d + W_A^{ab} \quad (3)$$

$$\Delta G_A = \Delta G_A^d + \Delta G_A^{ab} \quad (4)$$

as the W_A^d is defined by Fowkes approach [25]

$$W_A^d = 2(\gamma_1^d \gamma_2^d)^{1/2} \quad (5)$$

if we use n-alkanes as probe molecules W_A^{ab} equals zero and the dispersion component of the surface tension of the stationary phase can be deduced from the cross-sectional area of n-alkanes and from their surface tension by using Eqs. 1-5. Thus the basic equation of the first approach (Schultz method [26]) to determine γ_s^d takes the following form

$$RT \ln V_N = 2N(\gamma_s^d)^{1/2} a_{LV} (\gamma_{LV}^d)^{1/2} + C \quad (6)$$

where γ_s^d is the dispersion component of the surface tension of the adsorbent to be determined and γ_{LV}^d is that of the probe.

The second approach to determine γ_s^d was proposed by Dorris and Gray [27]. If the value of $RT \ln V_N$, which is derived from the retention volumes measured with n-alkanes of different chain

lengths, is plotted against the number of carbon atoms in their chain, we obtain a straight line, the slope of which is given by Eq. 7

$$-RT \ln \frac{V_N^n}{V_N^{n+1}} = 2N(\gamma_s^d)^{1/2} a_{CH_2} (\gamma_{CH_2})^{1/2} \quad (7)$$

where V_N^n and V_N^{n+1} are the retention volumes of n-alkanes with n and $n+1$ carbon atoms, respectively, a_{CH_2} is the surface area occupied by a $-CH_2-$ group and γ_{CH_2} is the surface tension of polyethylene.

Acid-base interaction (ΔG_A^{ab} , ΔH_A^{ab})

If the adsorbate also enters into interaction with the adsorbent through other than dispersion forces, ΔG_A^{ab} becomes different from zero and the component associated with acid-base interactions is related to the retention volume of the polar probe in the following way

$$\Delta G_A^{ab} = -[(RT \ln V_N + C) - (RT \ln V_N^{ref} + C)] = -RT \ln \frac{V_N}{V_N^{ref}} \quad (8)$$

where V_N is the net retention volume measured with the probe, while V_N^{ref} is the retention volume, which we would measure if the solvent entered only into dispersion interaction with the adsorbent. V_N^{ref} can be determined from any physico-chemical characteristics of solvents, which is closely related to their dispersion interaction potential, i.e. to their willingness to enter into dispersion interaction with the solid surface [28, 29]. ΔH_A^{ab} can be calculated from free energy values determined at different temperatures, since the two quantities are related to each other by Eq. 9.

$$\Delta G_A^{ab} = \Delta H_A^{ab} - T \Delta S_A^{ab} \quad (9)$$

where ΔS_A^{ab} is the entropy of the acid-base interaction of the components. Plotting $\Delta G_A^{ab}/T$ against $1/T$ yields a straight line with the slope of ΔH_A^{ab} .

Donor and acceptor numbers

The enthalpy of acid-base interaction (ΔH_A^{ab}) can be also derived from the acid-base parameters of the components according to the theories of Drago [30] or Gutmann [31], respectively. The donor-acceptor approach frequently used for the characterization of acid-base interactions was first suggested by Gutmann [31]. He described all compounds by an acceptor (AN) and a donor (DN) number, which indicate the Lewis acid or base character of a given component. According to his theory, ΔH_A^{ab} is defined in the following way

$$\Delta H_A^{ab} = \frac{(AN)_A (DN)_B}{100} \quad (10)$$

He used different methods for the determination of DN and AN . His donor numbers are measured by calorimetry and given in kcal/mol units. On the other hand, AN is a dimensionless quantity, which is measured by ^{31}P NMR spectroscopy. The value of 100 in the denominator of Eq. 10 accounts for the difference caused by the dissimilar techniques used for the determination of AN and DN . Because of the complications caused by the different techniques of determination and the resulting dissimilar dimensions of the AN and DN values obtained, often modified parameters are proposed and used in practice [28]. Riddle and Fowkes [32] proposed a new AN value, which is expressed in kcal/mol units and denoted as AN^* .

Based on Gutmann's theory [31], the most frequently used formula for the determination of the acid-base constants of polymers or inorganic materials is

$$\Delta H_A^{ab} = K_A DN + K_D AN^* \quad (11)$$

where K_A and K_D are constants characterizing the acidity or basicity of the solid surface, while AN^* and DN the acceptor and donor numbers of polar probe.

4. RESULTS AND DISCUSSIONS

4.1. Surface energy of the cellulosic substrates

As mentioned above, the dispersion component of surface tension, as well as the acid–base character of solid surface can be determined by IGC. The γ_s^d values of fibrous and ground cotton and linen samples were calculated from the retention data of n-alkanes by the Dorris-Gray method. As Fig. 1 and 2 show, the γ_s^d values decreased continuously with increasing the measurement temperature in the range of 30-70 °C independently of the type or form of samples. The slight decrease in the γ_s^d values as a function of increasing temperature, measured without any further changes in the fibre surface, can be explained by the thermal expansion of samples, as well as the decreasing adsorption ability of probes with increasing temperature [21].

Figure 1.

Figure 2.

Moreover, Fig. 1 clearly shows that dispersion component of surface tension of the fibrous cotton is a little bit higher than that of the linen fibre. These data are consistent with our earlier data [21] mentioned in the introduction section. Nevertheless, the ratio of γ_s^d values of the two fibrous samples are rather surprising, since it was proved by XPS that surface of the linen fibre includes more groups containing oxygen than that of the cotton fibre [21]. Furthermore, as Fig. 2 shows, the γ_s^d of the ground cotton was smaller than γ_s^d of the ground linen at 70 °C, as expected, but at lower temperatures similar tendency was observed as it was for the fibrous samples.

For comparison, surface energy of the two samples in fabric form was also tested by contact angle measurement using water and diiodomethane as wetting liquids. In Fig. 3 and 4 the drop images of water and diiodomethane, respectively, recorded immediately after reaching the fabric surface are presented. It is obvious that wettability of the linen fabric is better than that of the

cotton, since the contact angles of diiodomethane and water drops are smaller on the surface of linen fabric (42 and 98°, respectively) than on the surface of cotton fabric (55 and 107°, respectively) (Table 2). It is well known, that the increasing surface energy usually results in higher wettability, so the results of contact angle measurements are in accordance with our assumption that the surface energy of linen is higher than that of cotton. In order to determine the surface tension of the cellulosic fibres, the Owens-Wendt formula (equation 12) [33] was applied and contact angles measured with diiodomethane and water were used for the calculation of dispersion and polar components, respectively.

$$\gamma_{LV}(\cos\theta + 1) = 2 (\gamma_{LV}^d \gamma_{SV}^d)^{1/2} + 2 (\gamma_{LV}^p \gamma_{SV}^p)^{1/2} \quad (12)$$

where γ_{LV} , γ_{LV}^d and γ_{LV}^p are the surface tension of the liquid and its dispersion and polar components, respectively, used in the measurements. γ_S^d and γ_S^p are the dispersion and polar components of surface tension of solid polymers (i.e. fabrics), respectively.

Figure 3.

Figure 4.

Table 2

Although, the high standard deviations of contact angles indicate the uncertainty of the determination, it is obvious that the surface energy of cotton is less than that of linen (Table 2). Comparing the surface tension values obtained from two different experiments (Fig. 1 and 2, Table 2), the question then arises: why so unrealistic high values were measured for cotton samples by IGC? Our hypothesis is that trapping of the n-alkane probes by the high molecular weight fatty acids, esters, alcohols and hydrocarbon chains of the outer waxy layer on the cotton surface can be the explanation of the unexpected results. In order to confirm the trapping theory, we

ascertained the results from IGC by comparing them with those derived from the wetting experiments and by the knowledge available from earlier publications [34, 35].

As we demonstrated above, the γ_s^d values determined by IGC are larger than those calculated from the contact angles. This fact, however, is not unexpected if we consider that infinite dilution IGC measures exclusively the most active sites on the surface. Accepting the assumption of n-alkane trapping, it is understandable, that the surface energy for fibrous cotton is larger than that of fibrous linen at all temperatures. In spite of our expectation that the effect of trapping decreases with increasing temperature, Fig. 1 reveals that the difference between the γ_s^d values of the two substrates is almost independent of the measurement temperature.

Nevertheless, interpretation of the results shown in Fig. 2 is more difficult, since besides trapping, the effect of grinding has also to be considered. Previous work in this laboratory demonstrated that grinding increases the concentration of oxygen-containing groups on the surface and creates less perfect crystalline structure [21]. The former effect of grinding can result in an increase in the dispersion component of surface tension and also lead to a decrease in trapping of n-alkane probes especially on cotton. On the other hand, the less perfect crystal structure (i.e. the latter effect) which was more pronounced at linen, can bring about a less effective adsorption of probes on the substrates. That results in lower γ_s^d values measured by IGC especially on linen. The joint effect of these two actions can lead to the results presented in Fig. 2.

4.2. Acid–base parameters of cellulosic substrates

For obtaining the acid–base parameters of cotton and linen samples, the polar component of free energy (ΔG_A^{ab}) of various polar probes' adsorption at different temperatures was measured. The most important observations for the first round of experiments were that while polar probes were not retained at all at any temperature on fibrous cotton, a mild retention was detected on the

ground cotton, but exclusively in the temperature range of 30-50 °C. For linen, however, the polar probes were retained both on the fibrous and ground samples at any temperature.

In order to obtain ΔG_A^{ab} , first, a baseline with *n*-alkanes capable of only dispersion interaction was created. The approaches presented previously [28, 29] were used to define the baseline: the $RT \ln V_N$ values were plotted against the $a_{LV}(\gamma_{LV}^d)^{1/2}$. ΔG_A^{ab} values of four polar probes, namely chloroform, ethyl acetate, tetrahydrofuran and acetone were determined. For chloroform and tetrahydrofuran, the ΔG_A^{ab} values are presented in Fig. 5a and b, respectively. It is obvious that the ΔG_A^{ab} values vary between 2.5 and 5.0 kJ/mol. Similar data were obtained with ethyl acetate (Fig. 6a), but a slightly larger ΔG_A^{ab} values were measured with acetone (Fig. 6b).

Figure 5.

Figure 6.

Plotting the $\Delta G_A^{ab}/T$ values against the $1/T$ resulted in straight line, the slope of which equals ΔH_A^{ab} . The procedure followed and the straight line obtained is presented in Fig. 7 for chloroform adsorption on linen fibre. The derived ΔH_A^{ab} values for all probes and adsorbents are summarized in Table 3 together with the regression coefficients of the lines, from which they were calculated. In spite of the difficulties described previously [28], results in Table 3 indicate that ΔH_A^{ab} can be determined with acceptable accuracy. The regression coefficient of the straight lines exceeds 0.93 in each case, except for the acetone adsorption on cotton surface (0.7707). The similar values of ΔH_A^{ab} for chloroform and THF indicate that all the samples have amphoteric surface character. It is clear from Table 3, that the ΔH_A^{ab} values for ethyl acetate and especially for acetone are higher than those calculated for the acidic and basic probes. The high specific enthalpies of

amphoteric probes also confirm the amphoteric character of the surfaces investigated. The largest enthalpies can be measured on linen fibre, the smallest on ground linen.

Figure 7

Table 3

Understanding of these results is as difficult as it was in case of the dispersion component of surface tension. In our opinion the measured adsorption enthalpies are determined by the adsorption ability of polar probes on the given substrates, which depends on the surface energy and the crystalline structure of the surface. We think that the probability of trapping of polar probes on the waxy surface of cotton is smaller than that of n-alkanes, and the most important parameter is the less perfect crystalline surface created by grinding. As we proved earlier, the effect of grinding is stronger on linen than on cotton.

The acid-base parameters of cotton and linen samples were calculated from ΔH_A^{ab} using the AN^* and DN numbers proposed by Riddle, Fowkes and Guttmann [31, 32]. According to Eq. 11, the $\Delta H_A^{ab}/AN^*$ was plotted against the DN/AN^* in order to obtain the K_a and K_d parameters. The procedure is demonstrated in Fig. 8 for fibrous linen. The calculations, i.e. determination of K_a and K_d parameters were carried out for all samples and the results are listed in Table 4 together with the regression coefficients of the fit. It is obvious that the acid-base parameters can be calculated with practically the same accuracy for all samples. The calculated K_a and K_d parameters are very similar for cotton and linen samples. The larger donor numbers indicate basicity of the investigated cellulosic samples. The highest K_d/K_a value of ground linen can correspond to high surface oxygen concentration of the substrate. Comparing these values with the results of contact angle measurements and with our former results of energy dispersive spectroscopy as well as X-ray photoelectron spectroscopy [21], it can be concluded, that the measured parameters depend on

the adsorbability of probe molecules on the investigated surface. Beside surface energy, grinding also influences the measured characteristics.

Figure 8

Table 4

It is worth noting, however, that the calculated K_d/K_a values are not in accordance with the ΔH_A^{ab} values of different probes. While on the basis of K_d/K_a ratios the investigated substrates show strong basic character, according to ΔH_A^{ab} values the surface character is evenly basic and acidic, namely amphoteric. The reason of the anomaly may be the incomparable scale of AN and DN numbers of polar probes used for determination [16].

5. CONCLUSIONS

Surface properties of fibrous and ground cotton and linen were investigated by IGC and contact angle measurement was applied for the fabrics of both fibres. In spite of the better wettability and higher surface tension of linen sample determined by contact angle measurement, significantly larger γ_s^d was measured for cotton than for linen by IGC. It is well-known that surface of cotton fibres is covered with a continuous waxy outer layer, which can act as a trap for the n-alkanes. Thus, trapping of n-alkanes among the molecules of cotton wax can be the reason of the unexpectedly high γ_s^d values determined for fibrous cotton by IGC. For ground samples, besides surface energy and trapping effects, the higher surface oxygen content and the less perfect crystalline surface can also influence the γ_s^d values.

Experiments with polar probes revealed that free energy of adsorption can be determined on all the linen samples, as well as on the ground cotton in the temperature range of 30-50 °C, but polar probes were not retained at all on the fibrous cotton at any temperatures. For calculation of

the acid-base character of surfaces, specific enthalpies were determined from the temperature dependence of free energies. Similar ΔH_A^{ab} values were calculated with chloroform (acidic probe) and THF (basic probe), and relatively high ΔH_A^{ab} values of the amphoteric ethyl acetate and acetone probes were measured for each of the investigated samples. These results indicated that the surface character of the cellulosic substrates is evenly basic and acidic, namely amphoteric.

Finally, it can be concluded that IGC is a suitable method for characterizing the surface properties of cellulosic substrates. If the influences of the different factors are considered, the determined properties can be understood and explained. With the aid of XPS, IGC gives valuable information on the surface physico-chemical properties of materials.

ACKNOWLEDGEMENTS

The financial support of the National Scientific Research Fund of Hungary (OTKA Grant No. K 108934) is highly appreciated.

6. REFERENCES

1. O. Faruk, A. K. Bledzki, H.-P. Fink, and M. Sain, *Progr. Polym. Sci.*, **37**, 1552 (2012).
2. E. Papirer, E. Brendle, H. Balard, and C. Vergelati, *J. Adhes. Sci. Technol.*, **14**, 321 (2000).
3. E. Cantergiani and D. Benczedi, *J. Chromatogr. A*, **969**, 103 (2002).
4. P. Jandura, B. Riedl, and B. V. Kokta, *J. Chromatogr. A*, **969**, 301 (2002).
5. G. Buschle-Diller, M. K. Inglesby, and Y. Wu, *Colloids Surf., A*, **260**, 63 (2005).
6. B. A. P. Ass, M. N. Belgacem, and E. Frollini, *Carbohydr. Polym.*, **63**, 19 (2006).
7. X. Ren and G. Buschle-Diller, *Colloid. Surface. A*, **299**, 15 (2007).

8. N. Rjiba, M. Nardin, J.-Y. Drean, and R. Frydrych, *J. Colloid Interface Sci.*, **314**, 373 (2007).
9. J. Y. Y. Heng, D. F. Pearse, F. Thielmann, T. Lampke, and A. Bismarck, *Compos. Interfaces*, **14**, 581 (2007).
10. N. Rjiba, M. Nardin, J.-Y. Drean, and R. Frydrych, *J. Polym. Res.*, **17**, 25 (2010).
11. L. Zhao and Y. Boluk, *Appl. Surf. Sci.*, **257**, 180 (2010).
12. N. Cordeiro, C. Gouveia, and M. J. John, *Ind. Crops Prod.*, **33**, 108 (2011).
13. N. Cordeiro, C. Gouveia, A. G. O. Moraes, and S. C. Amico, *Carbohydr. Polym.*, **84**, 110 (2011).
14. N. Cordeiro, C. Mendonca, L. A. Pothan, and A. Varma, *Carbohydr. Polym.*, **88**, 125 (2012).
15. E. S. Abdel-Halim, *Carbohydr. Polym.*, **88**, 1201 (2012).
16. J. A. F. Gamelas, *Cellulose*, **20**, 2675 (2013).
17. S. Mohammadi-Jam and K. E. Waters, *Adv. Colloid Interface Sci.*, **212**, 21 (2014).
18. M. N. Belgacem, G. Czeremuszkina, S. Sapiuha, and A. Gandini, *Cellulose*, **2**, 145 (1995).
19. J. A. Trejo-O'Reilly, J. Y. Cavaille, N. M. Belgacem, and A. Gandini, *J. Adhes.*, **67**, 359 (1998).
20. E. Csiszar and E. Fekete, *Text. Res. J.*, **80**, 1307 (2010).
21. E. Csiszar and E. Fekete, *Langmuir*, **27**, 8444 (2011).
22. E. Csiszar, E. Fekete, A. Toth, E. Bandi, B. Koczka, and I. Sajo, *Carbohydr. Polym.*, **94**, 927 (2013).
23. J. A. F. Gamelas, E. Ferraz, and F. Rocha, *Colloids Surf., A*, **455**, 49 (2014).
24. J. R. Conder, Young, C.L., "Physicochemical Measurement by Gas Chromatography", Wiley, Chichester, 1979.
25. F. M. Fowkes, *Ind. Eng. Chem.*, **56**, 40 (1964).
26. J. Schultz, L. Lavielle, and C. Martin, *J. Adhes.*, **23**, 45 (1987).

27. G. M. Dorris and D. G. Gray, *J. Colloid Interface Sci.*, **77**, 353 (1980).
28. E. Fekete, J. Moczo, and B. Pukansky, *J. Colloid Interface Sci.*, **269**, 143 (2004).
29. A. Voelkel, B. Strzemiecka, K. Adamska, and K. Milczewska, *J. Chromatogr. A*, **1216**, 1551 (2009).
30. R. S. Drago, Wayland, B.B, *J. Am. Chem. Soc.*, **87**, 3571 (1965).
31. V. Gutmann, "The Donor–Acceptor Approach to Molecular Interactions", Plenum, New York, 1978.
32. F. L. Riddle and F. M. Fowkes, *J. Am. Chem. Soc.*, **112**, 3259 (1990).
33. D. K. Owens, Wendt, R.C., *J. Appl. Polym. Sci.*, 13, 1741 (1969).
34. H. L. Lee and P. Luner, *J. Colloid Interface Sci.*, **146**, 195 (1991).
35. N. E. Zafeiropoulos, D. R. Williams, C. A. Baillie, and F. L. Matthews, *Composites, Part A*, **33**, 1083 (2002).

Table 1. Physico-chemical properties of the IGC probes used in the study [16, 31]

Probe	a (Å) ²	γ^d_L (mJ m ⁻²)	AN [*] (kJ mol ⁻¹)	DN (kJ mol ⁻¹)	Specific character
<i>n</i> -Hexane	51.5	18.4	–	–	Neutral
<i>n</i> -Heptane	57.0	20.3	–	–	Neutral
<i>n</i> -Octane	62.8	21.3	–	–	Neutral
<i>n</i> -Nonane	69.0	22.7	-	-	Neutral
<i>n</i> -Decane	74.0	24.2	-	-	Neutral
Chloroform	44.0	25.0	22.6	0	Acid
Ethyl acetate	48.0	19.6	6.3	71.6	Amphoteric
Acetone	42.5	16.5	10.5	71.2	Amphoteric
Tetrahydrofuran	45.0	22.5	2.1	83.8	Base

Table 2. Results of contact angle measurements for linen and cotton fabrics

	Linen	Cotton
$\theta_{\text{diiodomethane}} (^{\circ})$	42 ± 4	55 ± 4
$\theta_{\text{water}} (^{\circ})$	98 ± 5	107 ± 4
γ_s^d (mJ/m ²)	38.6	31.4
γ_s^p (mJ/m ²)	0.12	0

Table 3. Acid-base component of the adsorption enthalpy of polar probes for fibrous and ground linen and for ground cotton

	Linen, fibrous		Linen, ground		Cotton, ground	
	ΔH_A^{ab} (kJ/mol)	R^2	ΔH_A^{ab} (kJ/mol)	R^2	ΔH_A^{ab} (kJ/mol)	R^2
Chloroform	19.3	0.9942	11.2	0.9682	18.8	0.9956
Ethyl acetate	22.5	0.9907	17.5	0.9333	19.0	0.9523
Tetrahydrofuran	17.3	0.9872	11.5	0.9377	15.3	0.9998
Acetone	26.2	0.9800	21.1	0.9940	24.1	0.7701

Table 4. Acid–base properties of fibrous and ground linen and ground cotton, and the standard deviation of determination

Samples	K_a	K_d	K_d/K_a	R^2
Linen, fibrous	0.18	1.18	6.55	0.9918
Linen, ground	0.12	1.00	8.33	0.9587
Cotton, ground	0.16	1.07	6.68	0.9952

Figure captions

- Fig. 1 Effect of temperature on the dispersion component of surface tension (γ_s^d) of fibrous cotton and linen samples
- Fig. 2 Effect of temperature on the dispersion component of surface tension (γ_s^d) of ground cotton and linen samples
- Fig. 3 Water contact angles on the surface of raw cotton (a) and linen (b) fabrics
- Fig. 4 Diiodomethane contact angles on the surface of raw cotton (a) and linen (b) fabrics
- Fig. 5 ΔG_A^{ab} of chloroform (a) and THF (b) adsorption at different temperatures for fibrous and ground linen and for ground cotton
- Fig. 6 ΔG_A^{ab} of adsorption of amphoteric probes (a: ethyl acetate, b: acetone) at different temperatures for fibrous and ground linen and for ground cotton
- Fig. 7 Determination of specific enthalpy of adsorption of chloroform on linen fibre
- Fig. 8 Determination of acid-base constants of linen fibre

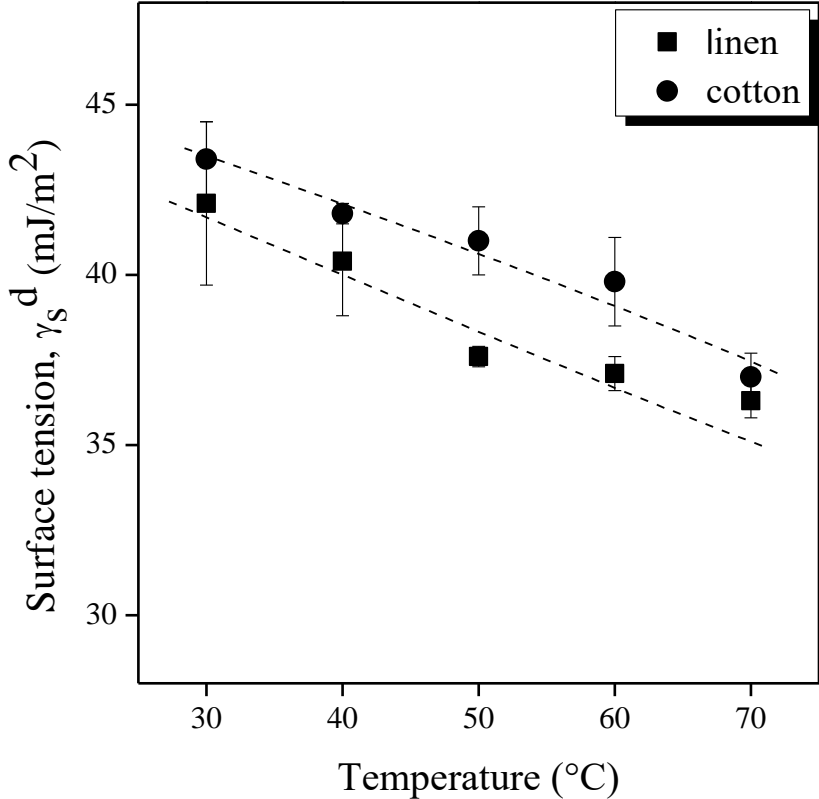


Fig. 1 Effect of temperature on the dispersion component of surface tension (γ_s^d) of fibrous cotton and linen samples

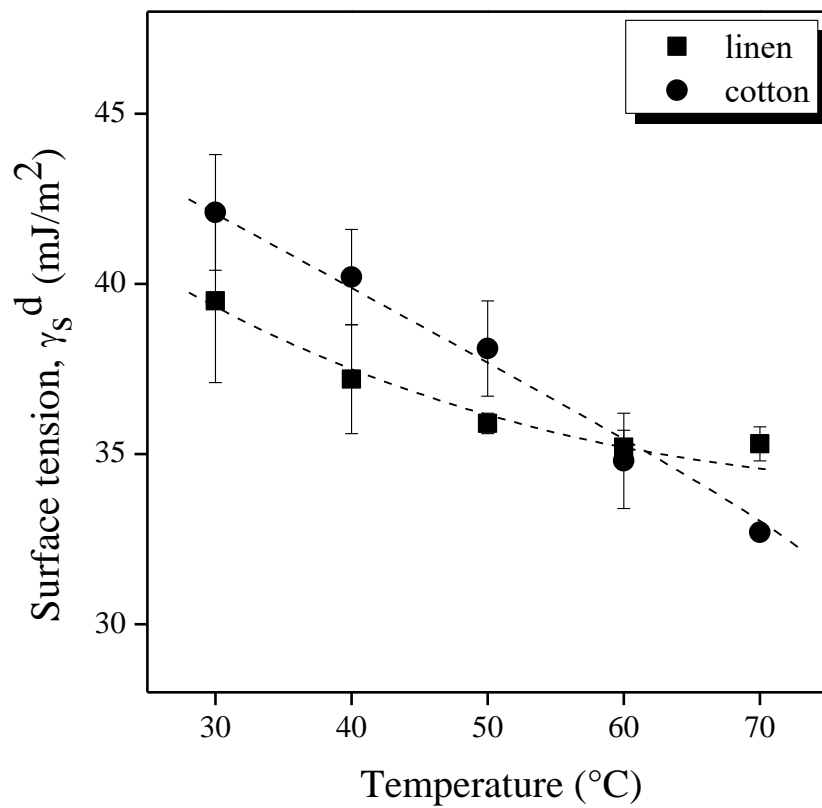


Fig. 2 Effect of temperature on the dispersion component of surface tension (γ_s^d) of ground cotton and linen samples

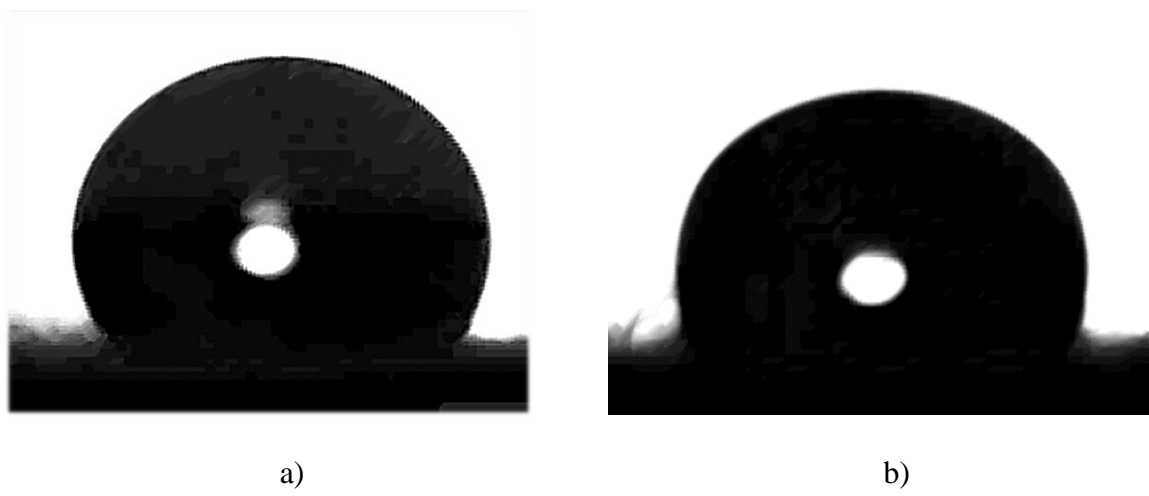


Fig. 3 Water contact angles on the surface of raw cotton (a) and linen (b) fabrics

Fekete, Fig.4

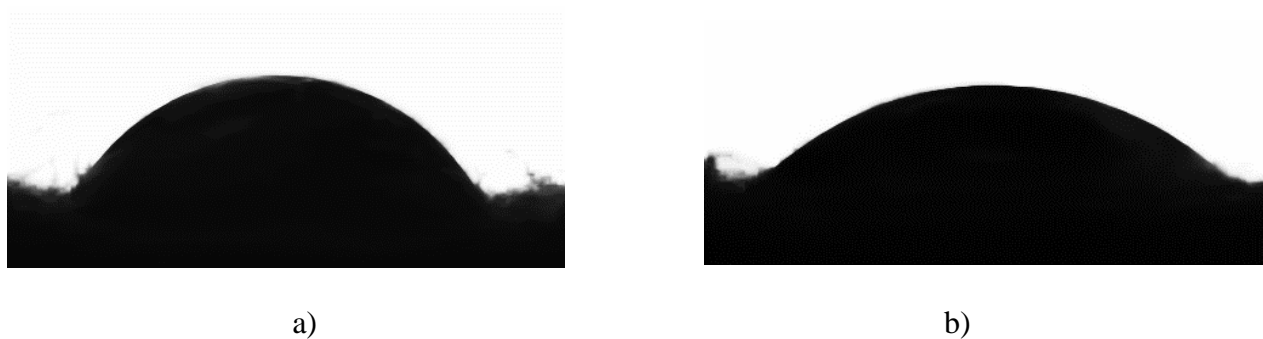


Fig. 4 Diiodomethane contact angles on the surface of raw cotton (a) and linen (b) fabrics

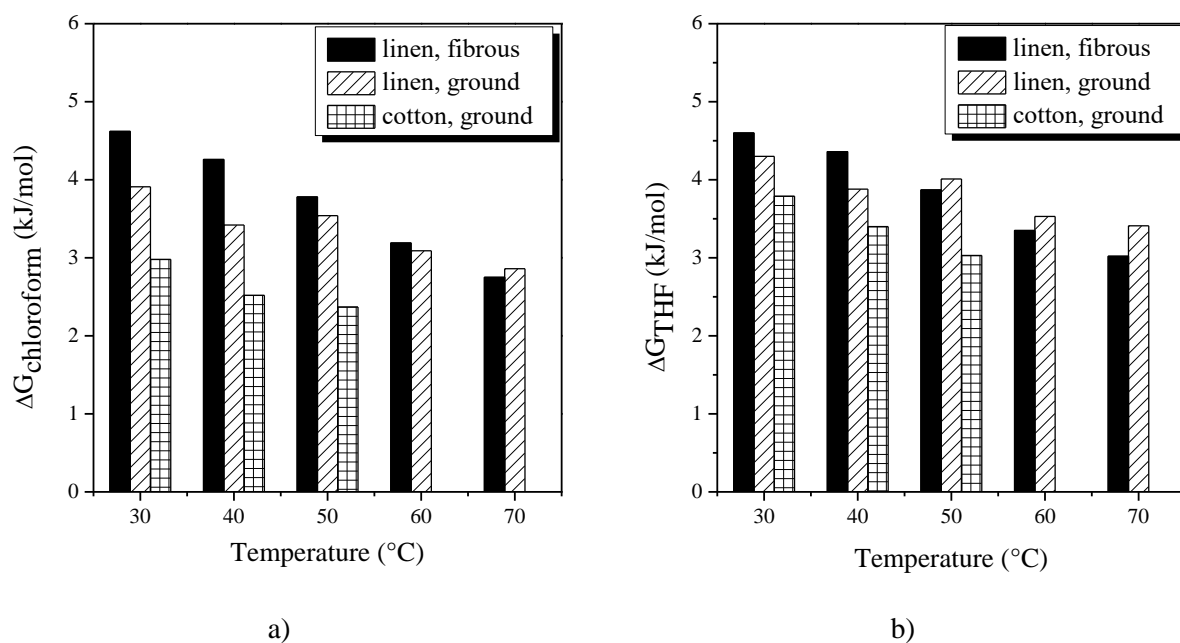


Fig. 5 ΔG_A^{ab} of chloroform (a) and THF (b) adsorption at different temperatures for fibrous and ground linen and for ground cotton

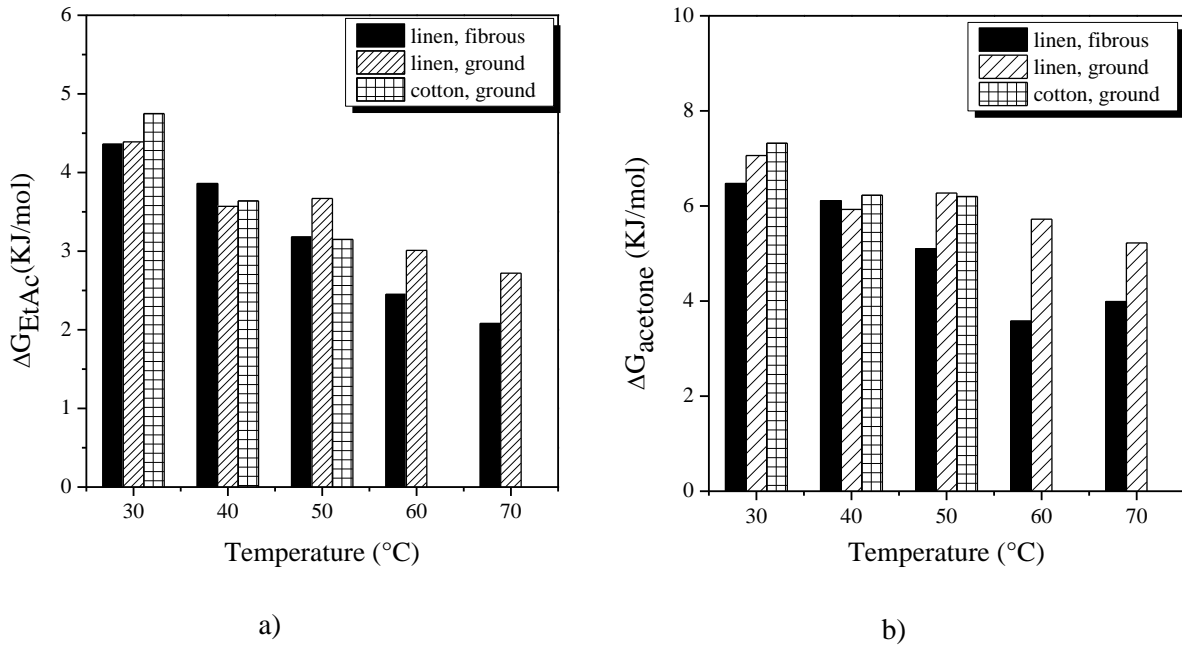


Fig. 6 ΔG_A^{ab} of adsorption of amphoteric probes (a: ethyl acetate, b: acetone) at different temperatures for fibrous and ground linen and for ground cotton

Fekete, Fig.7

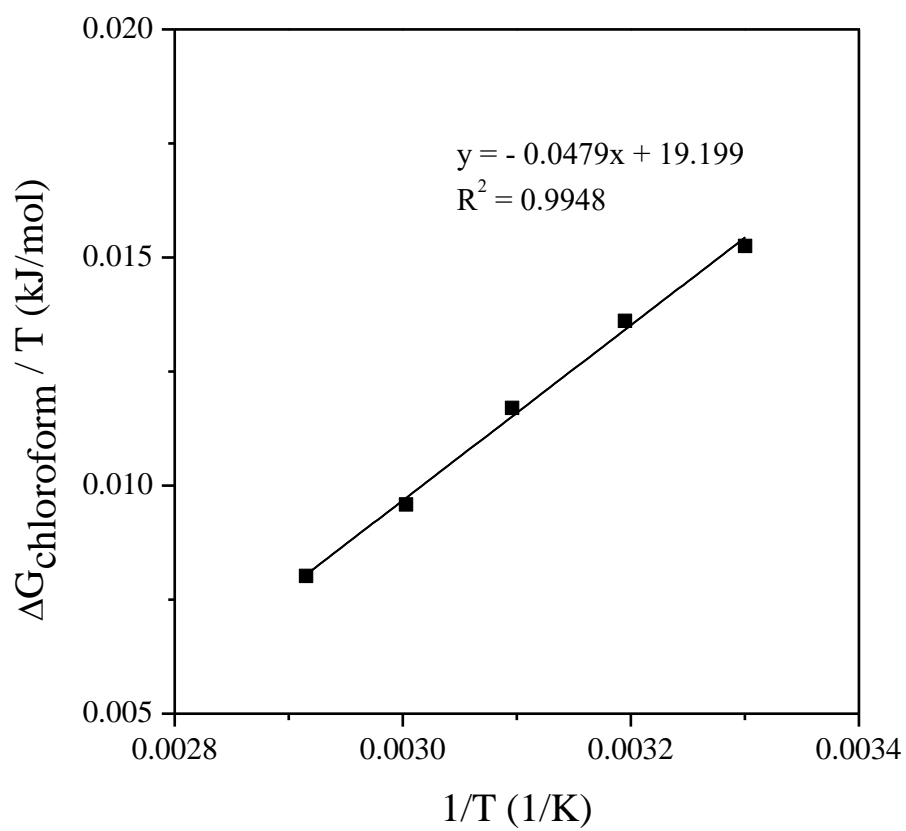


Fig. 7 Determination of specific enthalpy of adsorption of chloroform on linen fibre

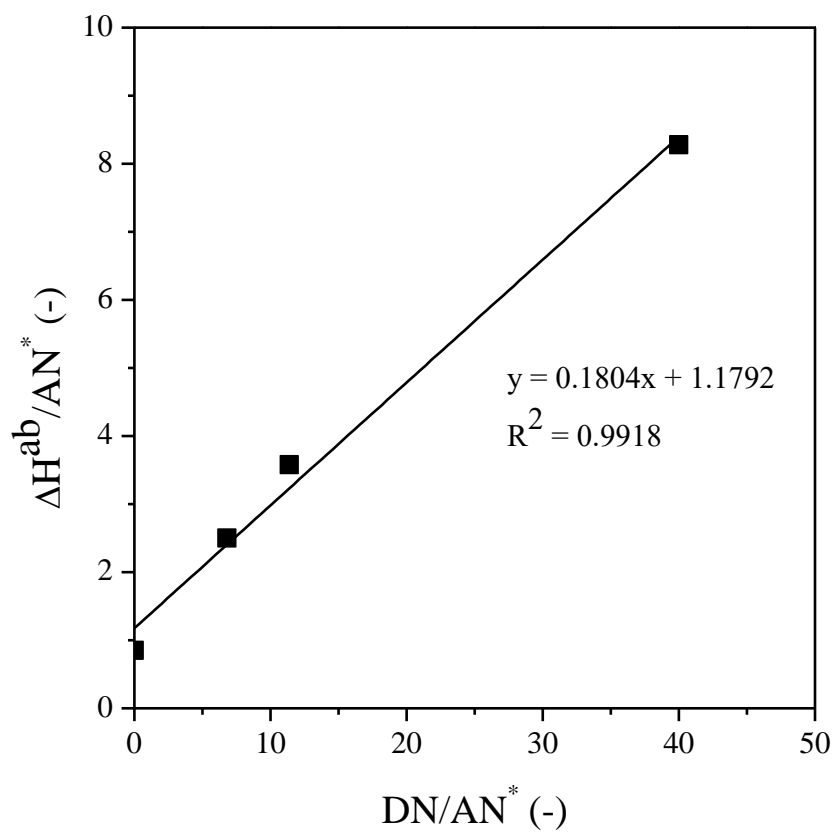


Fig. 8 Determination of acid-base constants of linen fibre