

# Synthesis of Zeolite Y from Kaolin Using Novel Method of Dealumination

<sup>1</sup>Adeoye, J. B., <sup>2</sup>Omoleye, J. A., <sup>3</sup>Ojewumi, M. E. and <sup>4</sup>Babalola, R.

<sup>1,2,3</sup>Chemical Engineering Department, Covenant University, P.M.B 1023, Ota, Ogun state, Nigeria.

<sup>4</sup>Chemical and Petrochemical Engineering Department, Akwa Ibom State University, Ikot Akpaden.

<sup>1</sup>[john.adeoye@stu.cu.edu.ng](mailto:john.adeoye@stu.cu.edu.ng), <sup>2</sup>[james.abiodun@covenantuniversity.edu.ng](mailto:james.abiodun@covenantuniversity.edu.ng), <sup>3</sup>[modupe.ojewumi@covenantuniversity.edu.ng](mailto:modupe.ojewumi@covenantuniversity.edu.ng),

<sup>4</sup>[Rasheedbabalola@ksu.edu.ng](mailto:Rasheedbabalola@ksu.edu.ng)

## Abstract

In this study Zeolite Y was successfully synthesized from local kaolin in Ado-Odo Ota, Ogun state Nigeria through a novel process of dealumination. The thermal activation of kaolin was achieved through the process of metakaolinization at 850 °C for 6 hours in a furnace and dealumination with H<sub>2</sub>SO<sub>4</sub> in order to achieve a desire silica/alumina molar ratio between 3 and 8. Zeolitization involved alkaline attack of dealuminated metakaolin and its consequent transformation into Zeolite Y crystal. Silica/Alumina molar ratio of 5.84 of metakaolin was synthesized under hydrothermal treatment with aqueous NaOH at atmospheric pressure. It was then aged for 7 days at room temperature and crystallized at 100 °C for 24 hours; Zeolite NaY of molar ratio of 3.46 was achieved and then modified to its hydrogen form by ion exchange with NH<sub>4</sub>Cl. The molar ratio of Zeolite Y in hydrogen form is 3.22. The samples were characterized with X-ray Fluorescence (XRF), X-Ray Diffraction (XRD), and Scanning Electron Microscope (SEM). The result showed that zeolite Y was synthesized from Arobieye mined kaolin with a molar ratio of 6SiO<sub>2</sub> : Al<sub>2</sub>O<sub>3</sub> : 9Na<sub>2</sub>O : 24H<sub>2</sub>O by ageing at room temperature for 24 hours and crystallized at 100 °C for 24 hours.

**Keyword;** Arobieye mined kaolin, Crystallization, Hydrothermal Reaction, Novel dealumination, Zeolite Y

## INTRODUCTION

Zeolites are crystalline microporous, aluminosilicate minerals, with a unique three or two dimensional structural pattern of arrays of uniform pores, cavities and channels in molecular dimensional order. They are referred to as solid acids with

fascinating chemisorptions, high selectivity and thermal stability properties [1]. Zeolites are synthesis traditionally by hydro gel of Sodium aluminate and silicate [2]. The production of zeolite from clay as a source of silica and alumina are been investigates with positive achievement [3-4]. The benefits of using kaolin as an aluminosilicate source in zeolite production are widely known [5].


## MATERIALS AND METHOD

### Materials

Kaolinite clay used in the course of synthesis of zeolite Y was procured from Arobieye village in Ado-Odo, Ota, Ogun state. Sodium hydroxide pellets (Sigma-Aldrich, Lobal Chemie, ≥98 %) and concentrated sulfuric acid (Sigma-Aldrich, Lobal Chemie, 98%) were used in this work for zeolite Y preparation. The chemical composition (XRF) and mineralogical analysis of Arobieye kaolin are shown in Table 1.0.

### Experimental procedure for the synthesis of zeolite Y

Arobieye clay was thoroughly purified by a clay-split method. The purified kaolin was calcined and converted to metakaolin at 850 °C for 6 hours. The metakaolin was dealuminated by using concentrated sulphric acid. Novel method of dealumination was used in this research work. Sodium hydroxide pellets (Sigma-Aldrich, Lobal Chemie, ≥98 %) was reacted with dealuminated kaolinite in a ratio of 2.5: 1 by weight and molar composition of 6SiO<sub>2</sub> : Al<sub>2</sub>O<sub>3</sub> : 9Na<sub>2</sub>O : 24H<sub>2</sub>O [6]. The gel obtained was aged for 7 days at room temperature and then hydrothermally crystallized at 100 °C for 24 hours. Figure 1.0 shows the flow diagram of the processes involved in the synthesis of zeolite Y from kaolin.

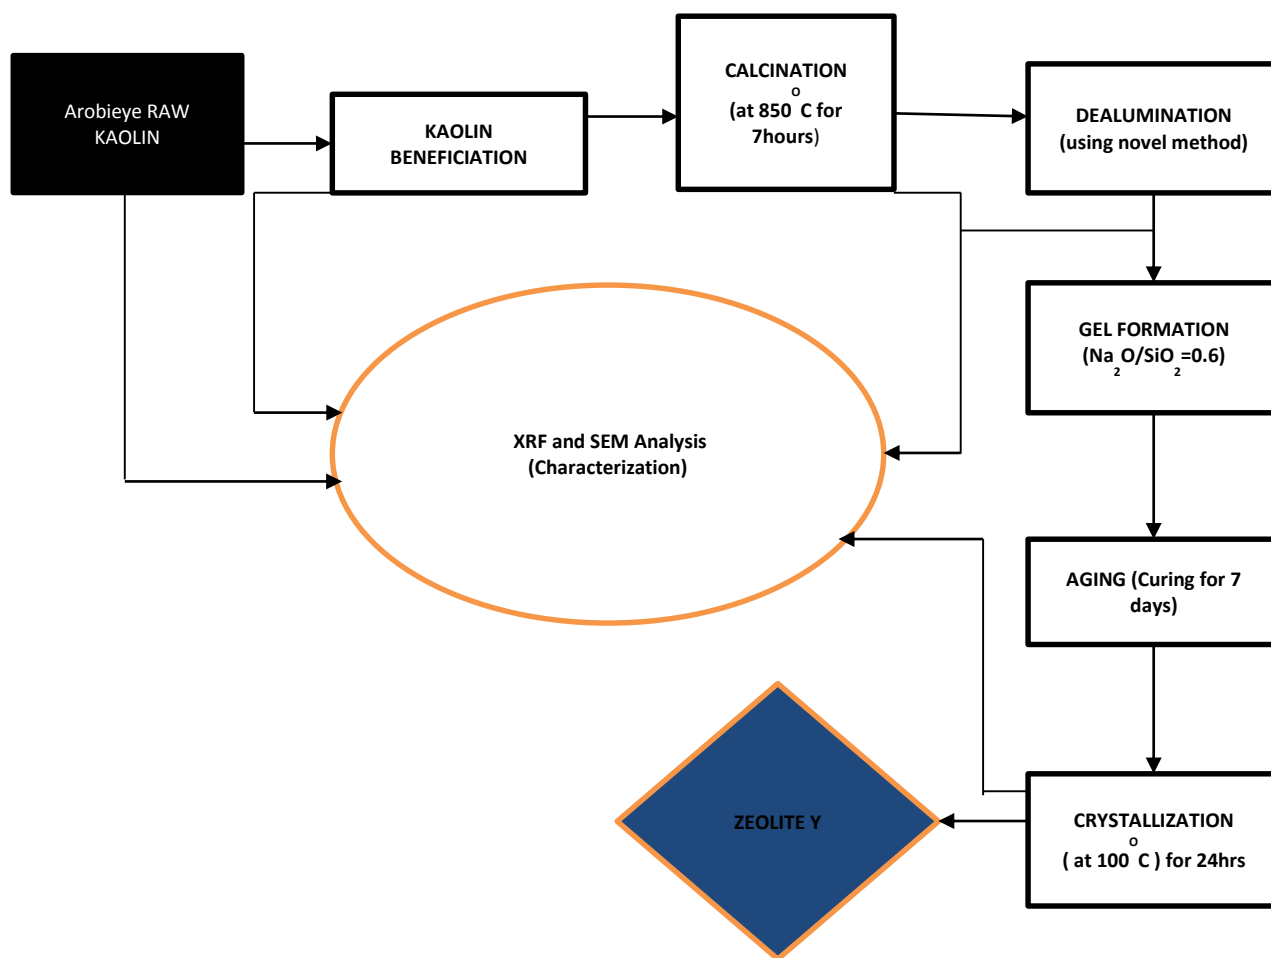

**Figure 1.0:** Flow diagram of zeolite Y synthesis from Arobieye mined clay [7]

### Transformation of zeolite NaY to his hydrogen form (zeolite HY)

The synthesized zeolite NaY produced from Arobieye kaolin was modified to its hydrogen

form by ion exchange reaction. 0.1M  $\text{NH}_4\text{Cl}$  solution was prepared and mixed with zeolite NaY at room temperature using a ratio of 100ml of solution to 10g of zeolite NaY and stirred vigorously using a magnetic stirrer for 10 minutes. This operation was carried out twice to obtain optimum ammonium exchange. The sample was filtered from the slurry and washed with deionized water until the solid was free of chloride. The zeolite  $\text{NH}_4\text{Y}$  was dried at room temperature for 24 hours and then transferred into a crucible and charged into a furnace at  $450^\circ\text{C}$  for residence time of 4 hours in order to remove ammonia and leave the zeolite Y in its hydrogen form.

### Characterization

In order to know the crystal structure and the relative crystallinity of zeolite, the X-ray diffraction (XRD) patterns were recorded on an X-ray diffraction machine (Cubic 3 Cement PAN analytical) using Cu-ka radiation with a

wavelength of 1.540598. To determine the morphology of zeolite, the scanning electron micrograph (SEM) was analyzed by Phenom prox SEM, manufactured: 2012, model number: 800-07334, part number: MVE0224651193. Chemical composition of kaolin was analyzed by X-ray machine (Axios Pananalytical).

### RESULTS AND DISCUSSION

Table 1.0 show that Arobieye mined kaolin is rich in oxides of iron, calcium and titanium. It indicates that there are large quantities of quartz in the sample. It also indicates that it is rich in the oxides of iron and Calcium but poor in the oxides of potassium and manganese.

Pure raw kaolinite clay is expected to have silica/Alumina ratio of 1 to 2 [8, 9]. Table 1.0 shows that  $\text{SiO}_2/\text{Al}_2\text{O}_3$  ratio of Arobieye mined clay is to 1.45, and it is within the theoretical value.

Table 2.0 shows the XRF analysis of the Synthesized Zeolite NaY and Zeolite HY. The results show that the silica/alumina ratio of 3.46 and 3.22 respectively are typical of zeolite Y.

**Table 1.0:** Chemical and mineralogical analysis of the Arobieye mined kaolin


Chemical composition of Arobieye kaolin		Mineralogical composition	
Oxide	Conc. Wt.%	Mineral	%
SiO <sub>2</sub>	48.79	Kaolinite	40.68
Al <sub>2</sub> O <sub>3</sub>	33.58	Quartz	52.28
Fe <sub>2</sub> O <sub>3</sub>	2.65	Illite/mica	6.89
CaO	2.98	Palygorskite	0.18
MgO	0.58		
SO <sub>3</sub>	0.04		
Na <sub>2</sub> O	0.07		
K <sub>2</sub> O	0.01		
TiO <sub>2</sub>	1.48		
P <sub>2</sub> O <sub>5</sub>	0.10		
Mn <sub>2</sub> O <sub>3</sub>	0.01		
<b>Si/Al (wt%)</b>	<b>1.45</b>		

**Table 2.0:** XRF analysis of the synthesis Zeolite NaY, Zeolite NH<sub>4</sub>Y and Zeolite HY


Oxide	Synthesis zeolite	Synthesis zeolite	Synthesis zeolite
	NaY Conc. Wt.%	NH <sub>4</sub> Y Conc. Wt.%	HY Conc. Wt.%
SiO <sub>2</sub>	37.57	38.58	39.71
Al <sub>2</sub> O <sub>3</sub>	18.44	18.68	20.94
Fe <sub>2</sub> O <sub>3</sub>	2.03	2.00	2.26
CaO	3.14	3.08	3.15
MgO	0.23	0.24	0.28
SO <sub>3</sub>	7.30	6.46	6.76
Na <sub>2</sub> O	33.27	30.07	28.47
K <sub>2</sub> O	0.07	0.07	0.06
TiO <sub>2</sub>	1.39	1.42	1.67
P <sub>2</sub> O <sub>5</sub>	0.07	0.07	0.07
Mn <sub>2</sub> O <sub>3</sub>	0.02	0.01	0.02
<b>Si/Al (Mol ratio)</b>	<b>3.46</b>	<b>3.51</b>	<b>3.22</b>

Figure 2(a-b) shows the XRD pattern of the synthesized Zeolite NaY and Zeolite HY. The Zeolite peaks could be observed in both XRD patterns at Bragg's angles of 14, 19, 21, 24, 26.8, 31.9, 34.9, 39.9, 49.8, 51°. The intensities of the peaks at Bragg's angles of 14, 19, 21, 24, 26.8, 31.9, 34.9, 49.8 and 51° corresponding to 980, 589, 2500, 500, 8000, 500, 500, 980 and 510 counts, respectively and characteristic of zeolite Y [10-11].

The XRD patterns of Zeolite NaY and zeolite HY are identical which indicated that modification of Zeolite with the exchange solutions did not lead to significant structural changes but there are differences in intensities.




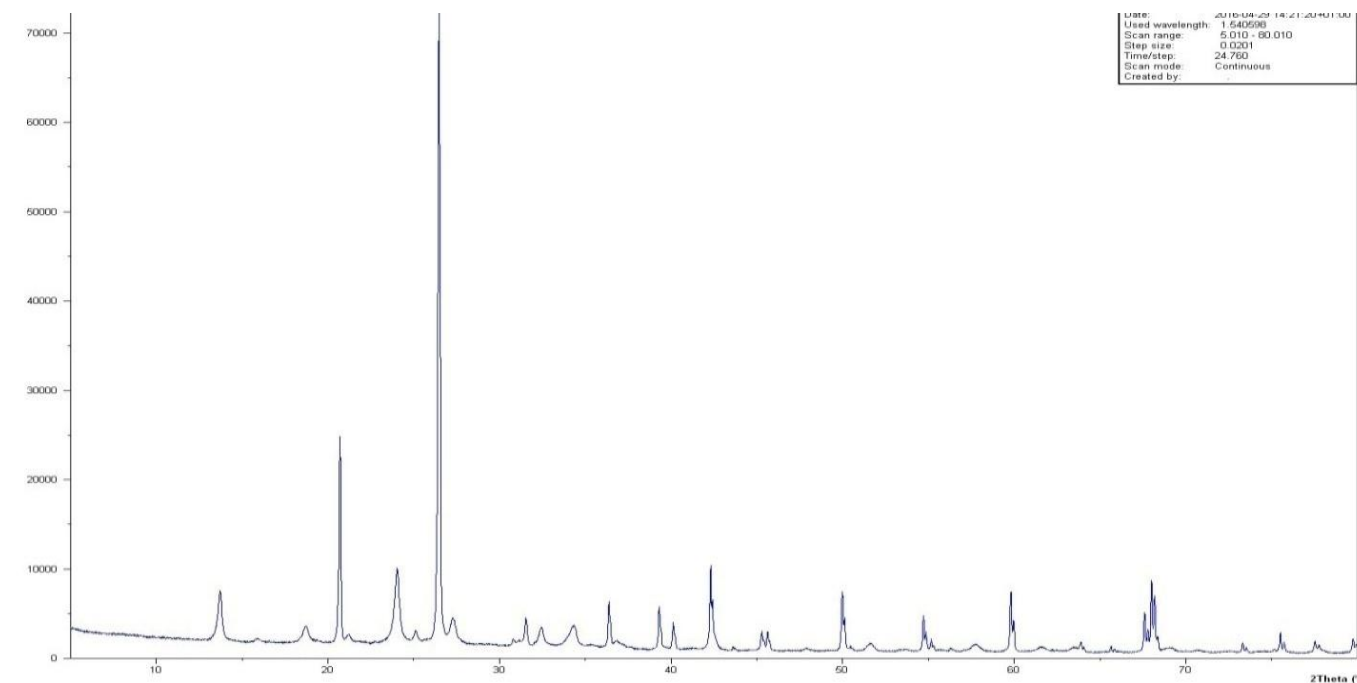


**Figure 2a:** XRD pattern of the zeolite NaY


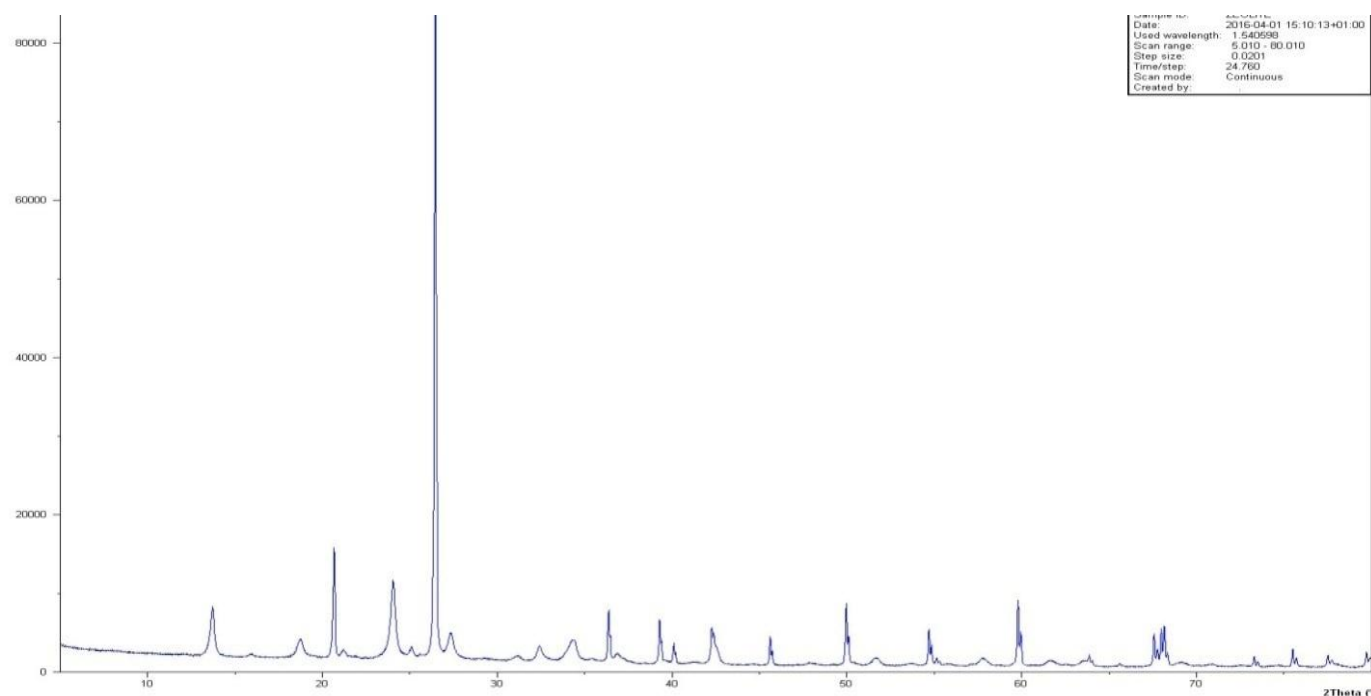



**Figure 2b:** XRD pattern of the zeolite HY

Figures 3(a- d) and 4(a-d) show the structural morphology of the synthesized Zeolite NaY and Zeolite HY at different magnifications of 3500, 5000, 8000 and 10000 respectively. The clear structural boundaries and shapes are evident of clear crystal formation of zeolite Y.

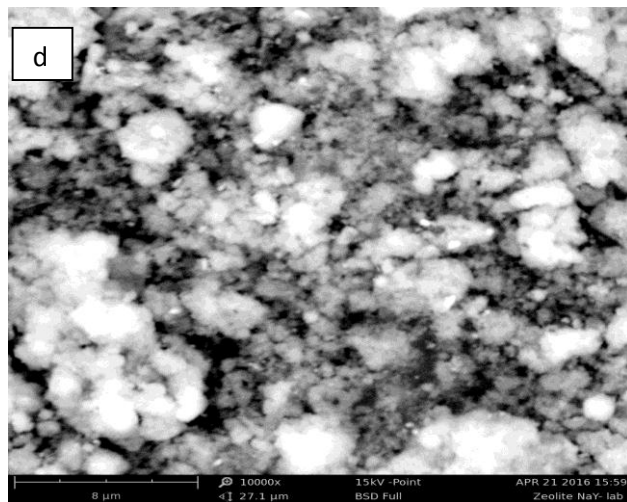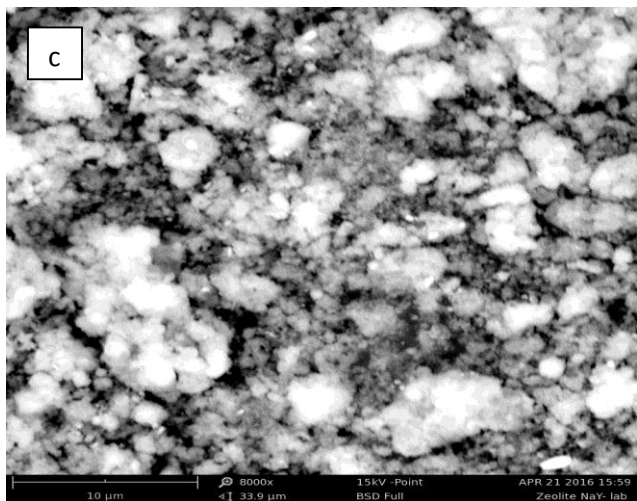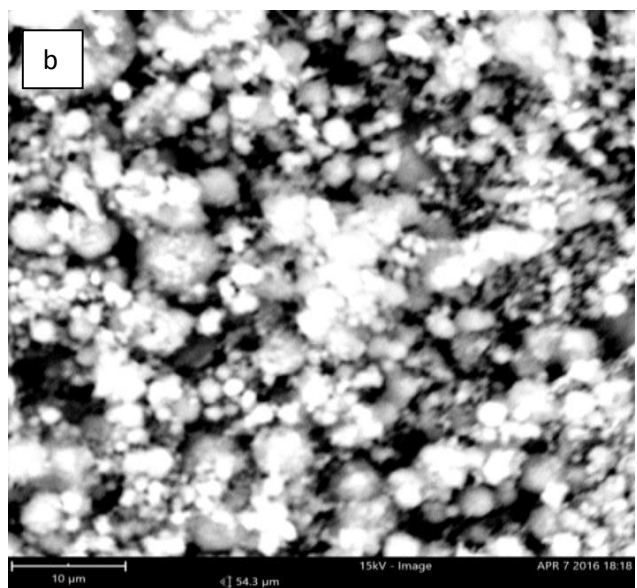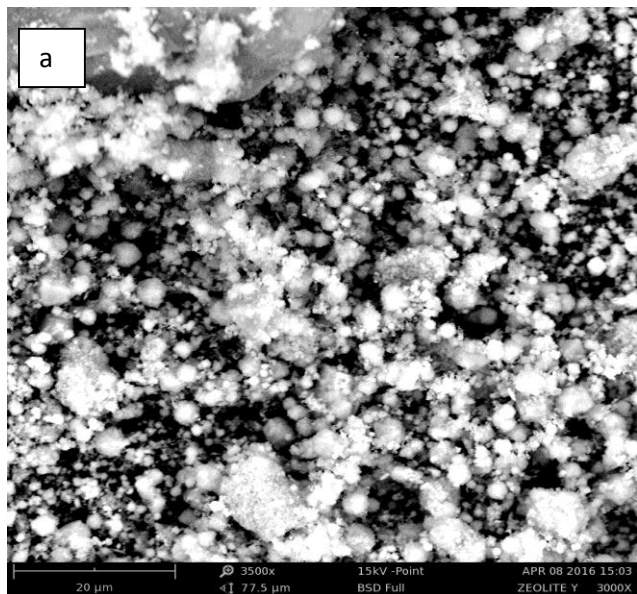

**Figure 3(a-d):** SEM images for the synthesized zeolite NaY at various magnifications (a) 3500; (b) 5000; (c) 8000; (d) 10000

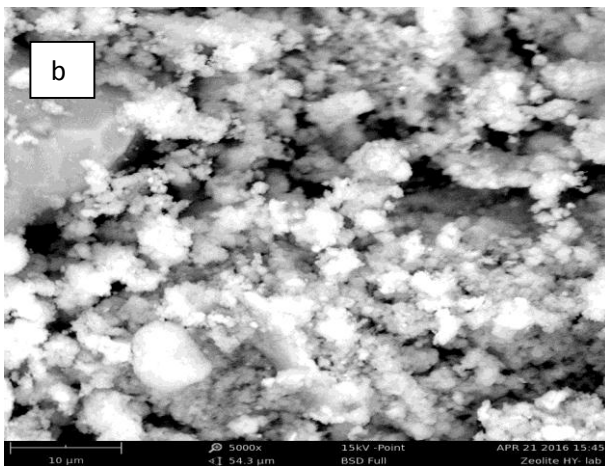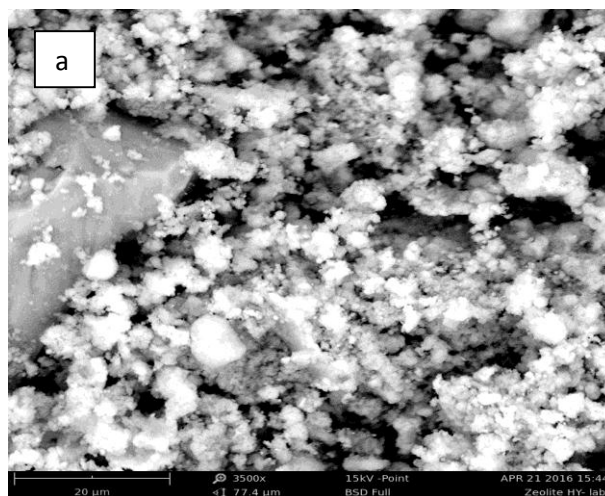

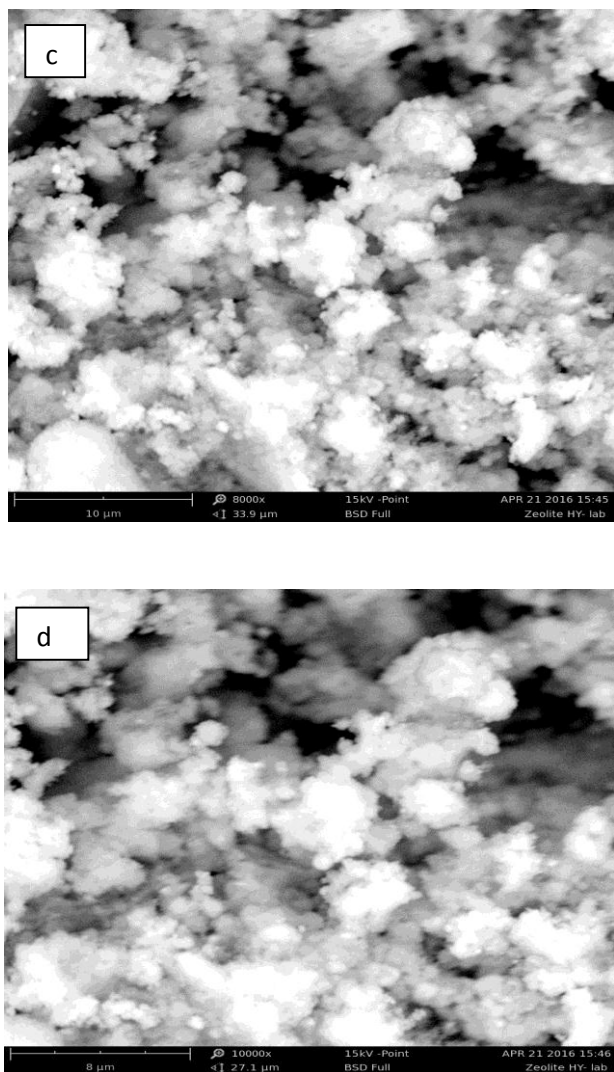

**Figure 4(a-d):** SEM images for the synthesized zeolite HY at various magnifications (a) 3500; (b) 5000; (c) 8000; (d) 10000

## CONCLUSION

Zeolite Y was successfully synthesized from Arobieye mined clay from Ota, Ogun state, Nigeria. Zeolite Y with  $\text{SiO}_2/\text{Al}_2\text{O}_3$  molar ratio of 3.46 was achieved from dealuminated metakaolin of  $\text{SiO}_2/\text{Al}_2\text{O}_3$  molar ratio 5.84 by treatment with sodium hydroxide and ageing for 7 days under proper condition. The zeolite NaY was modified by ion exchange ( $\text{NH}_4\text{Cl}$ ) and give a  $\text{SiO}_2/\text{Al}_2\text{O}_3$  molar ratio of 3.22. The ion exchange decreased the peak intensities of zeolite HY. The results of XRF analysis show that the major components of synthesized zeolite are  $\text{SiO}_2$ ,  $\text{Al}_2\text{O}_3$ ,  $\text{SO}_3$  and  $\text{Na}_2\text{O}$ , along with a small quantity of  $\text{CaO}$  and trace amounts of  $\text{K}_2\text{O}$ ,  $\text{Fe}_2\text{O}_3$ ,  $\text{TiO}_2$ ,  $\text{P}_2\text{O}_5$ ,  $\text{Mn}_2\text{O}_3$  and  $\text{MgO}$ . The XRD analysis pattern refers to nearly crystalline of zeolite Y type, indicating the formation of zeolite NaY and HY.

## ACKNOWLEDGEMENTS

The author would like to express her gratitude to the management of Lafarge Cement Company Ewekoro Plant for their permission to carry out XRF and XRD analysis in their facility.

## REFERENCES

- [1] David, T. W., 2007, "Zeolites- earliest solids state acids," *AU J. Technol.*, 11(1) pp. 36- 41
- [2] Breck, D.W., 1975, "Zeolite Molecular Sieves: Structure, Chemistry, and uses" (Union Carbide Corporation, Tarrytown, New York) John Wiley and Sons, New York, London, Sydney and Toronto. *J. Chromatogr. Sci.*, 13 (4) pp. 18A.
- [3] Chandrasekhar, S., and Pramada, P.N., 1999, "Investigation on the Synthesis of Zeolite NaX from Kerala Kaolin," *J. Por. Mat.*, 6 (4) pp. 283-297.
- [4] Aderemi, B.O., "Preliminary Studies on Synthesis of Zeolites from Local Clay," 2004, *Nig. J. Sci. Res.*, 4(2), pp. 7-12.
- [5] Liu, X., Yan, Z., Wang, H., and Luo, Y., 2003, "In-situ Synthesis of NaY Zeolite with Coal-Based Kaolin". *J. Nat. Gas Chem.*, 12 pp. 63-70.
- [6] Babalola, R., Omoleye, J.A., Ajayi, O., Adefila, S.S., and Hymore, F. K., 2015, "Comparative Analysis of Zeolite Y from Nigerian Clay and Standard Grade", 2<sup>nd</sup> International Conference on African Development Issues (CU-ICADI), Materials Technology Track, pp. 179-182
- [7] Adeoye, J. B., and Omoleye, J. A., 2016, "Development of Zeolite Y from Arobieye Mined Kaolin" 3<sup>rd</sup> International Conference on African Development Issue (CU-ICADI), pp. 582-583.
- [8] Atta, A.Y., Ajayi, O.A., and Adefila, S.S., 2007, "Synthesis of Faujasite Zeolites from Kankara kaolin Clay", *J. App. Sci. Res.*, 3 (10) pp.1017-1021.
- [9] Kovo, A.S., 2010, "Development of Zeolites and Zeolite membrane from Ahoko Nigerian Kaolin", Ph.D. thesis, University of Manchester, UK.
- [10] Harry, R., 2001, "Verified synthesis of Zeolitic materials", Published on behalf of Synthesis Commission of the International Zeolite Association. Amsterdam: Elsevier, London New York.
- [11] Ginter, D.M., Bell A.T, Radke, C.J., 1992, "Synthesis of Microporous Materials", *Molecular Sieves (Synthesis of Microporous Materials)*, M. L. Occelli, H. E. Robson (eds.), Van Nostrand Reinhold, New York, (1) pp. 6.