



Title	Valleytronics: Magnetization without polarization
Author(s)	Yu, H; Yao, W
Citation	Nature Materials, 2017, v. 16 n. 9, p. 876-877
Issued Date	2017
URL	http://hdl.handle.net/10722/246102
Rights	This work is licensed under a Creative Commons Attribution-NonCommercial-NoDerivatives 4.0 International License.

Magnetization without polarization

A pure electrical generation of magnetization through electrons' valley magnetic moment has been observed in strained two-dimensional semiconductor.

Hongyi Yu and Wang Yao

In solids, the crystalline structure can endow electron a valley degree of freedom, which labels the degenerate energy minima in momentum space. The possibility for varieties of dynamic controls on valley has led to the concept of valleytronics¹, which aims at using valley, in addition to charge and spin, to carry and process information. Now, writing in *Nature Materials*, Jieun Lee and colleagues² have reported experimental evidences for a valley magnetoelectric effect in strained MoS₂ monolayer, where charge current generates bulk magnetization through valley. The finding implies a new possibility for integrating valleytronic controls with magnetic information storage.

MoS₂ is a member of the semiconducting transition metal dichalcogenides (TMD) family in which the monolayers all host similar valley physics³. Electrons and holes both have a pair of valleys centered at the K and -K corners of the hexagonal Brillouin zone. As a manifestation of the Berry phase of the electronic wave function⁴, carriers in a 2D hexagonal lattice acquire an orbital magnetic moment, which points out of the 2D plane in opposite directions at K valley and its time-reversal counterpart -K (Fig. 1a)^{5,6}. Such a magnetic moment signifies valley state of carrier, just like the one associated with spin, and thus makes possible interplay of valley with magnetism. Unlike the constant spin moment, the magnitude of the valley magnetic moment depends on carrier's momentum (Fig. 1a). This leads to a new way to link valley with magnetization.

As the analog of spin polarization, valley polarization refers to the population unbalance between the valleys (Fig. 1a). Through the valley magnetic moment arising from Berry phase effect, valley polarization leads to the magnetization of the material. Interestingly, in the absence of valley polarization, valley magnetization can still arise from the manipulation of carriers' momentum distribution as schematically depicted in Fig. 1b, because valley magnetic moment has the momentum dependence. Lee and co-workers demonstrated one such possibility from the joint effect of current and strain².

The three-fold rotational symmetry of the MoS₂ hexagonal lattice requires the valley moment distribution to have its maxima at the valley center (Fig. 1a). When strain breaks this rotational symmetry, the distribution of valley magnetic moment is displaced in momentum space with respect to the valley centers⁷, while time reversal symmetry dictates the displacement at K valley is opposite to that at -K (Fig. 1b). In a charge current, the Fermi pockets at K and -K, both shifted along the current direction (c.f. solid circles in Fig. 1b), can enclose different amount of magnetic moment. A net magnetization is thus associated with this nonequilibrium distribution even though the population remains balanced between the two valleys. This magnetization is linearly proportional to the charge current projection along the displacement of valley magnetic moment distribution by strain (\mathbf{k}_0 in Fig. 1b).

In the experiments, valley magnetization of either type, from valley polarization or without valley polarization, can be detected using the Kerr rotation microscopy, a standard technique to image spin magnetization. It works equally well for valley magnetization, thanks to the intrinsic connection of valley magnetic moment to circular dichroism⁶ that underlies Kerr rotation, a change in light polarization upon reflection. In an earlier work from the same group⁸, Kerr rotation microscopy was used to image the valley polarization accumulated at the edges of bilayer MoS₂ by the valley Hall current, the latter being another manifestation⁵ of the Berry phase effect that has led to valley

magnetic moment. In the work by Lee and colleagues², the valley Hall effect in monolayer MoS₂ is also evidenced by the opposite Kerr rotation signal at the two edges. The new finding here is a much stronger Kerr rotation signal observed nearly uniformly over the entire monolayer bulk when, and only when current and strain are both present as shown in Fig. 1c. They examined the dependences of the Kerr rotation angle on the magnitude of bias current, and on the current and strain directions with respect to the crystalline axis², which consistently point to the valley magnetization in the valley-unpolarized nonequilibrium momentum distribution.

It is worth pointing out that the two types of valley magnetization have distinct relaxation dynamics. The one associated with valley polarization decays through the intervalley scattering (Fig. 1a), which is typically slow due to the large separation of valleys in momentum space. The magnetization without valley polarization decays through the much faster intravalley momentum relaxation (Fig. 1b), and disappears instantaneously when charge current is switched off. Nevertheless, this magnetoelectric effect that is shown to persist at room temperature provides a practical mechanism for charge-magnetization conversion in valleytronic devices. One can envision van der Waals heterostructure devices composed of semiconducting TMD monolayer and ferromagnetic monolayer such as CrI₃⁹, where the lateral current flow in TMD channel can exert a torque, via the induced valley magnetization, to switch the proximity ferromagnetic layer in magnetic memories.

Hongyi Yu and Wang Yao are at the Department of Physics and Center of Theoretical and Computational Physics, The University of Hong Kong, Hong Kong, China.

e-mails: yuhongyi@hku.hk and wangyao@hku.hk

References:

- [1] Schaibley, J., Yu, H., Clark, G., Rivera, P., Ross, J., Seyler, K., Yao, W. & Xu, X., Valleytronics in 2D materials. *Nature Reviews Materials* 1, 16055 (2016).
- [2] Lee, J., Wang, Z., Xie, H., Mak, K. F., & Shan, J. Valley Magnetoelectricity in Single-Layer MoS₂. *Nat. Mater.*, in press.
- [3] Xiao, D., Liu, G.-B., Feng, W., Xu, X., & Yao, W., Coupled spin and valley physics in monolayers of MoS₂ and other group VI dichalcogenides. *Phys. Rev. Lett.* 108, 196802 (2012).
- [4] Chang, M.-C. & Niu, Q., Berry phase, hyperorbits, and the Hofstadter spectrum: Semiclassical dynamics in magnetic Bloch bands, *Phys. Rev. B* 53, 7010 (1996).
- [5] Xiao, D., Yao, W. & Niu, Q., Valley Contrasting Physics in Graphene: Magnetic Moment and Topological Transport, *Phys. Rev. Lett.* 99, 236809 (2007).
- [6] Yao, W., Xiao, D. & Niu, Q., Valley-dependent Optoelectronics from Inversion Symmetry Breaking, *Phys. Rev. B* 77, 235406 (2008).
- [7] Rostami, H., Roldán, R., Cappelluti, E., Asgari, R. & Guinea, F., Theory of strain in single-layer transition metal dichalcogenides, *Phys. Rev. B* 92, 195402 (2015).
- [8] Lee, J., Mak, K. F. & Shan, J., Electrical control of the valley Hall effect in bilayer MoS₂ transistors, *Nat. Nanotechnol.* 11, 421-425 (2016).
- [9] Zhong, D. et al., Van der Waals engineering of ferromagnetic semiconductor heterostructures for spin and valleytronics, *Science Advances* 3, e1603113 (2017).

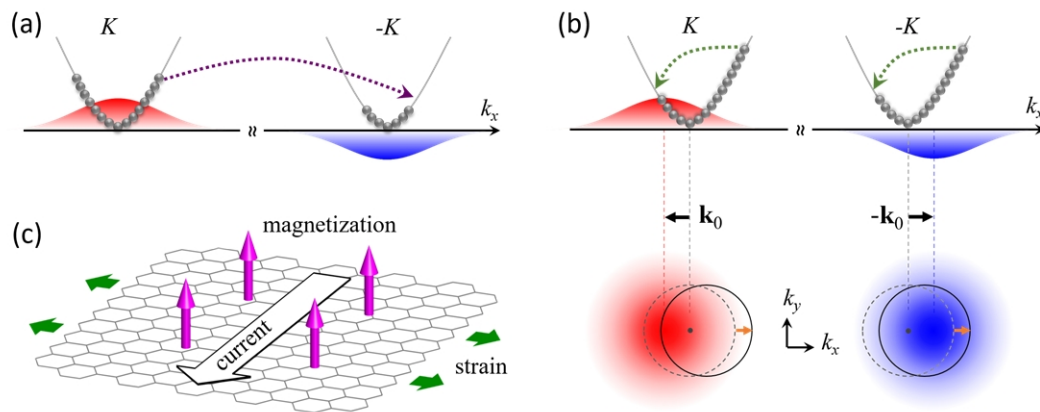


Figure 1 Magnetization with and without valley polarization. **a**, Magnetization from valley polarization. Shaded curve denotes the distribution of valley magnetic moment as a function of momentum. **b**, Magnetization without valley polarization. The distribution of valley magnetic moment has a displacement \mathbf{k}_0 ($-\mathbf{k}_0$) from the valley center at K ($-K$), due to strain. In equilibrium, the magnetization remains zero as the Fermi pockets at K and $-K$ (dashed circles) enclose the same amount of magnetic moment with opposite sign. In a charge current, the shifted Fermi pockets (solid circles) enclose different amount of magnetic moment at the two valleys, giving rise to a net magnetization. The two types of valley magnetization in **a** and **b** decay through intervalley and intravalley scattering respectively (dotted arrows). **c**. Schematic of current induced valley magnetization in the strained monolayer.