
# **NASA TECH BRIEF**

# NASA Headquarters



NASA Tech Briefs announce new technology derived from the U.S. space program. They are issued to encourage commercial application. Tech Briefs are available on a subscription basis from the National Technical Information Service, Springfield, Virginia 22151. Requests for individual copies or questions relating to the Tech Brief program may be directed to the Technology Utilization Office, NASA, Code KT, Washington, D.C. 20546.

# **Humidity Resistant Solar Cell Contacts**

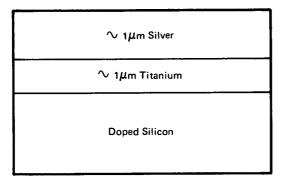

Present Solar-Cell Contact

## The problem:

The present silver-titanium solar-cell contacts are protected with solder to avoid damage in humid environments. To decrease weight, solderless silver-titanium contacts were tried, but they degraded in humid environments.

## The solution:

A gold-platinum contact was developed, as shown in the figure, which does not exhibit the chemical reactivity of titanium or the porosity of silver. This contact offers excellent ohmic characteristics and stability in humid air.

### How it's done:

Approximately 0.1  $\mu$ m of platinum is sputtered onto the doped silicon layer. The assembly is sintered in vacuum to form a platinum-silicide ohmic contact which has a good mechanical adhesion to silicon. Afterwards,

1 to 3 μm Gold
$\sim$ 0.1 $\mu$ m Platinum
Doped Silicon

Proposed Solar-Cell Contact

1 to 3 µm of gold is evaporated or electroplated onto the platinum to form the finished contact.

#### Note:

Requests for further information may be directed to: Technology Utilization Officer NASA Headquarters Code KT Washington, D.C. 20546 Reference: B72-10517

### Patent status:

No patent action is contemplated by NASA.

Source: C. J. Bishop of Boeing Corp. under contract to NASA Headquarters (HQN-10674)

Category 04