


NASA/TM-2005-213765

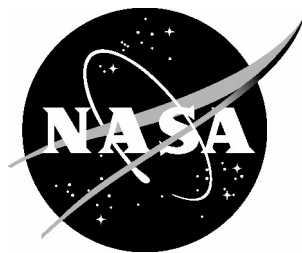

Test and Analysis of a Hyper-X Carbon-Carbon Leading Edge Chine

*Russell W. Smith, Joseph G. Sikora, and Michael C. Lindell
Langley Research Center, Hampton, Virginia*

May 2005

The NASA STI Program Office . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the lead center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counterpart of peer-reviewed formal professional papers, but having less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.


- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or co-sponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that complement the STI Program Office's diverse offerings include creating custom thesauri, building customized databases, organizing and publishing research results ... even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at <http://www.sti.nasa.gov>
- E-mail your question via the Internet to help@sti.nasa.gov
- Fax your question to the NASA STI Help Desk at (301) 621-0134
- Phone the NASA STI Help Desk at (301) 621-0390
- Write to:
NASA STI Help Desk
NASA Center for AeroSpace Information
7121 Standard Drive
Hanover, MD 21076-1320

NASA/TM-2005-213765

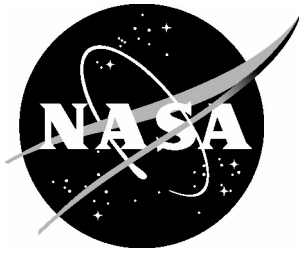

Test and Analysis of a Hyper-X Carbon-Carbon Leading Edge Chine

*Russell W. Smith, Joseph G. Sikora, and Michael C. Lindell
Langley Research Center, Hampton, Virginia*

National Aeronautics and
Space Administration

Langley Research Center
Hampton, Virginia 23681-2199

May 2005

The use of trademarks or names of manufacturers in the report is for accurate reporting and does not constitute an official endorsement, either expressed or implied, of such products or manufacturers by the National Aeronautics and Space Administration.

Available from:

NASA Center for AeroSpace Information (CASI)
7121 Standard Drive
Hanover, MD 21076-1320
(301) 621-0390

National Technical Information Service (NTIS)
5285 Port Royal Road
Springfield, VA 22161-2171
(703) 605-6000

Abstract

During parts production for the X43A Mach 10 hypersonic vehicle nondestructive evaluation (NDE) of a leading edge chine detected an imbedded delamination near the lower surface of the part. An ultimate proof test was conducted to verify the ultimate strength of this leading edge chine part. The ultimate proof test setup used a pressure bladder design to impose a uniform distributed pressure field over the bi-planar surface of the chine test article. A detailed description of the chine test article and experimental test set-up is presented. Analysis results from a linear static model of the test article are also presented and discussed. Post test inspection of the specimen revealed no visible failures or areas of delamination.

Introduction

The Hyper-X flight demonstrator program represents NASA's state of the art in hypersonic flight vehicles and technology. In addition to having SCRAM type engines (ref. 1) versus the more traditional RAM engines in a Mach regime of 7-10, the X43A also has Carbon-Carbon (C-C) leading edge sections to withstand peak heating conditions and flight pressure loads. Due to concerns over subsurface density variations, evidenced in a prototype leading edge chine that had delaminated near the surface, it was decided that an ultimate proof test was warranted to further evaluate the load carrying capability of the part. Additionally, due to the tight schedule required to accomplish the ultimate proof test, the concept of a pressurized bladder for load introduction was designed and implemented. This paper discusses the leading edge chine design and mission profile, the test article and test set-up, as well as the analytical and experimental results.

Mission Profile and Thermo-mechanical Loading

An artist's conceptual portrayal of the X43A vehicle in flight with the vehicle's projected flight profile is shown in Figure 1. During the ascent portion of the flight at Mach 2.8 and near maximum dynamic pressure (max-q) flight loads, an average worst case calculated flight load pressure of 1.13 psi over the leading edge chine section was determined. Figure 2 shows various views of the vehicle with the C-C leading edge area at the perimeter of the nose section (ref. 2). Peak heating flight data, for the second Mach 7 flight, indicated temperatures limited to the 1600°F-1800°F region (ref. 2). During the third and final Mach 10 flight, temperatures in the chine area were expected to be in the 2000°F range and above. The envisioned thermal environment in flight was not considered an issue for the cantilever chine section's structural response. Carbon-Carbon type materials tend to have increasing strength levels well into the 2000°F temperature range, and hence, a room temperature proof test was deemed conservative. The projected total limit load on the flight section was calculated to be 50 lb.; thus, with a Factor of Safety (FS) of 2.0 the total target ultimate load was determined to be 100 lb.

Test Specimen

The C-C chine test article section is shown in Figure 3 and consists of a bi-planar and curved contour surface that is 3 in. wide by 16 in. long and has a tapering thickness. The pressurized specimen area consists of a 3 in. wide flat at the thicker aft end of the specimen (Figure 3B), a nominal 16 in. length, and towards the thinned down forward section (Figure 3C) two planar areas with a combined planar dimension of approximately 3.25 in. Also shown in Figure 3 is a mounting flange area, 1 in. wide by 0.25 in. thick, that when attached to the flight vehicle forms a cantilever beam supported structure.

Load Introduction Pressure Bladder and Test Fixture Description

The concept behind the ultimate proof load test rig is that of a pressurized bladder or conformal pressure vessel. Since static pressurization within a cavity acts normal to the surface of the cavity the bladder concept allows for a simple, uniform distributed pressure load application. A sectional side view of the test fixture is shown in Figure 4 with the reactive/supportive test fixture wall sections. Also shown in Figure 4, is the 0.030 in. worst case gap offset which could result when the chine section is mounted to the supporting side walls of the X43A vehicle. Incorporating the gap offset allowed the chine test article to rotate in a manner representative of actual vehicle boundary conditions. The minimization of this gap would create an interface (with the supporting side-wall) which could serve to artificially stiffen the edge boundary conditions.

An isometric backside view of the aluminum test fixture is shown in Figure 5 with end sections and a spacer plate. Initially the pressure bladder was to be truncated by the end sections as shown in Figure 5, but during the test setup it was easier and more expedient, to have the end close out sections removed. This effectively eliminated all of the issues of how the bladder would deform onto the specimen in the close-out area, and the concern of possible perforation of the bladder. The spacer plate section, located at the rear of the fixture, allows for clamping of the fixture to the same thickness level as the C-C mounting flange preventing possible excessive compressive loads in the specimen flange area.

Test Sequence

During test set-up a reference load plate of 46 sq. in. was used to calibrate the desired final load based on the pressure input to the bladder (Figure 6). To achieve the 100 lb ultimate load, force would be equal to pressure multiplied by area (or $F = PA$). Therefore a pressure value of 2.2 psi based upon the reference load plate of 46 sq. in. would result in a load of 101 lb. However, due to the bi-planar contoured nature of the pressurized surface (Figure 3A), the actual pressurized area of the specimen was slightly larger than the 46 sq. in. used during the calibration process. Triangular and quadrilateral area calculations of the specimen top surface yielded a value of 48.9 sq. in., and two graphical area assessments yielded values of 48.6 sq. in. and 49.3 sq. in., respectively. An average of the three area measurements gives a value of 48.9 sq. in. Therefore, the final load applied to the cantilever section was equal to the ratio of the actual area divided by the reference area, which effectively becomes a scaling coefficient (or corrective coefficient) on the actual applied load. Therefore, the actual total load equals $(48.9/46) \times 100 \text{ lb} = 106.3 \text{ lb}$ total force applied to the specimen.

Figure 7 shows the X43A Carbon-Carbon chine specimen mounted in the test fixture for pressure testing. The required minimum load duration was determined to be 130 seconds (ref. 3). Shop air and a hand controlled pressure valve were used to implement the pressurization loads. The load sequence consisted of a 4 minute ramp to the target pressure, a 130 second hold period and then a subsequent rapid release of the pressure load over a 5 second interval.

Analysis

The finite element model (FEM) used for analysis of the X43A C-C chine section is shown in Figure 8. The model consists of 143,816 solid elements (8-noded brick and 6-noded wedge elements) utilizing the MSC NASTRAN (ref. 4) FEM code for analysis with MSC PATRAN (ref. 5) utilized as the pre, and post, processing software. The limit pressure load on the chine, from launch through the engine test, occurs during the ascent phase near the time of max q. A 1.13 psi uniform pressure distribution across the chine is a conservative approximation of the calculated aerodynamic pressure distribution. A 2.0 FS was applied to the limit pressure with the resulting load shown in Figure 8B.

As shown in Figure 9, stress contour plots for the chine section are given for two different imposed boundary conditions. Figure 9A shows the bending stress results due to the mounting flange (fig. 3) being fixed halfway across the width of the mounting flange tab resulting in a localized peak stress of 1260 psi. As shown in Figure 9B, a support condition fixed at a distance of 0.083 in. away from the thicker section shows peak stresses at the tab cross section of 583 psi. Hence, the stress result case, as shown in Figure 9A, is conservative, and stress values are reduced as the FEM boundary condition is fixed as close as possible to the chine/chine tab interface section. The C-C chine material has an expected failure strength in excess of 5000 psi. Therefore the part has an ample margin of safety (MS) during the ascent portion of the flight at Mach 2.8 and near max-q flight loads.

Post Test Inspection

After completion of the test sequence the specimen was visually inspected. Neither delaminations nor failure areas were evidenced. Additionally, there were no audible indications of specimen failure during the test as well.

Concluding Remarks

The pressure bladder load introduction concept performed very well. This approach provided a quick, simple, and efficient method of applying a uniform pressure field onto a bi-planar contoured specimen surface.

The potential of the pressure bladder load introduction concept for broad application in thermo-mechanical testing of structures would require experimentation in various thermal environments and on various test specimen geometries. Test specimen geometries could range from one such as that reported in this paper (a single bi-planar surface with no built up features) to geometries as complex as highly built-up integrated vehicle structures.


Acknowledgements

The authors wish to gratefully acknowledge the contributions of the following individuals in support of this research effort:


Dr. Max Blosser and Dr. Steve Scotti of the Metals and Thermal Structures Branch (MTSB) for their insight into thermo-structural testing as well as the graphic designers at the Dryden Flight Research Center for their excellent web-site graphics which are reproduced herein.

References

1. Huebner, Lawrence D.; Rock, Kenneth E.; Witte, David W.; Ruf, Edward G.; and Andrews, Earl H.: **Hyper-X Engine Testing in the NASA Langley 8-Foot High Temperature Tunnel** , *36th AIAA/ASME/SAE/ASEE Joint Propulsion Conference and Exhibit*, Huntsville, Alabama, AIAA 2000-3605, July 17-19, 2000, pp. 13.
2. Amundsen, Ruth M.; Leonard, Charles P.; and Bruce, Walter E. III.: **Hyper-X Hot Structures Comparison of Thermal Analysis and Flight Data**, *15th Thermal and Fluids Analysis Workshop (TFAWS)*, Pasadena, California , August 30 - September 3, 2004.
3. Ohlhorst, C. W.; Vaughn, W.L.; Lewis, R.K.; and Milhoan, J.D.: **Arc Jet Results on Candidate High Temperature Coatings for NASA's NGLT Refractory Composite Leading Edge Task** , *JANNAF 39th CS/27th APS/21st PSHS/3rd MSS Joint Subcommittee Meeting*, Colorado Springs, Colorado, December 1-5, 2003.
4. Kilroy, K., MSC/NASTRAN, Quick Reference Guide, The MacNeal-Schwendler Corporation, June 1997.
5. MSC/PATRAN User Manual, MacNeal-Schwendler Corporation. Version 2000 (r2). August 2000.

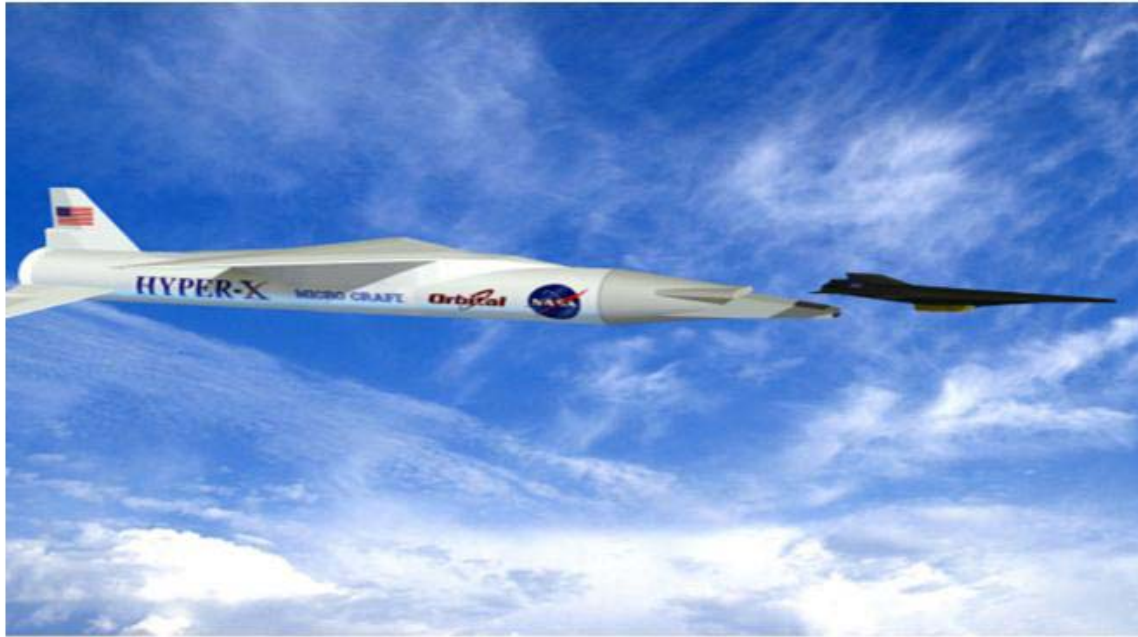

(A)

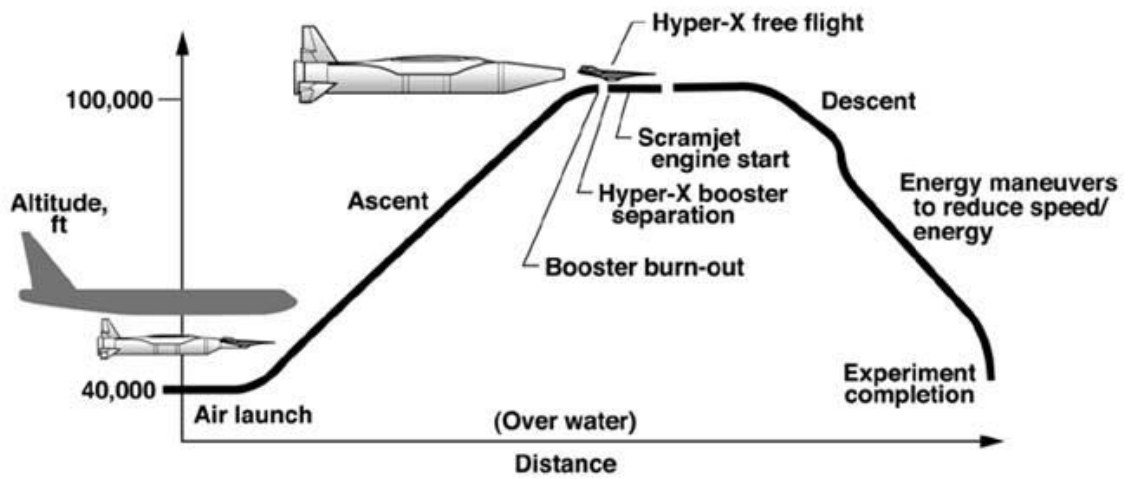

(B)

Figure 1: Hyper-X In-flight (artist's portrayal) and Flight Profile.
(<http://www.dfrc.nasa.gov/gallery/graphics/index.html>)


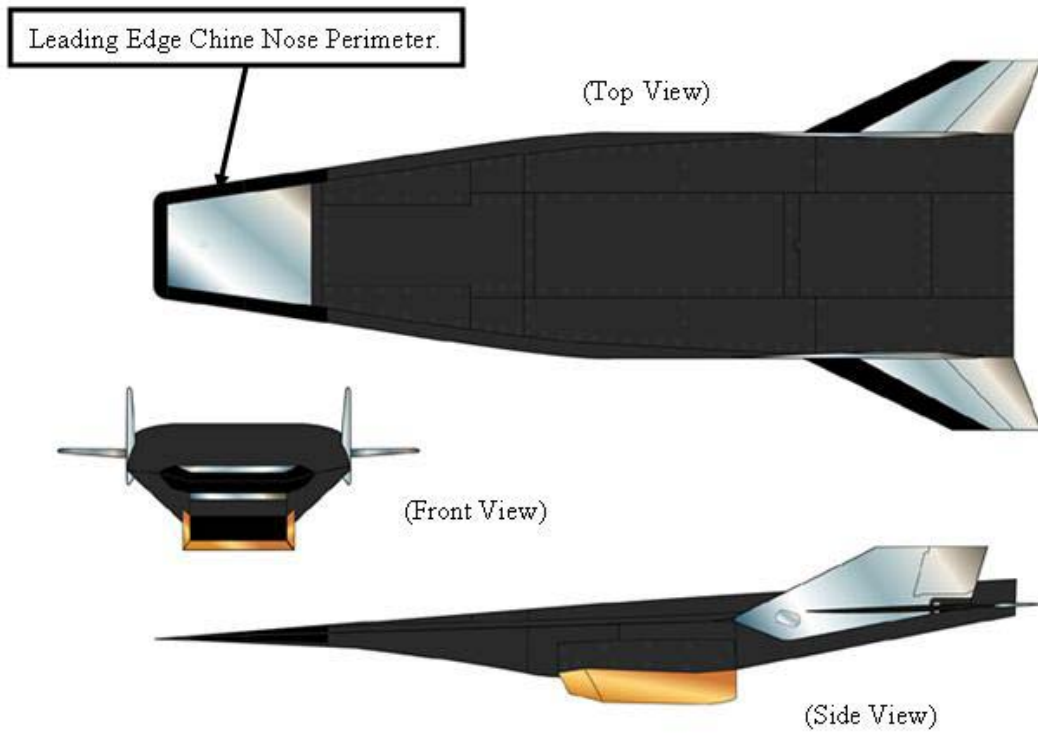



Figure 2: Various Views of X43A Flight Vehicle with Leading Edge Nose Perimeter.
(<http://www.dfrc.nasa.gov/gallery/graphics/index.html>)

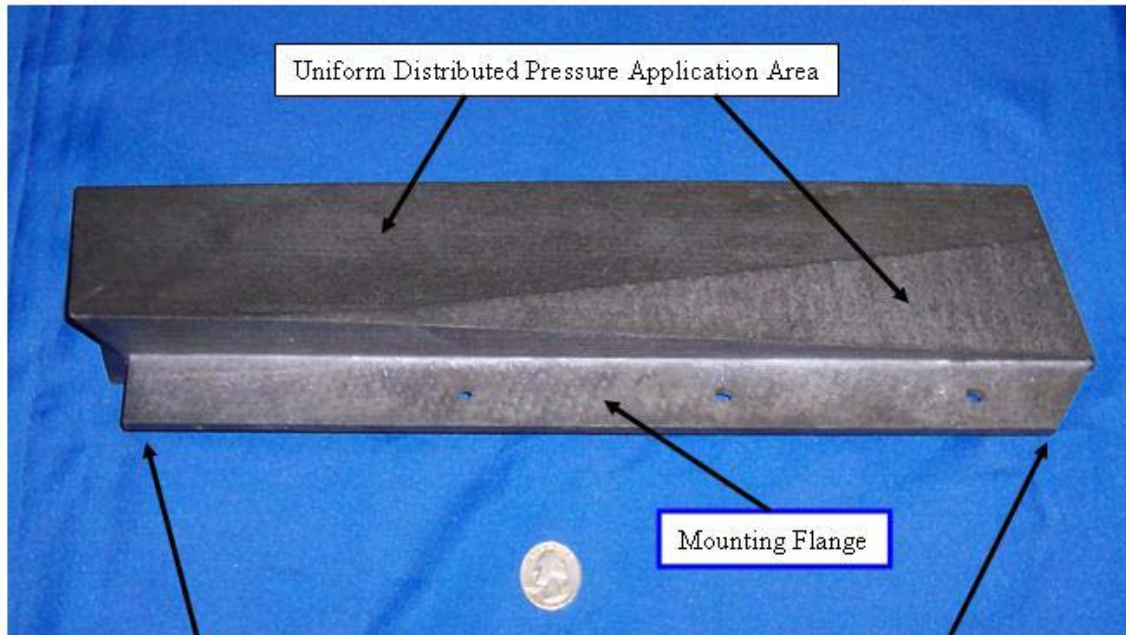

(A)

Aft, Thicker Cross Section

Forward, Thinner Cross Section

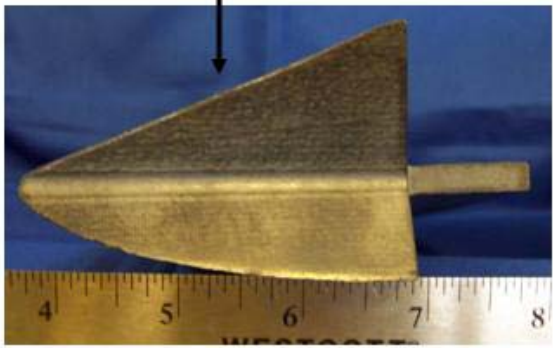

(B)



(C)

Figure 3: X43A Carbon-Carbon Leading Edge Chine as Tested.

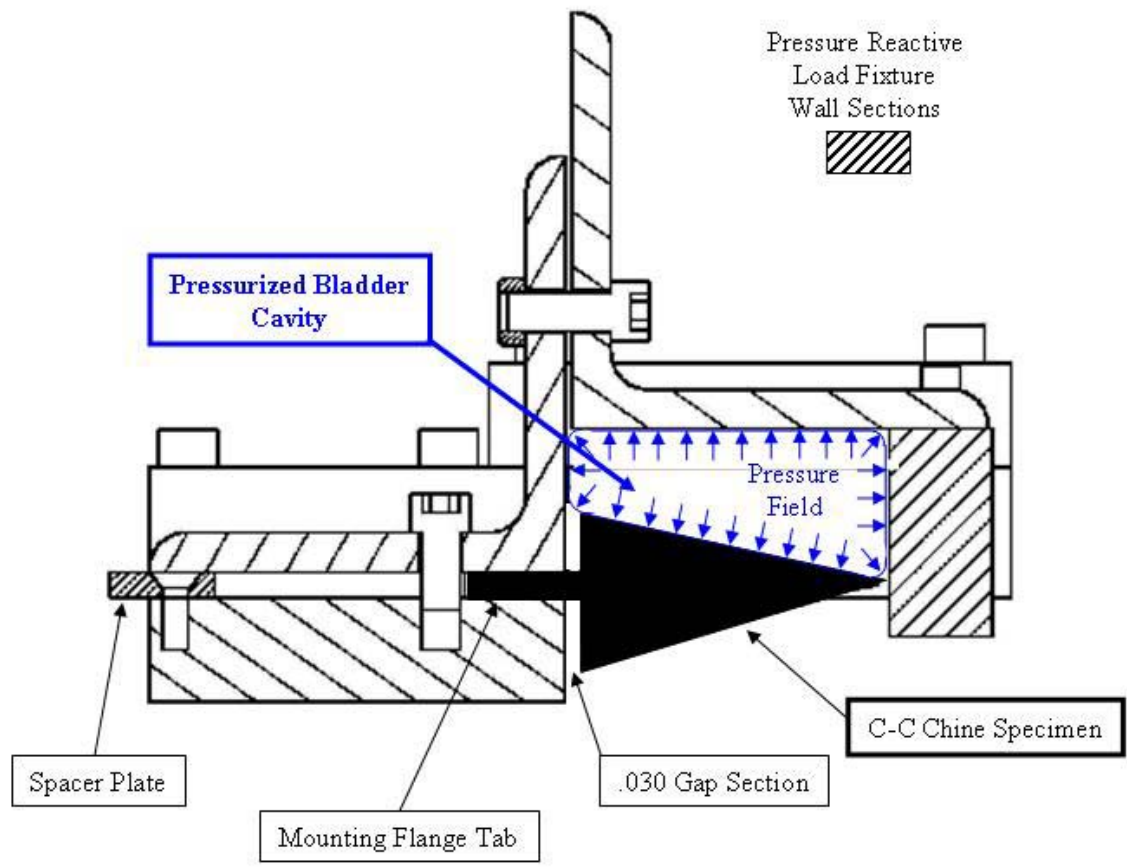


Figure 4: X43A Section Side View of Pressure Reactive Test Fixture.

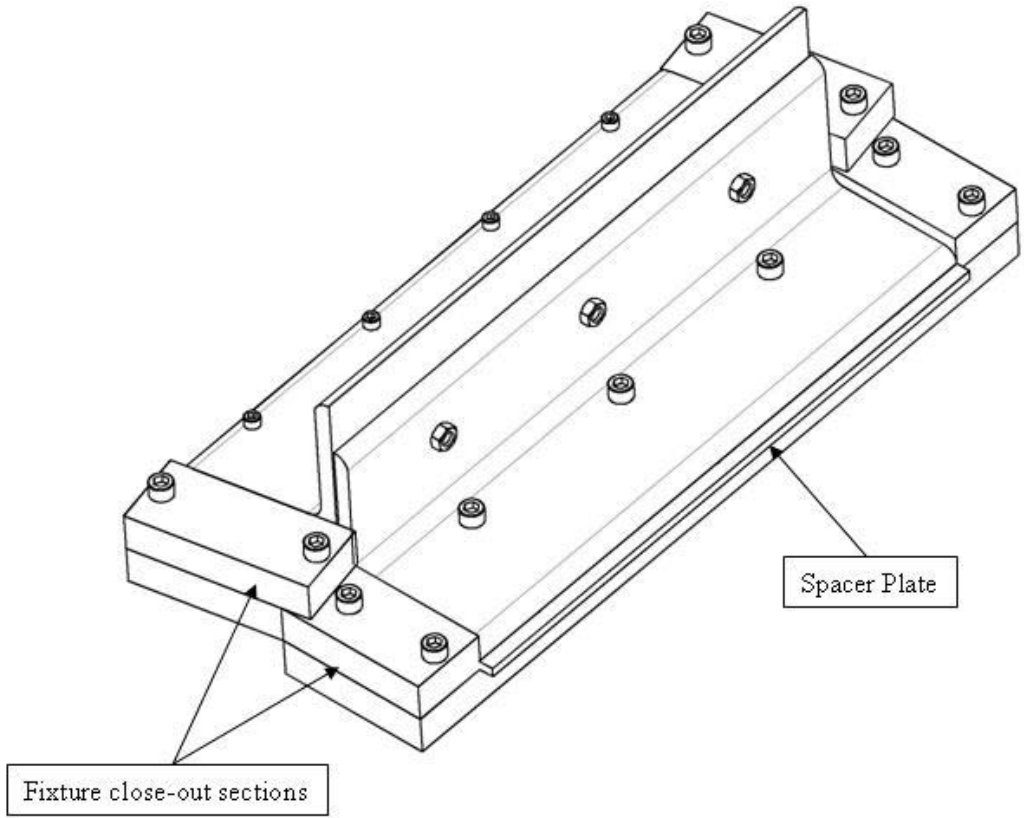


Figure 5: Isometric Backside View of Pressure Reactive Test Fixture.

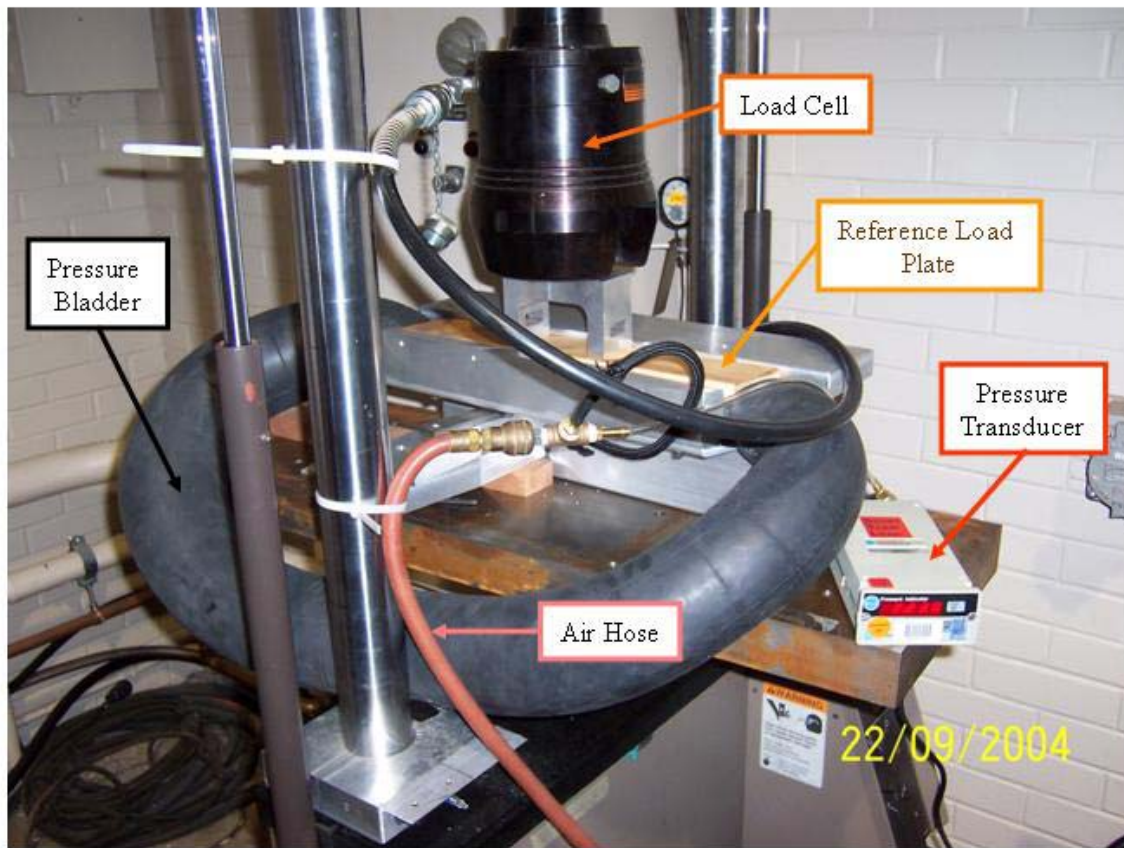


Figure 6: Calibration of Test Fixture Prior to Testing.




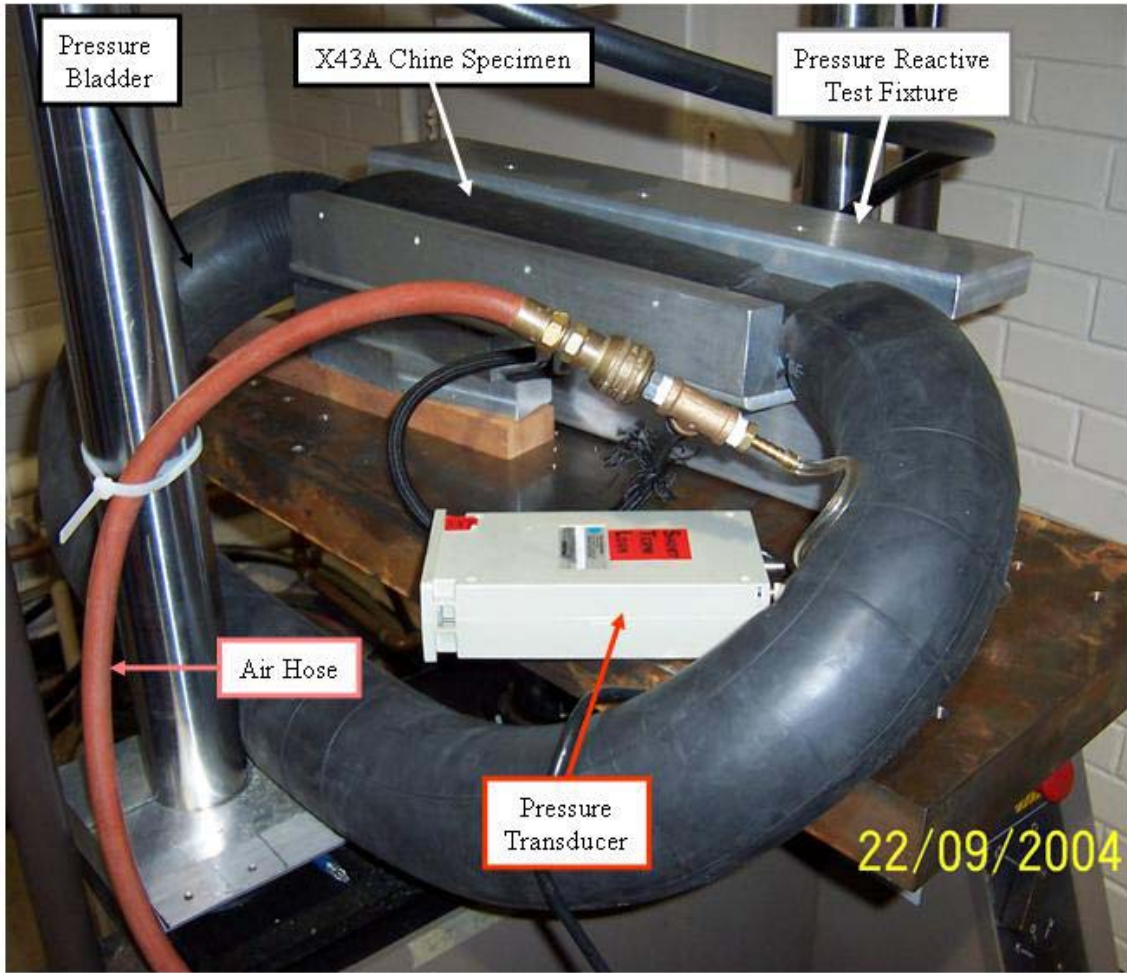


Figure 7: X43A Chine During Ultimate Proof Load Test.

**Hyper-X Nose Fwd Side Chine
Finite Element Model for Load Test**

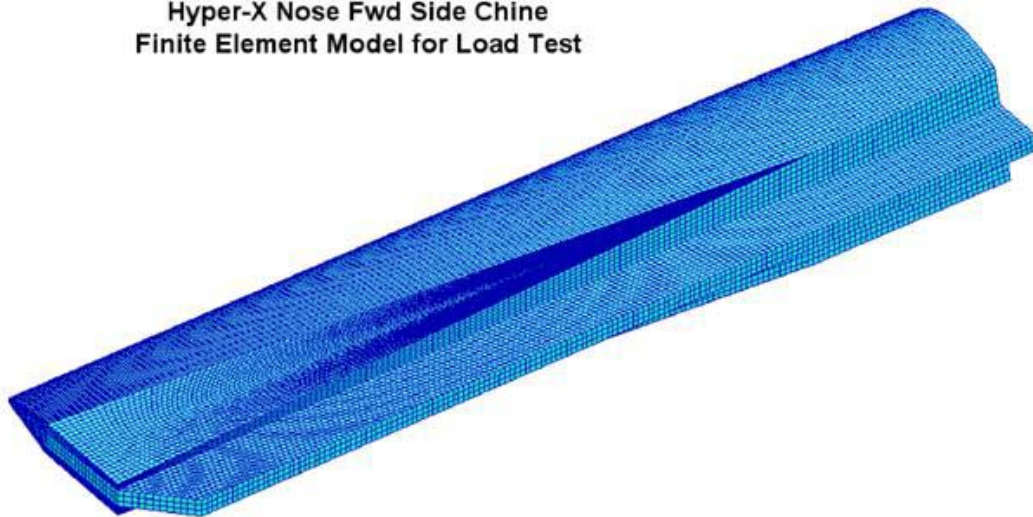


(A)

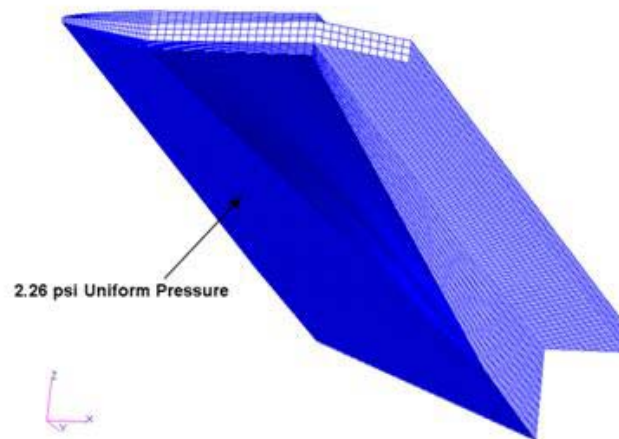

(B)


Figure 8: Finite Element Model of Carbon-Carbon Chine Showing Mesh & Elements.

MSC Patran 2004 r2 13-Oct-04 10:01:56
Peak Bending Stresses Due to Pressure Load (psi)

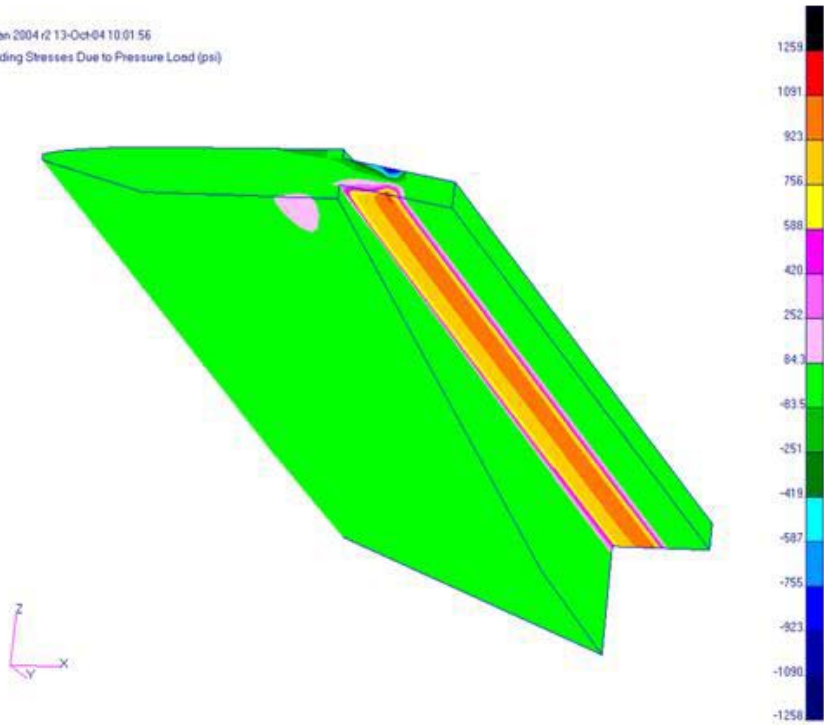

(A)

MSC Patran 2005 24-Nov-04 10:24:45
Peak Bending Stresses Due to Pressure Load (psi)

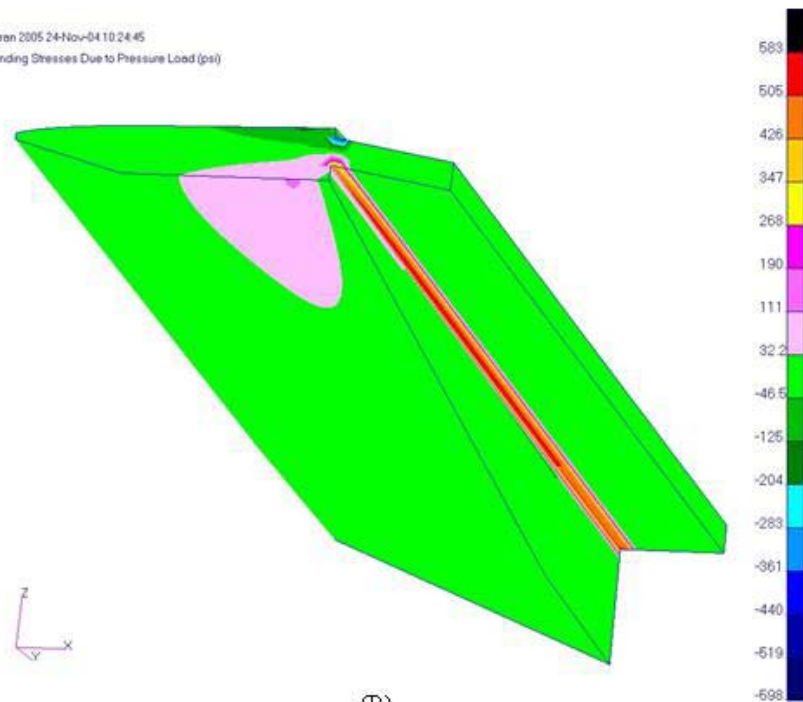

(B)

Figure 9: FEA Stress Contour Plots for C-C Chine.

REPORT DOCUMENTATION PAGE

*Form Approved
OMB No. 0704-0188*

The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.
PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.

1. REPORT DATE (DD-MM-YYYY) 01- 05 - 2005		2. REPORT TYPE Technical Memorandum		3. DATES COVERED (From - To)	
4. TITLE AND SUBTITLE Test and Analysis of a Hyper-X Carbon-Carbon Leading Edge Chine				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Smith, Russell W.; Sikora, Joseph G.; and Lindell, Michael C.				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER 23-376-70-30-04	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) NASA Langley Research Center Hampton, VA 23681-2199				8. PERFORMING ORGANIZATION REPORT NUMBER L-19133	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001				10. SPONSOR/MONITOR'S ACRONYM(S) NASA	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S) NASA/TM-2005-213765	
12. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Category 03 Availability: NASA CASI (301) 621-0390					
13. SUPPLEMENTARY NOTES An electronic version can be found at http://ntrs.nasa.gov					
14. ABSTRACT During parts production for the X43A Mach 10 hypersonic vehicle nondestructive evaluation (NDE) of a leading edge chine detected on imbedded delamination near the lower surface of the part. An ultimate proof test was conducted to verify the ultimate strength of this leading edge chine part. The ultimate proof test setup used a pressure bladder design to impose a uniform distributed pressure field over the bi-planar surface of the chine test article. A detailed description of the chine test article and experimental test setup is presented. Analysis results from a linear status model of the test article are also presented and discussed. Post-test inspection of the specimen revealed no visible failures or areas of delamination.					
15. SUBJECT TERMS Hypersonic; Leading edge chine; Nondestructive evaluation; X43A; Mach 10					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT	b. ABSTRACT	c. THIS PAGE			STI Help Desk (email: help@sti.nasa.gov)
U	U	U	UU	18	19b. TELEPHONE NUMBER (Include area code) (301) 621-0390