



Ceramic Spheres Derived From Cation Exchange Beads

Fred Dynys


National Aeronautics & Space Administration

Glenn Research Center

Sponsored: Ultra Efficient Engine Technology (UEET)



Thermal Barrier Coating

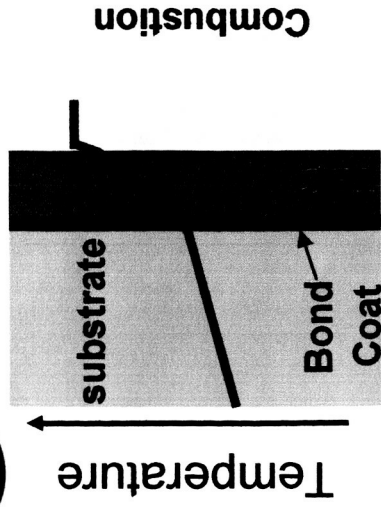

Benefits:

- Reduce Substrate Temp. (150° F to 325° F)
- Increase Combustion Temp.
- Increase part life
- Environmental Protection
- Increase efficiency


Ultra Efficient Engine Technology (UEET)

- Reduce CO₂/NO_x emission by increasing engine operating temperature → 3000 °F (1649 °C)

Radiation Barrier Coating

- Porous Coating to Reduce Photon Conduction
- Max. Scattering -Pores → 1-4 μm
- Hollow/Porous Ceramic Spheres

Blackbody

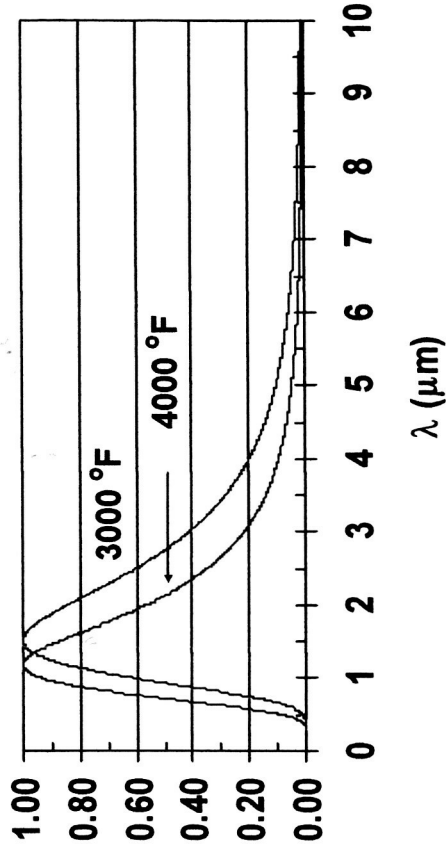



Objective

Establish a simple templating process to produce hollow ceramic spheres with a pore size 1 to 10 μm .


Template – Cation exchange beads -Polystyrene based polymer

Oxide – ZrO_2 , $\text{Y}_3\text{Al}_5\text{O}_{12}$




Templating


A. Ion Exchange Reaction
Aqueous Solution

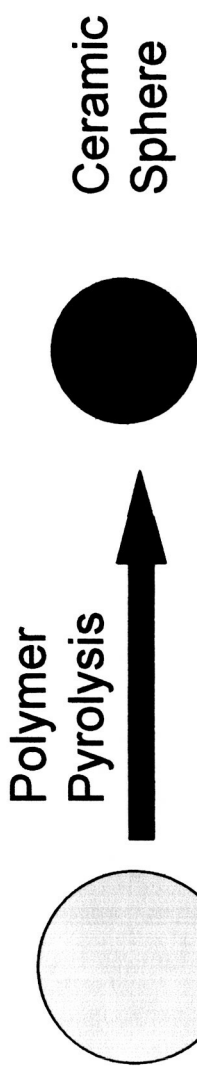

B. Coat Sphere Surface
 $M(OR)_n + H_2O$

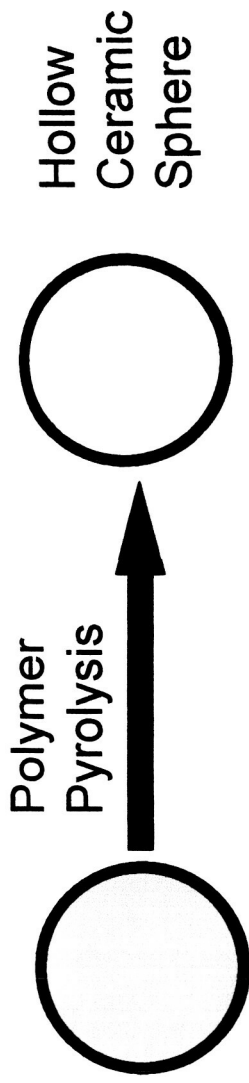


C. Composite Sphere
Methods A & B



- Optical Applications
- Environmental Coatings



Organic Cation Exchange Resin

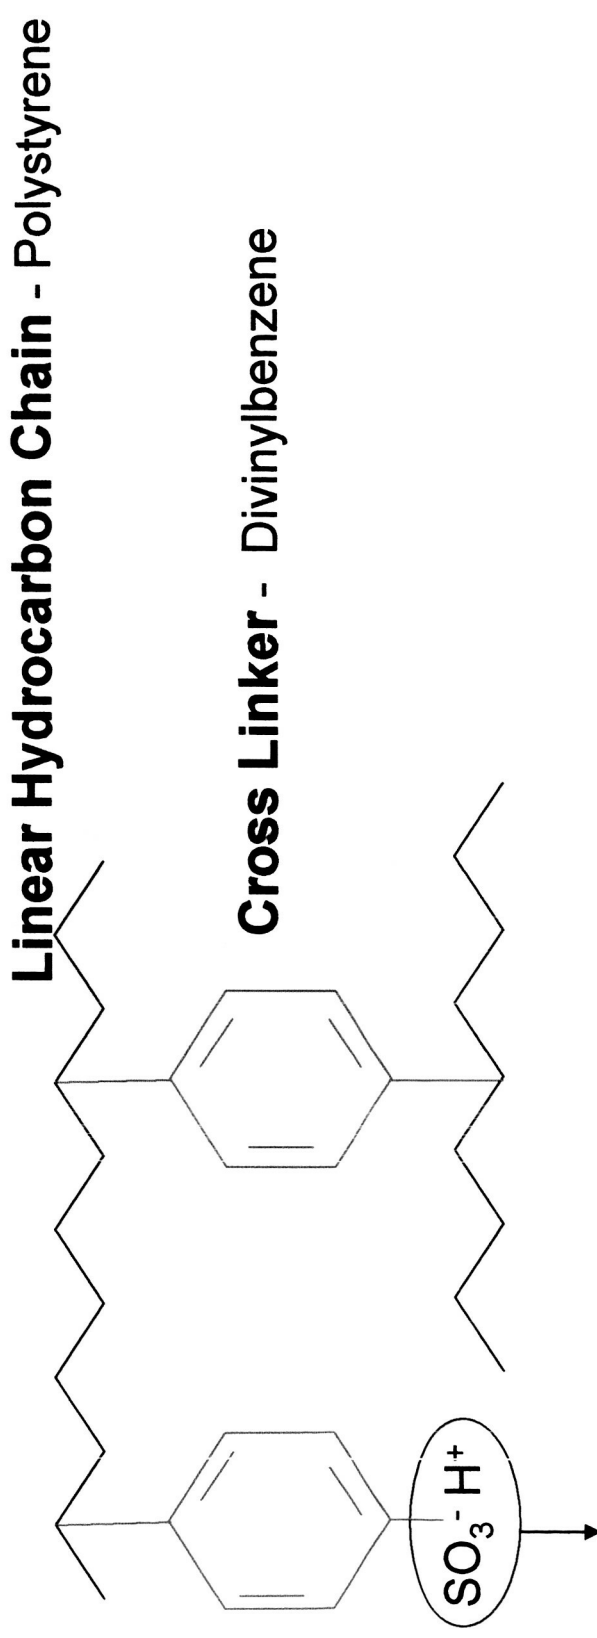

Functional Groups – SO_3^- , COO^- , PO_3^{-2} , AsO_3^{-2} , SeO_3^-

Cross Linking

- Swelling
- Regulates Pore Size – Ion Mobility
- Randomness in crosslinking produces disordered structure



Ion Exchange



General Remarks

- Reversible Reaction
- Maintain Charge Neutrally
- pH Independent - Strong Acid Functional Group – SO_3^-
- pH dependent - Weak Acid Functional Group – COO^-
- Number of groups determined exchange capacity equivalents/volume
- Cation Selective
Valence – $\text{M}^{+3} > \text{M}^{+2} > \text{M}^{+1}$
 $\text{Ba}^{+2} > \text{Pb}^{+2} > \text{Sr}^{+2} > \text{Ca}^{+2} > \text{Ni}^{+2} > \text{Cd}^{+2} > \text{Cu}^{+2} > \text{Zn}^{+2} > \text{Mg}^{+2} > \text{UO}_2^{+2}$



Procedure - Ion Exchange

1. 0.1-0.3 M Salt Solution – $ZrOCl_2$, $MgCl_2$, $AlCl_3$

2. Dowex 50x4 Beads - SO_3^-

3. Ion Exchange Time ≥ 18 Hrs.

4. Liquid/Solid Separation


5. Wash

6. Calcination

1. Single Step $\rightarrow \geq 6^\circ C/min - 600-900^\circ C - Air$

2. Double Step $\rightarrow 800-1000^\circ C - Inert$


$\rightarrow \geq 6^\circ C/min - 800-1000^\circ C - Air$

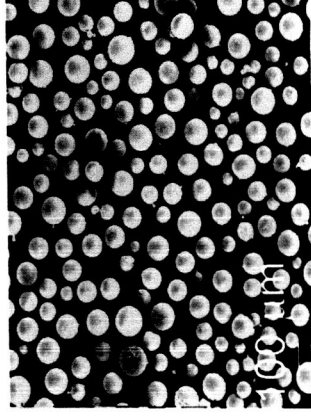







Process Variables

- Calcination Heating Rate $< 6^{\circ}\text{C}/\text{min}$
 - Ion Exchange Time < 18 Hrs.
- ↑**
- Defective Spheres**

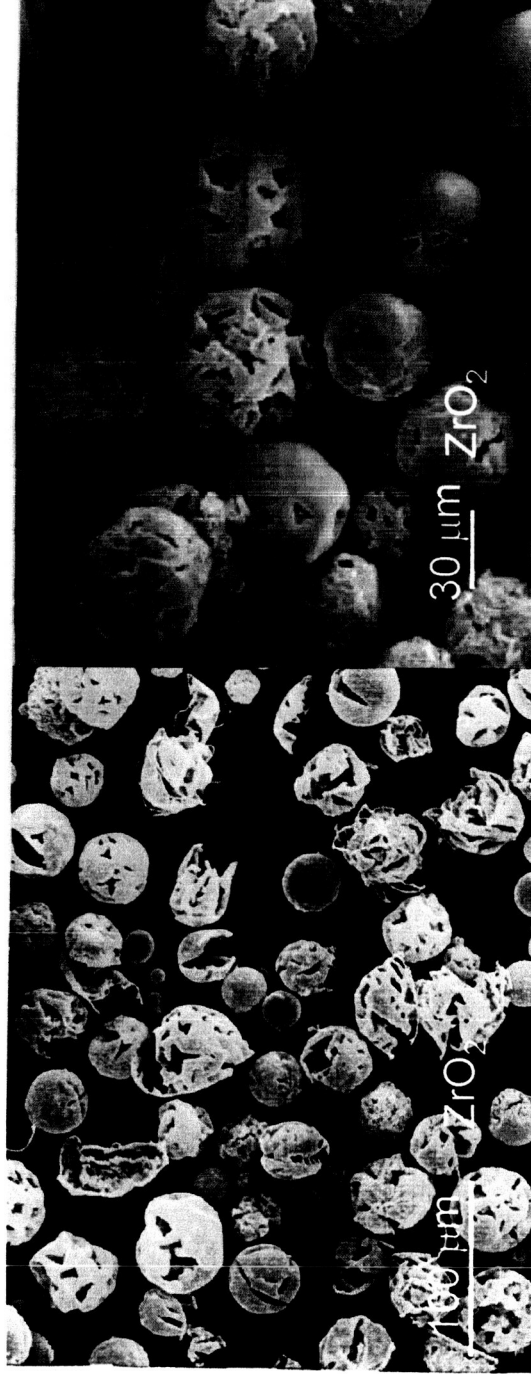







Single Step Calcination

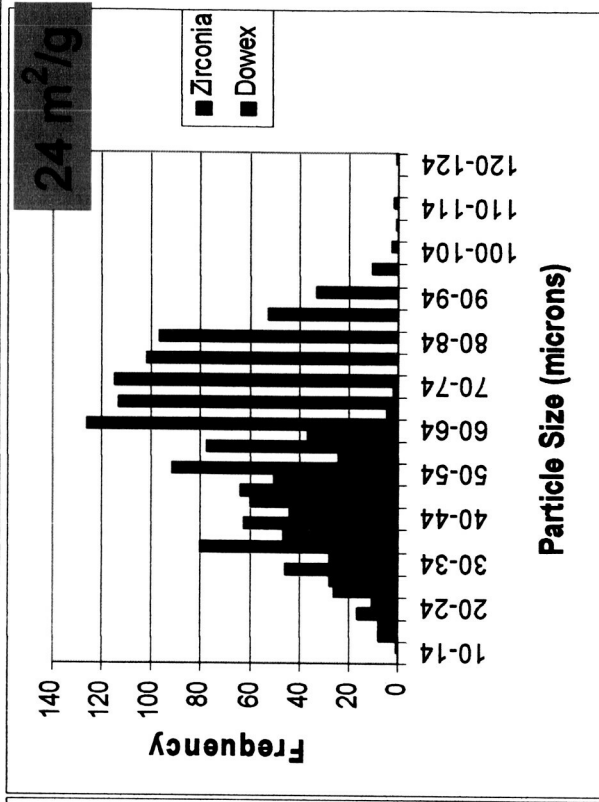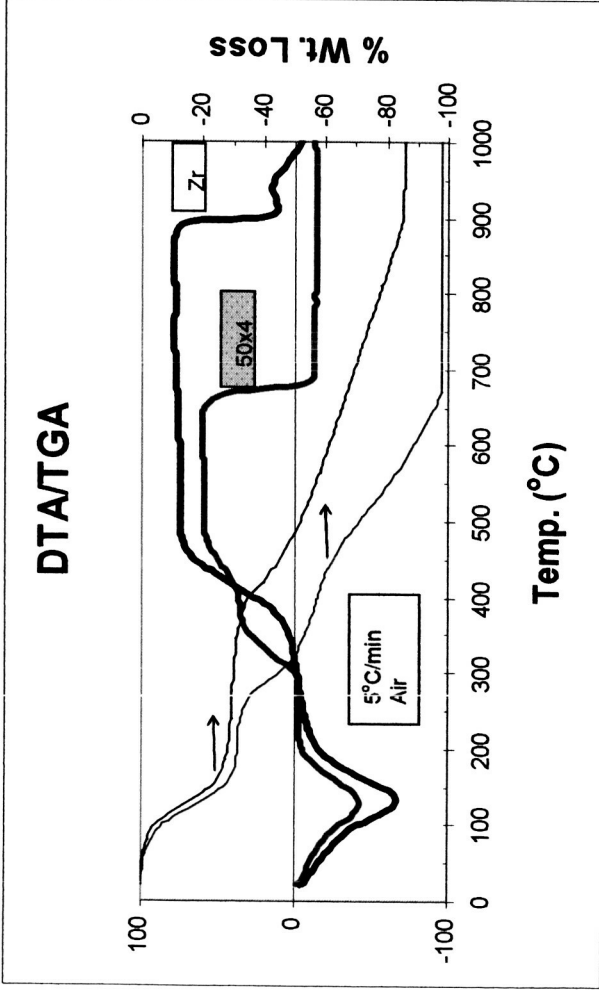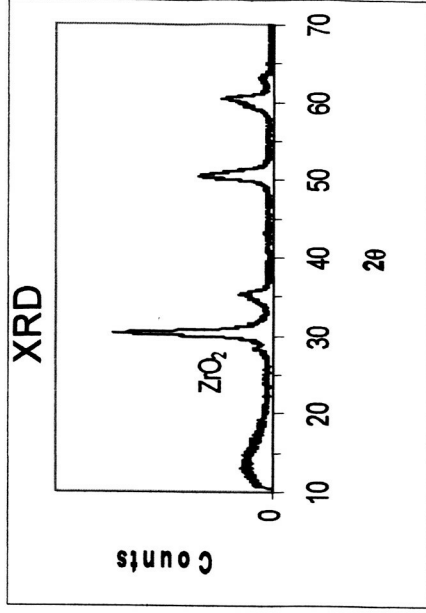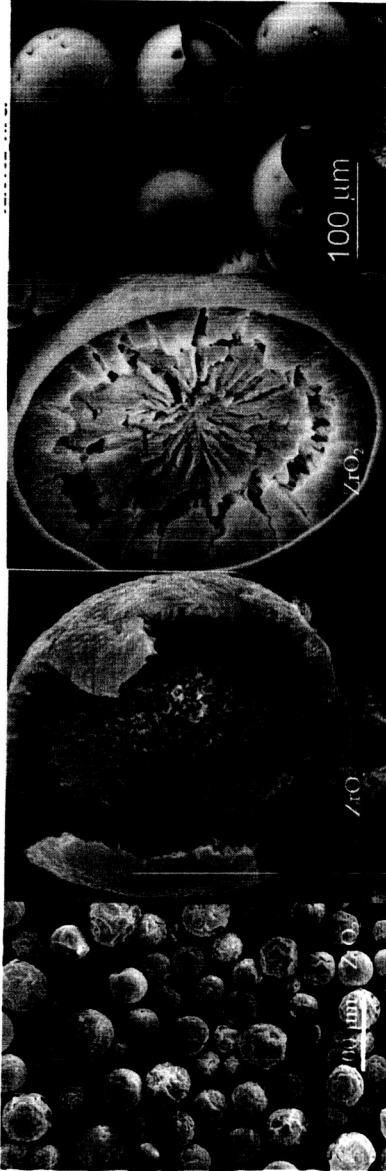







Double Calcination ZrO₂ – Step 1 - Inert

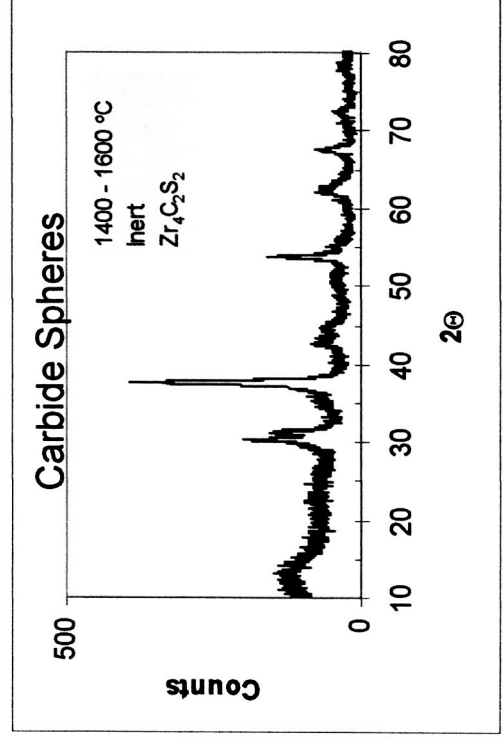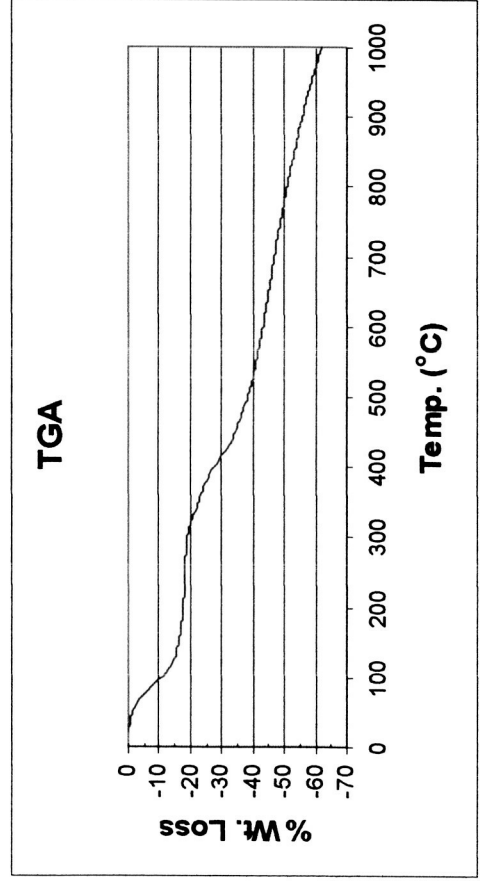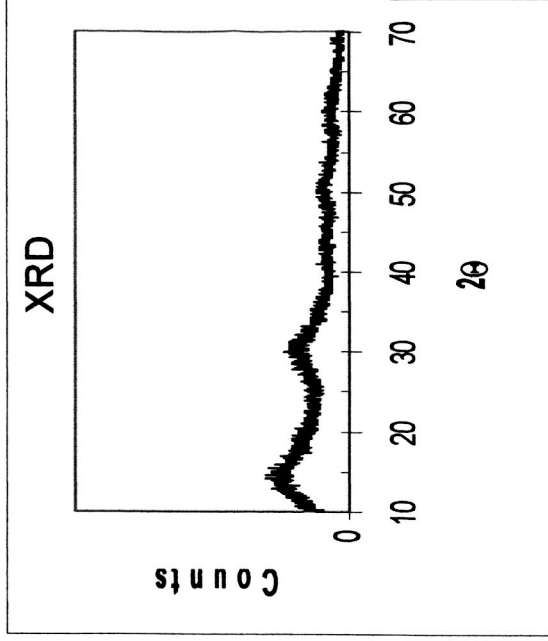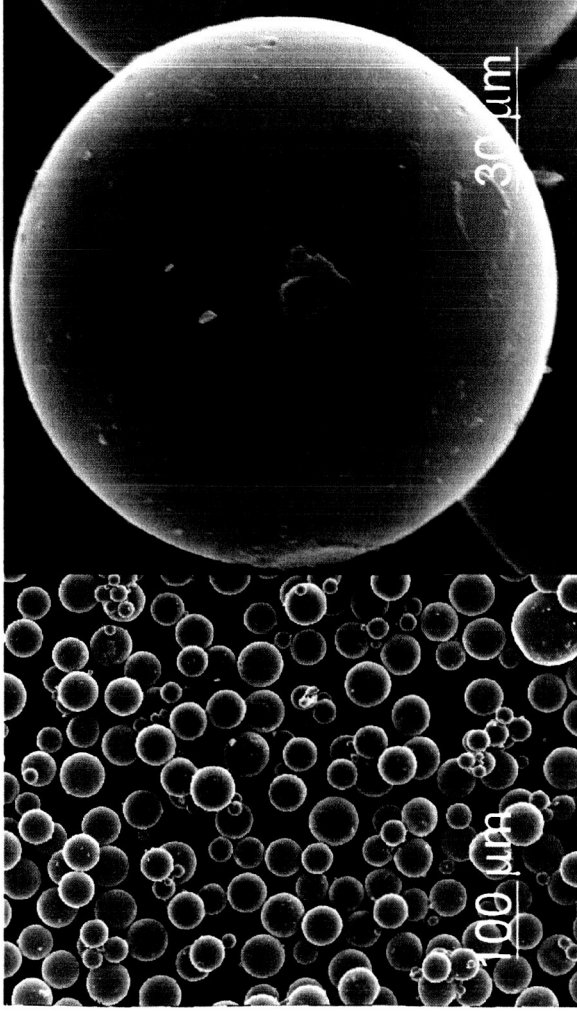



Double Calcination





ZrO₂ – Step 2 – Air

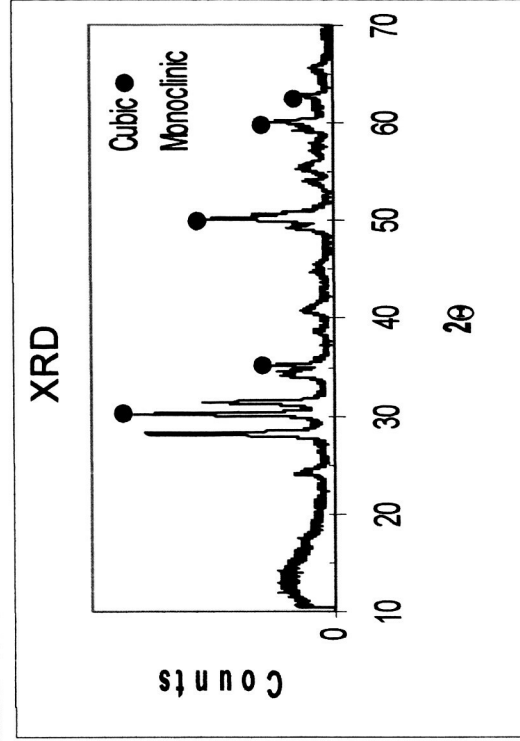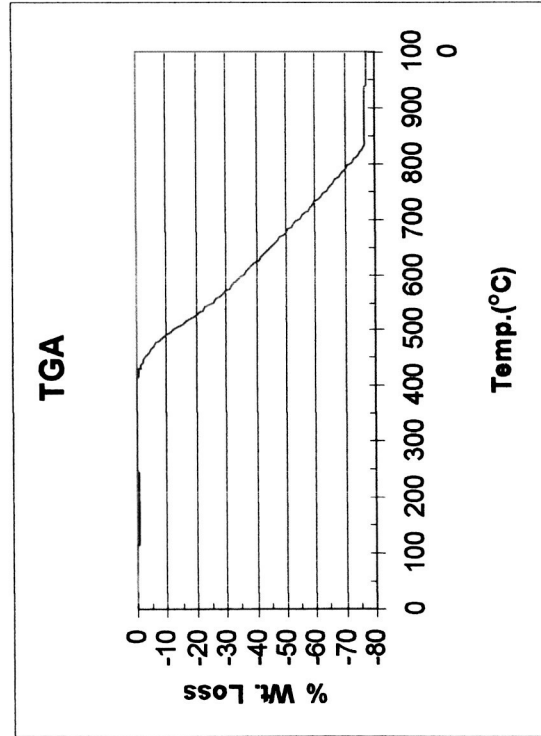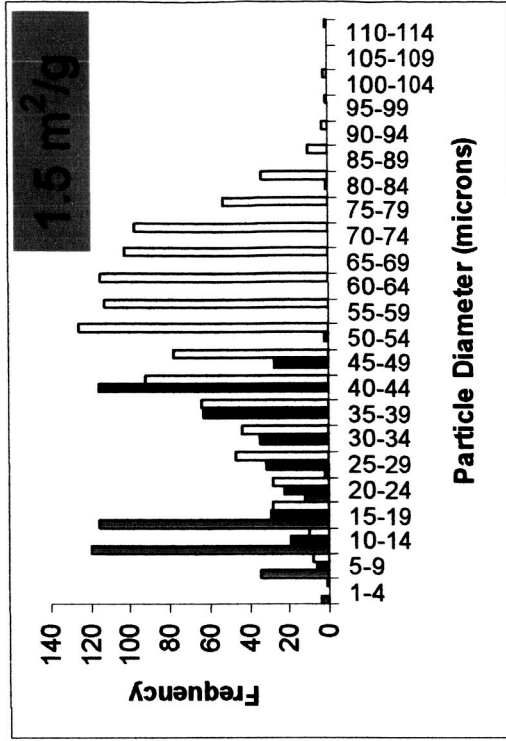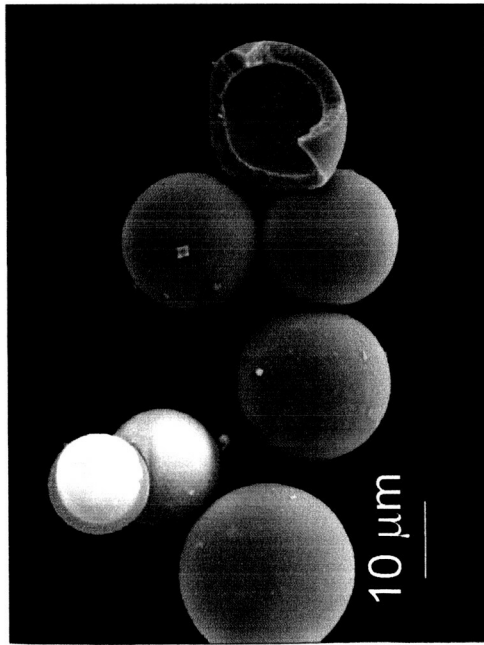




MgO/Al₂O₃ Spheres

Single Step Calcination

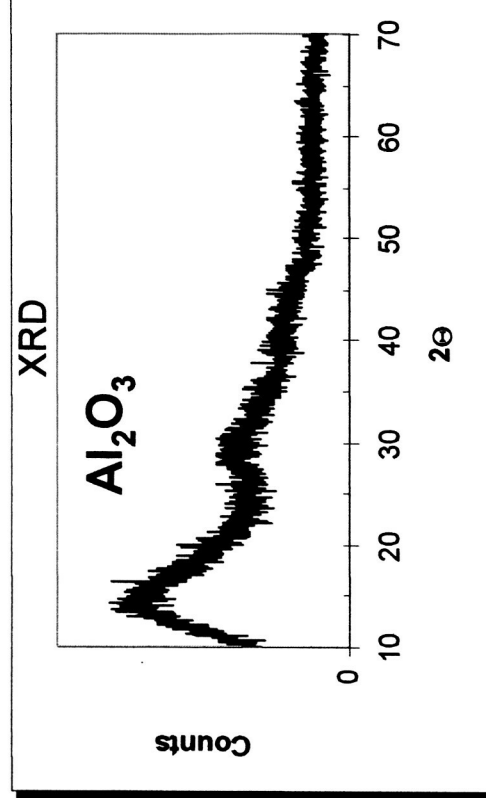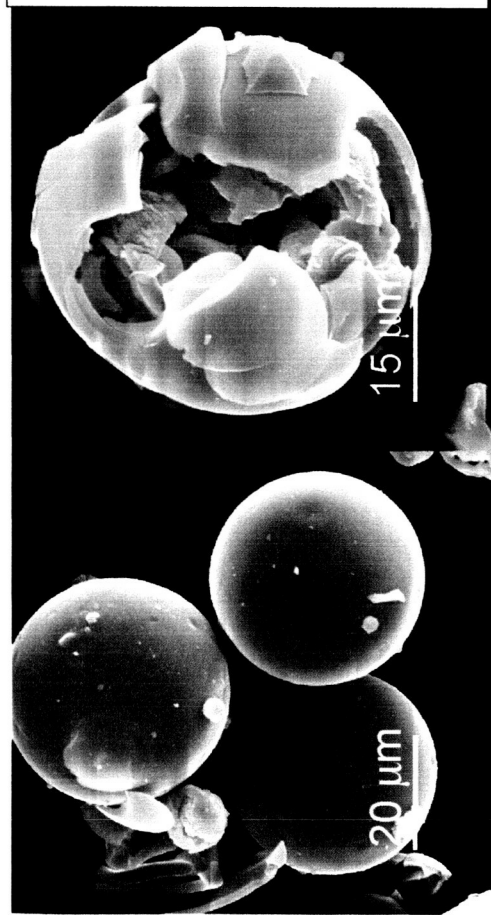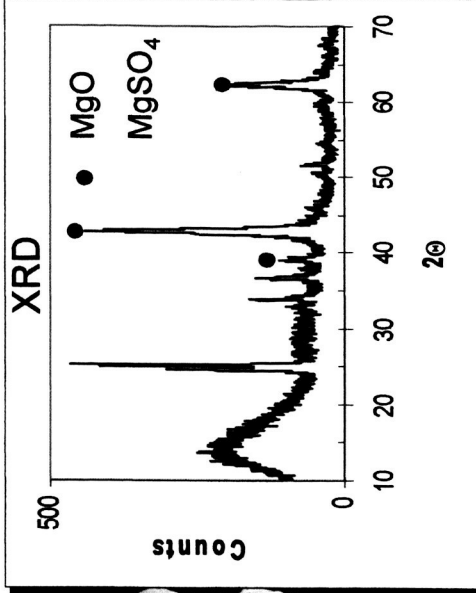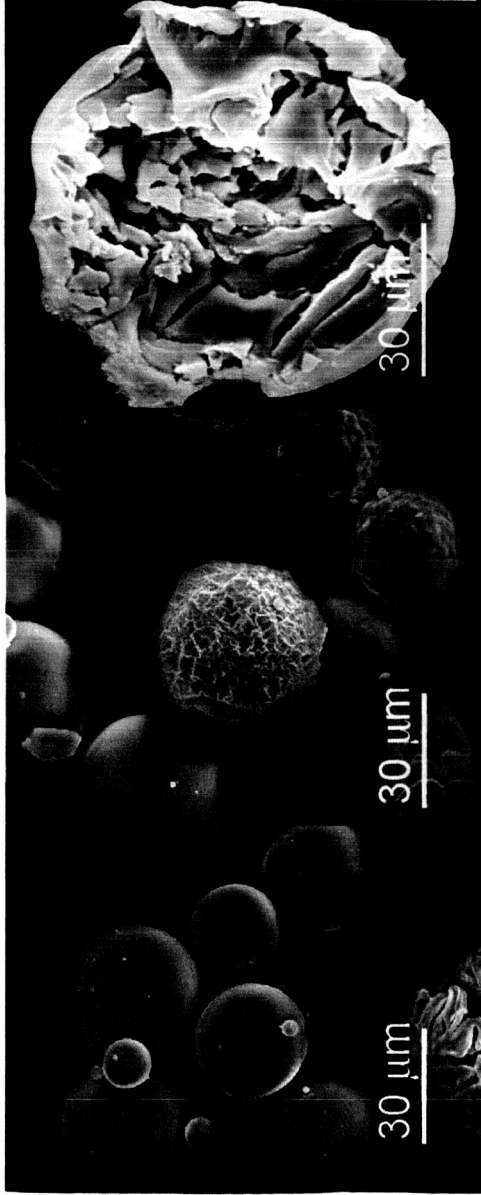



MgAl₂O₄/Y₃Al₅O₁₂ Spheres

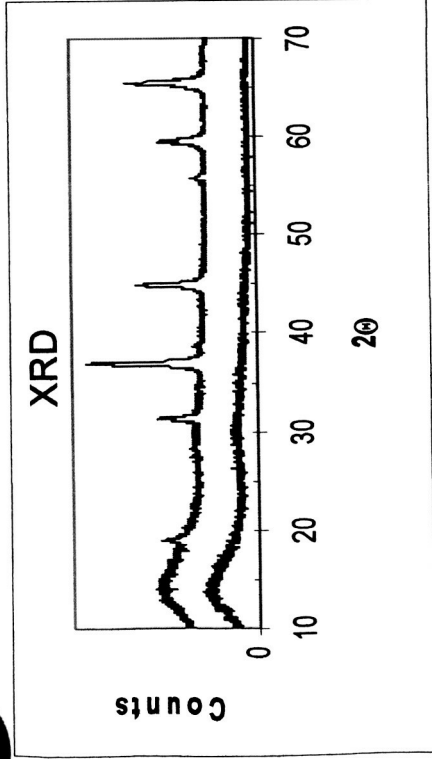

MgAl₂O₄

Molar Ratio


Phase Formation

AlCl₃/MgCl

● 1050 °C 12 hrs.

2/1

● 600 °C 5 hrs.

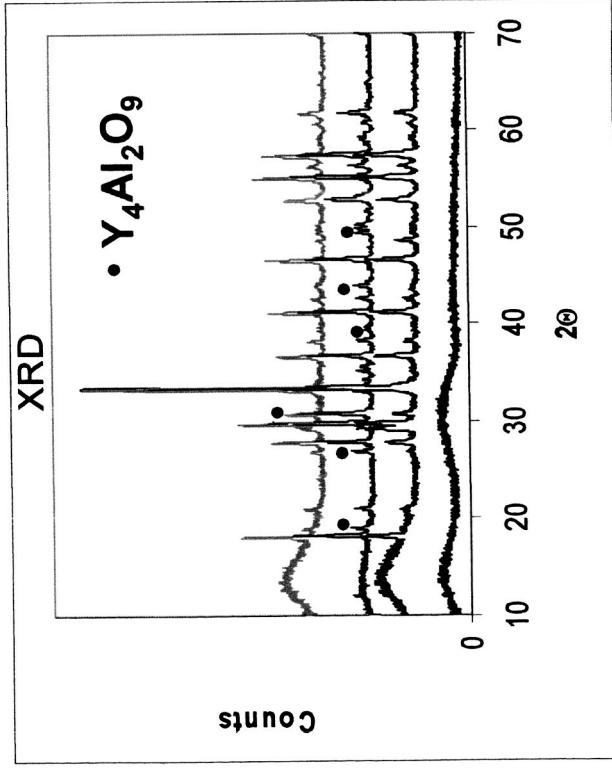

Y₃Al₅O₁₂/Y₄Al₂O₉ minor

Phase Formation

Molar Ratio

● 1200 °C 48 hrs

AlCl₃/Y(NO₃)₃

● 1200 °C 12 hrs


5/3

● 1150 °C 12 hrs

● 600 °C 6 hrs




Hollow TiO₂ Spheres

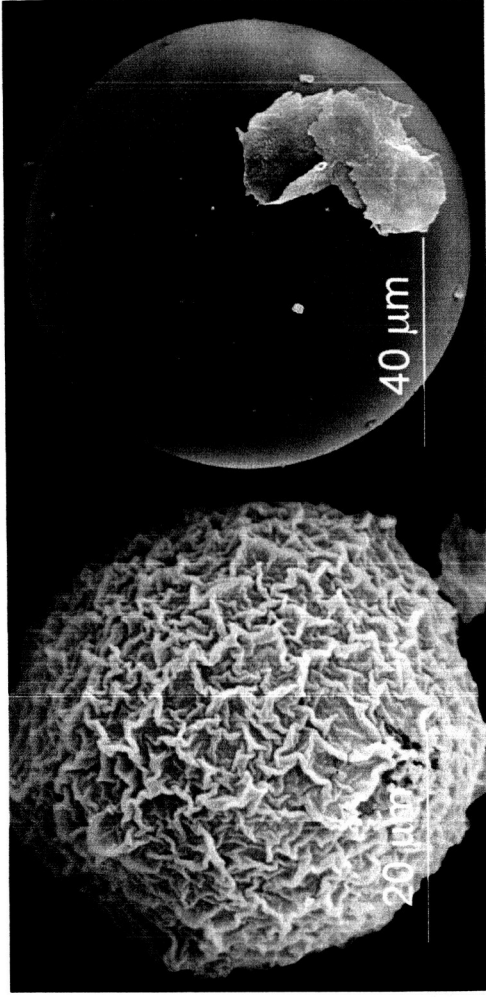

2,4- pentanedione
 $Ti(OC_3H_7)_4$
Isopropanol

Drip

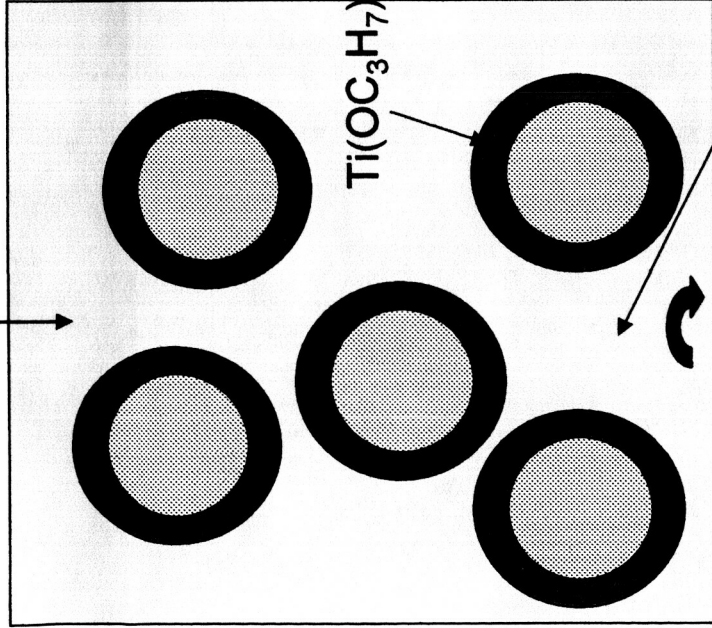




Coated Beads

- Solid/Liquid Separation
- Air Dry
- Calcine - ≥ 6 °C/min - 600-800 °C - Air

2,2,4-trimethyl pentane
Span 80





Hollow TiO₂ Spheres

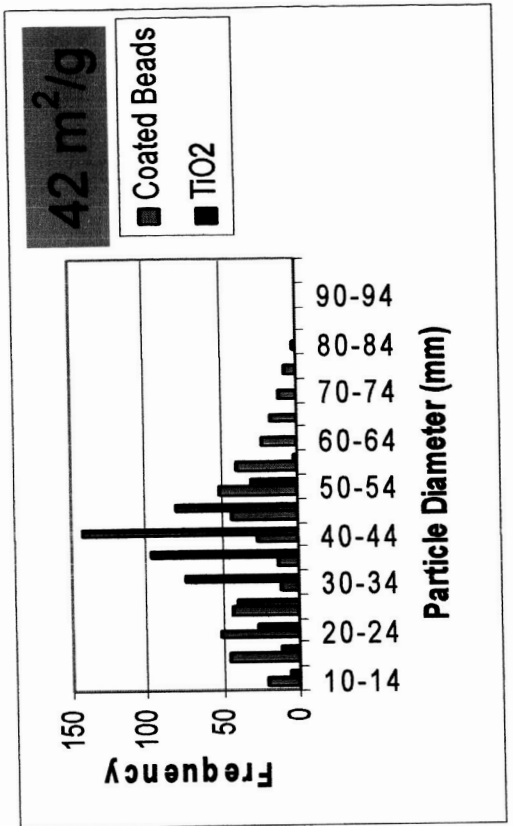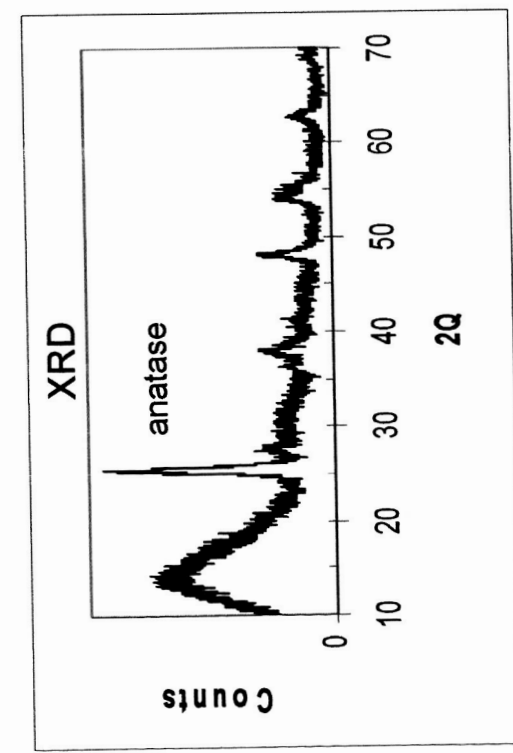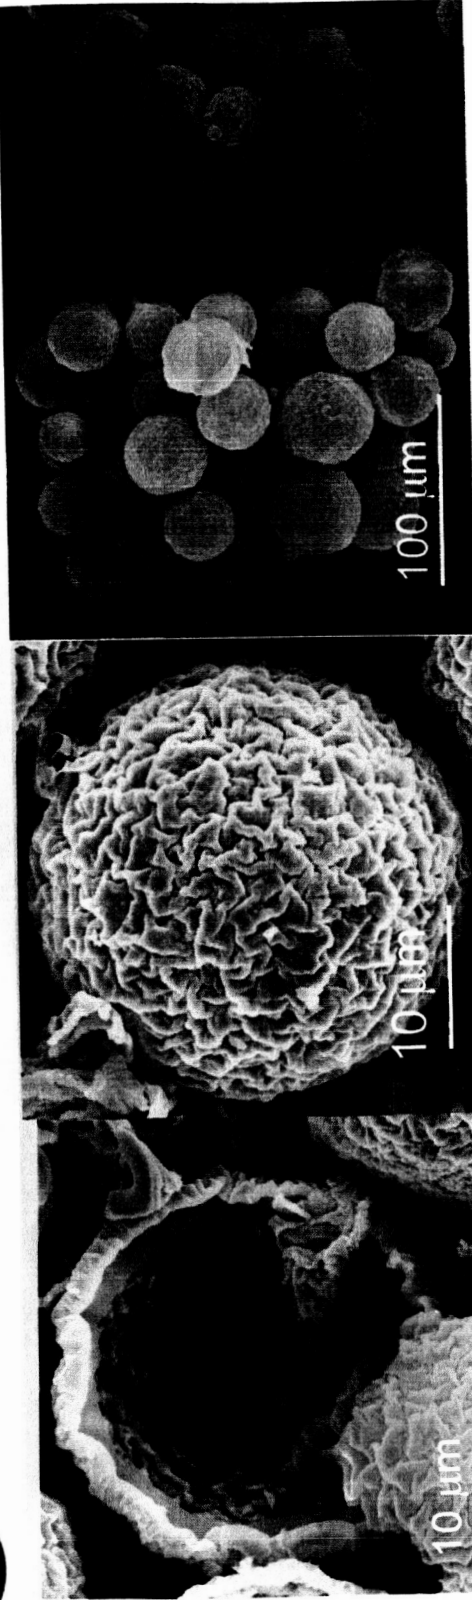



Al₂O₃ Coated ZrO₂ Spheres

Single Step Calcination

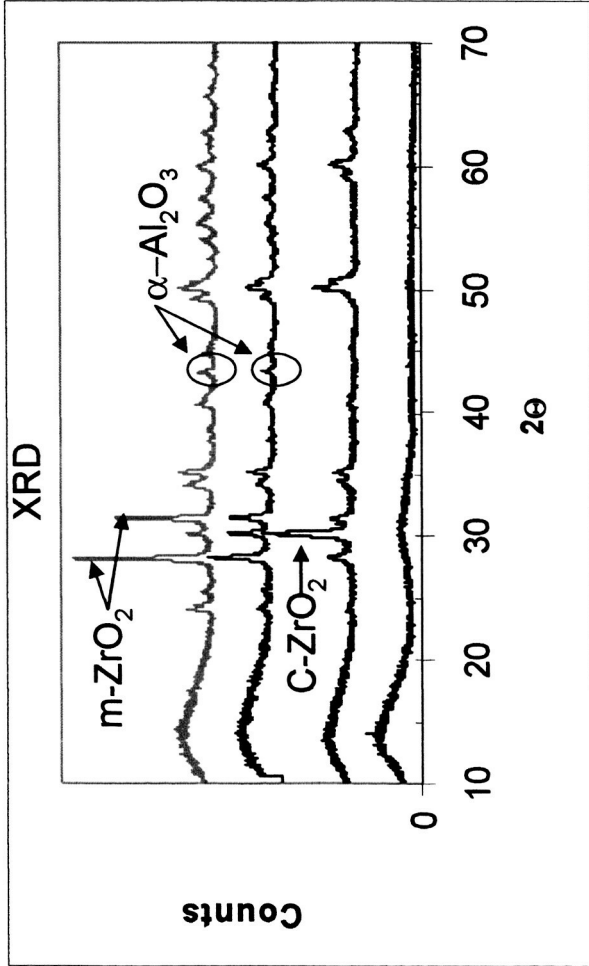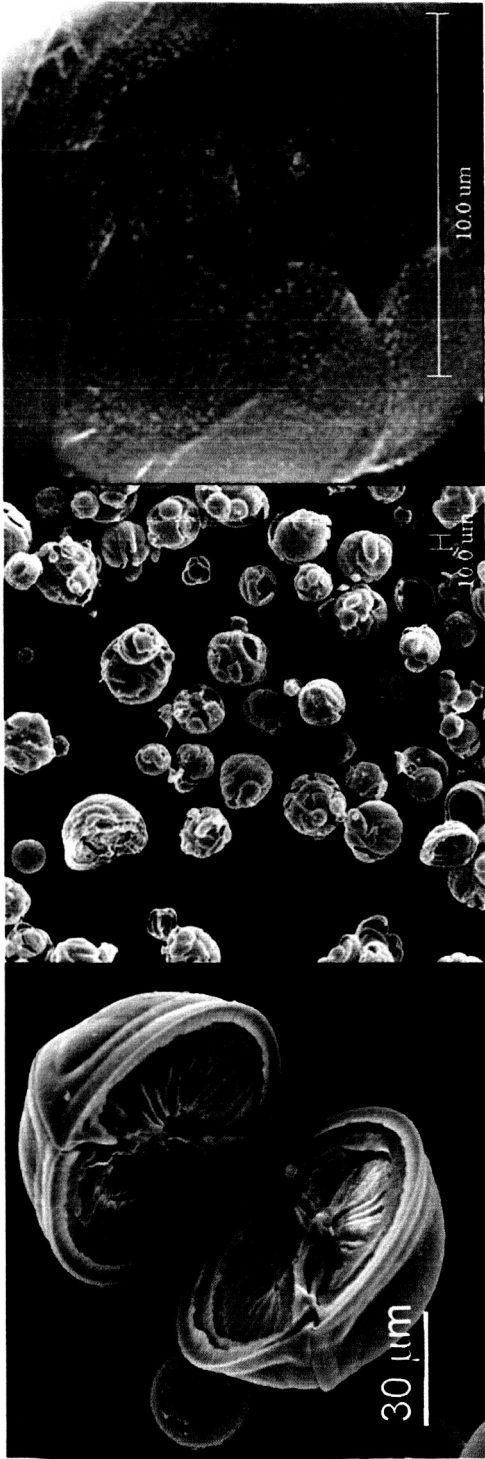

Phase Formation

- 1300 °C 12 hrs.
- 1200 °C 12 hrs.
- 1100 °C 12 hrs.
- 600 °C 5 hrs.



Summary

- Ion exchange using cation exchange beads can be used as shape forming template to make simple and complex oxides.
- Ion exchange method produces porous ceramic spheres with a unique structure; Inner sphere surrounded by a outer sphere.
- Porous spheres contained elongated pores with a pore width of 0.5 – 3 μm .
- Calcination rate and ion exchange time are important process parameters.
- Cation exchange beads can be utilized as a micro-reactor to form hollow ceramic spheres.
- Cation exchange bead size regulates the pore size of the hollow ceramic sphere.
- Composite particles can be formed by combining both templating methods.

Conference:	27TH ANNUAL COCOA BEACH CONFERENCE AND EXPOSITION ON ADVANCED CERAMICS & COMPOSITES
Sponsor:	THE AMERICAN CERAMIC SOCIETY
Location:	COCOA BEACH, FLORIDA
Start Date:	01/26/2003
End Date:	01/31/2003
Add Record	
Save Record	
Delete Record	
Print Record	
Close Form	