



A Joint MSFC/WSTF Test Activity

**Cycom 977-2 Composite
Material
Impact Test Results**

**Marshall Space Flight Center
Materials Combustion Research Center**

**Material Supplied by
Tod Palm & Jim Bohlen of
Northrop Grumman**

**Dr. Carl Engel - Qualis Corporation
Stephen Herald - ICRC
Casey Watkins - Qualis Corporation**



Outline

Background

VI Phase testing Program Description

Phase I testing

Phase II testing

Phase III testing

Phase IV testing

Data Summary

Conclusions

Recommendations



Four Phase Testing Program Description

Phase I: Ambient (13A) tests of Cycom 977-2 impact characteristics by the Bruce-ton and statistical method at MSFC & WSTF

Phase II: Repeat (13A) test of tested Cycom from Phase I at MSFC to expanded testing statistical database

Phase III: Conduct High-Pressure tests (13B) in LOX and GOX at MSFC and WSTF to determine Cycom reaction characteristics and batch effects

Phase IV: Conduct expanded Ambient (13A) LOX test at MSFC and High-Pressure (13B) testing to determine pressure effects in LOX. Expand 13B GOX database.



Phase I Objectives

Phase I: Ambient (13A) tests of Cycom 977-2 impact characteristics by the Bruceon and statistical method at MSFC & WSTF

- **Establish Cycom 977-2 reaction characteristics using Bruceon and statistical testing methods**
- **Using the forgoing data, provide a data set for comparison of facility results**



Phase I Test Matrix

Phase I Testing						
Ambient 13A LOX Ambient Pressure Multiple Impact						
Note: MSFC Nominal Pressure = 14.7 psia			Average Pre test sample Wt. = 0.774 g			
WSTF Nominal Pressure = 12.4 psia			Average sample thickness = 0.0895 in			
Energy Level ft-lb	MSFC samples	1st impact		all impact		Wt Change w/o Reaction %
		reactions	reactions	reactions	reactions	
27.2	40	6	18	-0.70%	0.43%	
31.2	30	4	17	-0.37%	-0.10%	
35.8	30	6	15	-0.38%	0.30%	
40.8	30	13	28	-0.55%	-0.19%	
54.5	60	51	59	not available	not available	
Subtotals=	190	80	137			

Energy Level ft-lb	WSTF samples	1st impact		all impact		Wt Change w/Reaction g	Wt Change w/o Reaction g
		reactions	reactions	reactions	reactions		
31.2	30	10	23	-0.31%	-0.46%		
35.8	30	22	29	0.12%	-0.13%		
40.8	30	25	30	0.30%	-		
Subtotals=	90	57	82				

Single Impact		Bruceton Method	
MSFC	34	50% energy	52.08 ft-lb
MSFC	34	50% energy	46.65 ft-lb
WSTF	34	50% energy	34 ft-lb
Multiple Impact		Bruceton Method	
MSFC	34	50% energy	24.18 ft-lb




Post Test Samples

**62.9 FT LBS/14.7 PSIA
BRUCETON METHOD POST-TEST SAMPLE**

Many post-test samples were found intact


#2

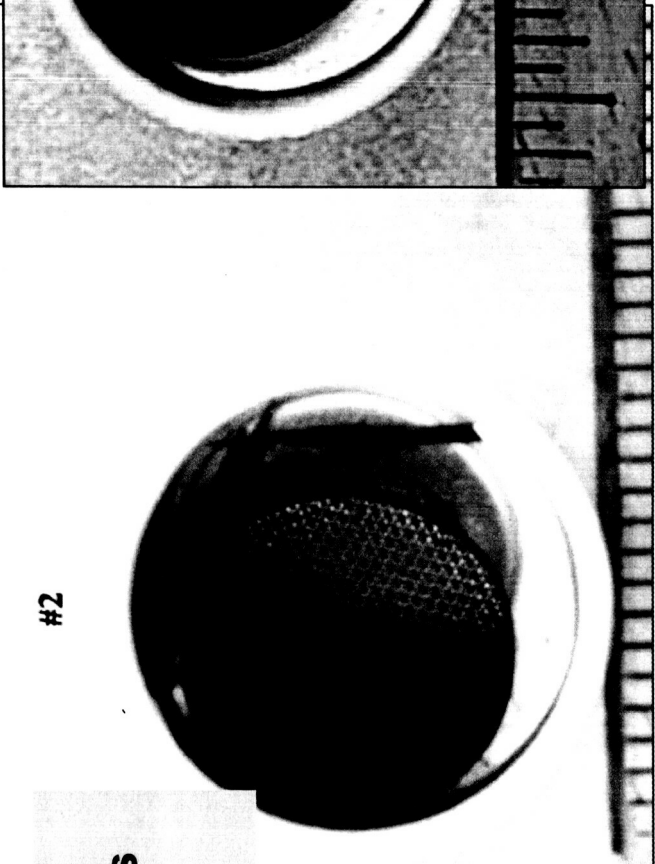

35.9 ft-lb




Weight Change Data

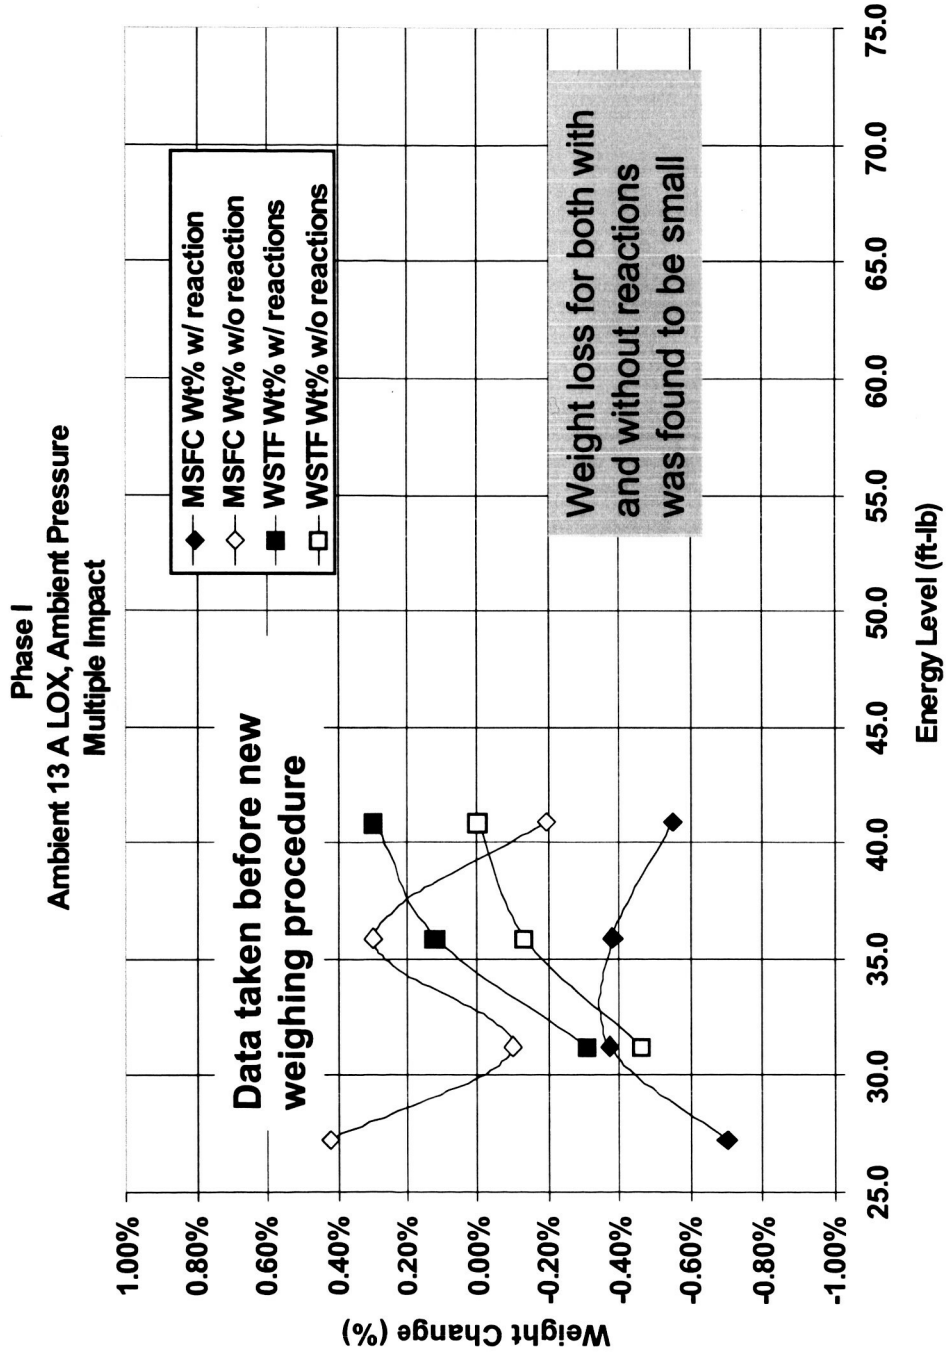




Mass Loss vs. Test Sequence MSFC Data

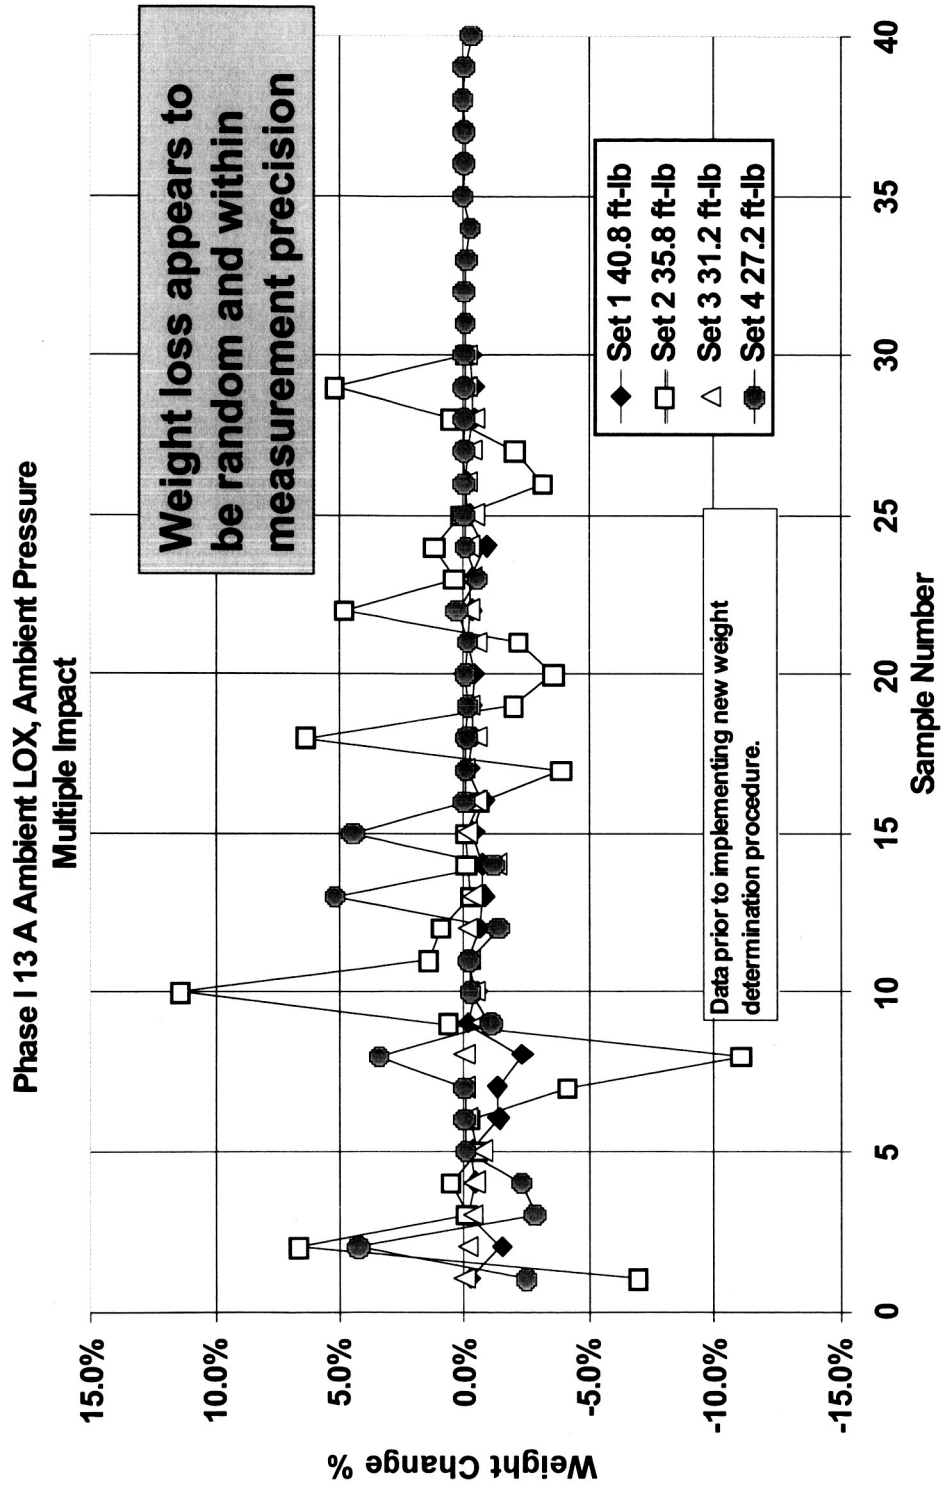



First Strike Reaction Frequency

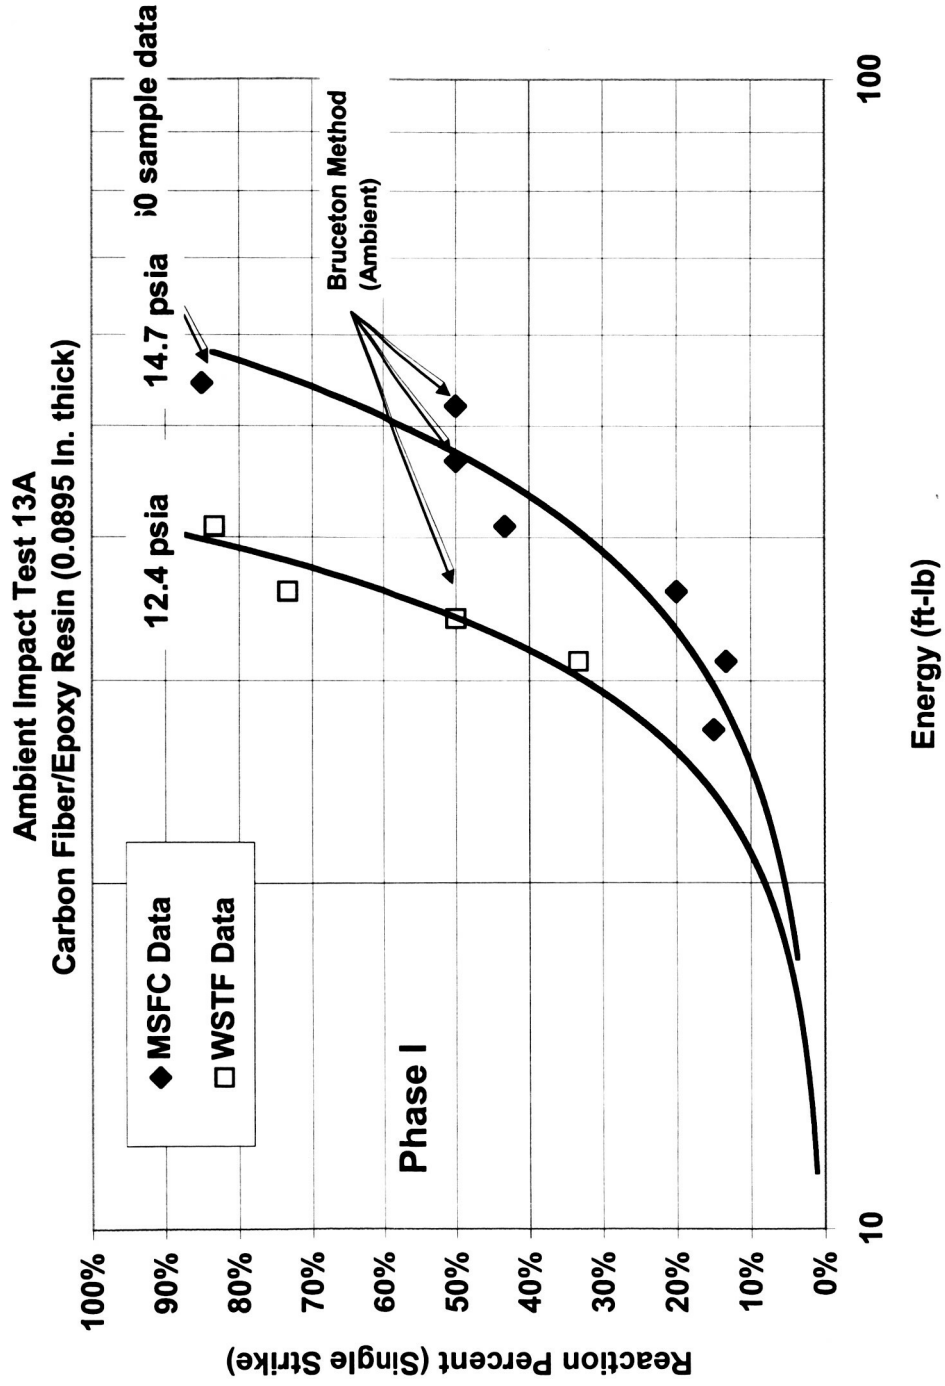



Phase I Conclusions

- **MSFC and WSTF reaction frequency data have been compared, revealing a shift between facilities.**
- **The Bruceston and statistical methods appear consistent.**
- **MSFC and WSTF weight loss due to reactions is quite small for Phase I conditions and appear consistent between facilities**
- **For conditions that initiated a reaction, no samples exhibited propagation of the reaction by consuming a significant portion of the material. The initiated reaction was quenched.**
- **The Phase I test data reveal a characteristic of this composite, which offers the acceptance of this material as impact resistant if the technical community accepts an alternate pass criterion.**
- **Phase I results encouraged the development of a more accurate methodology for measuring pre- and post-test sample weights and additional testing.**



New Sample Weighing Procedure

- Samples are placed within a humidity chamber at 40% for 24 hours.
- After 24 hours, the samples are weighed via (mg) scale.
- Pretest weights are recorded for all samples.
 - Sample is removed from the humidity chamber.
 - The chamber is closed.
 - The sample is weighed.
 - The sample is placed into its designated bag and the bag is closed.
 - The next sample is removed from the humidity chamber and the weighing procedure is repeated with this sample.
- Immediately after all weights are obtained, standard testing begins.
- After each sample is tested, the entire cup with sample is placed into the humidity chamber at 40% for 24 hours.
- Note: The samples are tested in order and placed on their proper identification labels on a foil sheet inside the humidity chamber after testing.
- The time that each sample is placed into the humidity chamber is noted.
- After 24 hours within the chamber, each sample is weighed in the same manner as the above procedure and the post-test weights are recorded.



Phase II Objectives

Phase II: Repeat (13A) test of tested Cycom from Phase I at MSFC to expand testing statistical database

- **Retest tested Phase I samples that remained intact from Phase I testing to expand the database with minimal material available**
- **Implement new accurate pre- and post-test weighing method to determine if the weight loss was from the test procedure or from reaction of the material**



Phase II Test Matrix


Phase II Material Retest						
Ambient 13A LOX Ambient Pressure						
Energy level ft-lb	MSFC samples	Sample source (Note: 1, 2, 3)	1st impact		all impact	
			reactions	reactions	reactions	reactions
					WT Change w/Reaction %	WT Change w/o Reaction %
23.5	65	Prev Multiple Impact Bructon, Prev Single Impact Bructon, Prev 27.2	6	8	-0.40%	-0.16%
31.2	15	Prev. 31.2 samples	0	6	-0.54%	-0.14%
35.8	15	Prev. 35.8 samples	2	Catcher	-0.84%	-0.63%
40.8	14	Prev. 40.8 samples	8	Catcher	-1.01%	-0.38%
	109					

<p>Note 1: Post Phase I samples hand selected for completed disk. Samples are weighed. Samples greater than 0.72 gm were selected</p>	<p>Note 2: Use Std cleaning but keep individual sample identification</p>	<p>Note 3: Store 24 hr in 40% humidity before testing. Weigh sampled before testing after storage at controlled humidity. Place samples in controlled 40% humidity for 24 hours after testing Weigh sampled and package samples</p>
--	--	--




Average Weight Change Data

Phase II
Testing Ambient 13 A LOX Ambient Pressure

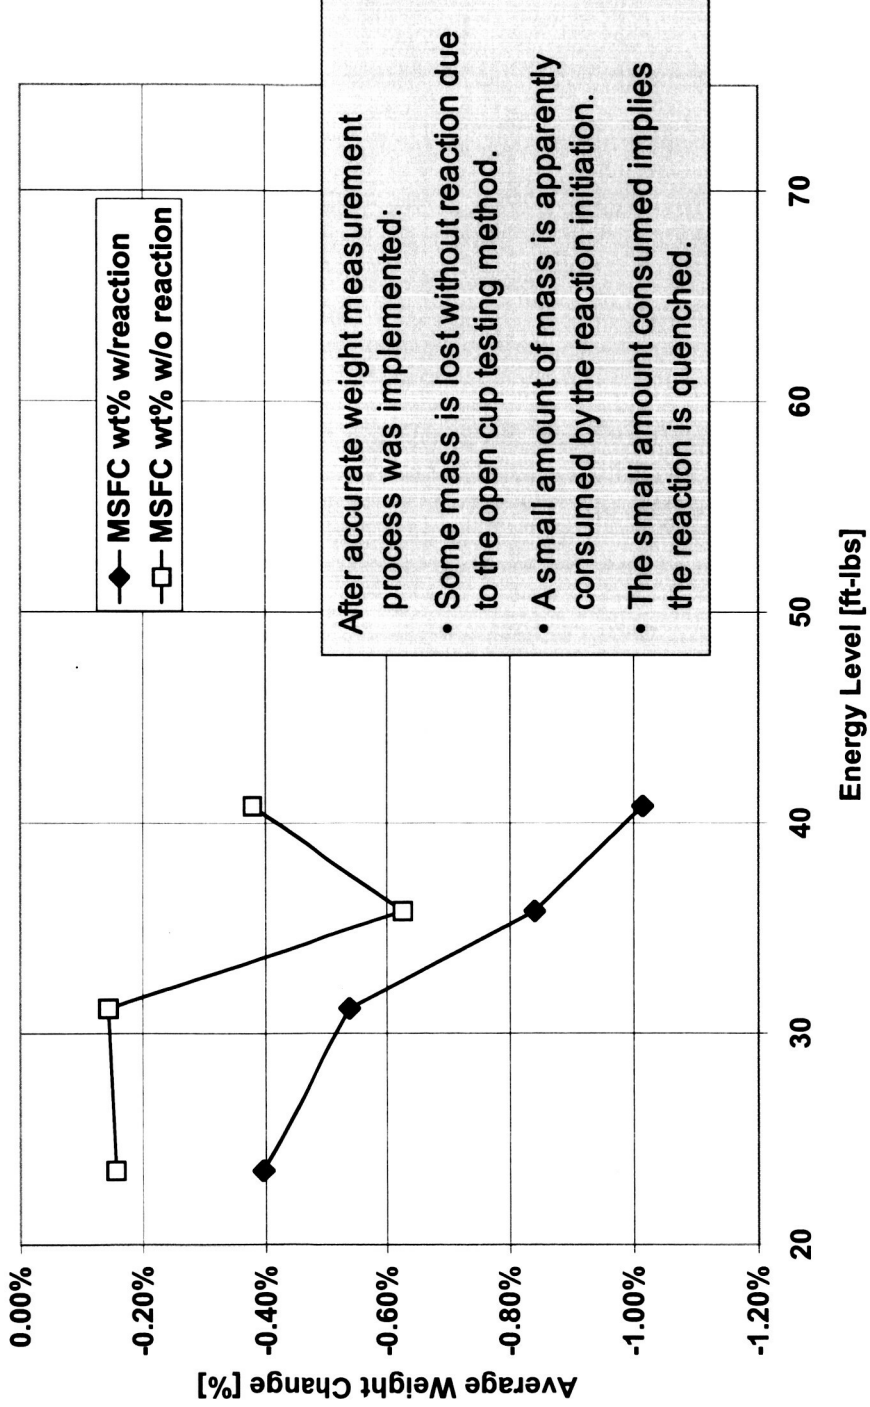



First Strike Reaction Frequency Data

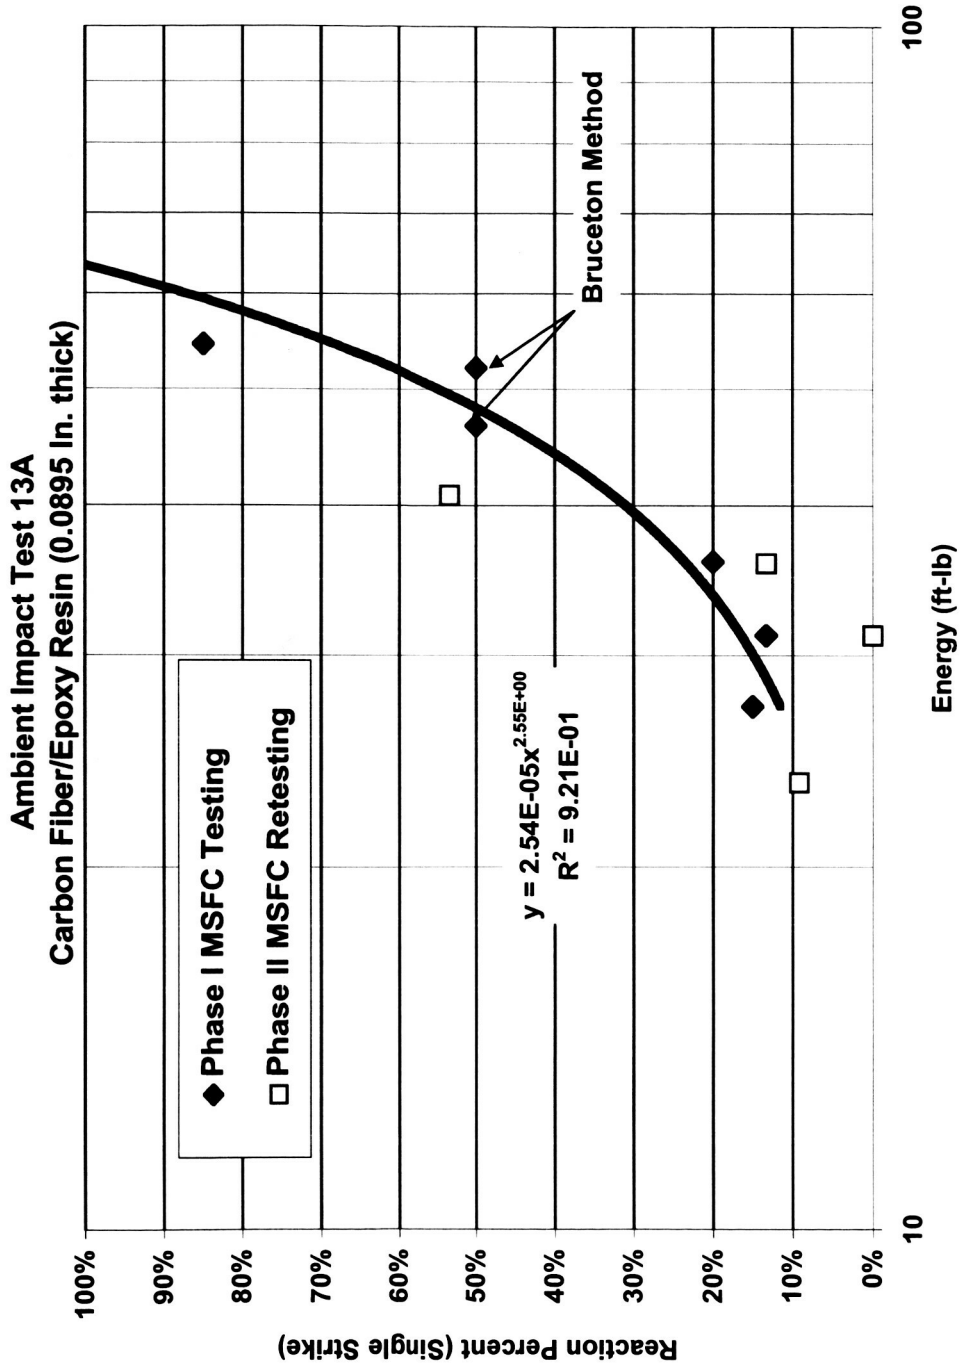



Phase II Conclusions

- The data from the retested material appears consistent with the Phase I material, which had not been tested. The data have been combined with Phase I data.
- The new mass loss measurement techniques and improved care of the post-test samples appear to have improved accuracy of mass loss measurements.
- The mass loss with reactions is small, i.e., less than 1.1%, indicating the reaction initiation did not propagate for any sample.
- The testing process and sample recovery process produce a small mass loss.



Phase III Objectives

Phase III: Conduct High-Pressure tests (13B) in LOX and GOX at MSFC and WSTF to determine Cycom reaction characteristics and batch effects

- Determine Cycom reactivity in LOX at 100 psia
- Determine Cycom reactivity in GOX at 100 psia
- Examine batch sensitivity in LOX at 100 psia
- Examine batch sensitivity in GOX at 100 psia
- Compare MSFC and WSTF 13B data for Cycom in LOX and GOX



Phase III Test Matrix

Phase III Testing 13 B Bruceton Method

MSFC


Batch # (ASDL #)	Sample Number	Test	Pressure psia	LOX/GOX	Reactions	No Reactions	50% Energy ft-lb	Wt Change w/ reactions %	Wt Change w/o reactions %
Set A, 18110	34	13 B Bruceton Method	100	LOX	4	30	67.23	-14.56%	-0.19%
Set B, 18109	34	13 B Bruceton Method	100	LOX	4	30	64.77	-26.25%	-0.01%
Set A, 18110	34	13 B Bruceton Method	100	GOX	0	34	-	-	0.00%
Set B, 18109	34	13 B Bruceton Method	100	GOX	0	34	-	-	-0.008%

WS TF

Batch # (ASDL #)	Sample Number	Test	Pressure psia	LOX/GOX	Reactions	No Reactions	50% Energy ft-lb	Wt Change w/ reactions %	Wt Change w/o reactions %
Set A, 18110	20	13 B Bruceton Method	100	LOX	0	20	-	-	-0.06%
Set A, 18110	25	13 B Bruceton Method	100	GOX	0	25	-	-	-0.03%



Weight Change in LOX at 100 Psia at MSFC

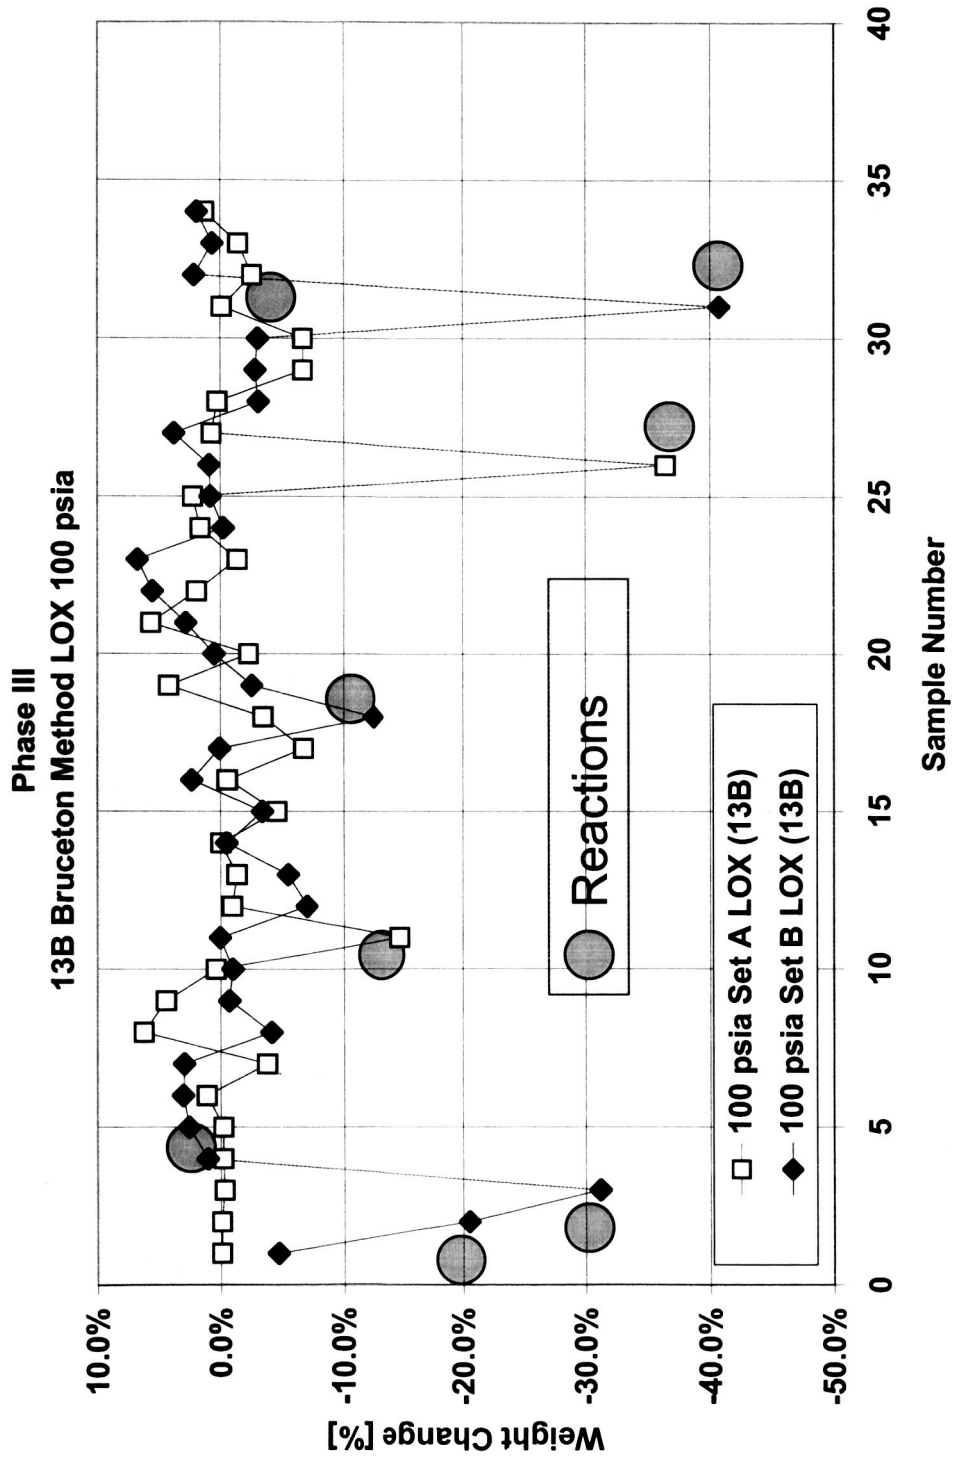



Phase III Conclusions

- **Cycom does not support initiation of reactions or propagate of reactions in GOX at 100 psia based on tests at MSFC and WSTF at 72 ft-lb impact energy.**
- **No batch effect was identified in LOX or GOX.**
- **WSTF show no reactions at 72 ft-lb and 100 psia in LOX whereas MSFC showed 4 of 34 reactions (11.7%) for both batches tested.**
- **Six of the eight reactions in LOX (72 ft-lb at 100 psia) supported initiation and propagation of reaction as indicated by the large amount of mass loss (ave. = 26%) by the impact promoted reaction.**



Phase IV Objectives

Phase IV: Ambient (13A) test at MSFC to examine average time of sample in test well effect and (13B) testing to determine pressure effects in LOX. Expand 13B GOX database

Determine the pressure effect on reaction frequency:

Hypothesis: If the reaction frequency is a function of the number of entrained bubbles, then higher pressure will reduce the number of bubbles and lower the reaction probability.

Note: Since no reactions were observed with GOX at 100 psia, the adiabatic compression of bubbles is considered an initiation mechanism for LOX impact.



Phase IV Test Matrix

Phase IV									
Ambient 13A (LOX)									
Batch (ASDL #)	Energy Level ft-lb	MSFC samples	Pressure psia	1st impact reactions	all impact reactions	Average Time s	Wt change w/ reaction g	Wt change w/o reaction g	
18109	72	30	14.7	26	catcher	40	-5.88%	0.96%	
18110	72	30	14.7	20	catcher	80	-8.39%	-5.40%	
	Subtotals	60							

Average time is defined as the time between the sample being placed into the sample well to the time the sample is impacted. Forty, 40, seconds is the average time for a 13A sample at MSFC under normal conditions.

Phase IV									
13B (LOX)									
Batch (ASDL #)	Energy Level ft-lb	MSFC samples	Pressure psia	Reactions	No reactions	Average Time	Wt change w/ reaction g	Wt change w/o reaction g	
18109	72	30	50	13	17	-	-57.07%	-5.75%	
18110	72	30	200	18	12	-	-51.51%	-0.44%	
18110	72	2	500	2	0	-	-37.33%	-	
	Subtotals	62							




Phase IV Test Matrix Continued

Phase IV-A							
Cycrom Impact Testing 13B							
Batch (ASDL #)	Medium	Energy Level ft-lb	MSFC samples	Pressure psia	1st impact		Wt change w/o reaction g
					reactions		
18109	GOX	72	30	500	22		-0.147%
18109	GOX	72	30	200	4		0.208%
		Subtotals	60				




Combined First Strike Reaction Frequency Data

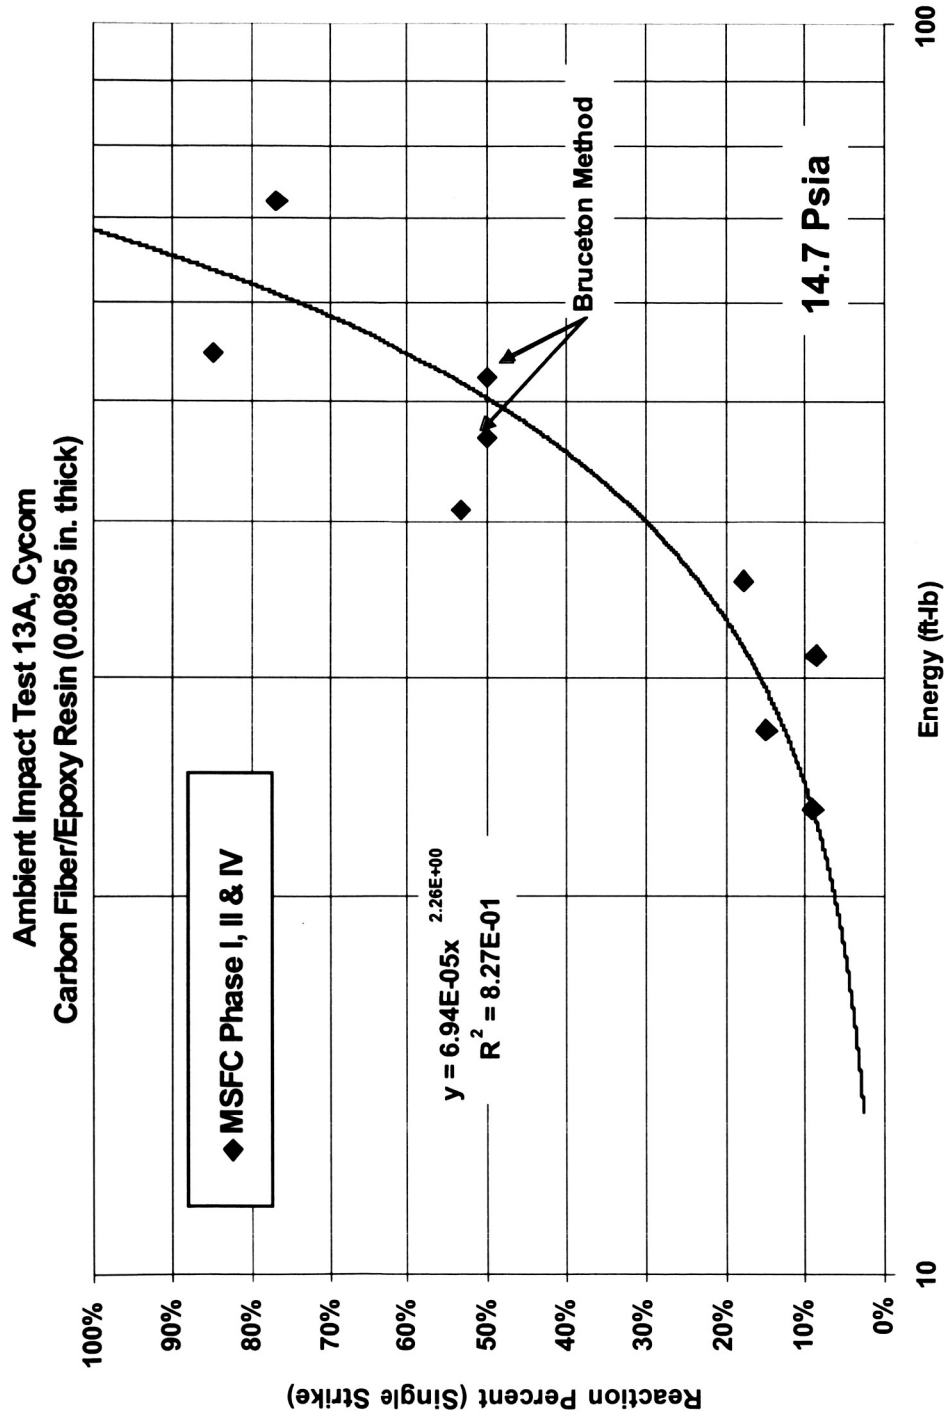



Mass Loss in LOX Testing

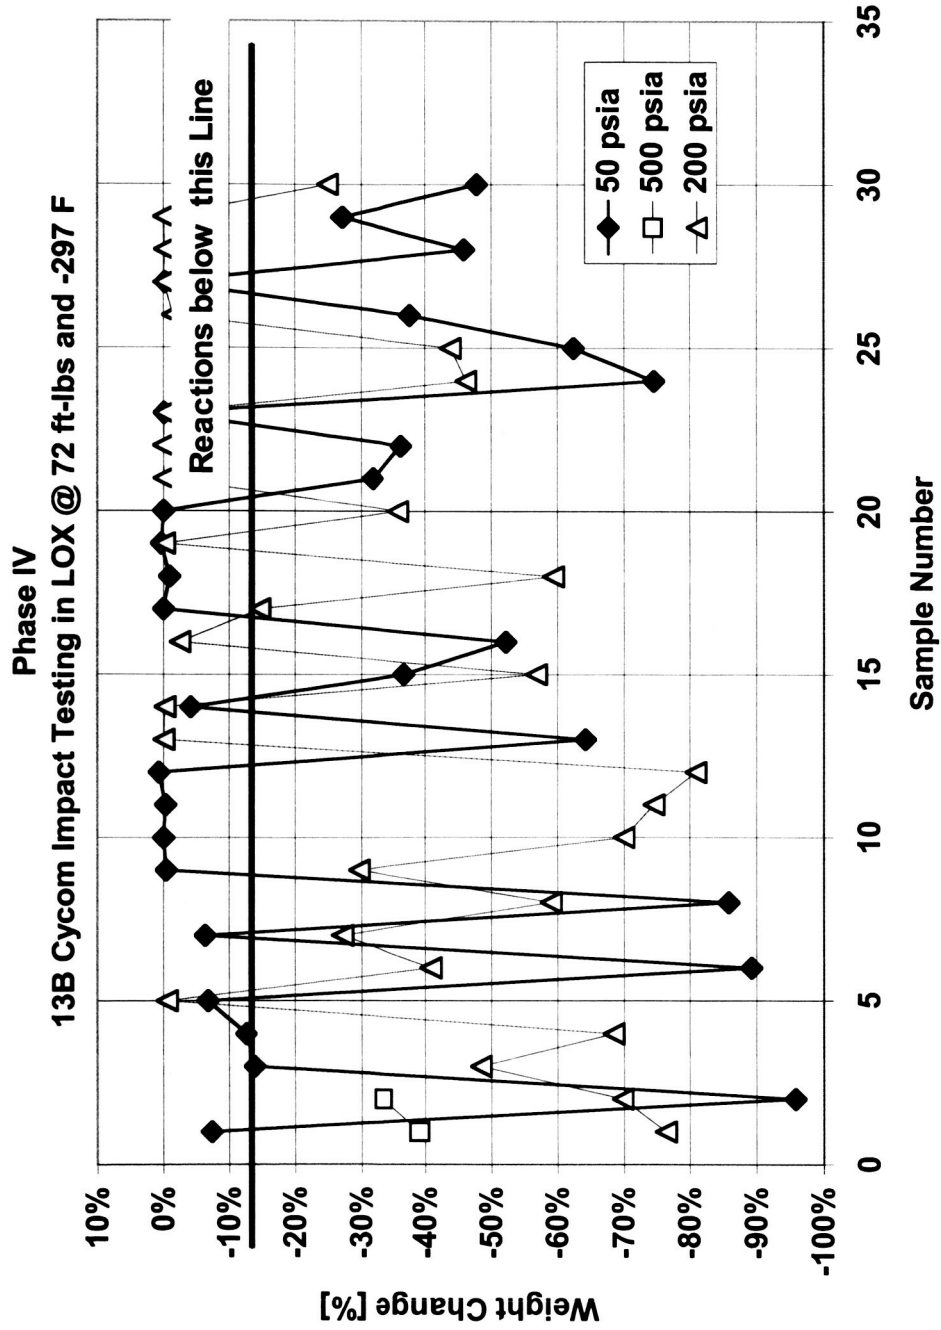




**No Reaction and
Non-Quenched Reaction Comparison**

Cycom 977-2 13B LOX 50 psia 72 ft-lbs

Sample 18 No Reaction

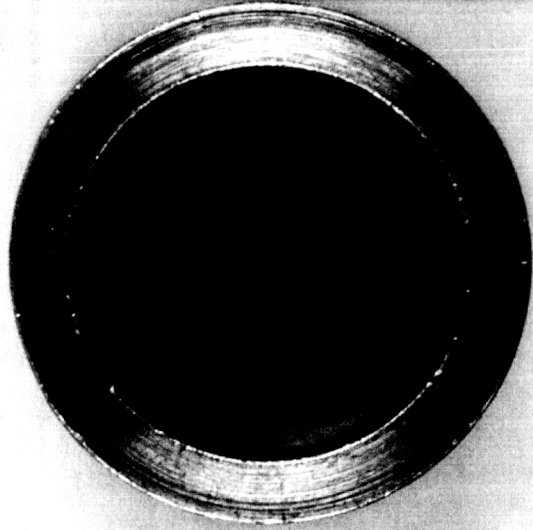

Sample 6 Reaction






**No Reaction and Non-Quenched
Reaction Comparison**

Cycom 977-2 13B LOX 50 psia 72 ft-lbs

Sample 18 No Reaction

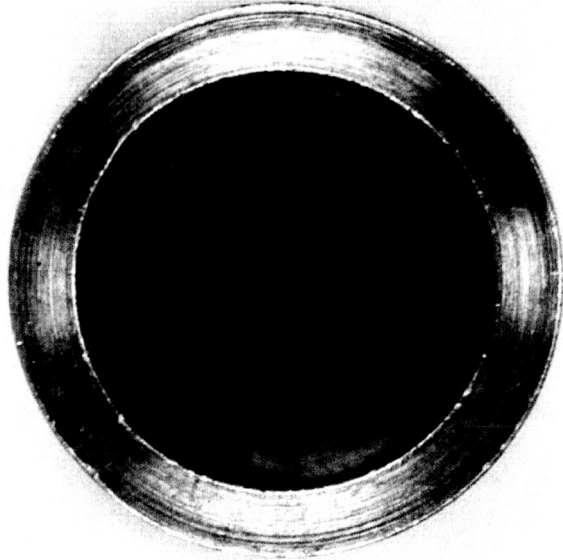


Sample 24 Reaction






Pressure Effect on Reaction Frequency

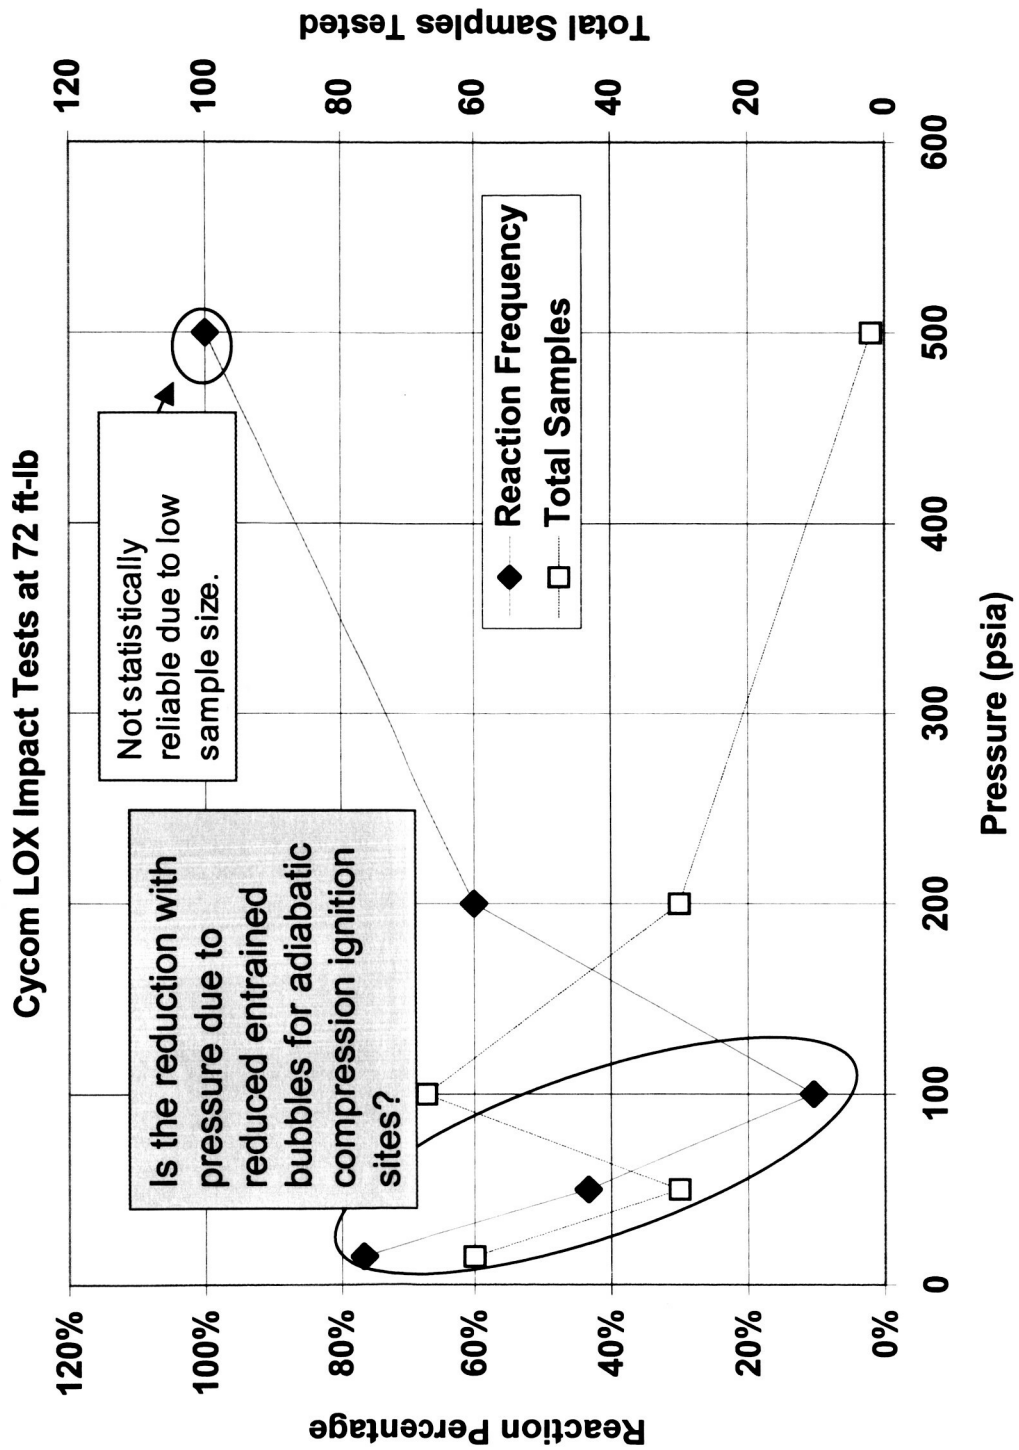




Average Weight Loss with Reactions at 72 ft-lb

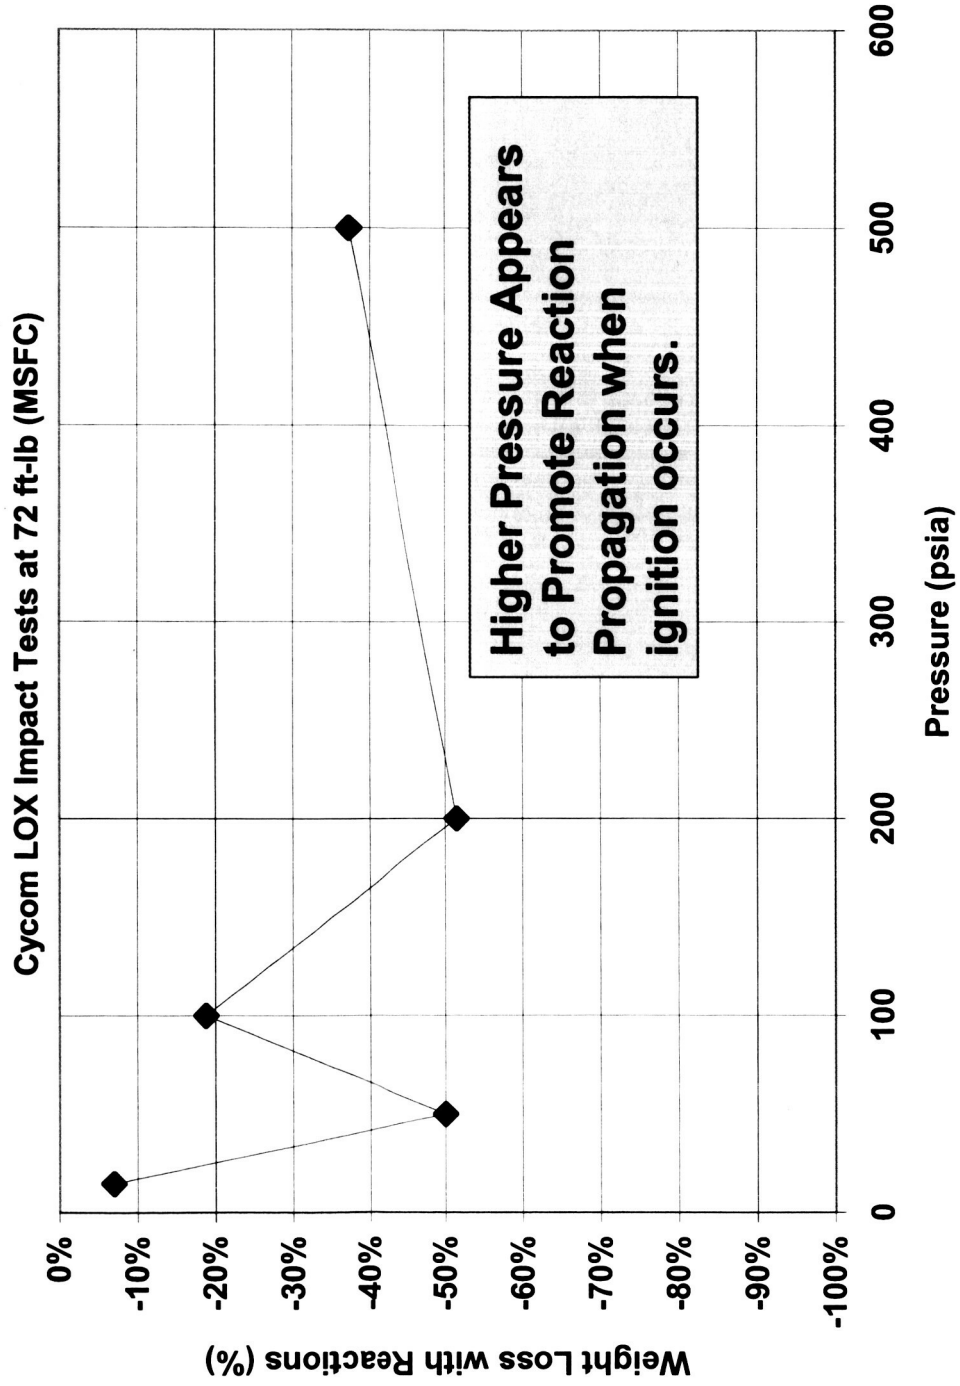




Reaction Frequency in GOX at 72 ft-lb

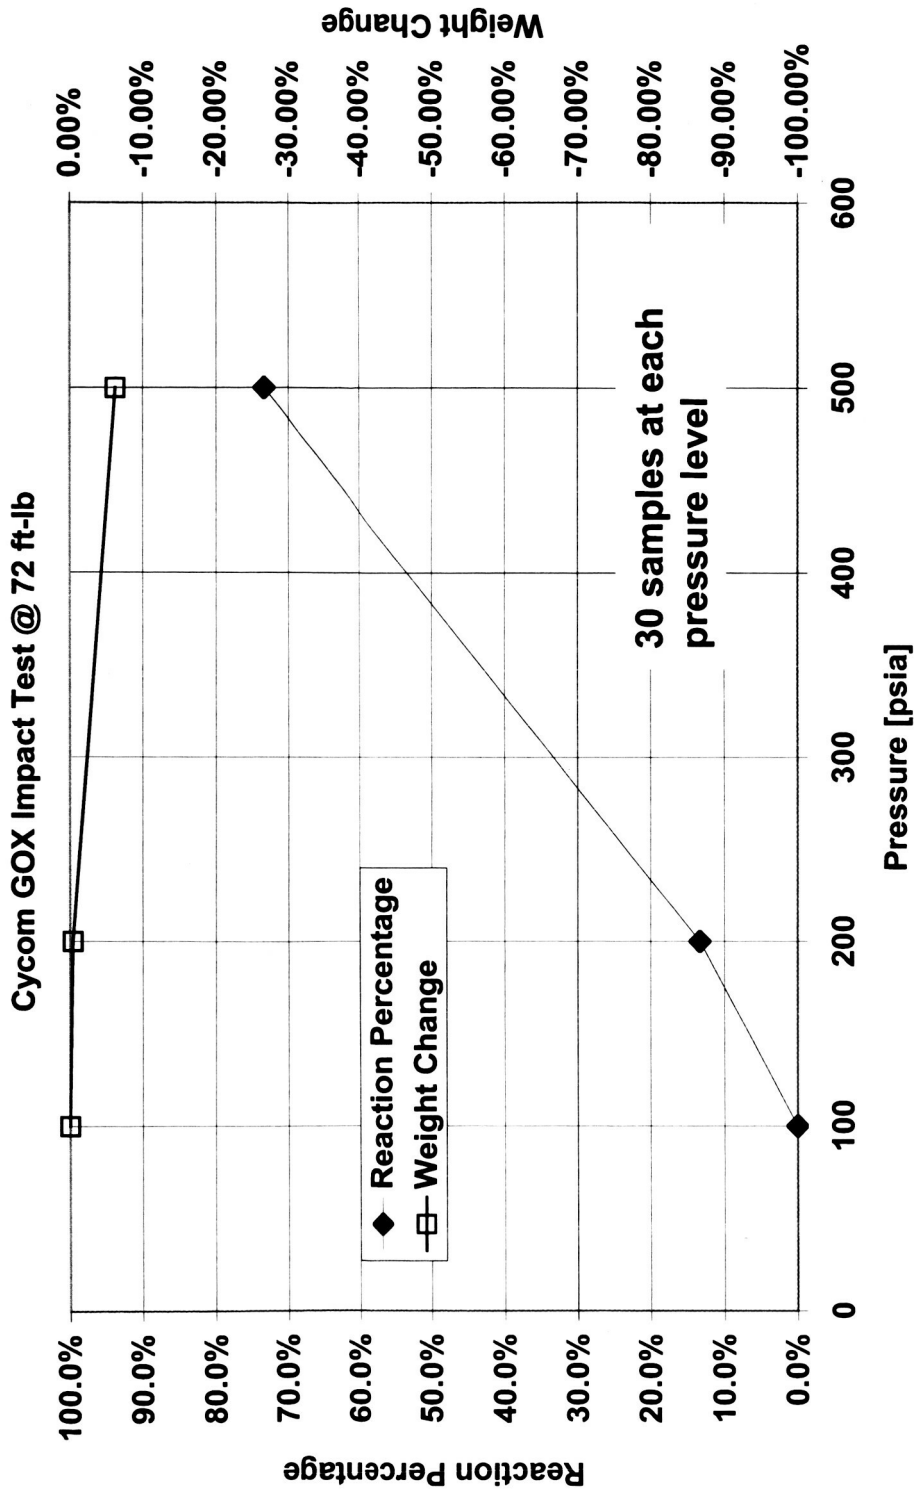



LOX/GOX Reaction Frequency Comparison

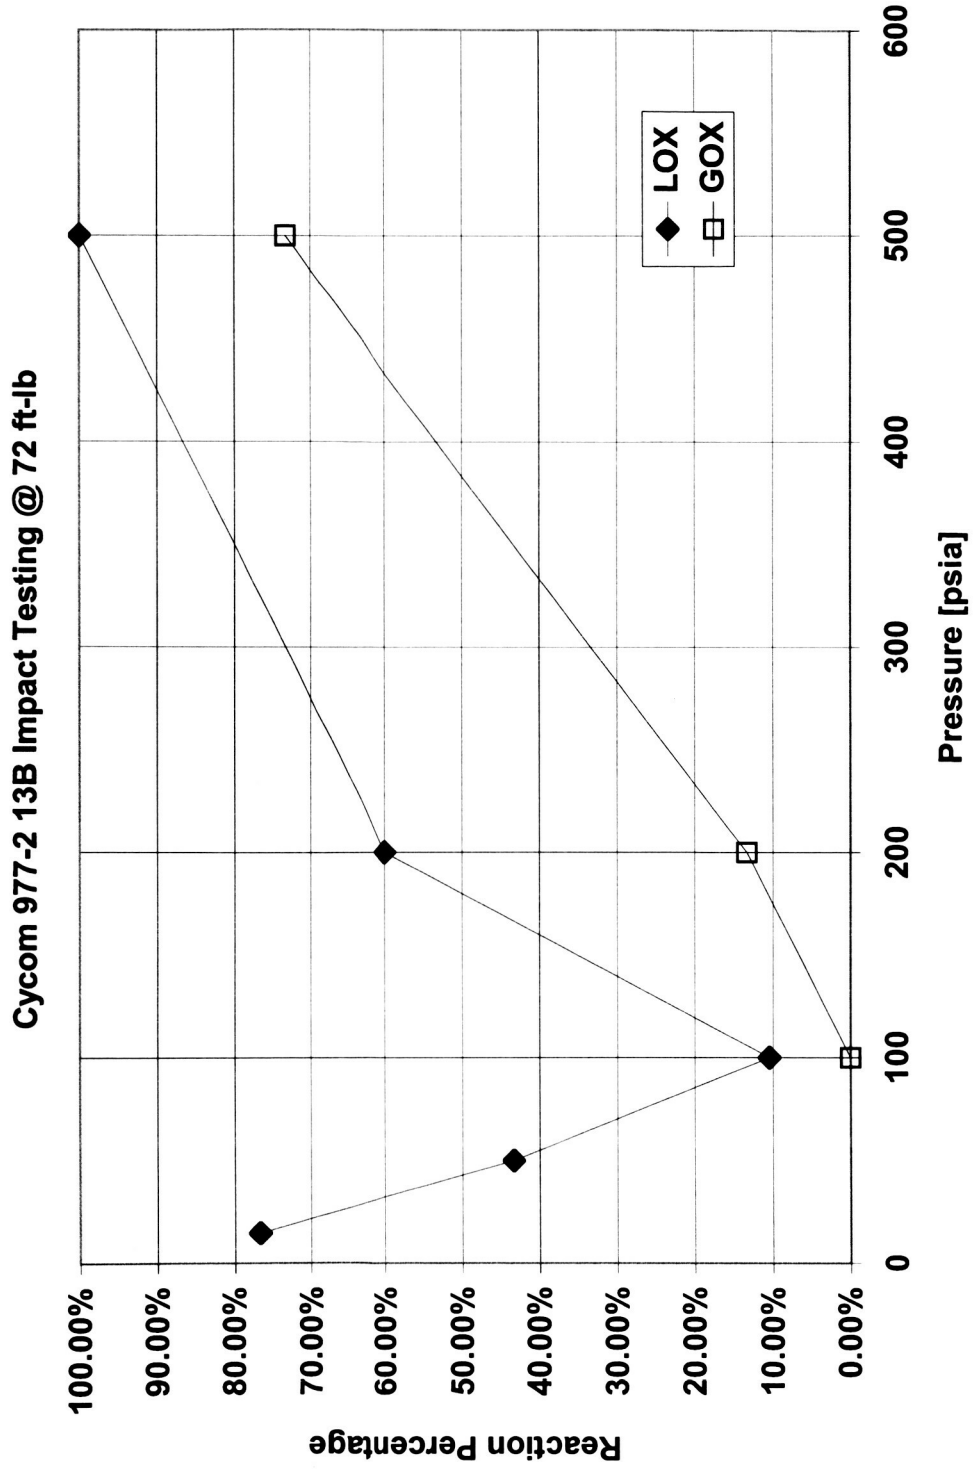



Phase IV Conclusions

- Phase IV 13A results were combined with Phases I to III data to provide a more complete reaction frequency data set.
- A small, but statistically insignificant, reduction in reaction frequency was observed by testing at double the sample dwell time before testing.
- Phase III and IV LOX data were combined to show a decrease in reaction frequency with increasing pressure and a corresponding increase in mass loss due to combustion.
- Cycom reaction frequency was shown to increase with pressure from 0% at 100 psia to xx% at 500 psia in GOX.



Overall Observations and Conclusions

- The reaction frequency data from 13A testing by MSFC and WSTF appear well behaved for the sample number used by each and exhibit the same type of energy level dependency. The reaction frequency shift in energy level is unexplained at this time.
- All the 13A data suggest that only a small amount of material is consumed when reactions take place.
- At ambient pressure, most if not all reactions are quenched as indicated by the small mass loss.
- As test pressure is increased in LOX, using 13B results,
 - The impact initiation has a greater probability of propagation.
 - The probability of ignition is reduced.
- Cycom does not support initiation of reactions or propagation of reactions in GOX at 100 psia based on tests at MSFC and WSTF at 72 ft-lb impact energy. Reactions do occur at higher test pressures.
- No batch effect was identified in LOX or GOX.



Recommendations


- **The technical community consider accepting a material for use, which exhibits consistent and universal quenching of impact induced reactions over the potential energy levels at the planned material use thickness.**
- **The technical committee formulating changes to NASA-STD- 6001 consider altering the testing method to require measurement of pre- and post-test weights.**
- **Impact combustion initiation be considered a quenched reaction when the mass loss is consistently below 10% of the pre-test mass when a reaction is observed.**
- **A quenched reaction condition be considered an acceptable risk similar to a flammability test burn length of less than 6.0 inches.**



In case we forget that initiation to sustained reaction of Cycom 977-2 can produce significant energy release, see the following slide.



**Impact Tester Vent Tube Burn Through
(Cycrom with LOX @ 500 psia & 72 ft-lb)**

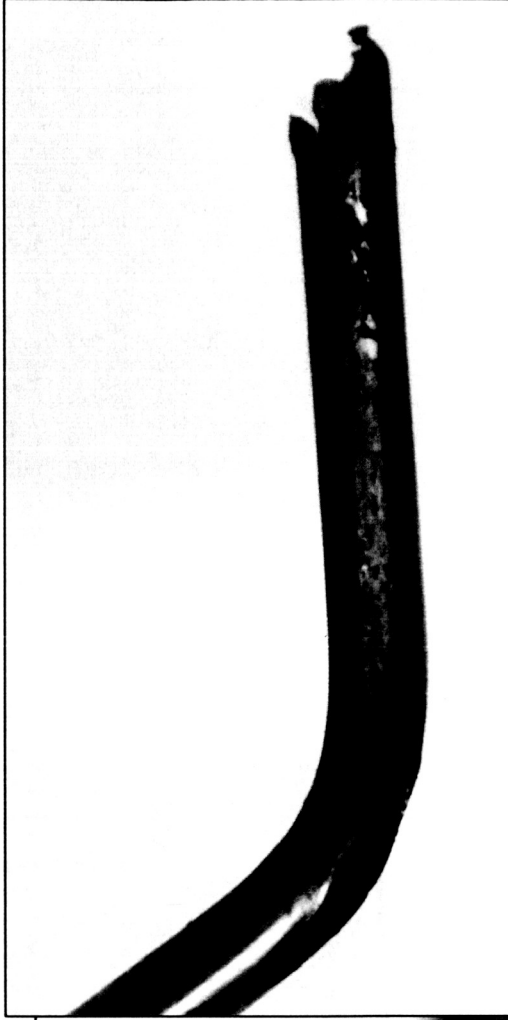

**Stainless Steel vent tube
Note: Less than 0.4 gm
of Cycrom consumed.**