

NASA/TP-2005-213906  
ARL-TR-3572



# Compression-Loaded Composite Panels With Elastic Edge Restraints and Initial Prestress

*Mark W. Hilburger and Michael P. Nemeth  
Langley Research Center, Hampton, Virginia*

*Jaret C. Riddick and Robert P. Thornburgh  
U.S. Army Research Laboratory  
Vehicle Technology Directorate  
Langley Research Center, Hampton, Virginia*

## The NASA STI Program Office . . . in Profile

Since its founding, NASA has been dedicated to the advancement of aeronautics and space science. The NASA Scientific and Technical Information (STI) Program Office plays a key part in helping NASA maintain this important role.

The NASA STI Program Office is operated by Langley Research Center, the lead center for NASA's scientific and technical information. The NASA STI Program Office provides access to the NASA STI Database, the largest collection of aeronautical and space science STI in the world. The Program Office is also NASA's institutional mechanism for disseminating the results of its research and development activities. These results are published by NASA in the NASA STI Report Series, which includes the following report types:

- **TECHNICAL PUBLICATION.** Reports of completed research or a major significant phase of research that present the results of NASA programs and include extensive data or theoretical analysis. Includes compilations of significant scientific and technical data and information deemed to be of continuing reference value. NASA counterpart of peer-reviewed formal professional papers, but having less stringent limitations on manuscript length and extent of graphic presentations.
- **TECHNICAL MEMORANDUM.** Scientific and technical findings that are preliminary or of specialized interest, e.g., quick release reports, working papers, and bibliographies that contain minimal annotation. Does not contain extensive analysis.
- **CONTRACTOR REPORT.** Scientific and technical findings by NASA-sponsored contractors and grantees.

- **CONFERENCE PUBLICATION.** Collected papers from scientific and technical conferences, symposia, seminars, or other meetings sponsored or co-sponsored by NASA.
- **SPECIAL PUBLICATION.** Scientific, technical, or historical information from NASA programs, projects, and missions, often concerned with subjects having substantial public interest.
- **TECHNICAL TRANSLATION.** English-language translations of foreign scientific and technical material pertinent to NASA's mission.

Specialized services that complement the STI Program Office's diverse offerings include creating custom thesauri, building customized databases, organizing and publishing research results ... even providing videos.

For more information about the NASA STI Program Office, see the following:

- Access the NASA STI Program Home Page at <http://www.sti.nasa.gov>
- E-mail your question via the Internet to [help@sti.nasa.gov](mailto:help@sti.nasa.gov)
- Fax your question to the NASA STI Help Desk at (301) 621-0134
- Phone the NASA STI Help Desk at (301) 621-0390
- Write to:  
NASA STI Help Desk  
NASA Center for AeroSpace Information  
7121 Standard Drive  
Hanover, MD 21076-1320

NASA/TP-2005-213906  
ARL-TR-3572



# Compression-Loaded Composite Panels With Elastic Edge Restraints and Initial Prestress

*Mark W. Hilburger and Michael P. Nemeth  
Langley Research Center, Hampton, Virginia*

*Jaret C. Riddick and Robert P. Thornburgh  
U.S. Army Research Laboratory  
Vehicle Technology Directorate  
Langley Research Center, Hampton, Virginia*

National Aeronautics and  
Space Administration

Langley Research Center  
Hampton, Virginia 23681-2199

August 2005

Available from:

NASA Center for AeroSpace Information (CASI)  
7121 Standard Drive  
Hanover, MD 21076-1320  
(301) 621-0390

National Technical Information Service (NTIS)  
5285 Port Royal Road  
Springfield, VA 22161-2171  
(703) 605-6000

## Abstract

*A parametric study of the effects of test-fixture-induced initial prestress and elastic edge restraints on the prebuckling and buckling responses of a compression-loaded, quasi-isotropic curved panel is presented. The numerical results were obtained by using a geometrically nonlinear finite element analysis code with high-fidelity models. The results presented show that a wide range of prebuckling and buckling behavior can be obtained by varying parameters that represent circumferential loaded-edge restraint and rotational unloaded-edge restraint provided by a test fixture and that represent the mismatch in specimen and test-fixture radii of curvature. For a certain range of parameters, the panels exhibit substantial nonlinear prebuckling deformations that yield buckling loads nearly twice the corresponding buckling load predicted by a traditional linear bifurcation buckling analysis for shallow curved panels. In contrast, the results show another range of parameters exist for which the nonlinear prebuckling deformations either do not exist or are relatively benign, and the panels exhibit buckling loads that are nearly equal to the corresponding linear bifurcation buckling load. Overall, the results should be of particular interest to scientists, engineers, and designers involved in simulating flight-hardware boundary conditions in structural verification and certification tests, involved in validating structural analysis tools, and interested in tailoring buckling performance.*

## Introduction

Curved panels are a common structural element found in many aerospace vehicles. With the need to reduce structural weight of aircraft and to exploit stiffness tailoring of fiber-reinforced, laminated-composite materials to enhance performance, there has come the need to understand the behavioral characteristics of thin-walled curved panels that may possess high degrees of material orthotropy and anisotropy. Orthotropy and anisotropy are manifested physically by couplings between deformation modes such as extension, bending, and twisting. These coupled deformations may enable the design of special-purpose, high-performance components that meet strict structural requirements. Because these structures are typically thin walled and are often subjected to compression loads, predicting their prebuckling and buckling behaviors is of fundamental importance. A necessary step in developing this predictive capability is the development of high-fidelity analysis capabilities and the corresponding validation procedures.

Significant advances in high-fidelity nonlinear finite-element analysis methods and validation-experiment requirements for buckling of thin-walled, laminated-composite cylindrical shells have been made in recent years (e.g., see ref. 1). These analysis methods are mature and lend themselves to compression-loaded curved panels, but the validation of these methods for curved panels is much less mature. The primary reasons for this lack of maturity, compared to that for compression-loaded cylindrical shells, are that laboratory testing of curved panels requires more complex fixtures to facilitate load introduction and edge support. Furthermore, the effects of the test fixture on the load introduction and edge support conditions can be difficult to characterize. These issues are significant because careful attention to the implementation and characterization of load introduction and edge support conditions used for validation tests is necessary to achieve relevancy and usefulness of a validation experiment in the development of practical structural design data. In particular, the test results may not be relevant if the test configuration does not accurately represent the structural configuration in question. Similarly, the test

data may be of limited use for model validation purposes if the load introduction and edge support conditions are not accurately characterized and thus are not properly accounted for in the analysis.

Many theoretical and experimental studies that are relevant to validation of high-fidelity analysis methods for buckling of compression-loaded curved panels have been conducted during the last thirty years (refs. 2-8). In particular, these studies have examined the effects of panel curvature, initial geometric imperfections, boundary conditions, and laminate stacking sequence on the buckling behavior. Many of these studies have shown significant discrepancies between the experimentally determined buckling loads and the corresponding analytical buckling predictions (refs. 5, 6 and 8). These discrepancies have been attributed to various effects such as improper simulation of boundary conditions, initial geometric imperfections, and initial prestress caused by mismatches between panel and test-fixture geometries. For example, experimental results obtained by Hui (ref.4) for buckling of symmetric cross-ply laminates show that compression-loaded curved panels can exhibit buckling loads greater than the corresponding classical, linear-bifurcation buckling load if an initial geometric imperfection in the form of an outward bulge is present in the panel. This result is in complete agreement with the unstable, asymmetric bifurcation behavior predicted by even simple analytical methods for compression-loaded curved panels (ref. 9).

Khot and Bauld (ref. 5) conducted an experimental study of the buckling response of compression-loaded curved panels made from specially orthotropic laminates that is particularly relevant to the development of validation experiments. In this study, the experimentally measured buckling loads were found to be bounded by the predicted buckling loads for the case where the circumferential displacements on the curved loaded edges are unrestrained (free circumferential expansion) and for the case where these displacements are fully restrained. The bounding of the experimental buckling loads by the analytical predictions for these two extreme, idealized boundary conditions was attributed to the presence of circumferential slippage of the panel edges in the test fixture, which was observed during the tests. It was also noted in this study that some of the geometrically imperfect panel specimens had to be forced slightly into the more geometrically precise test fixture, which produced initial stress and deformation states prior to compression loading. It was speculated that perhaps these test-fixture-induced states could have an influence on the buckling resistance that is comparable to that of an initial geometric imperfection.

Wilkins (ref. 6) conducted extensive buckling tests of compression-loaded, laminated-composite curved panels and suggested that friction between the test fixture and the specimen can affect the panel response. Wilkins minimized the friction that develops between the test fixture and the specimen by bordering the specimen edges with 0.003-in-thick Teflon tape. In addition, Wilkins showed that test-fixture edge supports that are intended to simulate simply supported boundary conditions on the unloaded edges actually provide a slight rotational constraint. For the curved panels he considered, the maximum value of the restraining moment was found to be approximately 10 in-lb/in. along the length of the panel edge. However, this restraining moment was determined to have a negligible effect on the magnitude of the buckling load of the panels considered.

A recent numerical and experimental study by Hilburger et. al (ref. 8) also investigated the effects of friction-induced circumferential edge restraint on the prebuckling and buckling response of compression-loaded, quasi-isotropic curved panels. Specifically, experimental results were obtained that revealed a significant amount of nonlinear prebuckling deformation. In addition, the experimental buckling loads were nearly twice the classical linear-bifurcation buckling load predicted by using a finite-element analysis. The experimental buckling load was found not to be bounded by the corresponding predicted buckling loads for the case where the circumferential displacements on the curved loaded edges are unrestrained (free circumferential expansion) and for the case where these displacements are fully restrained. This inability to bound the results for these two extreme boundary conditions led to the development and use of a finite-element model that simulates test-fixture-induced frictional forces by using circumferentially aligned elastic springs distributed along the curved, loaded edges of the panel.

The numerical results obtained with this enhanced finite-element model indicate that a panel with circumferential edge restraint provided by the elastic springs can exhibit significant nonlinear prebuckling deformations that are caused by a nonlinear coupling between the circumferential and out-of-plane displacements near the loaded edges. Additionally, the nonlinear prebuckling deformations result in a net radially outward bulge of the panel prior to buckling that increases the buckling resistance in the same manner as reported by Hui (ref. 4) for initial geometric imperfections. Moreover, the results obtained by using the springs at the loaded edges appear to more accurately represent the experimentally measured results and suggest that some amount of circumferential restraint of the loaded edges was present in the experimental setup.

The results presented in the literature reviewed herein indicate several factors related to load introduction, boundary conditions, and geometry that must be well understood in order to develop experiments that are adequate for validating analysis methods for laminated-composite curved panels. Three factors considered in this paper are the effects of circumferential edge restraint, the effects of rotational edge restraint, and the effects of a geometric mismatch between the panel and test-fixture at the support locations. Thus, the objective of the present study is to quantify these three effects, and their interactions, for the baseline case of a compression-loaded, quasi-isotropic composite curved panel by using high-fidelity nonlinear finite-element analyses. Toward this goal, results of a parametric study are presented that encompass a wide range of circumferential and rotational edge-restraint conditions and initial stress and deformation states associated with forcing a geometrically imperfect panel specimen into a more geometrically precise test fixture, prior to application of the destabilizing compression load. First, the finite-element model and analysis method are described. Then, results that illustrate the individual contributions of each of the three effects on the prebuckling and buckling response are presented and discussed. Lastly, results that show the nonlinear interaction of the three effects are presented.

## Finite-Element Model and Analysis Method

The panels considered in this study were analyzed with the STAGS (STRUCTURAL ANALYSIS of General Shells) nonlinear shell analysis code (ref. 10). STAGS is a finite-element code designed for the static and dynamic analysis of general shells, and includes the capability to model the effects of geometric nonlinearities. A typical finite-element model of a curved shell is shown in figure 1. Points making up the panel mid-surface are located by an  $x$ - $y$ - $z$  curvilinear coordinate system, with the origin at the center of the panel. The mid-surface axial, circumferential, and out-of-plane displacements are defined as  $u(x, y)$ ,  $v(x, y)$ , and  $w(x, y)$ , respectively, as shown in figure 1. Here, the term "out-of-plane" refers to the displacement that is normal to the tangent plane at a given point of panel mid-surface. For the case studied, the nominal panel radius  $R$  is 60 in. and the panel length  $L$  and arc width  $W$  are 14.75 in. and 14.5 in., respectively. The panel is modeled as a 24-ply-thick  $[\pm 45/0/90]_{3s}$  quasi-isotropic graphite-epoxy laminate with a nominal ply thickness of 0.005 in. and a total, nominal panel thickness of 0.12 in. The lamina material properties are as follows: longitudinal modulus  $E_1 = 18.5$  Msi, transverse modulus  $E_2 = 1.64$  Msi, inplane shear modulus  $G_{12} = 0.87$  Msi, and major Poisson's ratio  $\nu_{12} = 0.304$ .

Idealizations of the test-fixture support conditions were used in the finite-element model, referred to herein as the nominal boundary conditions, and are defined as follows. On the clamped loaded edges, the out-of-plane displacement  $w$ , is set equal to zero in the boundary regions of the finite-element model that extend 3/8 in. from both loaded ends of a panel (see figure 1). The compression load is introduced into the panel by applying a uniform end shortening displacement  $\Delta$  to one end of the model while holding the other end of the panel fixed on the boundary; that is,  $u(-L/2, y) = \Delta$  and  $u(L/2, y) = 0$ . The simply supported boundaries on the unloaded edges (knife-edge supports) were simulated by setting the out-of-plane displacement,  $w$ , equal to zero on a line 3/16 in. from each unloaded edge of a panel. The finite-element model uses four-noded, flat facet-type elements that are based on the kinematic hypothesis of Kirchhoff-Love thin-shell theory and the nonlinear Lagrangian strain tensor. The element nodes include

three translational degrees of freedom ( $u$ ,  $v$ ,  $w$ ) and three rotational degrees of freedom. The rotational degrees of freedom are denoted by  $r_x$ ,  $r_y$ , and  $r_z$  and correspond to rotations about the  $x$ ,  $y$ , and  $z$  axes, respectively. Large rotations are accounted for by using a co-rotational algorithm.

The STAGS finite-element code uses both the modified and full Newton methods for its nonlinear solution algorithms. The Riks pseudo arc-length path-following method (ref. 10) is used to continue a solution past the limit points of a nonlinear response. In this computational approach, the incrementally applied loading parameter is replaced by an arc length along the solution path, which is then used as the independent loading parameter. The arc-length increments are automatically adjusted by the program as a function of the nonlinearity exhibited in the solution.

The analysis considers idealized, geometrically perfect panels with nominal boundary conditions and panels having elastic boundary restraints with initial stress and deformation states caused by a mismatch between the panel and test-fixture geometry. In particular, two distinct elastic boundary restraints are considered; that is, elastic circumferential and elastic rotational edge restraints. An elastic circumferential edge restraint was applied to the curved, loaded edge as a “first-order” approximation of the frictional forces generated between the test fixture and the panel specimen. The elastic circumferential edge restraint is simulated in the finite element model by adding a linear spring-stiffness contribution  $K_v$  directly to the stiffness of the elements in the curved, loaded boundary that are indicated in figure 1. The magnitude of  $K_v$  varied from a value of 0.0 lb/in., corresponding to unrestrained circumferential motion, to a relatively high value of  $1.0 \times 10^9$  lb/in. In addition, complete circumferential restraint at the loaded edges, given by  $v = 0$ , was also evaluated. As a point of reference, the circumferential membrane stiffness ( $A_{22}$ ) of the panel is  $9.22 \times 10^5$  lb/in.

To better understand the effects of the restraint generated by the knife-edge supports on the unloaded edges of the panels, an elastic rotational edge restraint was applied to each unloaded edge that is representative of a “first-order” approximation to the true support condition. The elastic rotational edge restraint is simulated in the finite-element model by a beam on both sides of the panel that has a prescribed torsional stiffness and values for the bending and extensional stiffness that are equal to zero. The magnitude of the torsional stiffness  $K_\theta$  varied from a value of 0.0 lb-in, corresponding to free rotation, to a relatively high value of  $1.0 \times 10^9$  in-lb. In addition, complete rotational restraint at the unloaded edges (i.e., clamped), given by  $r_x = 0$ , was also considered. As a point of reference, the corresponding circumferential bending stiffness ( $D_{22}$ ) of the panel is  $1.2 \times 10^3$  in-lb.

Initial stress and deformation states caused by a geometric mismatch between the panel and the test fixture at the edge supports were also modeled. For conciseness, these states are referred to herein collectively as a prestress state or a prestress condition. For example, the test fixture used in ref. 8, and modeled in the present study, is made for a 60-in-radius curved panel, however, because of residual stresses from the curing process, the curved laminated-composite test specimens had a measured average constant radius of about 53 to 54 in. Thus, when a panel was inserted into the 60-in-radius fixture, the panel was forced to conform to the shape of the fixture, which generates unknown stresses and deformations in the panel. This misfit condition is modeled by first simulating a stress-free panel with an initial radius of  $R_i$  that represents the as-built average panel radius. Then, displacements are applied to the edges of the panel that simulate insertion of the panel into the 60-in-radius test fixture. The deformation associated with inserting the panel in the fixture is accomplished by applying an out-of-plane displacement to all the nodes on the edges that are based on the difference between the initial, as-built panel radius and the test-fixture radius. After the initial stress and deformation states are applied to the panel, the destabilizing compression load is applied by prescribing a uniform end shortening that is increased monotonically from a value of zero.

Model convergence studies and model verification studies were conducted at various stages in the development of the finite-element models to verify the adequacy of each model. Specifically, convergence studies on the mesh refinement were conducted for each panel configuration; e.g., panel



configurations with elastic edge restraint only, initial prestress only, and combinations of elastic edge restraint and initial prestress. The convergence criteria used in the study required that the buckling load could not change by more than one percent with additional mesh refinement. In addition, the convergence criteria required that the overall predicted global response characteristics could not change with additional mesh refinement, e.g., the load-shortening response curves and the prebuckling and buckling displacements. The rationale for using a convergence criteria with requirements on the buckling load as well as other global response characteristics is to assure convergence on the correct overall panel response and not just the value for the buckling load. Model verification studies were also conducted to insure that the model inputs were correct. For example, the displacements applied to the clamped boundary region of the panel that were used to simulate the mismatch between the panel and the fixture geometry were verified by comparing the displacements reported in the finite-element model output file with the displacements predicted by basic analytical geometry.

## Results and Discussion

Numerical results are presented in this section for 60-in-radius, quasi-isotropic panels that are subjected to uniaxial compression loads. First, results are presented that show the effects of elastic circumferential edge restraints applied to the curved, loaded edges of the panels. Similar results that have been presented in ref. 8 are included herein for completeness. Then, results are presented that show the effects of elastic rotational restraints applied to the straight, unloaded edges of the panels. Next, results are presented that show the effects of the initial prestress condition that is caused by the panel-test-fixture misfit. Finally, results are presented that show the interaction effects for various combinations of elastic edge restraint and initial misfit prestress. The values of the axial load  $P$  and buckling loads  $P_{cr}$  are normalized by the linear-bifurcation buckling load of a geometrically perfect, quasi-isotropic panel with nominal dimensions and boundary conditions; that is,  $P_{cr}^o = 15.78$  kips (1 kip = 1000 lbs). Various displacement quantities presented herein are normalized by either the nominal panel thickness,  $t = 0.13$  in., the nominal panel length,  $L = 14.75$  in., or the nominal panel width,  $W = 14.5$  in.

### Elastic Circumferential Edge Restraint

Results that show the effects of elastically restraining the circumferential movement of the loaded edges on the normalized buckling load are presented in figures 2-5. Specifically, load-shortening response curves for the geometrically perfect, quasi-isotropic panel with nominal dimensions and different degrees of circumferential restraint on the loaded edges are presented in figure 2. The corresponding curves for load versus normalized central out-of-plane displacement  $\delta/t$  are shown in figure 3, where  $\delta = w(0, 0)$ . Positive values of  $\delta/t$  correspond to movement of the center of the panel outward, away from the center of curvature. Similarly, the corresponding curves for load versus normalized circumferential displacement  $v_o/W$  at one corner of the panel is shown in figure 4, where  $v_o = v(L/2, -W/2)$ . Negative values of  $v_o/W$  correspond to circumferential Poisson-like expansion that is normally associated with an axially compressed panel. Two curves are shown in each of figures 2-4 that correspond to values of the circumferential edge-restraint stiffness  $K_v = 0$  lb/in. (unrestrained) and  $K_v = 10^7$  lb/in., which is approximately 10.8 times the circumferential stiffness ( $A_{22}$ ). A third curve is shown in each figure for the case of complete edge restraint, for which  $v = 0$  at the loaded edges. The curves include the results for the prebuckling and postbuckling range of loading. The point at which buckling occurs for each case is marked on the curves with filled circles. Contour plots of the corresponding out-of-plane displacement field at the onset of buckling are shown in figures 5(a-c) for the three edge-restraint cases. The slight skewing that appears in the contour plots is associated with a relatively small degree of flexural anisotropy.

The results in figures 2-4 indicate that the degree of circumferential edge restraint on the curved loaded edges of the compression-loaded panel has a significant effect on the response. For the case of

unrestrained edges ( $K_v = 0$ ), the load-shortening response curve shown in figure 2 is linear up to the buckling point at  $P/P_{cr}^o = 0.98$ . Likewise, the corresponding center out-of-plane displacement shown in figure 3 is slightly inward prior to buckling, and the loaded edge of the panel undergoes circumferential expansion (figure 4), as expected for a circumferentially unrestrained edge. Near the buckling point, and in the postbuckling range of loading, the magnitude of the center out-of-plane displacement increases to many times the wall thickness of the panel. For the value of  $K_v = 10^7$  lb/in., the load-shortening behavior is different from the case of unrestrained edges. For this case, the load-shortening response curve (figure 2) shows nonlinearity in the form of a slope change above  $P_{cr}/P_{cr}^o = 1$ , and it has a relatively high buckling load of  $P_{cr}/P_{cr}^o = 1.95$ . This nonlinearity in the response curve is caused by coupling of the circumferential and out-of-plane displacements near the loaded edges, which produce an outward bulge in the panel as the loading increases. The coupling of the displacement fields is indicated in figure 4 by the initial, slight circumferential expansion followed by circumferential contraction that is caused by local out-of-plane deformation. The outward bulge is evidenced by the corresponding monotonically increasing central out-of-plane displacement shown in figure 3 and the displacement contours shown in figure 5(b). The outward bulge acts to stiffen the panel, by increasing the moment of inertia in the central region, and raises the buckling resistance in the same manner as reported by Hui (ref. 4) for panels with a geometric imperfection in the shape of an outward bulge. For the case with fully restrained loaded edges ( $\nu = 0$ ), the panel exhibits much less nonlinearity in its load-shortening response curve (figure 2), compared to the curve for  $K_v = 10^7$  lb/in. In addition, a less pronounced outward bulge (figures 3 and 5(c)) and a lower buckling load given by  $P_{cr}/P_{cr}^o = 1.52$  is predicted for the panel with fully restrained loaded edges.

Overall, the results in figures 2-5 show that prebuckling deformations retard the onset of buckling and result in increases in the buckling load of about 55% and 99%, with respect to the buckling load predicted for the panel with the loaded edges unrestrained, for the circumferential edge-restraint conditions defined by  $\nu = 0$  and  $K_v = 10^7$  lb/in., respectively. Moreover, the results (figure 5) show that the prebuckling deformations are very sensitive to changes in the circumferential boundary condition. For example, the out-of-plane prebuckling displacements shown for the case of unrestrained edges ( $K_v = 0$ ) are characterized by a large, centrally located ellipse-shaped contours and an inward deformation pattern. For a value of  $K_v = 10^7$  lb/in., the predicted displacement contours are characterized by a hour-glass-like pattern, with maximum displacements on the order of 2.6 times the nominal panel wall thickness (figure 5(b)). For  $\nu = 0$ , the displacement contours are characterized by a centrally located ellipse-shaped outward deformation pattern and the maximum displacement of about 1.5 times the nominal panel thickness (figure 5(c)). It is important to note that the results are contrary to intuition in that they predict that the magnitude of the buckling loads and the severity of the nonlinear prebuckling deformations are not bounded by the corresponding results for the extreme boundary conditions defined by  $K_v = 0$  (unrestrained) and  $\nu = 0$  (completely restrained).

The predicted effects of elastic circumferential edge restraint on the magnitude of the buckling load are presented in figure 6 as a function of the circumferential stiffness parameter  $K_v$ . The buckling load values are marked in the figure by filled square symbols and can be placed into three distinct groups that were found to exhibit similar prebuckling behavioral characteristics. The first group of results is for  $0 < K_v < 10^{5.2}$  lb/in. Panels with edge-restraint stiffnesses in this group exhibit a linear prebuckling load-shortening response that is similar to that predicted for  $K_v = 0$ , shown in figure 2. The normalized buckling load values for this group are all between 0.98 and 1.15. In addition, these panels exhibit prebuckling displacements similar to those shown in figures 3-5 for  $K_v = 0$ . The second group of results are for panels with edge-restraint stiffnesses in the range  $10^{5.2}$  lb/in.  $< K_v < 10^{7.2}$  lb/in. Panels in this group are predicted to exhibit some nonlinearity in their prebuckling response; that is, similar to the response characteristics shown in figures 2-5 for the panel with  $K_v = 10^7$  lb/in. Specifically, the prebuckling load-shortening response curves exhibit a nonlinear response above a load level of  $P/P_{cr}^o = 0.95$ , and the buckling loads are on the order of two times the linear-bifurcation buckling load for the corresponding unrestrained panel. The third group of results is for panels with edge-restraint stiffnesses in the range  $K_v > 10^{7.2}$  lb/in. The panels associated with this group are predicted to exhibit response characteristics similar

to those predicted for the fully restrained case ( $\nu = 0$ ), as shown in figures 2-5. The portion of the curve shown in figure 6 for this group converges from above to the value of  $P_{cr}/P_{cr}^o = 1.52$ , which is the value for the fully restrained panel.

### Elastic Rotational Edge Restraints

Results that illustrate the effects of elastic rotational edge restraints on the buckling response of a compression-loaded curved panel are presented in figures 7-10. Specifically, load-shortening response curves for a compression-loaded panel with different degrees of rotational edge restraint on the straight, unloaded edges of the panel are presented in figure 7. The corresponding curves for load versus normalized central out-of-plane displacement  $\delta/t$  are shown in figure 8, where  $\delta = w(0, 0)$ . Three curves are shown in each of figures 7 and 8 that correspond to rotational edge restraint stiffnesses of  $K_\theta = 0$  (equivalent to the classical simply supported boundary condition),  $K_\theta = 10^3$  in-lb, and the fully restrained case; that is,  $r_x(x, -W/2 + 3/16 \text{ in.}) = r_x(x, W/2 - 3/16 \text{ in.}) = 0$ . The buckling points are marked with the filled circles.

The results in figures 7 and 8 indicate that the rotational edge restraint has a relatively small effect on the response and the buckling load of the panel. In particular, the load-shortening response curves are linear up to buckling and the buckling loads range from  $P/P_{cr}^o = 0.98$  to 1.08. The effective postbuckling stiffness increases slightly as the rotational constraint stiffness increases. This increase in postbuckling stiffness is caused by a reduction in the out-of-plane postbuckling deformations in the panel at a given load level, as shown in figure 8, and a subsequent increase in the effective load-carrying cross-section of the panel. The results in figure 8 indicate that the prebuckling center displacement of the panel is small and inward. However, near the buckling point, and in the postbuckling range of the loading, the center displacement increases to many times the wall thickness of the panel. For all cases, the predicted out-of-plane displacement contours at the onset of buckling are similar in character to that exhibited by a panel with nominal boundary conditions ( $K_\nu = 0$ ) and are characterized by a large ellipse-shaped inward deformation pattern (e.g., see figure 5(a)).

A summary of the predicted effects of the rotational edge restraint on the buckling load of the panel is presented in figure 9. These results indicate that the buckling load increases very slightly from  $P_{cr}/P_{cr}^o = 0.98$  to 1.08, as  $K_\theta$  increases from 0 to  $10^9$  in-lb, which is somewhat counterintuitive. This slight increase in the buckling load occurs in a transition zone for  $10^2 \text{ in-lb} < K_\theta < 10^4 \text{ in-lb}$ , in which the panel displacement response near the restrained edge transitions from the response for a simply supported edge to that for a clamped edge. More specifically, displacement traces for the panel with various rotational edge restraints are shown in figure 10 and illustrate the effects of the rotational restraint on the deformation response near the unloaded edge of the panel. These displacement traces are taken at the panel mid-length and span the panel arc from  $y = 0$  to  $y = W/2$ . It is important to point out that the curves shown in this figure are not bounded by the curves that correspond to the classical simply supported and clamped boundary conditions because the curves correspond to different load levels incipient to buckling.

For values of  $K_\theta < 10^2$  in-lb, the displacement response near the rotational restraint is similar to a free-rotation response that occurs with a classical simply supported boundary condition, as indicated in figure 10. For  $10^2 \text{ in-lb} < K_\theta < 10^4 \text{ in-lb}$ , the panel exhibits a significant reduction in the rotation near the unloaded edge and a reduction in the magnitude of the out-of-plane deformations at buckling, as compared to the simply supported boundary condition. For  $K_\theta > 10^4$  in-lb, the panel exhibits a similar displacement response to that of the fully restrained edge condition corresponding to  $r_x = 0$ .

Given the significant variation in the deformation response near the unloaded edge shown in figure 10, one might expect a much larger increase in the buckling load with an increase in the degree of rotational edge restraint. To address this expectation, and to understand better the panel behavior, a numerical parametric study of the effects of the panel (length-to-arc-width) aspect ratio,  $L/W$ , on the buckling response was conducted. Predicted buckling loads are plotted as a function of  $L/W$  for  $K_\theta = 0$

and  $r_x = 0$  in figure 11. The curves shown in this figure are festoon curves, similar to the well-known corresponding festoon curves for buckling of flat, compression-loaded rectangular plates (e.g., see ref. 11). The results indicate that the sensitivity of the panel response to variations in the degree of rotational restraint is clearly dependent on the panel aspect ratio. In addition, the results show that the particular panel configuration considered herein exhibits a relatively small difference between the buckling load for a panel with clamped unloaded edges and the buckling load of a panel with simply supported unloaded edges, at  $L/W = 1.02$ . Comparing these curves with the corresponding curves shown in ref. 11 for flat isotropic plates suggests that panel curvature amplifies the effect of clamping the loaded edges of the panels to the extent that the differences in buckling load associated with restraining the unloaded edges becomes less noticeable. This behavior would account for the relatively small variation in buckling load with  $K_\theta$  that is shown in figure 9.

### Initial Misfit Prestress

Results that illustrate the effects of an initial misfit prestress (also referred to herein as an initial panel misfit) on the buckling response of the compression-loaded, quasi-isotropic curved panels considered herein are presented in figures 12-17. As discussed previously, the initial misfit prestress is caused by a mismatch between a 60-in-radius test fixture and a stress-free panel with a different initial radius  $R_i$ , and is comprised of panel deformations and stresses that result from forcing the panel to conform to the 60-in-radius fixture. Displacement contours associated with the initial prestress of panels with initial radii  $R_i$  equal to 52-in., 56-in., and 64-in. are presented in figure 12. Each panel configuration has two displacement contour plots associated with it. The first contour plot for each panel (figures 12(a)-1, 12(b)-1, and 12(c)-1) shows the predicted out-of-plane deformation that results from placement in the test fixture, as measured with respect to corresponding initial, undeformed geometry. The second contour plot for each panel (figures 12(a)-2, 12(b)-2, and 12(c)-2) shows the predicted deformed panel geometry, as measured with respect to a geometrically perfect 60-in-radius panel and is analogous to an initial geometric imperfection shape that is commonly used in shell buckling analyses. In general, the results indicate that the initial prestress deformations of the panels with  $R_i < 60$  in. are outward bulges with magnitudes equal to 1-3% of the nominal wall thickness (see figures 12(a)-2, 12(b)-2). In contrast, panels with  $R_i > 60$  in. exhibit initial prestress deformations that are inward bulges, as shown in figure 12(c)-2. In addition, initial inplane stress resultants and moment resultants were predicted for each case (not presented herein) and indicate that the stresses caused by forcing the panels into the test fixture are typically several orders of magnitude smaller than the corresponding stresses at the onset of buckling.

Load-shortening response curves for panels with different amounts of prestress are presented in figure 13. The corresponding curves for load versus normalized central out-of-plane displacement  $\delta/t$  are shown in figure 14, where  $\delta = w(0, 0)$ . Similarly, the corresponding curves for load versus normalized circumferential displacement  $v_o/W$  at one corner of the panel are shown in figure 15, where  $v_o = v(L/2, -W/2)$ . The initial center displacements and circumferential displacements for  $P/P_{cr}^o = 0$  in figures 14 and 15 are attributed to the initial prestress deformation response that occurs in the panels before the compression load is applied. Four curves are shown in each of figures 13-15 that correspond to panels with initial radii  $R_i$  equal to 52 in., 56 in., 60 in. (no prestress), and 64 in., and illustrate the overall effects of an initial prestress on the compression response. The buckling points are marked with filled circles.

The results in figures 13-15 indicate that the level of initial prestress in the panel has a significant effect on the prebuckling response. Panels with  $R_i = 60$  in. (no prestress) and 64 in. exhibit linear prebuckling load-shortening response curves and have normalized buckling loads of 0.98, and 0.90, respectively. Likewise, the corresponding center out-of-plane displacement shown in figure 14 is small and inward prior to buckling, with the displacements for the 60-in. panel being practically negligible, and the loaded edges undergo circumferential expansion, as shown in figure 15. The panel with  $R_i = 56$  in. exhibits a similar linear prebuckling load-shortening response and has normalized buckling loads of 1.17. However, the corresponding center out-of-plane displacement shown in figure 14 is small and outward

prior to buckling. In addition, the load edge initially undergoes circumferential expansion followed by slight circumferential contraction at approximately  $P/P_{cr}^o = 1.02$ , as shown in figure 15.

For a panel with an initial radius  $R_i = 52$  in., the behavior is significantly different. For this case, the panel exhibits a significant increase in the nonlinearity of the prebuckling response beyond a load level of  $P/P_{cr}^o = 1.2$  and buckles at  $P/P_{cr}^o = 1.80$ . This nonlinearity in the response is caused by a coupling between the out-of-plane and circumferential displacements near the loaded edges of the panel, which produces an outward central displacement of the panel as loading increases. The strong coupling of the displacement fields is indicated in figure 15 by the initial, slight circumferential expansion followed by circumferential contraction that is caused by local bending. The outward prebuckling deformation is evidenced by the corresponding monotonically increasing central out-of-plane displacement shown in figure 14 and the displacement contours shown in figure 16(a). This response is similar in character to the response previously described for a geometrically perfect panel with a tangential, loaded-edge stiffness given by  $K_v = 1.0 \times 10^7$  lb/in. (see Figs 2-5). Overall, the results for  $R_i = 52$  in. and 56 in. shown in figures 13-16 indicate that the outward prebuckling deformations retard the onset of buckling and result in increases in the buckling load of about 84% with respect to the buckling load of the panel with no initial prestress. Moreover, the results in figure 16 indicate that the prebuckling displacement response can change greatly as the initial prestress in the panel changes. In particular, the results show that panels with  $R_i \leq 55$  in. exhibit prebuckling displacements that are characterized by an hour-glass-like pattern with maximum displacements of approximately three times the nominal panel wall thickness, as shown in figure 16(a). This displacement pattern is very similar to that exhibited by the corresponding geometrically perfect panel with the circumferential edge restraint  $K_v = 10^7$  lb/in. that is shown in figure 5(b). Panels with  $55 \text{ in.} < R_i < 60 \text{ in.}$  exhibit prebuckling deformations that are characterized by a large centrally located ellipse-shaped outward deformation pattern with maximum displacements of approximately 60% of the nominal panel wall thickness, as shown in figure 16(b). This displacement pattern is very similar to that of the corresponding geometrically perfect panel with the fully restrained circumferential edge condition,  $\nu = 0$ , shown in figure 5(c). Finally, panels with  $R_i = 64$  in. exhibit a prebuckling displacement response that is characterized by a large centrally located ellipse-shaped inward deformation pattern, as shown in figure 16(c), that is similar to that of a geometrically perfect panel with a circumferential edge restraint that ranges from  $0 < K_v < 10^3$  lb/in., as shown in figure 5(a).

The predicted effects of the initial, test-fixture induced prestress on the magnitude of the buckling load of the panel are summarized in figure 17. The buckling load values are marked in the figure by filled square symbols and can be divided into three groups; that is,  $R_i < 55$  in.,  $55 \text{ in.} < R_i < 60$  in., and  $R_i > 60$  in. In general, panels with  $R_i \geq 60$  in. exhibit a linear prebuckling load-shortening response and inward prebuckling displacements similar to those predicted for panels with  $R_i = 60$  in. and 64 in. that are shown in figures 13-16. The buckling-load values for this group range from  $P_{cr}/P_{cr}^o = 0.88$  to 0.98. Panels with  $55 \text{ in.} < R_i < 60$  in. exhibit linear prebuckling load-shortening response and outward prebuckling displacements similar to those predicted for panels with  $R_i = 56$  in., as shown in figures 13-16. The buckling load values for this group range from  $P_{cr}/P_{cr}^o = 1.1$  to 1.2. Finally, panels with  $R_i < 55$  in. exhibit a definite nonlinearity in their prebuckling response; that is, similar in character to the response shown in figures 13-16 for  $R_i = 52$  inches. In particular, the prebuckling load-shortening response curves exhibit a large amount of nonlinearity above a load level of  $P/P_{cr} = 1.2$ , the prebuckling deformations are outward, and the buckling loads are on the order of two times the linear-bifurcation buckling load for the corresponding geometrically perfect panel with no initial prestress.

### **Combined Effects of Initial Misfit Prestress and Elastic Edge Restraints**

Selected results illustrating the combined effects of an initial misfit prestress and elastic edge restraints on the compression response of a 60-in-radius, quasi-isotropic panel are presented in figures 18-21. More specifically, buckling loads for initial panel radii given by  $R_i = 52$  in., 56 in., 60 in., and 64 in. are presented in figures 18(a), 18(b), 18(c), and 18(d), respectively. Each figure presents normalized

buckling loads as a function of rotational restraint stiffness,  $K_\theta$ , and contains seven curves that correspond to different degrees of circumferential restraint on the loaded edges of the panel. In general, the results indicate that there is a large amount of nonlinear coupling between the two elastic edge restraint conditions and the test-fixture-induced prestress. The results can be subdivided into three major groups that correspond to various combinations of parameters  $K_v$ ,  $K_\theta$ , and  $R_i$  that are affecting the response. Group 1 is associated with panel responses that are affected by variations in  $K_v$  only and correspond to panel configurations with  $K_\theta > 10^4$  in-lb and for all values of initial radius considered herein. The effect of  $K_v$  on the panel response has already been presented herein and, as a result, will not be discussed in this section, since it was covered in one of the earlier sections. Group 2 is associated with panel responses that are affected by a combination of  $K_v$  and initial prestress and corresponds to all panel configurations with  $K_\theta < 10^2$  in-lb. Group 3 is associated with panel responses that are affected by a combination of  $K_v$ ,  $K_\theta$ , and initial prestress and include panel configurations with  $10^2$  in-lb  $< K_\theta < 10^4$  in-lb. The overall behavioral characteristics associated with the panels in Groups 2 and 3 are described next.

Typical predicted effects of initial prestress and circumferential edge restraint on the buckling loads of panels in Group 2, panels that are affected by a combination of  $K_v$  and initial prestress for  $K_\theta < 10^2$  in-lb, are presented in figure 19. The results in this figure are for  $K_\theta = 0$ . In general, the results indicate that the buckling loads of panels with  $R_i \geq 56$  in. exhibit a similar dependency on the circumferential edge restraint  $K_v$  as geometrically perfect panels with the circumferential edge restraint only (see figures 2-5 and the related discussion). However, the prestress can affect the value of the circumferential edge restraint stiffness at which the panels transition from linear prebuckling behavior, associated with the relatively low buckling-load values of 0.98 to 1.15, to nonlinear prebuckling behavior, associated with the relatively high buckling-load values that range from 1.8 to 2.0. For panels with  $R_i \leq 54$  in. and  $K_v < 10^8$  lb/in., the response is primarily governed by the initial prestress and exhibits characteristics similar to those exhibited by the panels with only an initial prestress (see figures 12-17 and the related discussion).

The response of the panels in Group 3 are affected by a combination of edge restraint conditions and initial prestress for values of  $10^2$  in-lb  $< K_\theta < 10^4$  in-lb. Within this group there are two subgroups; Group 3-1 for panels with  $K_v < 10^5$  lb/in. and Group 3-2 for panels with  $K_v > 10^5$  lb/in. The panels in Group 3-1 with  $R_i = 52$  in. exhibit nonlinear prebuckling behavior similar to that shown previously for a panel with  $K_v = 10^7$  lb/in. (see figures 2-5 and the corresponding discussion), and this behavior is characterized by large-magnitude, outward prebuckling deformations and buckling-load levels that approach 1.9 times the classical linear-bifurcation buckling load of the nominal panel, as shown in figure 18(a). However, as  $R_i$  increases, the panel response transitions to one that is characterized by a linear prebuckling response similar to that exhibited by a panel with nominal boundary conditions (see figures 2-5 and the corresponding discussion for  $K_v = 0$ ), with relatively small inward prebuckling deformations and normalized buckling load levels between 0.90 and 1.08. Furthermore, the value of  $K_\theta$  at which this transition from linear to nonlinear prebuckling behavior occurs is a function of the panel prestress and circumferential edge restraint  $K_v$ , as indicated in figures 18(a) through 18(d).

The buckling loads for panels in Group 3-2 ( $10^2$  in-lb  $< K_\theta < 10^4$  in-lb and  $K_v > 10^5$  lb/in.) are influenced strongly by variations in the elastic edge restraints and to a lesser extent by the prestress, as shown figures 18(a) through 18(d). In particular, the curves for this class of panels exhibit a festoon-like behavior that is analogous to the curves associated with buckling of flat, compression-loaded, finite-length rectangular plates (for example, see Brush and Almroth, ref. 11). This festoon-like behavior is attributed to a distinct change in prebuckling and buckling response characteristics with an increase in the magnitude of the rotational edge restraint. For example, a panel with  $R_i = 52$  in.,  $K_v = 10^8$  lb/in., and  $K_\theta = 10^2$  in-lb exhibits response characteristics similar to those of a panel with  $\nu = 0$  on the loaded boundaries (e.g., see figures 2-5). The response is characterized by a nonlinear prebuckling load-shortening curve, a normalized buckling-load value that ranges from  $P_{cr} / P_{cr}^o = 1.5$  to 1.6, and a large centrally located,

ellipse-shaped deformation pattern at the onset of buckling (e.g., see figure 20(a)). As  $K_\theta$  is increased to  $10^{2.7}$  in-lb, the prebuckling response changes to become more like that of a panel with  $K_v = 10^7$  lb/in. (e.g., see figures 2-5). This response is characterized by a nonlinear prebuckling load-shortening curve, a normalized buckling-load value that ranges from  $P_{cr} / P_{cr}^o = 1.80$  to 1.98, and an hour-glass-shaped deformation pattern at the onset of buckling (e.g., see figure 20(b)). If  $K_\theta$  is increased further to  $10^4$  in-lb, the prebuckling response changes once again. In particular, the buckling load is reduced from around 1.98 to 1.5 and the magnitude of the maximum out-of-plane displacement decreases from 2.4 times to 1.0 times the nominal panel wall thickness, as shown in figure 20(c). In addition, the character of the initial buckling displacements also changes. Specifically, for a panel with  $K_\theta = 10^2$  in-lb, buckling initiates near the loaded edges of the panel, as illustrated by the initial buckling displacement contours shown in figure 21(a).

These displacement contours illustrate, qualitatively, the change in the panel displacements at the onset of buckling and are determined by subtracting the initial buckling displacement field from the displacement field of previous solution step just prior to buckling and, as a result, are referred to herein as  $\Delta w$  contours. Displacement magnitudes are omitted from the plot because the displacement contours are intended to represent an infinitesimal change in the displacements in the neighborhood of the buckling point. For  $K_\theta = 10^{2.7}$  in-lb, the results indicate that buckling initiates near the unloaded boundary of the panel, as indicated by the initial buckling displacement contours shown in figure 21(b). In contrast, the initial-buckling displacements shown in figure 20(c) for the panel with  $K_\theta = 10^4$  in-lb show that buckling initiates in the center of the panel.

## Concluding Remarks

A parametric study of the effects of test-fixture-induced initial prestress and elastic edge restraints on the prebuckling and buckling responses of a compression-loaded quasi-isotropic curved panel has been presented. Numerical results were obtained by using a geometrically nonlinear finite-element analysis code and high-fidelity models. Idealizations of the circumferential loaded-edge restraint and the rotational unloaded-edge restraint provided by the test fixture were included in the finite-element models to obtain insight into response-trend variations observed in previously conducted experiments. In addition, the effects of initial stress and deformations states, referred to herein as initial prestress, that result from a mismatch in radius of curvature between a test specimen and the test fixture were simulated analytically.

Several of the effects of the test-fixture-induced initial prestress and elastic edge restraints have been presented, described, and discussed. In many cases, the results clearly indicate significant effects of the initial prestress and the two types of elastic edge restraint on the panel response. In particular, the results indicate that the initial prestress and elastic edge restraints can produce nonlinear prebuckling deformations in the panel that result in increases in the buckling resistance of the panel. In addition, the results indicate that various combinations of the initial prestress and elastic edge restraints can exhibit coupling and affect the overall nonlinear response of the panel in three different ways. Specifically, the predicted results can generally be categorized into three groups that exhibit distinct behavioral characteristics, depending on the relative degrees of the initial prestress and the elastic edge restraints. For some combinations of initial prestress and edge restraints, the panel exhibits a linear load-shortening response prior to buckling. The prebuckling deformations are negligible and the magnitude of the buckling load for these panels is typically very near the corresponding buckling load obtained from a linear-bifurcation buckling analysis. For other combinations of the initial prestress and edge restraints, the panel exhibits nonlinear prebuckling deformations and buckling loads that approach two times the corresponding linear bifurcation buckling load. For still other combinations of initial prestress and edge restraints, the panels exhibit smaller prebuckling nonlinearities and typically have buckling loads that are approximately 40% to 60% higher than the corresponding linear-bifurcation buckling load.

Overall, the results indicate, in a quantitative manner, how laminated-composite, curved-panel test specimens that are subjected to compression loads can exhibit significant sensitivity to the degree of circumferential and rotational edge restraint provided by a test fixture and the initial stress and deformation states that result from a small mismatch in the specimen and test-fixture geometries. Furthermore, since several combinations of initial prestress and edge restraints can result in similar response characteristics and buckling resistance, one must accurately characterize all pertinent aspects of the test fixture and panel specimen before each test in order to have the information needed to assess the influence of each factor on the panel response.

In addition to the fundamental information presented herein that is relevant to structural testing, the results also provide insight into enhancements in buckling resistance that can be achieved by tailoring the support conditions for curved panels. The results should also be of particular interest to engineers and designers involved in simulating flight-hardware boundary conditions in structural verification and certification tests, and validating structural analysis tools.

## References

1. Hilburger, M. W.; Starnes, J. H. Jr.: Effects of Imperfections on the Buckling Response of Composite Shells. *Thin-Walled Structures*, vol. 42, 2004, pp. 369-397.
2. Snell, M. B.; and Morley, N. T.: The Compression Buckling Behavior of Highly Curved Panels of Carbon Fibre Reinforced Plastic. *Proceedings of the Fifth International Conference on Composite Materials*, ICCM Volume 5, 1985, pp. 1327-1354.
3. Leissa, A. W.: *Buckling of Laminated Composite Plates and Shell Panels*. Report AFWAL-TR-85-3069, Air Force Wright Aeronautical Laboratories, June, 1985.
4. Hui, D.: Asymmetric Postbuckling of Symmetrically Laminated Cross-ply Short Cylindrical Panels Under Compression. *Composite Structures*, vol. 3, 1985, pp. 81-95.
5. Khot, N. S.; and Bauld, N. R., Jr.: A Numerical and Experimental Investigation of the Buckling Behavior of Composite Panels. *Computers and Structures*, vol. 15, no. 4, 1982, pp. 393-403.
6. Wilkins, D. J.: Compression Buckling Tests of Laminated Graphite-Epoxy Curved Panels. *AIAA Journal*, vol. 13, no. 4, 1975, pp. 465-470.
7. Knight, N. F.; and Starnes, J. H. Jr.: Postbuckling Behavior of Selected Graphite-Epoxy Cylindrical Panel Loaded In Compression. *Proceedings of the AIAA/ASME/ASCE/AHS 27th Structures, Structural Dynamics, and Materials Conference*, 1986, AIAA paper 86-0881-CP.
8. Hilburger, M. W.; Britt, V. O.; and Nemeth, M. P.: Buckling Behavior of Compression-Loaded Quasi-Isotropic Curved Panels With a Circular Cutout. *International Journal of Solids and Structures*, vol. 38, 2001, pp.1495-1522.
9. Librescu, L.; Nemeth, M. P.; Starnes, J. H., Jr.; and Lin, W.: Nonlinear Response of Flat and Curved Panels Subjected to Thermomechanical Loads. *Journal of Thermal Stresses*, vol. 23, 2000, pp. 549-582.
10. Rankin, C. C.; Brogan, F. A.; Loden, W. A.; and Cabiness, H. D.: *STAGS Users Manual, Version 4.0*. Lockheed Martin Missiles & Space Co., Inc., Advanced Technology Center, Report LMSC P032594, May 2001.
11. Brush, D. O.; and Almroth, B., O.: *Buckling of Bars, Plates, and Shells*, McGraw Hill, 1975, p. 97.



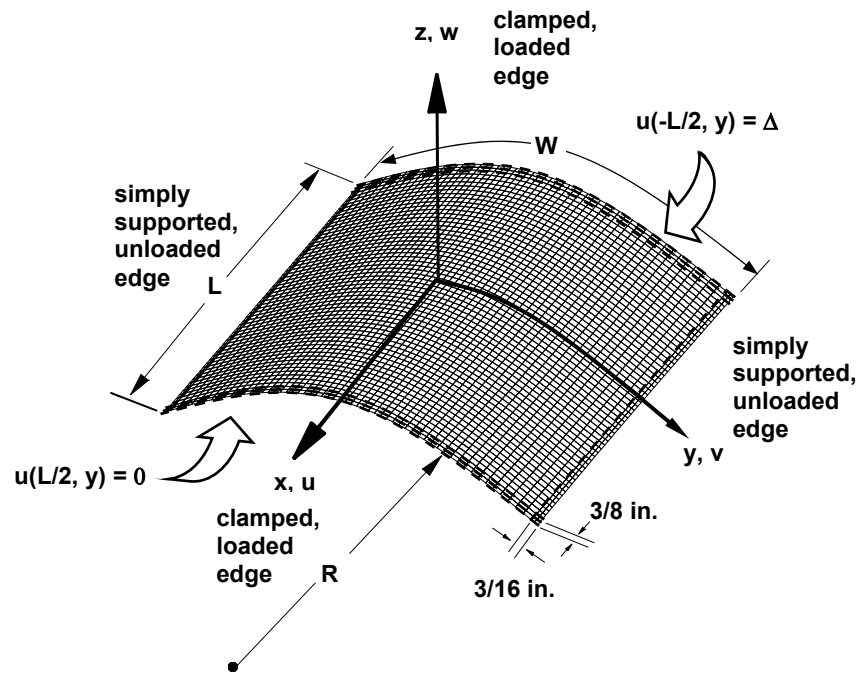


Figure 1. Typical model geometry and boundary conditions (dashed lines mark the rows and columns where the boundary conditions are applied).

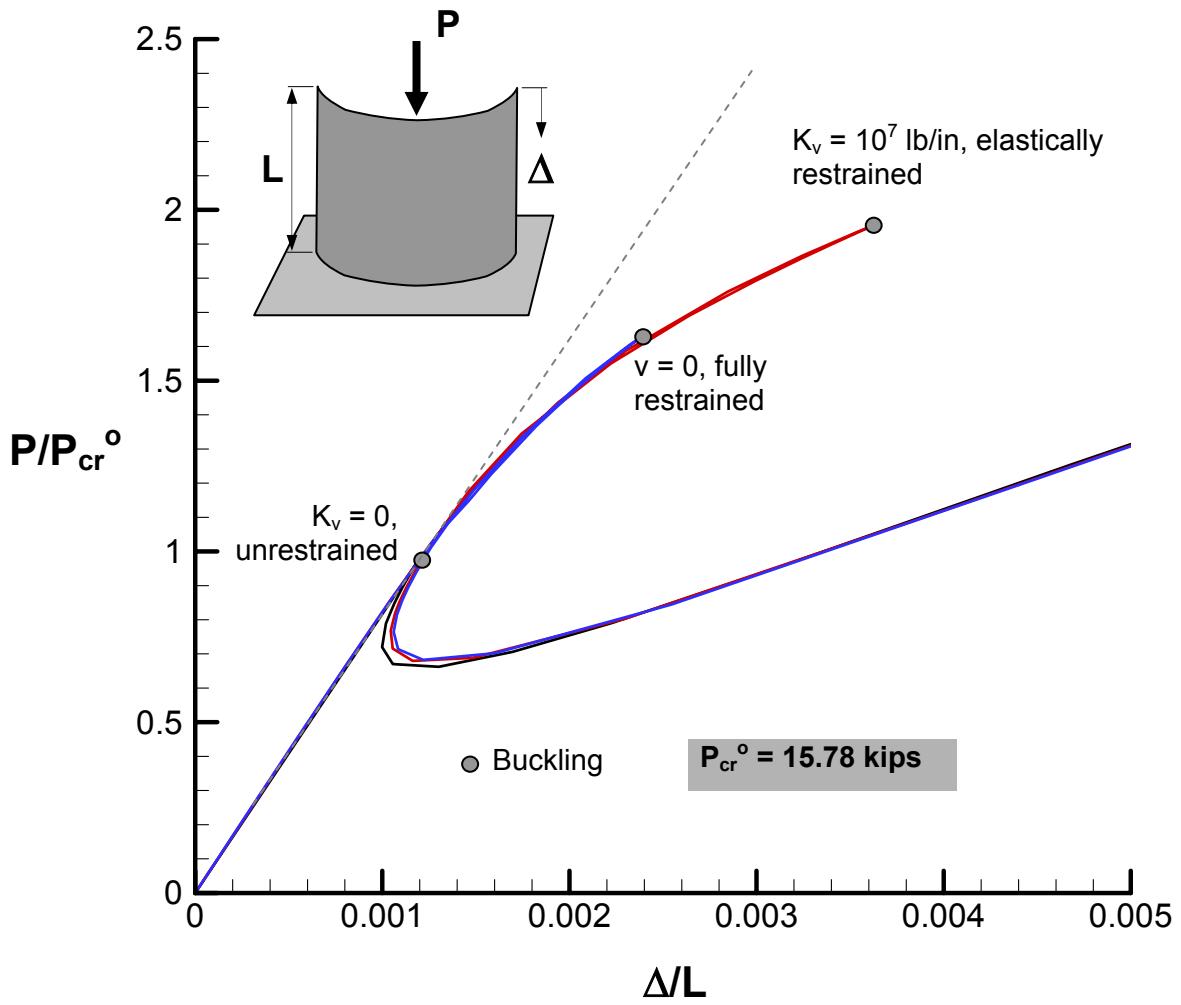


Figure 2. Effects of circumferential loaded-edge restraint on the load-shortening response of a compression-loaded, 60-in-radius, quasi-isotropic panel.

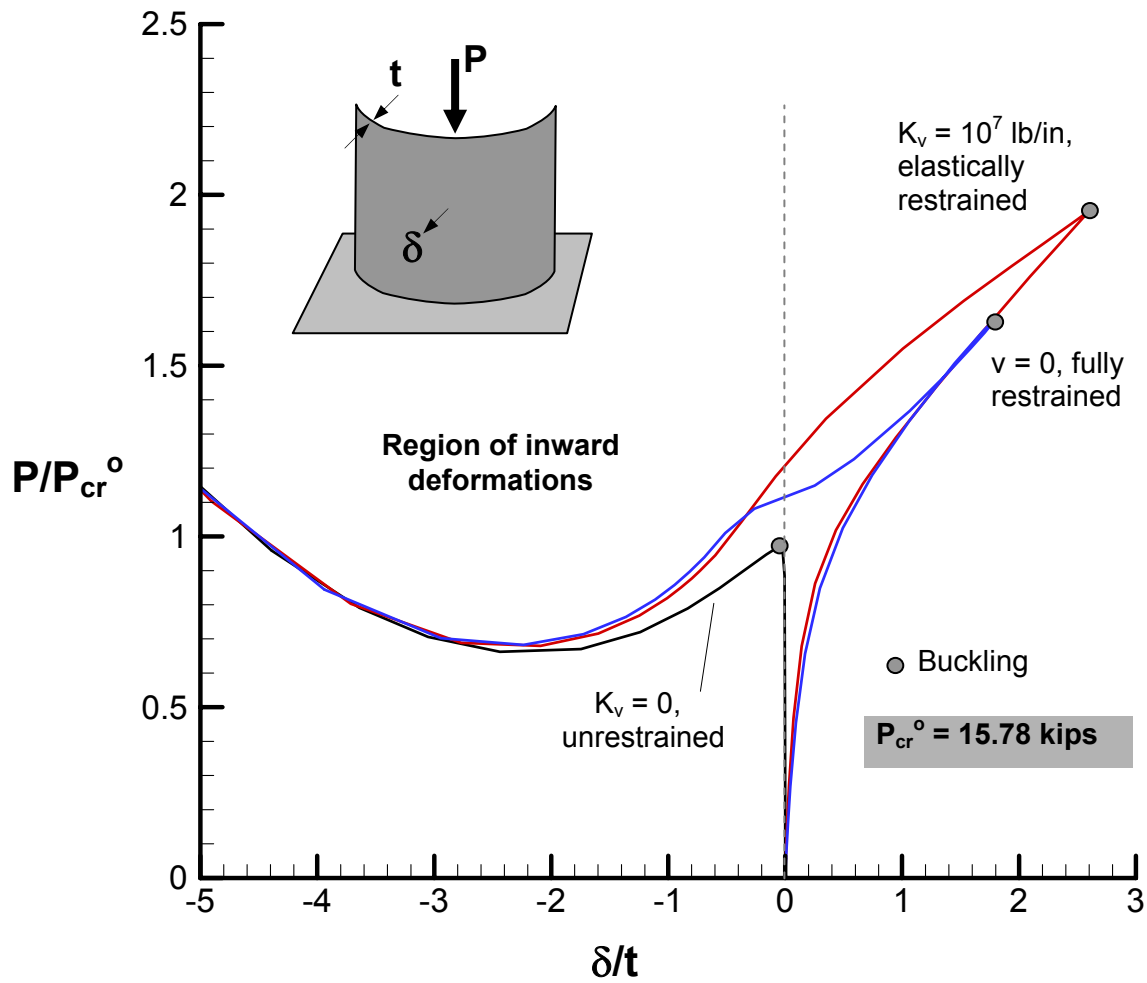


Figure 3. Effects of circumferential loaded-edge restraints on the out-of-plane center displacement of a compression-loaded, 60-in-radius, quasi-isotropic panel.


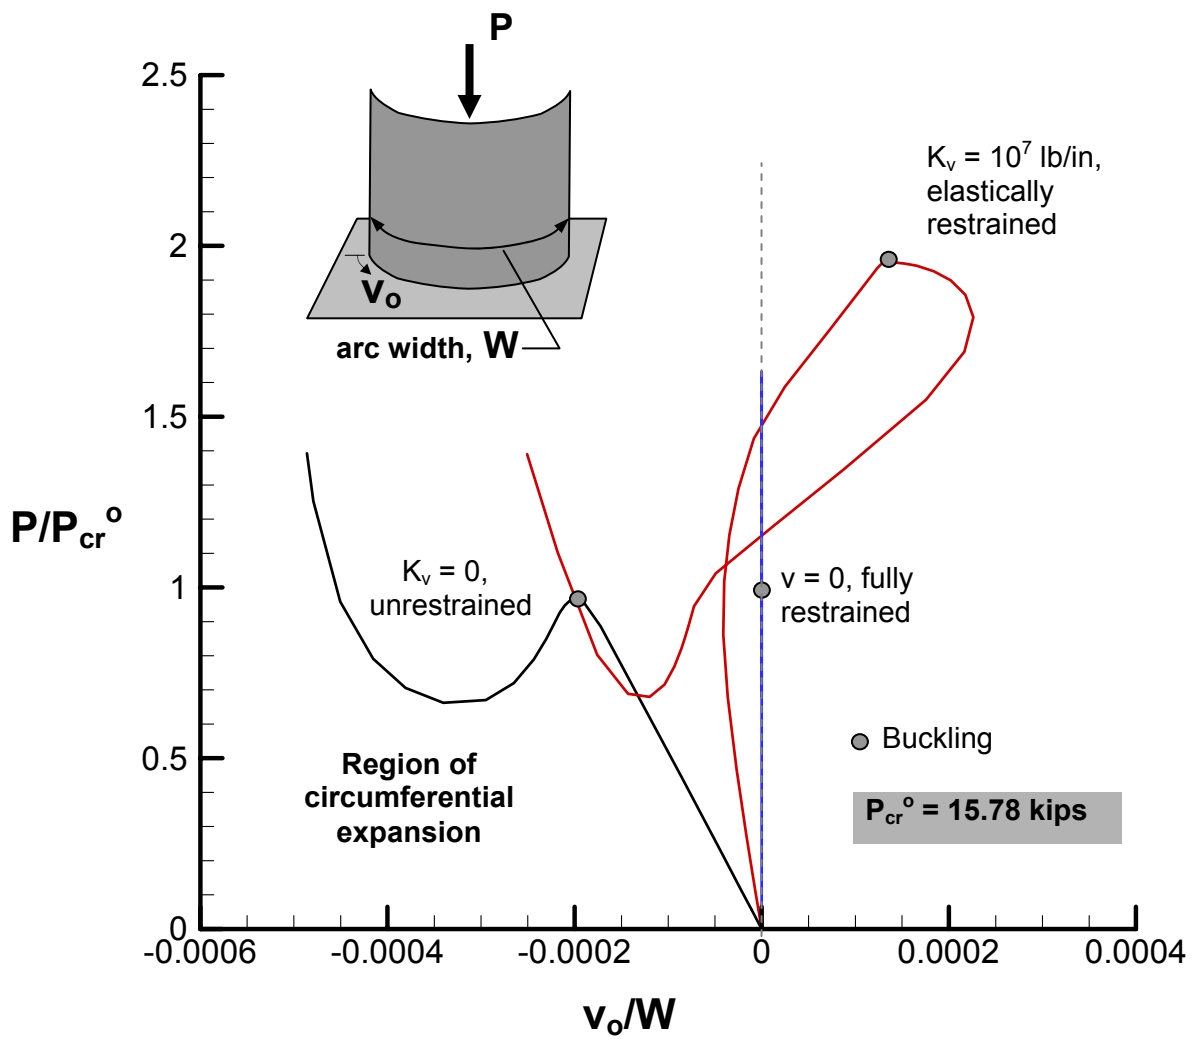


Figure 4. Effects of circumferential loaded-edge restraint on the circumferential of displacement of a compression-loaded, 60-in-radius, quasi-isotropic panel.

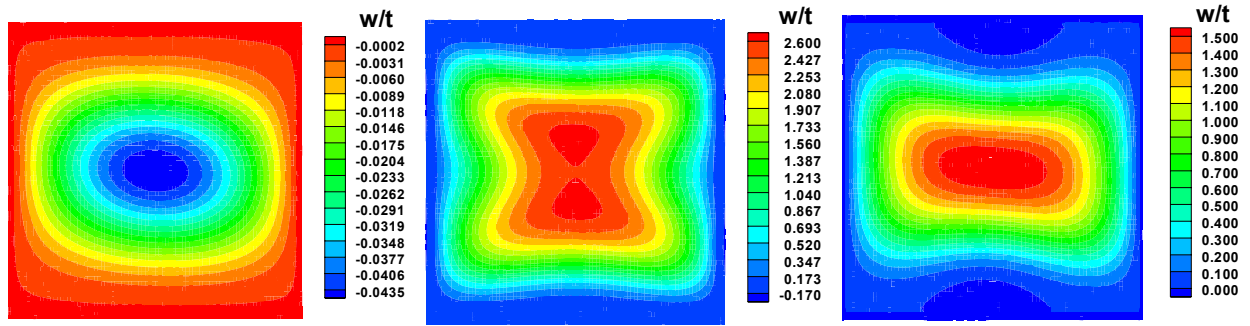

(a)  $K_v = 0$ ,  $P/P_{cr}^0 = 0.98$       (b)  $K_v = 10^7$  lb/in.,  $P/P_{cr}^0 = 1.95$       (c)  $v = 0$ , clamped,  $P/P_{cr}^0 = 1.52$

Figure 5. Effects of circumferential boundary stiffness  $K_v$  on the out-of-plane displacements at the onset of buckling of a 60-in-radius, quasi-isotropic panel ( $P_{cr}^0 = 15.78$  kips).

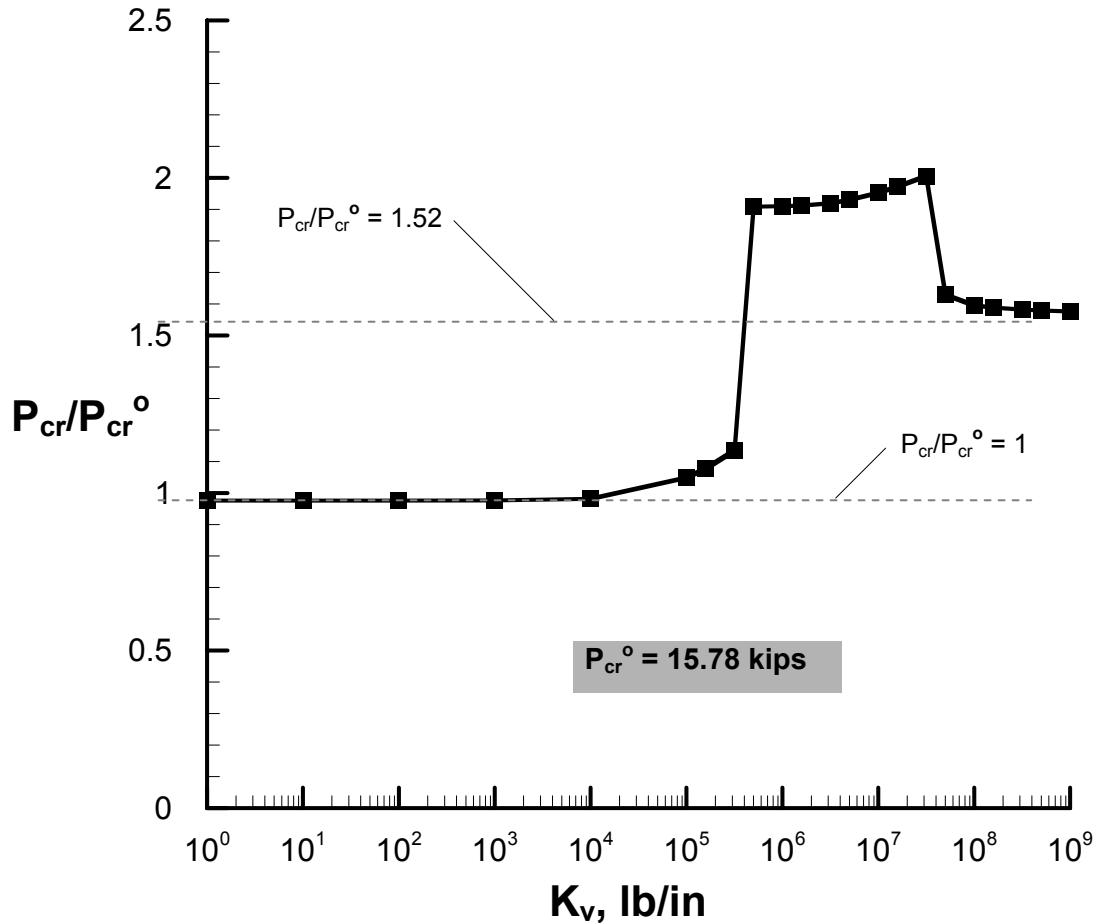


Figure 6. Effects of circumferential edge restraints on the buckling load of a compression-loaded, 60-in-radius, quasi-isotropic panel.

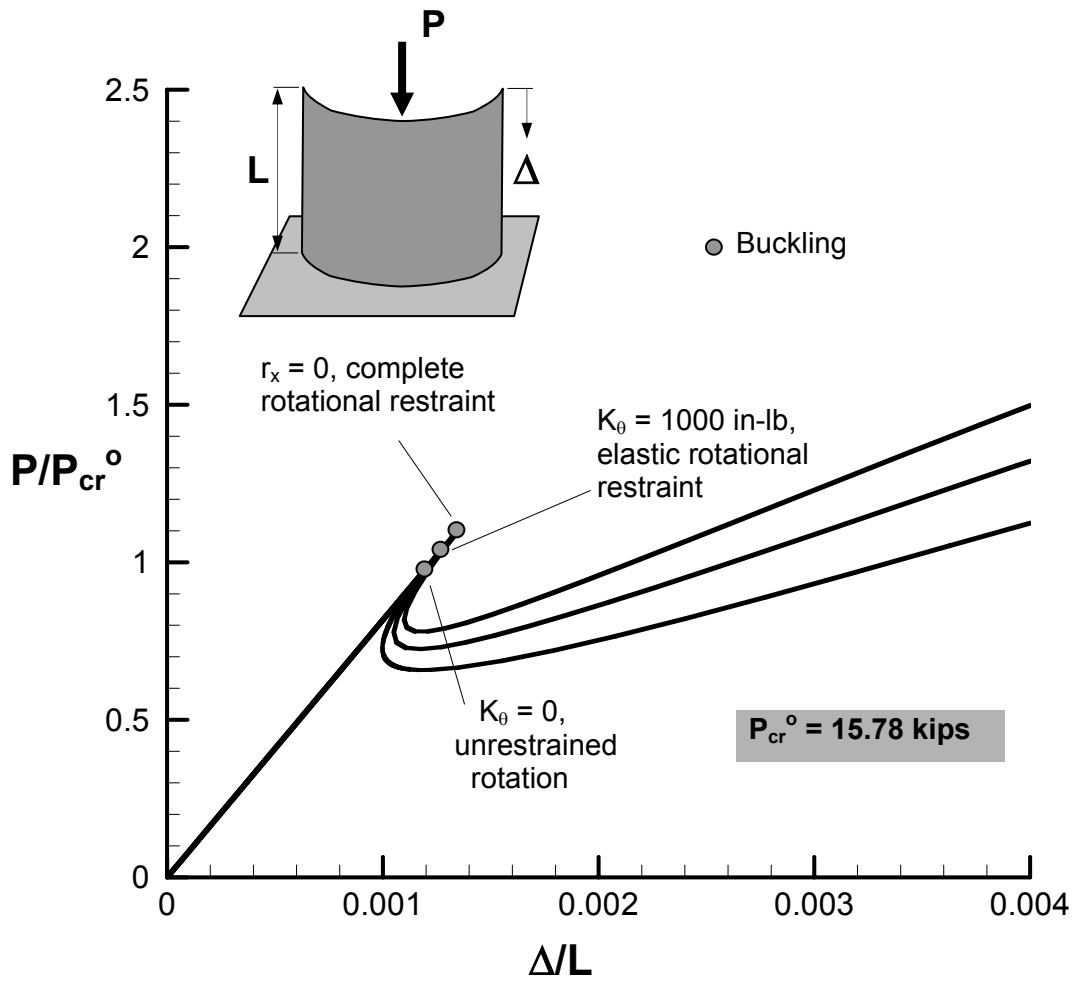


Figure 7. Effects of rotational unloaded-edge restraint on the load-shortening response of a compression-loaded, 60-in-radius, quasi-isotropic panel.

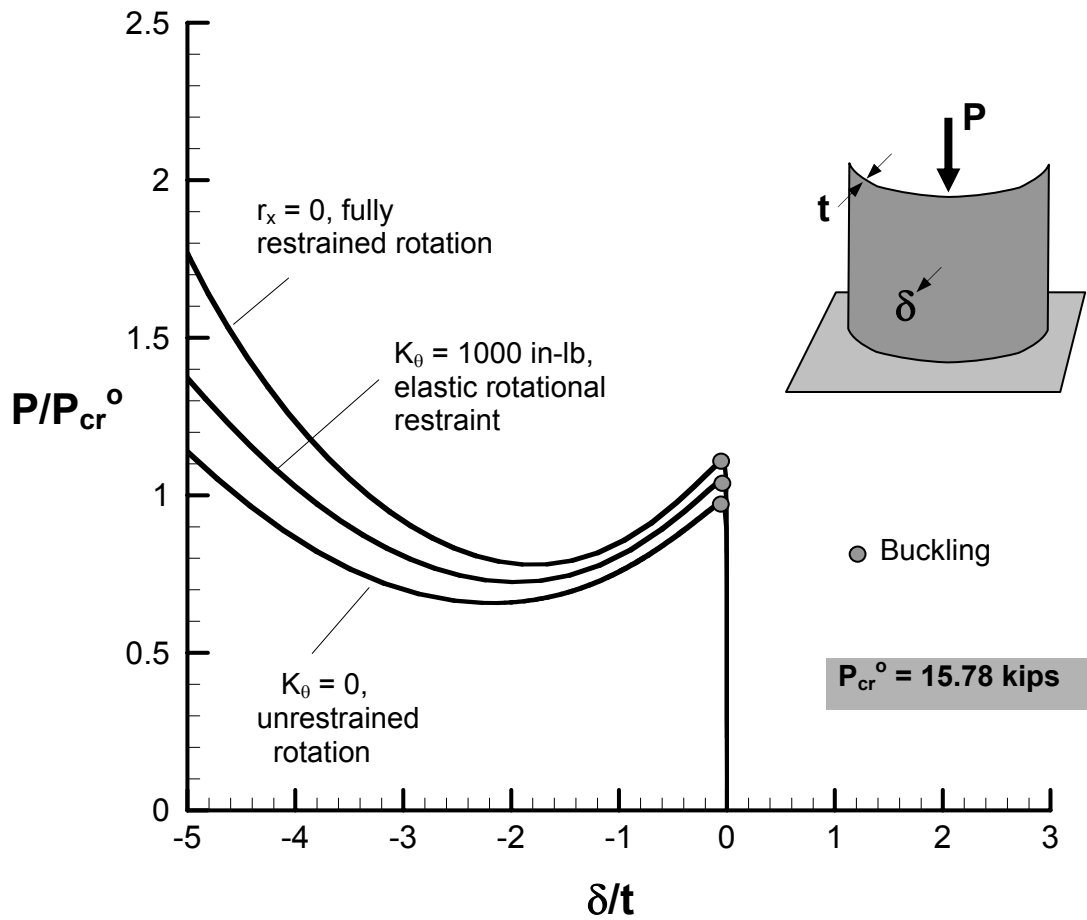


Figure 8. Effects of rotational unloaded-edge restraint on the out-of-plane center displacement of a compression-loaded, 60-in-radius, quasi-isotropic panel.

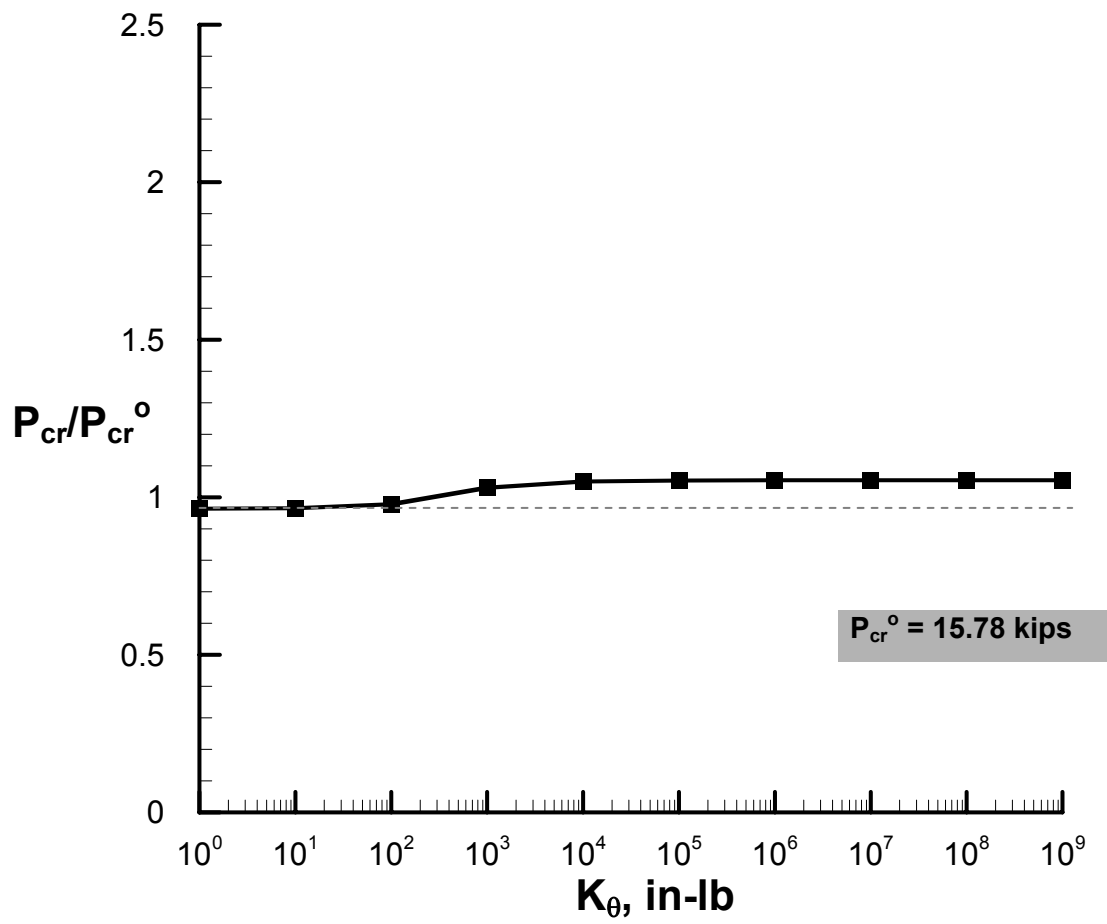


Figure 9. Effects of rotational unloaded-edge restraint on the buckling load of a compression-loaded, 60-in-radius, quasi-isotropic panel.



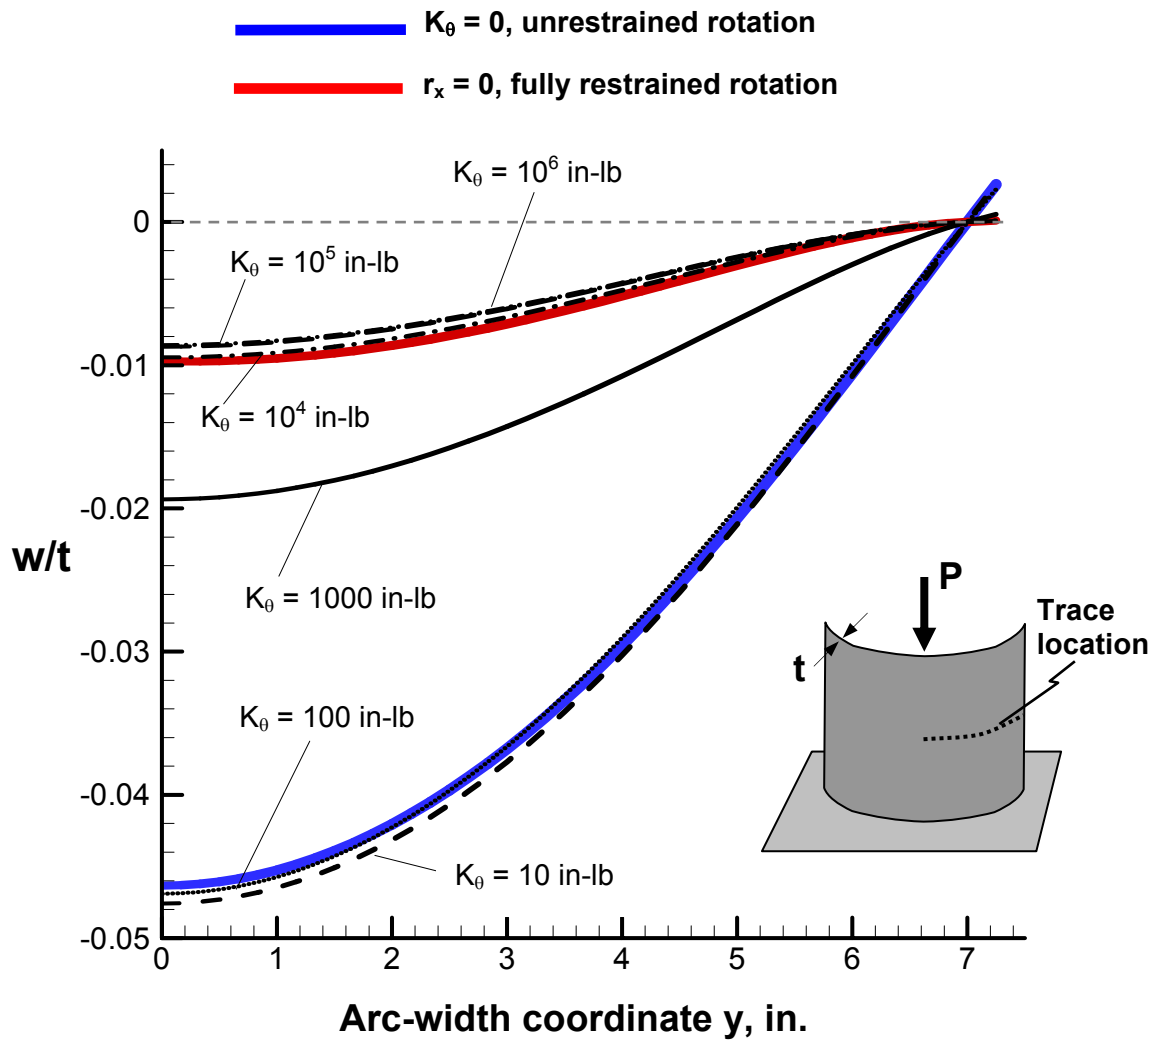


Figure 10. Effects of the rotational unloaded-edge restraint on the mid-length panel deformations of a compression-loaded, 60-in-radius, quasi-isotropic panel.



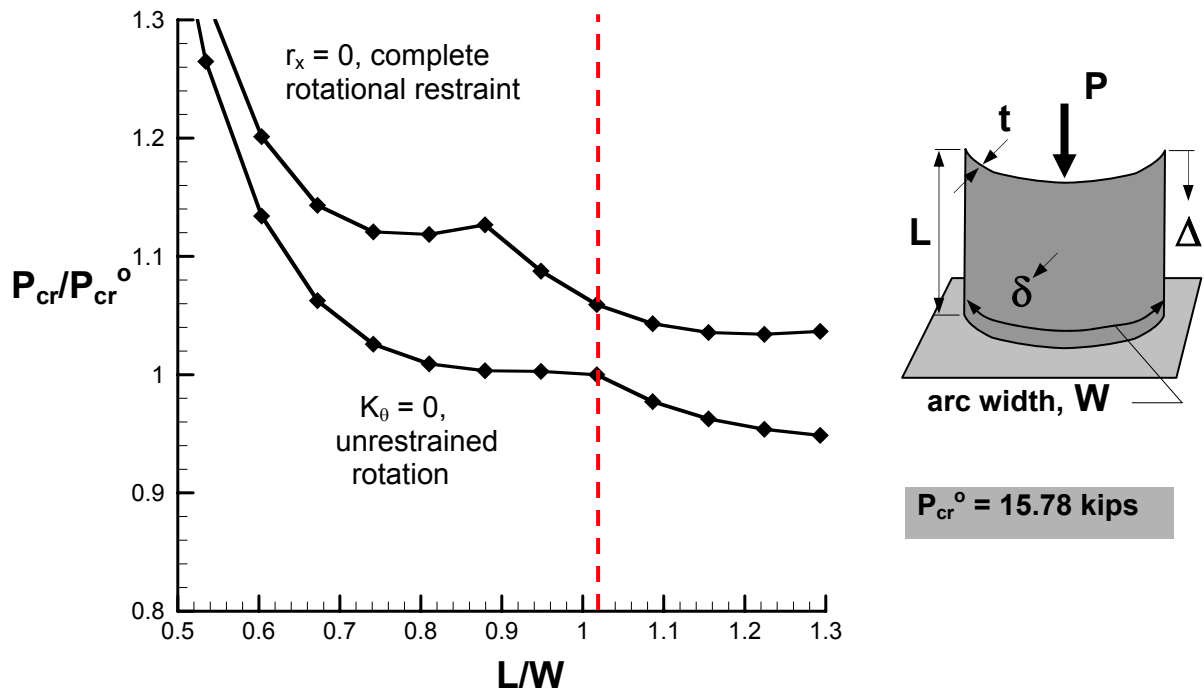



Figure 11. Effects of panel aspect ratio  $L/W$  on the buckling load of panels with simply supported ( $K_\theta = 0$ ) and clamped ( $r_x = 0$ ) boundary conditions on the unloaded edges of a compression-loaded, 60-in-radius, quasi-isotropic panel.

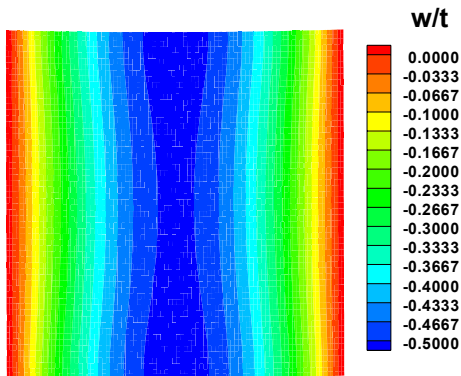


(a-1)  $R_i = 52$  in., referenced to the initial undeformed geometry

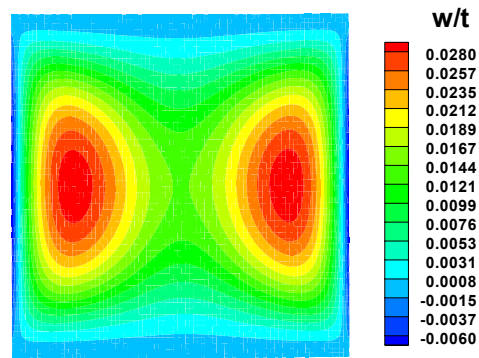


(a-2)  $R_i = 52$  in., referenced to a geometrically perfect 60-in-radius panel

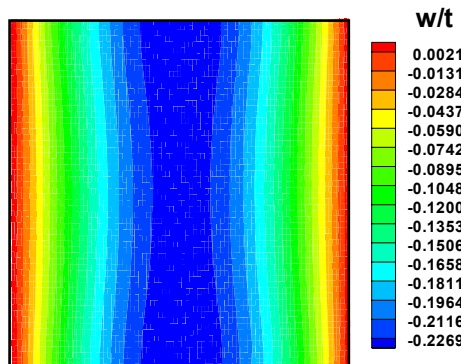


(b-1)  $R_i = 56$  in., referenced to the initial undeformed geometry

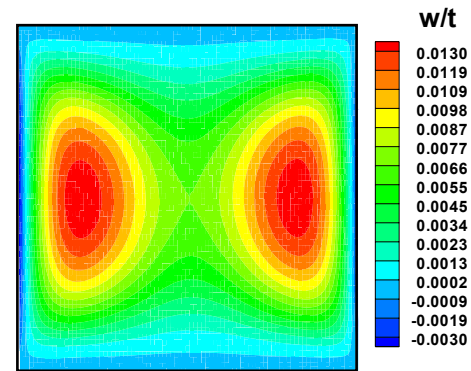

(b-2)  $R_i = 56$  in., referenced to a geometrically perfect 60-in-radius panel

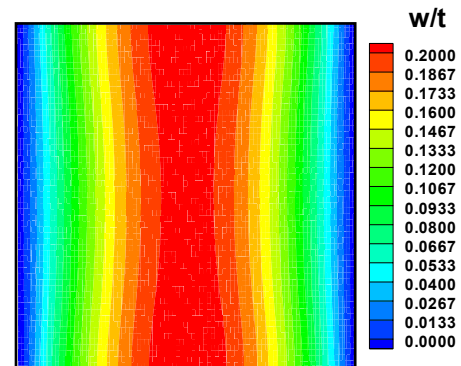

(c-1)  $R_i = 64$  in., referenced to the initial undeformed geometry

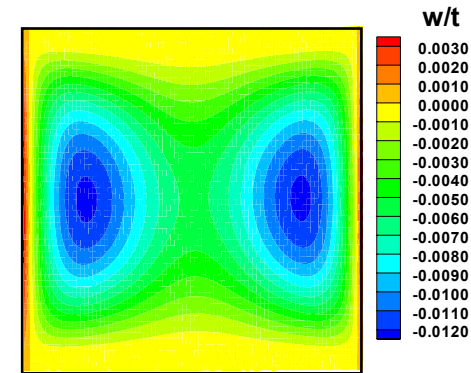

(c-2)  $R_i = 64$  in., referenced to a geometrically perfect 60-in-radius panel

Figure 12. Effects of initial radius  $R_i$  on the prestress displacements of a quasi-isotropic curved panel placed into a 60-in-radius test fixture.

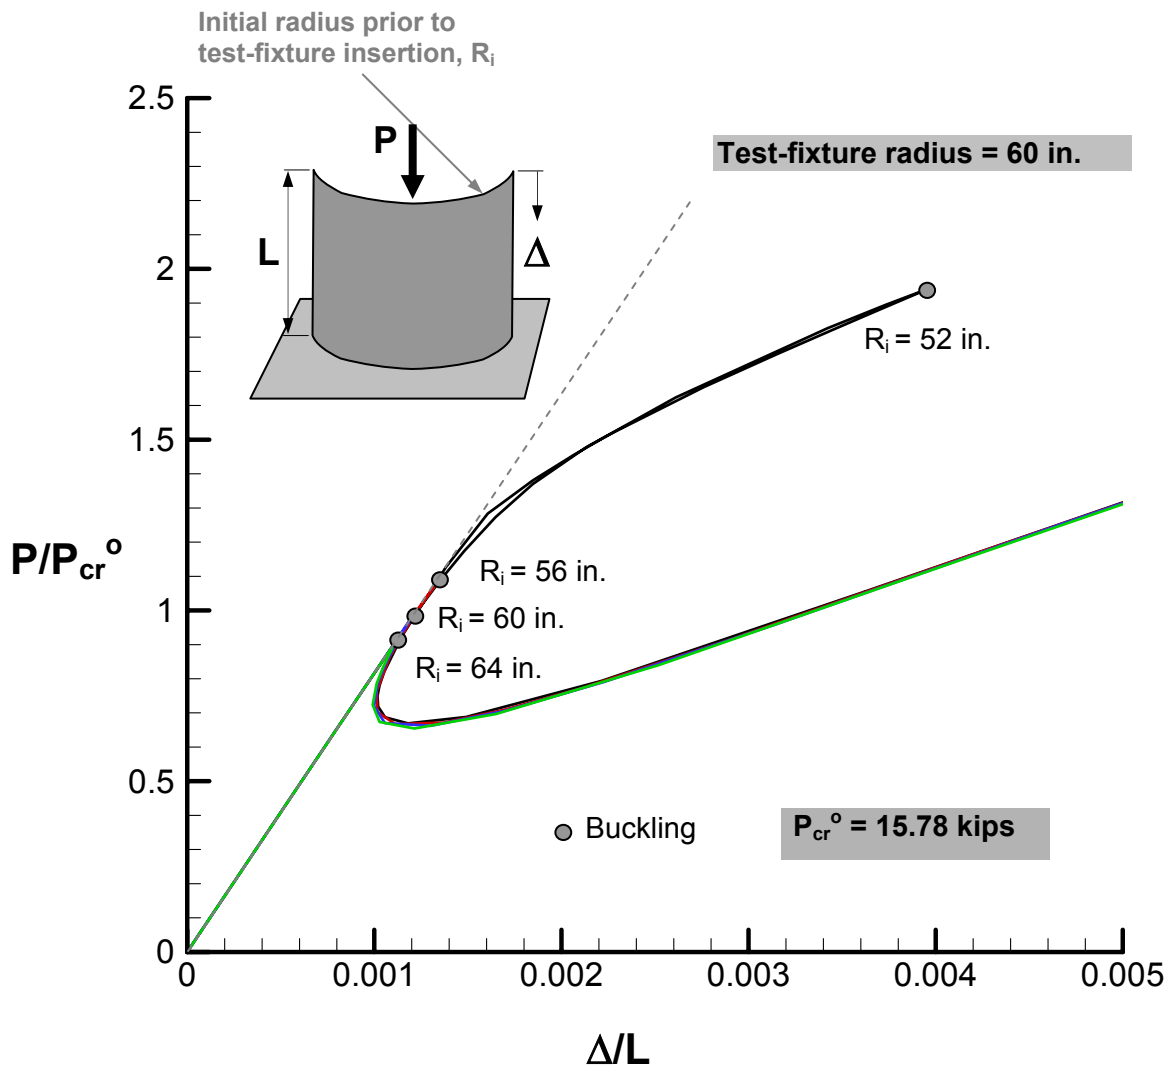


Figure 13. Effects of prestress on the load-shortening response of compression-loaded, quasi-isotropic curved panels in a 60-in-radius test fixture.

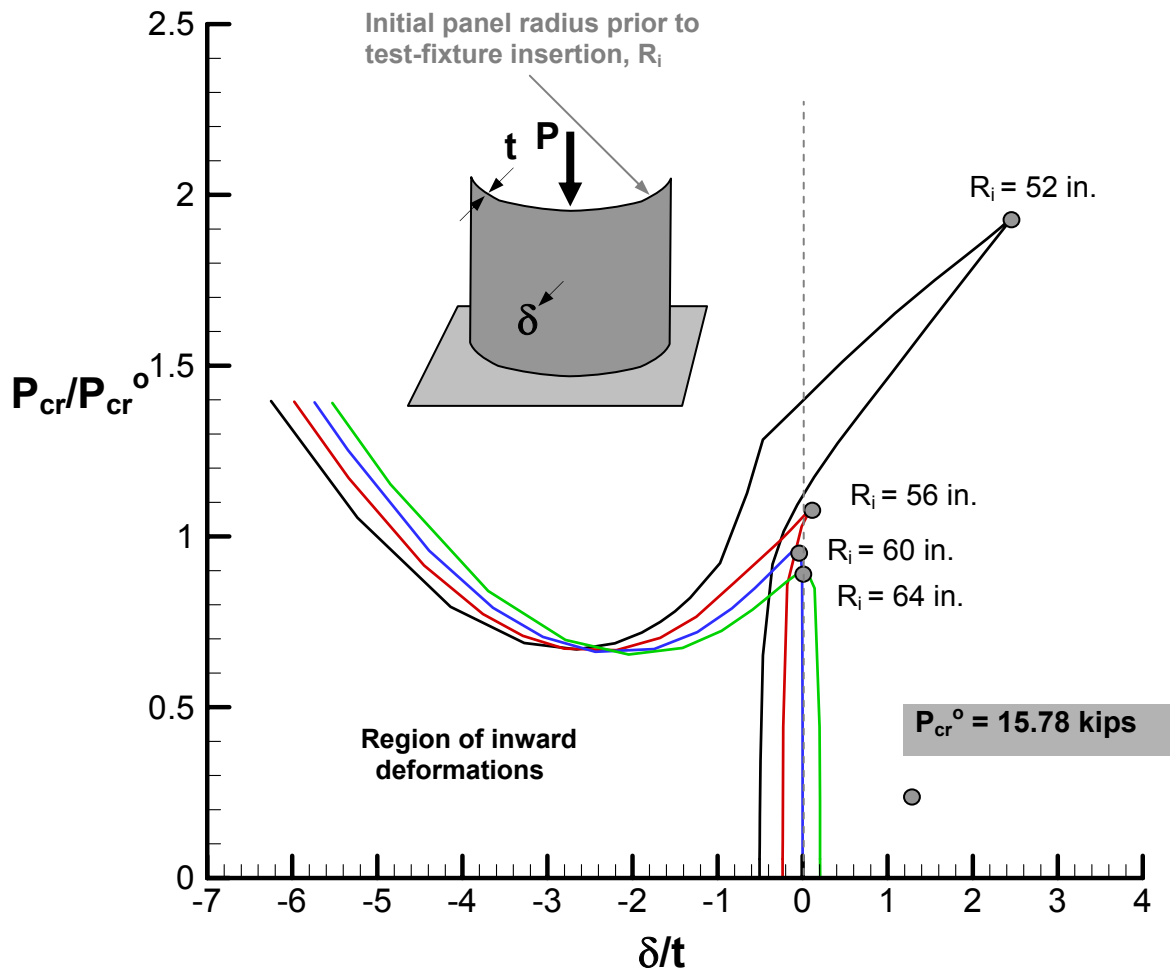


Figure 14. Effects of prestress on the out-of-plane center displacement of compression-loaded, quasi-isotropic curved panels in a 60-in-radius test fixture.

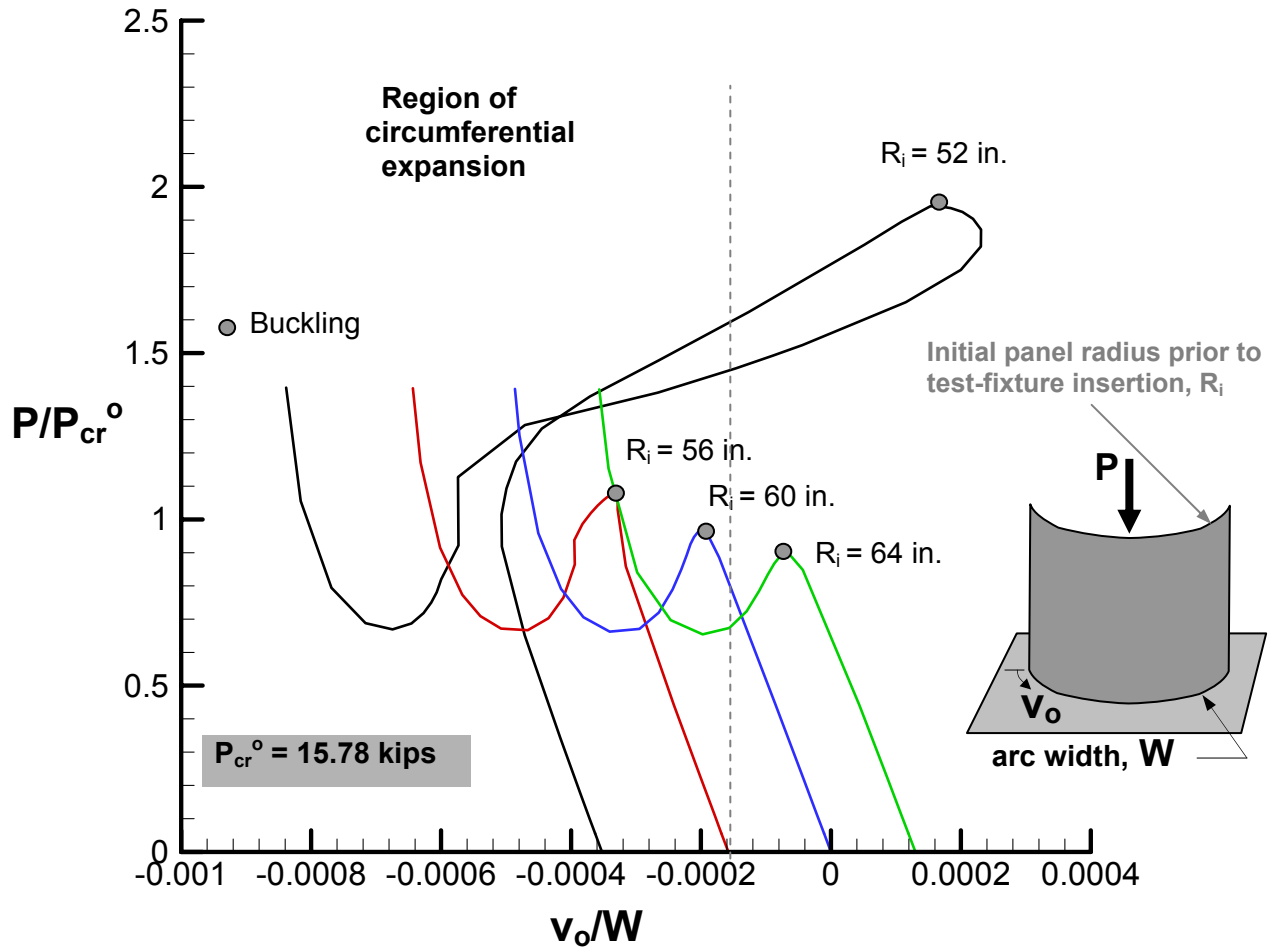


Figure 15. Effects of prestress on the circumferential displacement response of compression-loaded, quasi-isotropic curved panels in a 60-in-radius test fixture.

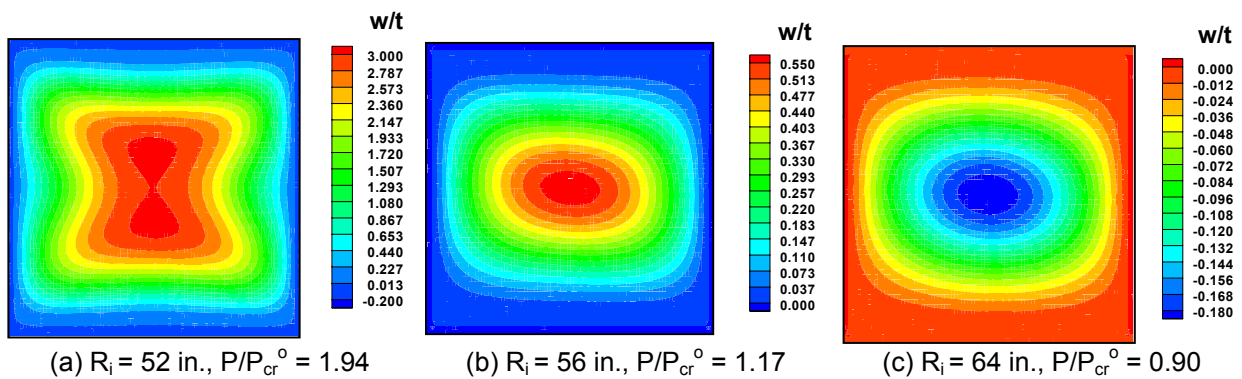


Figure 16. Effects of prestress on the out-of-plane displacements of compression-loaded, quasi-isotropic curved panels in a 60-in-radius test fixture.

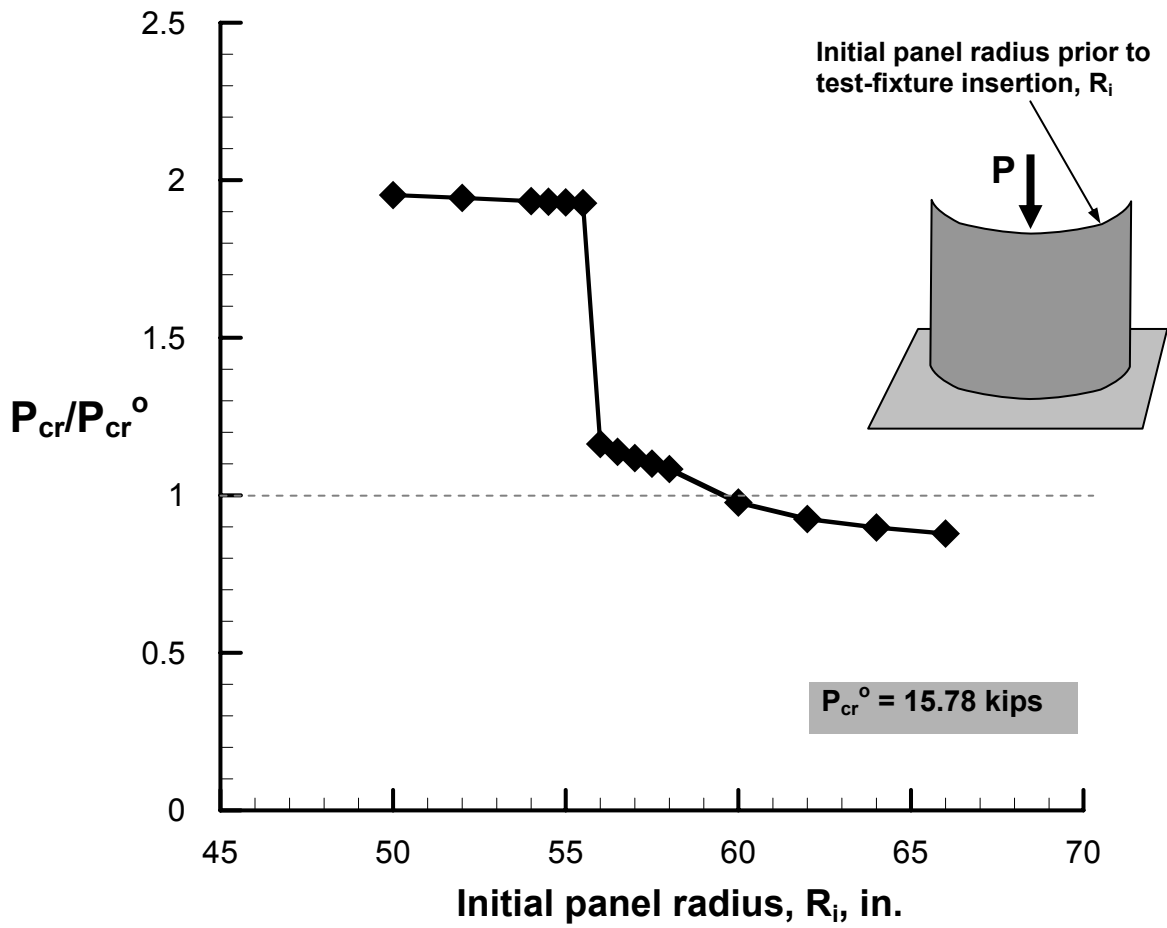


Figure 17. Effects of prestress on the buckling load of compression-loaded, quasi-isotropic curved panels in a 60-in-radius test fixture.

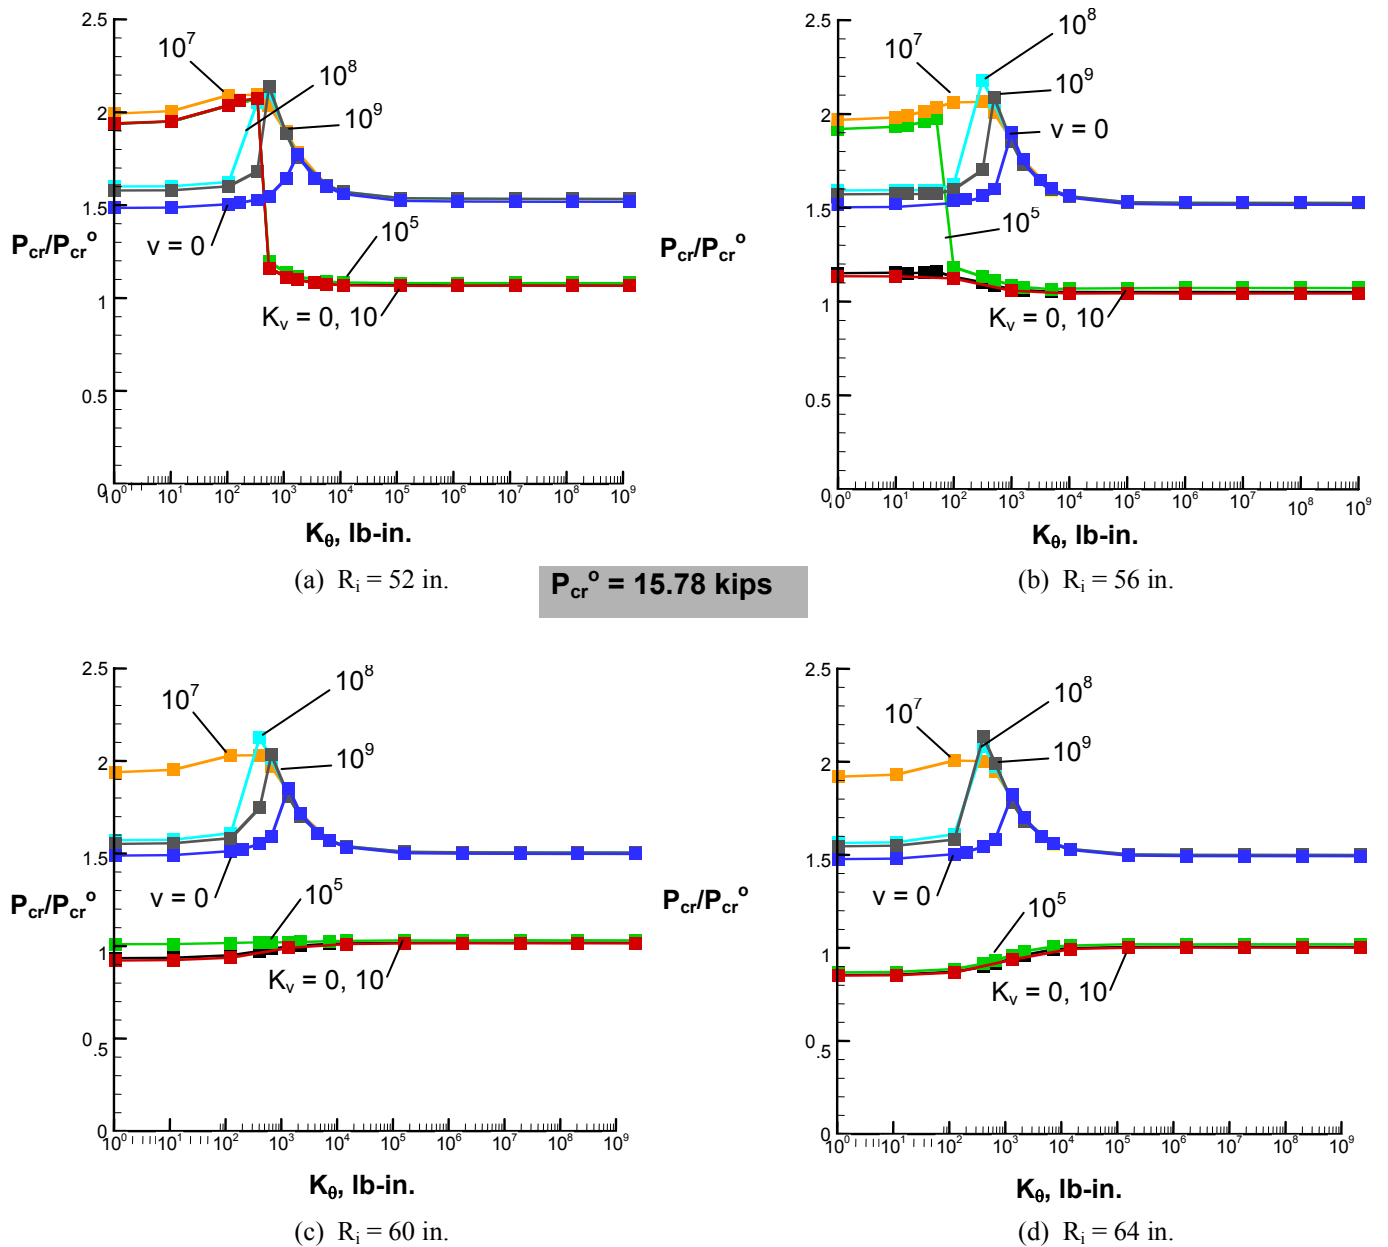


Figure 18. Effects of rotational boundary stiffness  $K_\theta$ , circumferential boundary stiffness  $K_v$ , and initial prestress on the buckling load of a compression-loaded, quasi-isotropic, curved panel.



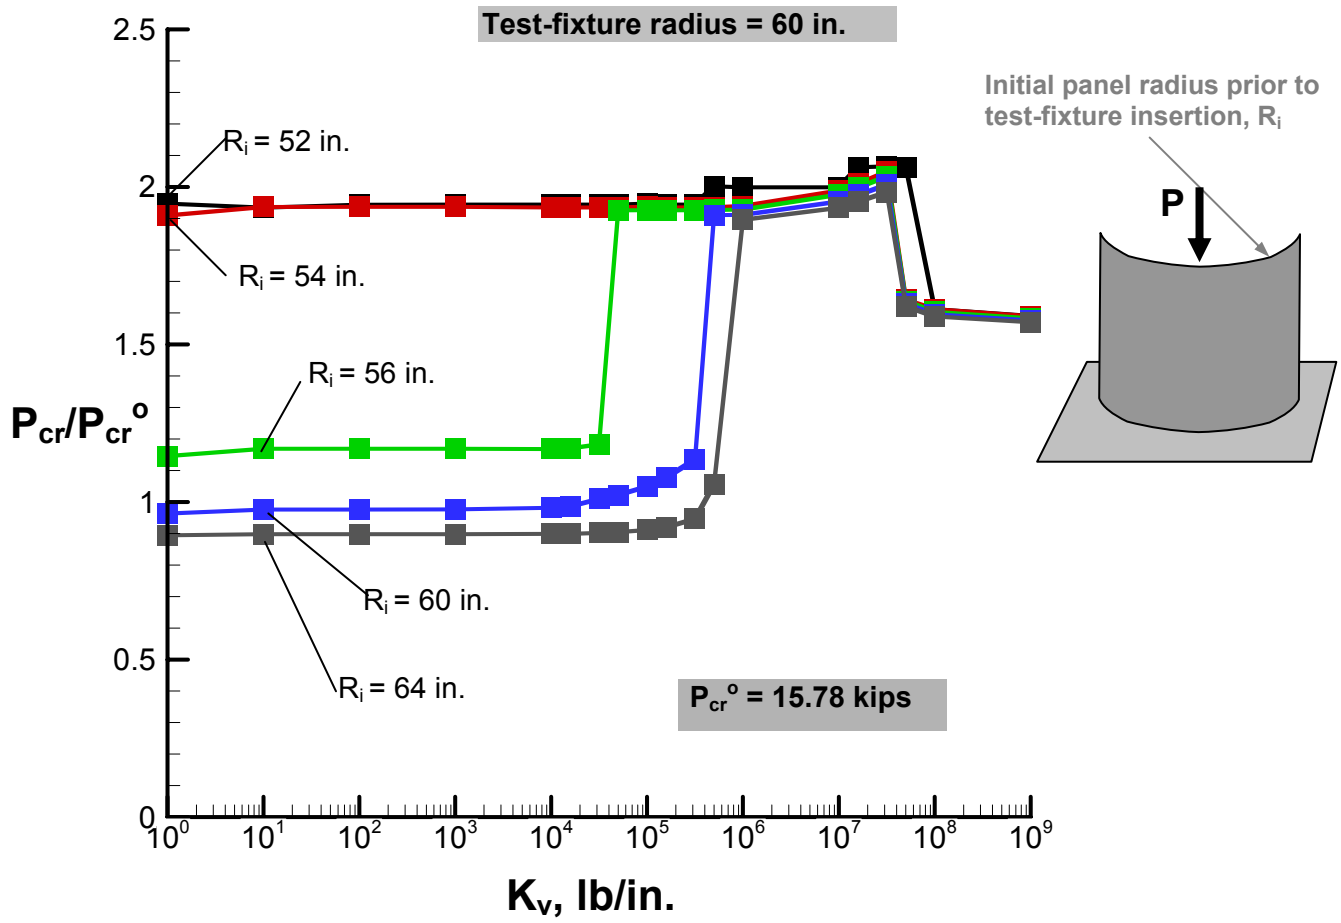


Figure 19. Effects of initial prestress and circumferential stiffness  $K_v$  on the buckling load of compression-loaded, quasi-isotropic, curved panels,  $K_\theta = 0$ .

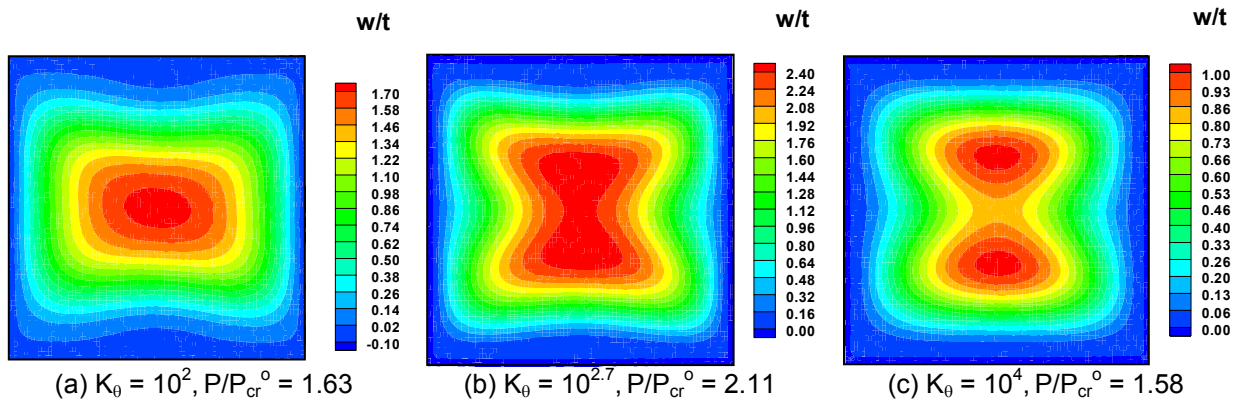


Figure. 20 Combined effects of circumferential boundary stiffness  $K_v = 108$  lb/in., rotational boundary stiffness  $K_\theta$  (in-lb), and prestress on the out-of-plane displacements at the onset of buckling of a 52-in. radius curved panel in a 60-in.-radius test fixture.

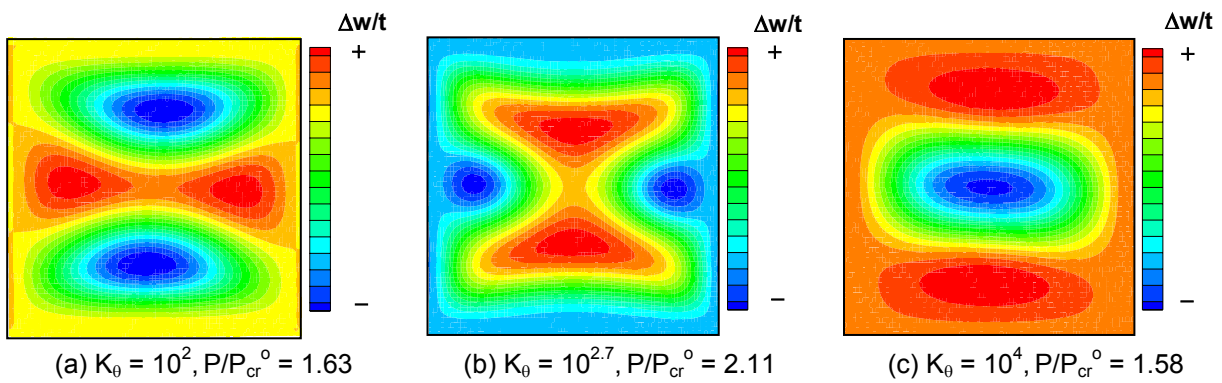


Figure 21. Combined effects of circumferential boundary stiffness  $K_v = 108$  lb/in., rotational boundary stiffness  $K_\theta$  (in-lb), and prestress the initial out-of-plane displacements at the onset of buckling of a 52-in-radius curved panel in a 60-in-radius test fixture.

REPORT DOCUMENTATION PAGE				Form Approved OMB No. 0704-0188	
<p>The public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Department of Defense, Washington Headquarters Services, Directorate for Information Operations and Reports (0704-0188), 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to any penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.</p> <p><b>PLEASE DO NOT RETURN YOUR FORM TO THE ABOVE ADDRESS.</b></p>					
1. REPORT DATE (DD-MM-YYYY)		2. REPORT TYPE		3. DATES COVERED (From - To)	
01-08-2005		Technical Publication			
4. TITLE AND SUBTITLE Compression-Loaded Composite Panels With Elastic Edge Restraints and Initial Prestress				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S) Hilburger, Mark W.; Nemeth, Michael P.; Riddick, Jaret C.; and Thornburger, Robert P.				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER 23-376-10-30-02	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) NASA Langley Research Center Hampton, VA 23681-2199			8. PERFORMING ORGANIZATION REPORT NUMBER  L-19162		
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) National Aeronautics and Space Administration Washington, DC 20546-0001			10. SPONSOR/MONITOR'S ACRONYM(S)  NASA		
			11. SPONSOR/MONITOR'S REPORT NUMBER(S) NASA/TP-2005-213906 ARL-TR-3572		
12. DISTRIBUTION/AVAILABILITY STATEMENT Unclassified - Unlimited Subject Category 24 Availability: NASA CASI (301) 621-0390					
13. SUPPLEMENTARY NOTES An electronic version can be found at <a href="http://ntrs.nasa.gov">http://ntrs.nasa.gov</a>					
14. ABSTRACT A parametric study of the effects of test-fixture-induced initial prestress and elastic edge restraints on the prebuckling and buckling responses of a compression-loaded, quasi-isotropic curved panel is presented. The numerical results were obtained by using a geometrically nonlinear finite element analysis code with high-fidelity models. The results presented show that a wide range of prebuckling and buckling behavior can be obtained by varying parameters that represent circumferential loaded-edge restraint and rotational unloaded-edge restraint provided by a test fixture and that represent the mismatch in specimen and test-fixture radii of curvature. While a certain range of parameters exists for which the nonlinear prebuckling deformations are small and the buckling loads are nearly equal to the corresponding linear bifurcation buckling load, there is another range of parameters for which the panels exhibit substantial nonlinear prebuckling deformations that yield buckling loads nearly twice the corresponding linear bifurcation buckling load.					
15. SUBJECT TERMS Composite; Compression; Edge; Elastic; Initial; Panels; Prestress; Restraints					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT	18. NUMBER OF PAGES	19a. NAME OF RESPONSIBLE PERSON
a. REPORT	b. ABSTRACT	c. THIS PAGE			STI Help Desk (email: <a href="mailto:help@sti.nasa.gov">help@sti.nasa.gov</a> )
U	U	U	UU	35	19b. TELEPHONE NUMBER (Include area code) (301) 621-0390