

ELECTROCONDUCTIVE PET/SWNT FILMS BY SOLUTION CASTING

Brian W. Steinert and Derrick R. Dean

University of Alabama at Birmingham, Department of Materials Science and Engineering,
1150 10th Avenue South, BEC 254, Birmingham, AL 35294

ABSTRACT

The market for electrically conductive polymers is rapidly growing, and an emerging pathway for attaining these materials is via polymer-carbon nanotube (CNT) nanocomposites, because of the superior properties of CNTs. Due to their excellent electrical properties and anisotropic magnetic susceptibility, we expect CNTs could be easily aligned to maximize their effectiveness in imparting electrical conductivity to the polymer matrix. Single-walled carbon nanotubes (SWNT) were dispersed in a polyethylene terephthalate (PET) matrix by solution blending then cast onto a glass substrate to create thin, flexible films. Various SWNT loading concentrations were implemented (0.5, 1.0, and 3.0 wt.%) to study the effect of additive density. The processing method was repeated to produce films in the presence of magnetic fields (3 and 9.4 Tesla). The SWNTs showed a high susceptibility to the magnetic field and were effectively aligned in the PET matrix. The alignment was characterized with Raman spectroscopy. Impedance spectroscopy was utilized to study the electrical behavior of the films. Concentration and dispersion seemed to play very important roles in improving electrical conductivity, while alignment played a secondary and less significant role. The most interesting result proved to be the effect of a magnetic field during processing. It appears that a magnetic field may improve dispersion of unmodified SWNTs, which seems to be more important than alignment. It was concluded that SWNTs offer a good option as conductive, nucleating filler for electroconductive polymer applications, and the utilization of a magnetic field may prove to be a novel method for CNT dispersion that could lead to improved nanocomposite materials.

KEY WORDS: Materials – Electrically Conductive, Nanotechnology – CNT/CNF Alignment, Advanced Composite Materials/Structures

1. INTRODUCTION

Carbon nanotubes (CNTs) have come to the forefront of nanostructured materials research in the past decade, and interest has grown exponentially since the official discovery and characterization of CNTs in 1991 [1]. This incredible growth and excitement in CNT research is almost solely due to their excellent, inherent properties and physical parameters. Extensive work has been done to characterize CNTs, including their exceptional mechanical [2-5], thermal [6-9] and electrical characteristics [10-14]. CNTs have also been shown to have extremely high aspect ratios (length/diameter), with diameters of one to tens of nanometers and lengths up to the micrometer, or even centimeter, scale [14, 15]. These features make CNTs highly useful in a

wide range of potential applications, such as reinforcement nanofiller, probes, energy storage, and various electronic or thermal devices.

Polymer nanocomposites with CNT filler have been around almost as long as CNTs themselves, with Ajayan et al. publishing the first report on this topic in 1994 [16]. The interest in this area stems from the fact that polymers offer many desirable qualities, such as toughness, space saving, low weight, good surface finish, flexibility, and low cost. Using CNTs as a property enhancing nanofiller for a high performance, lightweight composite is one of the lynchpins of nanocomposite research. The exceptional and unique properties of CNTs offer a great advantage for the production of improved composites, but their utilization within a matrix depends primarily on relationships between the matrix and nanoconstituent; specifically the particle's spatial orientation and interactions at the particle interface [17].

CNTs have been shown to be a practical polymer reinforcement material for low weight structural materials by significantly enhancing the toughness, tensile strength, and modulus of a polymer nanocomposite [18-25]. Also, the extreme thermal stability and thermal conductivity that CNTs have exhibited make polymer nanocomposites equally as viable for many thermal management applications, including as packaging and coatings [6-8, 24-26]. At the same time, the electrical behavior of CNTs has been one of the most highly studied areas in all of CNT research. Theoretical calculations have shown that the electrical properties of CNTs are very dependent upon their structure, or their rolled configuration (i.e. armchair, zig-zag, or chiral) and diameter, more specifically [10, 27]. The nanoscale dimensions, one-dimensional structure, and tubular symmetry of CNTs produce amazing quantum transport effects. Studies have shown that individual CNTs can behave electrically as a single molecule and be defined as quantum wires [13, 28]. Very high conductive capability (resistivity, $R = 10^{-8} \Omega\text{-cm}$) has been reported [11, 14, 29]. This is greater than iron or copper ($R = 10^{-6} \Omega\text{-cm}$) [30], as well as crystalline graphite ($R = 10^{-5} \Omega\text{-cm}$) [31].

CNTs are naturally highly anisotropic because of their high aspect ratios and strong carbon-carbon bonds parallel to the fiber axis. Therefore, it is critical to take advantage of these facts by manipulating the nanoscale particle and imparting anisotropy into the system to produce the highest-performance nanocomposites. Numerous alignment techniques have been attempted to produce this effect, including fiber spinning with drawing [32] and/or with a rotating collector [33], shearing [34, 35], plasma-enhanced deposition [36-38], and electric field-induced alignment [39, 40]. Another technique that has gained recent attention is magnetic alignment [41-44].

CNTs have been shown to be highly susceptible to a magnetic field [45-51]. Magnetic susceptibility (χ) is the degree of magnetization of a material in response to an applied magnetic field, and it has been the subject of multiple theoretical predictions with respect to CNTs [46, 51]. It was found that χ has an increasing, linear dependence on CNT diameter. Also, it has been determined that the χ is dependent on magnetic field direction and temperature. The dependence on magnetic field direction imparts magnetic anisotropy, and therefore CNTs are able to align in the presence of a magnetic field [51].

The objective of this work was to produce an effective conductive polymer by studying the effect of single-wall carbon nanotube (SWNT) inclusion and alignment on the electrical conductivity behavior of polymer nanocomposite films. The relevance of conductive polymers for antistatic or electrostatic dissipation applications is rapidly growing in the marketplace, and this type of research has become increasingly valuable. In a report published by Business Communications Company, Inc., the total North American market for electroactive/conductive

polymers reached 128.5 million pounds valued at \$205.3 million in 2003 [52]. These numbers are estimated to rise to 745 million pounds at a value of almost \$1.6 billion in 2008, representing a growth of 9.8% in total volume per year and 15.3% in value per year [52]. Previous research in the area of CNT alignment and electrical properties has produced promising results. Kimura et al. showed an increase in electrical conductivity and dynamic modulus parallel to aligned multi-wall carbon nanotubes (MWNTs) when compared to the perpendicular direction in a polyester matrix processed with a 10 Tesla magnetic field [41]. Choi et al. presented similar results, establishing a 35% decrease in electrical resistivity when an epoxy-SWNT composite was processed with a 25 Tesla field [42]. Last, Camponeschi et al. interestingly reported that CNT alignment was highly matrix dependent and observed enhancements in an array of property areas for an epoxy-based aligned CNT nanocomposite [44].

2. EXPERIMENTAL

2.1 Materials

PET flakes were purchased from Scientific Polymer Products, Inc. (Ontario, NY), while HiPco processed SWNTs were acquired from Rice University. 1,1,1,3,3,3-Hexafluoro-2-propanol ($\geq 99\%$) (HFP) was purchased from Sigma-Aldrich Co. (St.Louis, MO) to be used as a solvent for the PET polymer.

2.2 Film Preparation

2.2.1 Randomly-oriented Films

Polymer and nanocomposite thin films (thickness, $t \sim 160 \mu\text{m}$) were created using a simple solution blending and casting technique. For the nanocomposite samples, SWNTs were dispersed in HFP with a Cole-Parmer 8892 ultrasonic bath (frequency, $\nu = 42 \text{ kHz}$) for 4 hours to assure the dispersion of large SWNT aggregations throughout the solvent. PET flakes (1:10 PET/HFP) were placed in the HFP-SWNT solution over heat ($\sim 75 \text{ }^\circ\text{C}$) and continuously mixed with a magnetic stir bar until it appeared that the PET was dissolved in the solution. This was indicated by a visual lack of flakes and an increase in solution viscosity. Solution casting was completed by pouring the solution on top of a glass substrate under a fume hood. A square-shaped polydimethylsiloxane (PDMS) barrier (height, $h = 859 \mu\text{m}$) was used to contain and shape the solution and subsequent film. A doctor's blade was used to level the solution to the barrier height. One large film (area, $A = 400 \text{ cm}^2$) of each sample type was produced. Once the solvent had evaporated and crystallization was completed, the film was placed in a Curtin Matheson Scientific, Inc. Equatherm vacuum oven at approximately $90 \text{ }^\circ\text{C}$ to assist in the removal of any residual solvent in the film. Figure 2 shows a digital image of various PET films which were solution cast with SWNT loadings of 0.0, 0.5, and 1.0 wt. %.

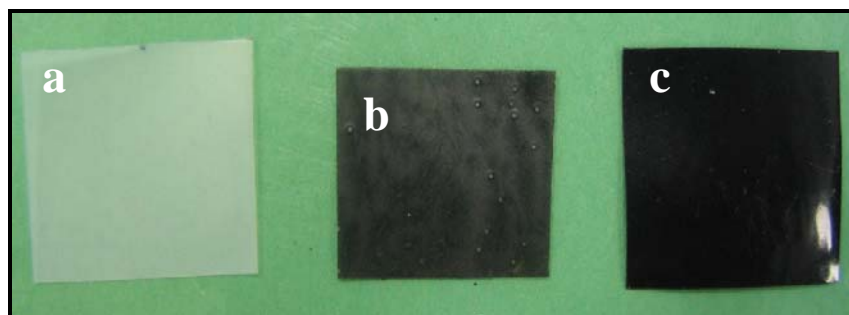


Figure 1. Digital image of solution cast PET films of varying SWNT loadings (a) 0.0 wt.% SWNT, (b) 0.5 wt.% SWNT, and (c) 1.0 wt.% SWNT.

2.2.2 Magnetically Aligned Films

The aligned films were produced in the same manner as the unaligned films, except after the PET-SWNT solutions were poured onto a glass substrate they were subsequently placed in a large magnetic resonance imaging (MRI) scanner. Two separate MRI scanners were used, each producing different magnetic field strengths. A Siemens Magnetom Allegra was used to produce a 3 Tesla magnetic field, while a Bruker BioSpec® was used to produce a 9.4 Tesla magnetic field. Figure 2 presents the experimental setup.

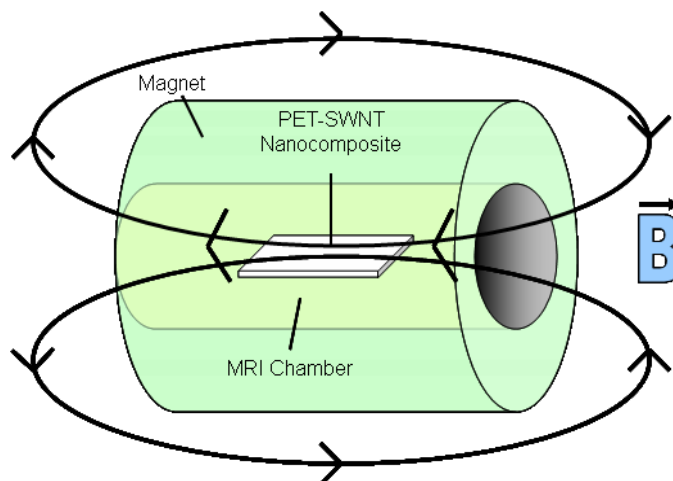


Figure 2. MRI schematic displaying the placement of the samples with respect to the instrument and subsequent magnetic field (\vec{B}).

2.3 Magnetic Alignment Characterization

2.3.1 Raman Spectroscopy

Raman spectroscopy was performed with a Renishaw inVia microRaman microscope. Raman spectra were obtained each magnetically aligned nanocomposite sample (0.5, 1.0, and 3.0 wt.% SWNT). The tangential mode, or G-peaks ($\sim 1600 \text{ cm}^{-1}$), of these spectra were highlighted

and analyzed with respect to the degree of SWNT orientation in the films. Each sample was measured at different angles with respect to the direction of the magnetic field, with 0 degrees corresponding to a direction parallel to the magnetic field and 90 degrees being perpendicular to the field. The experimental parameters include using a 785 nm excitation wavelength, a power of 0.1 mW, a 50x objective lens, a 20 second accumulation time, and 3 accumulations per direction per sample.

2.3.2 Transmission Electron Microscopy (TEM)

TEM micrographs were acquired with an FEI Tecnai™ G² Spirit microscope. Each nanocomposite film was microtomed prior to imaging, parallel and perpendicular to the largest surface area plane, and micrographs were acquired at various magnifications. TEM was used to gather a qualitative understanding of the SWNT alignment.

2.4 Impedance Spectroscopy

The AC electrical impedance of the PET-SWNT nanocomposites was measured with a Hewlett Packard 4284A Precision LCR Meter at room temperature. Measurements were acquired across a frequency range of 20 Hz to 10⁶ Hz. Each aligned sample was measured parallel to the direction of the magnetic field that was placed upon it during processing.

3. RESULTS AND DISCUSSION

3.1 Magnetic Alignment

Due to their magnetic susceptibility [45-51], it should be possible to place SWNTs in a magnetic field and align them in a common orientation parallel to the field direction. Raman spectroscopy is a vital tool when attempting to characterize the degree of alignment of SWNTs in a polymer matrix. A crucial Raman spectra feature of SWNTs can be found at 1590 cm⁻¹. This peak is commonly referred to as the tangential mode (TM), or G-peak, and is attributed to elongations of the carbon-carbon bonds along the longitudinal axis of the CNT. Therefore, if the CNTs are aligned, there should be an increase in the G-peak intensity when they are parallel to the polarized laser excitation plane.

Figure 3 presents the G-peaks of a representative example of an unaligned film. Each peak is identical and independent of the measurement angle, which illustrates the isotropic nature of the CNTs within the nanocomposite. Figure 4 shows the G-peak intensities for 0.5, 1.0, and 3.0 wt.% SWNT samples processed under a 3 Tesla and 9.4 Tesla magnetic field at varying orientation angles (0 degrees is parallel to the magnetic field and 90 degrees is perpendicular to the magnetic field). An additional, higher SWNT concentration sample (3.0 wt.% SWNT) was prepared in order to gain a better understanding of the effect that SWNT concentration has on orientation.

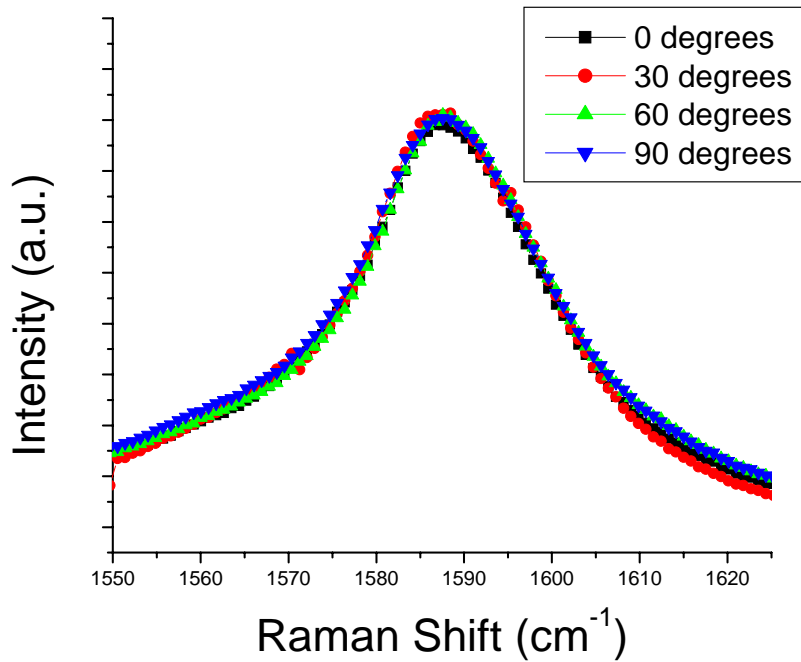


Figure 3. G-peak spectra of an unaligned PET-SWNT nanocomposite film showing the independence of the measurement angle relative to the orientation of the SWNTs.

The spectra (Figure 4) present some very interesting results about the effect of magnetic field strength and SWNT concentration on orientation. Both seem to play a very important role in completing SWNT alignment. An ideal case (perfect alignment along the direction of the magnetic field for 100% of the SWNTs) would produce a Raman spectrum with an intense G-peak parallel to the magnetic field (0 degrees), and extremely minute to almost flat (no intensity) peaks for every other orientation.

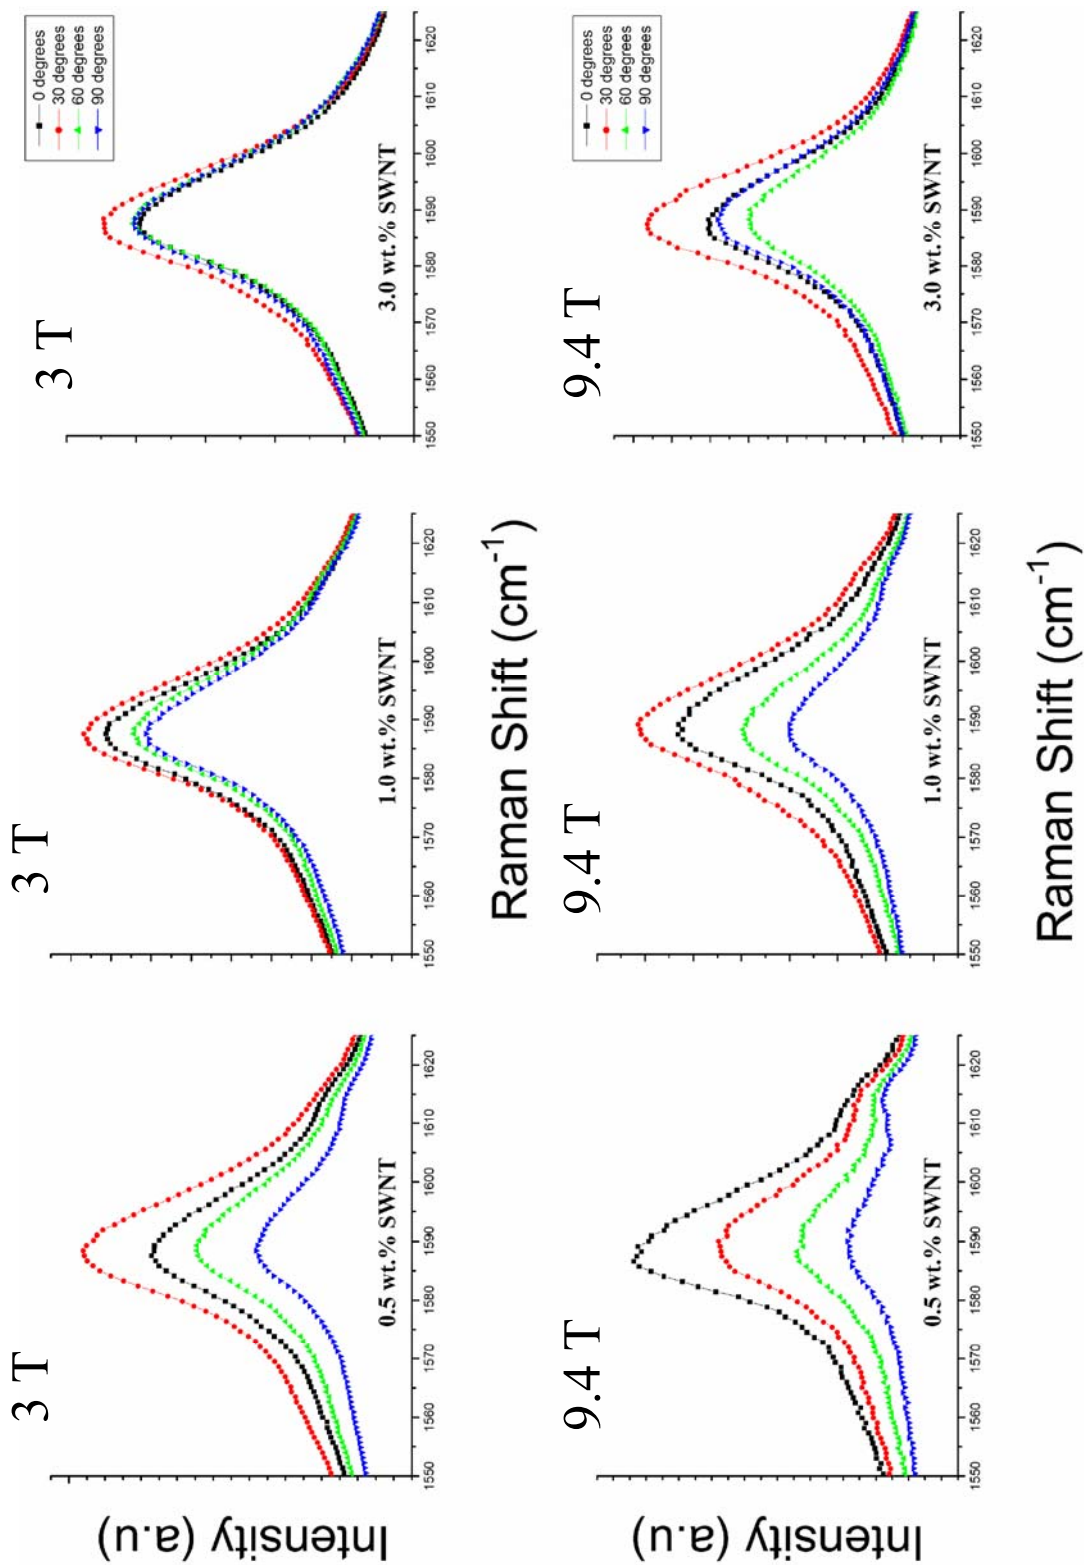


Figure 4. G-band intensities relative to the magnetic field direction (0 degrees = parallel) of Raman spectra for samples with varying SWNT loadings and magnetic field processing parameters.

The G-peak intensity results of this study present incomplete alignment for all three SWNT concentrations processed with a 3 Tesla magnetic field, with the primary orientation being approximately 30° off-parallel. Also, the peak spacing between each orientation (0° - 90°) give a good visual representation of the anisotropy of the SWNTs in the PET matrix. As the SWNT concentration increases, there is a decrease in the peak spacing which corresponds to a more isotropic behavior. This is most likely caused by increasing restrictions on SWNT mobility due to an increase in solution viscosity and nanotube bundling/interactions. Alignment with a much stronger magnetic field (9.4 Tesla) supports this idea. Important to note is that a 9.4 Tesla magnetic field is able to overcome the obstacles that inhibited complete alignment at a low SWNT concentration (0.5 wt.%), while the more isotropic behavior at higher concentrations is less prominent. The peak spacing is further apart for the 9.4 Tesla processed samples as compared to their 3 Tesla counterparts, which means the higher field strength is able to produce more aligned samples at higher SWNT concentrations. This behavior can be visually interpreted through digital TEM micrographs showing the extent of SWNT alignment as a function of magnetic field strength (Figure 5).

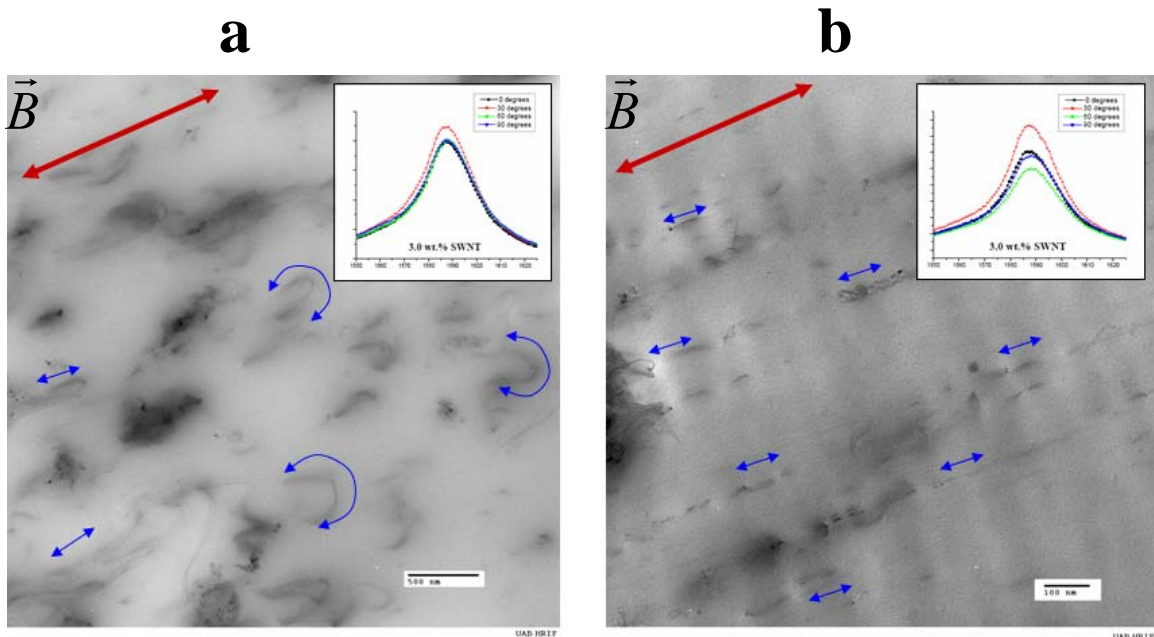


Figure 5. TEM micrographs showing the effect of magnetic field strength at a constant SWNT loading (3.0 wt.%), but with varying magnetic field strengths of (a) 3.0 Tesla and (b) 9.4 Tesla.

The micrographs present a qualitative measurement of the effect of magnetic field strength on SWNT alignment within a PET matrix. The 3.0 wt.% SWNT sample processed at 3 Tesla (Figure 5a) shows slight, generalized alignment of the SWNTs while a large quantity of the nanotubes are unextended. Due to the manner in which many of the SWNTs in the micrograph appear bent but directed towards the direction of the magnetic field, it would seem to indicate that the SWNTs were in the process of aligning to the field but were not able to completely extend before solidification impeded their motion. The 9.4 magnetic field was strong enough to achieve much better SWNT alignment (Figure 5b), while the resistive forces were too great for a

weaker magnetic field to completely overcome them in the allotted processing time. This implies that an adjusted solution-based sample preparation process with slower solvent evaporation may yield aligned SWNTs in a 3 Tesla magnetic field.

Therefore, it appears that magnetic alignment may be a practical technique for establishing anisotropy in a nanocomposite system. It can partially occur under magnetic field strengths as low as 3 Tesla, with the SWNT concentration and magnetic field strength playing important roles in determining the degree of orientation. Though a 3 Tesla magnetic field was not able to achieve complete alignment, even at low SWNT loadings, the samples processed at this parameter may still prove to be a very effective conductive material. It has been reported that complete alignment may not be ideal for enhancing conductivity, due to an increase in void space between nanotubes [53, 54]. Straight lines of SWNTs do not agree with the model of an interconnecting network that produces percolation. Improving SWNT behavior by taking advantage of their anisotropic nature while reducing void space and nanotube-to-nanotube distance with only slight alignment (30° off-parallel) could potentially produce the best electrically conductive behavior [34, 55].

3.2 Electrical Conductivity

From the impedance spectroscopy data, the electrical conductivity as a function of frequency can be determined (Figure 6). By plotting conductivity as a function of SWNT concentration, the relative percolation threshold of each sample type was estimated (Figure 7). Figure 7 shows the conductivities at 60 Hz as a function of SWNT mass fraction and dependent upon magnetic field strength. Based on the conductivity of pure PET material, the addition of 0.5 and 1.0 wt.% SWNTs approximately produced a 7 order of magnitude increase, while the addition of 3.0 wt.% SWNTs in a 3 and 9.4 Tesla magnetic field produced an 8 and 9 order of magnitude increase, respectively. Therefore, it can be safely assumed that the percolation threshold is approximately 0.5 wt.% SWNT. This value agrees satisfactorily with previous values observed in other polymer-CNT nanocomposite studies [53, 56-61].

Also shown in Figure 7 are the relative applications for these materials based on their conductive behaviors. It is noticeable that at 0.5 wt.% SWNT, the conductivity of the samples exceeds the antistatic and electrostatic dissipation conditions, but electromagnetic interference (EMI) shielding ($\sim 10^{-4}$ S/cm) would not be possible. Meeting the standards of specific, targeted applications is a very important goal of this work.

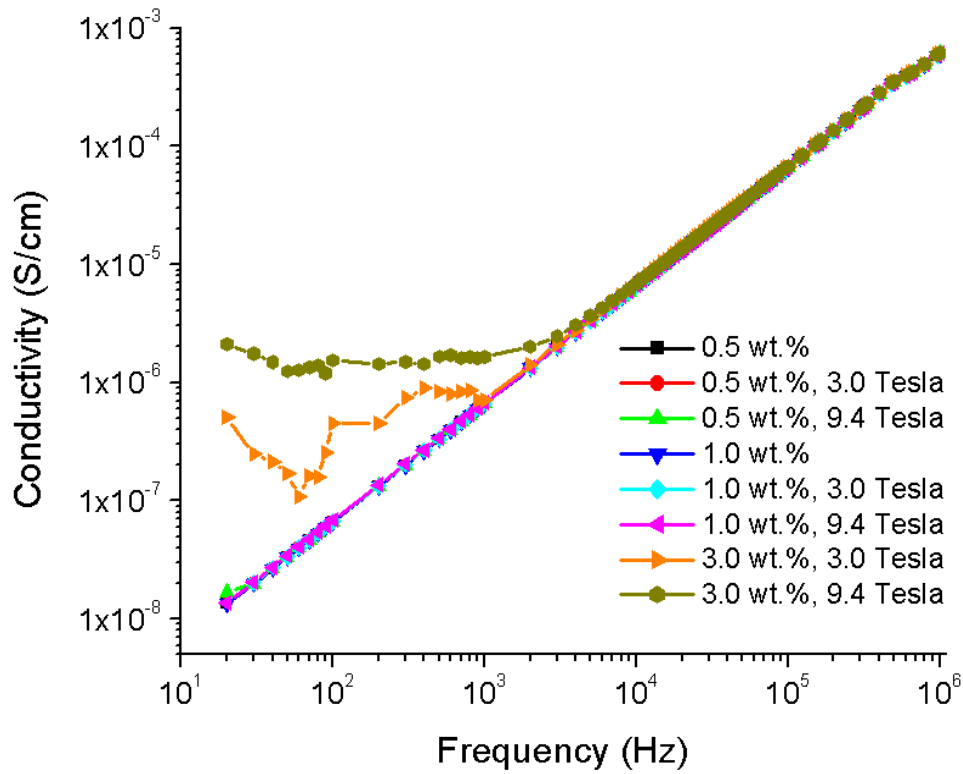


Figure 6. Log-log plot of the AC conductivity as a function of frequency for various nanocomposite samples.

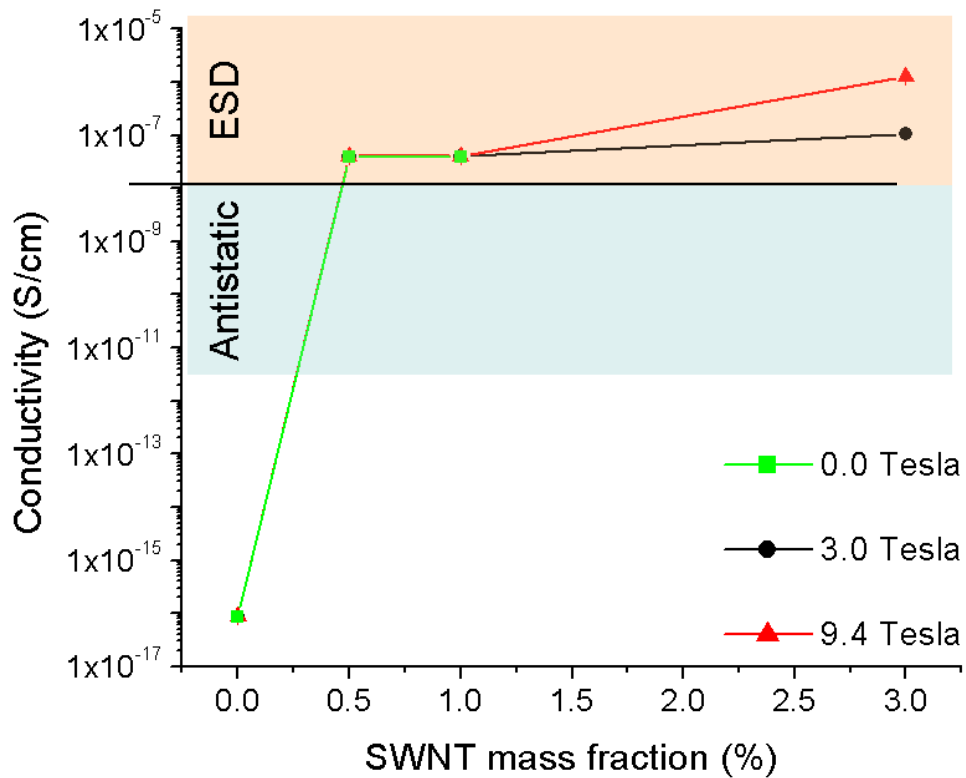


Figure 7. Log(AC conductivity) as a function of SWNT mass fraction at 60 Hz showing dependence on magnetic field strength, and the relative applications based on the values.

From the results, it was observed that when SWNT concentration reaches 3.0 wt.% there is an increase in electrical conductivity and non-dielectric behavior. The simple explanation to describe this behavior is to associate it with the increase in filler concentration and conclude that more filler material produces a more extensive electron flow network. However, a similar increase is not observed when the SWNT concentration reaches 0.5 and 1.0 wt.% for the unaligned or aligned samples, and so there must be supplementary details that require rationalization. Also, the explanation cannot be directly connected to the creation of a percolation network at 3.0 wt.%, because as previously stated, a percolation threshold was achieved at no more than 0.5 wt.%.

The frequency dependent behavior observed at 0.5 and 1.0 wt.% implies the existence of large gap distances between conductive particles within the matrix, and thus the formation of aggregated SWNT domains. This is synonymous with relatively poor dispersion. This behavior is not unusual for SWNTs, because SWNTs express fairly strong self-attraction due to van der Waals forces between the nanotubes [62, 63]. The increase in gap distance between domains results in a build up of electron flow in the matrix void space. Percolation is ideal, and conductivity is maximized, when physical contact exists between the CNTs, but it is not absolutely necessary to allow current to flow across a device [64], which occurred in the 0.5 and 1.0 wt.% neat samples.

When the SWNT concentration is 3.0 wt.% and manipulated with a magnetic field, there is a dramatic change in the electrical behavior at low frequencies. As mentioned, the change cannot be attributed solely to filler concentration. This suggests that the magnetic fields must be invoking an effect. If the SWNTs have a tendency to aggregate, then something must be inhibiting this aggregation to some extent in the aligned 3.0 wt.% samples, because they display a frequency-independent, non-dielectric region at low frequencies (Figure 6). This behavior is more prominent (wider non-dielectric range, greater conductivity) for the 9.4 Tesla processed sample than for the 3 Tesla processed sample. The increased conductivity and non-dielectric range in the 9.4 Tesla sample suggests that the sample has better dispersion. A more dispersed sample possesses smaller gaps between conductive particles, which means more electrons can easily 'hop' between particles and flow across a device.

How is the improved dispersion and greater electrical conductivity at higher concentrations of the aligned samples explained? It cannot be solely due to improved alignment, because it has been concluded in the previous section (3.1) that ideal alignment occurs at a low filler concentration and a high magnetic field strength. According to the Raman spectra (Figure 4), the 3.0 wt.% sample processed at 3 Tesla is basically isotropic with respect to the SWNTs. The 9.4 Tesla processed sample has slightly better alignment according to the respective spectra. Also, there is almost no difference in the electrical behavior between the aligned SWNTs processed at each magnetic field strength of the 0.5 and 1.0 wt.% samples. If the improved results had a direct correlation with alignment, then the same improvement observed at 3.0 wt.% should be observed at lower concentrations, especially since there is much greater disparity in the degree of alignment when comparing the effect of field strength at lower concentrations.

Therefore, if the explanation cannot be attributed to concentration or alignment alone, then the answer may be a combination of these effects. The ability to flow into aggregated domains appears to be a problem for samples with lower concentration (0.5 and 1.0 wt.%), because there is plenty of void space between SWNTs and their motion is therefore not significantly inhibited. This same effect was observed and discussed in the G-peak analysis of the Raman spectra to describe the alignment behavior. This may also help to explain the

dispersion and conductivity improvement shown in the 3.0 wt.% samples. As shown in Figure 4, the SWNTs were not able to completely align and overcome the resistive forces that arise with increased tube-to-tube interaction and solution viscosity. If this interaction can inhibit motion in one plane, then why can it not have the same effect in all others? The 3.0 wt.% SWNT samples appear to exceed a ‘density threshold’, where the tendency to flow into aggregated domains is counteracted by the lack of void space and freedom to do so. Therefore, the SWNTs, for the most part, are forced to remain in a semi-dispersed state, which creates a better network and improved conductivity.

At the same time, the magnetic field is also producing a beneficial effect to the material. The 3.0 wt.% sample processed at 3 Tesla is essentially isotropic, and so the electrical improvement observed for this sample can be considered almost identical to the improvement that would be expected from a 3.0 wt.% sample not processed with an applied magnetic field. However, a 9.4 Tesla field is strong enough to invoke an effect, which could be explained with either of the following scenarios, or a combination of the two:

1. The magnetization, or force upon the nanotube, that a SWNT experiences from an applied magnetic field reduces the effect of the van der Waals forces that attract the SWNTs to each other. It has been reported that weakly bound van der Waals complexes can dissociate in a magnetic field through coupling between the Zeeman energy levels [65]. At zero magnetic field, van der Waals complexes are stable while an external magnetic field can split Zeeman energy levels, and bound states may be higher in energy. This encourages molecular dissociation, and the dissociation efficiency increases with increasing field strength. Thus, even though there is very little motion due to overcrowding of the SWNTs, any motion that does occur is halted and reduced further. This results in a more dispersed sample, and the increase in the non-dielectric range and conductivity observed in the results (Figures 6 and 7).

2. The slight improvement in alignment observed in Figure 4, when comparing the 3.0 wt.% sample processed at 3 Tesla to the 9.4 Tesla sample, creates a better and more anisotropic network, which improves electrical behavior. This same effect is not observed at lower concentrations (despite greater alignment), because the distance between the conductive particles is too great. Most likely, the effect of the magnetic fields is a combination of this scenario with the first scenario.

Overall, it appears that the most important contributing factors to electrical conductivity in a nanocomposite are filler concentration and dispersion. Alignment appears to impart a secondary consequence, as long as a ‘density threshold’ has been reached. An interesting finding seems to be that a strong enough magnetic field may improve dispersion by disrupting the effect of the van der Waals forces and inhibiting SWNT flow. This could prove to be a very important attribute to consider for future nanocomposite manufacturing, because developing a method to achieve good dispersion of unmodified SWNTs in a polymer could produce unprecedented properties. However, questions remain about the effect thresholds and cost effectiveness of such a method.

4. CONCLUSIONS

Solution casting was effectively employed to produce PET-SWNT nanocomposite films. Magnetic fields were employed to produce SWNT alignment within the PET matrix. Raman spectroscopy was used to measure the effectiveness of the magnetic fields, and it was determined

that the field strength and filler concentration play the most important roles in determining the degree of alignment. Low concentration and high magnetic field strength produce the most highly aligned samples. The electrical properties of unaligned and aligned film samples were investigated by impedance spectroscopy, and it was shown that sufficient conductivity for antistatic and electrostatic dissipation purposes can be achieved at concentrations as low as 0.5 wt.% SWNT. It was also concluded that dispersion and filler concentration have the greatest effect upon electrical conductivity, and alignment plays a secondary role. However, it was determined that it may be possible to use a magnetic field to improve dispersion, or at least produce a more anisotropic network. This could have important implications in future applications, and it may prove to be a novel method for achieving good dispersion of unmodified SWNTs.

5. ACKNOWLEDGEMENTS

This work was supported by the National Science Foundation (NSF) through the Division of Materials Research (DMR) Grant No. 0404278.

6. REFERENCES

- [1] Iijima S. Helical microtubules of graphitic carbon. *Nature* 1991; 354(6348):56-58.
- [2] Treacy MMJ, Ebbesen TW, Gibson JM. Exceptionally high Young's modulus observed for individual carbon nanotubes. *Nature* 1996; 381(6584):678-680.
- [3] Krishnan A, Dujardin E, Ebbesen TW, Yianilos PN, Treacy MMJ. Young's modulus of single-walled nanotubes. *Phys. Rev. B* 1998; 58(20):14013-14019.
- [4] Pan ZW, Xie SS, Lu L, Chang BH, Sun LF, Zhou WY, Wang G, Zhang DL. Tensile tests of ropes of very long aligned multiwall carbon nanotubes. *Appl. Phys. Lett.* 1999; 74(21):3152-3154.
- [5] Natsuki T, Tantrakarn K, Endo M. Effects of carbon nanotube structures on mechanical properties. *Appl. Phys. A - Mater.* 2004; 79(1):117-124.
- [6] Hone J, Whitney M, Piskoti C, Zettl A. Thermal conductivity of single-walled carbon nanotubes. *Phys. Rev. B* 1999; 59(4):R2514-R2516.
- [7] Berber S, Kwon Y-K, Tománek D. Unusually High Thermal Conductivity of Carbon Nanotubes. *Phys. Rev. Lett.* 2000; 84(20):4613-4616.
- [8] Che J, agin T, Iii WAG. Thermal conductivity of carbon nanotubes. *Nanotechnology* 2000; 11(2):65-69.
- [9] Motoo F, Xing Z, Huaqing X, Hiroki A, Koji T, Tatsuya I, Hidekazu A, Tetsuo S. Measuring the Thermal Conductivity of a Single Carbon Nanotube. *Phys. Rev. Lett.* 2005; 95(6):0655021-0655024.
- [10] Hamada N, Sawada S-i, Oshiyama A. New one-dimensional conductors: Graphitic microtubules. *Phys. Rev. Lett.* 1992; 68(10):1579-1581.
- [11] Ebbesen TW, Lezec HJ, Hiura H, Bennett JW, Ghaemi HF, Thio T. Electrical conductivity of individual carbon nanotubes. *Nature* 1996; 382(6586):54-56.

- [12] Langer L, Bayot V, Grivei E, Issi JP, Heremans JP, Olk CH, Stockman L, Van Haesendonck C, Bruynseraede Y. Quantum Transport in a Multiwalled Carbon Nanotube. *Phys. Rev. Lett.* 1996; 76(3):479-482.
- [13] Tans SJ, Devoret MH, Dai H, Thess A, Smalley RE, Geerligs LJ, Dekker C. Individual single-wall carbon nanotubes as quantum wires. *Nature* 1997; 386(6624):474-477.
- [14] Li S, Yu Z, Rutherglen C, Burke PJ. Electrical Properties of 0.4 cm Long Single-Walled Carbon Nanotubes. *Nano Lett.* 2004; 4(10):2003-2007.
- [15] Zheng LX, O'Connell MJ, Doorn SK, Liao XZ, Zhao YH, Akhadvov EA, Hoffbauer MA, Roop BJ, Jia QX, Dye RC, Peterson DE, Huang SM, Liu J, Zhu YT. Ultralong single-wall carbon nanotubes. *Nat Mater* 2004; 3(10):673-676.
- [16] Ajayan P, Stephan O, Colliex C, Trauth D. Aligned Carbon Nanotube Arrays Formed by Cutting a Polymer Resin--Nanotube Composite. *Science* 1994; 265(5176):1212-1214.
- [17] Krishnamoorti R, Vaia RA, Polymer Nanocomposites: Synthesis, Characterization, and Modeling. ACS Symposium Series 804, ed. A.C. Society. 2002, Oxford UP: Washington D.C.
- [18] Andrews R, Weisenberger MC. Carbon nanotube polymer composites. *Curr. Opin. Solid State Mater. Sci.* 2004; 8(1):31-37.
- [19] Coleman JN, Khan U, Gun'ko YK. Mechanical Reinforcement of Polymers Using Carbon Nanotubes. *Adv. Mater.* 2006; 18(6):689-706.
- [20] Wu M, Shaw L. Electrical and mechanical behaviors of carbon nanotube-filled polymer blends. *J. Appl. Polym. Sci.* 2006; 99(2):477-488.
- [21] Cadek M, Coleman JN, Barron V, Hedicke K, Blau WJ. Morphological and mechanical properties of carbon-nanotube-reinforced semicrystalline and amorphous polymer composites. *Appl. Phys. Lett.* 2002; 81(27):5123-5125.
- [22] Safadi B, Andrews R, Grulke EA. Multiwalled carbon nanotube polymer composites: Synthesis and characterization of thin films. *J. Appl. Polym. Sci.* 2002; 84(14):2660-2669.
- [23] Cadek M, Coleman J, Ryan K, Nicolosi V, Bister G, Fonseca A, Nagy J, Szostak K, Beguin F, Blau W. Reinforcement of Polymers with Carbon Nanotubes: The Role of Nanotube Surface Area. *Nano Lett.* 2004; 4(2):353-356.
- [24] Breuer O, Sundararaj U. Big returns from small fibers: A review of polymer/carbon nanotube composites. *Polym. Compos.* 2004; 25(6):630-645.
- [25] Moniruzzaman M, Winey KI. Polymer Nanocomposites Containing Carbon Nanotubes. *Macromolecules* 2006; 39(16):5194-5205.
- [26] Fei D, Quan-Shui Z, Li-Feng W, Ce-Wen N. Effects of anisotropy, aspect ratio, and nonstraightness of carbon nanotubes on thermal conductivity of carbon nanotube composites. *Appl. Phys. Lett.* 2007; 90(2):021914-1 - 021914-3.
- [27] Mintmire JW, Dunlap BI, White CT. Are fullerene tubules metallic? *Phys. Rev. Lett.* 1992; 68(5):631-634.
- [28] Dekker C. Carbon Nanotubes as Molecular Quantum Wires. *Physics Today* 1999:22-28.
- [29] McEuen PL, Fuhrer MS, Hongkun P. Single-walled carbon nanotube electronics. *Nanotechnology, IEEE Transactions on* 2002; 1(1):78-85.
- [30] MatWeb. 2007, Automation Creations, Inc.
- [31] Primak W, Fuchs LH. Electrical Conductivities of Natural Graphite Crystals. *Physical Review* 1954; 95(1):22-31.

- [32] Sennett M, Welsh E, Wright JB, Li WZ, Wen JG, Ren ZF. Dispersion and alignment of carbon nanotubes in polycarbonate. *Appl. Phys. A - Mater.* 2003; 76(1):111-113.
- [33] Jose MV, Steinert BW, Thomas V, Dean DR, Abdalla MA, Price G, Janowski GM. Morphology and mechanical properties of Nylon 6/MWNT nanofibers. *Polymer* 2007; 48(4):1096-1104.
- [34] Lanticse LJ, Tanabe Y, Matsui K, Kaburagi Y, Suda K, Hoteida M, Endo M, Yasuda E. Shear-induced preferential alignment of carbon nanotubes resulted in anisotropic electrical conductivity of polymer composites. *Carbon* 2006; 44(14):3078-3086.
- [35] Abdalla M, Dean D, Adibempe D, Nyairo E, Robinson P, Thompson G. The effect of interfacial chemistry on molecular mobility and morphology of multiwalled carbon nanotubes epoxy nanocomposite. *Polymer* 2007; 48(19):5662-5670.
- [36] Ren ZF, Huang ZP, Xu JW, Wang JH, Bush P, Siegal MP, Provencio PN. Synthesis of Large Arrays of Well-Aligned Carbon Nanotubes on Glass. *Science* 1998; 282(5391):1105-1107.
- [37] Chris B, Wei Z, Sungho J, Otto Z. Plasma-induced alignment of carbon nanotubes. *Appl. Phys. Lett.* 2000; 77(6):830-832.
- [38] Huang ZP, Xu JW, Ren ZF, Wang JH, Siegal MP, Provencio PN. Growth of highly oriented carbon nanotubes by plasma-enhanced hot filament chemical vapor deposition. *Appl. Phys. Lett.* 1998; 73(26):3845-3847.
- [39] Park C, Wilkinson J, Banda S, Ounaies Z, Wise KE, Sauti G, Lillehei PT, Harrison JS. Aligned single-wall carbon nanotube polymer composites using an electric field. *J. Polym. Sci., Part B: Polym. Phys.* 2006; 44(12):1751-1762.
- [40] Martin CA, Sandler JKW, Windle AH, Schwarz MK, Bauhofer W, Schulte K, Shaffer MSP. Electric field-induced aligned multi-wall carbon nanotube networks in epoxy composites. *Polymer* 2005; 46(3):877-886.
- [41] Kimura T, Ago H, Tobita M, Ohshima S, Kyotani M, Yumura M. Polymer Composites of Carbon Nanotubes Aligned by a Magnetic Field. *Adv. Mater.* 2002; 14(19):1380-1383.
- [42] Choi ES, Brooks JS, Eaton DL, Al-Haik MS, Hussaini MY, Garmestani H, Li D, Dahmen K. Enhancement of thermal and electrical properties of carbon nanotube polymer composites by magnetic field processing. *J. Appl. Phys.* 2003; 94(9):6034-6039.
- [43] Garmestani H, Al-Haik MS, Dahmen K, Tannenbaum R, Li D, Sablin SS, Hussaini MY. Polymer-Mediated Alignment of Carbon Nanotubes under High Magnetic Fields. *Adv. Mater.* 2003; 15(22):1918-1921.
- [44] Camponeschi E, Vance R, Al-Haik M, Garmestani H, Tannenbaum R. Properties of carbon nanotube-polymer composites aligned in a magnetic field. *Carbon* 2007; 45(10):2037-2046.
- [45] Heremans J, Olk CH, Morelli DT. Magnetic susceptibility of carbon structures. *Phys. Rev. B* 1994; 49(21):15122-15125.
- [46] Lu JP. Novel Magnetic Properties of Carbon Nanotubes. *Phys. Rev. Lett.* 1995; 74(7):1123-1126.
- [47] Smith BW, Benes Z, Luzzi DE, Fischer JE, Walters DA, Casavant MJ, Schmidt J, Smalley RE. Structural anisotropy of magnetically aligned single wall carbon nanotube films. *Appl. Phys. Lett.* 2000; 77(5):663-665.
- [48] Walters DA, Casavant MJ, Qin XC, Huffman CB, Boul PJ, Ericson LM, Haroz EH, O'Connell MJ, Smith K, Colbert DT, Smalley RE. In-plane-aligned membranes of carbon nanotubes. *Chem. Phys. Lett.* 2001; 338(1):14-20.

- [49] Likodimos V, Glenis S, Guskos N, Lin CL. Magnetic and electronic properties of multiwall carbon nanotubes. *Phys. Rev. B* 2003; 68(4):045417.
- [50] Ajiki H, Ando T. Aharonov-Bohm effect in carbon nanotubes. *Physica B: Condensed Matter* 1994; 201:349-352.
- [51] Ajiki H, Ando T. Magnetic Properties of Ensembles of Carbon Nanotubes. *J. Phys. Soc. Jpn.* 1995; 64(11):4382-4391.
- [52] *Conductive Polymers*. 2003, Business Communications Company, Inc.: Norwalk, CT.
- [53] Du F, Fischer JE, Winey KI. Coagulation method for preparing single-walled carbon nanotube/poly(methyl methacrylate) composites and their modulus, electrical conductivity, and thermal stability. *J. Polym. Sci., Part B: Polym. Phys.* 2003; 41(24):3333-3338.
- [54] Munson-McGee SH. Estimation of the critical concentration in an anisotropic percolation network. *Phys. Rev. B* 1991; 43(4):3331.
- [55] Du F, Fischer JE, Winey KI. Effect of nanotube alignment on percolation conductivity in carbon nanotube/polymer composites. *Physical Review B (Condensed Matter and Materials Physics)* 2005; 72(12):121404.
- [56] Hu G, Zhao C, Zhang S, Yang M, Wang Z. Low percolation thresholds of electrical conductivity and rheology in poly(ethylene terephthalate) through the networks of multi-walled carbon nanotubes. *Polymer* 2006; 47(1):480-488.
- [57] Sandler JKW, Kirk JE, Kinloch IA, Shaffer MSP, Windle AH. Ultra-low electrical percolation threshold in carbon-nanotube-epoxy composites. *Polymer* 2003; 44(19):5893-5899.
- [58] Chang TE, Kisliuk A, Rhodes SM, Brittain WJ, Sokolov AP. Conductivity and mechanical properties of well-dispersed single-wall carbon nanotube/polystyrene composite. *Polymer* 2006; 47(22):7740-7746.
- [59] Antonucci V, Faiella G, Giordano M, Nicolais L, Pepe G. Electrical Properties of Single Walled Carbon Nanotube Reinforced Polystyrene Composites. *Macromolecular Symposia* 2007; 247(1):172-181.
- [60] Seo M-K, Park S-J. Electrical resistivity and rheological behaviors of carbon nanotubes-filled polypropylene composites. *Chem. Phys. Lett.* 2004; 395(1-3):44-48.
- [61] Anand KA, Agarwal US, Joseph R. Carbon nanotubes-reinforced PET nanocomposite by melt-compounding. *J. Appl. Polym. Sci.* 2007; 104(5):3090-3095.
- [62] Dresselhaus MS, Dresselhaus G, Avouris P, *Carbon Nanotubes: Synthesis, Structure, Properties, and Applications*. Top. Appl. Phys. Vol. 80. 2001, Springer: New York, NY.
- [63] Meyyappan M, *Carbon Nanotubes: Science and applications*. 2005, CRC Press LLC: Boca Raton, FL.
- [64] Curran S, Zhang D, Wondmagegn W, Ellis A, Cech J, Roth S, Carroll D. Dynamic electrical properties of polymer-carbon nanotube composites: Enhancement through covalent bonding. *J. Mater. Res.* 2006; 21(4):1071-1077.
- [65] Krems RV. Breaking van der Waals Molecules with Magnetic Fields. *Phys. Rev. Lett.* 2004; 93(1):013201.