

Photocatalytic Activity of S-doped TiO₂ Photocatalyst under Visible Light

著者	Ohno Teruhisa, Mitsui Takahiro, Matsumura Michio
journal or publication title	Chemistry Letters
volume	32
number	4
page range	364-365
year	2003-04
URL	http://hdl.handle.net/10228/00006476

doi: info:doi/10.1246/cl.2003.364

Photocatalytic Activity of S-doped TiO₂ Photocatalyst under Visible Light

Teruhisa Ohno,* Takahiro Mitsui, and Michio Matsumura
 Research Center for Solar Energy Chemistry, Osaka University,
 1-3 Machikaneyama, Toyonaka, Osaka 560-8531

(Received January 20, 2003; CL-030053)

In order to effectively utilize visible light in photocatalytic reactions, we have developed S-doped TiO₂ particles. They show strong absorption for visible light and high activities for degradation of methylene blue in aqueous solution under irradiation at wavelengths longer than 440 nm. The oxidation state of the S atoms incorporated into the TiO₂ particles is determined to be S⁶⁺ from the XPS spectra.

After the discovery of photoinduced water splitting at titanium dioxide (TiO₂) electrodes,¹ the phenomena have been applied to TiO₂-mediated heterogeneous photocatalyses.²⁻¹⁷ Because electrons and holes photogenerated in the TiO₂ photocatalysts have strong reduction and oxidation power, respectively, they can drive a variety of reactions. By utilizing this property, it has been reported that pollutants in air and water can be effectively decomposed.²⁻⁶ It has also been reported that unique organic synthetic reactions occur on irradiated TiO₂.⁷⁻¹⁷ Most of these investigations have been carried out under UV light, because TiO₂ absorbs light of wavelength 400 nm or shorter.

In order to utilize sunlight or rays from artificial sources more effectively in photocatalytic reactions, photocatalysts with strong absorption in the visible region should be developed. For this purpose, doping of TiO₂ with transition metals has been investigated.^{18,19} Treatment of TiO₂ powder with hydrogen peroxide²⁰ or chelating agents²¹ allows some kind of photocatalytic reactions to proceed under visible light. However, most of these catalysts do not show long term stability or do not have activities high enough for a wide range of applications. Asahi et al.²² reported that N-doped TiO₂ shows photoabsorption at wavelengths longer than 400 nm. It has also been reported that the N-doped TiO₂ has photocatalytic activity under visible light. Recently, Umebayashi et al. have also succeeded in synthesizing TiO₂ doped with S atoms.²³ The compound absorb visible light. This result is supported by a theoretical calculation using full-potential linearized augmented plane wave formalism.²² However, the absorption spectra of these compounds in the visible region are extremely small. It is noted that the dopants are incorporated as anions and take the place of oxygen in the lattice of TiO₂.

Here, we report synthesis of new S-doped TiO₂ powders. In contrast to the S-doped TiO₂ reported by Umebayashi et al., S atoms are incorporated as cations and are expected to be replaced with Ti ions. Furthermore, these powders absorb visible light more strongly than the N-doped TiO₂ and the S-doped TiO₂ powders, and show photocatalytic activity under visible light.

For synthesizing the S-doped TiO₂ powders, titanium isopropoxide (50 g, 0.175 mol) was mixed with thiourea (53.6 g, 0.70 mol) at a molar ratio of 1 to 4 in ethanol (500 mL). The solution was stirred at room temperature for 1 h and evaporated completely under reduced pressure. After evaporation of ethanol, white powder was obtained. We calcined the powder at different temperatures under aerated conditions, and obtained yellow

powder. We call this powder S-doped TiO₂, because a small amount of S atoms, but no C and N atoms, are included in it, as shown later.

The density of the yellow color depends on the calcination temperatures. Some examples of diffuse reflectance spectra of these powders, together with pure rutile and anatase powders, are shown in Figure 1. Photoabsorption in the visible region is strongest when the powder was calcined at about 500 °C. The photoabsorption in the visible region is stronger than that of the N-doped TiO₂ powder, which was prepared according to the literature.²¹ With the increase of the calcination temperature above 500 °C, the absorption in the visible region decreases gradually. When it reaches 700 °C, the absorption decreases drastically. Despite the drastic decrease of the absorption in the visible region, the S-doped TiO₂ powder calcined at temperatures higher than 700 °C keeps strong photoabsorption at wavelengths near 400 nm (see Figure 1).

The relative surface area of S-doped TiO₂ powders was determined by the BET method using a surface area analyzer (Micromeritics, FlowSorb II 2300). When the powder was calcined at 400 °C for 3 h, the surface area was 75.8 m²/g. The surface area decreases with increasing calcination temperature (Table 1). Contents of the anatase and rutile phases in the S-doped TiO₂ powders were determined from the X-ray diffraction (XRD) patterns obtained by using an X-ray diffractometer (Philips, X'Pert-MRD) with a Cu target K α -ray ($\lambda = 1.5405 \text{ \AA}$). The

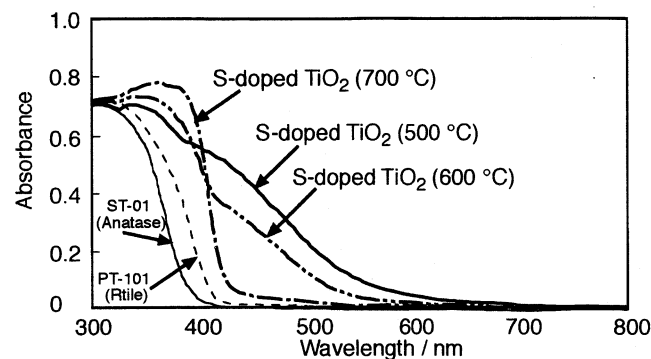


Figure 1. Diffuse reflectance spectra of S-doped and pure TiO₂ powders.

Table 1. Specific surface area and content of anatase phase of S-doped TiO₂ powders calcined under different conditions

Calcination temperature /time	Specific Surface area /m ² /g	Content of anatase /%
400 °C/3 h	75.8	100
400 °C/10 h	60.1	100
500 °C/3 h	17.7	99
500 °C/10 h	16.9	97
600 °C/3 h	9.3	43
600 °C/10 h	8.7	38
700 °C/3 h	5.3	0
700 °C/10 h	4.9	0

content of the anatase phase in the particles is also shown in Table 1. By comparing the changes of the diffuse reflectance spectra and the contents of the anatase phase, one can conclude that the anatase particles are strongly colored. However, it should also be noted that the rutile powder still shows weak photoabsorption in the visible region; see the spectrum of S-doped TiO₂ (700 °C) in Figure 1.

The chemical states of S atoms incorporated into TiO₂ were studied by measuring the XPS spectra of the S-doped TiO₂. From the results, it was found that S atoms are in the state of S²⁻ before the calcination of the sample. By calcination under aerated conditions at temperatures above 400 °C, the S2p(3/2) peak appears at 170 eV, which is attributed to S⁶⁺ state, as shown in Figure 2. By washing the powder with deionized water and HCl aqueous solution for several times, the XPS peak due to S⁶⁺ is lowered, suggesting that S⁶⁺ species such as sulfuric acid are adsorbed on the surface of TiO₂. However, it should be emphasized that a weak peak attributable to S⁶⁺ remains after complete washing. The peak was also observed after the Ar⁺ ion etching of the sample. The atomic content of S atoms on the surface of the S-doped powder is about 1.6% after the washing treatment. With the increase of the depth from the surface of TiO₂, the concentration of S⁶⁺ decreases gradually to about 0.5% in the bulk. These results strongly indicate that S atoms are incorporated into the bulk phase of TiO₂. It is important to note that no peak attributable to C and N atoms was observed after calcination of the S-doped TiO₂ powders.

By comparing the XRD patterns of the S-doped TiO₂ powders with those of pure anatase and rutile powders having nearly the same particle sizes, we found that the S-doped samples show broader peaks than those of pure TiO₂ samples. On the other hand, the peak positions are nearly the same. These results suggest that the crystal lattices of S-doped TiO₂ powders are locally distorted by incorporating S⁶⁺ species into TiO₂, while the averaged unit cell length is unchanged. Whether the S⁶⁺ species are introduced interstitially or at the lattice sites is to be clarified. However, the distortion of the local lattice is probably responsible to the absorption in the visible region and to the shift of the onset of their absorption edge near 400 nm.

Photocatalytic activity of the S-doped TiO₂ powders was evaluated by measuring the decomposition rates of methylene blue

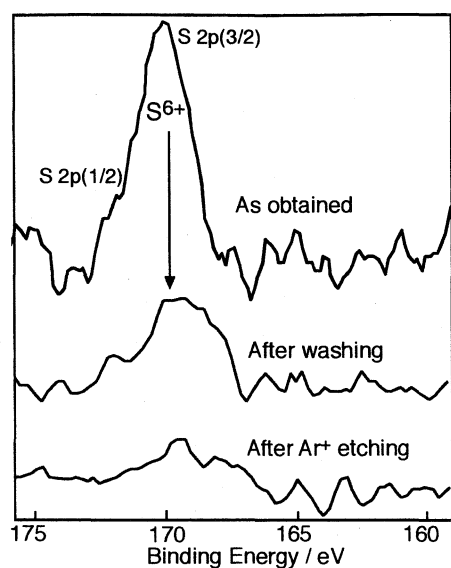


Figure 2. XPS spectra of S-doped TiO₂ powder (calcined at 500 °C).

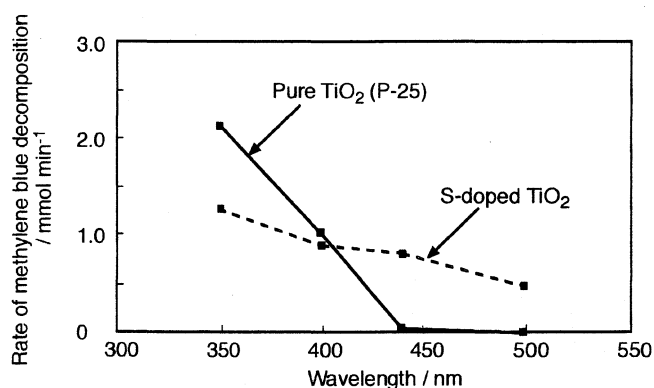


Figure 3. Photocatalytic decomposition of methylene blue using S-doped TiO₂ or pure TiO₂ as a function of the cutoff wavelength for irradiation from a 1000 W Xe lamp.

(50 mmol dm⁻³) in aqueous solution (5 mL) containing 100 mg of the TiO₂ photocatalyst. As the photocatalyst S-doped TiO₂ or pure TiO₂ powder (Degussa, P-25) was used. As the light source a 1000 W Xe lamp was used, and the short-wavelength components of the light was removed using cutoff glass filters with different cutoff wavelengths. Under UV irradiation, the activity of S-doped TiO₂ was a little lower than that of pure TiO₂. However, under irradiation at wavelengths longer than 440 nm, only S-doped TiO₂ showed the activity. Figure 3 shows the activities of S-doped TiO₂ (calcined at 500 °C for 3 h) and pure TiO₂ (Degussa, P-25), as a function of the cutoff wavelengths of the glass filters. In addition, no degradation of methylene blue was observed in the absence of TiO₂ powders or without irradiation.

It is of importance that we obtained a new class of TiO₂ powder which shows photocatalytic activity under visible light. We expect that the activity will be much improved by optimizing the preparing conditions of the S-doped TiO₂ powders.

References

1. A. Fujishima and K. Honda, *Nature*, **238**, 5551 (1972).
2. M. R. Hoffman, S. T. Martin, W. Choi, and D. W. Bahnemann, *Chem. Rev.*, **95**, 69 (1995).
3. L. Cao, F. Spiess, A. Huang, S. L. Suib, T. N. Obee, S. O. Hay, and J. D. Freihaut, *J. Phys. Chem.*, **103**, 2912 (1999).
4. D. S. Muggli and J. L. Falconer, *J. Catal.*, **187**, 230 (1999).
5. E. J. Wolfrum, J. Huang, D. M. Blake, P. C. Maness, Z. Huang, J. Fiest, and W. A. Jacoby, *Environ. Sci. Technol.*, **36**, 3412 (2002).
6. J. Theurich, D. W. Bahnemann, R. Vogel, F. E. Dhamed, G. Alhakimi, and I. Rajab, *Res. Chem. Intermed.*, **23**, 247 (1997).
7. S. Yanagida, Y. Ishimaru, Y. Miyake, T. Shiragami, C. Pac, K. Hashimoto, and T. Sakata, *J. Phys. Chem.*, **93**, 2576 (1989).
8. B. Ohtani, J. Kawaguchi, M. Kozawa, S. Nishimoto, and T. Inui, *J. Chem. Soc., Faraday Trans.*, **91**, 1103 (1995).
9. T. Ohno, T. Kigoshi, K. Nakabeya, and M. Matsumura, *Chem. Lett.*, **1998**, 877.
10. T. Ohno, K. Nakabeya, and M. Matsumura, *J. Catal.*, **176**, 76 (1998).
11. F. Soana, M. Sturini, L. Cermenati, and A. Albini, *J. Chem. Soc., Perkin Trans. 2*, **2000**, 699.
12. R. W. Matthews, *J. Chem. Soc., Faraday Trans. 1*, **80**, 457 (1984).
13. M. Fujihira, Y. Satoh, and T. Osa, *Nature*, **293**, 206 (1981).
14. M. Dusi, C. A. Muller, T. Mallat, and A. Baiker, *Chem. Commun.*, **1999**, 197.
15. E. Baciocchi, C. Rol, G. V. Sevastiani, and L. Taglieri, *J. Org. Chem.*, **59**, 5272 (1994).
16. E. Baciocchi, T. D. Giacco, M. I. Ferrero, C. Rol, and G. V. Sevastiani, *J. Org. Chem.*, **62**, 4015 (1997).
17. T. Ohno, K. Tokieda, S. Higashida, and M. Matsumura, *Appl. Catal.*, **A**, **6462**, 1 (2003).
18. T. Ohno, F. Tanigawa, K. Fujihira, S. Izumi, and M. Matsumura, *J. Photochem. Photobiol.*, **A**, **127**, 107 (1999).
19. M. Anpo, *Catal. Surv. Jpn.*, **1**, 169 (1997).
20. T. Ohno, Y. Masaki, S. Hirayama, and M. Matsumura, *J. Catal.*, **204**, 163 (2001).
21. S. Ikeda, C. Abe, T. Torimoto, and B. Ohtani, *Electrochemistry*, **70**, 442 (2002).
22. R. Asahi, T. Morikawa, T. Ohwaki, K. Aoki, and Y. Taga, *Science*, **293**, 269 (2001).
23. T. Umebayashi, T. Yamaki, H. Ito, and K. Asai, *Appl. Phys. Lett.*, **81**, 454 (2002).