



UNIVERSITI PUTRA MALAYSIA

***PRODUCTION AND CHARACTERIZATION OF COLLAGEN AND GELATIN
FROM EDIBLE JELLYFISH (*Acromitus hardenbergi* Stiasny, 1934) FOR
FABRICATION OF BIOFUNCTIONAL SCAFFOLD***

NICHOLAS KHONG MUN HOE

IB 2014 12



**PRODUCTION AND CHARACTERIZATION OF COLLAGEN AND
GELATIN FROM EDIBLE JELLYFISH (*Acromitus hardenbergi* Stiasny, 1934)
FOR FABRICATION OF BIOFUNCTIONAL SCAFFOLD**

By

NICHOLAS KHONG MUN HOE

**Thesis Submitted to the School of Graduate Studies, Universiti Putra Malaysia,
in Fulfilment of the Requirements for the Degree of Doctor of Philosophy**

December 2014

All material contained within the thesis, including without limitation text, logos, icons, photographs and all other artwork, is copyright material of Universiti Putra Malaysia unless otherwise stated. Use may be made of any material contained within the thesis for non-commercial purposes from the copyright holder. Commercial use of material may only be made with the express, prior, written permission of Universiti Putra Malaysia.

Copyright © Universiti Putra Malaysia



DEDICATIONS

To those whom I love dearly, and

To those who love me selflessly.

To those that finds competition in me, nonetheless.

To you, especially,

who is reading this,

May this little piece illustrates you some marvels of knowledge,

May it brings you joy of explorations,

May it brings you hope and inspirations.

Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfilment of the requirement for the degree of Doctor of Philosophy

PRODUCTION AND CHARACTERIZATION OF COLLAGEN AND GELATIN FROM EDIBLE JELLYFISH (*Acromitus hardenbergi* Stiasny, 1934) FOR FABRICATION OF BIOFUNCTIONAL SCAFFOLD

By

NICHOLAS KHONG MUN HOE

December 2014

Chair: Fatimah Md. Yusoff, PhD

Institute: Bioscience

Jellyfish have always been an important fishery commodity and a multi-million business widely practised in China, Japan, Malaysia, Indonesia, Thailand, Vietnam and the Philippines. This study aimed to explore food and nutritional properties of indigenous jellyfishes; which contributes to the development of simple and efficient extraction procedures of jellyfish collagen and gelatin that would be practical in the production of biomedical-significant matrices for potential tissue engineering applications. It was found that edible jellyfishes were food of low calorific value (ranged from 1.0 to 4.9 kcal/g dry weight) and high protein (ranged from 20.0 to 53.9 g/ 100g dry weight) and minerals (total ash ranged from 15.9 to 57.2 g/ 100g dry weight) components. Collagen was estimated to comprise approximately half the total protein content of edible jellyfishes, hence the major protein component of edible jellyfishes. Among the jellyfishes, *A. hardenbergi* exhibited significantly ($p < 0.05$) better protein quality (higher total amino acids and collagen content) and richer in major minerals compared to other two species. Subsequently, two novel procedures were devised for efficient collagen and gelatin extraction from *A. hardenbergi*. It was found that this improved process significantly increased the production yield ($p < 0.05$) by approximately seven times and two times compared to the conventional acid-assisted and pepsin-assisted extraction, respectively. Proximate composition and amino acids profile of collagen extracted using the improved process was found to be similar ($p > 0.05$) to those extracted using the pepsin-assisted extraction. However, the collagen produced by the improved process retained high molecular weight distributions and polypeptide profiles similar to the conventional acid-assisted extraction. They possessed better appearance, instrumental colour and were found to be non-toxic *in vitro* and free of heavy metal contaminations. Findings from comparisons between the novel and the conventional procedures illustrated that different treatments of collagen extraction process imparts significant impacts to the quality, quantity and cost of the collagen produced. The study also managed to extract gelatin successfully from jellyfish tissues with satisfactory yield, gelling (Bloom) and sensory properties. Jellyfish gelatin has high protein content (>80%) with low moisture (<2.5%), ash (<2.0%) and negligible fat contents. All gelatins had very mild to undetectable fishy odour and were all whitish in appearance. Jellyfish collagen and gelatin were then used to fabricate porous scaffolds suitable for tissue engineering application by freeze-drying the mixture with different proportions of chitosan solutions. The addition of jellyfish gelatin into

the scaffold formulation, to partially substitute collagen, was able to reduce the production cost while improving functional characteristics of the scaffolds. The combinations of different jellyfish collagen and gelatin concentrations were observed to have significant effects on the cross-section morphology and the molecular integrity of the cross-linked scaffolds. Proportional combination of jellyfish collagen into the ternary scaffolds was found to significantly ($p < 0.05$) increase mean pore size and porosity. All ternary scaffolds exhibited mean pore size in the range of 200-300 μm and porosity above 90%. These results suggested that the chitosan: jellyfish-derived collagen and gelatin tripolymer matrix is a potential candidate for soft tissues equivalent with enhanced biostability and good biocompatibility. Overall, the findings of this study supported that jellyfish is potentially practical as a sustainable source of high quality collagen and gelatin. Jellyfish-derived biomaterials were also found to exhibit good biophysicofunctionality in the fabrication of scaffolds for tissue engineering. Scaffolds, fabricated in the current study is but a beginning for more forms of functional matrices such as hydrogel, sol, liquid, concentrate and powder.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia sebagai memenuhi keperluan untuk ijazah Doktor Falsafah

**PENGHASILAN DAN PENCIRIAN KOLAGEN DAN GELATIN DARIPADA
UBUR-UBUR (*Acromitus hardenbergi* Stiasny, 1934) UNTUK FABRIKASI
PERANCAH BIOFUNGSIAN**

Oleh

NICHOLAS KHONG MUN HOE

Disember 2014

Pengerusi: Fatimah Md. Yusoff, PhD

Fakulti: Biosains

Ubur-ubur merupakan komoditi perikanan yang penting dan pemakanannya diamalkan secara meluas di China, Jepun, Malaysia, Indonesia, Thailand, Vietnam dan Filipina. Kajian ini bertujuan untuk menerokai ciri-ciri makanan dan nutrisi ubur-ubur tempatan dan membangun prosedur cekap pengekstrakan kolagen dan gelatin yang akan menyumbang kepada pembuatan matriks bioperubatan untuk aplikasi kejuruteraan tisu. Hasil pengajian menunjukkan bahawa ubur-ubur ialah makanan berkalori rendah (antara 1.0 – 4.9 kcal/g berat kering) yang kaya dengan protein (antara 20.0 - 53.9 g/100g berat kering) dan mineral (jumlah abu antara 15.9 – 57.2 g/100 g berat kering). Kira-kira separuh daripada jumlah kandungan protein ubur-ubur dianggarkan terdiri daripada kolagen. Antara ubur-ubur yang dikaji, *A. hardenbergi* menunjukkan jumlah asid amino, kandungan kolagen dan mineral yang lebih tinggi berbanding spesies yang lain, dengan ketara ($p < 0.05$). Selepas itu, dua prosedur baru telah berjaya dicipta untuk penghasilan kolagen dan gelatin yang efisien daripada *A. hardenbergi*. Proses pengekstrakan kolagen baru mampu meningkatkan hasil pengeluaran dengan ketara ($p < 0.05$), kira-kira tujuh kali dan dua kali ganda berbanding dengan kaedah pengekstrakan konvensional yang menggunakan asid dan enzim (pepsin), masing-masing. Komposisi proksimat dan asid amino kolagen yang diekstrak menggunakan proses baru adalah seakan kolagen yang diekstrak dengan bantuan pepsin ($p > 0.05$). Pada masa yang sama, kolagen yang diekstrak dengan kaedah baru mengekalkan profil pengagihan berat molekul polipeptida seakan kolagen yang diekstrak dengan kaedah asid konvensional ($p > 0.05$). Kolagen tersebut mempunyai penampilan dan warna yang lebih baik dan didapati bebas daripada pencemaran logam berat serta toksik *in vitro*. Perbandingan antara kaedah baru dan konvensional menunjukkan bahawa rawatan yang berbeza semasa proses pengekstrakan kolagen memberi kesan yang ketara kepada kualiti, kuantiti dan kos kolagen yang dihasilkan. Kajian ini juga berjaya merumuskan kaedah penghasilan gelatin daripada tisu ubur-ubur yang mempunyai ciri gel (Bloom) dan sensori yang memuaskan. Gelatin ubur-ubur mempunyai kandungan protein yang tinggi (> 80%), air (<2.5%), abu (<2.0%) dan kandungan lemak (>0.1%) yang rendah. Gelatin yang terhasil mempunyai bau hanyir ikan yang sangat ringan dan mempunyai penampilan putih salji. Kolagen dan gelatin ubur-ubur kemudiannya digunakan untuk mereka perancah berliang yang sesuai untuk aplikasi kejuruteraan tisu dengan kaedah pengeringan beku campuran kolagen-gelatin dengan peredaran yang berbeza dengan kitosan. Penambahan gelatin ubur-ubur ke dalam formulasi

perancah, sebagai pengganti kolagen dalam nisbah terpilih, dapat mengurangkan kos pengeluaran sambil meningkatkan ciri-ciri fungsian perancah. Kombinasi nisbah kolagen dan gelatin ubur-ubur yang berbeza didapati mempunyai kesan yang ketara ($p > 0.05$) ke atas keratan rentas morfologi dan integriti molekul perancah. Turut diperhatikan adalah peningkatan saiz liang dan keliangan perancah yang ketara ($p < 0.05$) hasil penambahan kolagen ubur-ubur. Semua perancah mempamerkan saiz purata liang dalam julat 200-300 μm dan keliangan melebihi 90%. Keputusan ini mencadangkan bahawa kolagen dan gelatin ubur-ubur mampu menambahbaik perancah perubatan kitosan dan merupakan calon yang berpotensi untuk penggantian tisu manusia seperti kulit, tulang dan hati. Secara keseluruhannya, hasil kajian ini menyokong usul potensi ubur-ubur sebagai sumber lestari kolagen dan gelatin yang berkualiti tinggi dan praktikal. Biopolimer yang diperolehi daripada ubur-ubur juga mempamerkan ciri-ciri fizikal dan fungsian yang baik dalam pembuatan perancah untuk aplikasi kejuruteraan tisu. Kolagen dan gelatin terhasil daripada kajian ini mampu berfungsi baik dalam pelbagai bentuk termasuk bentuk serbuk, matriks, hidrogel, sol mahupun cecair.

ACKNOWLEDGEMENTS

"We can only appreciate the miracle of a sunrise if we have waited in the darkness."
Many thanks to whoever and whatever that have showed me kindness, patience and guidance throughout this roller-coaster ride. No words can express, no act of gratitude can relay and no gift can represent what your love and support have meant to me. Please accept this note as an indicator of my heartfelt appreciation for everything you are.

First and foremost, to my family: my mother Mdm. Chan Ooi Yee; my grandmothers Mdm. Chan King Chen and Mdm. Wong Swee Lan; my sisters Elaine and Evon; brother Eric, and uncle Foong Kin Tuck, many thanks for the unconditional love and understanding. For those you do not understand, you trust me nevertheless. This, I will be forever grateful.

My sincerest gratitude to my supervisors, Prof. Dr. Fatimah Md. Yusoff, Prof. Dr. Jamilah Bakar, Prof. Dr. Mahiran Basri and Prof. Dr. Maznah Ismail, for plenty of what I am today is born from your kindness and tolerance. Words cannot express all that I wish to say to you. The difference you make is nothing short of legendary.

To my mentor, Chan Kim Wei, my beloved brother concurrently, friend like you are a rare gift. Many thanks for all you have done for me. Your love and support will always be remembered, fondly in good times, and as encouragement in bad. Dearest Lai Wee Ting, thanks for everything and for being there. You are a gem to my life. I cannot imagine the world without you. I only know it would be a much different, much less comforting place.

To my sponsor, Khazanah Foundation (Yayasan Khazanah) and all dedicated people within. For your trust and expectations, maintaining steps ahead has gradually become my apparel. Thank you for all the memorable moments, the timely trainings and the generous encouragements you have provided me. Special thanks to my scholarship managers: Pn. Sariza Ibrahim, Pn. Salawati Awang and Pn. Raja Nordianna Raja Harun. My live has never been the same, ever, with all of you.

To truly appreciate life, we seek companionship. To those that share my enthusiasms, Siti Balqis Abdul Razak, Foo Su Chern, Yau Sook Kun, Dora Lai, Nur Leena Wong and Che Azuranim. My IFTSA Developing Solutions for Developing Countries (DSDC) team, Prof. Dr. Lai Oi Ming, Lim Sue Shan, Lau Kah Yan, Hee Yen Yi and Sim Biow Ing; and my housemates, Khoo Li Teng and Liew Sien Yei. I appreciate the fights and quarrels but I especially treasure the kind words you spoke and the memorable challenges we cruised along. Thank you for accompany.

To those in the lab, Mr. Perumal Kuppan, Dr. Sanjoy, Dr. Helena, Farhan, Hasina, Suhayati, Adibah, KB, Tahhir, Kak Ita, Kak Farah, Nur Arifa, Aini, Shu Chee, Rozhin, Roazita, Umi Hartina, Sharmila, Fizah, Nana, Nia, Sarega, DJ, Jhi Biau, Hadiza, Umar, Aisyah, Nisah, Kak Siti, Kak Yat and Kak Norsha. I just wanted to let you know—the things you do for me do not go unnoticed. You're a necessary piece to this puzzle. I appreciate your dedication and service, and I know others, among us, do too.

I have had the privilege to be helped by too many good people. You know who you are. To those seen or unseen, recalled perhaps later or forgotten nonetheless, you have bent over backwards for me. I will try my best to repay all of your kindness by means of reflecting them upon others just like how I like them to be done on myself. This ride has never been smooth but at the end of it all, I am glad I had it with you.

Thank you.



I certify that a Thesis Examination Committee has met on 22 December 2014 to conduct the final examination of Nicholas Khong Mun Hoe on his thesis entitled “Production and Characterization of Collagen and Gelatin from Edible Jellyfish (*Acromitus hardenbergi* Stiasny, 1934) for Fabrication of Biofunctional Scaffold” in accordance with the Universities and University Colleges Act 1971 and the Constitution of the Universiti Putra Malaysia [P.U.(A) 106] 15 March 1998. The Committee recommends that the student be awarded the degree of Doctor of Philosophy.

Members of the Thesis Examination Committee were as follows:

Md. Zuki bin Abu Bakar @ Zakaria, PhD

Professor
Faculty of Veterinary Medicine
Universiti Putra Malaysia
(Chairman)

Aziz bin Arshad, PhD

Professor
Faculty of Agriculture
Universiti Putra Malaysia
(Internal Examiner)

Suhaila binti Mohamed, PhD

Professor
Institute of Bioscience
Universiti Putra Malaysia
(Internal Examiner)

Marco Nemesio E. Montaña, PhD

Professor
The Marine Science Institute,
College of Science,
University of the Philippines Diliman,
Philippines
(External Examiner)



ZULKARNAIN ZAINAL, PhD

Professor and Deputy Dean
School of Graduate Studies
Universiti Putra Malaysia

Date: 12 March 2015

This thesis was submitted to the Senate of Universiti Putra Malaysia and has been accepted as fulfillment of the requirement for the degree of Doctor of Philosophy. The members of the Supervisory Committee were as follows:

Fatimah Md. Yusoff, PhD

Professor
Institute of Bioscience
Universiti Putra Malaysia
(Chairman)

Jamilah Bakar, PhD

Professor
Faculty of Food Science and Technology
Universiti Putra Malaysia
(Member)

Mahiran Basri, PhD

Professor
Faculty of Science
Universiti Putra Malaysia
(Member)

Maznah Ismail, PhD

Professor
Faculty of Medicine and Health Sciences
Universiti Putra Malaysia
(Member)

BUJANG KIM HUAT, PhD

Professor and Dean
School of Graduate Studies
Universiti Putra Malaysia

Date:

Declaration by Graduate Student

I hereby confirm that:

- this thesis is my original work;
- quotations, illustrations and citations have been duly referenced;
- this thesis has not been submitted previously or concurrently for any other degree at any other institutions;
- intellectual property from the thesis and copyright of thesis are fully-owned by Universiti Putra Malaysia, as according to the Universiti Putra Malaysia (Research) Rules 2012;
- written permission must be obtained from supervisor and the office of Deputy Vice-Chancellor (Research and Innovation) before thesis is published (in the form of written, printed or in electronic form) including books, journals, modules, proceedings, popular writings, seminar papers, manuscripts, posters, reports, lecture notes, learning modules or any other materials as stated in the Universiti Putra Malaysia (Research) Rules 2012;
- there is no plagiarism or data falsification/fabrication in the thesis, and scholarly integrity is upheld as according to the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) and the Universiti Putra Malaysia (Research) Rules 2012. The thesis has undergone plagiarism detection software.

Signature : _____

Date : _____

Name and Matric No.: Nicholas Khong Mun Hoe (GS25864)

Declaration by Members of Supervisory Committee

This is to confirm that:

- the research conducted and the writing of this thesis was under our supervision;
- supervision responsibilities as stated in the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) are adhered to.

Signature : _____ Signature : _____
Name of Chairman of Supervisory Committee : Fatimah Md. Yusoff Name of Member of Supervisory Committee : Jamilah Bakar

Signature : _____ Signature : _____
Name of Member of Supervisory Committee : Mahiran Basri Name of Member of Supervisory Committee : Maznah Ismail

TABLE OF CONTENTS

	Page
ABSTRACT	i
ABSTRAK	iii
ACKNOWLEDGEMENTS	v
APPROVAL	vii
DECLARATION	ix
LIST OF TABLES	xv
LIST OF FIGURES	xvi
LIST OF ABBREVIATIONS	xx
CHAPTER	
1	
INTRODUCTION	1
1.1 Background of the study	1
1.2 Problem statements	4
1.3 Hypotheses	5
1.4 Objectives	6
2	
LITERATURE REVIEW	7
2.1 Jellyfish (Cnidaria: Scyphozoa)	7
2.1.1 Biology and anatomy	9
2.1.2 Abundance and implications	11
2.2 Edible jellyfish	15
2.2.1 Fisheries and processing	15
2.2.2 Current utilization and profusion	18
2.3 Potentials of jellyfish in the development of novel actives	19
2.4 Jellyfish as source of natural protein hydrocolloids	19
2.4.1 Collagen and collagen hydrolysates from jellyfish	21
2.4.2 Gelatin and gelatin hydrolysates from jellyfish	26
2.5 Scaffolds for tissue engineering purposes	28
2.5.1 Collagen scaffolds for tissue engineering	28
2.5.2 Jellyfish collagen for the development of biomedical scaffolds and sponges	29
3	
GENERAL METHODS	31
3.1 Jellyfishes	31
3.1.1 Sampling	31
3.1.2 Morphological characteristics of <i>Acromitus hardenbergi</i>	32
3.2 Preparation of collagen samples	34

3.2.1	Collagen powder	34
3.2.2	Collagen solution	34
3.3	Determination of extraction yield	34
3.4	Proximate analysis (AOAC, 2005)	34
3.4.1	Determination of total moisture content	34
3.4.2	Determination of total ash content	34
3.4.3	Determination of total protein content	35
3.4.4	Determination of total lipid content	35
3.4.5	Determination of total carbohydrate content	36
3.5	Gross energy	36
3.6	Determination of pH	36
3.7	Isoelectric point, pI	36
3.8	Colour analysis	36
3.9	Physical appearance and odour	37
3.10	Gel strength	37
3.11	Determination of molecular weight	37
3.12	Amino acids composition	38
3.12.1	Acid digestion	38
3.12.2	Phenylisothiocyanate precolumn derivatization	39
3.12.3	HPLC-DAD analysis	39
3.13	Attenuated Total Reflectance Fourier Transform Infrared Spectroscopy (ATR-FTIR)	39
3.14	UV-Vis Spectroscopy	39
3.15	Differential Scanning Calorimetry (DSC)	40
3.16	X-Ray Diffraction (XRD) analysis	40
3.17	Elemental analysis	40
3.18	Scanning Electron Microscopy (SEM)	40
3.18.1	Ultrastructural analysis	40
3.18.2	Mean pore diameter	41
3.19	Porosity and density	41
3.20	Cytotoxicity <i>in vitro</i>	41
3.20.1	Cells and materials	41
3.20.2	MTT colourimetric assay	42
3.20.3	LDH release assay	42
3.20.4	Morphological observations	42
3.21	Statistical analyses	43

4	NUTRITIONAL COMPOSITION AND TOTAL COLLAGEN CONTENT OF COMMERCIALY IMPORTANT EDIBLE JELLYFISHES OF MALAYSIA	45
4.1	Introduction	45
4.2	Materials and methods	46

4.3	Results and discussion	47
4.3.1	Nutritional composition and physical characteristics	47
4.3.2	Energy density	48
4.3.3	Amino acid profile	50
4.3.4	Total hydroxyproline and collagen content	53
4.3.5	Elemental analysis	55
4.4	Conclusion	58
5	PHYSICOCHEMICAL AND CYTOTOXIC EVALUATION OF COLLAGEN FROM THE EDIBLE JELLYFISH, <i>Acromitus hardenbergi</i> Stiasny, 1934, USING AN IMPROVED PHYSICAL-AIDED ACID ASSISTED EXTRACTION	59
5.1	Introduction	59
5.2	Materials and methods	60
5.3	Results and discussion	63
5.3.1	Yield	63
5.3.2	Proximate composition and physical properties	65
5.3.3	Amino acid composition	68
5.3.4	Molecular weight distribution	71
5.3.5	Cytotoxic and allergenic possibility of jellyfish collagen	72
5.3.6	Elemental content	79
5.4	Conclusion	80
6	IMPACTS OF EXTRACTION PROCESSES ON THE SECONDARY STRUCTURES AND BIOPHYSICAL CHARACTERISTICS OF THE COLLAGEN PRODUCED FROM THE EDIBLE JELLYFISH, <i>Acromitus hardenbergi</i> Stiasny, 1934	81
6.1	Introduction	81
6.2	Materials and methods	83
6.3	Results and discussion	83
6.3.1	UV-Vis spectroscopy	83
6.3.2	Molecular order	85
6.3.3	X-Ray diffraction (XRD)	88
6.3.4	Differential scanning calorimetry (DSC)	89
6.3.5	Particle size	90
6.4	Conclusion	93

7	EXTRACTION AND CHARACTERIZATION OF GELATIN FROM THE EDIBLE JELLYFISH, <i>Acromitus hardenbergi</i> Stiasny, 1934	95
7.1	Introduction	95
7.2	Materials and methods	96
7.3	Results and discussion	99
7.3.1	Extraction recovery	99
7.3.2	Proximate composition	101
7.3.3	Gel strength	101
7.3.4	Physical characteristics	102
7.3.5	Amino acids composition	106
7.3.6	ATR-FTIR analysis	109
7.3.7	Ultrastructural study	111
7.4	Conclusion	113
8	JELLYFISH-DERIVED COLLAGEN AND GELATIN IMPROVED ARCHITECTURAL EDIFICE AND MOLECULAR ORDER OF TERNARY MULTIPURPOSE CHITOSAN HYBRID SCAFFOLD	115
8.1	Introduction	115
8.2	Materials and methods	117
8.3	Results and discussion	117
8.3.1	Mean pore size	117
8.3.2	Porosity and density	120
8.3.3	Thermodynamic properties	121
8.3.4	Molecular order	123
8.3.5	Ultrastructural morphology	125
8.4	Conclusions	128
9	SUMMARY, CONCLUSION AND RECOMMENDATIONS FOR FUTURE RESEARCH	129
	REFERENCES	131
	APPENDICES	142
	BIODATA OF STUDENT	151
	LIST OF PUBLICATIONS	153

LIST OF TABLES

Table		Page
1	Global occurrence of jellyfish blooms and their socioeconomic implications.	12
2	Edible jellyfishes harvested in different locations of the world.	16
3	Comparison between native collagen and collagen hydrolysates.	23
4	Collagen extracted from different types of jellyfishes.	25
5	Jellyfish collagen hydrolysates and their bioactivities.	27
6	Characteristics of an ideal scaffold for tissue engineering purposes.	28
7	Weight range used in accordance to protein content of sample.	35
8	Materials for the preparation of 12.5% resolving gels.	38
9	Materials for the preparation of stacking gels.	38
10	Proximate composition (g/100g) and gross energy content of bell and oral arms from different edible jellyfishes.	49
11	Proximate composition, pH, pI and appearance of collagen from jellyfish (<i>Acromitus hardenbergi</i>).	67
12	Fourier transform infrared (FTIR) peak locations for various jellyfishes and aquatic collagens.	87
13	Thermal properties of jellyfish collagens as affected by various treatments.	91
14	Extraction yield (g/100g) of gelatin from jellyfish extracted using two different methods at different temperatures.	100
15	Physicochemical properties of gelatin from jellyfish extracted using two different methods at different temperatures.	104
16	Sensory attributes of of gelatin from jellyfish extracted using two different methods at different temperatures.	105
17	Amino acid composition (number of residues/1000 residues) of gelatins from jellyfish extracted using two different methods at different temperatures.	108
18	The porosity and apparent density of composite scaffolds.	120

LIST OF FIGURES

Figure		Page
1	Edible jellyfishes fished in the waters of Malaysia. (A) <i>Rhopilema esculentum</i> ; (B) <i>Rhopilema hispidum</i> ; (C) <i>Lobonema smithii</i> ; and (D) <i>Acromitus hardenbergi</i> .	2
2	Simple pictorial order classification of Scyphozoa and their examples.	8
3	Morphological structures of a simple scyphozoan medusa.	9
4	Global production of all jellyfish species in thousand tonnes from 1950 to 2009, as reported by the FAO.	15
5	Ready-to-eat cured jellyfish processed using large amount of salt, alum and soda, available in Malaysia. (A) <i>Rhopilema esculentum</i> ; (B) <i>Rhopilema hispidum</i> ; (C) <i>Lobonema smithii</i> ; and (D) <i>Acromitus hardenbergi</i> .	18
6	Potential jellyfish derivatives for drug discovery and the development of novel functional food, cosmetics and pharmaceuticals.	20
7	Structure of collagen and their classification based on average molecular weight. Native collagen is hydrolysed by heating or enzymes to produce gelatin or collagen hydrolysates depending on the degree of hydrolysis.	21
8	Location of jellyfish fishery grounds where jellyfishes were sampled and collected in Peninsular Malaysia.	31
9	<i>Acromitus hardenbergi</i> Stiasny. A. Whole body in lateral view, B. Rhopalar lappets and a sensory pit, in exumbrellar view, C. Schematic drawing of anastomosing canal system of subumbrella.	32
10	<i>Acromitus hardenbergi</i> Stiasny. A. Gross structure, B. Stained canal system. Species identification was conducted by examining the canal system, stained by methylene blue.	33
11	Amino acids composition (mg/g dry weight) of the bells of various edible jellyfishes. Error bars represent SDs. Groups with different letters (a–c) are significant, (One-way ANOVA followed by Tukey <i>post hoc</i> test, $p < 0.05$, $n = 3$).	51

12	Amino acids composition (mg/g dry weight) of the oral arms of various edible jellyfishes. Error bars represent SDs. Groups with different letters (a–c) are significant, (One-way ANOVA followed by Tukey <i>post hoc</i> test, $p < 0.05$, $n = 3$).	52
13	Estimated total collagen content (g/100g dry weight). Error bars represent SDs. Groups with different letters (a–c) are significant, (One-way ANOVA followed by Tukey <i>post hoc</i> test, $p < 0.05$, $n = 3$).	54
14	Estimated proportion of collagen to total protein content (g/100g) of various body parts of different jellyfishes. Error bars represent SDs. Groups with different letters (a–c) are significant, (One-way ANOVA followed by Tukey <i>post hoc</i> test, $p < 0.05$, $n = 3$).	54
15	Elemental EDX microanalysis (Weight%) of the bells of various edible jellyfishes. Values ≤ 1 Weight% were considered trace. Error bars represent SDs. Groups with different letters (a–c) are significant, (One-way ANOVA followed by Tukey <i>post hoc</i> test, $p < 0.05$, $n = 3$).	56
16	Elemental EDX microanalysis (Weight%) of the oral arms of various edible jellyfishes. Values ≤ 1 Weight% were considered trace. Error bars represent SDs. Groups with different letters (a–c) are significant, (One-way ANOVA followed by Tukey <i>post hoc</i> test, $p < 0.05$, $n = 3$).	57
17	Comparison of different collagen extraction processes. (A) Conventional acid-assisted extraction, (B) Conventional pepsin-assisted extraction, (C) Improved acid-assisted extraction.	62
18	Yield of collagen extraction by different extraction procedures in terms of (A) wet weight basis, (B) dry weight basis, and (C) protein basis. Error bars represent SDs. Groups with different letters (a–c) are significant, (One-way ANOVA followed by Tukey <i>post hoc</i> test, $p < 0.05$, $n = 3$).	64
19	Variation of amino acids composition of collagen extracted from the bell of <i>A. hardenbergi</i> using two conventional methods as compared to the improved extraction process. Error bars represent SDs. Groups with different letters (a–c) are significant, (One-way ANOVA followed by Tukey <i>post hoc</i> test, $p < 0.05$, $n = 3$).	69
20	Variation of amino acids composition of collagen extracted from the oral arms of <i>A. hardenbergi</i> using two conventional methods as compared to the improved extraction process. Error bars represent SDs. Groups with different letters (a–c) are significant, (One-way ANOVA followed by Tukey <i>post hoc</i> test, $p < 0.05$, $n = 3$).	70

21	SDS-polyacrylamide gel electrophoresis of extracted collagens and wide range protein molecular weight markers. Lane 1: Acid-soluble collagen from jellyfish bell, Lane 2: Acid-soluble collagen from jellyfish oral arms, Lane 3: Pepsin-soluble collagen from jellyfish bell, Lane 4: Pepsin-soluble collagen from jellyfish oral arms, Lane 5: Improved acid-soluble collagen from jellyfish bell, Lane 6: Improved acid-soluble collagen from jellyfish oral arms.	72
22	Cell viability (percentage) of skin cells upon 72 h exposure to various concentrations of collagen and its derivatives. Error bars represent SDs (n = 3). Higher percent cell viability denotes lesser toxicity <i>in vitro</i> .	73
23	LDH release (percentage) as affected by 72 h treatment of various concentrations of collagen and its derivatives. Error bars represent SDs (n = 3). Lower total LDH content denotes lesser toxicity <i>in vitro</i> and lower allergic potential.	74
24	Morphological changes of 3T3 cells treated with different types of collagen and gelatin at 125 µg/ mL concentration for 72 h viewed under an inverted light microscope (400× magnification). No decrease in cell population was noted in comparison with the control, blank and standard collagen treatment (far left column).	77
25	Morphological changes of 3T3 cells treated with different types of collagen and gelatin at 1000 µg/ mL concentration for 72 h viewed under an inverted light microscope (400× magnification). No decrease in cell population was noted in comparison with the control, blank and standard collagen treatment (far left column).	78
26	Major elements found in the collagen from the jellyfish bell extracted using various methods. Data are represented as the mean ± SD (one-way ANOVA, followed by Tukey <i>posthoc</i> test). Values with different letters (a–c) are significant, $p < 0.05$; n = 3.	79
27	Major elements found in the collagen from the jellyfish oral arms extracted using various methods. Data are represented as the mean ± SD (one-way ANOVA, followed by Tukey <i>posthoc</i> test). Values with different letters (a–c) are significant, $p < 0.05$; n = 3.	80
28	UV-Vis analysis of collagens extracted using various processes.	83
29	ATR-FTIR spectra of collagen extracted using different procedures.	86
30	Effects of different extractive procedures onto X-ray diffraction (XRD) pattern of various collagens extracted.	88

31	Particle size distribution of jellyfish collagen extracted using different procedures. A: Acid-soluble collagen from jellyfish bell, B: Acid-soluble collagen from jellyfish oral arms, C: Pepsin-soluble collagen from jellyfish bell, D: Pepsin-soluble collagen from jellyfish oral arms, E: Improved acid-soluble collagen from jellyfish bell, F: Improved acid-soluble collagen from jellyfish oral arms.	92
32	Schematic representation of different approaches used in the acidic gelatin extraction from jellyfish.	98
33	ATR-FTIR spectra of gelatins from jellyfish extracted using different methods at different temperatures.	110
34	Ultrastructural morphology of jellyfish gelatins extracted using different methods at different temperatures.	112
35	Mean pore size (diameter) of various combinations of jellyfish-derived collagen-gelatin/chitosan scaffolds. Error bars represent SDs. Horizontal distance (length) of boxplots represents data distributions (Interquartile range, IQR). Means that do not share a letter (a–c) are significantly different, $p < 0.05$; $n = 20$ (One-way ANOVA followed by Tukey <i>post hoc</i> test).	119
36	Thermodynamic study of jellyfish-derived collagen-gelatin/chitosan scaffolds (cross-sectional plane) with different composition of collagen: gelatin: chitosan: (a) 0:10:0, (b) 0:0:10, (c) 0:5:5, (d) 1:4:5, (e) 2:3:5, (f) 3:2:5, (g) 4:1:5, (h) 5:0:5, (i) 10:0:0.	122
37	ATR-FTIR spectra of various jellyfish-derived collagen-gelatin/chitosan scaffolds.	124
38	Scanning electron micrographs of jellyfish-derived collagen-gelatin/chitosan scaffolds (cross-sectional plane) with different composition of collagen: gelatin: chitosan: (a) 0:5:5, (b) 1:4:5, (c) 2:3:5, (d) 3:2:5, (e) 4:1:5, (f) 5:0:5, (g) 10:0:0, (h) 0:10:0 and (i) 0:0:10.	127

LIST OF ABBREVIATIONS

&	and
×g	gravitation force
°C	degree Celcius
µg	microgram
µL	microliter
µm	micrometer
AB	acid solubilized collagen from the bell of jellyfish
ANOVA	analysis of variance
AOA	acid solubilized collagen from the oral arms of jellyfish
ASC	acid soluble collagen
ca.	approximately; <i>circa</i>
cm	centimeter
e.g.	for example; <i>exempli gratia</i>
et al.	and others; <i>et alii</i>
etc	and other things; <i>et cetera</i>
g	gram
h	hour
HCl	hydrochloric acid
i.e.	that is; <i>id est</i>
IB	improved acid solubilized collagen from the bell of jellyfish
IOA	improved acid solubilized collagen from the oral arms of jellyfish
kDa	kilo Dalton
L	liter
M	mole
mg	milligram
min	minutes
mL	milliliter
mm	millimeter
MW	molecular weight
N	normality
NaOH	sodium hydroxide
PB	pepsin solubilized collagen from the bell of jellyfish
pI	isoelectric point
POA	pepsin solubilized collagen from the oral arms of jellyfish
PSC	pepsin soluble collagen
SD	standard deviation
SEM	scanning electron microscopy
v/v	volume (mL) per volume (mL)
v/w	volume (mL) per weight (g)
w/v	weight (g) per volume (mL)
w/w	weight (g) per weight (g)



© COP YRIGHT UPM

CHAPTER 1

INTRODUCTION

1.1 Background of the study

Jellyfishes, to the public, would always be associated to poisonous stinging nuisance that normally blooms in polluted waters, something which is not necessarily true. However, the fact that the blooms of jellyfishes are rapidly increasing is undeniable. Richardson et al. (2009) and Purcell et al. (2007) stressed that environmental changes (climate change and habitat modification) as well as anthropogenic developments (eutrophication, overfishing, translocation and reclamations) which took place rapidly nowadays, are among factors promoting jellyfish blooms to the disadvantage of other marine organisms. Damages inflicted by jellyfish blooms are increasingly experienced worldwide (Uye, 2008; Dong et al., 2010; Kim et al., 2012; Quinones et al., 2013). Among the negative impacts of jellyfish blooms includes diminished fishery production, malfunctionings of coastal energy plants; fatal consequences of envenomations and reduction of tourism and eco-activities. In Malaysia, Sim & Khairun (2008) reported the concerns of the public and the state government of Penang with the overflowing numbers of jellyfish now found in Penang waters that negatively affect the beach activities of the coastal areas. To address this issue which is steadily haunting the nation, the project intends to make use of these jellyfishes to produce *halal* and diseases-free value added biomaterial where none in Malaysia has been done so far.

Aside deadly venomous jellyfishes, some jellyfishes are edible and have long been served as delicacies in the world especially the Asian countries. Jellyfish fisheries is one of the oldest capture fisheries practised widely especially in Southeast Asia (Yusoff et al., 2010; Nishikawa et al., 2009). However, jellyfish fishery in Malaysia receives very little attention, regardless in scientific researches or socio-economical development, although Chinese all over the world are enjoying jellyfish as food and fine gourmet. Malaysia is one of the major exporters of jellyfish to Japan, Korea and China, which contributes to a multi-million dollars business in Southeast Asia. About three decades ago, trades of jellyfish commodities from Southeast Asia to Japan valued at about US\$25.5 million (Omori and Nakano, 2001). There are generally four edible species of jellyfish commercially available in Malaysia which are better known i.e. obor merah (*Rhopilema esculentum*), obor pasir (*Rhopilema hispidum*) and lambuh air (*Acromitus hardenbergi*), and lambuh cendol (*Lobonema smithii*) (Figure 1). The river jellyfish, *Acromitus hardenbergi* could be found in abundance in the Perak estuary, Malaysia and is the only known source in the world where their occurrence is not restricted by any periods of time. Known only as the river type for a very long time, scientific descriptions and taxonomic confirmation of this species of jellyfish have only been published recently (Kitamura & Omori, 2010). The fishery of *Acromitus hardenbergi* in the Perak River, Malaysia has been carried out continually for no less than three generations. There is very little information and study on jellyfish in Malaysia even though its industry provides a very important source of revenue to the country. To the fishing community, jellyfish could be a good source of income given more efforts in studying the organism and potential benefits it could offer to the world.

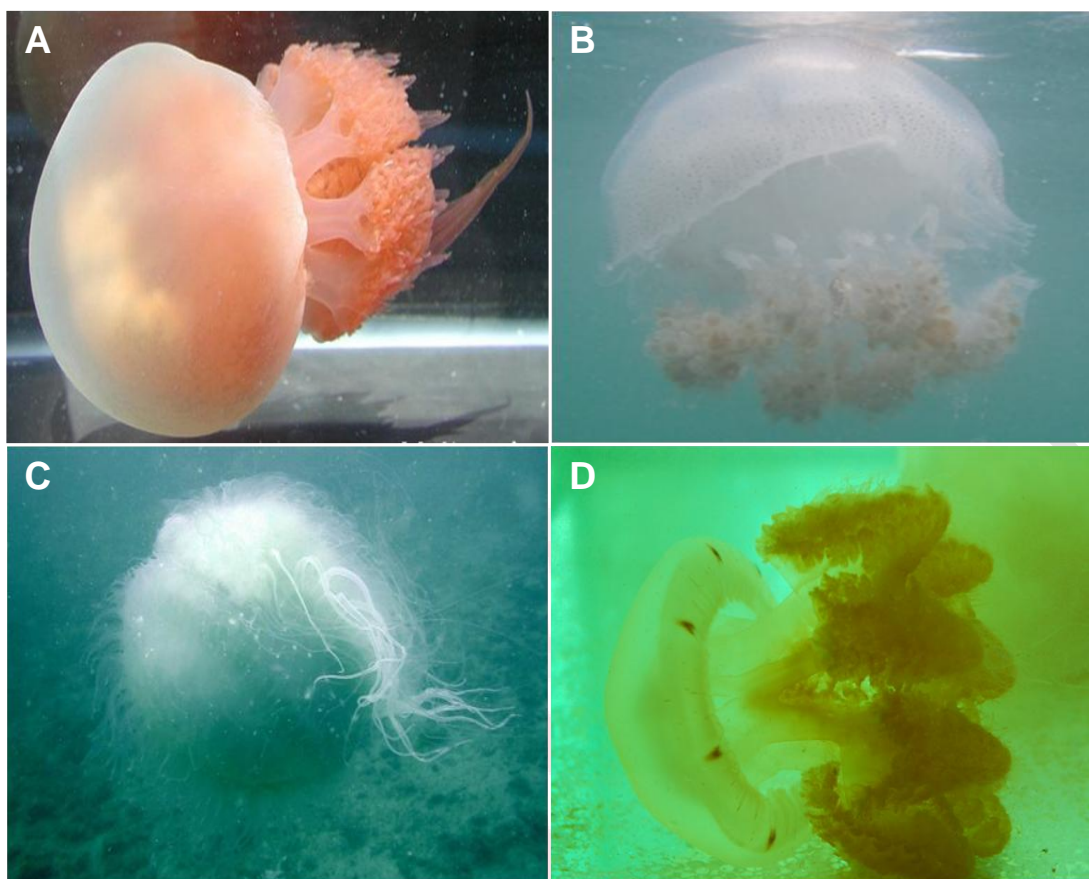


Figure 1. Edible jellyfishes fished in the waters of Malaysia. (A) *Rhopilema esculentum*; (B) *Rhopilema hispidum*; (C) *Lobonema smithii*; and (D) *Acromitus hardenbergi*.

Marine-derived biomolecules display arrays of functional activities, with compounds of lucrative economic importance having promising potentials of commercial and industrial relevances. Southeast Asia especially, is a mega diversified region in aquatic and marine bioresources. The phylum Cnidaria includes over 11,000 extant species of unique and unexplored marine invertebrates. Species from tropical waters, specially, poses great potentials as 84% of the most potent Cnidarian biomolecules where previously isolated from Cnidarians collected from tropical waters (mostly from Southeast Asia and the Caribbean Sea) as compared to occupying temperate waters (e.g., European countries and Japan) (Rocha et al., 2011).

Edible jellyfishes are a promising ingredient for the development of nutraceutical and functional food. It is highly believed that jellyfish is effective to improve the conditions of arthritis, hypertension, backpain and ulcers (Hsieh et al., 2001). Basic chemical categorizations of different jellyfishes are essential for initial screening, bioprospecting and comparative bioefficacy prior to any developments of lead, products or value-added compounds. Proximate values of jellyfishes are relatively scarce and non-standardized worldwide. Proximate analysis allows justifiable comparisons of ingredients on the basis of specific nutrients, allowing one to judge how much better one is than another, in standardized terms. Informations on the proximate components of various jellyfishes, and their processed products, would aid

in the development of regression equations to help predict nutritional performance of these food ingredients. In the more advance case, these proximate components could be utilised to predict performance-related factors e.g. bioavailability, digestibility and intake; that could be related to the development of novel products as well as the estimates of performance of these products. Many workers have presented on the potentials of jellyfishes as source of collagen (Barzansky et al., 1975; Kimura et al., 1983; Hsieh et al., 2001). However, similarly to proximate content, the comparison of total collagen content from different jellyfishes, especially commercially important ones, is yet to be performed.

Collagen exists in the skin, tendon, cartilage, blood vessels, bone and teeth of almost all vertebrates and recent researches have revealed that they are highly available in invertebrates as well. The degraded form of collagen is gelatin. The application of collagen stretches from making sausages in the food industry to delivering drugs in biomedical practices. It is most useful and convenient of collagen as compared to other biomaterials due to its well-defined structural, physical and biochemical properties as well as its biocompatibility and lack of allergenicity and toxicity. According to Foegeding et al. (2001), collagen exists in several polymorphic forms with collagen type I, III and V as the common ones while collagen type II and IV uncommon. Miura & Kimura (1985) found that the mesoglea of the jellyfish *Stomolophus nomurai* is composed of collagen chemically similar to vertebrate type V collagen. Meanwhile, Hsieh et al. (2005) isolated type II collagen from the jellyfish, *Stomolophus meleagris* which is capable of treating severe rheumatoid arthritis. Both experiments hinted that jellyfish could be a good source for rare and healthful collagen. Derivation of collagen from aquatic source is an exciting field with lots of enthusiasm from the world. However, the quality of collagen extracted is highly dependent upon its extraction process. Jamilah et al. (2010) have identified that many of the processing steps applied to mammalian collagen extraction are not directly applicable for the extraction of collagen from aquatic animals since the treatment may be harsh, or too strong for the matrix of aquatic animals. It would be highly desirable if a simplified extraction process which eliminates unnecessary extraction steps to increase yield and to reduce denaturation of the extracted collagen could be derived. Elimination of insignificant extraction steps could also save cost of chemicals and time. Therefore, it is necessary to comprehend the consequences of extraction conditions to achieve higher recovery of good quality collagen. Extraction of collagen from jellyfish has always been low yielding while extraction of gelatin from jellyfish has never been reported successful previously.

1.2 Problem statements

Malaysia is one of the countries where the activities of jellyfish fisheries were most active worldwide. Yet, the amount of research performed on jellyfish as a source of sustainable resources is scarce. The exotic nature of this organism stirred numerous claims and rumours behind their near miraculous efficacy in the treating Acquired Immune Deficiency Syndrome (AIDS), infertility and other chronic illnesses. Meanwhile, local fishermen have been attributing the cure of joint problems and prevention of aging, fatigue to the consumption of jellyfish. Proper experimentations are necessary for the verification and solid discovery of pro-health claims and medical leads from these indigenous jellyfish which is easily available.

Fundamental understanding on the chemical constituents of jellyfish is obligatory as the basis of nutritional and biotechnological exploitations. Earlier, jellyfishes have been reported to contain substantial amount of collagen, antioxidants, bioactive peptides and terpenoids (Hsieh et al., 2001, Rocha et al., 2011). However, the production yields of those bioactive compounds are poorly reported. Moreover, none have performed comparisons between different jellyfishes, especially edible ones, on their proximate compositions, nutritional contents and total bioactive contents. Chemical variations between different edible jellyfishes, if any, would provide significant insights into their potential utilizations and developments, and thus should be categorised standardizingly among other seafoods. Nonetheless, identification of jellyfish with noteworthy amount of highly-demanded compounds such as collagen and antioxidants would be a practical approach to create value from this underutilized fishery resource.

Collagen and its degraded counterpart gelatin are valuable biofunctional ingredients in many industries especially of food, nutricosmetics, nutraceutical, cosmeceutical, pharmaceutical and medical relevances. Unfortunately, collagen and gelatin available in the market nowadays are either from porcine sources which possess significant limitations by religious dilemmas or bovine sources which equally suffer religious constraints as well as threat of deadly transmissible diseases such as bovine spongiform encephalopathy (BSE) and transmissible spongiform encephalopathy (TSE). Constant fluctuations of raw materials availability and market price led to numerous adulterations as well as fraudulent products that cause severe financial loss and health detriments to the unknowing public. Bioprospection of sustainable alternative collagen source would be vital to satisfy the increasing demand for collagen to the future. Hence, it would be most favourable if the highly demanded collagen could be extracted from the highly unwanted mass of jellyfish. The current study proposed to utilize jellyfish as a source for rare, *halal/kosher* and high quality collagen and gelatin.

Although collagen has been extracted from jellyfishes previously, their yield is pitifully low and impractical for industrial up scaling. In efforts to increase the yield of collagen extraction from jellyfishes, costly protease enzymes are commonly utilised. However, lack of standardizations in the use of enzymes produces collagens of variable quality due to under- or over- enzymatic cleavages of the protein.

Moreover, the most common protease used is pepsin which is from porcine gastric mucosa and thus, again brought forth religious limitations. Others utilise hazardous and potentially lethal chemicals and irradiation to increase the yield of collagen extraction. It would be much profitable and consumer friendly given a simpler and green procedure could be devised for rapid and efficient extraction of collagen from jellyfish. Successful extraction of gelatin from jellyfish has yet to be reported so far.

Jellyfish blooms are steadily increasing from year to year due to rapid anthropogenic activities. For now, jellyfish blooms are already very much a nuisance to the fishermen, breaking nets and greatly reduce fish catch. Given the intensity of human developments, it would be most unlikely that the volume of jellyfish blooms would be shrinking at all. The removal of jellyfish is a no longer a matter of choice and it maybe a compulsory routines in coastal areas especially those with ports, industrial facilities, and power plants. Thereupon, it would be beneficial to derive something useful out these nuisances which may present the food, cosmetics and pharmaceutical industries with interesting new additives. Studies delving onto pro-health utilizations would also manifest prosperous and expensive products (outcomes) which would eventually compensate for the costly management of jellyfishes from the environment and upgrade the lifestyle of downtown community of poor jellyfish fishermen.

1.3 Hypothesis

Based on the problem statements above, it is hypothesized that:

- 1.3.1 Jellyfishes possess significant nutritional properties which pose potentials as functional food and different jellyfishes would exhibit different proximate content and nutritional properties.
- 1.3.2 Collagen could be extracted more effectively and efficiently by slight modification of the existing procedures.
- 1.3.3 Different extraction processes influenced the quality of jellyfish collagen produced. Functional properties of collagens will be different amongst those extracted using physical assisted processes and chemical (enzyme) assisted processes.
- 1.3.4 Gelatin of good sensory properties and high Bloom strength could be extracted from jellyfish.
- 1.3.5 Jellyfish collagen and gelatin possess the superior quality required to be applied as biomedical devices.

1.4 Objectives

The study embarked on the general aim to develop value-added biomaterials from indigenous underutilized edible jellyfish for biomedical applications. Specifically, the objective of the study involved:

- 1.4.1 To evaluate the nutritional quality and nutraceutical potentials of indigenous commercially available edible jellyfishes;
- 1.4.2 To assess effective processes for the production of high quality collagen with high yield from jellyfish tissues;
- 1.4.3 To characterize the physiochemical and biophysical properties of jellyfish collagen as affected by different extraction processes;
- 1.4.4 To develop effective processes for the extraction of highly functional jellyfish gelatin from jellyfish tissues and their physiochemical characterizations.
- 1.4.5 To fabricate and characterize jellyfish-derived scaffolds suitable for biomedical applications.

REFERENCES

- Addad, S., Exposito, J.Y., Faye, C., Ricard-Blum, S. & Lethias, C. (2011) Isolation, Characterization and Biological Evaluation of Jellyfish Collagen for Use in Biomedical Applications. *Mar. Drugs* 9(6): 967-983.
- Aewsiri, T., Benjakul, S. & Visessanguan, W. (2009) Functional properties of gelatin from cuttlefish (*Sepia pharaonis*) skin as affected by bleaching using hydrogen peroxide. *Food Chem.* 115: 243-249.
- AOAC (1990) Official method of analysis of AOAC International. Washington D.C., USA: Association of Official Analytical Chemists.
- Arai, M.N. (1997) A Functional Biology of Scyphozoa. London: Chapman & Hall. 316p.
- Armania, N., Yazan, L.S., Musa, S.N., Ismail, I.S., Foo, J.B., Chan, K.W., Noreen, H., Hisyam, A.H., Zulfahmi, S. & Ismail, M. (2013) *Dillenia suffruticosa* exhibited antioxidant and cytotoxic activity through induction of apoptosis and G₂/M cell cycle arrest. *J. Ethnopharmacol.* 146: 525–535.
- Balti, R., Jridi, M., Sila, A., Souissi, N., Nedjar-Arroume, N., Guillochon, D. & Nasri, M. (2011) Extraction and functional properties of gelatin from the skin of cuttlefish (*Sepia officinalis*) using smooth hound crude acid protease-aided process. *Food Hydrocolloids* 25: 943-950.
- Barzansky, B., Lenhoff, H. M. & Bode, H. (1975) *Hydra* mesoglea: similarity of its amino acid and neutral sugar composition to that of vertebrate basal lamina. *Comp. Biochem. Physiol.* 50B: 419-424.
- Barzideh, Z., Latiff, A.A., Gan, C.-Y., Benjakul, S. & Abd Karim, A. (2013) Isolation and characterization of collagen from the ribbon jellyfish (*Chrysaora* sp.). *Int. J. Food Sci. Technol.* doi: 10.1111/ijfs.12464.
- BBC (2007, Nov) Jellyfish attack destroys salmon. *BBC News*. Accessed online 19 April 2014. <http://news.bbc.co.uk/>.
- Bermueller, C., Schwarz, S., Elsaesser, A.F., Sewing, J., Baur, N., von Bomhard A., Scheithauer, M., Notbohm, H. & Rotter, N. (2013) Marine collagen scaffolds for nasal cartilage repair: prevention of nasal septal perforations in a new orthotopic rat model using tissue engineering techniques. *Tissue Eng.* 19: 1–14.
- Bornstein, P. & Sage, H. (1980) Structurally distinct collagen types. *Ann. Rev. Biochem.* 49: 957-1003.
- Brodeur, R.D. (1998) In situ observations of the associations of juvenile fishes and scyphomedusae in the eastern Bering Sea. *Mar. Ecol. Prog. Ser.* 163: 11-20.
- Brodeur, R.D., Sugisaki, H. & Hunt Jr, G.L. (2002) Increases in jellyfish biomass in the Bering Sea: implications for the ecosystem. *Mar. Ecol. Prog. Ser.* 233: 89-103.
- Brotz, L. (2011) Are jellyfish the food of the future? *INFOFISH Int.* 4: 60-63.

- Brotz, L., Cheung, W.W.L., Kleisner, K., Pakhomov, E. & Pauly, D. (2012) Increasing jellyfish populations: trends in Large Marine Ecosystems. *Hydrobiologia* 690: 3-20.
- Chan, J. K. (2007) The effects of particle size of collagen and mold material on the pore structure of freeze-dried collagen-GAG scaffolds. Degree Dissertation, Massachusetts Institute of Technology.
- Cheow, C.S., Norizah, M.S., Kyaw, Z.Y. & Howell, N.K. (2007) Preparation and characterization of gelatins from the skins sin croaker (*Johnius dussumieri*) and shortfin scad (*Decapterus macrosoma*). *Food Chem.* 101: 386-391.
- Chidambaram, L. (1984) Export oriented processing of Indian jellyfish (*Muttai chori*, TAMIL) by Indonesian method at Pondicherry region. *Mar. Fish. Infor. Serv.* 60: 11–13.
- Cole, C.G.B. (2000) Gelatin In Frederick J. Francis (ed.), *Encyclopedia of Food Science and Technology*, 2nd edition (pp. 1183-1188). New York: John Wiley & Sons.
- Condon, R.H., Duarte, C.M., Pitt, K.A., Robinson, K.L., Lucas, C.H., Sutherland, K.R., Mianzan, H.W., Bogeberg, M., Purcell, J.E., Decker, M.B., Uye, S., Madin, L.P., Brodeur, R.D., Haddock, S.H.D., Malej, A., Parry, G.D., Eriksen, E., Quiñones, J., Acha, M., Harvey, M., Arthur, J.M. & Graham, W.M. (2013) Recurrent jellyfish blooms are a consequence of global oscillations. *PNAS* 110: 1000–1005.
- Condon, R.H., Graham, W.M., Duarte, C.M., Pitt, K.A., Lucas, C.H., Haddock, S.H.D., Sutherland, K.R., Robinson, K.L., Dawson, M.N., Decker, M.B., Mills, C.E., Purcell, J.E., Malei, A., Mianzan, H., Uye, S., Gelcich, S & Madin, L.P. (2012) Questioning the Rise of Gelatinous Zooplankton in the World's Oceans. *BioScience* 62: 160-169.
- DeFelice, S.L. (1993) A comparison of the U.S., European and Japanese nutraceutical health and medical claim rules. *Regulatory Affairs* 5: 163-168.
- Ding, J.F., Li, Y.Y., Xu, J.J., Su, X.R., Gao, X. & Yue, F.P. (2011) Study on effect of jellyfish collagen hydrolysate on anti-fatigue and anti-oxidation. *Food Hydrocolloids* 25: 1350-1353.
- Dong, Z., Liu, D. & Keesing, J.K. (2010) Jellyfish blooms in China: Dominant species, causes and consequences. *Marine Pollution Bulletin* 60(7): 954–963.
- Doyle, T.K., Houghton, J.D.R., Mcdevitt, R., Davenport, J. & Hays, G.C. (2007) The energy density of jellyfish: estimates from bomb-calorimetry and proximate-composition. *J. Exp. Mar. Biol. Ecol.* 343, 239-252.
- Eysturskarð, J., Haug, I.J., Elharfaoui, N., Djabourov, M. & Draget, K.I. (2009) Structural and mechanical properties of fish gelatin as a function of extraction conditions. *Food Hydrocolloids* 23: 1702-1711.

- Fan, J., Zhuang, Y. & Li, B. (2013) Effects of Collagen and Collagen Hydrolysate from Jellyfish Umbrella on Histological and Immunity Changes of Mice Photoaging. *Nutrients* 5(1): 223–233.
- FAO (2003) Food energy - methods of analysis and conversion factors. FAO Food and Nutrition Paper 77. Report of a Technical Workshop, Rome, 3-6 December 2002.
- Faruqi, S., Wilmot, R., Wright, C. & Morice, A.H. (2012) Serum LDH in chronic cough: a potential marker of airway inflammation. *The Clinical Respiratory Journal* 6: 81–87.
- Foegeding, E. A., Lanier, T. C. & Hultin, H. O. (1996) Characteristics of edible muscle tissue. In O.R. Fennema (Ed.), *Food Chemistry* (3rd ed.), pp. 902-906. New York: Marcel Dekker, Inc.
- Gershwin, L.A., Nardi, M.D., Winkel, K.D. & Fenner, P.J. (2010) Marine stingers: review of an under-recognised global coastal management issue. *Coastal Management* 38: 22-41.
- Giraud-Guille, M.M. (1992) Liquid crystallinity in condensed type I collagen solutions: A clue to the packing of collagen in extracellular matrices. *J. Mol. Biol.* 224: 861-873.
- GME (2005, June). Standard method for the testing of edible gelatin. Gelatin Monograph Version 4. Gelatin Manufactures of Europe (GME).
- Gómez-Guillén, M. C., Sarabia, A. I., & Montero, P. (2000). The effect of added salts on the viscoelastic properties of fish skin gelatins. *Food Chem.* 70: 71-76.
- Graham, W.M., Martin, D.L., Felder, D.L., Asper, V.L. & Perry, H.M. (2003) Ecological and economic implications of a tropical jellyfish invader in the Gulf of Mexico. *Biological Invasions* 5: 53-69.
- Greaser, M.L. (2009) Proteins. In L.M.L. Nollet, & F. Toldra (Eds.), *Handbook of Muscle Foods Analysis* (pp. 57-73). USA: CRC Press.
- Green, N.P.O., Stout, G.W. & Taylor, D.J. (1995) *Biological Science 1: Organism, Energy and Environment* 2nd edition. R. Soper (Ed). Great Britain: Cambridge University Press. 480 pp.
- Grossman, S. & Bergman, M. (1992) Process for the production of gelatin from fish skin. *United States Patent No.* 5093474.
- Gudmundsson, M. & Hafsteinsson, H. (1997) Gelatin from cod skins as affected by chemical treatments. *J. Food Sci.* 62: 37–39.
- Herman, S. (2013, Dec) Cosmetics and the Chemistry of Life. GCI Magazine. Assessed 4 April 2014 from <http://www.gcimagazine.com/>.
- Hoyer, B., Bernhardt, A., Lode, A., Heinemann, S., Sewing, J., Klinger, M., Notbohm, H. & Gelinsky, M. (2014) Jellyfish collagen scaffolds for cartilage tissue engineering. *Acta Biomaterialia* 10: 883-892.

- Hsieh, Y-H.P. (2005) Use of jellyfish collagen (Type II) in the treatment of rheumatoid arthritis. United States Patent No. US 6,894,029 B1.
- Hsieh, Y-H.P., Leong, P.M. & Rudloe, J. (2001) Jellyfish as food. *Hydrobiologia* 451: 11-17.
- Ignat'eva, N. Yu., Danilov, N.A., Averkiev, S.V., Obrezkova, M.V., Lunin, V.V. & Sobol, E.N. (2007) Determination of hydroxyproline in tissues and the evaluation of the the collagen content of the tissues. *J. Anal. Chem.* 62: 51-57.
- Isobe, T., Kato, Y., Okubo, Y. & Koga, M. (2001) Evaluation of patch testing in atopic dermatitis using commercially available environmental antigens. *Allergol Int.* 50: 153-162.
- Jabs, Andreas (2014) Determination of Secondary Structure in Proteins by Fourier Transform Infrared Spectroscopy (FTIR). Jena Library of Biological Macromolecules assessed online: http://jenalib.fli-leibniz.de/ImgLibDoc/ftir/IMAGE_FTIR.html on 1 June 2014.
- Jamilah, B. & Harvinder, K.G. (2002) Properties of gelatins from skins of fish - black tilapia (*Oreochromis mossambicus*) and red tilapia (*Oreochromis nilotica*). *Food Chem.* 77: 81-84.
- Jamilah, B., Tan, K.W., Umi Hartina, M.R. and Azizah, A. (2011). Gelatins from three cultured freshwater fish skins obtained by liming process. *Food Hydrocolloids* 25: 1256-1260.
- Jamilah, B., Umi Hartina, M.R., Mat Hashim, D. & Sazili, A.Q. (2013) Properties of collagen from barramundi (*Lates calcarifer*) skin. *Int. Food Res. J.* 20: 835-842.
- Jamilah, B., Umi Hartina, R., Mat, M.H.D., Qurni, S.A. & Kaur, H. (2010) Collagen extraction from aquatic animals. Patent WO 2010074552 A1.
- Jeffrey, J. (1995) Metalloproteinases and tissue turnover. *WOUNDS* 7(Suppl A):13A-22A.
- Jeong, S.I., Kim, S.Y., Cho, S.K., Chong, M.S., Kim, K.S., Kim, H., Lee, S.B. & Lee, Y.M. (2007) Tissue-engineered vascular grafts composed of marine collagen and PLGA fibers using pulsatile perfusion bioreactors. *Biomaterials* 28(6): 1115-1122.
- Kawahara, M., Uye, S., Ohtsu, K., Iizumi, H. (2006) Unusual population explosion of the giant jellyfish *Nemopilema nomurai* (Scyphozoa: Rhizostomeae) in East Asian waters. *Mar. Ecol. Prog. Ser.* 307: 161-173.
- Keogh, M.B., O' Brien, F.J. & Daly, J.S. (2010) A novel collagen scaffold supports human osteogenesis--applications for bone tissue engineering. *Cell Tissue Res.* 340: 169-177.
- Kim, D.H., Seo, J.N., Yoon, W.D. & Suh, Y.S. (2012) Estimating the economic damage caused by jellyfish to fisheries in Korea. *Fish Sci.* 78: 1147-1152.
- Kimura, S., Miura, S. & Park, Y.H. (1983) Collagen as the major edible component of jellyfish (*Stomolophus nomurai*). *J. Food Sci.* 48: 1758-1760.

- Kitamura, M. & Omori, M. (2010) Synopsis of edible jellyfishes collected from Southeast Asia, with notes on jellyfish fisheries. *Plankton Benthos Res.* 5: 106-118.
- Kittiphattanabawon, P., Benjakul, S., Visessanguan, W., Nagai, T. & Tanaka, M. (2005) Characterization of acid soluble collagen from the skin and bone of bigeye snapper (*Priacanthus tayenus*). *Food Chem.* 89, 363-372.
- Kligman, A.M. (2005) Cosmeceuticals: A broad spectrum category between cosmetics and drugs. In Peter Elsner & Howards I. Maibach. (eds), *Cosmeceuticals and Active Cosmetics: Drug Versus Cosmetics 2nd Edition*. Taylor & Francis Group, USA.
- Kliment, C.R., Englert, J.M., Crum, L.P. & Oury, T.D. (2011) A novel method for accurate collagen and biochemical assessment of pulmonary tissue utilizing one animal. *Int. J. Clin. Exp. Pathol.* 4(4): 349-355.
- Kondo, Y., Ohtsuka, S., Nishikawa, J., Metillo, E., Pagliawan, H., Sawamoto, S., Moriya, M., Nishida, S. & Urata, M. (2014) Associations of fish juveniles with rhizostome jellyfishes in the Philippines, with taxonomic remarks on a commercially harvested species in Carigara Bay, Leyte Island. *Plankton Benthos Res.* 9: 51-56.
- Kramp, P.L. (1961) Synopsis of the Medusae of the World. *Journal of the Marine Biological Association of the United Kingdom*, 40. 469p.
- Krishnan, S. & Perumal, P. (2013) Preparation and Biomedical Characterization of Jellyfish (*Chrysaora quinquecirrha*) Collagen from Southeast Coast of India. *Int. J. Pharm. Pharm. Sci.* 5(3): 698-701.
- Kwon, J. & Kwon, O. (2010) Benefit-cost analysis of eliminating the jellyfish by the natural predator in Korean coastal waters. *APEC Youth Scientist Journal* 3: 76-90.
- Lee, S.J., Kim, S.Y. & Lee, Y.M. (2007) Preparation of porous collagen/hyaluronic acid hybrid scaffolds for biomimetic functionalization through biochemical binding affinity. *J. Biomed. Mater. Res. B.* 82: 506-518.
- Li, H., Liu, B.L., Gao, L.Z. & Chen, H.L. (2004) Studies on bullfrog skin collagen. *Food Chem* 84: 65–69.
- Li, S.T. (2000) Biologic biomaterials: Tissue-derived biomaterials (Collagen) In *The biomedical engineering handbook 2nd edition* (ed) Joseph D. Bronzino. Boca Raton: CRC Press LLC.
- Lin, Y.K. & Liu, D.C. (2006) Comparison of physical–chemical properties of type I collagen from different species. *Food Chem* 99: 244–251.
- Liu, X., Zhang, M., Zhang, C. & Liu, C. (2012) Angiotensin converting enzyme (ACE) inhibitory, antihypertensive and antihyperlipidaemic activities of protein hydrolysates from *Rhopilema esculentum*. *Food Chem.*, DOI: <http://dx.doi.org/10.1016/j.foodchem.2012.04.023>.

- Lynam, C.P., Gibbons, M.J., Axelsen, B.E., Sparks, C.A.J., Coetzee, J., Heywood, B.G. & Brierley, A.S. (2006) Jellyfish overtake fish in a heavily fished ecosystem. *Current Biology* 16(13): R492-493.
- Manickavasagam, B. (2008) Extraction of gelatin. US Patent US2008/0167447 A1.
- Matusiewicz, S.P., Williamson, I.J., Sime, P.J., Brown, P.H., Wenham, P.R., Crompton, G.K. & Greening, A.P. (1993) Plasma lactate dehydrogenase: a marker of disease activity in cryptogenic fibrosing alveolitis and extrinsic allergic alveolitis? *Eur. Respir. J.* 6: 1282-1286.
- Mayer, A.G. (1910) Medusae of the world, Hydromedusae and Scyphomedusae. Carnegie Institute Washington, Publication 109(3): 735p.
- Mazorra-Manzano, M.A., Torres-Llanez, M.J., Gonzalez-Cordova, A.F. & Vallejo-Cordoba, B. (2012) A capillary electrophoresis method for the determination of hydroxyproline as a collagen content index in meat products. *Food Anal. Methods* 5, 464-470.
- Miura, S. & Kimura, S. (1985) Jellyfish mesogloea collagen: characterization of molecules as $\alpha 1\alpha 2\alpha 3$ heterotrimers. *J. Biol. Chem.* 260(28): 15352-15356.
- Morais, Z.B., Pintão, A.M., Costa, I.M., Calejo, M.T., Bandarra, N.M. & Abreu, P. (2009) Composition and in vitro antioxidant effects of jellyfish *Catostylus tagi* from Sado Estuary (SW Portugal). *J. Aquatic Food Prod. Technol.* 18, 90-107.
- Morishige, H., Sugahara, T., Nishimoto, S., Muranaka, A., Ohno, F., Shiraishi, R. & Doi, M. (2011) Immunostimulatory effects of collagen from jellyfish *in vivo*. *Cytotechnology* 63(5): 481-492.
- Muhammed, F. & Sultana, R. (2007) New records of edible jellyfish, *Rhizostoma pulmo* (Cnidaria: Scyphozoa: Rhizostomidae) from Pakistani waters. *JMBA2 – Biodiversity Records*. Published online.
- Mujiono, N. (2010) Jellyfish (*Crambionella* sp.) fisheries around Cilacap waters, Central Java (Cnidaria: Scyphozoa). *Oceanologi & Limnologi di Indonesia* 36(1): 37-48.
- Muyonga, J.H., Cole, C.G.B. & Duodu, K.G. (2004) Extraction and physico-chemical characterisation of Nile perch (*Lates niloticus*) skin and bone gelatin. *Food Hydrocolloids* 18: 581-592.
- Nagai, T., Ogawa, T., Nakamura, T., Ito, T., Nakagawa, H., Fujiki, K., Nakao, M. & Yano, T. (1999) Collagen of edible jellyfish exumbrella. *J Sci. Food Agric.* 79: 855-858.
- Nagai, T., Worawattanamateekul, W., Suzuki, N., Nakamura, T., Ito, T., Kazuhiro, F., Nakao, M. & Yano, T. (2000) Isolation and characterization of collagen from rhizostomous jellyfish (*Rhopilema asamushi*). *Food Chem.* 70: 205-208.
- Nagarajan, M., Benjakul, S., Prodpran, T., Songtipya, P. & Kishimura, H. (2012) Characteristics and functional properties of gelatin from splendid squid (*Loligo formosana*) skin as affected by extraction temperatures. *Food Hydrocolloids* 29: 389-397.

- Nishikawa, J., Thu, N.T., Ha, T.M. & Thu, P.T. (2008) Jellyfish fisheries in northern Vietnam. *Plankton Benthos Res.* 3: 227-234.
- Nishikawa, J., Thu, N.T., Yusoff, F.M., Lindsay, D.J., Mulyadi, Mujiono, N., Ohtsuka, S. & Nishida, S. (2009) Jellyfish fisheries in Southeast Asia, with special reference to those in Vietnam, Indonesia and Malaysia (*in Japanese*). *Kaiyo Monthly*, 41: 401-411.
- Nomura, Y., Toki, S., Ishii, Y. & Shirai, K. (2000) Improvement of the material property of shark Type I collagen by composing with pig Type I collagen. *J. Agric. Food Chem.* 48: 6332-6336.
- Ohtsuka, S., Koike, K., Lindsay, D., Nishikawa, J., Miyake, H., Kawahara, M., Mulyadi, Mujiono, N., Hiromi, J. & Komatsu, H. (2009) Symbionts of marine medusa and ctenophores. *Plankton Benthos Res.* 4: 1-13.
- Ohtsuka, S., Kondo, Y., Sakai, Y., Shimazu, T., Shinomura, M., Komai, T., Yanagi, K., Fujita, T., Nishikawa, J., Miyake, H., Venmathi Maran, B.A., Go, A., Nagaguchi, K., Yamaguchi, S., Dechsakulwatana, C., Srinui, K., Putchakarn, S., Mulyadi, Mujiono, N., Sutomo & Yusoff, F.M. (2010) In-situ observations of symbionts on medusa occurring in Japan, Thailand, Indonesia and Malaysia. *Bulletin of the Hiroshima University Museum* 2: 9-18.
- Omori, M. & Nakano, E. (2001) Jellyfish fisheries in Southeast Asia. *Hydrobiologia* 451: 19-26.
- Ovchinnikova, T.V., Balandin, S.V., Aleshina, G.M., Tagaev, A.A., Leonova, Y.F., Krasnodembsky, E.D., Men'shenin, A.V. & Kokryakov, V.N. (2006) Aurelin, a novel antimicrobial peptide from jellyfish *Aurelia aurita* with structural features of defensins and channel-blocking toxins. *Biochem. Biophys. Res. Comm.* 348: 514-523.
- Park, J.S., Choi, J.B., Jo, S.Y., Lim, Y.M., Gwon, H.J., Khil, M.S. & Nho, Y.C. (2012) Characterization and structure analysis of PLGA/collagen nanofibrous membranes by electrospinning. *J. Appl. Polym. Sci.* 125: E595-E603.
- Parks, W.C. (1995) The production, role, and regulation of matrix metalloproteinases in the healing epidermis. *WOUNDS* 7(Suppl A): 23-37.
- Peng, L., Cheng, X. R., Wang, J. W., Xu, D. X., & Wang, G. E. (2006). Preparation and evaluation of porous chitosan/collagen scaffolds for periodontal tissue engineering. *J. Bioact. Compat. Polym.* 21: 207-220.
- Peng, Y., Glattauer, V., Werkmeister, J.A. & Ramshaw, J.A.M. (2004) Evaluation of collagen products for cosmetic application. *J. Cosmet. Sci.* 55: 327-341.
- Perera, L. (2008, Sept.) Jellyfish exports need checking: Environmentalists warn of consequences of over-exploitation of a natural resource. *The Sunday Times*. Accessed online 14 April 2014. <http://www.sundaytimes.lk/>.
- Perez-Ruzafa, A., Gilabert, J., Gutierrez, J.M., Fernandez, A.I., Marcos, C. & Sabah, S. (2002) Evidence of a planktonic food web response to changes in nutrient

- input dynamics in the Mar Menor coastal lagoon, Spain. *Hydrobiologia* 475/476: 359–369.
- Pew Research Center (2012, Dec) The Global Religious Landscape: A Report on the Size and Distribution of the World's Major Religious Groups as of 2010. The Pew Forum on Religion & Public Life. 81p.
- Pierce, J. (2005) A system for mass culture of Upside-down jellyfish *Cassiopea* spp. as a potential food item for medusivores in captivity. *Int. Zoo Yb.* 39: 62-69.
- Pitt, K.A. & Kingsford, M.J. (2003) Temporal variation in the virgin biomass of the edible jellyfish, *Catostylus mosaicus* (Scyphozoa, Rhizostomeae). *Fisheries Res.* 63(3): 303-313.
- Purcell, J.E., Uye, S. & Lo, W. (2007) Anthropogenic causes of jellyfish blooms and their direct consequences for humans: a review. *Mar. Ecol. Prog. Ser.* 350: 153-174.
- Putra, A.B.N., Morishige, H., Nishimoto, S., Nishi, K., Shiraishi, R., Doi, M. & Sugahara, T. (2012) Effect of collagens from jellyfish and bovine Achilles tendon on the activity of J774.1 and mouse peritoneal macrophage cells. *J. Functional Foods* 4: 504-512.
- Quinones, J., Monroy, A., Acha, E.M. & Mianzan, H. (2013) Jellyfish bycatch diminishes profit in an anchovy fishery off Peru. *Fisheries Res.* 139: 47-50.
- Raskoff, K.A., Sommer, F.A., Hamner, W.M. & Cross, K.M. (2003) Collection and culture techniques for gelatinous zooplankton. *Biol. Bull.*, 204, 68-80.
- Rault, I., Frei, V., Herbage, D., Abdul-Malak, N & Huc, A. (1996) Evaluation of different chemical methods for cross-linking collagen gel, films and sponges. *J. Mater. Sci. Mater. Med.* 7: 215–221.
- Richardson, A.J., Bakun, A., Hays, G.C. & Gibbons, M.J. (2009) The jellyfish joyride: causes, consequences and management responses to a more gelatinous future. *Trends in Ecology and Evolution* 24(6): 312-322.
- Riisgard, H.U., Anderson, P. & Hoffmann, E. (2012) From fish to jellyfish in the eutrophicated Limfjorden (Denmark). *Estuaries and Coasts* 35: 701-713.
- Rocha, J., Peixe, L., Gomes, N.C.M. & Calado, R. (2011) Cnidarians as source of new marine bioactive compounds – an overview of the last decade and future steps for bioprospecting. *Mar. Drugs* 9: 1860-1886.
- Ruiz-Capillas, C., Moral, A., Morales, J. & Montero, P. (2003) Characterization and functionality of frozen muscle protein in volador (*Illex coindetii*), pota (*Todaropsis eblanae*), and octopus (*Eledone cirrhosa*). *J. Food Sci.* 68(7), 2164-2168.
- Rumpet, R. (1991) Some aspects of the biology and fishery of jellyfish found along the coast of Sarawak, Malaysia. Fishery Development Report No. 164, Department of Fisheries: Ministry of Agriculture, Malaysia.

- Ruppert, E. E. & Barnes, R. D. (1994) *Invertebrate Zoology* (6th ed.). Harcourt Brace College Publishers, Fort Worth.
- Ryall, J. (2009) Giant Jellyfish Sink Japanese Trawler. *Scuba Diving News: CDNN—Cyber Diver News Network*. Cyber Diver., Web. 17 Nov. 2010.
- Sadowska, M., Kolodziejska, I. & Niecikowska, C. (2003) Isolation of collagen from the skins of Baltic cod (*Gadus morhua*). *Food Chem.* 81: 257-262.
- Schaadt, M., Yasukochi, L., Gershwin, L. & Wrobel, D. (2001) Husbandry of the black jelly (*Chrysaora achlyos*), a newly discovered scyphozoan in the eastern North Pacific *Ocean. Bull. Inst. Oceanogr.* (Monaco), spec. num. 20 (1): 289–296.
- Schiariti, A. (2008) Life history and population dynamics of *Lychnorhiza lucerna* (Scyphozoa): an alternative fishing resource? *PhD Thesis (In Spanish)*.
- Schiariti, A., Mianzan, H., Juana, L., Hsieh, Y.H.P., Brotz, L. & Quinonez, J.A. (2013) Jellyfish fisheries in the Americas: origin, state of the art, and perspectives on new fishing grounds. *Poster presentation*. Fourth International Jellyfish Bloom Symposium, June 5-7, 2013, Hiroshima, Japan.
- Schubring, R. (2010) Quality assessment of fish and fishery products by colour measurement. In Leo M.L. Nollet & Fidel Toldra (eds), *Handbook of Seafood and Seafood Products Analysis*. CRC Press, USA.
- Shoulders, M.D. & Raines, R.T. (2009) Collagen structure and stability. *Annu. Rev. Biochem.* 78: 929 – 958.
- Sigma-Aldrich, Inc. (2014) Gelatin: product information. Accessed online on 21 May 2014 at www.sigmaaldrich.com.
- Sim, Y.K. & Khairun, Y. (2008) Monthly distribution and abundance of jellyfish (Medusae) species in the coastal waters of Penang National Park. Presented at the 7th IOC/WESTPAC International Scientific Symposium, Kota Kinabalu, Sabah, Malaysia, 21-25 May 2008.
- Song, E., Kim, S.Y., Chun, T., Byun, H.J. & Lee, Y.M. (2006) Collagen scaffolds derived from a marine source and their biocompatibility. *Biomaterials* 27: 2951–2961.
- Songchotikunpan, P., Tattiyakul, J. & Supaphol, P. (2008) Extraction and electrospinning of gelatin from fish skin. *Int. J. Biol. Macromol.* 42: 247-255.
- Sugahara, T., Ueno, M., Goto, Y., Shiraiishi, R., Doi, M., Akiyama, K. & Yamauchi, S. (2006) Immunostimulation effect of jellyfish collagen. *Biosci. Biotechnol. Biochem.*, 70: 2131-2137.
- Uriarte-Montoya, M.H., Santacruz-Ortega, H., Cinco-Moroyoqui, F.J., Rouzaud-Sandez, O., Plascencia-Jatomea, M. & Ezquerro-Brauer, J.M. (2011) Giant squid skin gelatin: Chemical composition and biophysical characterization. *Food Res. Int.* 44: 3243-3249.

- Uye, S. (2008) Blooms of the giant jellyfish *Nemopilema nomurai*: a threat to the fisheries sustainability of the East Asian Marginal Seas. *Plankton Benthos Res.* 3 (Suppl.): 125-131.
- Voet, D. & Voet, J.G. (2004) Biochemistry 3rd ed. Chapter 8 Three dimensional structures of proteins. USA: John Wiley & Sons, Inc. pp. 233-240.
- Wallace, R.L. & Taylor, W.K. (2002) Invertebrate zoology: A laboratory manual 6th ed. Chapter 3 Phylum Cnidaria (Coelenterata). USA: Prentice Hall, Inc. pp. 47-74.
- Widmer CL (2005) Effects of temperature on growth of northeast Pacific moon jellyfish ephyrae, *Aurelia labiata* (Cnidaria: Scyphozoa). *J Mar Biol Assoc UK* 85: 569–573.
- Williams, P.A. & Phillips, G.O. (2009) Introduction to food hydrocolloids In Handbook of hydrocolloids (ed.) G.O. Phillips & P.A. Williams, pp.1-22. Cornwall, UK, CRC Press.
- Yasuda, T. & Suzuki, Y. (1992) Notes on an edible medusa, *Rhopilema asamushi* Uchida, caught in Wakasa Bay, Japan. *Bulletin of Plankton Society of Japan* 38: 147-148.
- Yoon, H.D., Kim, Y.K., Lim, C.W., Yeun, S.M., Lee, M.H., Moon, H.S., Yoon, N.Y., Park, H.Y. & Lee, D.S. (2011) ACE-inhibitory properties of proteolytic hydrolysates from giant jellyfish *Nemopilema nomurai*. *Fish. Aquat. Sci.* 14(3): 174-178.
- You, K., Ma, C., Gao, H., Li, F., Zhang, M., Qiu, Y. & Wang, B. (2007) Research on the jellyfish (*Rhopilema esculentum* Kishinouye) and associated aquaculture techniques in China: Current status. *Aquacult. Int.* 15: 479-488.
- Yu, H.H., Liu, X.G., Xing, R.E., Liu, S., Guo, Z.Y., Wang, P.B., Li, C.P. & Li, P.C. (2006) In vitro determination of antioxidant activity of proteins from jellyfish *Rhopilema esculentum*. *Food Chem.* 95: 123-130.
- Yusoff, F.M., Bakar, J., Basri, M., Ismail, M. & Khong, N.M.H. (2013) A method for Extracting Collagen and Aquatic Animals, Collagen and Products Containing it. *Patent pending* PI2013701277.
- Yusoff, F.M., Nishikawa, J. & Kuppan, P. (2010) Commercial jellyfish, a little known fishery industry in Malaysia. *Fishmail* 18(1): 8-12.
- Zhang, F., Wang, A., Li, Z., He, S. & Shao, L. (2011) Preparation and characterisation of collagen from freshwater fish scales. *Food Nutr. Sci.* 2: 818-823.
- Zhang, J., Duan, R., Huang, L., Song, Y. & Regenstein, J.M. (2014) Characterization of acid-soluble and pepsin-solubilised collagen from jellyfish (*Cyanea nozakii* Kishinouye). *Food Chem.* 150: 22-26.
- Zhuang, Y., Hou, H., Zhao, X., Zhang, Z. & Li, B. (2009) Effects of collagen and collagen hydrolysate from jellyfish (*Rhopilema esculentum*) on mice skin photoaging induced by UV irradiation. *J. Food Sci.* 74: 183-188.

- Zhuang, Y., Li, B., Zhao, X., Yan, M. & Zhang, X. (2009) Extraction of gelatin from jellyfish by high pressure treatment. *Food and Fermentation Industries*. Abstract assessed online: http://en.cnki.com.cn/Article_en/CJFDTOTAL-SPFX200905032.htm
- Zhuang, Y., Li, B., Zhao, X., Yan, M. & Zhang, X. (2009) Extraction of gelatin from jellyfish by high pressure treatment. *Food and Fermentation Industries*. Abstract assessed online: http://en.cnki.com.cn/Article_en/CJFDTOTAL-SPFX200905032.htm.
- Zhuang, Y., Sun, L., Zhao, X., Wang, J., Hou, H. & Li, B. (2009) Antioxidant and melanogenesis-inhibitory activities of collagen peptide from jellyfish (*Rhopilema esculentum*). *J. Sci. Food Agric.* 89: 1722–1727.
- Zhuang, Y., Zhao, X. & Li, B. (2009) Optimization of antioxidant activity by response surface methodology in hydrolysates of jellyfish (*Rhopilema esculentum*) umbrella collagen. *Journal of Zhejiang University SCIENCE B* 10: 572-579.
- Zlatanov, S., Laskaridis, K., Feist, C. & Sagredos, A. (2006) Proximate composition, fatty acid analysis and protein digestibility-corrected amino acid score of three Mediterranean cephalopods. *Mol. Nutr. Food Res.* 50: 967-970.