

Ammonia removal using activated carbons: Effect of the surface chemistry in dry and moist conditions

Journal:	<i>Environmental Science & Technology</i>
Manuscript ID:	es-2011-03093v.R1
Manuscript Type:	Article
Date Submitted by the Author:	n/a
Complete List of Authors:	Gonçalves, Maraisa; Facultad de Ciencias, Universidad de Alicante Sánchez-García, Laura; Facultad de Ciencias, Universidad de Alicante Oliveira Jardim, Erika; Facultad de Ciencias, Universidad de Alicante Silvestre-Albero, Joaquin; University of Alicante, Inorganic Chemistry Department Rodríguez-Reinoso, Francisco; Facultad de Ciencias, Universidad de Alicante

SCHOLARONE™
Manuscripts

1
2
3
4 Ammonia removal using activated carbons: Effect of the
5
6
7
8 surface chemistry in dry and moist conditions
9
10

11
12
13 *Maraisa Gonçalves, Laura Sánchez-García, Erika Oliveira-Jardim, Joaquín Silvestre-Albero**,
14

15
16 *Francisco Rodríguez-Reinoso*
17

18
19 Laboratorio de Materiales Avanzados, Departamento de Química Inorgánica-Instituto Universitario de
20
21 Materiales, Universidad de Alicante, Ap. 99, E-03080 Alicante, Spain
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54

55 *Corresponding author: Joaquín Silvestre-Albero (joaquin.silvestre@ua.es)
56
57

58 **Tel./Fax.: +34965909350/3454**
59
60

ABSTRACT

The effect of surface chemistry (nature and amount of oxygen groups) in the removal of ammonia was studied using a modified resin-based activated carbon. NH_3 breakthrough column experiments show that the modification of the original activated carbon with nitric acid, i.e. the incorporation of oxygen surface groups, highly improves the adsorption behaviour at room temperature. Apparently, there is a linear relationship between the total adsorption capacity and the amount of the more acidic and less stable oxygen surface groups. Similar experiments using moist air clearly show that the effect of humidity highly depends on the surface chemistry of the carbon used. Moisture highly improves the adsorption behaviour for samples with a low concentration of oxygen functionalities, probably due to the preferential adsorption of ammonia via dissolution into water. On the contrary, moisture exhibits a small effect on samples with a rich surface chemistry due to the preferential adsorption pathway via Brønsted and Lewis acid centers from the carbon surface. FTIR analyses of the exhausted oxidized samples confirm both the formation of NH_4^+ species interacting with the Brønsted acid sites, together with the presence of NH_3 species coordinated, through the lone pair electron, to Lewis acid sites on the graphene layers.

KEYWORDS: Activated carbon, ammonia, surface chemistry.

Introduction

1
2
3 New air quality emission standards are forcing the different governments to adopt new regulations in
4
5 order to control pollutant emissions. Among them, ammonia is considered an important health hazard
6
7 because it is poisonous if inhaled in great quantities (breathing levels above 50-100 ppm) while it can
8
9 cause eyes, throat and nose irritation in lesser concentrations.¹
10

11
12 Actual ammonia emissions are generated mainly from the fertilizer manufacture industry, coke
13
14 manufacture, fossil fuel combustion, livestock and poultry management, and refrigeration methods.
15
16 Among all these sources, livestock waste management and fertilizers production account for about 90%
17
18 of total ammonia emissions.^{1,2} Many techniques have been proposed in the literature for the removal of
19
20 NH_3 in industrial effluents. These include absorption by solution, reaction with other gases, ion
21
22 exchange using polymeric resins, separation using membranes, thermal treatment, catalytic
23
24 decomposition and adsorption by porous solids.³⁻⁵ Some of these techniques (e.g. thermal combustion)
25
26 are economically convenient for high concentration pollutants, whereas they become economically
27
28 unviable for diluted waste streams. For these special cases adsorption on porous solids (e.g. activated
29
30 carbons, zeolites, and so on) can be an excellent approach.⁶⁻¹² Among the different porous solids
31
32 described in the literature, activated carbons exhibit certain advantages such as a high “apparent” surface
33
34 area, a highly developed porous structure and, most importantly, the possibility to tailor the porous
35
36 structure and surface chemistry in order to adapt it for a special application.¹³ These modifications using
37
38 pre- and post-synthesis treatments are very convenient when trying to adsorb polar gases (e.g. NH_3),
39
40 because activated carbons usually exhibit non-polar surfaces and surface modifications are mandatory.
41
42
43
44
45
46

47
48 Previous studies described in the literature indicated that the surface chemistry is probably the most
49
50 critical parameter defining the total adsorption capacity of activated carbons for a basic molecule such as
51
52 ammonia.^{6,7,9} Kim et al. showed that not only the amount but also the nature of the oxygen surface
53
54 groups present on the carbon surface, i.e. acidic groups, are responsible for the total amount adsorbed.⁷
55
56 Furthermore, Huang et al. reported a linear correlation between NH_3 breakthrough capacity and the total
57
58
59
60

1 amount of acidic groups.⁶ A similar beneficial effect for the ammonia removal has been described in the
2 literature for metal-modified (Fe, Co, Cr, Mo and W) activated carbons.^{8,10,14}
3
4

5 Different reaction mechanisms have been proposed for the adsorption process involving mainly
6 Brønsted acid sites, but the true pathway is still under debate. Unfortunately, many of these studies
7 described in the literature deal with a wide variety of carbon samples, i.e. different textural and chemical
8 properties, together with additional effects due to the presence of metal species, which makes difficult a
9 clear correlation between the inherent parameters of the carbon support and the adsorption
10 mechanism.^{8,10,14} Furthermore, only few studies have paid attention to the role of moisture usually
11 present in industrial streams.
12
13
14
15
16
17
18
19
20

21 The objective of this paper is to evaluate the real role of the oxygen surface groups present on the
22 surface of activated carbons in the removal of ammonia, either in the presence or absence of moisture.
23 For this purpose, an activated carbon prepared from a resin precursor was modified by an oxidation
24 treatment with HNO₃, followed by a subsequent thermal treatment at different temperatures in order to
25 selectively remove some of the oxygen surface groups. Compared to previous analysis described in the
26 literature, the sole modification of the surface chemistry in a controlled way will allow to analyze the
27 effect of the surface chemistry in the ammonia adsorption process, under dry or moist conditions,
28 avoiding the influence of additional parameters (e.g. porous structure or inorganic matter).
29
30
31
32
33
34
35
36
37
38
39
40
41

42 **2. Experimental Section**

43 **2.1. Materials**

44 A spherical activated carbon (MA2, supplied by MAST Carbon International, UK) with particle size
45 around 0.32 mm was prepared by carbonization and subsequent activation using CO₂ (43 % burn-off) of
46 a porous resin obtained by cross-linking of phenol-formaldehyde Novolac precursor with
47 hexamethylenetetramine and using ethylene glycol as solvent-pore former. For the oxidation treatment,
48 25 g of carbon were treated with 250 ml HNO₃ solution (6M) at 90°C for 1h. The oxidized sample
49 (MA2ox) was washed until neutral pH and dried overnight at 85°C. In order to selectively remove the
50
51
52
53
54
55
56
57
58
59
60

1 surface functional groups, sample MA2ox was submitted to a subsequent thermal treatment at 300, 500
2 and 700°C under a helium flow (50 ml/min) for 1h. Samples were labelled MA2ox300, MA2ox500 and
3 MA2ox700, respectively.
4
5
6
7
8

9 2.2. Characterization

10 N₂ adsorption/desorption isotherms were performed at -195°C in a home-made high precision
11 volumetric equipment. Before any experiment samples were degassed under vacuum (10⁻³ Pa) at 150°C
12 for 4h. “Apparent” surface area was calculated from the nitrogen adsorption data after application of the
13 BET equation while the micropore volume (V₀) was obtained after application of the Dubinin-
14 Radushkevich (DR) equation. CO₂ adsorption isotherms were performed in the same apparatus at 0°C
15 following the same protocol. Application of the DR equation to the CO₂ adsorption data was used to
16 calculate the volume of narrow micropores (V_n), i.e. those below 0.7 nm.¹⁵
17
18
19
20
21
22
23
24
25
26
27

28 Temperature programmed decomposition experiments (TPD) were performed in order to evaluate the
29 amount and nature of oxygen surface functionalities for the different samples. 100 mg of carbon were
30 placed in a quartz reactor under a helium flow (50 ml/min) and submitted a heat treatment up to 1000°C
31 (10°C/min). The different gas species evolved as a result of surface groups decomposition (mainly CO
32 and CO₂) were analyzed using an on-line mass spectrometer (Omnistar TM, Balzers). Quantitative
33 analyses were performed after calibration using CaC₂O₄·H₂O as a reference material.
34
35
36
37
38
39
40
41

42 FTIR spectra of the exhausted samples were obtained in the range 4000-700 cm⁻¹, by adding 100 scans
43 at a resolution of 5 cm⁻¹, using a Mattson Infinity Gold FTIR spectrometer in the diffuse reflectance
44 method. Before any experiment all samples were diluted with KBr.
45
46
47
48
49
50

51 2.3. Breakthrough column experiments

52 The adsorption capacity under dynamic conditions for ammonia removal at room temperature (23°C)
53 was measured using a 1 cm i.d. column containing 2 cm carbon bed height (~ 0.6 g of sorbent). A total
54 flow of 300 ml/min of air containing 1000 ppm of ammonia was passed through the column containing
55
56
57
58
59
60

1 the fresh sample (without any pre-treatment). The concentration of ammonia at the exit was followed
2 using a Polytron 3000 (Dräger) detector. Adsorption experiments were performed using either dry or
3 moist air (70% humidity). For moist conditions, humidity was introduced into the NH₃/air flow using a
4 calibrated syringe. The breakthrough experiment was arbitrarily stopped when the ammonia
5 concentration at the outlet reached a concentration of 100 ppm. The adsorption capacity was determined
6 by integration of the area above the breakthrough curve and considering the inlet concentration, the total
7 flow rate and the amount of sorbent used. To further clarify the role of humidity, additional experiments
8 were performed using pre-humidified samples (20%, 40% and 70% relative humidity). For this purpose,
9 the carbon samples were first submitted to a thermal treatment at 100°C overnight in order to remove the
10 residual humidity and, in a subsequent step, samples were exposed to a given H₂O/H₂SO₄ mixture for
11 24h at room temperature under controlled humidity conditions. Breakthrough column experiments using
12 the pre-humidified samples were always performed under dry conditions.
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30

31 **3. Results and discussion**

32 3.1. Sample characterization

33 Figure 1 shows the nitrogen adsorption/desorption isotherms for the original and the modified
34 activated carbon. As it can be observed, the resin-based activated carbon (MA2) exhibits a highly
35 developed microporous structure, i.e. closed knee in the nitrogen adsorption isotherm at low relative
36 pressure, together with capillary condensation processes at $p/p_0 \sim 0.8$, corresponding to the filling of
37 large mesopores. The oxidation treatment with HNO₃ produces slight changes in the porous structure,
38 the main effect being the partial blockage of the microporosity due to the creation of polar oxygen
39 surface groups at the entrance of narrow pores; this slightly decreases the adsorption of a molecule such
40 as nitrogen, due to steric effects at the pore mouth.^{16,17} A subsequent thermal treatment at high
41 temperature (700°C) under a helium flow produces the widening of the existing micro/mesopores due to
42 the partial gasification of the carbon structure.^{13, 18} The textural properties of the modified activated
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

carbon obtained from the N₂ and CO₂ adsorption data, after application of the corresponding equations, are reported in Table 1.

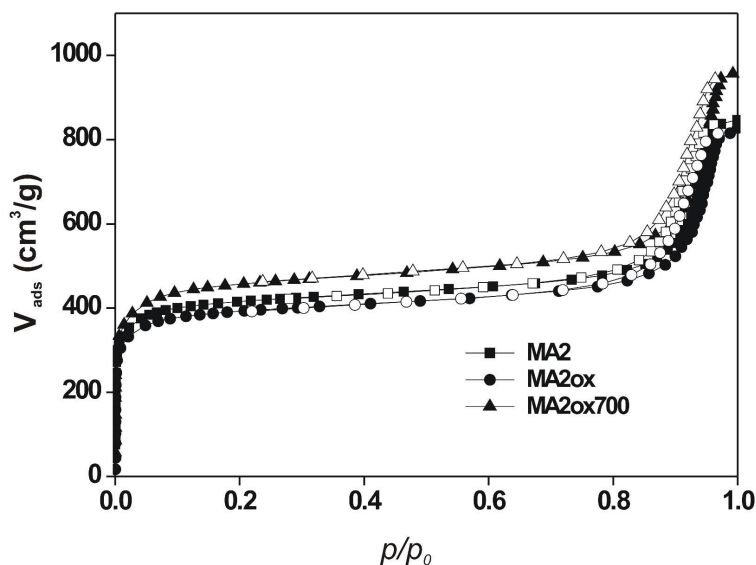


Figure 1. Nitrogen adsorption/desorption isotherms at -195°C for the different activated carbons.

Table 1. Textural parameters for the different activated carbons obtained from the N₂ and CO₂ adsorption data at -195°C and 0°C, respectively.

Samples	S_{BET} (m ² /g)	V_0 (cm ³ /g)	V_{meso} (cm ³ /g)	$V_{t(0.97)}$ (cm ³ /g)	V_n^* (cm ³ /g)
MA2	1550	0.61	0.68	1.29	0.55
MA2ox	1470	0.61	0.63	1.24	0.53
MA2ox300	1570	0.63	0.67	1.30	0.54
MA2ox500	1580	0.64	0.67	1.31	0.54
MA2ox700	1700	0.69	0.74	1.43	0.61

* Obtained after application of the D-R equation to the CO₂ adsorption data at 0°C

The surface chemistry of the original and modified activated carbons was evaluated using temperature-programmed decomposition (TPD) experiments. The amount of CO₂ and CO evolved in the temperature range from room temperature up to 1000°C was analyzed as described in the experimental

1 section. Quantitative data for the different samples are compiled in Table 2. CO₂ groups usually evolve
2 at low temperatures and they correspond to the decomposition of the more acidic and less stable oxygen
3 surface groups (mainly carboxylic and lactone groups), while CO evolution is due to the decomposition
4 of the more stable and less acidic oxygen groups (mainly phenolic, carbonyl and quinone groups) and
5 takes place at a higher temperature.¹⁹

14 **Table 2.** Total amount of CO₂ and CO groups evolved in the TPD experiment.

Carbons	CO (mmol/g)	CO ₂ (mmol/g)
MA2	0.837	0.18
MA2ox	2.800	1.770
MA2ox300	2.820	0.862
MA2ox500	1.822	0.245
MA2ox700	1.048	0.093

19 The as-received activated carbon (MA2) shows a relatively poor surface chemistry, i.e. it has a small
20 amount of oxygen surface groups, with a larger content of the less acidic groups compared to those
21 evolved as CO₂ (CO/CO₂ ratio of 4.6). As expected, the oxidation treatment with nitric acid produces a
22 large increase in the amount of both types of oxygen surface groups, this enhancement being larger for
23 the CO₂ groups (CO/CO₂ ratio of 1.6), in accordance with previous observations.¹⁷ A subsequent
24 thermal treatment at low temperature (300°C) produces an important decrease in the amount of the less
25 stable and more acidic oxygen groups, i.e. those evolved as CO₂, while the more stable groups remain
26 mainly unaffected. Temperatures higher than 300°C are required to selectively remove not only the more
27 acidic but also the majority of the more stable oxygen surface groups, i.e. those evolved as CO in the
28 TPD experiment.

3.2. Breakthrough column experiments

Breakthrough column experiments were performed in a glass tubular reactor using a total flow of 300 ml/min of either dry or moist air (70% humidity) containing 1000 ppm NH_3 . Figure 2 shows the corresponding curves obtained using (a) dry air and (b) moist conditions. The total adsorption capacity (mg/g) for the different samples is reported in Table 3.

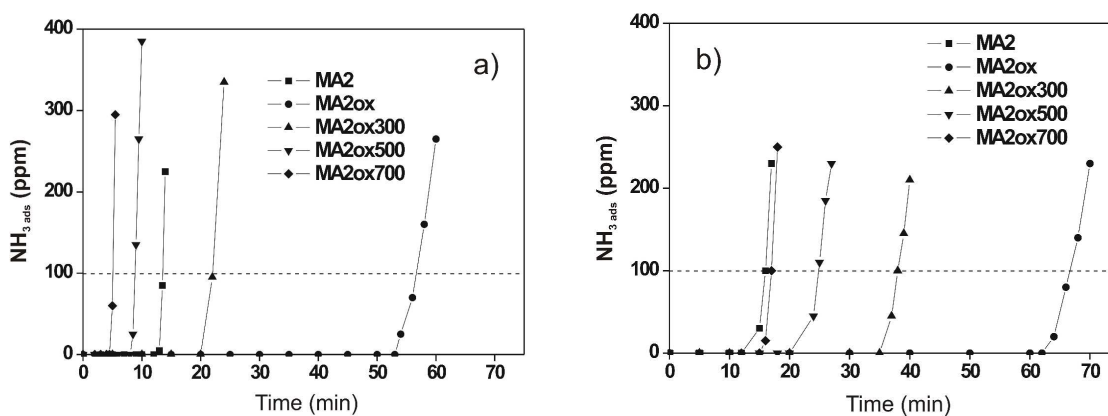


Figure 2. Breakthrough curves of ammonia adsorbed on the different activated carbons (1000 ppm, 300 ml/min, 23°C) using (a) dry and (b) moist (70% relative humidity) air.

Dynamic adsorption experiments show important differences among the different samples either in the presence or absence of moisture. In general all samples exhibit a sharp breakthrough saturation profile that proves the absence of kinetic restrictions in the adsorption process. This observation must be attributed to fast adsorption kinetics of NH_3 through the mesoporous network on these carbon materials, since the mesopores constitute the channels to access the inner microporosity. Under dry conditions (see Figure 2a) the total adsorption capacity largely improves (close to five fold increase) after an oxidation treatment of the original carbon with HNO_3 . The total adsorption capacity for the oxidized sample (MA2ox) achieves a value as high as 17.5 mg/g, in close agreement with previous measurements reported in the literature for oxidized activated carbons.^{6,8,20} A subsequent thermal treatment at low and high temperature produces a large decrease in the uptake down to a residual value even lower than the one of the original sample. Interestingly, the decline in the adsorption capacity is very drastic after the

1 thermal treatment at low temperature (sample MA2ox300), whereas a small decrease is observed
2 thereafter (up to 700°C). This observation anticipates the crucial role of the oxygen surface groups in the
3
4 gas phase removal of ammonia and, more specifically, the important effect of the more acidic and less
5
6 stable (those decomposing at low temperature) oxygen surface groups (mainly carboxylic groups) in the
7
8 adsorption process under dry conditions.^{6,7} Incorporation of 70 % relative humidity in the inlet stream
9
10 has a different effect depending on the surface chemistry (Figure 2b). The oxidized sample (MA2ox)
11
12 exhibits a moderate improvement in the adsorption behaviour after moisture incorporation, this clearly
13
14 suggesting the predominant role of the oxygen surface groups in the adsorption process, i.e. water must
15
16 exhibit a marginal effect in the adsorption mechanism. Concerning the thermally treated samples, Figure
17
18 2b shows that the improvement in the adsorption capacity due to moisture incorporation is larger
19
20 compared to the oxidized sample and it remains mainly constant for all samples, independently of the
21
22 temperature of the thermal treatment applied (see Table 3). Apparently on these thermally treated
23
24 samples, i.e. these samples were the more acidic and less stable oxygen surface groups have been
25
26 removed, moisture exhibits a crucial role in the adsorption mechanism, independently of the amount and
27
28 nature of the remaining surface functionalities. On the contrary, on carbons with a rich surface chemistry
29
30 the preferential interaction of ammonia with the carbon surface, assisted by the oxygen surface groups
31
32 and, more specifically, by the more acidic groups, could be the key factor defining the total adsorption
33
34 capacity, independently of the presence or absence of moisture. The large adsorption capacity achieved
35
36 with the oxidized sample (MAox) under dry conditions, together with the slight improvement observed
37
38 after moisture incorporation is somehow in contradiction with previous studies described in the
39
40 literature, which proposed a crucial role of water in the formation of NH_4^+ ions, necessary for the
41
42 adsorption process via interaction with the Brønsted acid groups of the carbon surface.⁸
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Table 3. Total adsorption capacity for ammonia under dry and moist (70% relative humidity) air conditions.

Carbons	NH ₃ dried (mg/g)	NH ₃ 70% RH (mg/g)	Δm (mg/g) (0-70% RH)
MA2	4.7	5.3	0.6
MA2ox	17.5	20.1	2.6
MA2ox300	7.6	12.3	4.7
MA2ox500	3.4	7.6	4.2
MA2ox700	1.9	6.1	4.2

To further clarify the real role of the oxygen surface groups in the adsorption process Figure 3a compares the total adsorption capacity, either under dry or moist conditions, and the total amount of acidic oxygen surface groups, i.e. those decomposing as CO₂ in a typical TPD run. As described above, the total adsorption capacity is larger in the presence of moist air for all samples, independently of the surface chemistry. However, contrary to previous analysis described in the literature, the presence of moisture does not seem to be so critical for the ammonia adsorption process when oxygen surface groups, mainly acidic, are present (e.g. sample MAox); in other words, the adsorption capacity of the oxidized sample under dry conditions is rather high and the improvement after moisture incorporation is rather small.⁸ Interestingly, there is a linear correlation between the amount of ammonia adsorbed and the total amount of acidic groups on the carbon surface, either in the presence or absence of humidity. Furthermore, a closer look to Figure 3a shows that the beneficial effect of moisture slightly decreases when the amount of oxygen surface groups increases, thus suggesting a different adsorption mechanism in the presence or absence of surface functionalities (mainly acidic oxygen surface groups). While moisture highly improves the adsorption behaviour of the carbon materials with a poor surface chemistry (69% improvement on sample MA2ox700), moisture seems to exhibit a minor effect (13% improvement on sample MA2ox) in the presence of oxygen functionalities (mainly acidic groups), probably due to the preferential adsorption mechanism involving these oxygen surface groups.

1
2
3
4
5
6
7
8
9
10
11
12
13
14
15
16
17
18
19
20
21
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

Incorporation of oxygen functionalities to the carbon surface can modify the adsorption behaviour through two different mechanisms: i) the creation of active sites, preferentially acidic oxygen groups, at the periphery of the basal planes, which will promote NH_3 adsorption via a Brønsted acid-base process through ammonium ion formation (NH_4^+) or ii) the creation of Lewis acid centers on the graphene layers due to the withdraw of electron density by the more electronegative oxygen surface groups on the periphery, thus promoting the interaction of ammonia (Lewis base) via the lone pair electron. Taking into account that the incorporation of the oxygen functionalities to the carbon surface promotes both processes at the same time, the presence of a linear correlation as observed in Figure 3a does not provide enough information to exclude one mechanism against the other.

Previous studies described in the literature using a large variety of activated carbons have shown that when the adsorption process is governed by a pure Brønsted acid-base process, the adsorption behaviour increases exponentially below a certain pH (~ 4.5), which corresponds to the pK_a for dissociation of carboxylic acid groups on the carbon surface.⁸ In this sense, Figure 3b shows the relationship between the total amount adsorbed and the surface pH of the different samples used. At this point it is important to highlight that at the pH of all activated carbons used in this manuscript ($\text{pH} < 6.5$), NH_3 will be protonated to NH_4^+ in a proportion close to 100% (pK_a for ammonia is 9.3). As it can be observed, the absence of an exponential increase in the amount adsorbed below a certain pH value, either in the presence or absence of moisture, clearly suggests that the NH_3 adsorption mechanism on activated carbons is not exclusively governed by the Brønsted acid sites on the surface, as proposed in the literature.⁸ Most probably, both adsorption mechanisms, i.e. Lewis and Brønsted mechanisms, take place on activated carbons even in the presence or absence of moisture.

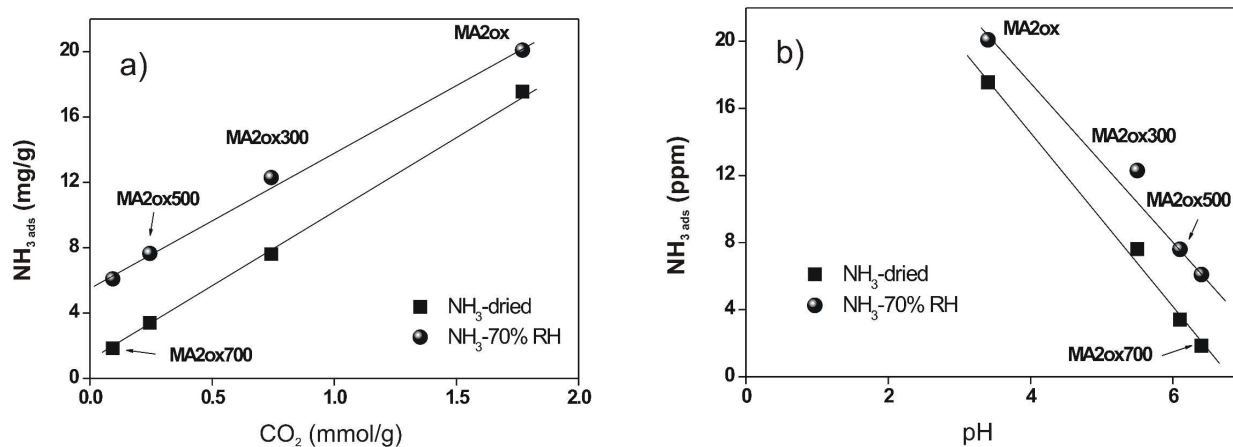


Figure 3. Dependence of the total breakthrough column capacity (a) as a function of the amount of acidic oxygen surface groups and (b) as a function of surface pH, in the presence or absence of moisture.

To further clarify the role of humidity, a new series of experiments were performed using pre-humidified samples. In a first step, carbon materials were heat treated at 100°C overnight in order to remove the residual humidity; in a second step, activated carbons were submitted to a pre-humidification treatment at different percentages (20%, 40% and 70% relative humidity) using a $\text{H}_2\text{O}/\text{H}_2\text{SO}_4$ mixture and, in a final step, carbon samples were analyzed in ammonia breakthrough column experiments using dry air. Figure 4 reports the amount of NH_3 adsorbed for samples MA2ox and MA2ox700, i.e. samples with a completely different surface chemistry, under different pre-humidification conditions and as a function of the weight gain after the pre-humidification step, i.e. the amount of humidity retained by the sample. As expected, the oxidized sample (MA2ox) is more hydrophilic and, consequently, it is able to absorb a larger amount of water under the pre-humidification conditions used. Figure 4 shows that for the sample with a poor surface chemistry (sample MA2ox700) there is a linear relationship between the amount of water adsorbed by the carbon sample and the subsequent adsorption capacity for a basic molecule such as ammonia. This linear relationship confirms that moisture plays a crucial role in the adsorption behaviour on this sample. Most probably in samples with a poor surface chemistry (absence of acidic groups), adsorption of ammonia takes place via dissolution into water, in such a way that the

1 amount of ammonia dissolved increases with the amount of solvent. The total adsorption capacity ranges
2 from 1.1 mg/g for the dried sample to 5.3 mg/g for the sample pre-humidified with 70% RH, this
3 meaning a 4.8 fold increase. On the contrary, the oxidized sample exhibits a completely different
4 behaviour. As described above, the adsorption capacity of the untreated sample, i.e. in the absence of
5 humidity, is as large as 15.6 mg/g, thus confirming the crucial role of the oxygen surface groups in the
6 adsorption of a basic molecule such as ammonia. At this point it must be highlight that this value is
7 slightly smaller than the one reported in Table 3 (17.5 mg/g vs 15.6 mg/g) for the same sample, thus
8 confirming the beneficial effect of the inherent humidity on the fresh sample. Pre-humidification with
9 20% RH produces a slight increase in the adsorption capacity up to a value of 17.5 mg/g, remaining
10 constant thereafter (up to 70% RH). Taking into account that the amount of water adsorbed highly
11 increases with the pre-humidification step (from 0 to 70% RH) on sample MA2ox, the absence of
12 significant changes in the adsorption capacity for this sample above 20 % RH clearly suggests that the
13 adsorption mechanism in carbons with a rich surface chemistry follows a different pathway. Under these
14 conditions moisture exhibits a scarce effect, the main contribution to the adsorption process coming
15 from the oxygen groups, mainly acidic groups, present on the carbon surface as suggested in Figure 3a.
16 As described above, the adsorption mechanism on oxidized samples can proceed following two
17 approaches: i) by interaction of NH_3 through the lone pair electron with the Lewis acidic sites on the
18 graphene planes; or ii) by interaction of NH_3 with acidic oxygen surface groups via NH_4^+ ions
19 formation. Apparently, both adsorption mechanisms take place in the oxidized samples either in the
20 presence and absence of moisture, although with a certain prevalence for the Lewis acid-base
21 mechanism, according to Figure 3b.
22
23
24
25
26
27
28
29
30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60


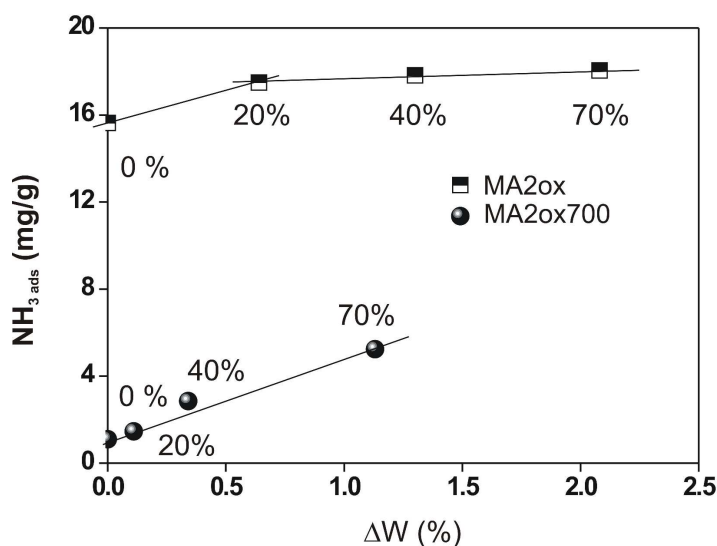


Figure 4. Dependence of ammonia adsorption capacity on the amount of water adsorbed under different humidity conditions (RH 0-70 %) for samples MA2ox and MA2ox700.

In a final step, the nature of the active species after the adsorption process has been analyzed on the exhausted samples using FTIR. As it can be observed in Figure 5, the heat-treated sample MA2ox700 exhibits a poor FTIR profile, i.e. the amount of surface species after the adsorption process is very small, in accordance with the above breakthrough column tests. FTIR spectra of the oxidized sample, MA2ox, after the adsorption process show intense bands, mainly when the experiment is performed in the presence of moisture. Mutually overlapping bands of OH and NH stretching vibration appear as a broad contribution at 3271 cm^{-1} as a result of NH_3 adsorption. Furthermore, bands at 1637 cm^{-1} and 1082 cm^{-1} , $\delta_{\text{as}}\text{ NH}_3$ and $\delta_{\text{sym}}\text{ NH}_3$, respectively, denote the presence of NH_3 coordinated to Lewis acid sites on the carbon surface (graphene layers).¹¹ Formation of surface ammonium salts of carboxylic acid appears as a band at 1439 cm^{-1} ($\delta_{\text{sym}}\text{ NH}_4^+$ ion), as well as bands at 1521 cm^{-1} ($\nu_{\text{as}}\text{ COO}^-$) and $1393\text{-}1236\text{ cm}^{-1}$ ($\nu_{\text{sym}}\text{ COO}^-$). Consequently, FTIR analysis of the exhausted samples confirms the presence of two different adsorption mechanisms for ammonia adsorption on oxidized activated carbons: adsorption on Brønsted acid sites (carboxylic acid sites), via ammonium ion (NH_4^+) formation, and ii) adsorption on Lewis acid

1 sites on the graphene layers, via the lone pair electron of the ammonia molecule. Interestingly, both
 2 mechanisms dominate in oxidized carbon samples either in the presence or absence of moisture.
 3
 4
 5
 6
 7

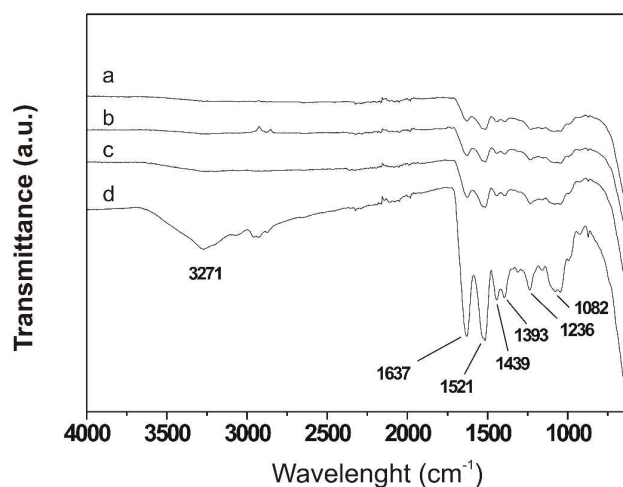

8
 9
 10
 11
 12
 13
 14
 15
 16
 17
 18
 19
 20
 21
 22
 23
 24 **Figure 5.** FTIR spectra of activated carbons (a) MA2ox700, (b)MA2ox700-70% RH, (c) MA2ox, (d)
 25 MA2ox-70% RH, after NH₃ breakthrough column experiments.
 26
 27
 28
 29
 30

31 ACKNOWLEDGMENT

32
 33
 34 Authors acknowledge financial support from MEC (projects MAT2007-61734 FEDER) and Generalitat
 35 Valenciana (PROMETEO/2009/002). European Commission is also acknowledge (project FRESP CA,
 36 contract 218138). J.S.A. acknowledges support from MEC, GV and UA (RyC2137/06).
 37
 38
 39
 40
 41

42 REFERENCES

- 43
 44
 45 (1) Phillips, J. *Control and pollution prevention options for ammonia emissions*, EPA-456/R-95-
 46 002, 1995.
 47 (2) Calvert, S.; Englund, H. M. *Handbook of Air Pollution Technology*; Willey: New York, 1984.
 48 (3) Pez, G. P.; Laciak, D. V. *Ammonia Separation using semipermeable membranes*, US patent n
 49 4,762,535, 1988.
 50 (4) Blonigen, S. J.; Fassbender, A. G.; Litt, R. D.; Monzyk, B. F.; Neff, R. *Method for ammonia*
 51 *removal from waste streams*, US patent n 6,558,643, 2003.
 52 (5) Blonigen, S. J.; Fassbender, A. G.; Litt, R. D.; Monzyk, B. F.; Neff, R. *Apparatus and method*
 53 *for ammonia removal from waste streams*, US patent n 6,838,069, 2005.
 54 (6) Huang, C.-C.; Li, H.-S.; Chen, C.-H. Effect of surface acidic oxides of activated carbon on
 55 adsorption of ammonia. *J. Hazard. Mater.* **2008**, *159*, 523-527.
 56 (7) Kim, B.-J.; Park, S.-J. Effect of carbonyl group formation on ammonia adsorption of porous
 57 carbon surfaces. *J. Colloid Interface Sci.* **2007**, *311*, 311-314.
 58
 59
 60

- 1 (8) Le Leuch, L. M.; Bandosz, T. J. The role of water and surface acidity on the reactive adsorption
2 of ammonia on modified activated carbons. *Carbon* **2007**, *45*, 568-578.
- 3 (9) Park, S.-J.; Jin, S.-Y. Effect of ozone treatment on ammonia removal of activated carbons. *J.*
4 *Colloid Interface Sci.* **2005**, *286*, 417-419.
- 5 (10) Petit, C.; Bandosz, T. J. Role of surface heterogeneity in the removal of ammonia from air on
6 micro/mesoporous activated carbons modified with molybdenum and tungsten oxides. *Microp. Mesop.*
7 *Mater.* **2009**, *118*, 61-67.
- 8 (11) Zawadzki, J.; Wisniewski, M. In situ characterization of interaction of ammonia with carbon
9 surface in oxygen atmosphere. *Carbon* **2003**, *41*, 2257-2267.
- 10 (12) Bernal, M. P.; Lopez-Real, J. M. Natural zeolites and sepiolite as ammonium and ammonia
11 adsorbent materials. *Bioresource Technology* **1993**, *43*, 27-33.
- 12 (13) Marsh, H.; Rodriguez-Reinoso, F. *Activated Carbon*; Elsevier: London, 2006.
- 13 (14) Bandosz, T. J.; Petit, C. On the reactive adsorption of ammonia on activated carbons modified by
14 impregnation with inorganic compounds. *J. Colloid Interface Sci.* **2009**, *338*, 329-345.
- 15 (15) Garrido, J.; Linares-Solano, A.; Martín-Martínez, J. M.; Molina-Sabio, M.; Rodríguez-Reinoso,
16 F.; Torregrosa, R. Use of nitrogen vs. carbon dioxide in the characterization of activated carbons.
17 *Langmuir* **1987**, *3*, 76-81.
- 18 (16) Rodríguez-Reinoso, F.; Molina-Sabio, M.; Muñecas-Vidal, M. A. Effect of microporosity and
19 oxygen surface groups of activated carbon in the adsorption of molecules of different polarity. *J. Phys.*
20 *Chem.* **1992**, *96*, 2707-2713.
- 21 (17) Silvestre-Albero, A.; Silvestre-Albero, J.; Sepúlveda-Escribano, A.; Rodríguez-Reinoso, F.
22 Ethanol removal using activated carbon: Effect of porous structure and surface chemistry. *Microp.*
23 *Mater.* **2009**, *120*, 62-68.
- 24 (18) Molina-Sabio, M.; Muñecas, M. A.; Rodríguez-Reinoso, F. Modification in porous texture and
25 oxygen surface groups of activated carbons by oxidation. *Stud. Surf. Sci. & Catal.* **1991**, *62*, 329-339.
- 26 (19) Figueiredo, J. L.; Pereira, M. F. R.; Freitas, M. M. A.; Orfao, J. J. M. Modification of the surface
27 chemistry of activated carbons. *Carbon* **1999**, *37*, 1379-1389.
- 28 (20) Rodrigues, C. C.; Moraes Jr., D. d.; da Nóbrega, S. W.; Barboza, M. G. Ammonia adsorption in
29 a fixed bed activated carbon. *Bioresource Technology* **2007**, *98*, 886-891.
- 30
31
32
33
34
35
36
37
38
39
40
41
42
43
44
45
46
47
48
49
50
51
52
53
54
55
56
57
58
59
60

SYNOPSIS TOC

