

Separating exchange splitting from spin mixing in gadolinium by femtosecond laser excitation

Beatrice Andres,* Marc Christ, Cornelius Gahl, Marko Wietstruk, and Martin Weinelt
Freie Universität Berlin, Fachbereich Physik, Arnimallee 14, 14195 Berlin, Germany

Jürgen Kirschner

Max-Planck-Institut für Mikrostrukturphysik, Weinberg 2, 06120 Halle/Saale, Germany

(Dated: October 16, 2015)

Employing spin-, time-, and energy-resolved photoemission spectroscopy, we present the first study on the spin polarization of a single electronic state after ultrafast optical excitation. Our investigation concentrates on the majority-spin component of the d -band-derived Gd(0001) surface state $d_{z^2}^{\uparrow}$. While its binding energy shows a rapid Stoner-like shift by 90 meV with an exponential time constant of $\tau_E = 0.6 \pm 0.1$ ps, the $d_{z^2}^{\uparrow}$ spin polarization remains nearly constant within the first picoseconds and decays with $\tau_S = 15 \pm 8$ ps. This behavior is in clear contrast to the equilibrium phase transition, where the spin polarization vanishes at the Curie temperature.

PACS numbers: 78.47.-p, 71.45.Gm, 73.20.At

Laser excitation is capable of creating new transient states of matter, that are not reached on equilibrium pathways [1–6]. In magnetically ordered materials this opens new routes to the ultrafast manipulation of the magnetic order [7–10]. Investigating the underlying processes provides a yet unseen view on the very basics of magnetism such as the relation between the electronic and magnetic structure. Contrary to thermal heating, laser excitation drives the electronic, phonon, and spin subsystems out of equilibrium [11]. It may therefore lead to a response quite different from the equilibrium magnetic phase transition as we show in this letter.

The first experiment on the laser-induced demagnetization of Gd metal applied spin-resolved photoemission on the nanosecond timescale [12]. A decrease of the spin polarization of the secondary electrons was observed, which was explained by spin-lattice relaxation with a characteristic time of 100 ± 80 ps. This result was corroborated by measurements of the magnetic linear dichroism (MLD) observed in $4f$ core-level photoemission [13]. Later studies with sub-picosecond time resolution revealed an additional much faster decrease of magnetic figures: The X-ray magnetic circular dichroism (XMCD) at the M_5 edge decreases within 0.76 ± 0.25 ps [14]. So do rotation and ellipticity of the magneto-optical Kerr effect (MOKE) [15, 16] as well as the ($5d6s$) valence-band exchange-splitting [17, 18]. A binding energy shift on this timescale has also been found for the majority-spin component of the surface state [19, 20]. In contrast, the magnetic component of the surface-sensitive second harmonic generation (SHG) shows an immediate response within the laser pulse duration of 100 fs [19, 21, 22]. Whereas a recent photoemission experiment reveals again a ps response of the MLD in the $4f$ states [23]. Obviously different observables of the magnetization dynamics suggest significantly different response times, while in the equilibrium phase transition all techniques map

the same behavior. Furthermore, most of the femtosecond pump-probe experiments are not consistent with the spin-resolved measurements of Ref. 12, which may be attributed to its 10-ns pump-pulse duration. It is thus still unclear on which timescale we can modify the spin polarization in Gd using an ultrafast laser pulse.

In this letter we present a comparative study of equilibrium *vs.* laser-induced demagnetization of Gd using spin-resolved photoemission. Upon excitation with a 48-fs laser pulse the majority-spin component $d_{z^2}^{\uparrow}$ of the Gd surface state shifts towards the Fermi level, reducing the exchange splitting on a sub-ps timescale. In contrast, the $d_{z^2}^{\uparrow}$ spin polarization changes only slightly with a one order of magnitude slower ps dynamics.

For pump we use s -polarized pulses at the fundamental photon energy of 1.6 eV of a 300-kHz Ti:Sapphire regenerative amplifier (RegA, Coherent) incident at an angle of 45° off normal along the Gd[1000] direction. The absorbed pump fluence was 3.9 mJ/cm². A time-delayed p -polarized ultraviolet probe is generated by frequency quadrupling the fundamental to 6.3 eV. The temporal resolution is ≤ 70 fs as determined from fitting the rising edge of the electronic temperature (Fig. 3 (a)). A cylindrical sector analyzer (CSA 300, Focus) transmits the photoemitted electrons to the spin detector with an energy and angular resolution of 65 meV and $\pm 2.5^\circ$, respectively. We use an exchange-scattering-based spin detector [24], which supports two measurement modes: A spin-integrated mode, where all incoming electrons impinge directly on a channeltron, and a spin-resolved mode, where we place an oxygen-passivated Fe/W(001) target into the electron beam for spin-dependent exchange scattering at 6 eV kinetic energy into a second channeltron in back-reflection geometry. The spin detector has a figure of merit of $2.2 \cdot 10^{-3}$ with an intensity loss of 2 orders of magnitude [24]. We took advantage of switching on the fly between spin-integrated and spin-resolved mode, to ac-

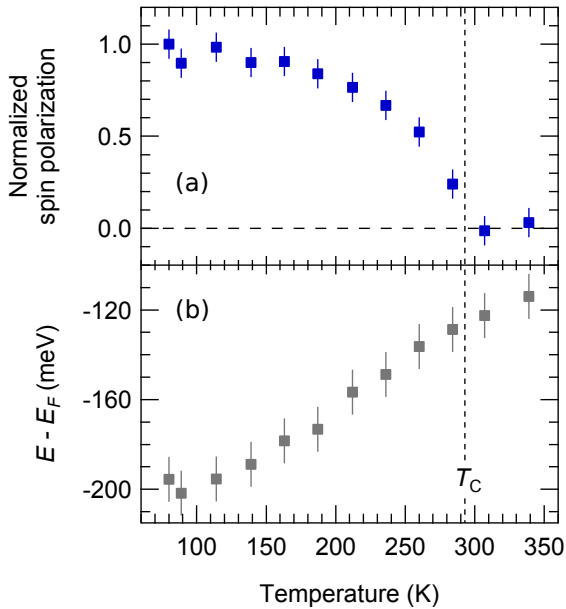


FIG. 1. Spin polarization (a) and binding energy (b) of the majority-spin surface state $d_{z_2}^{\uparrow}$ in the ferro- to paramagnetic phase transition in thermal equilibrium. The spin polarization vanishes at $T_C = 293$ K but the exchange splitting remains finite.

quire high-intensity spin-integrated data on the energetic behavior and valuable information on the spin polarization in the same experiment. The investigated Gd(0001) samples were prepared by evaporating 100 \AA of Gd onto a W(110) substrate at a temperature of 300 K , a deposition rate of $5 \text{ \AA}/\text{min}$ and a pressure of $6 \times 10^{-10} \text{ mbar}$. Beforehand, the substrate was cleaned from carbon impurities as described in Ref. 25. To obtain a smooth and contaminant-free surface, the Gd films were annealed for 1 minute at 780 K . During the measurements at a pressure of $2 \times 10^{-11} \text{ mbar}$, we kept a sample temperature of 90 K by liquid nitrogen cooling. All spectra were taken at $\bar{\Gamma}$ under normal emission. The Gd films were magnetized remanently in plane along the Gd[1100] direction applying a field pulse of 20 mT via a freestanding coil.

The ferro- to paramagnetic phase transition of gadolinium at the Curie temperature $T_C = 293 \text{ K}$ is a prototype system to study spin-mixing *vs.* Stoner behavior. The latter two limiting cases turned out to be helpful for distinguishing the temperature dependence of the electronic structure of a ferromagnet in thermal equilibrium. The Stoner model [26–29] treats delocalized electronic states and predicts a gradual decrease of the exchange splitting, which collapses at T_C . By contrast, spin mixing [30–34] describes localized states with a constant magnitude but fluctuating direction of the magnetic moment. In this model the exchange splitting stays constant while the spin-polarization of the states falls steadily with increasing temperature to vanish at T_C .

Evidence for the existence of a finite exchange splitting

above T_C has been found in the Gd(0001) surface state [35–39], where the majority- (minority-)spin component $d_{z_2}^{\uparrow}$ ($d_{z_2}^{\downarrow}$) is situated below (above) the Fermi level E_F . Fig. 1 displays the temperature-dependent spin polarization (a) and binding energy $E - E_F$ (b) of the $d_{z_2}^{\uparrow}$ determined by spin-resolved laser photoemission with 4.5-eV photons. When Gd(0001) is heated across T_C the $d_{z_2}^{\uparrow}$ spin polarization collapses while its exchange splitting is only partly lowered but remains at finite values. For more than 100 K above T_C , the $d_{z_2}^{\uparrow}$ remains below E_F [38] while the minority-spin part still has a binding energy above E_F [35–37]. To conclude, in the equilibrium phase transition the surface state shows spin mixing accompanied by a partly decreasing exchange splitting, *i.e.* a partly Stoner-like behavior.

In the following, we investigate the laser-driven phase transition. The spin-integrated photoemission intensity near E_F is shown in Fig. 2 (a) as a function of energy $E - E_F$ and pump-probe delay. Fig. 2 (b) compares the majority- and minority-spin intensities at selected delays. Independent of spin, there is a remarkable intensity redistribution after the excitation by the pump pulse at 0 ps . Compared to the spectra before pumping at -0.5 ps , the $d_{z_2}^{\uparrow}$ surface state is significantly depopulated at 0.2 ps and electrons are excited above E_F . This redistribution is attributed to an increasing electronic temperature reflected in a broadening of the Fermi edge as well as a broadening of the surface-state line-shape. In addition the maximum of the $d_{z_2}^{\uparrow}$ shifts to lower binding energy (indicated by the gray horizontal bars in Fig. 2 (b)). Directly after laser excitation, at a delay of 0.2 ps , the peak position is shifted by 27 meV towards E_F . This shift increases to 90 meV at 10 ps delay, when the population of the $d_{z_2}^{\uparrow}$ already recovers, most of the laser-excited electron population above E_F is decayed, and electron and phonon subsystems are equilibrated at an elevated temperature [40]. At this temperature a part of the peak is cut by the broad Fermi edge, such that the peak position obtained from a fit to the data (indicated by the gray bar) is closer to E_F as the maximum intensity visible in the spectrum [41]. Sample cooling shifts the $d_{z_2}^{\uparrow}$ binding energy back to the initial value and the broadening of line shape and Fermi edge further reduces as exemplified by the spectrum at 50 ps delay. Despite these significant changes, the ratio of majority- and minority-spin intensity and thus the spin polarization alters only weakly for all displayed pump-probe delays.

For a more detailed discussion, the temporal evolutions of the above-mentioned parameters: electronic temperature, surface-state binding energy, and spin polarization are shown in Fig. 3. The data were obtained from a fit to the spectra as described in the supplemental material [41]. The spin polarization calculates as $P = \frac{I^{\uparrow} - I^{\downarrow}}{I^{\uparrow} + I^{\downarrow}}$, where $I^{\uparrow/\downarrow}$ is either the intensity integrated over the energy range of the full majority/minority peak (\bullet) or

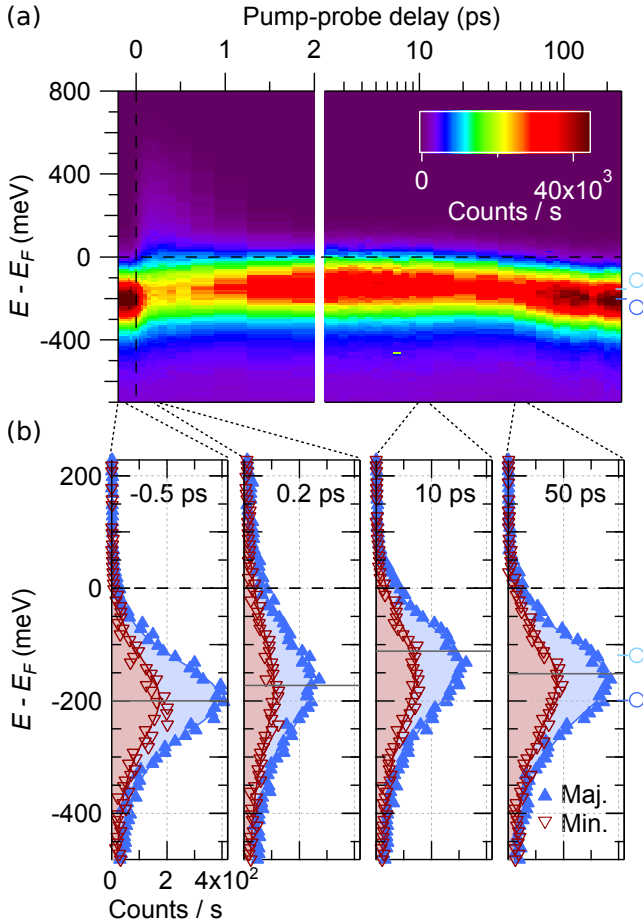


FIG. 2. (a) False color representation of spin-integrated photoemission spectra of the gadolinium $d_{z^2}^\uparrow$ surface state as a function of pump-probe delay. (b) Spin-resolved photoemission spectra at selected pump-probe delays. The spin polarization (asymmetry between majority (\blacktriangle) and minority (\blacktriangledown) count rates) shows only weak changes in all four spectra.

the photoemission intensity measured at a single binding energy (\circ , \circ). Integrating over the full peak yields more accurate values but also requires a lot more data acquisition-time and is thus more susceptible to changes of the surface quality. We therefore complemented the data by measurements at distinct energies with a significant spin polarization. Here we chose the maximal and minimal binding energy of the $d_{z^2}^\uparrow$ of -200 (\circ) and -120 meV (\circ) (indicated in Fig. 2 on the right ordinate) [42].

Figure 3 (a) shows the immediate increase of the electronic temperature up to 2,000 K within the temporal resolution of 70 fs. The subsequent temporal evolution of the temperature within the first picoseconds can be described (solid line) by an exponential decay that is overlaid by a rise in lattice temperature (dashed line). We thus assume that the electrons cool down predominantly transferring energy to the lattice at a time constant of $\tau_E = 0.6 \pm 0.1$ ps. We find that the shift in binding en-

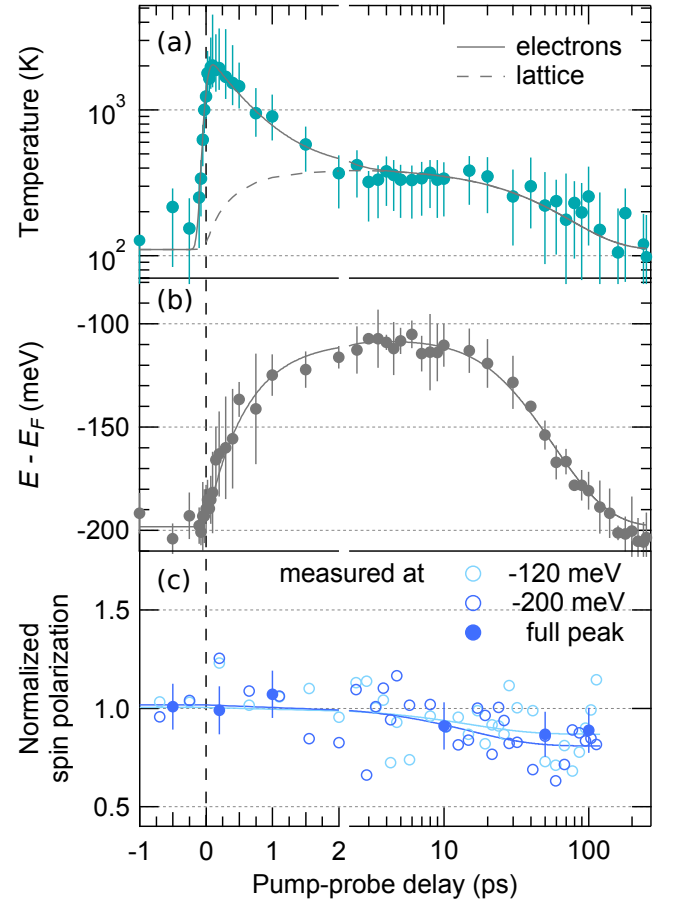


FIG. 3. Temporal evolution of (a) electronic temperature as obtained from the broadening of the Fermi edge, (b) binding energy, and (c) spin polarization of the $d_{z^2}^\uparrow$. The spin polarization integrated over the energy-range of the full peak (\bullet) is complemented by data taken at 120 meV (\circ) and 200 meV (\circ) binding energy indicated in Fig. 2 on the right ordinate.

ergy (Fig. 3 (b)) occurs with the same exponential time constant τ_E and must therefore be induced by a heating of the lattice due to electron-phonon scattering. Thus, the peak position is determined by the lattice temperature. This is in perfect agreement with the results in the equilibrium phase transition (*cf.* Fig. 1). In contrast, the spin polarization itself shows in fact a much slower decrease of small magnitude. An exponential fit to the spin polarization results in a decay time of $\tau_S = 15 \pm 8$ ps (dark and light blue lines for -200 and -120 meV). This slow decrease can already be explained by spin-lattice coupling as has been suggested in Ref. 12.

The evolutions of the spin polarization in the laser-driven experiment and in the thermal phase transition (filament heating) are compared in Fig. 4. The bottom axis shows the corresponding peak energy for each temperature in the equilibrium experiment (\blacksquare) and for each pump-probe delay in the laser-driven experiment (\bullet , \circ) respectively. We find that upon optical excitation the

peak position shifts to $E - E_F = -110$ meV with almost no decrease in spin polarization. In the equilibrium phase transition, the $d_{z_2}^\uparrow$ already loses its spin polarization when it reaches the same energy, since this is when the sample is heated across T_C (*cf.* Fig. 1). In the laser-driven experiment we observe a small reduction of the spin polarization to ~ 0.9 , which is much slower than the changes in binding energy. The reduced spin polarization remains during the cooling of the lattice when the peak energy is already shifting back.

It has been reported for a photoemission experiment with a lower pump fluence of 1 mJ/cm^2 [19] that the $d_{z_2}^\uparrow$ shift has not much effect on the total exchange splitting of the surface state. Nevertheless, experiments applying fluences similar to that in our experiment, find a breakdown of magnetic signals like XMCD [14] or MOKE [15] occurring on the same timescale as the $d_{z_2}^\uparrow$ shift. Also the exchange splitting of the ($5d6s$) valence-bands decreases with the same time constant [17, 18]. Therefore, we interpret the shift in our experiment as a change in exchange splitting, which is not accompanied by a reduction of spin polarization. We thus demonstrate that the response of the Gd(0001) $d_{z_2}^\uparrow$ surface state to an ultrafast laser excitation is completely Stoner-like within the first picoseconds. While in the equilibrium phase transition Stoner and spin-mixing behavior occur simultaneously, in the laser-driven experiment the spin polarization decreases exponentially with $\tau_S = 15 \pm 8$ ps subsequent to the Stoner-like change of the binding energy with $\tau_E = 0.6 \pm 0.1$ ps.

Three processes are reflected in the dynamics of the $d_{z_2}^\uparrow$ surface state. i) The fastest process, the direct heating of the electrons by the laser (< 70 fs), causes the fast response found in magnetic SHG [19, 21, 22]. According to Ref. 21, the highly spin-polarized surface state contributes dominantly to the SHG process. Thus, its depopulation lowers the magnetic component of the signal. ii) Subsequently, energy is transferred from the electrons to the lattice thereby inducing the Stoner-like shift of $d_{z_2}^\uparrow$ with $\tau_E = 0.6 \pm 0.1$ ps. MOKE depends on all possible transitions in the Brillouin zone [43]. It is therefore sensitive to the exchange splitting of the ($5d6s$) bands and hence shows a corresponding response time. It is however surprising that the XMCD contrast at the M_5 edge decreases on this timescale as well [14]. iii) XMCD and MOKE also reveal a second timescale in the ten picosecond regime similar to the response we find in the $d_{z_2}^\uparrow$ spin polarization. Recent results revealed that the MLD in photoemission from the $4f$ core-levels decreases on the same slow ps-timescale [23]. This suggests that the spin polarization of the valence states is determined by the $4f$ magnetic moment [44]. Such a demagnetization on two distinct timescales was already predicted by Koopmans *et al.* [45], but their model is solely based on a mean field description. It does not distinguish between exchange

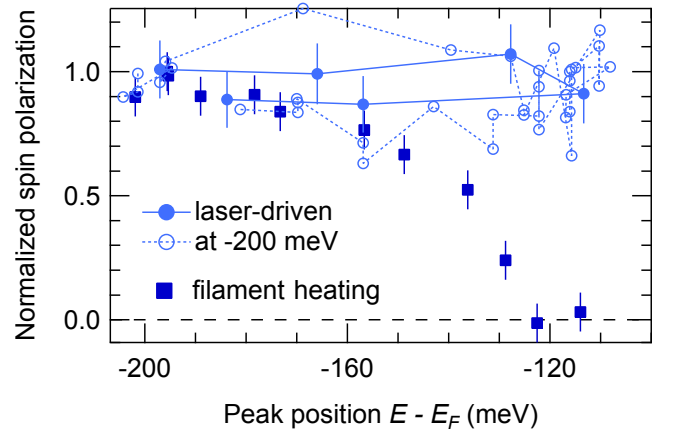


FIG. 4. Comparison of laser-driven (\bullet, \circ) and thermal phase transition (\blacksquare). The spin polarization is plotted *vs.* the binding energy corresponding to a pump-probe delay or temperature, respectively. Open symbols (\circ) display the spin polarization obtained at a single energy (-200 meV). Filled symbols (\bullet) show energy-integrated values for the full $d_{z_2}^\uparrow$ peak. The uncertainties of the peak position are shown in Figs. 1 and 3.

splitting and spin polarization, and hence misses important ingredients to describe the magnetization dynamics of $4f$ metals.

It is reasonable to assume that the observed behavior is characteristic for Gd, since spin-resolved photoemission measurements on Fe and Ni find an ultrafast breakdown of the overall spin polarization, though without orbital resolution [43, 46, 47].

In conclusion, we find that the response times of spin polarization and exchange splitting differ by more than one order of magnitude. This leads to a Stoner-like behavior of the surface state during the first picoseconds. We expect the huge difference between the Stoner and spin-mixing timescales in Gd to arise from the indirect exchange interaction. While the ($5d6s$) valence electrons are directly affected by the laser excitation leading to the decreasing exchange splitting, the $4f$ spin system remains cold for a long time stabilizing the spin polarization [23]. In contrast, in the equilibrium phase transition, these processes can not be separated. Using ultrafast laser excitation, we are able to disentangle exchange splitting and spin polarization, which opens a completely new view on the magnetic phase transition.

We thank the Helmholtz Virtual Institute *Dynamic Pathways in Multidimensional Landscapes* and the DFG for financial support.

* Corresponding author: andres@physik.fu-berlin.de

[1] A. Cavalleri, C. Tóth, C. W. Siders, J. A. Squier, F. Rákai, P. Forget, and J. C. Kieffer, Phys. Rev. Lett. **87**, 237401 (2001).

- [2] L. Perfetti, P. A. Loukakos, M. Lisowski, U. Bovensiepen, H. Berger, S. Biermann, P. S. Cornaglia, A. Georges, and M. Wolf, *Phys. Rev. Lett.* **97**, 067402 (2006).
- [3] D. Fausti, R. I. Tobey, N. Dean, S. Kaiser, A. Dienst, M. C. Hoffmann, S. Pyon, T. Takayama, H. Takagi, and A. Cavalleri, *Science* **331** (2011), 10.1126/science.1197294.
- [4] L. Stojchevska, I. Vaskivskiy, T. Mertelj, P. Kusar, D. Svetin, S. Brazovskii, and D. Mihailovic, *Science* **344** (2014), 10.1126/science.1241591.
- [5] D. Wegkamp, M. Herzog, L. Xian, M. Gatti, P. Cudazzo, C. L. McGahan, R. E. Marvel, R. F. Haglund, A. Rubio, M. Wolf, and J. Stähler, *Phys. Rev. Lett.* **113**, 216401 (2014).
- [6] M. Dell'Angela, T. Anniyev, M. Beye, R. Coffee, A. Föhlisch, J. Gladh, T. Katayama, S. Kaya, O. Krupin, J. LaRue, A. Møgelhøj, D. Nordlund, J. K. Nørskov, H. Öberg, H. Ogasawara, H. Öström, L. G. M. Pettersson, W. F. Schlotter, J. A. Sellberg, F. Sorgenfrei, J. J. Turner, M. Wolf, W. Wurth, and A. Nilsson, *Science* **339**, 1302 (2013).
- [7] I. Radu, K. Vahaplar, C. Stamm, T. Kachel, N. Pontius, H. A. Dürr, T. A. Ostler, J. Barker, R. F. L. Evans, R. W. Chantrell, A. Tsukamoto, A. Itoh, A. Kirilyuk, T. Rasing, and A. V. Kimel, *Nature* **472**, 205 (2011).
- [8] C. D. Stanciu, F. Hansteen, A. V. Kimel, A. Kirilyuk, A. Tsukamoto, A. Itoh, and T. Rasing, *Phys. Rev. Lett.* **99**, 047601 (2007).
- [9] A. Kirilyuk, A. V. Kimel, and T. Rasing, *Rev. Mod. Phys.* **82**, 2731 (2010).
- [10] S. Mangin, M. Gottwald, C.-H. Lambert, D. Steil, V. Uhlir, L. Pang, M. Hehn, S. Alebrand, M. Cinchetti, G. Malinowski, Y. Fainman, M. Aeschlimann, , and E. E. Fullerton, *Nature Mater.* **13**, 286 (2014).
- [11] E. Beaurepaire, J.-C. Merle, A. Daunois, and J.-Y. Bigot, *Phys. Rev. Lett.* **76**, 4250 (1996).
- [12] A. Vaterlaus, T. Beutler, and F. Meier, *Phys. Rev. Lett.* **67**, 3314 (1991), gd004.
- [13] A. Melnikov, H. Prima-Garcia, M. Lisowski, T. Giesel, R. Weber, R. Schmidt, C. Gahl, N. M. Bulgakova, U. Bovensiepen, and M. Weinelt, *Phys. Rev. Lett.* **100**, 107202 (2008).
- [14] M. Wietstruk, A. Melnikov, C. Stamm, T. Kachel, N. Pontius, M. Sultan, C. Gahl, M. Weinelt, H. A. Dürr, and U. Bovensiepen, *Phys. Rev. Lett.* **106**, 127401 (2011).
- [15] M. Sultan, U. Atxitia, A. Melnikov, O. Chubykalo-Fesenko, and U. Bovensiepen, *Phys. Rev. B* **85**, 184407 (2012).
- [16] M. Sultan, A. Melnikov, and U. Bovensiepen, *Phys. Status Solidi B* **248**, 2323 (2011).
- [17] R. Carley, K. Döbrich, B. Frietsch, C. Gahl, M. Teichmann, O. Schwarzkopf, P. Wernet, and M. Weinelt, *Phys. Rev. Lett.* **109**, 057401 (2012).
- [18] M. Teichmann, B. Frietsch, K. Döbrich, R. Carley, and M. Weinelt, *Phys. Rev. B* **91**, 014425 (2015).
- [19] M. Lisowski, P. A. Loukakos, A. Melnikov, I. Radu, L. Ungureanu, M. Wolf, and U. Bovensiepen, *Phys. Rev. Lett.* **95**, 137402 (2005).
- [20] P. A. Loukakos, M. Lisowski, G. Bihlmayer, S. Blügel, M. Wolf, and U. Bovensiepen, *Phys. Rev. Lett.* **98**, 097401 (2007).
- [21] A. Melnikov, I. Radu, U. Bovensiepen, O. Krupin, K. Starke, E. Matthias, and M. Wolf, *Phys. Rev. Lett.* **91**, 227403 (2003).
- [22] A. Melnikov, I. Radu, A. Povolotskiy, T. Wehling, A. Lichtenstein, and U. Bovensiepen, *Journal Of Physics D-Applied Physics* **41**, 164004 (2008).
- [23] B. Frietsch, J. Bowlan, R. Carley, M. Teichmann, S. Wienholdt, D. Hinzke, U. Nowak, K. Carva, P. M. Oppeneer, and M. Weinelt, *Nat Commun* **6**, (2015).
- [24] A. Winkelmann, D. Hartung, H. Engelhard, C.-T. Chiang, and J. Kirschner, *Rev. Sci. Instrum.* **79**, 083303 (2008).
- [25] B. Andres, P. Weiss, M. Wietstruk, and M. Weinelt, *Journal of Physics: Condensed Matter* **27**, 015503 (2015).
- [26] E. C. Stoner, *Proceedings of the Royal Society of London. Series A, Mathematical and Physical Sciences* **154**, pp. 656 (1936).
- [27] J. C. Slater, *Phys. Rev.* **49**, 537 (1936).
- [28] J. C. Slater, *Phys. Rev.* **49**, 931 (1936).
- [29] E. C. Stoner, *Proceedings of the Royal Society of London. Series A, Mathematical and Physical Sciences* **165**, pp. 372 (1938).
- [30] V. Korenman, J. L. Murray, and R. E. Prange, *Phys. Rev. B* **16**, 4032 (1977).
- [31] H. Capellmann, *Zeitschrift für Physik B Condensed Matter* **34**, 29 (1979).
- [32] H. Hasegawa, *Journal of the Physical Society of Japan* **46**, 1504 (1979).
- [33] R. E. Prange and V. Korenman, *Phys. Rev. B* **19**, 4691 (1979).
- [34] A. J. Pindor, J. Staunton, G. M. Stocks, and H. Winter, *Journal of Physics F: Metal Physics* **13**, 979 (1983).
- [35] M. Bode, M. Getzlaff, S. Heinze, R. Pascal, and R. Wiesendanger, *Applied Physics A: Materials Science & Processing* **66**, S121 (1998-03-01).
- [36] M. Getzlaff, M. Bode, S. Heinze, R. Pascal, and R. Wiesendanger, *Journal of Magnetism and Magnetic Materials* **184**, 155 (1998).
- [37] M. Donath, B. Gubanka, and F. Passek, *Phys. Rev. Lett.* **77**, 5138 (1996).
- [38] E. Weschke, C. Schüssler-Langeheine, R. Meier, A. V. Fedorov, K. Starke, F. Hübinger, and G. Kaindl, *Phys. Rev. Lett.* **77**, 3415 (1996).
- [39] K. Maiti, M. C. Malagoli, A. Dallmeyer, and C. Carbone, *Phys. Rev. Lett.* **88**, 167205 (2002).
- [40] U. Bovensiepen, *J. Phys.: Cond. Matter* **19**, 083201 (2007).
- [41] See Supplemental Material at [URL will be inserted by publisher] for a decomposition of the fit.
- [42] See Supplemental Material at [URL will be inserted by publisher] for the corresponding spin-resolved photoemission intensities.
- [43] A. Weber, F. Pressacco, S. Günther, E. Mancini, P. M. Oppeneer, and C. H. Back, *Phys. Rev. B* **84**, 132412 (2011).
- [44] L. M. Sandratskii, *Phys. Rev. B* **90**, 184406 (2014).
- [45] B. Koopmans, G. Malinowski, F. Dalla Longa, D. Steiauf, M. Fahnle, T. Roth, M. Cinchetti, and M. Aeschlimann, *Nat Mater* **9**, 259 (2010).
- [46] A. Fognini, T. U. Michlmayr, G. Salvatella, C. Wetli, U. Ramsperger, T. Bähler, F. Sorgenfrei, M. Beye, A. Eschenlohr, N. Pontius, C. Stamm, F. Hieke, M. Dell'Angela, S. d. Jong, R. Kukreja, N. Gerasimova, V. Rybnikov, A. Al-Shemmary, H. Redlin, J. Raabe, A. Föhlisch, H. A. Dürr, W. Wurth, D. Pescia, A. Vaterlaus, and Y. Acremann, *Applied Physics Letters* **104**,

032402 (2014).

[47] A. Scholl, L. Baumgarten, R. Jacquemin, and W. Eberhardt, Phys. Rev. Lett. **79**, 5146 (1997).