

Lehigh University Lehigh Preserve

Fritz Laboratory Reports

Civil and Environmental Engineering

1968

Research on plate girders at Lehigh University, discussion, IABSE, Final Report, September 1968 (68-30)

B. T. Yen

L. S. Beedle

A. Ostapenko

Follow this and additional works at: <http://preserve.lehigh.edu/engr-civil-environmental-fritz-lab-reports>

Recommended Citation

Yen, B. T.; Beedle, L. S.; and Ostapenko, A., "Research on plate girders at Lehigh University, discussion, IABSE, Final Report, September 1968 (68-30)" (1968). *Fritz Laboratory Reports*. Paper 1921.
<http://preserve.lehigh.edu/engr-civil-environmental-fritz-lab-reports/1921>

This Technical Report is brought to you for free and open access by the Civil and Environmental Engineering at Lehigh Preserve. It has been accepted for inclusion in Fritz Laboratory Reports by an authorized administrator of Lehigh Preserve. For more information, please contact preserve@lehigh.edu.

RESEARCH ON PLATE GIRDERS AT LEHIGH UNIVERSITY

Recherche sur les poutres de grandes dimensions
a ame mince a L'Universite de Lehigh

Forschungsarbeit an Blechträgern an der Lehigh University

ALEXIS OSTAPENKO

BEN T. YEN

LYNN S. BEEDLE

Discussion of "Thin-Walled Deep Plate Girders"

by Professor Charles Massonnet

Theme IIc

1. INTRODUCTION

The purpose of this discussion is to report on the most recent work which is currently in progress at Lehigh University and on some of the results obtained. Particular areas which will be discussed and which are in addition to and will supplement the presentation by Mr. Massonnet⁽¹⁾ are:

1. Edge loading - girders with loads applied to the compression flange between transverse stiffeners (Item 11 of the research problems proposed by M. Massonnet).
2. Ultimate strength of unsymmetrical plate girders.
3. Fatigue strength of plate girders (Item 2).

2. EDGE LOADING

Quite often the question arises in design as to whether a bearing stiffener is needed when the loads are relatively small. This problem becomes important not only for service loads, but also for erection loads, when for example the girder must be rolled out as a cantilever. Figure 1 shows a typical girder with a web panel under stresses due to bending moment M , shear V , and the edge loading q . Theoretical analysis of the buckling strength of a plate girder web subjected to an edge loading has been performed recently by Wilkesmann,⁽²⁾ Klöppel and Wageman,⁽³⁾ Warkenthin,⁽⁴⁾ and Kawano and Yamakoshi.⁽⁵⁾ In all these solutions the

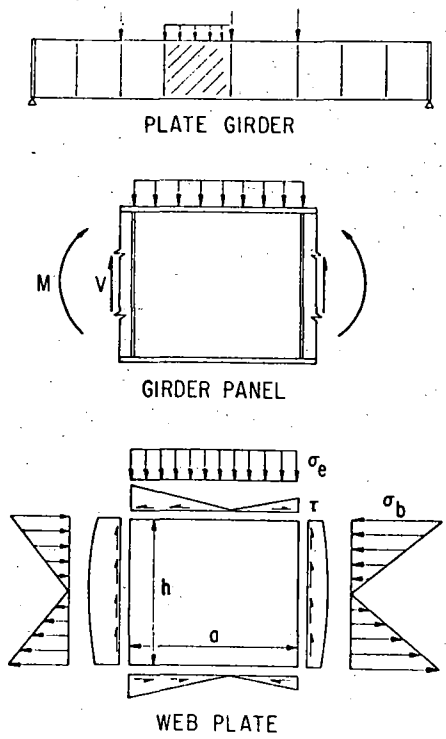


Figure 1

edges of the plate were assumed to be simply supported. Basler proposed a simplified buckling analysis considering the top edge of the web to be simply supported or fixed.⁽⁶⁾ However, neither the effect of bending nor of shear was included. Basler's approach was later incorporated in the Specification of the American Institute of Steel Construction.⁽⁷⁾

Normally the ultimate strength of plates is substantially greater than the buckling strength; but, in general, there is no direct relationship between these two quantities. Since all previous work on edge loaded web has been concerned only with the elastic buckling strength, a series of tests was conducted at Lehigh University to investigate the ultimate strength and to arrive at a method of evaluating it.⁽⁸⁾

The theoretical buckling stress was computed by means of the finite difference method. The web plate was assumed to be fixed at the flanges and simply supported at the stiffeners. This assumption is based on the observations of the web behavior during tests on plate girders of ordinary proportions. Figure 2 gives the buckling coefficient K as a function of the aspect ratio, $\alpha = a/h$, and the bending stress ratio σ_b/σ_e . The bending stress is seen to have a pronounced effect on the value of the buckling coefficient and thus on the critical edge stress.

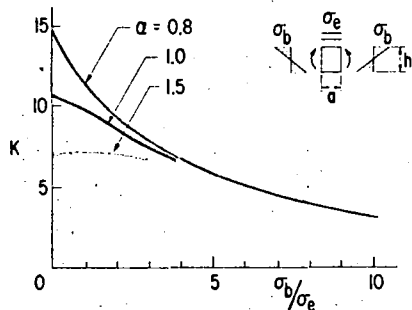


Figure 2

Ten tests were conducted on three plate girder specimens. The principal parameters were:

1. Aspect ratio a/h which varied from 0.8 to 1.6.
2. The ratio of the bending stress to the edge stress, σ_b/σ_e ,

which varied from 0 to 5.0.

The edge loading consisted of two to four concentrated loads spread over the compression flange through 1.5 inch thick plates to simulate uniform distribution.

The ultimate strength from the tests is plotted non-dimensionally in Fig. 3. It is remarkable that the plotted points lie in a relatively

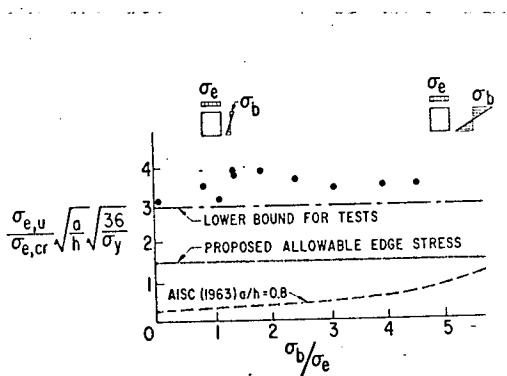


Figure 3

narrow band seemingly independent of the bending stress ratio σ_b/σ_e . A horizontal line passing through the ordinate equal to 3.0 is seen to give a conservative estimate of the ultimate strength. It follows then that the ultimate strength can be approximated fairly well from the buckling strength. The resulting equation for the allowable intensity of the edge stress σ_a , with a factor of safety against the ultimate strength equal to 2.0, is shown in Fig. 3 by the light horizontal line.

$$\sigma_a = \frac{\sigma_{e,u}}{\text{F.S.} = 2.0} = \frac{4000}{(d/t)^2 \sqrt{a/h}} \sqrt{\frac{36}{\sigma_y}} K \quad (\text{ksi})$$

where

- h = girder depth
- t = web plate thickness
- a = distance between transverse stiffeners
- σ_y = yield stress of the web plate in ksi
- K = buckling coefficient

Pending results of an analytical study and additional tests, this formula is subjected to the following limitations: $34 \text{ ksi} < \sigma_y < 45 \text{ ksi}$; $240 < h/t < 300$; $\sigma_b/\sigma_e < 5$; $0.8 < a/h < 2.0$.

For comparison, the dashed curve in Fig. 3 gives the allowable edge stress according to the American Institute of Steel Construction Specification ($a/h = 0.8$, loaded edge fixed). Although quite conservative, this curve leads to a reduction of the margin of safety with an increasing bending stress.

3. UNSYMMETRICAL GIRDERS

Most prior research on the ultimate strength of plate girders has been concerned with symmetrical members, that is, girders with the centroidal axis at the mid-depth, such as the cross section in Fig. 4(a).^(9, 10, 11, 12) However, many plate girders are unsymmetrical in the sense that

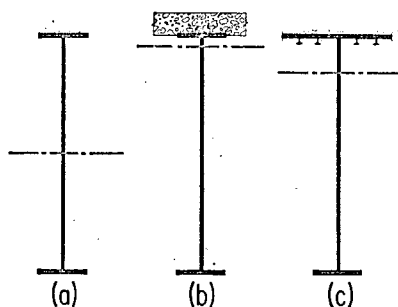


Figure 4

they have unequal flanges and their centroidal axis is close to the larger flange, for example, composite and orthotropic deck girders shown in Figs. 4(b) and 4(c). Designing such girders as symmetrical members would lead to results that are either overconservative or unconservative depending on whether the larger portion of the web is in tension or in compression. Currently, a study is being conducted at Lehigh University on the ultimate strength of unsymmetrical plate girders subjected to bending, shear, and a combination of bending and shear.

The experimental phase of the study consisted of fourteen tests conducted on four plate girders with transverse stiffeners.^(13, 14) One flange had approximately double the area of the other flange.

In the new method of analysis developed as part of the theoretical work, the ultimate strength of a plate girder panel is assumed to be controlled principally by the following three contributions shown schematically in Fig. 5:

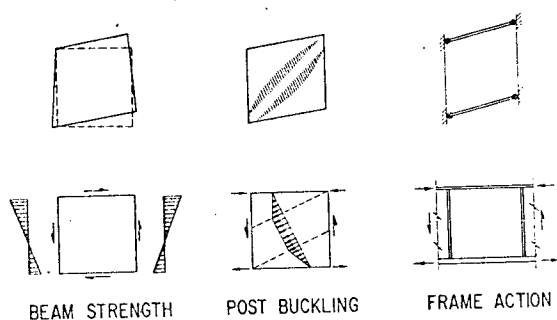


Figure 5

- a) Beam strength up to the point at which web buckling would theoretically occur,
- b) Post-buckling strength of the web, and,
- c) Frame action which is based on the formation of a panel mechanism with plastic hinges in the flanges.

An interaction relationship between moment and shear for a typical plate girder panel is shown in Fig. 6. The non-dimensionalizing values are the ultimate capacity in shear V_u and the ultimate bending capaci-

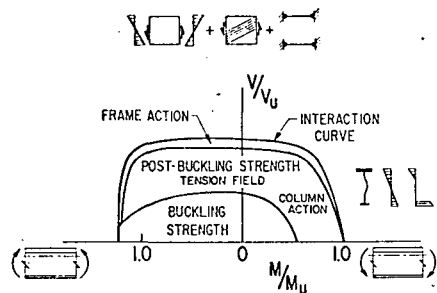


Figure 6

ty M_u , a moment which acts to produce compression in the larger portion of the web. To the right is the interaction plot for a loading condition when a larger portion of the web is in compression and to the left is the interaction plot for a loading condition when a larger portion of the web is in tension. The ultimate strength is seen to be different for these two cases.

The buckling strength (called beam strength in Fig. 5) is obtained for a combination of shearing and bending stresses assuming the web plate to be fixed at the flanges and simply supported at the stiffeners. It represents the upper limit of ordinary beam action.

The post-buckling strength of the web is developed differently in shear and in bending. In shear, it means a tension field assumed to be of the pattern shown in Fig. 5. In bending it means redistribution of the additional web stresses toward the compression flange.

The frame action contributes to the shear capacity by developing a panel mechanism with plastic hinges in the flanges. A portion of the web equal to 20 times the thickness is considered to be part of the flange and the axial flange force is included in the evaluation of the plastic moments.

The ultimate strength in shear is given as a sum of all three contributions as shown in the top sketch of Fig. 6.

The ultimate strength on pure bending is limited by the buckling capacity of the compression flange or the yielding of the tension flange with a portion of the web. Shear reduces the bending strength by contributing to the flange forces through the development of a full or partial tension field and frame mechanism.

The effect of the location of the centroidal axis on the mode of failure of a girder panel under pure bending is depicted in Fig. 7. Fixed values for this plot are the yield stress, the bracing spacing for the compression flange, and the ratio of the compression flange area to the web area. Compression flange failure is to be expected in the region

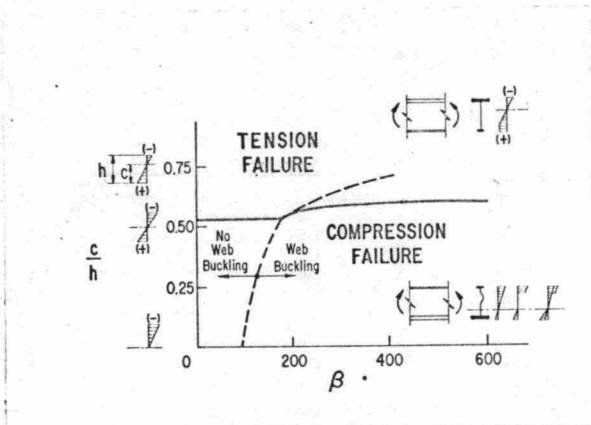


Figure 7

below the heavy solid line whereas tension flange yielding would be expected above that line. The dashed line separates the regions in which the web will buckle or will not buckle before the ultimate panel strength is reached.

The method is compared with the available test results in Fig. 8. Symmetrical and unsymmetrical girders are grouped separately for each of the loading cases: shear, combined bending and shear, and bending. The average agreement is within 5 percent with the maximum deviation being approximately 12 percent.

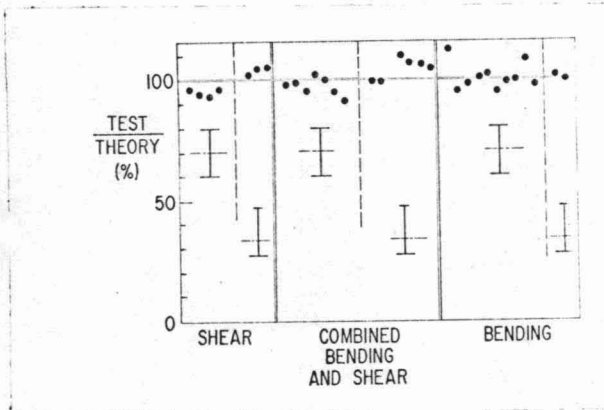


Figure 8

The method has also been extended to girders with one longitudinal stiffener and the correlation with test results is within the same range.

4. FATIGUE

A special problem arises in "thin-walled" plate girders, because of web deflection. Figure 9 shows exaggerated deformation in a panel as accentuated by painted black lines. Under repeated loading, a web plate moves back and forth, and fatigue cracks occur at the boundaries.^(15,16,17)

The most probable locations of the fatigue cracks are compared with the contours of the web deflection in Fig. 10. Crowding of contours indicates high curvature, hence high plate bending stress and thus the possibility of a fatigue crack.

A preliminary analysis has been made, and Fig. 11 gives an example of the results.⁽¹⁸⁾ The web panel of a test girder



Figure 9

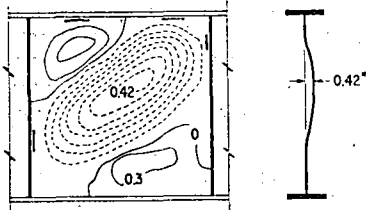


Figure 10

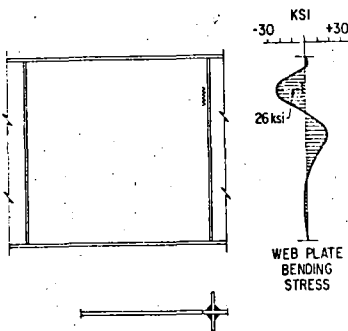


Figure 11

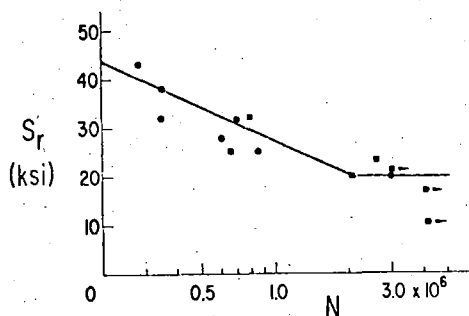


Figure 12

is shown with a fatigue crack at the toe of the web fillet weld. The web plate bending stresses have been estimated from web deflections measured under load, and Fig. 11 shows that the crack occurred at the point of highest stress.

The results of all fatigue tests for which deflection data are available are shown in Fig. 12. The relationship is a typical S-N curve between the range of variation of web plate bending stress and the number of load applications that were needed to develop a crack.

Generally speaking, large web deflections generate large stresses and thus lead to early cracks. If the web deflections are small, the corresponding stresses are small; and there is a run-out.

Based on these results, limits of web plate bending stresses and web deflections are being established. Two "proof" girders, designed according to preliminary rules, have endured at least 2,000,000 cycles without cracks.

5. CONCLUDING REMARKS

It is the eventual objective of the Lehigh research to develop design recommendations for symmetrical and unsymmetrical girders, both transversely and longitudinally stiffened, taking advantage of the most recent findings both in the United States and from abroad.

REFERENCES

1. Massonnet, Charles
THIN WALLED DEEP PLATE GIRDERS, International Association for Bridge and Structural Engineering, Preliminary Publication, 8th Congress, Theme II C, New York, 1968
2. Wilkesmann, F. W.
STEGBLECHBEULUNG BEI LAENGSRANDBELASTUNG, Stahlbau (October, 1960)
3. Klöppel, K. and Wagemann, C. H.
BEULEN EINES BLECHES UNTER EINSEITIGER GLEICHSTRECKENLAST, Stahlbau (July, 1964)
4. Warkenthin, W.
ZUR BEURTEILUNG DER BEULSICHERHEIT QUERBELASTETER STEGBLECHFELDER, Stahlbau (January, 1965)
5. Kawana, K., and Yamakoshi, M.
ON THE BUCKLING OF SIMPLY SUPPORTED RECTANGULAR PLATES UNDER UNIFORM COMPRESSION AND BENDING, Journal of the Society of Naval Architects of West Japan, Vol. 29 (1965)
6. Basler, K.
NEW PROVISIONS FOR PLATE GIRDER DESIGN, National Engineering Conference Proceedings, AISC, 1961
7. American Institute of Steel Construction
SPECIFICATION FOR THE DESIGN, FABRICATION, AND ERECTION OF STRUCTURAL STEEL FOR BUILDINGS, AISC, New York, 1963
8. Bossert, T. W., and Ostapenko, A.
BUCKLING AND ULTIMATE LOADS FOR PLATE GIRDER WEB PLATES UNDER EDGE LOADING, Fritz Engineering Laboratory Report No. 319.1, Lehigh University, June 1967
9. Basler, K., Yen, B. T., Mueller, J. A., and Thürlimann, B.
WEB BUCKLING TESTS ON WELDED PLATE GIRDERS, Welding Research Council Bulletin No. 64, September 1960
10. Lew, H. S., and Toprac, A. A.
RESEARCH ON THE STATIC STRENGTH OF HYBRID PLATE GIRDERS, Structures Fatigue Research Laboratory, Tech. Rept. P 550-11, University of Texas, Austin, January 1968
11. Fujii, Tokio
MINIMUM WEIGHT DESIGN OF STRUCTURES BASED ON BUCKLING STRENGTH AND PLASTIC COLLAPSE (3rd Report), Journal of the Society of Naval Architects of Japan, Vol. 122 (1967)
12. Association of Western Japan for Research on Bridges, Steel Buildings, and Welding
THEORETICAL AND EXPERIMENTAL WORK ON THE ULTIMATE STRENGTH OF PLATE GIRDERS (In Japanese), Osaka, July 1965

13. Dimitri, J. R., and Ostapenko, A.
PILOT TESTS ON THE ULTIMATE STATIC STRENGTH OF UNSYMMETRICAL
PLATE GIRDERS, Fritz Engineering Laboratory Report No.
328.5, June 1968
14. Schueller, W., and Ostapenko, A.
STATIC TESTS ON UNSYMMETRICAL PLATE GIRDERS--MAIN TEST
SERIES, Fritz Engineering Laboratory Report No. 328.6,
September 1968
15. Yen, B. T., and Mueller, J. A.
FATIGUE TESTS OF LARGE-SIZE WELDED PLATE GIRDERS, Welding
Research Council Bulletin No. 118, November 1966
16. Goodpasture, D. W., and Stallmeyer, J. E.
FATIGUE BEHAVIOR OF WELDED THIN WEB GIRDERS AS INFLUENCED BY
WEB DISTORTION AND BOUNDARY RIGIDITY, Structural Research
Series No. 328, University of Illinois, August 1967
17. Lew, H. S., and Toprac, A. A.
FATIGUE STRENGTH OF HYBRID PLATE GIRDERS UNDER CONSTANT
MOMENT, Highway Research Record 167, 1967
18. Mueller, J. A., and Yen, B. T.
GIRDER WEB BOUNDARY STRESSES AND FATIGUE, Welding Research
Council Bulletin No. 127, January 1968

SUMMARY

Current topics of research on plate girders and some of the findings are discussed. A formula is proposed for the ultimate capacity of a girder panel subjected to edge loading and bending moment; it is based on an elastic buckling analysis and ultimate strength tests. Ultimate strength of unsymmetrical plate girders is given by the sum of the beam action, post-buckling strength, and frame action; the theory is in good agreement with test results. Occurrence of fatigue cracks in plate girder web is dependent on the lateral web deflections and can be controlled by limiting the web slenderness ratio.

RESUME

Cet article présente, les recherches en cours, ainsi que quelques résultats obtenus sur les poutres de grandes dimensions à âme mince. Une formule est proposée pour la charge de ruine d'un panneau d'âme de poutre située entre deux raidisseurs assujetti à une charge répartie agissant sur la semelle supérieure. Elle est basée sur l'analyse élastique du voilement, et sur la charge de ruine obtenus lors des essais. La charge de ruine des grandes poutres à âmes minces est donnée comme étant la superposition d'une action de flexion, de l'effet du voilement postcritique, et d'un mécanisme de panneau; la théorie concorde bien avec les résultats d'essais. L'apparition de fissures dues à la fatigue dans l'âme des poutres dépend de la flexion latérale de l'âme et peut être anticipé en limitant l'élan-cement de l'âme.

ZUSAMMENFASSUNG

Die Themen und einige Ergebnisse der gegenwärtigen Forschung auf dem Gebiet der Blechträger werden erörtert. Eine Formel für die Traglast von Stegblechfeldern unter Längsrandbelastung und Biegung ist vorgeschlagen. Diese Formel basiert auf der elastischen Beultheorie sowie auf Ergebnissen von Traglastversuchen. Die Traglast von unsymmetrischen Blechträgern wird aus der Balkenwirkung, der Überkritischen Tragfähigkeit und der Rahmenwirkung zusammengesetzt angenommen; diese Theorie stimmt mit Versuchsergebnissen gut überein. Das Auftreten von Ermüdungsrissen im Steg ist von der Stegdurchbiegung abhängig und kann durch eine Begrenzung der Steg-schlankheit verhindert werden.

327.9
8/7/68

RESEARCH ON PLATE GIRDERS AT LEHIGH UNIVERSITY

By Alexis Ostapenko
Bung-Tseng Yen
Lynn S. Beedle

Discussion of "Thin-Walled Deep Plate Girders"
by Professor Charles Massonnet

It is a pleasure to respond to the excellent paper by my friend, Professor Charles Massonnet with a review of additional work at Lehigh University. It is being carried out under the immediate direction of my colleagues, Professor A. Ostapenko and Professor B. T. Yen.

Slide (A1)

This slide shows four phases of the work currently underway:

- a) Edge loading
- b) Unsymmetrical girders
- c) Fatigue
- d) Design recommendations

My remarks are about the first three of these.

EDGE LOADING

What is the influence of edge loading?

Slide (B4-1)

These are theoretical buckling curves in which the buckling coefficient, K , is plotted against the bending stress ratio for three values of aspect ratio ($\alpha = a/h$). The top edge of the web is assumed to be fixed.

It is seen that the edge buckling stress is considerably reduced by bending stress.

Slide (B6)

Tests were conducted to determine the difference between the ultimate strength and buckling strength and to aid in developing an analysis.

This slide shows the results of tests for one α -value (0.8) plotted in comparison with the theoretical buckling stress.

The experimental ultimate stress appears to have a constant ratio to the buckling stress.

A line is plotted at $3 \times \sigma_{cr}$ to accentuate this proportionality.

Slide (B7)

All ten test points, non-dimensionalized with respect to σ_{cr} , α , and σ_y , are seen to fall in a relatively narrow band, seemingly independent of the bending stress ratio.

Slide (B7-2)

Shown here is a possible design formula using a load factor of 2.0. In comparison is the AISC provision (1963) for $\alpha = 0.8$.

UNSYMMETRICAL GIRDERS

Slide (C1)

Many plate girders have unequal flanges. Examples are composite girders and those with orthotropic decks--where the neutral axis is closer to the larger flange.

Current studies are exploring the effect of neutral axis position.

Slide (C2)

A new and more general theory has been developed, taking into account:

- a) Beam strength up to the point of buckling,
- b) Post-buckling strength of the web, and,
- c) Frame action

In the latter instance a panel mechanism forms with plastic hinges in the flanges.

Slide (C3-1)

Results of this analysis are illustrated in this plot of

$$\frac{V}{V_u} \text{ vs } \frac{M}{M_{uc}}$$

for a particular unsymmetrical girder. To the right is the shear-moment interaction with the web more in compression. To the left is the shear-moment interaction with the web more in tension.

First is the buckling strength. It is the upper limit of ordinary beam action.

Slide (C3-2)

Next is the post-buckling strength of the web. In shear this means tension-field action. In bending it means redistribution of web stresses (after buckling) to the compression flange.

Slide (C3-5)

Finally comes the effect of frame action. The influence is rather modest and has its maximum effect is pure shear with the development of a panel mechanism and four plastic hinges.

Slide C4

What is the effect of location of the neutral axis--and of web slenderness?

To the left of the line there is no web buckling. In the lower region (to the right) is the zone of compression flange failure. In the upper region failure involves plastic yield of the flange.

Slide (C5)

Most of the available tests results are shown here in comparison with the proposed theory. It is a table in graphical form arranged in four groups:

- 1) Shear
- 2) Shear and bending
- 3) Bending, and
- 4) Symmetrical and unsymmetrical girders

The correlation is within about 5%.

FATIGUESlide (D1)

A special problem arises in "thin-walled" plate girders. Because of web deflection, fatigue cracks develop on the boundaries.

This photo shows the deformation in a panel as accentuated by painted black lines.

Slide (D3)

The cracks occur at the boundaries due to lateral movement under combined shear and bending. These are the typical locations of cracks.

Slide (D4)

If we draw in the contours of the web deflection, we find that cracks occur at the most probable locations. Crowding of contours means high curvature--which means high plate bending stress--which means cracking (if stress is high enough and cycles large enough).

Slide (D5)

An attempt at an analysis has been made and this is an example of the result. A web panel is shown with a fatigue crack. The crack occurs at the toe of the web fillet weld. The web plate bending stresses have been computed from web deflections measured under load. The plot at the right shows that the crack occurs at the point of highest stress.

Slide (D6)

Shown in this slide are the results of all fatigue tests for which deflection data are available. The range of variation in web plate bending stress is plotted against the number of load applications to crack. The solid line is from a least squares analysis.

We learn from this slide that:

- 1) Results show the typical fatigue relationship,
- 2) The scatter is within reasonable limits, and,
- 3) There is run-out if the stress is small (web deflection is small).

Slide (D7)

Based on these studies, two "proof" girders were designed. The first was tested without cracks up to $N = 2,200,000$ cycles.. The second girder will be tested shortly.

CONCLUDING REMARK

It is our eventual objective to develop design recommendations for symmetrical and unsymmetrical girders, both transversely and longitudinally stiffened, taking advantage of the most recent findings both here in the United States and from abroad.