



# Journal of Advanced Research in Fluid Mechanics and Thermal Sciences

Journal homepage: [www.akademiabaru.com/arfmts.html](http://www.akademiabaru.com/arfmts.html)  
ISSN: 2289-7879



## Oxygen Separation Process using Ceramic-Based Membrane: A Review

Open Access

Fatin Nurwahdah Ahmad<sup>1</sup>, Norazlianie Sazali<sup>1,2,\*</sup>, Safwan Shalbi<sup>1</sup>, Nor Hasrul Akhmal Ngadiman<sup>3,♣</sup>, Mohd Hafiz Dzarfan Othman<sup>4</sup>

<sup>1</sup> Faculty of Mechanical Engineering, Universiti Malaysia Pahang, 26600 Pekan, Pahang, Malaysia

<sup>2</sup> Centre of Excellence for Advanced Research in Fluid Flow (CARIFF), Universiti Malaysia Pahang, Lebuhraya Tun Razak, 26300 Gambang, Kuantan, Pahang, Malaysia

<sup>3</sup> School of Mechanical Engineering, Faculty of Engineering, Universiti Teknologi Malaysia, 81310 Skudai, Johor Darul Takzim, Malaysia

<sup>4</sup> Advanced Membrane Technology Research Centre (AMTEC), School of Chemical and Energy, Faculty of Engineering, Universiti Teknologi Malaysia, 81310 Skudai, Johor Darul Takzim, Malaysia

### ARTICLE INFO

#### Article history:

Received 28 July 2019

Received in revised form 19 August 2019

Accepted 20 September 2019

Available online 12 October 2019

#### Keywords:

Membrane technology; ceramic-based membrane; oxygen separation and selectivity

### ABSTRACT

Membrane technology is known as a cheaper alternative approach that capable to yield high purity oxygen compared to the conventional separation technologies which are pressure swing adsorption (PSA) and cryogenic distillation. The status of advanced ceramic-based membranes in the application of separating oxygen at high temperature is discussed in this paper, including arising issues related to performance in selectivity and separation of membranes. This review paper covers various approaches to solve the problems and issues of the ceramic-based membrane, also, its expected tendency in separating oxygen from the air.

Copyright © 2019 PENERBIT AKADEMIA BARU - All rights reserved

## 1. Introduction

Oxygen contributes about 21 volume percentage towards the air. Oxygen is one of the gases that extensively used globally in which it is in the top five rankings for chemicals production as it involves in various applications for most industrial sectors [1]. The oxygen separation is a very significant process in the industry in which the annual oxygen production is about hundred million tonnes [2]. For the reason that every large-scale and clean energy technologies need feed gas (oxygen), oxygen gas is expected to receive increasing demands soon [3,4]. The high demand for operations of the chemical process requires a great capacity of oxygen such as the process of oxygen-blown gasification and oxyfuel combustion. Oxygen is required in converting natural gas and coal to form intermediate synthesis gas which will be processed for electricity and chemical products including fuel


\* Corresponding author.

E-mail address: [melya.jandi@yahoo.com](mailto:melya.jandi@yahoo.com) (Norazlianie Sazali)

♣ Corresponding author.

E-mail address: [norhasrul@utm.my](mailto:norhasrul@utm.my) (Nor Hasrul Akhmal Ngadiman)

transportation [5]. There are two conventional technologies in separating desired gas from air called cryogenic distillation and non-cryogenic distillation. By comparing both technologies, cryogenic distillation is more preferable for the production of oxygen in a large quantity at ultra-low temperature as illustrated in Figure 1 [6]. Whereas, non-cryogenic distillations are either pressure swing adsorption (PSA) involving separating air at ambient temperatures by passing through molecular sieve adsorptions, or membrane technology which involves gas separation via polymeric membranes [7]. Nowadays, membrane technology is a leading separation method as this technology is capable of fast process operation with energy-efficient and involves no chemical additives and changes of phase [42]. This technology has been implemented in various sectors, for example, chemical and food industries [43,44]. The implementation of membrane is not only because it is economically excellent about 30% compared to other technologies, but also due to its ability for the reduction of waste disposal by allowing material to be recycled and recovered as required by regulation of environment [41].

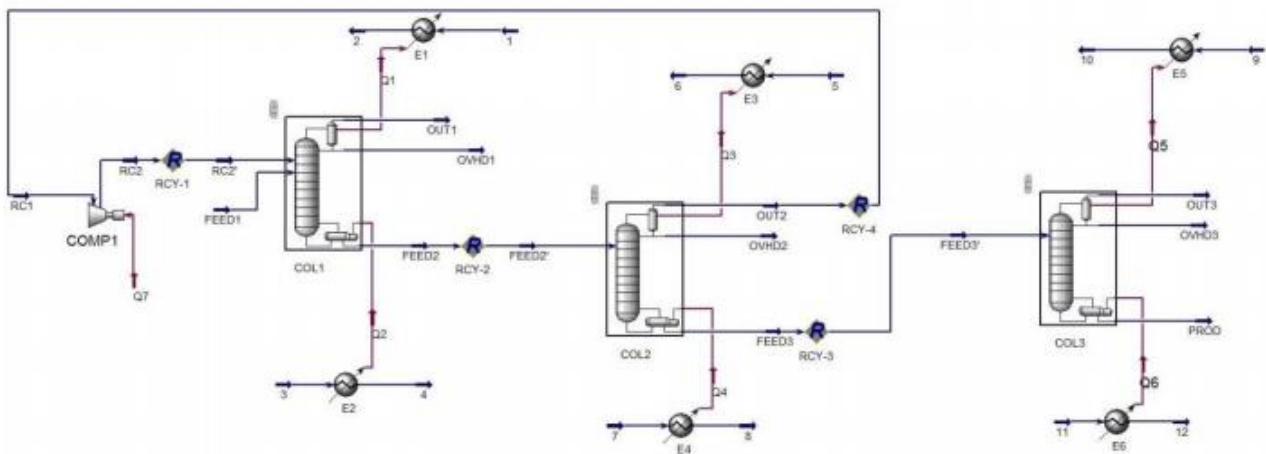

**Fig. 1.** Process flow diagram of oxygen-18 production using cryogenic oxygen distillation [6]

Besides, the study of membrane technology is increasing which produces various findings related to precursors that are suitable for the gas separation process [8-10]. One of the materials is specialized ceramic membranes that are capable of oxygen separation process at an arising temperature which is different compared to cryogenic distillation where the super-cooled temperature is required. These innovative ceramic-based membranes separate oxygen from the air at an arising temperature in the range between 800 up to 900 °C. The ceramic membranes which have high solvents and chemical resistance, high mechanical strength and stability, also long term durability causes them to be preferable [41]. The acronyms for high-temperature ceramic membranes that typically used are Oxygen Transport Membranes (OTM), Ion Transport Membranes (ITM) and Mixed Ionic Electronic Conducting (MIEC) which will be used in this paper. Various scientific publications regarding this study have been made in the early 2000s up to now showing there is high attention has been given in this research field [11]. A review has been done by Sunarso *et al.*, for the last three decades, on the development of dense ceramic-based membranes focusing on separating oxygen using mixed ionic-conducting ceramic membranes [12]. The development of ion transport membranes (ITM) in gas separation, specifically for separation of oxygen from the air has been discussed in a chapter of a book published by Bose *et al.*, [13]. The changes of oxygen permeation flux by modifying mixed ionic-electron materials has been emphasized in several publications such as Yang *et al.*, have reviewed the developments and issues of perovskite-type ceramic membrane including their applications in SOP, POH, POM, OCM, and SOE [14]. Since ceramic-based membranes have shown their potential to

separate oxygen from the air, the objective of this study is to review the advancement of ceramic-based membranes in separating oxygen from air under high temperature including the challenges in the context of separation and selectivity in membrane performance also, various methods to counter the challenges. This paper covers the potential of ceramic-based membranes for oxygen separation applications and to be commercially marketed in the industry shortly.

## 2. Implementation of Ceramic-Based Membranes in Separating Oxygen

Researches focusing on the development and enhancement of ceramic-based membranes at high temperatures has been done for oxygen applications in the past years. There are two categories of oxygen separation systems using ceramic-based membranes which are pure oxygen conducting membranes and impure oxygen conducting membranes. Pure oxygen conducting membranes use solid electrolytes that create an electron pathway in the presence of electrodes [15]. Its major advantage compared to impure oxygen conducting membranes is the ability to control the generation of oxygen through the electric current application. Impure oxygen conducting membranes or also commonly known as mixed ionic-electronic conducting membranes which can operate without the presence of electrodes and an external circuit. Even though the partial pressure gradient of oxygen involved in this system where oxygen permeates from higher partial pressure side oxygen to lower partial pressure side oxygen, its conductivity of electrons acts as an internal short circuit [16]. The neutrality of charge is controlled by neutralizing the electrons' flux. The advantage of using this system is its capability to produce high purity oxygen. The combination of ceramic materials and mixed ionic-electronic conducting characteristics commonly produce well-defined phase structures fabricated from precursors such as perovskite, brownmillerite, fluorite and other corresponding materials [17]. Perovskite and fluorite are the best materials among other combinations of ceramic membranes and mixed ionic-electronic conducting characteristics in terms of permeation properties for oxygen. This paper is focusing on the combination of perovskite and ceramic membranes with the highest permeability that shows good potential to be enhanced in the future [3,18].

The ceramic-based membrane is considered as a new approach compared to the cryogenic distillation approach to separate oxygen from the air to supply for fuel production and power generation usage such as coal gasification systems, production of syngas and oxyfuel combustion process. The most significant criteria for membrane-based separation involving high temperatures under high oxygen flux are comprehensively strong, stable, and high creep-resistant [19]. Therefore, the membrane performance needs to be improved under reducing and oxidizing conditions by doing research and development (R&D) widely. Since a large amount of oxygen is needed in the industry, efforts in developing appropriate demonstration-scale projects need to be performed at practical operating conditions. A project called MEM-BRAIN is carried out with the aim to combine the skills and knowledge of scientists and engineers to improve the performance of membranes, to specify targets in developing the system of the membrane and to determine the technical specifications for optimum operation. Research and development work should be done extensively to obtain clear identification for optimum membrane enhancement allowing applications in a long-term and reduced operation time [20,21]. Membrane surface area is the most important factor to be controlled as reduces in differential oxygen partial pressure will increase the surface area that causes increases in oxygen recovery rate. Monolithic tubes, honeycomb structures, planar arrangements, and hollow fiber membranes are the convenience conceptual alternatives [5]. The previous study by Tablet *et al.*, recommended a hollow fiber membrane has high flux properties and high packing density. The engineering parameters for scaling up need to be considered in hollow fiber membrane

usage since they are fragile and complex to be sealed [22]. Vente *et al.*, have performed research on designing scale-up modules to separate oxygen resulting that tubes are preferable compared to flat plate multi-channel monoliths or hollow fibers [23]. Companies such as Air Products and Chemicals has used flat membranes with wafer configuration module in developing ion transport membrane with operating temperature 800 °C to 900 °C [24]. The combination of the composite multi-channel heat exchanger and membrane modules in extruded ceramics has been developed by Hashim and co-workers under operating temperatures which is around 1300 °C whereas tubes are used by Praxair at an operating temperature of 800 °C up to 900 °C [25]. Sealing multi-channel monoliths is a complex process especially involving small channels with the purpose of membrane surface area maximization compared to sealing single tube configurations. Glass ceramic seals which composed of boron silicate glass has been used. It requires a design that is suitable for each application and it can be extremely brittle [17,25]. Previous researcher has reviewed the material options, design of module and membrane, seal enhancement and issues related to the fabrication process [26]. Silica ceramic membrane have been synthesized by Nor *et al.*, using the method of sol-dip coating. In the research, variety number of silica sol dipping are used in which resulting conversion of rough surface into a smoother surface and ceramic support pore size is reduced [41].

### 3. Current Challenges and Future Prospect of Ceramic Based Membrane

Ceramics are well-known with the high compressive strength but have lower impact strength characteristics. Those characteristics make ceramics become highly brittle and easily fracture when low force is applied [27]. The sensitivity of ceramics makes it hard to fabricate. Based on the previous study, the lower force applied on ceramics can the driving force (pressure ratio) was lower, the selectivity results were higher and the separation process said to be more appropriate; in fact, the operating costs for the separation system also lower [8]. When the permeability was higher, the cost of the system was lowered and the membrane needed to be was also small. To overcome the challenges, the mixed ceramic membrane was studied and develop. On the other hand, the ceramic membrane also faces the high weight and high cost of ceramic components.

The ceramic membranes have a bright future ahead, the use of ceramic membrane not only applicable for produced and filter pure oxygen but the ceramic membrane was a function in medical applications. Due to the corrosion problem in medical mechanical appliances such as dental implants, hip sockets, joint implants, and heart valves, ceramic biomaterials have received much attention. The development of synthetic material such as ceramic membrane with specific characteristics can be induced by advances in material sciences [27]. The ceramic membrane also is known with bacteria resistance properties, high durability, high fluxes, high abrasion resistance, mechanical, chemical and thermal stability. The application of ceramic membrane was believed can be utilized not only for medical and oxygen separation but also for various industry such as food and beverages industry, textile industry, metal industry and environmental [24,27,28]. In the food and beverage industry, the ceramic membrane can be used to sterilize the milk and whey, to purify the drinking water, to dewatering of products and the clarification of juice produced. For the textile industry, the ceramic membrane can use for desalination, separation of yeast and disposal of fat emulsions. Moreover, the ceramic membrane has a bright future in the metal industry as a platform for water/oil treatment, recovery of heavy metals and treatment of wastewater from the glass fiber production. In terms of environment, the ceramic membrane can be used for purification of the drain sewage plants. The future of ceramic membrane was very promising and applicable in the various industry [22,24].

#### 4. Significant Issues of Mixed Conducting Ceramic Membranes and Directions in Future

Issues related to mixed conducting ceramic membranes remain even though various advancements have been applied for the past decades. The issues highlighted are

- i. membranes should have extensively high oxygen permeation flux at high operational temperature
- ii. membranes are required to be stable at elevated temperature with reduced atmosphere for a long operational period
- iii. membranes are necessary to have acceptable mechanical strength
- iv. materials of the membranes must be cost-effective and
- v. involves high temperature sealing of the membranes.

Other than that, membrane stability is also an issue regarding mixed conducting ceramic membranes. High ionic conductivity membrane materials have a property of low chemical or/and mechanical stability. Perovskite-type ceramic membranes are usually composed of alkaline-earth compounds which have a very high oxygen permeation flux. However, these materials can react with gas, for example,  $\text{SO}_2$ ,  $\text{CO}_2$  or water vapor which will cause problems in terms of its long-term stability [3]. The efforts to improve its stability have been done by several researchers such as Tong *et al.*, who blends B-site cation from perovskite compounds with zirconium B-site in which showing moderate prospects for certain composition [29]. The results from the previous study conducted by Xu *et al.*, revealed that the new mixed ionic-electronic conducting compounds without cobalt causes a reduction in oxygen permeation flux [30]. Research on improvement of higher valence cations, for example, La into A also B-site cation of perovskite compounds has been carried out [31]. The result shows that there is an enhancement in membrane structure stability and reduction in electronic conductivity which reduces the oxygen permeation flux [32]. Figure 2 shows summary of synthesis methods for nanoporous metal oxide perovskites [33].

Presently, manufacturers are fabricating membranes with the thickness of the order of tens of micrometers as the relationship between oxygen permeation flux and thickness of the membrane is inversely proportional. The thin dense membrane that has structural support on the porous substrate in which functions to provide mechanical support is called an asymmetric structure. A very thin dense layer asymmetric membranes with porous support and porous substrate which usually fabricated from similar materials as the membrane may resolve these issues [34-36]. Research on changes of membrane surface having an oxide porous layer has been performed with properties of exchange kinetics in high oxygen surface [37]. Even though enhancement has been done using thick membrane configuration, the low absolute oxygen permeation flux is not suitable for practical applications due to the presence of low oxygen bulk diffusion [22,29]. The study of thin-film oxygen separation membranes with supported porous substrate shows that they are supposed to have a smaller size of pore than the top layer thickness used to allow them to have relatively high mechanical strength. Its support should have high-temperature resistance under the long-period operating temperature which will prevent them to undergo structural and chemical changes. Other than that, the top layer applied should be similar to both chemical and thermal expansion. Besides, the application of membrane gas absorption (MGA) can be used to enhance the performance of ceramic membrane by eliminating channeling and foaming issues during the process of separation takes place [44].

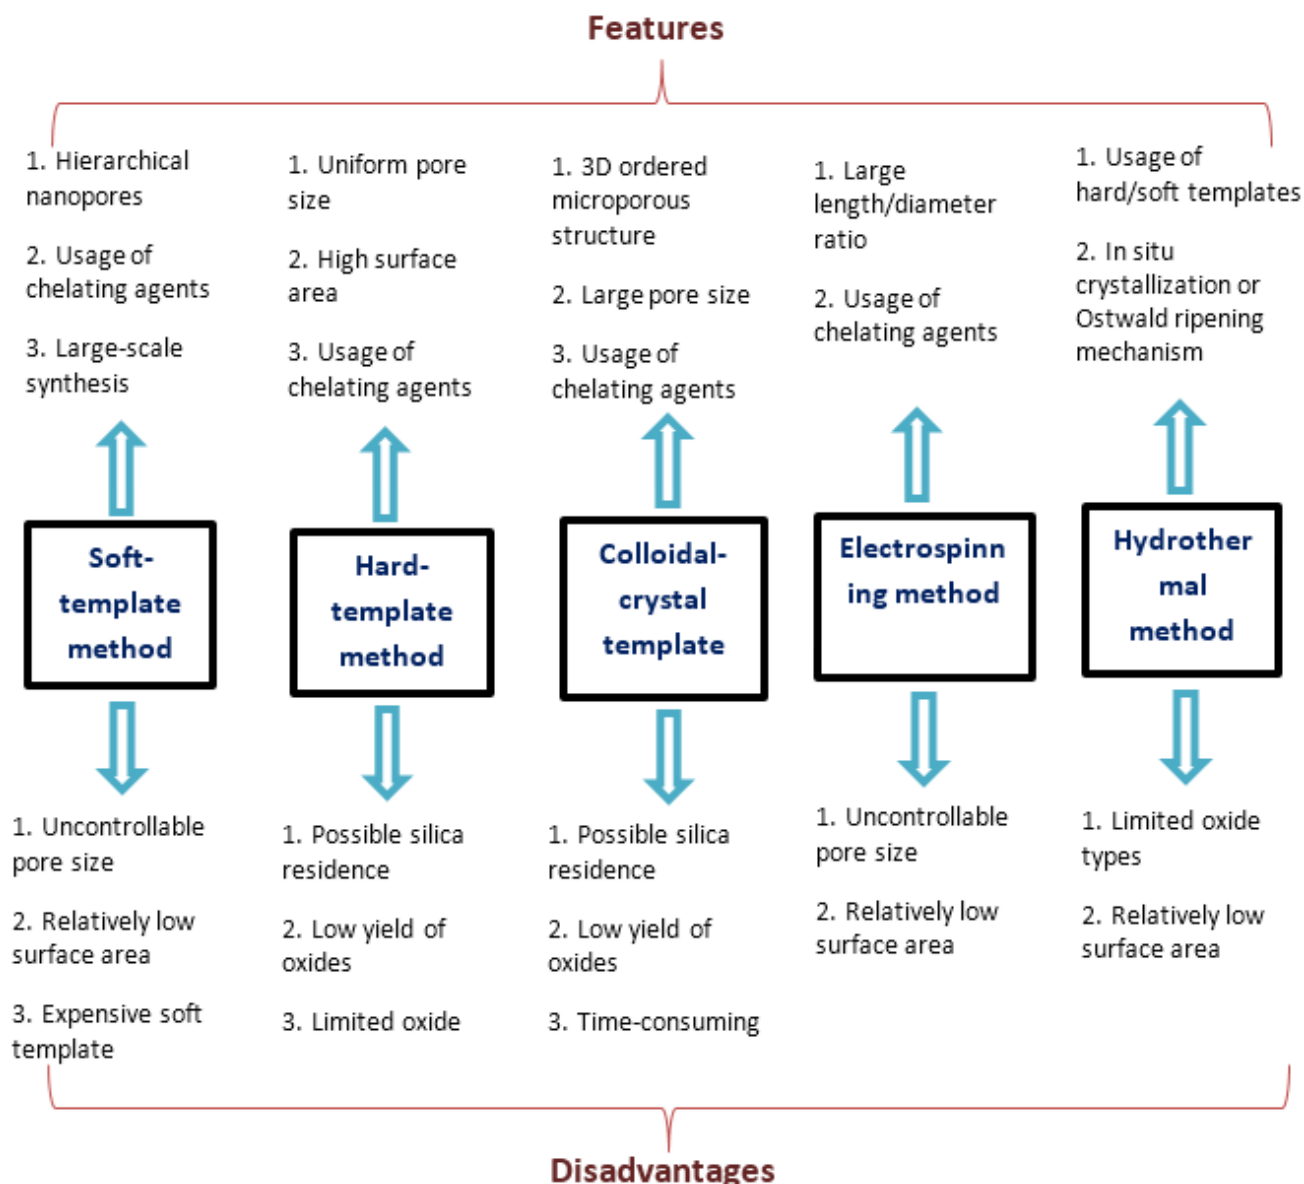


Fig. 2. Summary of synthesis methods for nanoporous metal oxide perovskites [33]

## 5. Conclusions

The ceramic-based membranes which have been enhanced for oxygen separation purposes and its potential to commercialized are already well-known globally. Several important issues such as module design, sealing, and geometry of membrane need to be considered to improve the performance of the membranes [38,39,40]. One of the interesting alternatives which shows a better quality and performance than planar, disk also tubular membranes is mixed-conducting ceramic-based hollow fiber membranes. These membranes have a large surface to volume ratio and high-temperature sealing. More research regarding perovskite-type mixed conducting membrane needs to be done on these lab scale membranes to widen its potential to be a large scale membrane for industrial applications. Even though a lot of improvements have been done on this membrane technology for oxygen separation, there are still challenges and problems that need to be considered. Therefore, studies focusing on properties of membrane especially thermal and chemical stability, geometries of membranes also sealing technology are required to be carried out. Scientific and engineering information is crucial to determine the effect of high-temperature membrane operation

on the efficiency and energy required to implement this technology to produce and separate tonnage oxygen from the air. It is expected ceramic-based membrane technology with high potential in the context of production of fuel, sustainable energy also a cleaner environment can replace the energy-intensive traditional air separation method and can be implemented for the oxygen separation process in the near future.

### Acknowledgement

The authors wish to thank the Ministry of Higher Education (MOHE), Universiti Teknologi Malaysia (UTM) and Research Management Centre, UTM for the financial support to this work through Research University Grant (RUG) funding number Q.J130000.2524.20H47. Authors would also like to extend their gratitude to University Malaysia Pahang (UMP) with grant number RDU190379.

### References

- [1] Sadykov, Vladislav A., Alexey V. Krasnov, Yulia E. Fedorova, Anton I. Lukashevich, Yulia N. Bepalko, Nikita F. Ereemeev, Pavel I. Skriabin, Konstantin R. Valeev, and Oleg L. Smorygo. "Novel nanocomposite materials for oxygen and hydrogen separation membranes." *International Journal of Hydrogen Energy* (2018).
- [2] Sazali, Norazlianie, Wan Norhayati Wan Salleh, Ahmad Fauzi Ismail, Kumaran Kadirgama, Mahendran Samykan, Gholamhassan Najafi, and Nur Izwanne Mahyon. "PI/NCC-Based Tubular Carbon Membrane: Influence of Aging Times Towards Oxygen Separation Performance." *membranes* 51, no. 2 (2018): 187-196.
- [3] Hu, Tianmiao, Hangyue Zhou, Hui Peng, and Heqing Jiang. "Nitrogen production by efficiently removing oxygen from air using a perovskite hollow-fiber membrane with porous catalytic layer." *Frontiers in chemistry* 6 (2018).
- [4] Sazali, N., W. N. W. Salleh, A. F. Ismail, N. A. H. M. Nordin, N. H. Ismail, M. A. Mohamed, F. Aziz, N. Yusof, and J. Jaafar. "Incorporation of thermally labile additives in carbon membrane development for superior gas permeation performance." *Journal of Natural Gas Science and Engineering* 49 (2018): 376-384.
- [5] Liang, Can Zeng, Wai Fen Yong, and Tai-Shung Chung. "High-performance composite hollow fiber membrane for flue gas and air separations." *Journal of Membrane Science* 541 (2017): 367-377.
- [6] Shourkaei, Meysam Akbarian, Abbas Rashidi, and Javad Karimi-Sabet. "Life cycle assessment of oxygen-18 production using cryogenic oxygen distillation." *Chinese Journal of Chemical Engineering* 26, no. 9 (2018): 1960-1966.
- [7] Dixit, Savita, Gajendra Dixit, and Vijesh Verma. "Thermal degradation of polyethylene waste and jute fiber in oxidative environment and recovery of oil containing phytol and free fatty acids." *Fuel* 179 (2016): 368-375.
- [8] Sazali, N., W. N. W. Salleh, M. Nur Izwanne, Z. Harun, and K. Kadirgama. "Precursor Selection for Carbon Membrane Fabrication: A Review." *Journal of Applied Membrane Science & Technology* 22, no. 2 (2018).
- [9] Salleh, W. N. W., and Ahmad Fauzi Ismail. "Carbon membranes for gas separation processes: Recent progress and future perspective." *Journal of Membrane Science and Research* 1, no. 1 (2015): 2-15.
- [10] Chen, Xinwei, Liang Hong, Xinling Chen, Wen Hao Au Yeong, and Wan Ki Isabel Chan. "Aliphatic chain grafted polypyrrole as a precursor of carbon membrane." *Journal of membrane science* 379, no. 1-2 (2011): 353-360.
- [11] Spallina, V., Daniele Pandolfo, A. Battistella, MATTEO CARMELO Romano, M. Van Sint Annaland, and Fausto Gallucci. "Techno-economic assessment of membrane assisted fluidized bed reactors for pure H<sub>2</sub> production with CO<sub>2</sub> capture." *Energy conversion and management* 120 (2016): 257-273.
- [12] Sunarso, J., Siti Salwa Hashim, Y. S. Lin, and S. M. Liu. "Membranes for helium recovery: An overview on the context, materials and future directions." *Separation and Purification Technology* 176 (2017): 335-383.
- [13] Bose, Susmita, Samuel Ford Robertson, and Amit Bandyopadhyay. "Surface modification of biomaterials and biomedical devices using additive manufacturing." *Acta biomaterialia* 66 (2018): 6-22.
- [14] Yang, Ying, TrungHieu Le, Feiyu Kang, and Michio Inagaki. "Polymer blend techniques for designing carbon materials." *Carbon* 111 (2017): 546-568.
- [15] HPS, A.K., Saurabh, C.K., Adnan, A.S., Fazita, M.N., Syakir, M.I., Davoudpour, Y., Rafatullah, M., Abdullah, C.K., Haafiz, M.K.M. and Dungani, R., 2016. A review on chitosan-cellulose blends and nanocellulose reinforced chitosan biocomposites: Properties and their applications. *Carbohydrate polymers*, 150, pp.216-226.
- [16] Tan, X., and K. Li. "Dense ceramic membranes for membrane reactors." In *Handbook of Membrane Reactors*, pp. 271-297. Woodhead Publishing, 2013.
- [17] Hashim, S. S., A. R. Mohamed, and S. Bhatia. "Oxygen separation from air using ceramic-based membrane technology for sustainable fuel production and power generation." *Renewable and Sustainable Energy Reviews* 15, no. 2 (2011): 1284-1293.

- [18] Sun, Zhongyu, Lei Zhang, Feng Dang, Yao Liu, Zhiying Fei, Qian Shao, Hong Lin et al. "Experimental and simulation-based understanding of morphology controlled barium titanate nanoparticles under co-adsorption of surfactants." *CrystEngComm* 19, no. 24 (2017): 3288-3298.
- [19] Belaissaoui, Bouchra, Yann Le Moullec, Hayato Hagi, and Eric Favre. "Energy efficiency of oxygen enriched air production technologies: Cryogeny vs membranes." *Separation and Purification Technology* 125 (2014): 142-150.
- [20] Ismail, N. H., W. N. W. Salleh, N. Sazali, and A. F. Ismail. "Effect of intermediate layer on gas separation performance of disk supported carbon membrane." *Separation Science and Technology* 52, no. 13 (2017): 2137-2149.
- [21] Sazali, N., W. N. W. Salleh, A. F. Ismail, K. C. Wong, and Y. Iwamoto. "Exploiting pyrolysis protocols on BTDA-TDI/MDI (P84) polyimide/nanocrystalline cellulose carbon membrane for gas separations." *Journal of Applied Polymer Science* 136, no. 1 (2019): 46901.
- [22] Tablet, Cristina, Gerd Grubert, Haihui Wang, Thomas Schiestel, Michael Schroeder, Bernd Langanke, and Jürgen Caro. "Oxygen permeation study of perovskite hollow fiber membranes." *Catalysis today* 104, no. 2-4 (2005): 126-130.
- [23] Vente, Jaap F., Wim G. Haije, Ruud Ijpelaan, and Frans T. Rusting. "On the full-scale module design of an air separation unit using mixed ionic electronic conducting membranes." *Journal of membrane science* 278, no. 1-2 (2006): 66-71.
- [24] Bernardo, Paola, Enrico Drioli, and G. Golemme. "Membrane gas separation: a review/state of the art." *Industrial & Engineering Chemistry Research* 48, no. 10 (2009): 4638-4663.
- [25] Hashim, Salwa Meredith, Abdul Rahman Mohamed, and Subhash Bhatia. "Current status of ceramic-based membranes for oxygen separation from air." *Advances in Colloid and Interface Science* 160, no. 1-2 (2010): 88-100.
- [26] Paglieri, S. N., and J. D. Way. "Innovations in palladium membrane research." *Separation and Purification Methods* 31, no. 1 (2002): 1-169.
- [27] Mohd Syafiq Sharip, Norazlianie Sazali, Ahmad Shahir Jamaludin, Muhammad Atif Mohamed Azmi, Farhana Aziz, and Wan Norharyati Wan Salleh. "Current Advancement by Membrane Technology: A Review." *Journal of Advanced Research in Fluid Mechanics and Thermal Sciences* 59, no. 2 (2019): 283-290.
- [28] Abadi, Sareh Rezaei Hosein, Mohammad Reza Sebzari, Mahmood Hemati, Fatemeh Rekabdar, and Toraj Mohammadi. "Ceramic membrane performance in microfiltration of oily wastewater." *Desalination* 265, no. 1-3 (2011): 222-228.
- [29] Tong, Jianhua, Weishen Yang, Baichun Zhu, and Rui Cai. "Investigation of ideal zirconium-doped perovskite-type ceramic membrane materials for oxygen separation." *Journal of membrane science* 203, no. 1-2 (2002): 175-189.
- [30] Xu, Dong, Feifei Dong, Yubo Chen, Bote Zhao, Shaomin Liu, Moses O. Tade, and Zongping Shao. "Cobalt-free niobium-doped barium ferrite as potential materials of dense ceramic membranes for oxygen separation." *Journal of membrane science* 455 (2014): 75-82.
- [31] Knapp, Meghan C., and Patrick M. Woodward. "A-site cation ordering in AA' BB' O6 perovskites." *Journal of Solid State Chemistry* 179, no. 4 (2006): 1076-1085.
- [32] Levin, Igor, Julia Y. Chan, Richard G. Geyer, James E. Maslar, and Terrell A. Vanderah. "Cation ordering types and dielectric properties in the complex perovskite Ca (Ca<sub>1/3</sub>Nb<sub>2/3</sub>) O<sub>3</sub>." *Journal of Solid State Chemistry* 156, no. 1 (2001): 122-134.
- [33] Huang, Xiubing, Guixia Zhao, Ge Wang, and John TS Irvine. "Synthesis and applications of nanoporous perovskite metal oxides." *Chemical science* 9, no. 15 (2018): 3623-3637.
- [34] Krzysztoforski, Jan, and Marek Henczka. "Porous membrane cleaning using supercritical carbon dioxide. Part 1: Experimental investigation and analysis of transport properties." *The Journal of Supercritical Fluids* 136 (2018): 12-20.
- [35] Lee, Pyung-Soo, Daejin Kim, Seung-Eun Nam, and Ramesh R. Bhave. "Carbon molecular sieve membranes on porous composite tubular supports for high performance gas separations." *Microporous and Mesoporous Materials* 224 (2016): 332-338.
- [36] Wang, Chan, Lin Ling, Yan Huang, Yagang Yao, and Qijun Song. "Decoration of porous ceramic substrate with pencil for enhanced gas separation performance of carbon membrane." *Carbon* 84 (2015): 151-159.
- [37] Chen, Pei, Xinbing Chen, Xiangshu Chen, Zhongwei An, and Hidetoshi Kita. "Pervaporation Separation and Catalysis Activity of Novel Zirconium Silicalite-1 Zeolite Membrane." *Chinese Journal of Chemistry* 27, no. 9 (2009): 1692-1696.
- [38] Ismail, N. H., W. N. W. Salleh, N. Sazali, and A. F. Ismail. "Effect of intermediate layer on gas separation performance of disk supported carbon membrane." *Separation Science and Technology* 52, no. 13 (2017): 2137-2149.
- [39] Ismail, Nor Hafiza, Wan Norharyati Wan Salleh, Norazlianie Sazali, and Ahmad Fauzi Ismail. "The effect of polymer composition on CO<sub>2</sub>/CH<sub>4</sub> separation of supported carbon membrane." *Chemical Engineering Transactions* 45 (2015): 1465-1470.



- 
- [40] Sazali, N., W. N. W. Salleh, A. F. Ismail, N. H. Ismail, F. Aziz, N. Yusof, and H. Hasbullah. "Effect of stabilization temperature during pyrolysis process of P84 co-polyimide-based tubular carbon membrane for H<sub>2</sub>/N<sub>2</sub> and He/N<sub>2</sub> separations." In *IOP Conference Series: Materials Science and Engineering*, vol. 342, no. 1, p. 012027. IOP Publishing, 2018.
- [41] N.A.Z. Kahlib, F.D.M. Daud, M. Mel, A.Z.A. Azhar, and N.A. Hassan. "Synthesis and characterization of silica membranes via sol-dip coating." *Journal of Advanced Research in Materials Science* 39, (2017): 1-7.
- [42] W.A.F.W. AbdulKadir, K.F.M. Yunos, A.R. Hassan, and N.A.M. Amin. "Fabrication and Performance of PSf/CA Blend Ultrafiltration Membrane on Effect of Different of Polymer Ratio." *Journal of Advanced Research in Materials Science* 45, (2018): 1-14.
- [43] Sivakumar, Muthusamy, Doraisamy Raju Mohan, Ramamoorthy Rangarajan, and Yoshiharu Tsujita. "Studies on cellulose acetate-polysulfone ultrafiltration membranes: I. Effect of polymer composition." *Polymer international* 54, no. 6 (2005): 956-962.
- [44] Sivakumar, Muthusamy, Doraisamy Raju Mohan, and Ramamoorthy Rangarajan. "Studies on cellulose acetate-polysulfone ultrafiltration membranes: II. Effect of additive concentration." *Journal of Membrane Science* 268, no. 2 (2006): 208-219.
- [45] A.R. Sunarti and A.L. Ahmad. "Performances of Automated Control System for Membrane Gas Absorption: Optimization Study." *Journal of Advanced Research in Applied Mechanics* 6, (2015): 1-20.