

MOISTURE UPTAKE IN MONOLITHIC AND COMPOSITE MATERIALS: EDGE CORRECTION FOR RECTANGULOID SAMPLES

M.J. Starink, L.M.P. Starink* and A.R. Chambers

Materials Research Group, School of Engineering Sciences,
University of Southampton, Southampton SO17 1BJ, UK

*currently at QinetiQ, Farnborough GU14 OLX, UK

Abstract

Experiments on moisture uptake of monolithic and composite materials are generally performed by immersing rectanguloid (square plate) samples in water. An edge correction factor is derived which, in a mathematically simple way, takes water uptake through all 6 faces (2 broad and 4 smaller faces) into account. Analysis shows this edge correction factor to be very accurate (deviations typically less than 2%). New expressions for moisture uptake in composites with unidirectionally aligned fibres are derived, by incorporating this edge correction factor as well as proper boundary conditions which depend on volume fraction of fibres. Experimental data on moisture uptake in these types of composite samples is successfully analysed using these expressions.

1. Introduction

Many materials that are exposed to a moist environment degrade due to the uptake of water. Degradation of mechanical properties is important in polymers or polymer based carbon fibre reinforced composites (CFRP). For experimental determinations of moisture uptake in materials, small plate-shaped samples are generally used (see e.g. Refs. [1,2,3]). The dimensions are usually chosen such that one of the sides is much smaller than the other two, and thus the moisture uptake is mainly determined by the moisture uptake through the two broad faces of the plate. In this approximation, diffusion is sometimes assumed to occur in one direction only, i.e. diffusion is one-dimensional (1D). Hence, if moisture uptake is determined by classical Fickian diffusion, the moisture concentration can be approximated by the well known solution for diffusion in an infinite plate, which yields a linear increase in the total amount of moisture in the sample with $t^{1/2}$ over the initial part of the moisture uptake. However, in order to accurately compare results obtained from samples with different shapes corrections have to be made for so-called edge effects. Shen and Springer [1] have in the past claimed to have derived a correction factor for edge effects, and their correction factor has been used in many publications on moisture absorption [1,2,3].

In the present publication it will be shown that Shen and Springer's edge correction factor is inaccurate and in section 2.2 a new accurate edge correction factor will be derived. The new edge correction factor will be used to obtain expressions for the moisture uptake composites with unidirectional fibres (section 2.3). The latter expressions will be used to analyse data on the moisture uptake in composites with unidirectional fibres (section 3).

2 Mathematical treatment of diffusion in monolithic and composite materials

2.1 1D and 3D Fickian diffusion

If moisture uptake is determined by classical 1D Fickian diffusion, the moisture concentration as a function of time, t , and distance from the surface, x , is given by the well known solution for diffusion in an infinite plate (see for instance Refs. [4,5,6]):

$$\frac{c(x,t) - c_i}{c_m - c_i} = 1 - \frac{4}{\pi} \sum_{j=0}^{\infty} (2j+1)^{-2} \sin \frac{(2j+1)\pi x}{a} \exp \left[-\frac{(2j+1)^2 \pi^2 D_x t}{a^2} \right] \quad (1)$$

where $c(x,t)$ is the moisture concentration, c_i is the initial moisture concentration (assumed to be uniform), c_m is the maximum moisture concentration, D_x is the diffusivity in the x direction (the direction normal to the broad faces) and a is the thickness of the sample in the x direction.

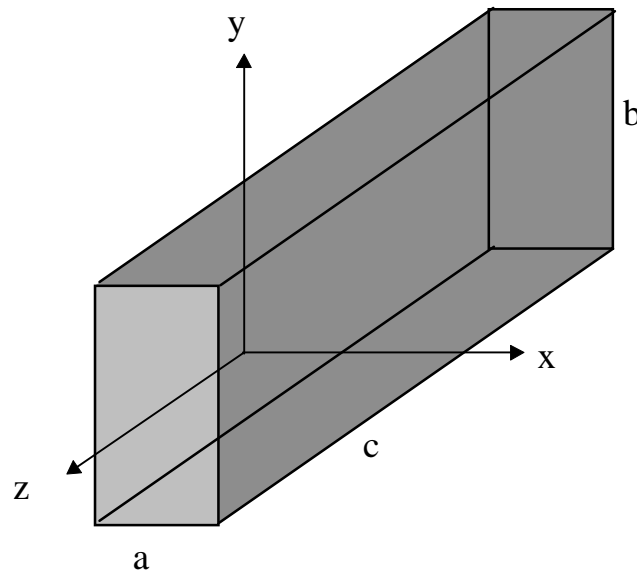


Fig. 1 Orientation of rectanguloid with respect to the axes.

The average moisture content at time t , $M(t)$, can be obtained by integrating the above equation, which leads to:

$$M = G(M_m - M_i) + M_i \quad (2)$$

where M_i is the initial moisture content, M_m is the maximum moisture content, and

$$G = G_{1D} = 1 - \frac{8}{\pi^2} \sum_{j=0}^{\infty} (2j+1)^{-2} \exp\left[-\frac{(2j+1)^2 \pi^2 D_x t}{a^2}\right] \quad (3)$$

For $G < 0.6$ the above equation can be approximated very accurately by:

$$G_{1D} \cong \frac{4}{a} \sqrt{\frac{D_x t}{\pi}} \quad (4)$$

Hence the moisture uptake is a linear function of $t^{1/2}$ and the diffusion coefficient D_x can be obtained directly from the initial slope of a plot of $(M-M_i)/(M_m-M_i)$ vs. $t^{1/2}/a$, using:

$$slope \cong 4 \sqrt{\frac{D_x}{\pi}} \quad (5)$$

For samples of finite dimensions Eq. 4 is only a rough approximation and in order to make accurate determinations of the diffusion constant, and to be able to compare samples of different shapes, the uptake through the smaller faces needs to be taken into account. One could of course resort to the solution for the full three dimensional problem of diffusion in a rectangular (ie. a rectangular) [2,4]:

$$G_{3D} = 1 - \left(\frac{8}{\pi^2}\right)^3 \sum_{k=0}^{\infty} \sum_{l=0}^{\infty} \sum_{m=0}^{\infty} \frac{\exp\left[-\pi^2 t \left(\frac{(2k+1)^2}{a^2} D_x + \frac{(2l+1)^2}{b^2} D_y + \frac{(2m+1)^2}{c^2} D_z\right)\right]}{(2k+1)^2 (2l+1)^2 (2m+1)^2} \quad (6)$$

where k , l and m are positive whole integers, D_x , D_y and D_z are the diffusion coefficients in the direction of the 3 axes, and a , b and c are the sides of the rectangular parallelepiped (or rectangular) the x , y and z directions. (See Fig. 1, we will take $a \leq b \leq c$.) In monolithic materials D_x , D_y and D_z will, in general, be equal. For $a \ll b, c$ and $G_{3D} < 0.6$ a plot of G_{3D} vs. $t^{1/2}/a$ is again in good approximation linear (see Fig. 2 and Ref. [2]). In analogy to the 1D diffusion case we can thus define an effective apparent diffusion coefficient, D_{eff} , by:

$$slope \cong 4 \sqrt{\frac{D_{eff}}{\pi}} \quad (7)$$

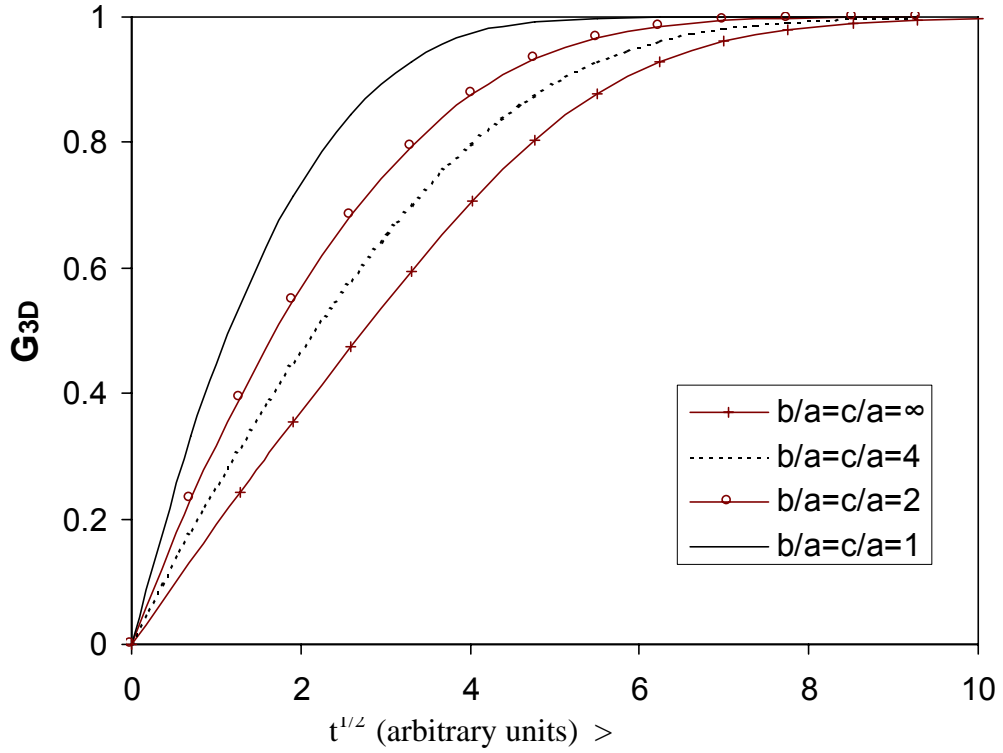


Fig. 2 Total normalised moisture uptake in a rectangularoid (G_{3D}) as a function of $t^{1/2}$.

2.2 Edge correction factors for monolithic rectangularoids

Eq. 6 can only be evaluated at the expense of much more computer time than is needed for evaluation of Eq. 1. A more important drawback of Eq. 6 is that although for $a \ll b, c$ and $G_{3D} < 0.6$ a plot of G vs. $t^{1/2}$ is again approximately linear [2], a method for calculation of the diffusion constant from the slope of such a plot is not easily determined. For this reason it is very useful to derive a correction factor, f , that takes the influence of diffusion through the smaller faces into account such that:

$$G_{3D} = f G_{1D} \quad (G_{3D} < 0.6) \quad (8)$$

and hence,

$$D_c = f^{-2} D_{eff} \quad (9)$$

Where D_c is the diffusion constant estimated from moisture uptake data for in a rectangular parallelepiped corrected using factor f . Shen and Springer [1] have in the past claimed to have derived just such a correction factor. For $D = D_x = D_y = D_z$ Shen and Springer's edge correction factor is given as:

$$f \approx f_{S\&S} = 1 + \frac{a}{b} + \frac{a}{c} \quad (10)$$

However, as will be shown below, Shen and Springer's edge correction factor is inaccurate and overestimates f by a considerable amount. In the following we will show that a much more accurate edge correction factor can be derived.

For the derivation of the edge correction factor we will consider a rectanguloid solid of dimensions a, b, c ($a \leq b \leq c$) which is exposed to a constant humidity environment.

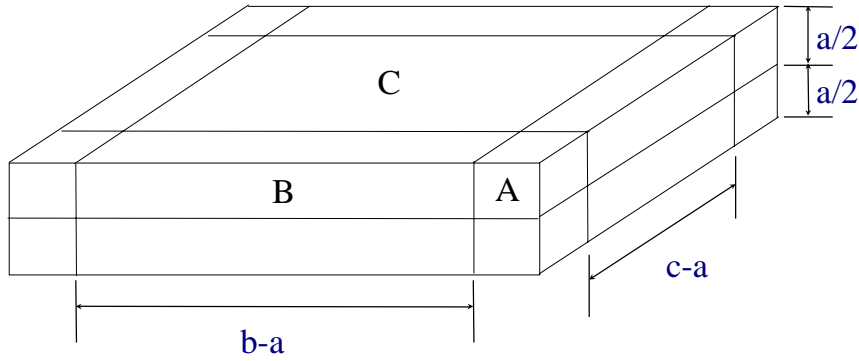


Fig. 3 Rectanguloid divided into 3 types of different sub-rectanguloids.

Table 1 Properties of rectanguloids in Fig. 3.

rectanguloid type	number of diffusion directions	total volume rectanguloid	average concentration in rectanguloid
A	3	a^3	λ_{3D}
B	2	$(b-a)a^2 + (c-a)a^2$	λ_{2D}
C	1	$(b-a)(c-a)a$	0.5

In order to derive the general mathematical form that f will take we will first consider an approximate treatment. In this first approximate treatment we will make the following simplifying assumptions:

- i) the concentration at any given point in the solid is determined solely by the time and the distance to the nearest external surface.
- ii) the concentration drops linearly with distance to the nearest surface.

Consider the time, t_x , at which the moisture has just reached all parts of the solid, i.e. the time at which the moisture just reaches the point(s) furthest away from the surfaces. To calculate

the average moisture content it is convenient to subdivide the solid into three types of rectangularoids according to the number of directions from which diffusion has occurred into these rectangularoids. For instance (see Fig. 3), on all 8 corners of the solid, cubes of side $\frac{1}{2}a$ are found in which the concentration profile is determined by diffusion from three mutually perpendicular directions. Connecting pairs of these cubes along the four smaller faces of the solid are rectangularoids in which the diffusion profile is determined by diffusion from two directions. In the remainder of the solid, the diffusion profile is determined by diffusion perpendicular to the broad faces only. Properties of the three types of rectangularoids (termed A, B and C, respectively) are listed in Table 1.

The average concentration in rectangularoids of each type is constant and can be calculated through integration. From the data in table 1 the average concentration in the solid, \bar{C} , equals:

$$\bar{C} = \frac{a^3 \lambda_{3D} + a^2 [(b-a) + (c-a)] \lambda_{2D} + a(b-a)(c-a) \frac{1}{2}}{abc} \quad (11)$$

If the diffusion had only occurred through the two broad faces the average concentration would have been $\frac{1}{2}$, hence it follows that,

$$f = \frac{\bar{C}}{\frac{1}{2}} = 1 + 2(\lambda_{2D} - \frac{1}{2}) \frac{a[(b-a) + (c-a)]}{bc} + 2(\lambda_{3D} - \frac{1}{2}) \frac{a^2}{bc} \quad (12)$$

which simplifies to:

$$f_{SSC} = 1 + \lambda_1 \frac{a}{b} + \lambda_1 \frac{a}{c} + \lambda_2 \frac{a^2}{bc} \quad (13)$$

where λ_1 and λ_2 are functions of λ_{2D} and λ_{3D} . There are several ways in which λ_1 and λ_2 (or λ_{2D} and λ_{3D}) can be derived*, the most accurate analysis being obtained by fitting their values using the complete 3D diffusion equation and calculating the slope of the initial part. Thus, in the next stage of the analysis, average moisture uptake as a function of t was calculated with Eq. 6 for various shapes of rectangularoids, using $D = D_x = D_y = D_z$. From these profiles D_{eff} and D_c were obtained from the slope of a plot of G vs. $t^{1/2}$ (G from 0 to 0.5) for:

- i) $f = 1$ (i.e. assuming one dimensional diffusion only),
- ii) $f = f_{S\&S}$ (Shen and Springer's edge correction),
- iii) $f = f_{SSC}$ (our edge correction factor, Eq. 13), with optimised values for λ_1 and λ_2 . It was found that for Eq. 13 the best results were obtained for $\lambda_1 = 0.54$, $\lambda_2 = 0.33$. Hence Eq 13 becomes:

* Using assumptions i) and ii) one finds $\lambda_1 = \frac{1}{3}$ and $\lambda_2 = \frac{1}{6}$. Analysis of the accuracy of this expression using the true 3D diffusion equation shows that the resulting edge correction factor is more accurate than Shen and Springer's one. However, the edge correction factor presented in Eq. 14 is clearly the most accurate of all expressions considered.

$$f_{SSC} = 1 + 0.54 \frac{a}{b} + 0.54 \frac{a}{c} + 0.33 \frac{a^2}{bc} \quad (14)$$

Final results are presented in Table 2, which shows:

- a) $f_{S\&S}$ (Shen and Springer's edge correction) is quite inaccurate and it considerably over corrects for the edge effect for all sample shapes. For realistic sample shapes deviations in D are between 16 and 37%.
- b) Eq. 13 gives an accurate approximation for the edge effect. Deviations in D are typically less than 2%.

Thus, in concluding this section, in analysis of moisture uptake data for a finite monolithic sample the diffusion coefficient can be obtained from the initial slope (from $G = 0$ to 0.5) of a sorption curve via Eq. 5, where the edge correction factor f is given by Eq. 14.

Table 2 D_c calculated by applying edge correction factors derived by Shen and Springer ($f_{S\&S}$) and by the present authors (f_{SSC}).

a (mm)	b (mm)	c (mm)	D_{eff}/D (from Eq.7)	D_c/D (using $f_{S\&S}$)	D_c/D (using f_{SSC})
4	4	4	5.73	0.637	0.996
4	8	8	2.63	0.658	1.009
4	15	15	1.68	0.716	0.989
4	40	40	1.20	0.83	0.981
4	100	100	1.06	0.906	0.984
4	1000	1000	1.00	0.985	0.993
4	8	15	2.13	0.682	1.028
4	8	40	1.83	0.714	0.989
4	15	15	1.68	0.716	0.99
4	15	40	1.42	0.763	0.981

2.3 Diffusion in unidirectional composites

In unidirectional composites the diffusion rates can, in general, be expected to be direction dependent. Several authors [1,2] presented a mathematical treatment of this, but an overhaul of this work has become necessary because:

1. In earlier work [1,2] Shen and Springer's inaccurate edge correction factor, $f_{S\&S}$, was used.
2. Most expressions used in Refs. [1,2] for diffusion in composites are only valid for steady state conditions. The limitations for water uptake were not assessed in Refs. [1,2].
3. In Refs. [1,2], boundary conditions were considered to be independent of v_f . This is not valid for water uptake in composites.

A modified treatment of diffusion in unidirectional composites is presented below.

In a unidirectional composite containing cylindrical fibres, the thermal conductivity of the composite normal to the fibres, K_{\perp} , can be measured by taking a large thin plate and imposing two temperatures T_1 and T_2 on the two broad faces. In steady state conditions, K_{\perp} is in good approximation given by (see Ref. [1]):

$$K_{\perp} \cong \left(1 - 2\sqrt{\frac{v_f}{\pi}}\right) K_r + \frac{K_r}{B_k} \left[\pi - \frac{4}{\sqrt{1 - B_k^2 v_f / \pi}} \tan^{-1} \frac{\sqrt{1 - B_k^2 v_f / \pi}}{\sqrt{1 + B_k^2 v_f / \pi}} \right] \quad (15)$$

$$B_k = 2 \left(\frac{K_r}{K_f} - 1 \right) \quad (16)$$

where v_f is the volume fraction of fibres, K_r is the thermal diffusivity in the resin/matrix, and K_f is the thermal diffusivity in the fibres. As heat conduction in solids and diffusion are equivalent in mathematical terms (see e.g. Ref. [4]) it follows that, under equivalent boundary conditions, the diffusivity in the composite normal to the fibres, D_{\perp} , is in good approximation given by:

$$D_{\perp} \cong \left(1 - 2\sqrt{\frac{v_f}{\pi}}\right) D_r + \frac{D_r}{B_D} \left[\pi - \frac{4}{\sqrt{1 - B_D^2 v_f / \pi}} \tan^{-1} \frac{\sqrt{1 - B_D^2 v_f / \pi}}{\sqrt{1 + B_D^2 v_f / \pi}} \right] \quad (17)$$

$$B_D = 2 \left(\frac{D_r}{D_f} - 1 \right) \quad (18)$$

where D_r is the thermal diffusivity in the resin/matrix, and D_f is the thermal diffusivity in the fibres.

In the steady state, the diffusivity in the composite parallel to the fibres, $D_{//}$, is simply given by:

$$D_{//} = (1 - v_f) D_r + v_f D_f \quad (19)$$

It is important to note that the above equations are only valid provided:

1. Diffusion (heat conduction) occurs under steady state conditions i.e. local moisture concentration $c(x,y,z)$ (temperature $T(x,y,z)$) is independent of time.
2. Boundary conditions imposed are constant and independent of v_f .

However, moisture absorption is typically not a steady state process, and boundary condition will generally depend on v_f . This means that the validity of the above equations for moisture absorption in composites is limited and has to be carefully assessed for each case.

As an illustration of complexities encountered in composites we consider the case where $D_f \ll D_r$ and both the saturation levels in resin and fibre, $M_{m,r}$ and $M_{m,f}$ are significant. In this case diffusion of moisture will initially occur only in the matrix and only after the matrix has taken up a substantial amount of water the fibres will take up significant amounts of water, essentially acting as a sink for moisture within the matrix. Thus, steady state can only be reached a long time after substantial diffusion through the matrix has occurred. In such a case moisture uptake is a two stage process and solutions can *not* be derived on the basis of a single stage 3D diffusion equation (or a 1D equation with edge correction) with appropriate insertion of expressions for D_{\perp} and $D_{//}^{\dagger}$.

In general terms, the above equations can yield solutions or partial solutions for moisture uptake in the following cases:

- A. $M_{m,f} \ll M_{m,r}$. In this case moisture entering the fibre is insignificant. A complete solution can be obtained.
- B. $D_f = 0$. No moisture enters the fibre. A complete solution can be obtained.
- C. $a/\sqrt{D_r} \gg d/\sqrt{D_f}$ (d is the fibre diameter) Moisture uptake in the fibre becomes significant only in a second stage after the resin has saturated. A solution for the first stage can be obtained.

In the following we will obtain solutions for cases A, B, and the first stage of C.

In obtaining the solutions for the above cases we first need to obtain the appropriate boundary condition. As at each outer surface of the composite contains a fraction v_f of fibre ends which do not absorb water, the average boundary condition at the outer surfaces is given by:

$$c(\text{surface}) = (1 - v_f) M_{r,m} \quad (20)$$

(Note that this is different from the steady state heat conduction composites for which the surface temperature equals the environment temperature, i.e. the boundary condition is independent of v_f .) The volume averaged diffusivities parallel and normal to the fibres can now be obtained in the following manner. As no water is taken up by the fibre, the diffusivity in the direction parallel to the fibres is simply given by:

$$D_{//} = D_r \quad (21)$$

Average diffusivity normal to the fibres can be analysed using the simplified geometry of blocking of flow in a square packing array depicted in Fig. 4. Using Fick's first law:

$$F = -D \frac{\Delta c}{\Delta x} \quad (22)$$

it follows:

[†] Note that this is contrary to suggestions made in Ref. 1.

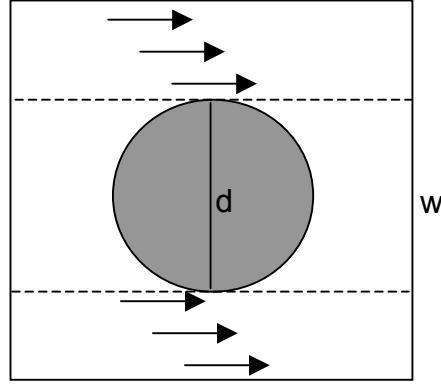


Fig. 4 Simplified geometry for diffusion normal to fibres in a square packing array.

$$D_{\perp} = D_r \left(1 - \frac{d}{w}\right) [1 - v_f]^{-1} \quad (23)$$

where d is the diameter of the fibre and w is the width of the square. In this equation the term $[1 - v_f]^{-1}$ reflects the change in boundary condition (average surface concentration) resulting from the introduction of the impermeable fibres. (This term does not appear in the case of steady state heat conduction in a composite and was not accounted for in Refs. [1,2].) From the latter equation it follows:

$$D_{\perp} = \frac{\left(1 - 2\sqrt{\frac{v_f}{\pi}}\right)}{1 - v_f} D_r \quad (24)$$

If the fibres are oriented relative to the axes in the manner presented in Fig. 5 then the diffusion coefficients in the different directions are given by:

$$D_x = D_{//} \cos^2 \alpha + D_{\perp} \sin^2 \alpha \quad (25)$$

$$D_y = D_{//} \cos^2 \beta + D_{\perp} \sin^2 \beta \quad (26)$$

$$D_z = D_{//} \cos^2 \gamma + D_{\perp} \sin^2 \gamma \quad (27)$$

From Eqs. 21 and 24-27 combined with Eqs. 2 and 6 the moisture uptake in a rectanguloid containing unidirectional fibres which are aligned in any direction with respect to the axis of the sample can be calculated, subject to specific conditions (see below). However, as before, Eq. 6 for 3D diffusion will complicate the mathematics. Hence, also here it is advantageous to introduce an edge correction factor.

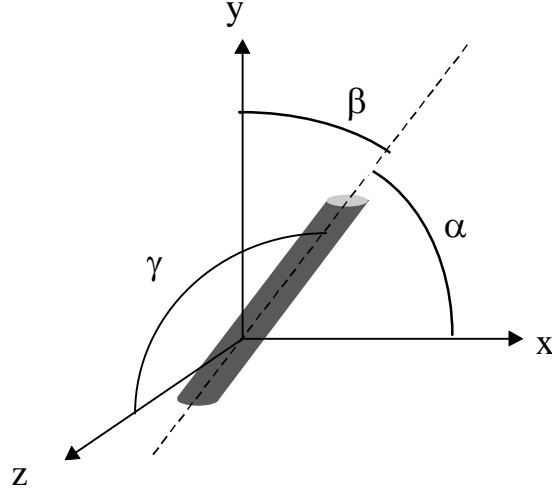


Fig. 5 Orientation of fibres with respect to the axes.

From Eq. 6 it follows that the edge correction factor for materials in which $D_x \neq D_y \neq D_z$ can be derived simply by substituting $a/\sqrt{D_x}$, $b/\sqrt{D_y}$ and $c/\sqrt{D_z}$ for a , b and c in the corresponding equations. Thus an accurate edge correction factor for materials with direction dependent diffusivity is:

$$f = 1 + \lambda_1 \frac{a}{b} \sqrt{\frac{D_y}{D_x}} + \lambda_1 \frac{a}{c} \sqrt{\frac{D_z}{D_x}} + \lambda_2 \frac{a^2}{bc} \sqrt{\frac{D_z D_y}{D_x^2}} \quad (28)$$

(Note that in substituting $a/\sqrt{D_x}$, $b/\sqrt{D_y}$ and $c/\sqrt{D_z}$ for a , b and c , the axes are chosen such that $a/\sqrt{D_x} \leq b/\sqrt{D_y} \leq c/\sqrt{D_z}$. Hence a is no longer necessarily the shortest edge of the rectangularoid.)[‡] Hence for $G < 0.6$ the moisture uptake can be obtained from:

$$G \cong f \frac{4}{a} \sqrt{\frac{Dt}{\pi}} \quad (29)$$

Thus for $G < 0.6$ the moisture uptake can be approximated accurately, using Eq. 21 and 24-27 combined with Eq. 2. As a specific examples we will consider the cases of rectangularoids with fibres parallel to one of the axes of the sample.

[‡] Similarly, Shen and Springer's edge correction factor for materials with direction dependent diffusivity becomes:

$$f_{S\&S} = 1 + \frac{a}{b} \sqrt{\frac{D_y}{D_x}} + \frac{a}{c} \sqrt{\frac{D_z}{D_x}}$$

Case 1: $D_f = 0$ and $\alpha = 0$

As the fibres are parallel to the x-axis (i.e. $\alpha = 0$):

$$D_x = D_{//} \quad (30)$$

$$D_y = D_z = D_{\perp} \quad (31)$$

The moisture uptake in the initial part ($G < 0.6$) can be obtained by using:

$$D_{eff}(\alpha = 0) \cong D_r \left[1 + \lambda_1 \left(\frac{a}{b} + \frac{a}{c} \right) \sqrt{\frac{1 - 2\sqrt{v_f/\pi}}{1 - v_f}} \right]^2 \quad (32)$$

(here second order edge effects are neglected by taking $\lambda_2 = 0$). The saturation level in the composite is given by:

$$M_{m,c} \cong (1 - v_f) M_{m,r} \quad (33)$$

Case 2: $D_f = 0$ and $\beta = 0$

In a similar fashion one obtains:

$$D_{eff}(\beta = 0) \cong D_r \frac{1 - 2\sqrt{v_f/\pi}}{1 - v_f} \left[1 + \lambda_1 \left(\frac{a}{b} \sqrt{\frac{1 - v_f}{1 - 2\sqrt{v_f/\pi}}} + \frac{a}{c} \right) \right]^2 \quad (34)$$

The saturation level is given by Eq. 33.

Case 3: $D_f = 0$ and $\gamma = 0$

This is obtained by exchanging b and c from the previous equation:

$$D_{eff}(\gamma = 0) \cong D_r \frac{1 - 2\sqrt{v_f/\pi}}{1 - v_f} \left[1 + \lambda_1 \left(\frac{a}{b} + \frac{a}{c} \sqrt{\frac{1 - v_f}{1 - 2\sqrt{v_f/\pi}}} \right) \right]^2 \quad (35)$$

The saturation level is given by Eq. 33.

To illustrate the results obtained with Eqs. 32 and 34, D_{eff}/D_r for an infinitely large plate and for finite plates (rectanguloids) of various shapes are presented in Fig. 6.

3 Experimental

In order to validate the expressions derived in the previous section, moisture absorption experiments were performed on sections cut from a single 1.6 mm thick panel with cylindrical fibres unidirectionally aligned parallel to the surface (for full details see Ref. [7]) as well as on sections from a corresponding unreinforced resin panel. The resin system in both cases was epoxy blended with 30wt% of thermoplastic (PES). The unreinforced panel was produced at ICI Wilton, using a standard technique for production of neat resin plaques. The thermoplastic was dissolved in a solvent and then added to the epoxy and hardener. The solvent was then evaporated off. Next, each blend was cast into an open mould, preheated to 413K, and degassed for 30 min under vacuum to remove residual solvent and trapped air. Samples were then cured at 458K for 120 min and allowed to cool to room temperature for a further 120 min. The reinforced panels (also produced at ICI Wilton) were manufactured using unidirectional carbon tape, which was pre-impregnated with the 30% thermoplastic resin before lay-up. The panel was made to be approximately 1.6 mm thick, and 130 mm square. The cure was carried out in a pressclave using edge dams to ensure maximum flow through the panel thickness, to minimise voidage. The cure cycle involved a heating ramp to 458K over 80 min, a dwell at 458 K for 180 min and a ramp down to room temperature over 80 min.

From the saturation levels of the composites and the corresponding unreinforced matrix the fibre content was calculated as 74 vol% (using Eq. 33). Optical microscopy on cross sections of the samples (see Ref. [7]) confirmed that porosity in the samples was low and that the fibres in the reinforced panel were generally well aligned.

The reinforced panel was cut into rectanguloid samples of varying shape ranging from $1.6 \times 10 \times 100$ mm to $1.6 \times 100 \times 10$ mm and $1.6 \times 60 \times 60$ to $1.6 \times 10 \times 10$ mm ($a \times b \times c$), see Table 3, with fibres aligned in the b direction. For some of the sample types duplicate experiments were employed, i.e. two nominally identical samples cut from the same panel and with identical dimensions and identical direction of fibres, were exposed in the same bath at the same time. The samples were totally immersed in water at 25°C and for all samples the initial part of the curve of $(M-M_i)/(M_m-M_i)$ vs. $t^{1/2}$ was in good approximation a straight line. M_m was assumed to be identical for all samples and D_{eff} was calculated from the slope.

4 Results and discussion

It should be noted that throughout the present analysis we will assume that the fibres do not absorb moisture. It is believed that this is a good approximation for the carbon fibres.

When comparing nominally identical samples generally some limited variability in measured D_{eff} was noted. This variability is thought to be related to local variability in volume fraction of fibres within the panel. The magnitude of this variability is consistent with v_f varying by about 0.005 vol% between samples (around the average value of 0.74 vol%). (One experiment with

an anomalously high value of D_{eff}/D_r was ascribed to a flawed section of the panel and omitted from the analysis.)

To analyse the data, first the theoretical predictions for D_{eff}/D_r were calculated using Eqs. 32 and 34 (using $\lambda_l = 0.54$, according to our edge correction factor). This data was used to obtain D_r through fitting to the experimental data and in Fig. 7 the resulting experimental D_{eff}/D_r values are compared with the theoretical predictions. Fig. 7 shows a good correspondence between experimental and measured D_{eff}/D_r (χ^2 is 1.0) proving that Eqs. 32 and 34 (which incorporate our new edge correction factor) are sound. Conversely, employing Shen and Springer's edge correction factor (i.e. Eqs. 32 and 34 with $\lambda_l = 1$) yields a much worse correspondence (χ^2 is about 6).

For a final comparison of the model predictions with the data the ratio of the diffusion coefficients of the $1.6 \times 100 \times 10$ mm composite panel to that of the unreinforced panel was calculated from the experimental data. This yields 0.11, which is in reasonable agreement with the results presented in Fig. 7. Thus, it is concluded that the present analysis leading to Eqs. 34 and 35 can explain all observations of the relative water uptake rates of the present unidirectionally reinforced panels and the unreinforced panel.

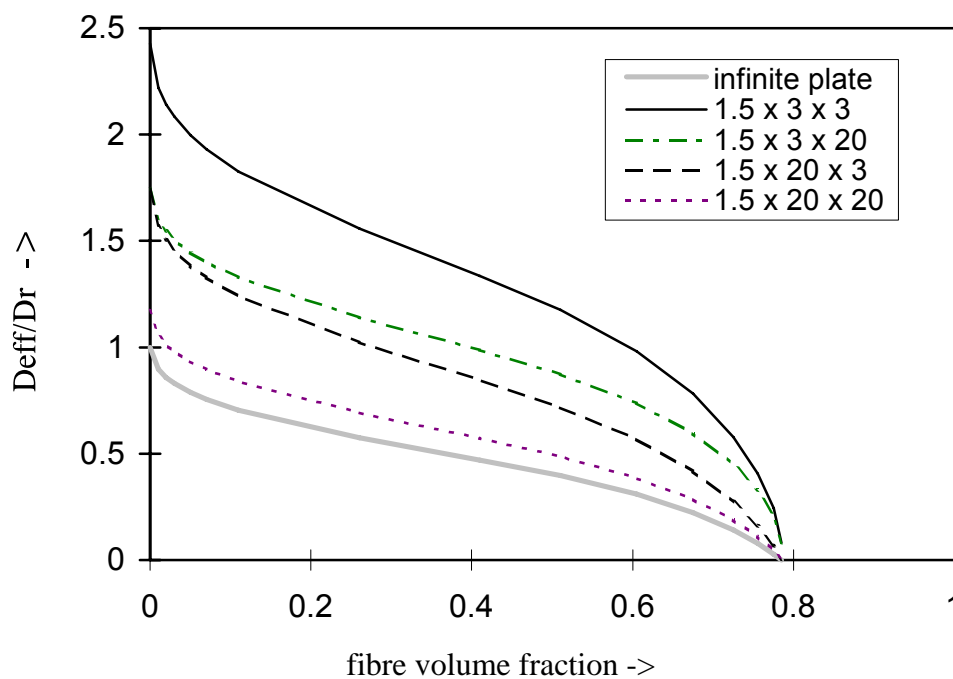


Fig. 6 D_{eff}/D_r vs. fibre volume fraction for unidirectional composite rectanguloids of different shapes ($a \times b \times c$). Fibres are aligned along the y-axis (i.e. parallel to edge of length b).

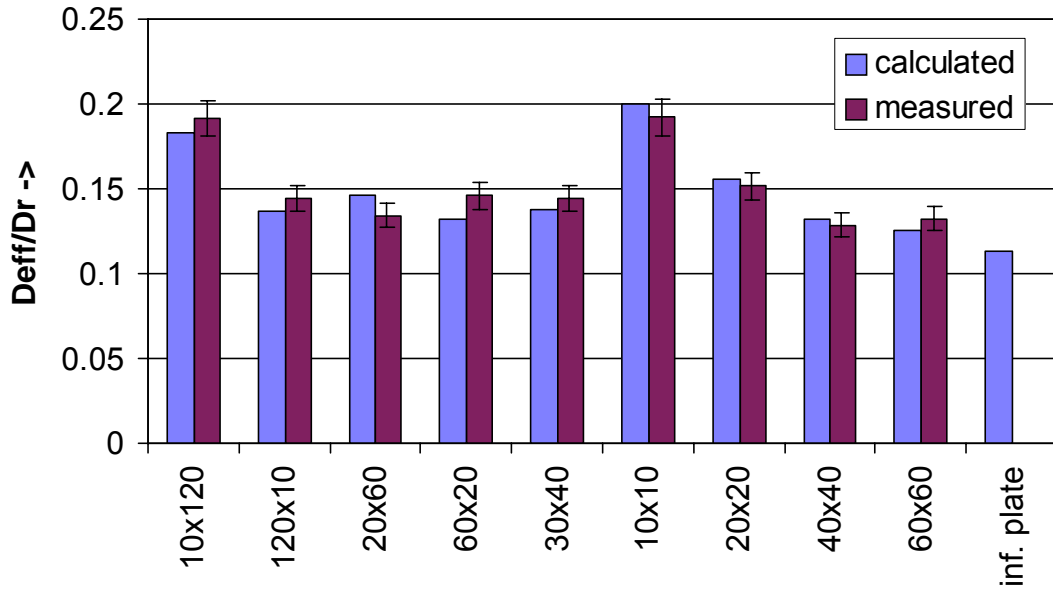


Fig. 7 D_{eff}/D_r for unidirectional composite rectangularoids of different shapes.

Table 3 Dimensions of rectangularoid shaped composites used for moisture uptake experiments. Fibres are aligned along the y-axis (i.e. parallel to edge of length b).

type	a (mm)	b (mm)	c (mm)
A	1.6	10	120
B	1.5	120	10
C	1.6	20	60
D	1.5	60	20
E	1.5	30	40
F	1.6	10	10
G	1.6	20	20
H	1.6	40	40
I	1.5	60	60

4 Concluding remarks

The analysis of edge effects in section 2.2 has shown that Shen and Springer's edge correction factor, $f_{S\&S}$ (Eq. 10), is inaccurate and analysis of experiments as presented in section 3 further confirmed this result. As $f_{S\&S}$ has in the past been used in many analyses of experimental data of moisture uptake D values obtained in these works should in general be corrected by

multiplying with $(f_{s&s}/f_{SSC})^2$. The magnitude of this correction is in the order of 15 to 30% for typical sample dimensions. It is further noted that also for disc shaped samples correction for edge effects is necessary. With the concepts presented in section 2.2, in principle, edge correction factors for discs and other types of regular shapes can be derived.

The treatment presented in section 2.3 shows that introduction of fibres that take up little or no water reduces the rate of water uptake in two ways:

1. the maximum moisture uptake is reduced
2. the diffusion rate of water in a direction perpendicular to the fibres is reduced.

Thus whilst the reduction of maximum moisture uptake is independent of fibre orientation the diffusion rate of water is strongly influenced by the way in which the fibres are oriented. As an example Fig. 7 shows that for an infinitely large plate $D_{eff}/D_r = 0.11$, i.e. the introduction of 0.74vol% of cylindrical fibres both decreases the maximum water uptake to 26% of that of the unreinforced resin and decreases the absorption rate by a factor 0.11, provided the plate is flawless and has a homogeneous distribution of fibres. Local variations of density of fibres and other flaws which yield high diffusivity paths perpendicular to the fibres can significantly increase the rate of moisture uptake in unidirectional panels.

References

- 1 C.H. SHEN and G.S. SPRINGER, *J. Comp. Mater.* **10** (1976) 2
- 2 M. T. ARONHIME, S. NEUMANN and G. MAROM, *J. Mater. Sci.* **22** (1987) 2435
- 3 M.E.R. SHANAHAN and Y. AURIAC, *Polymer* **39** (1998) 1155
- 4 H.G. CARSLAW and J.C. JAEGER, in “The Conduction of Heat in Solids”, 2nd ed (Oxford University Press, London, 1959)
- 5 J. CRANK, in “ The Mathematics of Diffusion”, 2nd ed. (Oxford University Press, London, 1975)
- 6 M.J. STARINK and P.J. GREGSON, *J. Mater. Sci. Lett.* **14** (1995) 1767
- 7 L.M.P. FELLOWS, PhD thesis, University of Southampton, 1998