

# PREFERENTIAL OXIDATION OF CO IN PRESENCE OF H<sub>2</sub> BEHAVIOR OF PtSn/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> CATALYSTS MODIFIED BY K OR Ba

G.J. SIRI<sup>†‡</sup>, G.R. BERTOLINI<sup>†‡</sup> and O.A. FERRETTI<sup>†‡</sup>

<sup>†</sup> Centro de Investigación y Desarrollo en Ciencias Aplicadas "Dr. Jorge Ronco" (CINDECA), Facultad de Ciencias Exactas, Universidad Nacional de La Plata-CONICET, 47 N°257, 1900 La Plata, Argentina.

*cindeca@unlp.edu.ar*

<sup>‡</sup> Facultad de Ingeniería, Universidad Nacional de La Plata, 1 esq 47, 1900 La Plata, Argentina.

*diqs@ing.unlp.edu.ar*

**Abstract**— The behavior of catalysts based on Pt/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> is analyzed in the CO oxidation reaction. Experiments were performed in the temperature range between 50°C and 250°C with a feed H<sub>2</sub> rich, and a concentration of 1% CO and 0.6% O<sub>2</sub>. Catalysts studied were: monometallic Pt/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub>, bimetallic PtSn/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> with a ratio Sn/Pt=1.6 at/at and two catalysts prepared by modification of the last one with K or Ba. The catalyst that showed maximum activity and selectivity levels is the PtSnK/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub>. The tin addition increases the activity which allows the reaction to occur at lower temperatures due to the decrease in the CO-Pt interaction. The addition of K or Ba produces a subsequent improvement with respect to the CO oxidation temperature, which leads to a selectivity increase. The selectivity of the CO oxidation passes through a maximum value as a function of the temperature. This maximum is explained by the importance acquired by the reverse of water gas shift reaction at temperatures near 200°C.

**Keywords**— Preferential Oxidation, Hydrogen purification, PtSn/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub>.

## I. INTRODUCTION

The requirements imposed world wide demand the search of technological alternatives, although the control of gaseous emissions from conventional thermal machines has experienced some advances. One of these alternatives is the use of fuel cells fed by hydrogen, that allow to optimize the use of the more scarce energetic resources since they are capable to convert the energy from chemical to mechanical one with an efficiency quite higher than the one of the conventional thermal machines. For example, in the case of internal combustion engines of mobile sources, the fuel cells are able to almost duplicate their efficiency with null or minimum emissions of pollutants.

The hydrogen is a fuel with difficulties for its distribution as well as for its storage, consequently the challenge is to generate it in situ (on board) or in a service station, from the reforming or partial oxidation of natural gas, hydrocarbons, methanol or ethanol. In all cases the formation of carbon oxides (CO and CO<sub>2</sub>) is unavoidable. The carbon monoxide must be eliminated because in concentrations higher than 20 ppm it leads to the deactivation of the electrodes of the fuel cells type PEM (Polymer Electrolyte Membrane) used for these

systems (Manasilp and Gulari, 2002)

The need that the generated hydrogen must be an ultra pure product forces to technological solutions such as membrane reactors or catalytic processes for purification. In the case of membrane reactors, that allow the selective passage of hydrogen, one of the difficulties to defeat with actual technologies is the necessity to operate with a high pressure difference on both sides of the membranes (Irusta *et al.*, 2005). In catalytic purification processes part of the carbon monoxide can be eliminated via water gas shift reaction (WGSR), up to levels between 500 and 1000 ppm fixed by thermodynamics. The CO remainder can be eliminated by methanization or by selective oxidation (Preferential oxidation, PROX), in which the conversion of hydrogen must be minimized. The methanization is easily performable in presence of catalysts based on Ni (Takenaka *et al.*, 2004; Schubert *et al.*, 2004; Farrauto, 2005); however, they present as a problem the need to reach high temperature levels for an effective elimination (>250°C); on the other hand the use of Ni in mobile applications is considered a potential health hazard.

Since investigations about the development of catalysts with higher tolerance to the CO presence continue, the PROX appears as the most adequate way to feed ultra pure hydrogen to the fuel cells. In this case different catalytic systems have been studied and they can be classified in three groups:

(i) Catalysts based on supported Au; they present a very high activity at low temperatures (Margitfalvi *et al.*, 2004; Trimm, 2005). These systems are strongly dependent on the preparation method and in general they present deactivation problems and penalization of the selectivity by hydrogen oxidation at temperatures higher than 80°C (Recupero *et al.*, 2004). Evidences about resistance to poisoning and to sintering through experiments at prolonged times seem necessary for these systems.

(ii) Catalysts based on supported Cu were also studied with good results for the activity, although problems inherent to Cu with respect to the stability and to the control of its oxidation state seem not to be defeated (Recupero *et al.*, 2004; Shiao *et al.*, 2006; de Souza, *et al.*, 2006).

(iii) Catalysts based on noble metals (Pt, Ru, Rh, Pd) have demonstrated to be active in the oxidation of CO to CO<sub>2</sub> even at low temperatures (Roberts *et al.*, 2003;

Mariño *et al.*, 2004; Wootsch *et al.*, 2004; Bourane and Bianchi, 2004; Avgouropoulos and Ioannides, 2005). In the case of these type of catalysts modified by tin, it has been demonstrated that the interaction MSn (M:Pt, Pd) increases the oxidizing activity (Grass and Lintz, 1977; Margitfalvi *et al.*, 2002), which is attributed to the presence of SnO<sub>x</sub> sites in intimate interaction with the noble metal. Furthermore, alkali-metal promotion of platinum and rhodium catalysts was observed to enhance the catalytic performance of these catalysts in preferential oxidation (PROX) of CO in hydrogen-rich streams for fuel-cell applications (Tanaka *et al.*, 2003, Mirkelamoglu and Karakas, 2006).

In this work, the behavior of Pt supported on  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalysts, modified by Sn, is analyzed in presence of alkaline or alkaline earth metals (K, Ba). The Sn addition by controlled preparation techniques coming from the surface organometallic chemistry on metals (SOMC/M) produces geometric and electronic modifications that induce to changes in the catalytic properties of the active phase as it was observed in previous works (Siri, *et al.*, 2005a). The changes by addition of alkaline and alkaline earth metals generate modifications not only on the acid-basic properties of the support but also on the properties of the metallic phase (Siri, *et al.*, 2005b).

## II. METHODS

### A. Catalyst Preparation.

A commercial  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> (Cyanamid Ketjen) crushed to a size of 60-100 mesh was used as support. For the preparation of the platinum monometallic catalyst, an impregnating solution of H<sub>2</sub>PtCl<sub>6</sub> was added onto the support so as to obtain 1% w/w Pt exchanged. Then, the solids were repeatedly washed, dried at 105 °C, calcined in air at 500 °C and reduced in flowing H<sub>2</sub> at the same temperature, leading to the monometallic Pt/  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalyst. After the reduction step, the Pt/  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalyst was washed several times with a NH<sub>3</sub> aqueous solution (0.1 M) at room temperature, in order to obtain a chlorine concentration under 0.1% in the resulting solid. The bimetallic systems have been prepared by reaction between the monometallic catalyst and SnBu<sub>4</sub> dissolved in n-decane, maintaining a H<sub>2</sub> flow of 30 cm<sup>3</sup> min<sup>-1</sup> and a temperature of 150°C during the reaction time in order to obtain Sn/Pt ratio of 1.6 as it is reported in references (Siri, *et al.*, 2005a). After 4 h of reaction, the systems were cooled to room temperature and were repeatedly washed with n-heptane under a H<sub>2</sub> atmosphere. The elimination of the organic groups heating the solids in a H<sub>2</sub> atmosphere at 500°C generates the supported bimetallic PtSn catalysts. PtSnM/  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> (M: Ba, K) were obtained by adding impregnating solutions of Ba(NO<sub>3</sub>)<sub>2</sub> and KOH, so as to obtain M/Pt ratios of 8.5 and 10, respectively. Metallic contents were determined by Atomic Spectrometry.

### B. Characterization.

*Transmission Electron Microscopy (TEM)*. The size distribution of metallic particles was determined by us-

ing a Jeol 100 CX instrument. To estimate the mean particle size ( $d_{va}$ ), the particles were considered spherical and the second moment of the distribution was employed.

*X-ray photoelectron spectroscopy (XPS)*. The samples were re-reduced in situ in the pre-treatment chamber of the spectrometer. Spectra were obtained with a VG ESCALAB 200R spectrometer equipped with a hemispherical electron analyzer and an Mg K $\alpha$  120 W X ray source. The reduction treatment was carried out in situ, by heating the samples under a hydrogen flow at 500°C for 1 h. As internal standards the binding energy (BE) of the Al 2p peak at 74.5 eV was considered. The intensities were estimated by calculating the integral of each peak after subtraction of the S-shaped background and fitting the experimental peak to a Lorentzian/ Gaussian mix of variable proportion.

### C. Activity Measurements.

The catalytic tests were performed by placing the sample in a conventional flow reactor (6 mm internal diameter, 50 mg of catalyst sample) at atmospheric pressure and 50-250°C. The composition of the reaction products was analyzed on line with the reactor by using a Carlo Erba Fractovap series 2150 gas chromatograph with a FID detector and a Shimadzu GC 8A with TCD detector. Total flow feed was 100 cm<sup>3</sup> min<sup>-1</sup>. Feed composition was 1% CO, 0.6% O<sub>2</sub>, 9% He and 89.4% Ar for tests in hydrogen absence and 1% CO, 0.6% O<sub>2</sub>, 9% He and 89.4% H<sub>2</sub> for oxidation tests in hydrogen presence. Carlo Erba chromatograph was employed to analyze CO and CO<sub>2</sub>. The effluent of the reactor contains carbon oxides which can be separated in a Porapak 60/80 column of 3 m length and 3 mm internal diameter, kept at 30°C and using H<sub>2</sub> as carrier. After separation, CO and CO<sub>2</sub>, in the presence of hydrogen carrier were methanized in a fixed bed reactor with a Ni/Al<sub>2</sub>O<sub>3</sub> catalyst at 450°C, so as to analyze the two methane peaks.

Shimadzu chromatograph was employed to analyze H<sub>2</sub>, N<sub>2</sub> and O<sub>2</sub> with a Molecular Sieve 4A column of 3 m length and 3 mm of internal diameter

### D. Results and Discussion

TEM results show a narrow distribution of metallic particle sizes, with a mean particle size of 1.8 nm for monometallic platinum catalyst. This value indicates a high dispersion of the platinum phase (around 60%, Farrauto and Bartholomew, 1997). The particle size distribution of the bimetallic system PtSn/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> is quite similar to the corresponding monometallic one, presenting a moderated shift (0.4 nm) compatible with a selective deposition of tin over platinum, in agreement with previously reported results involving these kind of preparation procedures (Siri, *et al.*, 2005a; Siri, *et al.*, 1997; Casella *et al.*, 2000). TPR diagrams show two main peaks of hydrogen consumption, in the regions of 75-110°C and 360-440°C, assigned to a weak and a strong metal support interaction, respectively (Kappenstein *et al.*, 1995).

XPS results show that platinum is completely reduced in all the samples studied, because the spectra contain only one peak corresponding to Pt centered around 314-315 eV (Pt  $4d_{5/2}$ ). The reference value was taken from the NIST X Ray Photoelectron Spectroscopy Database (Wagner, 1989). In PtSn/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> system, a downward shift of ca. 1 eV in the binding energy of platinum was observed with respect to the corresponding monometallic catalyst. This fact would be indicative of the existence of an electronic effect of tin over platinum, in agreement with previously published results for PtSn/SiO<sub>2</sub> catalysts prepared by Stagg *et al.* (1997). Studies carried out by Shen *et al.* (1999) from quantum chemical calculations employing density functional theories (DFT) for Pt<sub>19</sub> and Pt<sub>16</sub>Sn<sub>3</sub> clusters indicate that tin donates electrons to the  $6sp$  and  $5d$  orbitals of platinum. Rodríguez *et al.* (1998 a, b) investigated platinum-tin surface alloys using synchrotron-based high resolution photoemission and *ab-initio* self consistent field calculations and concluded that Pt-Sn bond involves a Sn ( $5s, 5p$ )  $\rightarrow$  Pt ( $6s, 6p$ ) charge transfer together with a Pt ( $5d$ )  $\rightarrow$  Pt ( $6s, 6p$ ) rehybridization. In this same sense, in a previous study of a PtSn/SiO<sub>2</sub> system by Pt L<sub>2,3</sub> XANES, the existence of an electronic effect was also explained by means of the  $d \rightarrow s, p$  rehybridization process taking place in PtSn 3-dimensional small nano-clusters leading to an increase in the number of Pt  $5d$  holes (Ramallo López *et al.*, 2003).


Concerning tin oxidation state, the Sn  $3d_{5/2}$  peak obtained by XPS contains two contributions. The first with a binding energy of around 484 eV is assigned to Sn(0) according to the well determined values (484.9 eV) obtained by Rodríguez *et al.* (1998a); the second contribution corresponds to Sn(II, IV), with a binding energy centered around 487 eV (Wagner, 1989). Results obtained for the fraction of metallic tin with respect to total tin (Sn(0)/Sn<sup>TOTAL</sup>) and Sn(0)/Pt ratio are also presented in Table 1. All supported bimetallic catalysts showed Sn(0)/Sn<sup>TOTAL</sup> and Sn(0)/Pt ratios of around 0.2 and 0.35, respectively. In this case, the existence of ionic tin is demonstrated. Its origin may be assigned to the migration of part of the tin, initially deposited onto the platinum via the reaction with SnBu<sub>4</sub>, to the platinum-support interface where it could be forming aluminate. It is important to mention that blank impregnation experiments of SnBu<sub>4</sub> onto  $\gamma$ -Al<sub>2</sub>O<sub>3</sub> demonstrated that in Pt absence there is no reaction between the or

**Table 1.** TEM and XPS results and denomination of the studied catalysts.

Catal.	Denom.	d <sub>TEM</sub> (nm)	K/Pt or Ba/Pt	Sn <sup>0</sup> /Sn <sup>Tot</sup> (Sn <sup>0</sup> /Pt)	Pt 4 $d_{5/2}$ (eV)	Sn 3 $d_{5/2}$ (eV)
Pt/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	Pt	1.8			314.8	
PtSn/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	PtSn	2.2		0.20 (0.32)	314.0	484.0 - 487.2
PtSnK/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	PtSnK	nd	10	0.21 (0.34)	315.0	483.6 - 487.3
PtSnBa/ $\gamma$ -Al <sub>2</sub> O <sub>3</sub>	PtSnBa	nd	8.5	0.22 (0.35)	314.3	484.3 - 487.3

ganometallic compound and the support. In relation to Sn(0) atoms, the existence of a PtSn alloy interacting with diluted metallic Pt atoms was shown in a previous paper by using EXAFS experiments for PtSn/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalysts. The evolution of active phases starting from the monometallic catalyst Pt/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> is shown in Scheme 1 (Siri *et al.*, 2005a).

**Scheme 1.** Representation of catalytic surface for PtSn catalysts.

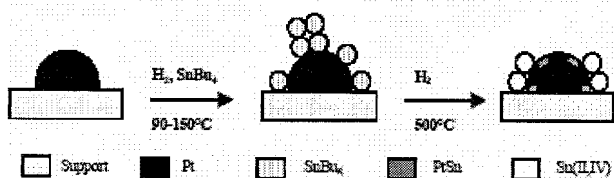

With respect to catalysts modified by Ba and K, an effect of electronic nature on the Pt is also observed. In this case, this effect is interpreted as a positive shift of 0.3 and 1 eV for Ba and K, respectively. This fact indicates that besides the known modifications that alkaline or alkaline earth metals produce on the acid-basic properties of the support (Siri *et al.*, 2005b), they also interact with the base metal as it appears from the changes observed in its electronic properties.

#### CO oxidation in hydrogen absence.


In these experiments, catalysts were previously reduced to 500 °C in H<sub>2</sub> atmosphere, then the hydrogen was replaced by Ar and the reactor was cooled up to a temperature of 50°C. Just in this moment, the reactive mixture was fed with the following composition: 1% CO, 0.6% O<sub>2</sub>, 9% He and 89.4% Ar. After two injections at the same conditions, the temperature was increased 50°C until reach a maximum temperature around 250°C. In this way, a precise information about the oxidizing properties with respect to the carbon monoxide is obtained for the different active phases by using a CO/O<sub>2</sub> ratio very near to the stoichiometric one. This means to be placed in the most possible severe condition with respect to the oxidation of CO to CO<sub>2</sub>. Results obtained are shown in Fig. 1, where it is possible to observe that all catalytic systems tested convert completely the CO at temperatures around 200°C.

Due to the reaction exothermicity, the existence of hot spots must not be discarded reaching in the solid phase temperatures higher than the ones really read by the thermocouple placed in the central sheath of the reactor (Ouyang and Besser, 2005). This situation would allow to explain the nature of the curves observed in this type of selective oxidation reactions of CO (Mariño *et al.*, 2004, Woosch *et al.*, 2004, Özdemir *et al.*, 2004, Dudfield *et al.*, 2001), where the conversion passes from values of about 15% to values of around 100% in a narrow temperature range; however, it is important to mention that this effect is interpreted by some authors as a change in the reaction mechanism as a function of the temperature (Bourane and Bianchi, 2004).

In Fig. 1, the monometallic catalyst of Pt presents the lowest activity level between the different catalysts tested, reaching a 15% CO conversion at 190°C. The bimetallic catalyst PtSn shows a better oxidation capacity since it reaches a conversion of about 15% at 160°C, while at 190°C, a 100% CO conversion is reached. Bimetallic PtSn catalysts modified with K or Ba are the ones that present the best activity levels achieving conversions of 15% at about 145°C reaching 100% at around 180°C.

Taking into account these results it is evident that the Sn as well as the K or Ba addition presents a promoter effect from the oxidizing capacity of the base metal (Pt). This is in agreement with that previously shown (Table 1) where it is possible to observe that the Sn addition to catalysts based on Pt modifies geometric and electronic properties of the active phase (Margitfalvi *et al.*, 2002, Akin *et al.*, 2001, Okanishi *et al.*, 2006). According to microcalorimetric studies it was possible to demonstrate that there is a strong diminution of the adsorption heat of the CO by the Sn addition to Pt/SiO<sub>2</sub> catalysts (Cortright and Dumesic, 1995), as the oxidation kinetics can be represented by an expression according to a Langmuir-Hinshelwood mechanism, where the CO appears in the denominator of such expression; this decrease of the adsorption heat allows to explain reasonably the increase of the catalytic activity (Akin *et al.*, 2001). On the other hand, the Sn as it arises from XPS results shown in Table 1 is present in important proportions as Sn ionic which confers it the capacity to promote the O<sub>2</sub> adsorption, followed by the reverse-spillover from the oxide onto Pt sites and surface reaction occurring on Pt sites between CO adsorbed and O (Grass and Lintz, 1997, Akin *et al.*, 2001).

The promotion of the CO oxidation by the addition of alkaline or alkaline earth metals (K, Ba) is in agreement with results reported in PdO/SnO<sub>2</sub> catalysts promoted by Na. In this case the catalyst showed an increase in the oxidizing activity of CO to CO<sub>2</sub>, explained

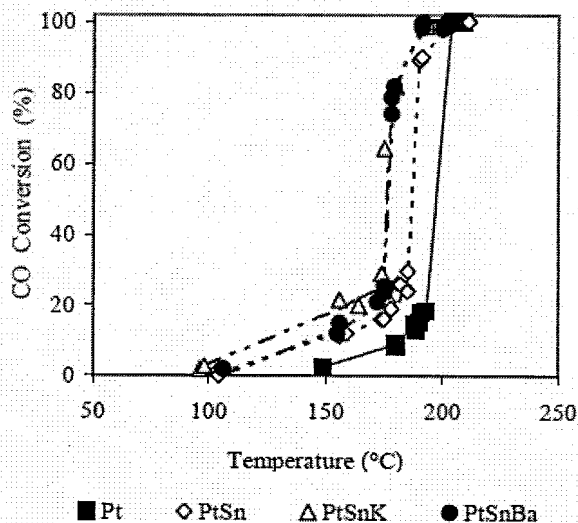


**Figure 1.** CO conversion as a function of the temperature for the different studied catalysts in H<sub>2</sub> absence. For experimental conditions see the text.

by the authors because of the formation of a ternary oxide (with the formula Na<sub>x</sub>Pd<sub>3</sub>O<sub>4</sub>) able to increase the O<sub>2</sub> storage capacity (Mirkelamoglu and Karakas, 2006).


#### CO oxidation in hydrogen presence.

In these experiments, catalysts were previously reduced at 500 °C in H<sub>2</sub> atmosphere, the reactor was cooled up to 50 °C and then the reactive mixture was fed with the following composition: 1% CO, 0.6% O<sub>2</sub>, 9% He and 89.4% H<sub>2</sub>. In this case an approximate stoichiometric ratio of CO/O<sub>2</sub> is maintained, for a H<sub>2</sub>/CO ratio around 90, which represents an extremely severe condition for the analysis of these systems from the point of view of the catalytic process.

Conversion results of CO and O<sub>2</sub> are shown in Fig. 2 and 3. In this case, in H<sub>2</sub> presence, the difference of the behavior between catalysts with and without Sn is ex-

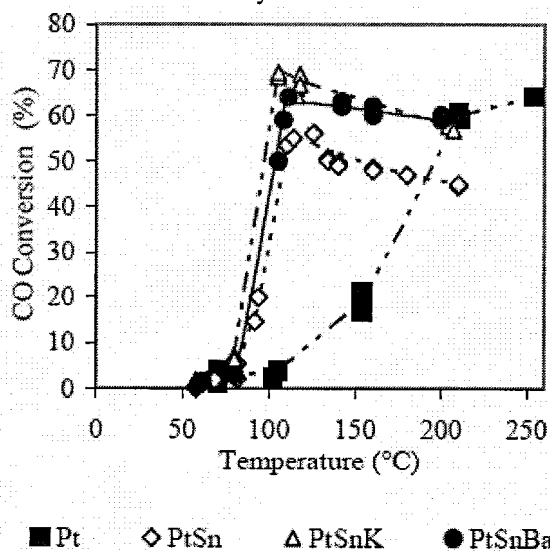

**Figure 2.** CO conversion as a function of the temperature for the different studied catalysts in H<sub>2</sub> presence. For experimental conditions see the text.

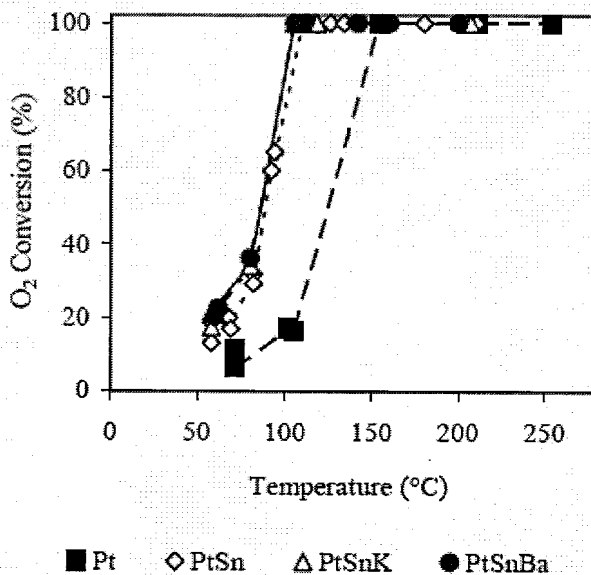

**Figure 3.** O<sub>2</sub> conversion as a function of the temperature for the different studied catalysts in H<sub>2</sub> presence. For experimental conditions see the text.

tremely marked. The monometallic catalyst shows that the CO conversion becomes appreciable at 100°C (3%), while the O<sub>2</sub> conversion reaches in these conditions the 15%. A 15% CO conversion is observed at 150°C and O<sub>2</sub> is completely consumed. At 210°C a CO conversion of about 68% is reached.

Defining the selectivity for the CO oxidation as the half of the CO<sub>2</sub> amount produced in relation to the O<sub>2</sub> amount consumed, it is clearly evident that at low temperatures the selectivity is low since the O<sub>2</sub> consumption is produced principally by water formation. The bimetallic catalyst PtSn produces the CO oxidation reaction at lower temperature than the monometallic catalyst. The selectivity increases with the temperature increase up to reaching a temperature of about 115°C. The maximum conversion reached is about 55%. A subsequent temperature increase decreases slightly the selectivity as it was also observed by Manasilp and Gulari (2002) and Kahlich *et al.* (1997). The addition of K or Ba decreases the temperatures of the CO maximum conversion as well as the total O<sub>2</sub> consumption. Multimetallic catalysts improve appreciably the activity of the CO oxidation and also the selectivity, as it is shown in Table 2.

In this case, where the selectivity at low temperatures depends on the relative activities of the oxidation of CO to CO<sub>2</sub> and the oxidation of H<sub>2</sub> to H<sub>2</sub>O, the mentioned effect, due to modifications in the CO adsorption in PtSn systems with respect to supported Pt, produces a selectivity increase. The decrease of the chemisorptive properties of both reagents influences on the reaction. On one hand, the decrease in the CO adsorption allows a higher reaction rate toward the CO<sub>2</sub> production due to a weakening of the strong interaction CO-Pt that originates the inhibition of the active sites (the global reaction order for the CO is negative). On the other hand, the decrease of the H<sub>2</sub> adsorption decreases the formation rate of water while the amount of active sites covered by this reagent diminishes.

In catalytic tests, the selectivity passes through a maximum with the temperature increase as it was observed in references (Manasilp and Gulari, 2002; Kahlich *et al.*, 1997). This analysis is quite complex and subject to interpretations that sometimes could be questionable. Generally, the occurrence of thermal effects produced by the strong exothermicity of involved reactions is not taken into account (reaction heats of CO to CO<sub>2</sub> = -2.83x10<sup>5</sup> J/mol and of H<sub>2</sub> to H<sub>2</sub>O = -2.42x10<sup>5</sup> J/mol, Ouyang and Besser, 2005). These thermal effects could explain the light off observed in Fig. 1, 2 and 3 (conversion vs. T), where it is clear that the slope of curves is lower in the monometallic Pt catalyst than in PtSn and PtSnK catalysts. These results are coherent with the higher oxidizing activity observed in multimetallic catalysts with respect to the monometallic one, which has a stronger Pt-CO interaction.

With conditions used in these tests, the reverse of water gas shift (RWGS) reaction must be taken into

**Table 2.** Maximum selectivities reached for the different studied catalysts.

Catalyst	Temperature (°C)	CO Selectivity (%)
Pt	200	50
PtSn	115	46
PtSnBa	111	53
PtSnK	105	58

**Table 3.** Values of the  $K_{eqCalc}$ ,  $T_{Calc}$ ,  $T_{React}$  and  $\Delta T = T_{Calc} - T_{React}$

Catalyst	$K_{eqCalc}$	$T_{Calc}$ (°C)	$T_{React}$ (°C)	$\Delta T$ (°C)
Pt	0.0062	190	210	-20
PtSn	0.0082	200	114	86
PtSnBa	0.0049	180	111	69
PtSnK	0.0034	170	105	65

account ( $CO_2 + H_2 \leftrightarrow CO + H_2O$ ). This reaction has been largely studied in homogeneous and heterogeneous catalysis associated in general to reactions that generate hydrogen or syngas, where it is accepted that the water gas shift reaction is in thermodynamic equilibrium (Wei and Iglesia, 2004). Taking this into account, the equilibrium constant was calculated from the exit compositions of the reactor ( $K_{eqCalc}$ ); with this value the temperature at which the thermodynamic equilibrium constant is equal at  $K_{eqCalc}$  was determined ( $T_{Calc}$ ). In Table 3, the temperature measured in the central sheath of the reactor ( $T_{React}$ ) and the estimated temperature ( $T_{Calc}$ ) was compared. The estimated temperature,  $T_{Calc}$ , would be an indicative of the actual temperature on the solid phase.

Table 3 shows for modified systems that, the estimated temperature is about 200°C, between 65-85°C, higher than the experimental value. Taking into account that the reverse of water gas shift reaction is found in almost thermodynamic equilibrium conditions, it is not surprising that the CO concentration remains about 0.5% and decreases as the temperature raises. For this reason, the search for systems reaching a high conversion of CO at low temperatures is very important to improve the global yields of this process. In our case, the best activities observed in bimetallic and multimetallic systems could be partially penalized by the RWGS reaction conversion assuming that the calculated reactor temperature ( $T_{Calc}$ ) gives a more real approximation of the temperature of the catalytic surface.

### III. CONCLUSIONS

The catalysts prepared for this work showed to be active for the CO oxidation in the presence of high H<sub>2</sub> concentrations at temperatures of about 200°C or lower.

The catalyst that showing maximum activity and selectivity is the PtSnK/  $\gamma$ -Al<sub>2</sub>O<sub>3</sub>. Addition of tin improves the activity and allows the reaction to occur at lower temperatures by a decrease in the CO-Pt interaction. The K or Ba addition produces a subsequent improvement with regard to the CO oxidation temperature, leading to a selectivity increase in the CO oxidation with respect to the H<sub>2</sub> oxidation.

The CO selectivity passes through a maximum value as a function of the temperature. This maximum is explained by the importance gained by the reverse of water gas shift reaction at temperatures near 200°C, which

is potentiated by thermal effects not always reported. The optimization of this process must take into account the search for catalytic systems that work at low temperature in order to avoid the influence of the RWGS reaction.

### REFERENCES

- Akin, A.N., G. Kilaz, A.I. Isli and Z.I. Onsan, "Development and characterization of Pt-SnO<sub>2</sub>/γ-Al<sub>2</sub>O<sub>3</sub> catalysts," *Chem. Engn. Sci.*, **56**, 881-888 (2001)
- Avgouropoulos, G. and T. Ioannides, "CO tolerance of Pt and Rh catalysts: effect of CO in the gas-phase oxidation of H<sub>2</sub> over Pt and Rh supported catalysts," *Appl. Catal. B: Env.*, **56**, 77-86 (2005).
- Bourane, A. and D. Bianchi, "Oxidation of CO on a Pt/Al<sub>2</sub>O<sub>3</sub> catalyst: from the surface elementary steps to light-off tests V. Experimental and kinetic model for light-off tests in excess of O<sub>2</sub>," *J. Catal.*, **222**, 499-510 (2004).
- Casella, M.L., G.J. Siri, G.F. Santori, O.A. Ferretti and M. Ramírez de Agudelo "Surface characterization of Li modified PtSn catalysts for isobutane dehydrogenation," *Langmuir*, **13**, 5639-5643 (2000).
- Cortright, R.D. and J.A. Dumesic, "Effects of potassium on silica-supported Pt and Pt/Sn catalyst for isobutane dehydrogenation," *J. Catal.*, **157**, 576-583 (1995).
- de Souza, T.R.O., A.J.S. Mascarenhas and H.M.C. Andrade, "Selective catalytic oxidation of CO in H<sub>2</sub>," *React. Kin. Catal. Lett.*, **87**, 3-9 (2006).
- Dudfield, C.D., R. Chen and P.L. Adcock, "A carbon monoxide PROX reactor for PEM fuel cell automotive application," *Int. J. of Hydrogen Energy*, **26**, 763-775 (2001).
- Farrauto, R. J., "Introduction to solid polymer membrane fuel cells and reforming natural gas for production of hydrogen," *Appl Catal B: Env.*, **56**, 3-7 (2005)
- Farrauto, R.J. and C.H. Bartholomew, *Fundamentals of Industrial catalytic Processes* Ed. Blackie Academic & Professional (1997)
- Grass, K. and H.G. Lintz, "The Kinetics of Carbon Monoxide Oxidation on Tin(IV) Oxide Supported Platinum Catalysts," *J. Catal.*, **172**, 446-452 (1997).
- Irusta, S., J. Múnera, C. Carrara, E.A. Lombardo and L.M. Cornaglia, "A stable, novel catalyst improves hydrogen production in a membrane reactor," *Appl Catal A: Gen.*, **287**, 147-158 (2005)
- Kahlich, M.J., H.A. Gasteiger and R.J. Behm "Kinetics of the Selective CO Oxidation in H<sub>2</sub>-Rich Gas on Pt/Al<sub>2</sub>O<sub>3</sub>," *J. Catal.*, **171**, 93-105 (1997).
- Kappenstein, C., M. Saouabé, M. Guérin, P. Marecot, I. Uszkurat and Z. Paál, "Characterization and activity of Pt-Sn/Al<sub>2</sub>O<sub>3</sub> catalysts of different preparation: coimpregnation and new Pt-Sn precursor," *Catal. Lett.*, **31**, 9-17 (1995)
- Manasilp, A. and E. Gulari, "Selective CO oxidation over Pt/alumina catalysts for fuel cell applications," *Appl. Catal. B: Env.*, **37**, 17-25 (2002)
- Margitfalvi, J. L., M. Hegedus, A. Szegedi and I. Sajó, "Modification of Au/MgO catalysts used in low temperature CO oxidation with Mn and Fe," *Appl. Catal. A: Gen.*, **282**, 87-97 (2004).
- Margitfalvi, J.L., I. Borbáth, M. Hegedus, Á. Szegedi, K. Lázár, S. Göbölös and S. Kristián, "Low temperature oxidation of CO over tin-modified Pt/SiO<sub>2</sub> catalysts," *Catalysis Today*, **73**, 343-353 (2002)
- Mariño, F., C. Descorme and D. Duprez, "Noble metal catalysts for the preferential oxidation of carbon monoxide in the presence of hydrogen (PROX)," *Appl. Catal. B: Env.*, **54**, 59-66 (2004).
- Mirkelamoglu, B. and G. Karakas, "The role of alkali-metal promotion on CO oxidation over PdO/SnO<sub>2</sub> catalysts," *Appl. Catal. A: Gen.*, **299**, 84-94. (2006).
- Okanishi, T., T. Matsui, T. Takeguchi, R. Kikuchi and K. Eguchi, "Chemical interaction between Pt and SnO<sub>2</sub> and influence on adsorptive properties of CO," *Appl. Catal. A: Gen.*, **298**, 181-187 (2006).
- Ouyang, X and R.S. Besser "Effect of reactor heat transfer limitations on CO preferential oxidation," *Chem. Journal of Power Sources*, **141**, 39-46 (2005).
- Özdemir, C., A.N. Akin and R. Yildirim, "Low temperature CO oxidation in hydrogen rich streams on Pt-SnO<sub>2</sub>/Al<sub>2</sub>O<sub>3</sub> catalyst using Taguchi method.," *Appl. Catal. A: Gen.*, **258**, 145-152 (2004).
- Ramallo López, J.M., G.F. Santori, L. Giovanetti, M.L. Casella, O.A. Ferretti and F.G. Requejo, "PS and XANES Pt L<sub>2,3</sub>-edge studies of dispersed metallic Pt and PtSn clusters on SiO<sub>2</sub> obtained by organometallic synthesis: structural and electronic characteristics," *J. Phys. Chem. B*, **107**, 11441-11451 (2003).
- Recupero, V., L. Pino, M. Cordaro, A. Vita, F. Cipitund and M. Lagana, "CO clean-up transient device integrated to a preferential oxidation reactor for PEFC electric vehicles," *Fuel Processing Technology*, **85**, 1445-1452 (2004).
- Roberts, G.W., P. Chin, X. Sun and J.J. Spivey "Preferential oxidation of carbon monoxide with Pt/Fe monolithic catalysts: interactions between external transport and the reverse water-gas-shift reaction," *Appl. Catal. B: Env.*, **46**, 601-611 (2003).
- Rodriguez, J.A., S. Chaturvedi, T. Jirsak and J. Hrbek, "Reaction of S<sub>2</sub> and H<sub>2</sub>S with Sn/Pt[111] surface alloys: Effects of metal-metal bonding on reactivity towards sulfur," *J. Chem. Phys.*, **109**, 4052-4062 (1998a).
- Rodriguez, J.A., T. Jirsak, S. Chaturvedi and J. Hrbek, "Surface Chemistry of SO<sub>2</sub> on Sn and Sn/Pt(111) Alloys: Effects of Metal-Metal Bonding on Reactivity toward Sulfur," *J. Am. Chem. Soc.*, **120**, 11149-11157 (1998b).
- Schubert, M.M., A. Venugopal, M. J. Kahlich, V. Plzak and R.J. Behm, "Influence of H<sub>2</sub>O and CO<sub>2</sub> on the selective CO oxidation in H<sub>2</sub>-rich gases over Au/α-Fe<sub>2</sub>O<sub>3</sub>," *J. Catal.*, **222**, 32-40 (2004).

- Shen, J., J.M. Hill, R.M. Watwe, B.E. Spiewak and J.A. Dumesic, "Microcalorimetric, Infrared Spectroscopic, and DFT Studies of Ethylene Adsorption on Pt/SiO<sub>2</sub> and Pt-Sn/SiO<sub>2</sub> Catalysts," *J. Phys. Chem. B*, **103**, 3923-3934 (1999)
- Shiau, C., M.W. Ma and C.S. Chuang, "CO oxidation over CeO<sub>2</sub>-promoted Cu/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> catalyst: Effect of preparation method," *Appl. Catal. A: Gen.*, **301**, 89-95 (2006).
- Siri, G.J., J.M. Ramallo López, M.L. Casella, J.L.G. Fierro, F.G. Requejo and O.A. Ferretti, "XPS and EXAFS study of supported PtSn catalysts obtained by surface organometallic chemistry on metals. Application to the isobutane dehydrogenation," *Appl. Catal. A: Gen.*, **278**, 239-249 (2005a).
- Siri, G.J., G.R. Bertolini, M.L. Casella and O.A. Ferretti, "PtSn/ $\gamma$ -Al<sub>2</sub>O<sub>3</sub> isobutane dehydrogenation catalysts: the effect of alkaline metals addition," *Mat. Lett.*, **59**, 2319-2324 (2005b).
- Siri, G.J., M.L. Casella, G.F. Santori and O.A. Ferretti, "Tin/platinum on alumina as catalyst for dehydrogenation of isobutane. Influence of the preparation procedure and of the addition of lithium on the catalytic properties of the catalyst," *IECR* 36 4821-4826 (1997)
- Stagg, S.M., C.A. Querini, W.E. Alvarez and D.E. Resasco "Isobutane Dehydrogenation on Pt-Sn/SiO<sub>2</sub> Catalysts: Effect of Preparation Variables and Regeneration Treatments," *J. Catal.*, **168**, 75-94 (1997).
- Takenaka, S., T. Shimizu and K. Otsuda, "Complete removal of CO in hydrogen-rich gas stream through methanation over supported metal catalysts," *Int. J. Hydrogen Energy*, **20**, 1065-1073 (2004).
- Tanaka, H., S. Ito, S. Kameoka, K. Tomishige and K. Kunimori, "Promoting effect of potassium in selective oxidation of CO in hydrogen-rich stream on Rh catalysts," *Catal Communication*, **4**, 1-4 (2003).
- Trimm, D., "Minimization of CO in a H<sub>2</sub> stream for fuel cell application," *Appl. Catal. A: Gen.*, **296**, 1-11 (2005).
- Wagner, C.D., *NIST X-Ray Photoelectron Spectroscopy Database*, Gathersburg (1989).
- Wei, J. and E. Iglesia, "Isotopic and kinetic assessment of the mechanism of reactions of CH<sub>4</sub> with CO<sub>2</sub> or H<sub>2</sub>O to form synthesis gas and carbon on nickel catalysts," *J. Catal.*, **224**, 370-383 (2004).
- Wootsch, A., C. Descorme and D. Duprez, "Preferential oxidation of carbon monoxide in the presence of hydrogen (PROX) over ceria-zirconia and alumina-supported Pt catalysts," *J. Catal.*, **225**, 259-266 (2004).

Received: May 12, 2006

Accepted: March 20, 2007

Recommended by Subject Editor: Ana Lea Cukierman

