

Defence Science Journal, Vol. 59, No. 1, January 2009, pp. 82-95
© 2009, DESIDOC

Microencapsulation Technology and Applications

Rama Dubey, T.C. Shami and K.U. Bhasker Rao

Defence Materials & Stores Research & Development Establishment, Kanpur- 208 013

ABSTRACT

Microencapsulation technology allows a compound to be encapsulated inside a tiny sphere known as microsphere/microcapsule, having an average diameter as small as 1 μm to several hundred micro meters. Many different active materials like drugs, enzymes, vitamins, pesticides, flavours and catalysts have been successfully encapsulated inside microballoons or microcapsules made from a variety of polymeric and non polymeric materials including poly(ethylene glycol)s, poly(methacrylate)s, poly(styrene)s, cellulose, poly(lactide)s, poly(lactide-co-glycolide)s, gelatin and acacia, etc. These microcapsules release their contents at appropriate time by using different release mechanisms, depending on the end use of encapsulated products. This technology has been used in several fields including pharmaceutical, agriculture, food, printing, cosmetic, textile and defence. In defence sector this technology has introduced the concept of self-healing composites as well as chemical decontaminating fabrics. This review paper highlights the major reasons behind microencapsulation, important techniques of microencapsulation and application of microencapsulated products in different areas of science and technology.

Keywords: Microencapsulation technology, microcapsule, release mechanisms, pharmaceuticals, polymers, stabilizers, emulsion

1. INTRODUCTION

Microencapsulation¹ is a technique by which solid, liquid or gaseous active ingredients are packaged within a second material for the purpose of shielding the active ingredient from the surrounding environment. Thus the active ingredient is designated as the core material whereas the surrounding material forms the shell. This technique has been employed in a diverse range of fields from chemicals and pharmaceuticals to cosmetics and printing. For this reason, widespread interest has developed in microencapsulation technology. Preparation of microcapsules dates back to 1950s when Green and Schleicher^{2,3} produced microencapsulated dyes by complex coacervation of gelatin and gum arabic, for the manufacture of carbonless copying paper. To this day, carbonless copy paper is one of the most significant products to utilize microencapsulation technology, and is still produced commercially. The technologies developed for carbonless copy paper have led to the development of various microcapsule products in later years.

In the 1960s, microencapsulation of cholesteric liquid crystal by complex coacervation of gelatin and acacia was reported to produce a thermosensitive display material. J. L. Ferguson developed nematic curvilinear aligned phase (NCAP), a liquid crystal display system by microencapsulation of nematic liquid crystal⁴. Encapsulation technology has provided the enlargement of display areas and wider viewing angles.

In defence applications this technology is used for fabrication of self-healing composites⁵⁻¹⁰ which form an

integral part of aerospace structures. Microencapsulation is also used for designing special fabrics for military personnel for their enhanced chemical protection against chemical warfare¹¹. Thus, since the mid of 1970s, microencapsulation has become increasingly popular in pharmaceutical industry as well as for many other products and processes in daily use.

2. CLASSIFICATION

Microcapsules can be classified on the basis of their size or morphology.

2.1 Micro/Nanocapsules

Microcapsules range in size from one micron (one thousandth of a mm) to few mm. Some microcapsules whose diameter is in the nanometer range are referred to as nanocapsules to emphasize their smaller size.

2.2 Morphology Microcapsules

Microcapsules can be classified into three basic categories as monocored, polycored and matrix types as shown in Fig. 1. Monocored microcapsules have a single hollow chamber within the capsule. The polycore microcapsules have a number of different sized chambers within the shell. The matrix type microparticle has the active ingredients integrated within the matrix of the shell material. However, the morphology of the internal structure of a microparticle depends largely on the selected shell materials and the microencapsulation methods that are employed.

Received 8 October 2007, revised 10 July 2008

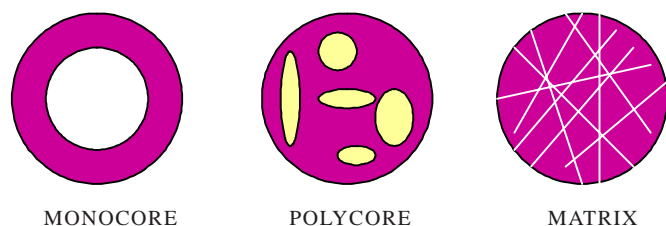


Figure 1. Different types of microcapsules.

3. IMPORTANT FEATURE OF MICROCAPSULES

The most significant feature of microcapsules is their microscopic size that allows for a huge surface area, for example, the total surface area of $1\ \mu\text{m}$ of hollow microcapsules having a diameter of $0.1\ \mu\text{m}$ has been reported to be about $60\ \text{m}^2$. The total surface area is inversely proportional to the diameter. This large surface area is available for sites of adsorption and desorption, chemical reactions, light scattering, etc. More detailed features of microcapsules are summarised in books by Gutcho¹² and Arshady¹³.

4. REASONS FOR MICROENCAPSULATION

Microencapsulation of materials is resorted to ensure that the encapsulated material reaches the area of action without getting adversely affected by the environment

through which it passes. Amongst the principal reasons for encapsulation are:

1. Separation of incompatible components
2. Conversion of liquids to free flowing solids
3. Increased stability (protection of the encapsulated materials against oxidation or deactivation due to reaction in the environment)
4. Masking of odour, taste and activity of encapsulated materials
5. Protection of the immediate environment
6. Controlled release of active compounds (sustained or delayed release)
7. Targeted release of encapsulated materials

5. TECHNIQUES OF MICROENCAPSULATION

Although a variety of techniques have been reported for microencapsulation¹⁴⁻²⁴, they can broadly be divided into two main categories (Table 1)²⁵⁻⁸³. The first category includes those methods in which starting materials are monomers/prepolymers. In these methods chemical reactions are also involved along with microsphere formation. The second category consists of those methods in which starting materials are polymers. Hence, in these methods no chemical reactions are involved and only shape fabrication takes

Table 1. Major Microencapsulation methods

Microencapsulation methods	Materials Investigated Shell[core]	Applications	References
<i>Chemical methods</i>			
Suspension Polymerization	Poly(styrene)[PCM]	Textile	25, 26
Emulsion Polymerization	Poly(alkyl acrylate)s[insulin]	Drug delivery	27, 28
Dispersion	Poly(2-hydroxyethyl-co-glycidyl methacrylate)[ferrofluid] , Poly (N-vinyl α -phenylalanine)[fluorescein isothiocyanate]	Biosciences	29, 30
Interfacial	Polyurea[insecticides, catalysts], Polyamide[oils], Polyurethane [insecticides], polyester[protein]	Crop protection, Catalysis, drug delivery	31-49
<i>Physical/Mechanical methods</i>			
Suspension crosslinking	Protein, Albumin[doxorubicin, magnetite], Polysaccharides	Drug delivery	50-52
Solvent evaporation/extraction	Poly(Lactide),Poly(Lactide-co-glycolide) [Drugs]	Drug delivery	53-61
Coacervation/phase separation	Protein, Polysaccharides, Ethyl cellulose, gelatin[Drugs]	Drug delivery	62-66
Spray drying	Polymers[Food ingredients]	Food Technology	67-70
Fluidized bed coating	Gelatin, carbohydrates, lipids	Food Technology	71-73
Melt solidification	Polyanhydride[insulin]	Food Technology	74
Precipitation	Phenolic polymers [enzymes]	Biocatalysis	75
Co-extrusion	Polyacrylonitrile[hepatocytes]	Biomedical	76, 77
Layer by Layer deposition	Polyelectrolytes[organic compounds]	Biosensor	78,79
Microencapsulation methods	Materials Investigated Shell[core]	Applications	References
Supercritical fluid expansion	Poly(ethylene glycol)[felodipine]	Drug delivery	80, 81
Spinning disk	Paraffin	Food engineering	82, 83

place.

Generally the choice of the microencapsulation method depends on the nature of the polymeric/monomeric material used. Thus appropriate combination of starting materials and synthesis methods can be chosen to produce microencapsulated products with a wide variety of compositional and morphological characteristics. For example, poly (alkyl cyanoacrylate) nanocapsules are obtained by emulsion polymerisation²⁷, whereas reservoir type nylon microcapsules are usually prepared by interfacial polymerisation⁴⁸⁻⁴⁹. Similarly albumin microcapsules are prepared by suspension crosslinking⁵¹, polylactide microcapsules by solvent evaporation/solvent extraction⁵³ and gelatin and related products by coacervation⁶³. Some of the important and most common microencapsulation techniques are discussed in detail below.

5.1 Emulsion polymerisation

According to this technique²⁸ the monomer (alkyl acrylates) is added dropwise to the stirred aqueous polymerisation medium containing the material to be encapsulated (core material) and a suitable emulsifier. The polymerisation begins and initially produced polymer molecules precipitate in the aqueous medium to form primary nuclei. As the polymerisation proceeds, these nuclei grow gradually and simultaneously entrap the core material to form the final microcapsules. Generally lipophilic materials (insoluble or scarcely soluble in water) are more suitable for encapsulation by this technique. Insulin loaded poly (alkyl cyanoacrylate) nanocapsules²⁷

have been synthesised by using this technique. In addition to the entrapment of drug during microcapsule formation, drug loading can also be accomplished by incubation of cyanoacrylate nanocapsules (empty nanocapsules) with the dissolved or finely dispersed drug.

5.2 Interfacial polycondensation

As the term "interfacial" implies, this technique involves the polycondensation (condensation polymerization) of two complementary monomers at the interface of a two phase system³¹⁻³⁴. For the preparation of microcapsules, this two-phase system is mixed under carefully-controlled conditions to form small droplets of one phase (dispersed phase) in the other one (continuous phase/suspension medium). The material to be encapsulated must be chosen in such a way as to be present (dissolved or dispersed) in the droplets. It is also necessary to use a small amount of a suitable stabilizer to prevent droplet coalescence or particle coagulation during the polycondensation process and capsule formation. Interfacial polycondensation can be utilized to produce both monocore type or matrix type microcapsules, depending on the solubility of the polycondensate in the droplet phase. The two basic mechanisms leading to the formation of both types of microcapsules are schematically depicted in Fig. 2⁸⁴. Thus if the polymer is soluble in the droplets, matrix type microcapsules are formed. On the other hand, if the polymer is not soluble, it precipitates around the droplets and leads to the formation of monocore type microcapsules. Preparation of microcapsules

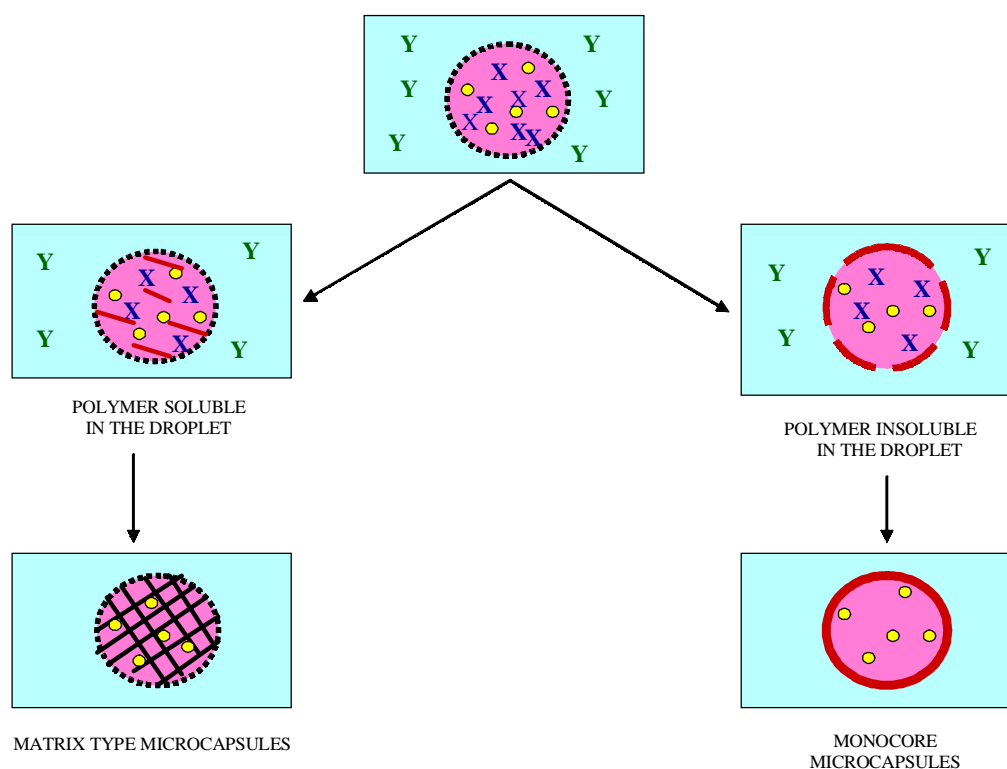


Figure 2. Mechanism of matrix type or monocore type microcapsule formation by interfacial polymerization (X and Y are bifunctional monomers).

by interfacial polycondensation is applicable to a large number of polymers including polyamides³⁵⁻³⁷, polyureas³⁸⁻⁴¹, polyurethanes⁴²⁻⁴⁵ and polyesters^{46,47}. In either case, the process can be adopted to produce micrometer or nanometer size particles. Polyurea microcapsules encapsulating osmium tetroxide have been synthesised by using this technique³⁹.

5.3 Suspension crosslinking

Suspension crosslinking is the method of choice for the preparation of protein and polysaccharide micro-capsules^{50,51}. Microcapsule formation by this technique involves dispersion of an aqueous solution of the polymer containing core material in an immiscible organic solvent (suspension/dispersion medium) in the form of small droplets. The suspension medium contains a suitable stabilizer to maintain the individuality of the droplet/microcapsules. The droplets are subsequently hardened by covalent crosslinking and are directly converted to the corresponding microcapsules. The crosslinking process is accomplished either thermally (at >500 °C) or by the use of a crosslinking agent (formaldehyde, terephthaloyl chloride, etc). Suspension crosslinking is a versatile method and can be adopted for microencapsulation of soluble, insoluble, liquid or solid materials, and for the production of both micro and nanocapsules. Albumin nanocapsules containing doxorubicin and magnetite particles have been synthesised by using this technique⁵².

5.4 Solvent Evaporation/Solvent Extraction

Microcapsule formation by solvent evaporation/solvent extraction⁵³⁻⁶⁰ is very similar to suspension crosslinking, but in this case the polymer is usually hydrophobic polyester.

The polymer is dissolved in a water immiscible volatile organic solvent like dichloromethane or chloroform, into which the core material is also dissolved or dispersed. The resulting solution is added dropwise to a stirring aqueous solution having a suitable stabilizer like poly (vinyl alcohol) or polyvinylpyrrolidone, etc. to form small polymer droplets containing encapsulated material. With time, the droplets are hardened to produce the corresponding polymer microcapsules. This hardening process is accomplished by the removal of the solvent from the polymer droplets either by solvent evaporation (by heat or reduced pressure), or by solvent extraction (with a third liquid which is a precipitant for the polymer and miscible with both water and solvent). Solvent extraction produces microcapsules with higher porosities than those obtained by solvent evaporation. Figure 3 shows a schematic representation of microencapsulation by solvent evaporation technique. Solvent evaporation/extraction processes is suitable for the preparation of drug loaded microcapsules based on the biodegradable polyesters such as polylactide, poly (lactide-co-glycolide) and polyhydroxybutyrate⁶¹.

5.5 Coacervation/Phase separation

Coacervation⁶² (or phase separation) is widely employed for the preparation of gelatin^{63,64} and gelatin-acacia⁶⁵ microcapsules, as well as for a large number of products

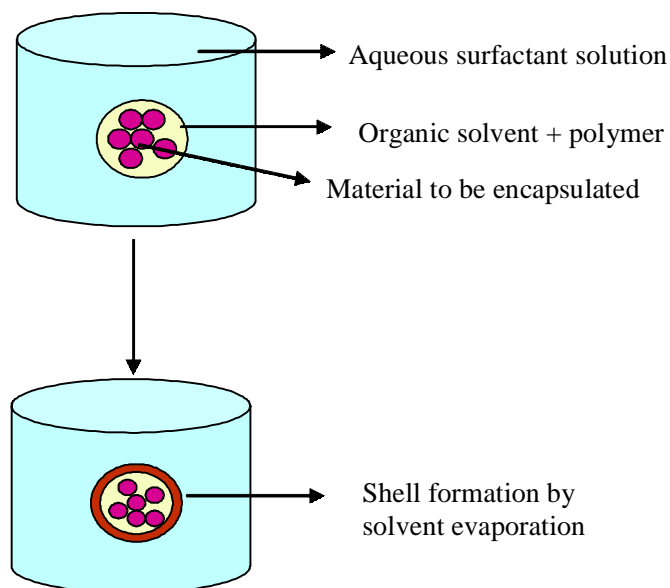


Figure 3. Schematic representation of microencapsulation by solvent evaporation technique.

based on cellulose derivatives and synthetic polymers⁶⁶. Phase separation processes are divided into simple and complex coacervation. Simple coacervation involves the use of a single polymer such as gelatin or ethyl cellulose, in aqueous or organic media, respectively. Complex coacervation involves two oppositely charged polymeric materials such as gelatin and acacia, both of which are soluble in aqueous media. In both the cases, coacervation is brought about by gradual desolvation of the fully solvated polymer molecules. Microencapsulation by coacervation is carried out by preparing an aqueous polymer solution (1-10 %) at 40-50 °C into which the core material (hydrophobic) is also dispersed. A suitable stabilizer may also be added to the mixture to maintain the individuality of the final microcapsules. A suitable desolvating agent (coacervating agent) is gradually introduced to the mixture, which leads to the formation of partially desolvated polymer molecules, and hence their precipitation on the surface of the core particles. The coacervation mixture is cooled to about 5-20 °C, followed by the addition of a crosslinking agent to harden the microcapsule wall formed around the core particles. Gelatin microcapsules loaded with carboquone⁶⁴ as well as gelatin acacia microcapsules loaded with sulfamethoxazole⁶⁵ have been produced by coacervation.

5.6 Other Techniques

In addition to the microencapsulation techniques described above, microencapsulation can also be carried out by spray drying⁶⁷⁻⁷⁰, fluidised bed coating⁷¹⁻⁷³, melt solidification⁷⁴, polymer precipitation⁷⁵, co-extrusion^{76, 77}, layer-by-layer deposition^{78, 79}, supercritical fluid expansion^{80,81}, and spinning disk^{82,83}.

Microencapsulation by spray drying is a low cost commercial process, which is mostly used for the encapsulation of fragrances, oils and flavors. In this process, an emulsion

is prepared by dispersing the core material, usually an oil or active ingredient immiscible with water, into a concentrated solution of wall material. The resultant emulsion is atomized into a spray of droplets by pumping the slurry through a rotating disc into the heated compartment of a spray drier. There the water portion of emulsion is evaporated, yielding dried capsules containing core material. Lycopene has been microencapsulated inside gelatin microcapsules by using this technique⁷⁰.

Fluidised bed coating⁷¹⁻⁷³ is used for encapsulation of solid core materials including liquids absorbed into porous solids. This technique is used extensively to encapsulate pharmaceuticals. Solid particles to be encapsulated are suspended in a jet of air and then covered by a spray of liquid coating material. The capsules are then moved to an area where their shells are solidified by cooling or solvent vaporization. The process of suspending, spraying and cooling is repeated until the capsule walls are of the desired thickness. Ascorbic acid has been microencapsulated in polymethacrylate as well as ethyl cellulose by using this technique⁷².

Biodegradable microcapsules are also produced by the solidification of molten polymer droplets⁷⁴ or by polymer precipitation⁷⁵. A dispersion of the drug in molten polymer is stirred in silicone oil to produce small droplets of the polymer drug mixture. The suspension mixture is then cooled, and the resulting solidified microcapsules are separated from the oil. Insulin has been microencapsulated in polyanhydride⁷⁴ by using this technique. In the polymer precipitation process, an aqueous solution of the polymer containing the drug is dropped into a stirred solution, which acts as the precipitating medium. Here, the polymer droplets precipitate immediately and are thus converted into the drug loaded microcapsules. Enzymes have been encapsulated in conjugated phenolic polymers by using this technique⁷⁵.

The co-extrusion process^{76,77} also possess a number of commercial applications. In this process a dual fluid stream of liquid core and shell materials is pumped through concentric tubes and forms droplets under the influence of vibration. The shell is then hardened by chemical crosslinking, cooling or solvent evaporation. Hepatocytes have been encapsulated in polyacrylonitrile⁷⁷ by using this technique.

One important method of microencapsulation is layer-by-layer deposition^{78,79}. In this process polyelectrolyte multilayers are prepared by sequentially immersing a substrate in positively and negatively charged polyelectrolyte solutions in a cyclic procedure. Core shell particles with tailored size and properties are prepared using colloidal particles as the core material that serves as a template onto which multilayers are fabricated. Hollow capsules of organic, inorganic or hybrid particles can be obtained by dissolving the core material. This technique is both versatile and simple, with the multiplayer film thickness being controlled precisely by varying the total number of layers deposited. In this way the final properties can be tuned. Glucose oxidase has been microencapsulated by alternate deposition of

polyallylamine and polystyrene sulfonate layers⁷⁸.

Microencapsulation has also been carried out by rapid expansion of supercritical fluid^{80,81}. Supercritical fluids are highly compressed gases that possess several advantageous properties of both liquids and gases. Most widely used ones are supercritical CO₂, alkanes (C₂ to C₄) and nitrous oxide (N₂O). Supercritical CO₂ is widely used for its low critical temperature value in addition to its non-toxic and non-flammable properties. It is also readily available, highly pure and cost effective. It has found applications in encapsulating active ingredients by polymers. Different core materials such as pesticides, pigments, pharmaceutical ingredients, vitamins, flavors and dyes have been encapsulated by using this method. A wide variety of shell materials that either dissolve (paraffin wax, acrylates, polyethylene glycol) or do not dissolve (proteins, polysaccharides) in supercritical CO₂ are used for encapsulating core substances. In this process, supercritical fluid containing the active ingredient and the shell material are maintained at high pressure and then released at atmospheric pressure through a small nozzle. The sudden drop in pressure causes desolvation of the shell material, which is then deposited around the active ingredient (core) and forms a coating layer. Felodipine has been encapsulated in poly(ethylene glycol) by using this technique⁸¹.

In the spinning disc^{82,83} method the microencapsulation of suspended core materials is carried out by using a rotating disc. Suspensions of core particles in liquid shell material are poured into a rotating disc and due to the spinning action of the disc, the core particles become coated with the shell material. The coated particles along with the excess shell material are then cast from the edge of the disc by centrifugal force, after which the shell material is solidified by external means (usually cooling). This technology is rapid, cost effective, simple and has high production efficiencies. Paraffin microbeads have been synthesized by using this technique⁸².

6. RELEASE MECHANISMS

Different release mechanisms of encapsulated materials provide controlled, sustained or targeted release of core material. Generally there are three different mechanisms by which the core material is released from a microcapsule - mechanical rupture of the capsule wall, dissolution or melting of the wall, and diffusion through the wall. Less common release mechanisms include ablation (slow erosion of the shell) and biodegradation. The release mechanism depends on the nature of application, for example, carbonless copy paper, scratch and sniff perfumes, and self healing structures rely on mechanical rupture of shell to release the core contents. The rupture may be caused by pressure as in case of carbonless copy paper and scratch and sniff perfumes or due to propagation of cracks as for self-healing structures. In the self-healing structures microcapsules act as means of storing and delivering an *in situ* glue, to prevent the spread of cracks. Thus a microencapsulated healing agent and a catalyst known to trigger polymerization in the chosen agent is embedded in a composite matrix. Rupture of any

microcapsules by an approaching crack defect releases the healing agent into the crack plane by capillary action. When the released healing agent comes in contact with the catalyst, the resulting polymerization bonds the crack face closed, stopping the defect in its track. For example urea formaldehyde microencapsulated dicyclopentadiene (DCPD) healing agent and Grubb's Ru catalyst have been incorporated into an epoxy matrix to produce a polymer composite capable of self healing⁸⁵.

Detergent industry utilises dissolution of shell wall of powder detergents for release of encapsulated protease enzyme in order to remove bloodstains from the clothing. In food industry baking mixes encapsulated in fat are released after shell melting (when proper temperature is reached) to react with food acid to produce leavening agents, which gives baked goods their volume and lightness of texture. In food industry some ingredients such as nutrients are encapsulated to mask taste, and flavorings are encapsulated due to their volatile nature, that would otherwise evaporate out and be lost as in chewing gum.

Pesticides are microencapsulated to be released over time, allowing farmers to apply the pesticides less often rather than requiring very highly concentrated and toxic initial applications. Similarly, in pharmaceutical industry microencapsulated products are designed for sustained/controlled release by either biodegradation of the shell, or by diffusion through the shell. Aspirin, for example provides effective relief from fever, inflammation and arthritis, but direct doses of aspirin can cause peptic ulcers and bleeding. The drug is, therefore, encapsulated in ethyl cellulose or hydroxypropylmethyl cellulose and starch. In this way the aspirin diffuses through the shell in a slow, sustained dose rather than being released all at once. Insulin has also been encapsulated in biodegradable polylactic acid microcapsules for its controlled release into the body⁸⁶.

One of the important diffusion controlled defence application is novel clothing fabric, which contains microcapsules composed of chemical decontaminants encapsulated within semipermeable polymers. The polymer being selectively permeable to toxic chemical agents but impermeable to the decontaminating agents, thereby allowing the toxic chemicals to diffuse into the microcapsules where they undergo irreversible detoxifying chemical reactions¹¹.

7. APPLICATIONS

7.1 Agriculture

One of the most important applications of microencapsulated products is in the area of crop protection⁸⁷⁻⁹³. Nowadays insect pheromones are becoming viable as a biorational alternative to conventional hard pesticides. Specifically, sex-attractant pheromones can reduce insect populations by disrupting their mating process. Hence small amounts of species-specific pheromone are dispersed during the mating season, raising the background level of pheromone to the point where it hides the pheromone plume released by its female mate^{91,93}. Polymer microcapsules, polyurea⁹², gelatin

and gum arabic⁹³ serve as efficient delivery vehicles to deliver the pheromone by spraying the capsule dispersion. Further, encapsulation protects the pheromone from oxidation and light during storage and release.

7.2 Pharmaceuticals

One of the major applications area of encapsulation technique is pharmaceutical/biomedical for controlled/sustained drug delivery⁹⁴⁻¹⁰³. Potential applications of this drug delivery system are replacement of therapeutic agents (not taken orally today like insulin)^{104,105}, gene therapy¹⁰⁶⁻¹⁰⁹ and in use of vaccines for treating AIDS¹¹⁰⁻¹¹², tumors^{113,114}, cancer¹¹⁵ and diabetes¹¹⁶⁻¹¹⁸. Protein such as insulin, growth hormone^{119,120}, and erythropoietin^{121,122} (used to treat anemia) are example of drugs that would benefit from this new form of oral delivery. The delivery of corrective gene sequences in the form of plasmid DNA¹²³ could provide convenient therapy for a number of genetic diseases such as cystic fibrosis^{124,125} and hemophilia¹²⁶. The spheres are engineered to stick tightly to and even penetrate linings in the gastrointestinal track before transferring their contents over time into circulatory system¹²⁷.

Based on this novel drug delivery technique, Lupin has already launched in the market worlds first Cephalexin (Ceff-ER) and Cefadroxil (Odoxil OD) antibiotic tablets for treatment of bacterial infections. Aspirin controlled release version ZORprin CR tablets are used for relieving arthritis symptoms. Quinidine gluconate CR tablets are used for treating and preventing abnormal heart rhythms. Niaspan CR tablet is used for improving cholesterol levels and thus reducing the risk for a heart attack. Glucotrol (Glipizide SR) is an anti diabetic medicine used to control high blood pressure.

7.3 Food Industry

Currently there is a trend towards a healthier way of living, which includes a growing awareness by consumers for what they eat and what benefits certain ingredients have in maintaining good health. Preventing illness by diet is a unique offering of innovative so called "functional foods", many of which are augmented with ingredients to promote health. However simply adding ingredients to food products to improve nutritional value can compromise their taste, colour, texture and aroma. Sometimes they slowly degrade and lose their activity, or become hazardous by oxidation reactions. Ingredients can also react with components present in the food system, which may limit bioavailability. Microencapsulation is used to overcome all these challenges by providing viable texture blending, appealing aroma release, and taste, odour and colour masking¹²⁸⁻¹³³. The technology enables food companies to incorporate minerals, vitamins, flavours and essential oils. In addition, microencapsulation can simplify the food manufacturing process by converting liquids to solid powder, decreasing production costs by allowing batch processing using low cost, powder handling equipment. Microcapsules also help fragile and sensitive

materials survive processing and packaging conditions and stabilize the shelf life of the active ingredient¹³⁴.

7.4 Energy Generation

Hollow plastic microspheres loaded with gaseous deuterium (a fusion fuel) are used to harness nuclear fusion for producing electrical energy¹³⁵. The capsules are multilayered. The inner layer, which compresses the fuel, is a polystyrene shell about 3 μm thick. Next is a layer of poly(vinyl alcohol) about 3 μm thick, that retards diffusion of deuterium out of the capsule. The outer layer (the ablator) is about 50 μm thick and consists of a highly crosslinked polymer made from 2-butene. During the fusion experiments, energy from high powered laser beams is absorbed by the surface of the microcapsule shell. As the outside of the shell (called ablator) burns off, the reaction force accelerates the rest of the shell inward, compressing and heating the deuterium inside. This results in high densities and temperature in the centre of the capsule leading to the fusion of deuterium nuclei to give tritium, helium and other particles releasing an enormous amount of energy. This process has been named as inertial confinement fusion (ICF). Such ICF targets made of organic microcapsules have been in use since 1980s.

7.5 Catalysis

Transition metal based catalytic processes are of vital importance to pharmaceutical, agrochemical and fine chemical industries. A vast proportion of such catalytic metal species are often expensive and toxic, thereby making operational handling potentially hazardous. Microencapsulation has recently been recognized as a useful alternative strategy to enable safe handling, easy recovery, reuse and disposal at an acceptable economic cost. Polyurea microcapsules due to their insolubility in aqueous and organic solvents, and resistance towards degradation have been used for encapsulation of different catalysts. Metal species such as palladium (II) acetate and osmium tetroxide have been encapsulated in polyurea microcapsules and used successfully as recoverable and reusable catalysts without significant leaching and loss of activity^{39,40}. It is thought that the urea functionality, which forms the backbone of the polymer, ligates and retains the metal species within the polymeric matrix. Futuristic trend is towards incorporation of other chelating and ligating functional groups within the polyurea framework to study rate enhancement in such reactions, and trying other polymers for encapsulation.

7.6 Defence

One of the important defence applications of microencapsulation technology is in self-healing polymers and composites¹³⁶⁻¹⁴². They possess microencapsulated healing agents embedded within the matrix and offer tremendous potential for providing long-lived structural materials. The microcapsules in self-healing polymers not only store the healing agent during quiescent states, but provide a mechanical trigger for the self-healing process when damage occurs

in the host material and the capsules rupture. The microcapsules possess sufficient strength to remain intact during processing of the host polymer, yet rupture when the polymer is damaged. High bond strength to the host polymer combined with a moderate strength microcapsule shell are required. To provide long shelf life the capsules must be impervious to leakage and diffusion of the encapsulated healing agent for considerable time. These combined characteristics are achieved with a system based on the *in situ* polymerisation of urea-formaldehyde microcapsules encapsulating dicyclopentadiene healing agent¹⁴³. The addition of these microcapsules to an epoxy matrix also provides a unique toughening mechanism for the composite system. Such microcapsules have tremendous application in aerospace area for making self-repairable spacecrafts. Such self-healing spacecrafts open up the possibility of longer duration missions by increasing the lifetime of a spacecraft.

Microencapsulation is also used for designing special fabrics for military personnel, for their enhanced chemical protection against chemical warfare¹¹. For this purpose special reactive microcapsules have been developed which can be applied to fabrics or finished garments to provide reactive sites for neutralisation of chemical reagents. This involves microencapsulation of conventional decontamination chemicals that are currently effective for deactivation of toxic mustard blistering agents (H agents) and toxic nerve agents known conventionally as G agents, for example isopropylmethyl phosphonofluoridate (GB, sarin) and the V agents, and formulation of the microcapsules in a resin finish that can be uniformly applied to fabric substrates. The preferred microcapsules containing a decontaminating agent were obtained by organic phase separation with ethyl cellulose microcapsules containing a solid decontamination agent consisting of sym-bis (N-chloro-2,4,6-trichlorophenyl) urea and ZnO. The microcapsules were then bonded to the fabric with an acrylic binder emulsion. The very thin walls (1 to 10 microns) of microcapsules allow for rapid agent permeation for optimum decontamination and thus protect the wearer from toxic chemical agents.

8. STATUS OF MICROENCAPSULATION RESEARCH IN DMSRDE

Defence Materials and Stores Research and Development Establishment, Kanpur is actively working in this area since last four years and has developed expertise in microencapsulation technology by using two techniques. One is solvent evaporation and the other one is interfacial polymerisation. Characterisation of all the synthesised microcapsules was done by using optical microscope (OM, Leica) and scanning electron microscope (SEM, Zeiss).

Polymethylmethacrylate (PMMA) was selected as the polymer for encapsulation using solvent evaporation technique. Different materials like carbon nanotubes (CNTs), polyaniline, carbon microcoils (CMCs) and magnetic nanoparticles have been successfully encapsulated inside PMMA microcapsules. In a typical synthesis for encapsulation of polyaniline,



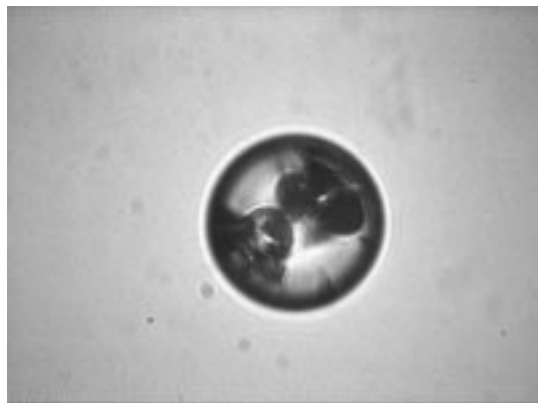


Figure 4. Optical micrograph of polyaniline encapsulated PMMA microcapsule.

PMMA was first dissolved in a low boiling solvent like dichloromethane/chloroform with the help of magnetic stirring. Polyaniline was added into the stirring solution. This solution was then added dropwise to a stirring emulsifier (polyvinyl alcohol/polyvinyl pyrrolidone) solution. The mixture was kept stirring till the evaporation of the solvent. After that, the polyaniline encapsulated PMMA microcapsules were collected by filtration, washed with water and dried. Figure 4 shows the optical micrograph of polyaniline encapsulated

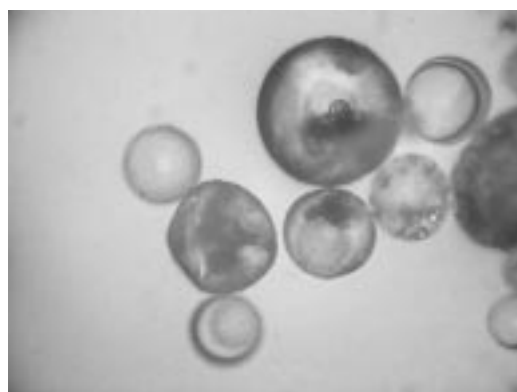

(a)

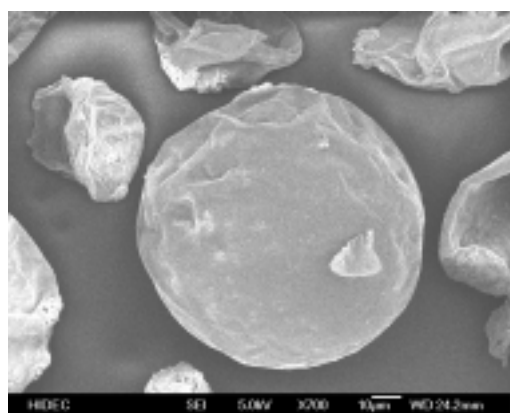

(b)

Figure 5. Optical (a) and SEM (b) micrographs of ferrofluid coated ZnO nanoparticles encapsulated polyamide microcapsules.

PMMA microcapsules. The formation of microcapsule is clearly evident from the micrograph. A perfect sphere is seen with the presence of green polyaniline inside the sphere. Using the same procedure microencapsulation of other materials was also carried out.

For microencapsulation of materials by utilising interfacial polymerisation technique, polyamide was selected as the polymer. Two types of materials, ferrofluid coated ZnO nanostructures and ferrofluid were encapsulated inside the polyamide microcapsules. For carrying out the microencapsulation, terephthaloyl chloride was dissolved in toluene followed by addition of the core material. This mixture was then added dropwise to a stirring polyvinyl alcohol emulsifier solution. After 15 min. the diamine/triamine monomer diluted with water was added to initiate the polymerisation. Few drops of NaOH solution was added, which acts as acid scavenger and neutralises the liberated HCl. The reaction was complete within 4 to 5 h. After completion of reaction the microcapsules were filtered, washed with water and freeze dried. The optical and SEM micrographs (Fig. 5) show clearly the presence of material inside the microcapsules as well as the formation of spherical microcapsules respectively. In addition to carrying out the microencapsulation of various materials inside polyamide microcapsules, hollow polyamide microcapsules were also synthesized by using the same technique of interfacial polymerisation¹⁴⁴.

9. CONCLUSIONS

The research in the area of microencapsulation has huge potential to give raw materials advantageous traits resulting in superior products. Periodically new developments in this area have led to new products, e.g. the first remarkable product was carbonless copy paper, the second was controlled release of drugs. At present, paper-like displays, self-healing structures and chemical decontaminating fabrics are receiving much attention.

REFERENCES

1. Mars, G. J. & Scher, H. B. Controlled delivery of crop protecting agents, Wilkens, R.M. (Ed.) Taylor and Francis, London. 1990, 65-90.
2. Green, B. K. & Schleicher, L. The National Cash Register Company, Dayton, Ohio. Oil containing microscopic capsules and method of making them. US Patent 2,800,457. 23 July 1957, 11.
3. Green, B.K. The National Cash Register Company, Dayton, Ohio. Oil containing microscopic capsules and method of making them. US Patent 2,800,458. 23 July 1957, 7.
4. Ferguson, J.L. Polymer encapsulated nematic liquid crystals for display and light control applications. SID Int. Symp. Digest, 1985, **16**, 68-70.
5. Zhang, M.Q.; Yin, T.; Rong, M.Z. & Yang, G.C. Self-healing epoxy composites—preparation and effect of the healant consisting of microencapsulated epoxy and latent curing agent. *Composites Sci. Technol.*, 2007, **67**(2), 201-12.

6. Sanada, K.; Yasuda, I. & Shindo, Y. Transverse tensile strength of unidirectional fibre-reinforced polymers and self-healing of interfacial debonding. *Plastics, Rubber Composites*, 2007, **35**(2), 67-72.
7. Jones, A.S.; Rule, J. D.; Moore, J. S.; Sottos, N. R. & White, S. R. Life extension of self-healing polymers with rapidly growing fatigue cracks. *J. R. Soc. Interface*, 2007, **4**(13), 395-403.
8. Brown, E. N.; White, S. R. & Sottos, N. R. Retardation and repair of fatigue cracks in a microcapsule toughened epoxy composite-Part II: *In situ* self-healing. *Composites Sci. Technol.*, 2005, **65**(15-16), 2474-80.
9. Rule, J. D.; Sottos, N. R. & White, S. R. Effect of microcapsule size on the performance of self-healing polymers. *Polymer*, 2007, **48**(12) 3520-29.
10. Kessler, M. R.; White, S. R. & Sottos, N. R. Self-healing structural composite materials. *Composites Part A: Appl. Sci. Manuf.*, 2003, **34**(8), 743-53.
11. Cowsar, D. R. The United States of America as represented by the Secretary of the Army, Washington, D. C. Novel Fabric containing microcapsules of chemical decontaminants encapsulated within semipermeable polymers. US Patent 4,201,822. 6 May 1980. 6.
12. Gutcho, M. M.(Ed). *Microcapsules and microencapsulation Techniques*, Noyes Data Co., New Jersey, USA. 1976.
13. Arshady, R. (Ed). *Microspheres, microcapsules and liposomes*, Citrus Books, London, United Kingdom. 1999.
14. Dziezak, J. D. Microencapsulation and encapsulated ingredients. *Food Technology*, 1988, **42**(4), 136-51.
15. Jackson, L. S. & Lee, K. Microencapsulation and encapsulated ingredients. *Lebensmittel Wissenschaft Technol.*, 1991, **24**, 289-97.
16. Shahidi, F. & Han, X.Q. Encapsulation of food ingredients. *Crit. Rev. Food Sci. Nutr.*, 1993, **33**, 501-47.
17. Scher, H. B. *In Proceedings of the 5th International Congress of Pesticides Chemistry*, edited by Miyamoto, J. & Kearney, P.C. Pergamon Press, Oxford. 1982. pp 295-300.
18. Schnoring, H.; Dahm, M. & Pampus, G. Fed. Rep. of Germany, Process for the Production of Microcapsules. US Patent 4,379,071. 5 April 1983. 9pp.
19. Kielbania, A.J.; Emmons, W.D. & Redlich, G.H. Rohm and Haas Company, Philadelphia. Process for Microencapsulation. US Patent 5,225,278. 6 July 1993. 11 pp.
20. Nastke, R. & Neuenschwander, E. Novartis Corporation, Summit, N.J. Process for the preparation of spherical microparticles containing biologically active compounds. US Patent 5, 908,632. 1 June 1999. 5 pp.
21. Redding, B.K. Apparatus and Method for Making Microcapsules US Patent 4,978,483. 18 December 1990. 26 pp.
22. Beestman, G.B. & Deming, J.M. Monsanto Company. Encapsulation by interfacial polycondensation, and aqueous herbicidal composition containing microcapsules produced thereby. US Patent 4,280,833. 28 July 1981. 11pp.
23. Nagano, H.; Hodosawa, Y. & Saitoh, H. Fuji. Photo. Film Co. Ltd. Kamagawa, Japan. Method of continuous production of microcapsules. US Patent 5,401,443. 28 March 1995. 7pp.
24. Luckham, P.F. Microencapsulation technique of formation and characterisation, *In Controlled Particle, Droplet and Bubble Formation*, edited by Wedlock, D.J. Butterworth Heinemann, Oxford. 1994.
25. Sanchez, L.; Sanchez, P.; De-Lucas, A.; Carmona, M. & Rodriguez, J. F. Microencapsulation of phase change materials with a polystyrene shell. *Colloid Polym. Sci.*, 2007, **285**(12), 1377-85.
26. Supsakulchai, A.; Ma, G. H.; Nagai, M. & Omi, S. Preparation of uniform titanium dioxide (TiO₂) polystyrene based composite particles using the glass membrane emulsification process with a subsequent suspension polymerization. *J. Microencapsulation.*, 2003, **20**(1), 1-18.
27. Damge, C.; Vranckx, H.; Balschmidt, P. & Couvreur, P. Poly (alkyl cyanoacrylate) nanospheres for oral administration of Insulin. *J. Pharm. Sci.* 1997, **86**(12), 1403-09.
28. Tiarks, F.; Landfester, K. & Antonietti, M. Preparation of Polymeric Nanocapsules by Miniemulsion Polymerization. *Langmuir*, 2001, **17**, 908-18.
29. Horak, D.; Semenyuk, N. & Lednicky, F. Effect of the reaction parameters on the particle size in the dispersion polymerization of 2-hydroxyethyl and glycidyl methacrylate in the presence of a ferrofluid. *J. Polym. Sci. Part A Polym. Chem.*, 2003, **41**, 1848-63.
30. Melamed, O. & Margel, S. Poly(N-vinyl α -phenylalanine) Microspheres: synthesis, characterization, and use for immobilization and microencapsulation. *J. Colloid Interface Sci.*, 2001, **241**(2), 357-65.
31. Janssen, J. M. & Nijenhuis, K. Encapsulation by interfacial polymerization I. The capsule production and a model for wall growth. *J. Membr. Sci.*, 1992, **65**, 59-68.
32. Janssen, J. M. & Nijenhuis, K. Encapsulation by interfacial polycondensation II. The membrane wall structure and the rate of the wall growth. *J. Membrane. Sci.*, 1992, **65**, 69-75.
33. Janssen, J. M.; Boersma, A. & Nijenhuis, K. Encapsulation by interfacial polycondensation III. Microencapsulation The influence of process conditions on wall permeability. *J. Membr. Sci.*, 1993, **79**, 11-26.
34. Morgan, P. W. Interfacial Polymerization *In Encyclopedia of Polymer Science and Engineering*, edited by Mark, H. F. John Wiley, New York. 1987, **8**, 221-37.
35. Desavigny, C. B. Pennwalt Corporation, Philadelphia. Microencapsulated methyl and Ethyl Parathion Insecticide in Aqueous Carrier. US Patent 3,959,464. 25 May 1976. 5pp.
36. Alexandridou, S.; Kiparissides, C.; Fransær, J. & Celis, J.P. On the synthesis of oil containing microcapsules and their electrolytic codeposition. *Surf. Coat. Technol.*, 1995, **71**, 267-76.

37. Argillier, J.F.; Soto-Portas, M.L.; Zydowicz, N.; Mechin, F. & Chomard A. Institut Francais du Petrole. Process for manufacturing microcapsules by interfacial polycondensation with polyoxyalkyleneamine and acid chlorides. US Patent 6,706,397. 16 March 2004. 6pp.
38. Chao, D.Y. The role of surfactants in synthesizing polyurea microcapsules. *J. Appl. Polym. Sci.*, 1993, **47**, 645-51.
39. Ley, S.V.; Ramarao, C.; Lee, A.L.; Ostergaard, N.; Smith, S.C. & Shirley, I.M. Microencapsulation of osmium tetroxide in polyurea. *organic letters*, 2003, **5**(2), 185-87.
40. Ley, S. V.; Ramarao, C.; Gordon, R. S.; Holmes, A.B.; Morrison, A. J.; McConvey, I. F.; Shirley, I. M.; Smith, S. C. & Smith, M. D. Polyurea encapsulated palladium (II) acetate: a robust and recyclable catalyst for use in conventional and supercritical media. *Chem. Commun.*, 2002, 1134-35.
41. Jabbari, E. Characterization of microcapsules prepared by interfacial polycondensation of methylene bis (Phenyl isocyanate) with hexamethylene diamine. *Iran. Polym. J.*, 2001, **10**(1), 33-43.
42. Shukla, P. G.; Sivaram, S. & Rajagopalan, N. Council of Scientific and Industrial Research, New Delhi, India. Process for the preparation of polyurethane microcapsules containing monocrotophos. US Patent 5,962,003. 5 October 1999. 5pp.
43. Frere, Y.; Danicher, L. & Gramain, P. Preparation of polyurethane microcapsules by Interfacial Polycondensation. *Eur. Polym. J.*, 1998, **34**(2), 193-99.
44. Ohtsubo, T.; Tsuda, S. & Tsuji, K. A Study of the physical strength of fenitrothion microcapsules. *Polymer*, 1991, **32**(13), 2395-99.
45. Ramanathan, L. S.; Shukla, P. G. & Sivaram, S. Synthesis and Characterization of Polyurethane Microspheres. *Pure Appl. Chem.*, 1998, **70**(6), 1295-99.
46. Luteri, G. F. Sandoz Ltd. Switzerland. Microencapsulated agricultural chemicals. US Patent 5,883,046. 16 March 1999. 6pp.
47. Wang, H.T.; Schmitt, E.; Flanagan, D.R. & Linhardt, R.L. Influence of formulation methods on the *in vitro* controlled release of protein from poly(ester) microspheres. *J. Controlled Release*, 1991, **17**, 23-32.
48. Persico, P.; Carfagna, C.; Danicher, L. & Frere, Y. Polyamide microcapsules containing jojoba oil prepared by interfacial polymerization. *J. Microencap.*, 2005, **22**(5), 471-86.
49. Zhang, M.; Ni, P. & Yan, N. Effect of operation variables and monomers on the properties of polyamide microcapsules. *J. Microencap.*, 1995, **12**(4), 425-32.
50. Arshady, R. Microspheres and microcapsules: A Survey of manufacturing techniques Part I Suspension crosslinking. *Polym. Eng. Sci.*, 1989, **29**(24), 1746-58.
51. Katti, D. & Krishnamurti, N. Preparation of albumin microspheres by an improved process. *J. Microencap.*, 1999, **16**(2), 231-42.
52. Widder, J. K.; Senyei, A. E. & Sears, B. Experimental methods in cancer therapeutics. *J. Pharm. Sci.*, 1982, **71**(4), 379-87.
53. Yamakawa, I.; Tsushima, Y.; Machida, R. & Watanabe, R. Preparation of neurotensin analogue containing Poly (DL-lactic acid) Microsphere formed by oil in water solvent evaporation. *J. Pharm. Sci.*, 1992, **81**, 899-903.
54. Arshady, R. Microspheres and microcapsules: A Survey of manufacturing techniques Part III Solvent evaporation. *Polym. Eng. Sci.*, 1990, **30**, 915-24.
55. Hausberger, A. G. & Deluca, P. P. Characterization of biodegradable poly (D,L- lactide-co-glycolide) polymers and microspheres. *J. Pharmaceut. Biomed. Anal.*, 1995, **13**(6), 747-60.
56. Yang, Y. Y.; Chung, T. S. & Ngee, N. P. Morphology, drug distribution, and *in vitro* release profiles of biodegradable polymeric microspheres containing protein fabricated by double emulsion solvent extraction/evaporation method. *Biomaterials*, 2001, **22**, 231-41.
57. Yang, Y.Y.; Chia, H.H. & Chung, T.S. Effect of preparation temperature on the characteristics and release profiles of PLGA microspheres containing protein fabricated by double emulsion solvent extraction/evaporation method. *J. Controlled Release*, 2000, **69**, 81-96.
58. Ogawa, Y.; Yamamoto, M; Okada, H; Yashiki, T. & Shimamoto, T. A new technique to efficiently entrap leuprolide acetate into microcapsules of polylactic acid or copoly (lactic/glycolic) acid. *Chem. Pharm. Bull.*, 1988, **36**, 1095-103.
59. Jeffery, H.; Davis, S. S. & Ohagan, D. T. The preparation and characterization of poly (lactide-co-glycolide) microparticles. II The entrapment of a model protein using a (water-in-oil)-in-water emulsion solvent evaporation technique. *Pharm. Res.*, 1993, **10**, 362-68.
60. Bodmerier, R. & McGinity, J. W. Polylactic acid microspheres containing quinidine base and quinidine sulphate prepared by the solvent evaporation techniques. *J. Microencap.*, 1987, **4**, 279-86.
61. Gursel, I. & Hasirci, V. Properties and drug release behavior of poly (3-hydroxybutyric acid) and various Poly(3-hydroxybutyrate-hydroxyvalerate) Copolymer Microcapsules. *J. Microencap*, 1995, **12**, 185-93.
62. Arshady, R. Microspheres and microcapsules: A survey of manufacturing techniques Part II Coacervation. *Polym. Eng. Sci.*, 1990, **30**(15), 905-14.
63. Burgess, D. J. & Carless, J. F. Manufacture of gelatin/gelatin coacervate microcapsules. *Int. J. Pharma.*, 1985, **27**, 61-70.
64. Okoda, J.; Kusai, A. & Ueda, S. Factors affecting microencapsulability in simple gelatin coacervation method. *J. Microencap.*, 1985, **2**(3), 163-73.
65. Takenaka, H.; Kamashima, Y. & Lin, S. Y. Micromeritic properties of sulfamethoxazole microcapsules prepared by gelatin-acacia coacervation. *J. Pharm. Sci.*, 1980, **69**(5), 513-16.
66. Nimmannit, U. & Suwanpatra, N. Microencapsulation

- of drugs by the coacervation technique using ethyl cellulose and acrylate methacrylate copolymer as wall materials. *J. Microencap.*, 1996, **13**(6), 643-49.
67. Re, M.I. Microencapsulation by spray drying. *Drying Technology*, 1998, **16**(6), 1195-236.
 68. Mulqueen, P.J.; Smith, G & Lubetkin, S.D. Microencapsulation process and product. Dow Agrosiences, Indianapolis. US Patent 5,925,464. 20 July 1999. 9pp.
 69. Gharsallaoui, A.; Roudaut, G; Chambin, O; Voilley, A & Saurel, R. Applications of spray drying in microencapsulation of food ingredients: An overview. *Food Res. Int.*, 2007, **40**(9), 1107-121.
 70. Shu, B.; Yu, W.; Zhao, Y. & Liu, X. Study of microencapsulation of lycopene by spray drying. *J. Food Eng.*, 2006, **76**(4), 664-69.
 71. Dewettinck, K. & Huyghebaert, A. Fluidized bed coating in food technology. *Trends in Food Sci. and Technol.*, 1999, **10**, 163-68.
 72. Knezevic, Z.; Gosak, D.; Hraste, M. & Jalsenjako, I. Fluid bed microencapsulation of ascorbic acid. *J. Microencap.*, 1998, **15**(2), 237-52.
 73. Fukumori, C.; Fukuda, Y. T.; Hanyu, Y.; Takeyuchi, Y. & Oruko, Y. Coating of pharmaceutical powders by fluidized bed process I. Aqueous enteric coating with methacrylic acid-ethylacrylate copolymer and the dissolution behaviour of products (pharmaceutical). *Chem. Pharm. Bull.*, 1987, **35**(7), 2949-957.
 74. Mathowitz, E. & Langer R. Polyanhydride microspheres as drug carriers I. Hot melt microencapsulation. *J. Controlled Release*, 1987, **5**(1), 13-22.
 75. Banerjee, S.; Premchandran, R.; Tata, M.; John, V. T.; Mcpherson, G. L.; Akkara, J. & Kaplan, D. Polymer precipitation using a micellar nonsolvent : The role of surfactant polymer interactions and the development of a microencapsulation technique. *Ind. & Eng. Chem. Res.*, 1996, **35**(9), 3100-107.
 76. Aebischer, P.; Wahlberg, L.; Tresco, P. A. & Winn S. R. Macroencapsulation of dopamine secreting cells by co-extrusion with an organic polymer solution, *Biomaterials.*, 1991, **12**, 50-56.
 76. Aebischer, P.; Wahlberg, L.; Tresco, P. A. & Winn S. R. Macroencapsulation of dopamine secreting cells by co-extrusion with an organic polymer solution, *Biomaterials.*, 1991, **12**, 50-56.
 77. Honiger, J.; Sarkis, R.; Baudrimont, M.; Delelo, R.; Chafai, N.; Benoist, S.; Sarkis, K. & Nordlinger, B. Semiautomatic macroencapsulation of large number of porcine hepatocytes by co-extrusion with a solution of AN 69 polymer. *Biomaterials*, 2000, **21**(12), 1269-274.
 78. Trau, D. & Renneberg, R. Encapsulation of glucose oxidase microparticles within a nanoscale layer by layer film: immobilization and biosensor applications. *Biosens. Bioelectron.*, 2003, **18**, 1491-499.
 79. Caruso, F.; Yang, W.; Trau, D. & Renneberg, R. Microencapsulation of uncharged low molecular weight organic materials by polyelectrolyte multilayer self assembly. *Langmuir*, 2000, **16**(23), 8932-936.
 80. Krober, H. & Teipel, U. Microencapsulation of particles using supercritical CO₂. *Chem. Eng. Processing.*, 2005, **44**(2), 215-19.
 81. Chiou, A. H.; Cheng, H. C. & Wang, D. P. Micronization and microencapsulation of felodipine by supercritical CO₂. *J. Microencap.*, 2006, **23**(3) 265-76.
 82. Cochrum, K. C. & Davis The reguents of the university of California, Oakland, California. Spin disk encapsulation apparatus and method of use. US Patent 6,001,387. 14 Dec 1999. 22pp.
 83. Teunou, E. & Poncelet, D. Rotary disc atomization for microencapsulation applications—prediction of the particle trajectories. *J. Food Eng.* 2005, **71**(4), 345-53.
 84. Arshady, R. Biodegradable microcapsular drug delivery systems: Manufacturing methodology, release control and targeting prospects. *J. Bioactive Compatible Polym.*, 1990, **5**, 315-42.
 85. Gould, P. Self help for ailing structures, *Mater. Today*, June 2003, 44-49.
 86. Lin, S.Y.; Ho, L.T. & Chiou, H.L. Microencapsulation and controlled release of insulin from polylactic acid microcapsules. *Biomater. Med. Devices Artif. Organs.*, 1985-1986, **13**(3-4), 187-201.
 87. Scher, H. B.; Rodson, M & Lee, K. S. Microencapsulation of pesticides by interfacial polymerization utilizing isocyanate or aminoplast chemistry. *Pestic. Sci.*, 1998, **54**, 394-400.
 88. Scher, H. B.; Groenwold, B. E., Pereiro, F. & Purnell, T. J. Microencapsulated thiocarbamate herbicides. *In Proc. Brit. Crop. Prot. Conf. Weeds*, 1980, pp 185-91.
 89. Scher, H. B. Development of herbicide and insecticide microcapsule formulations. *In Proc. Internat. Symp. Control Rel. Bioact. Mater.* 1985, 110-11.
 90. Bingham, G.; Gunning, R.V.; Gorman, K.; Field, L.M. & Moores, G.D. Temporal synergism by microencapsulation of piperonyl butoxide and-cypermethrin overcomes insecticide resistance in crop pests. *Pest Mgmt. Science*, 2007, **63**, 276-81.
 91. Ilichev, A.L.; Stelinski, L.L.; Williams, D.G. & Gut, L.J. Sprayable microencapsulated sex pheromone formulation for mating disruption of oriental fruit moth(Lepidoptera: Tortricidae) in Australian peach and pear orchards. *J. Econ. Entomol.*, 2006, **99**(6), 2048-054.
 92. Mihou, A. P. ; Michaelakis, A. ; Krokos, F. D.; Majomenos, B. E. & Couladouros, E. A. Prolonged slow release of (Z)-11-hexadecenyl acetate employing polyurea microcapsules. *J. Appl. Entomol.*, 2007, **131**(2), 128-33.
 93. Zengliang, C.; Yuling, F. & Zhongning, Z. Synthesis and assessment of attractiveness and mating disruption efficacy of sex pheromone microcapsules for the diamondback moth, *Plutella Xylostella* (L). *Chinese Sci. Bull.*, 2007, **57**(10), 1365-71.
 94. Langer, R. New methods of Drug Delivery. *Science*, 1990, **249**, 1527-533.
 95. Menei, P.; Benoit, J.; Boisdron, C.M.; Fournier, D.;

- Mercier, P. & Guy, G. Drug targeting into the central nervous system by stereotactic implantation of biodegradable microspheres. *Neurosurgery*, 1994, **34**, 1058-064.
96. Camarata, P. J.; Suryanarayanan, R.; Turner, D. A.; Parker, R. G. & Ebner, T. J. Sustained release of nerve growth factor from biodegradable polymer microspheres. *Neurosurgery*, 1992, **30**, 313-19.
 97. Boury, H.; Marchais, H.; Proust, J. P. & Benoit, J. P. Bovine Serum albumin release from poly(-hydroxy acid) microspheres: Effects of polymer molecular weight and surface properties. *J. Control. Release*. 1997, **45**, 75-86.
 98. Siegel, R. A. Controlled release of Drugs: polymers and aggregate systems, edited by Rosof, M. VCH Publishers Inc. New York, 1989, pp1-49.
 99. Baran, E. T.; Ozer, N. & Hasircil, V. Poly(hydroxybutyrate-co-hydroxyvalerate) nanocapsules enzyme carriers for cancer therapy: An *in vitro* study. *J. Microencap.*, 2002, **19**, 363-76.
 101. Das, M. K. & Rao, K. R. Microencapsulation of Zidovudine by double emulsion solvent diffusion technique using ethylcellulose. *Indian J. Pharm. Sci.*, March- April 2007, 244-50.
 102. Suttiruengwong, S.; Rolker, J.; Smirnova, I.; Arlt, W.; Seiler, M. Luderitz, L.; Perez de Diego, Y. & Jansens, P.J. Hyperbranched polymers as drug carriers: Microencapsulation and release kinetics. *Pharm. Dev. Technol.*, 2006, **11**, 55-70.
 103. Chowdary, K.P.R.; Mohapatra, P. & Murali Krishna M.N. Evaluation of olibanum resin as microencapsulating agent for controlled drug delivery. *Indian J. Pharm. Sci.*, 2006, **68**, 461-64.
 104. Naha, P.C.; Kanchan, V.; Manna, P.K. & Panda, A.K. Improved bioavailability of orally delivered insulin using Eudragit-L 30D coated PLGA microparticles. *J. Microencap.*, 2008, **25**(4), 248-56.
 105. Kim, C. H.; Kwon, J. H. & Choi, S. H. Mi Tech Company Limited, Seoul, Korea. Controlled Release preparation of Insulin and its method. US Patent 7,087,246 B2. 8 Aug 2006. 22pp.
 106. Jones, D.H.; Farrar, G.H. & Stephen, J.C. Microbiological Research Authority (GB). Method of making microencapsulated DNA for vaccination and Gene Therapy. US Patent 6,270,795. 7 Aug 2001. 23pp.
 107. Chang, P.L. Microencapsulation—An alternative approach to gene therapy. *Transf. Apheresis Sci.*, 1996, **17**(1), 35-43.
 108. Aihua, L.A.; Feng, S.; Tao, Z.; Pasquale, C.; Murray, P. & Patricia, C. Enhancement of myoblast microencapsulation for gene therapy. *J. Biomed. Mater. Res. Pt B Appl. Biomater*, 2006, **77**(2), 296-306.
 109. Ross, C. J. D.; Ralph, M. & Chang, P. L. Somatic gene therapy for a neurodegenerative disease using microencapsulated recombinant cells. *Exp. Neurol.*, 2000, **166**(2), 276-86.
 110. McMahon, J.; Schmid, S.; Weislow, O.; Stinson, S.; Camalier, R.; Gulakowski, R.; Shoemaker, R.; Kiser, R.; Harrison, S.; Mayo, J & Boyd, M. Feasibility of cellular microencapsulation technology for evaluation of anti-human immunodeficiency virus *in vivo*. *J. Nat. Cancer Inst.*, 1990, **82**(22), 1761-765.
 111. Cleland, J. L.; Powell, M. F.; Lim, A.; Barron, L.; Berman, P. W.; Eastman, D. J.; Nunberg, J. H.; Wrinn, T. & Vennari, J. C. Development of a single shot subunit vaccine for HIV-1. *AIDS-Res-Hum-Retroviruses.*, 1994, **10** (2), S21-6.
 112. Marx, P. A.; Compans, R. W.; Gettie, A.; Staas, J. K.; Gilley, R. M.; Mulligan, M. J.; Yamshchikov, G. V.; Chen, D. & Eldridge, J. H. Protection against vaginal SIV transmission with microencapsulated vaccine. *Science*, 1993, **260**(5112) 1323-327.
 113. Hao, S.; Su, L.; Guo, X.; Moyana, T. & Xiang, J. A novel approach to tumor suppression using microencapsulated engineered J558/TNF- α cells. *Exp. Oncol.*, 2005, **27**(1), 56-60.
 114. Zhang, Y.; Wang, W.; Zhou, J.; Yu, W.; Zhang, X.; Guo, X. & Ma, X. Tumor anti-angiogenic gene therapy with microencapsulated recombinant CHO cells. *Ann. Biomed. Eng.*, 2007, **35**(4), 605-14.
 115. Drone, P.; Bourgeois, J. M. & Chang, P. L. Antiangiogenic cancer therapy with microencapsulated cells. *Human Gene Therapy*, 2003, **14**(11), 1065-077.
 116. Maria-Engler, S. S.; Correa, M. L. C.; Oliveira, E. M. C.; Genzini, T.; Miranda, M. P.; Vilela, L. & Sogayar, M. C. Microencapsulation and tissue engineering as an alternative treatment of diabetes. *Brazilian J. Med. Biol Res*, 2001, **34**(6), 691-97.
 117. Sambanis, A. Encapsulated islets in diabetes treatment. *Diab. Technol. Therapeut.*, 2003, **5**(4), 665-68.
 118. Kizilel, S.; Wyman, J. L.; Mrksich, M.; Nagel, S. R. & Garfinkel, M. R. Brinks Hofer Gilson and Lione, Chicago (US), US Patent 2007/0190036 A1. 16 Aug 2007. 10pp.
 119. Kim, H.K. & Park, T.W. Microencapsulation of human growth hormone within biodegradable polyester microspheres: Protein aggregation stability and incomplete release mechanism. *Biotechnol. Bioeng.*, 1999, **65**(6), 659-67.
 120. Kim, H.K. & Park, T.G. Microencapsulation of dissociable human growth hormone aggregates within poly(D, L-lactic-co-glycolic acid) microparticles for sustained release. *Int. J. Pharmaceut.*, 2001, **229**(1-2), 107-16.
 121. Morlock, M.; Koll, H.; Winter, G. & Kissel, T. Microencapsulation of rh-erythropoietin, using biodegradable poly(d,l-lactide-co-glycolide): protein stability and the effects of stabilizing excipients. *Eur. J. Pharmaceut. Biopharmaceut.*, 1997, **43**(1), 29-36.
 122. Morlock, M.; Kissela, T.; Lia, Y. X.; Kollb, H. & Winterb, G. Erythropoietin loaded microspheres prepared from biodegradable LPLG-PEO-LPLG triblock copolymers: protein stabilization and *in-vitro* release properties. *J. Controlled Release*, 1998, **56**(1-3), 105-15.

123. Garcia del Barrio, G.; Novo, F. J. & Irache, J. M. Loading of plasmid DNA into PLGA microparticles using TROMS (Total Recirculation One-Machine System): evaluation of its integrity and controlled release properties. *J. Controlled Release*, 2003, **86**(1), 123-30.
124. Santini, B.; Antonelli, M.; Battistini, A.; Bertasi, S.; Collura, M.; Esposito, I.; Di Febbraro, L.; Ferrari, R.; Ferrero, L.; Iapichino, L.; Lucidi, V.; Manca, A.; Pisconti, C.L.; Pisi, G.; Raia, V.; Romano, L.; Rosati, P.; Grazioli, I. & Melzi, G. Comparison of two enteric coated microsphere preparations in the treatment of pancreatic exocrine insufficiency caused by cystic fibrosis. *Digestive Liver Disease*, 2000, **32**(5), 406-11.
125. Elliott, R.B.; Escobar, L.C.; Lees, H.R.; Akroyd, R.M. & Reilly, H.C. A comparison of two pancreatin microsphere preparations in cystic fibrosis. *The New Zealand Med. J.*, 1992, **105**(930), 107-8.
126. Liu, H. W.; Ofosu, F. A. & Chang, P. L. Expression of human growth factor IX by microencapsulated recombinant fibroblasts. *Human Gene Therapy*, 1993, **4**(3), 291-301.
127. Turner S. J. Microscopic spheres produced at brown may revolutionize oral drug delivery [assessed on 2 June 2008] Website: <http://www.brown.edu/>
128. Kirby, C. J.; Whittle, C. J.; Rigby, N.; Coxon, D. T. & Law, B. A. Stabilization of ascorbic acid by microencapsulation in liposomes. *Int. J. Food Sci. Technol.*, 1991, **26**, 437-49.
129. Pothakamury, U. R. & Barbosa-Canovas, G. V. Fundamental aspects of controlled release in Foods. *Trends Food Sci. Technol.*, 1995, **6**, 397-406.
130. Wagner, L. A. & Warthesen, J. J. Stability of spray dried encapsulated carrot carotenes. *J. Food Sci.*, 1995, **60**, 1048-053.
131. Schrooyen, P. M. M.; Meer, R. V. D. & Kruif, C. G. D. Microencapsulation: Its application in nutrition. *Proc. Nutr. Soc.*, 2001, **60**, 475-79.
132. Gibbs, B. F.; Kermasha, S.; Alli, I. & Mulligan, C. N. Encapsulation in the food industry: A Review. *Int. J. Food Sci. Nutr.*, 1999, **50**, 213-24.
133. Chiu, Y. T.; Chiu, C. P.; Chien, J. T.; Ho, G. H.; Yang, J. & Chen, B. H. Encapsulation of Lycopene extract from tomato pulp waste with gelatin and poly(-glutamic acid) as carrier. *J. Agric. Food Chem.*, 2007, **55**(13), 5123-130.
134. Vasistha, N. Microencapsulation: delivering a market advantage-food ingredients-cover story [assessed on 2 June 2008] website: <http://findarticles.com/p/articles/>
135. Mishra, K. K.; Khardekar, R. K.; Singh, R. & Pant, H. C. Fabrication of polystyrene hollow microspheres as laser fusion targets by optimized density matched emulsion technique and characterization. *Pramana, Journal of Physics*, 2002, **59**(1), 113-31.
136. Brown, E. N.; White, S. R. & Sottos, N. R. Microcapsule induced toughening in a self-healing polymer composite. *J. Mater. Sci.*, 2004, **39**, 1703-710.
137. Li, Y.; Guozheng, L.; Jianqiang, X.; Lan, Li. & Jing, G. Preparation and characterization of poly(urea-formaldehyde) microcapsules filled with epoxy resins. *Polymer*, 2006, **47**(15), 5338-349.
138. Toohey, K. S.; Sottos, N. R.; Lewis, J. A.; Moore, J. S. & White S. R. Self-healing materials with microvascular networks. *Nature Materials* 2007, **6**(8), 581-85.
139. White, S. R.; Sottos, N. R.; Guebelle, P. H.; Moore, J. S.; Kessler, M. R.; Sriram, S. R. & Brown, E. N. Autonomic healing of polymer composites. *Nature*, 2001, **409**(6822), 794-97.
140. Yuan, L.; Liang, G. Z.; Xie, J. Q.; Li, L. & Guo, J. The permeability and stability of microencapsulated epoxy resins. *J. Mater. Sci.*, 2007, **42**(12), 4390-397.
141. Yuan, L.; Liang, G. Z.; Xie, J. Q.; He, S. B. Synthesis and characterisation of microencapsulated dicyclopentadiene with melamine-formaldehyde resins. *Colloid Polym. Sci.*, 2007, **285**(7), 781-91.
142. Lee, J. K.; Liu, X. & Yoon, S. H. Characterization of diene monomers as self-healing agent for polymer composite and its microcapsules, *In Conference Proceedings, Society of Plastics Engineers, Annual Technical Conference 2005, ANTEC 2005*, **6**, 264-68.
143. Brown, E.N.; Kessler, M.R.; White, S.R. & Sottos, N.R. *In situ* poly(urea-formaldehyde) microencapsulation of dicyclopentadiene. *J. Microencap.*, 2003, **20**(6), 719-30.
144. Dubey, R.; Shami, T.C.; Bhasker Rao, K.U.; Yoon, H. & Varadan, V.K. Polyamide microcapsules: Effect of critical point drying on physical aspect, communicated to *Smart Mater. Structures*.

Contributors



Dr Rama Dubey is working as Sci C at the Defence Materials Stores Research and Development Establishment (DMSRDE) Kanpur. She obtained her MSc (Organic Chemistry) in 1990 and PhD (Applied Chemistry) in 2000 from Chatrapati Sahu Ji Maharaj (CSJM) University, Kanpur. She was deputed to Pennsylvania State University USA in 2002 and University of Arkansas USA in 2007 for training. Her area of interest is conducting polymers, microcapsules and microencapsulation, conducting and magnetic coating on different surfaces by electroless technique. She is at present involved in synthesis of conducting polymers having micro/nano dimensions, hollow polymeric microcapsules and microencapsulation of different materials inside microcapsules, coating of microcapsule surfaces with different types of conductive and magnetic materials, for development of radar absorbing coatings. She has 20 publications to her credit.



Mr Trilok Chand Shami is presently working as Scientist F in Defence Materials Stores Research and Development Establishment (DMSRDE) Kanpur. He obtained his MSc (Inorganic Chemistry) from Chaudhary Charan Singh University, Meerut and has submitted his PhD thesis at the same university in 2008. He is currently leading a team of 12 scientists

working in different areas. He has visited Pennsylvania State University, USA in 2002 and led his team of scientists to University of Arkansas, USA in 2007. He has successfully completed many projects in the areas of camouflage paint for broad band spectra and has 22 years of experience in this field. His areas of interest are: electromagnetic absorbing coatings/ composite, laser absorbing coatings and camouflage paint. He has more than 30 papers to his credit.



Dr K.U. Bhasker Rao obtained his MSc in Chemistry from Osmania University, Hyderabad and PhD in Explosives Chemistry from University of Pune, Pune. He joined DRDO at the High Energy Materials Research Laboratory, Pune in 1976. Dr. Rao took over as Director, DMSRDE, Kanpur in 2005, where, he is leading teams of scientists working on polymers, composites, CNTs and nanomaterials, textiles and camouflage systems. He has a number of publications in national and international journals to his credit. He is a member of Governing Council, High Energy Materials Society of India, Pune, Member of Indian Thermal Analysis Society, Mumbai and Aeronautical Society of India.